

Superconductivity coexisting with phase-separated static magnetic order in $(\text{Ba,K})\text{Fe}_2\text{As}_2$, $(\text{Sr,N a})\text{Fe}_2\text{As}_2$ and CaFe_2As_2

T. Goko,^{1,2,3} A. A. Aczel,³ E. Baggiot-Saitovitch,⁴ S. L. Bud'ko,⁵ P. C. Canfield,⁵ J. P. Carlo,² G. F. Chen,⁶ Pengcheng Dai,⁷ A. C. Hamann,⁸ W. Z. Hu,⁶ H. Kageyam a,⁹ G. M. Luke,³ J. L. Luo,⁶ B. Nachum i,² N. Ni,⁵ D. Reznik,⁸ D. R. Sanchez-Candela,⁴ A. T. Savici,¹⁰ K. J. Sikes,² N. L. Wang,⁶ C. R. Wiebe,¹¹ T. J. Williams,³ T. Yamamoto,⁹ W. Yu,³ and Y. J. Uemura²,

¹TRIUMF, 4004 Wesbrook Mall, Vancouver, B.C., V6T 2A3, Canada

²Department of Physics, Columbia University, New York, New York 10027, USA

³Department of Physics and Astronomy, McMaster University, Hamilton, Ontario L8S 4M1, Canada

⁴Centro Brasileiro de Pesquisas Físicas, Rua Xavier Sigaud 150 Urca, CEP 22290-180 Rio de Janeiro, Brazil

⁵Department of Physics and Astronomy and Ames Laboratory, Iowa State University, Ames, Iowa 50011, USA

⁶Beijing National Laboratory for Condensed Matter Physics, Institute of Physics, Chinese Academy of Sciences, Beijing 100080, Peoples Republic of China

⁷Department of Physics and Astronomy, University of Tennessee, Knoxville, Tennessee 37996, USA

⁸Forschungszentrum Karlsruhe, Institut für Festkörperphysik, Postfach 3640, D-76021 Karlsruhe, Germany

⁹Department of Chemistry, Kyoto University, Kyoto 606-8502, Japan

¹⁰Department of Physics and Astronomy, Johns Hopkins University, Baltimore, Maryland 21218, USA

¹¹Department of Physics, Florida State University, Tallahassee, Florida 32310, USA

(Dated: February 20, 2024)

The recent discovery and subsequent developments of FeAs-based superconductors have presented novel challenges and opportunities in the quest for superconducting mechanisms in correlated-electron systems. Central issues of ongoing studies include interplay between superconductivity and magnetism as well as the nature of the pairing symmetry reflected in the superconducting energy gap. In the cuprate and RE(O,F)FeAs (RE = rare earth) systems, the superconducting phase appears without being accompanied by static magnetic order, except for narrow phase-separated regions at the border of phase boundaries. By muon spin relaxation measurements on single crystal specimens, here we show that superconductivity in the AFe_2As_2 (A = Ca, Ba, Sr) systems, in both the cases of composition and pressure tunings, coexists with a strong static magnetic order in a partial volume fraction. The superfluid response from the remaining paramagnetic volume fraction of $(\text{Ba}_{0.5}\text{K}_{0.5})\text{Fe}_2\text{As}_2$ exhibits a nearly linear variation in T at low temperatures, suggesting an anisotropic energy gap with line nodes and/or multi-gap effects.

PACS numbers: 74.90.+n 74.25.Nf 75.25.+z 76.75.+i

The announcement of superconductivity in $\text{La}(\text{O,F})\text{FeAs}$ ($T_c = 26$ K) in February 2008 [1] triggered an unprecedented burst of research activities in FeAs-based superconductors and their parent systems. By now, superconductivity has been reported in systems with four different crystal structures, i.e., the "1111" systems RE(O,F)FeAs with Rare Earth = La, Nd, Ce, etc. [2], the "122" systems AFe_2As_2 (A = Ba, Sr, Ca) tuned by chemical substitutions [3] or application of hydrostatic pressure [4, 5], the "111" Li_xFeAs [6], and the "011" FeSe systems [7]. Extensive measurements by neutron scattering [8, 9, 10], Mössbauer effect [13, 14, 15] and muon spin relaxation (SR) [15, 16, 17, 18, 19] have been performed to characterize magnetism and superfluid responses. Notable results include the observations of collinear antiferromagnetic order in undoped parent compounds of the 1111 and 122 systems [8, 11, 12], hyperfine splitting of ^{57}Fe Mössbauer spectra and SR frequencies indicative of a static moment size ranging between 0.3 – 0.8 Bohr magnetons per Fe [13, 14, 19], static magnetism

in lightly-doped non-superconducting systems with possible incommensurate or stripe spin correlations [18], and nearly linear scaling between T_c and the superfluid density [16, 17, 18] in the 1111 systems following the trend found in cuprate and other exotic superconductors [20].

Three systematic studies of magnetic phase diagrams of the 1111 systems [9, 21, 22], however, exhibit significantly different behaviors. As a function of increasing (O,F) substitution, $\text{La}(\text{O,F})\text{FeAs}$ shows an abrupt and first-order like evolution from an antiferromagnetic to superconducting state, $\text{Ce}(\text{O,F})\text{FeAs}$ shows nearly second-order like evolution, and $\text{Sm}(\text{O,F})\text{FeAs}$ exhibits phase-separated coexistence of static magnetism and superconductivity in a small concentration region around the phase boundary. Despite these differences, superconductivity appears mostly in the region without static magnetic order in the 1111 systems, similarly to the case of the cuprates. In contrast, very little has been reported on the phase diagrams of the 122 systems. Recent powder neutron measurements on $(\text{Ba,K})\text{Fe}_2\text{As}_2$ [10] found a

phase diagram similar to the one for $\text{Sm}(\text{O},\text{F})\text{FeAs}$ with coexisting long-range magnetic order and superconductivity near the phase boundary. Due to the volume-integrated character of neutron intensity, however, information pertaining to the ordered volume fraction is missing in that work. We have also reported SR measurements on a single crystal of $(\text{Ba}_{0.55}\text{K}_{0.45})\text{Fe}_2\text{As}_2$ [19] which found the co-existence of phase-separated static magnetic order and superconductivity. However, the superfluid density of this crystal was much lower than that in the corresponding 1111 system with comparable T_c 's, which is suggestive of insufficient carrier doping. In the 122 systems, more definitive studies of magnetic phase diagrams can be expected due to the availability of large single crystals [23, 24, 25], recent improvement of the growth method, and applicability of pressure-tuning free from randomness due to substitution.

In this paper, we report muon spin relaxation (SR) measurements of superconducting single crystals of $(\text{Ba}_{0.5}\text{K}_{0.5})\text{Fe}_2\text{As}_2$ ($T_c = 37$ K) and $(\text{Sr}_{0.5}\text{Na}_{0.5})\text{Fe}_2\text{As}_2$ ($T_c = 35$ K) in ambient pressure, and of CaFe_2As_2 in ambient and applied pressure up to $p = 10$ kbar, performed at TRIUMF in Vancouver, Canada. The former two crystals, prepared at the Institute of Physics in Beijing using the FeAs flux method [25] and weighing 100 mg and 40 mg respectively, were mounted with their ab-planes perpendicular to the muon beam. Over 1 g of CaFe_2As_2 crystals (in more than 100 pieces), prepared in Ames Lab. using the Sn flux method [24], were mounted in a pressure cell having a sample space of 7 mm in diameter and 10–15 mm long. The crystals were aligned with their ab-planes perpendicular to the muon beam at the M9B channel, where the initial muon spin polarization is tuned to be perpendicular to the beam direction. SR measurements were performed in zero field (ZF) and weak transverse field (WTF) of 30–50 G to study magnetic ordering, and in transverse field (TF) of 300–500 G to study superfluid density. A recent study on $(\text{Ca},\text{Sr})\text{RuO}_3$ and MnSi in applied pressure [29] has demonstrated SR's unique capability of determining volume fractions of regions with and without static magnetic order in systems having phase separation. Details of the SR methods and pressure measurement techniques can be found in refs. [26, 27, 28] and the on-line Supplementary Documents A and B.

Figure 1 shows (a) the muon spin precession frequencies observed in ZF-SR and (b) the paramagnetic volume fraction derived from WTF-SR measurements in the (Ba,K) and (Sr,Na) crystals. The solid lines show the reported results in the undoped parent compounds BaFe_2As_2 [19] and SrFe_2As_2 [14]. In both systems, static magnetism sets in at temperatures well above the superconducting T_c 's, in a large volume fraction of 90% in the (Sr,Na) system and 50% in the (Ba,K) system. We observed two different precession frequencies in a given system, presumably coming from two different

muon sites, as was the case in BaFe_2As_2 [19]. The frequencies in the superconducting samples are reduced from the values in the undoped compounds only by 20–30%, indicating that static magnetic order with a significant Fe moment size exists in the magnetically-ordered regions. These results demonstrate phase separation between magnetically-ordered and paramagnetic volumes. However, it is difficult to estimate the length scale of each region from the SR results alone.

In TF-SR, the precession signal from the paramagnetic volume fraction exhibits damping below T_c due to an inhomogeneous field distribution in the flux vortex lattice. The relaxation rate, obtained by fitting the spectra to a Gaussian function $\exp(-t^2/\tau^2)$, is given by $1/\tau^2 = \mu_0^2 H_c^2 / n_s \lambda^2$, where λ is the penetration depth, n_s is the superconducting carrier density, and m is the effective mass [26, 27, 28]. An increase of λ was observed in both the (Ba,K) and (Sr,Na) crystals below the superconducting T_c 's. Since the statistical accuracy of the data is much better for the former system with the larger paramagnetic volume fraction, here we present the results of $(\text{Ba}_{0.5}\text{K}_{0.5})\text{Fe}_2\text{As}_2$ in TF = 500 G applied parallel to the c-axis in Fig. 2 (a) and (b). The temperature dependence of λ in (a) is nearly linear with T , as demonstrated by the good agreement with the scaled data from a YBCO system [26]. The observed behavior is distinctly different from the case for an isotropic energy gap shown by the broken line representing a calculation for BCS s-wave coupling. The observed temperature dependence may be attributed to (1) line nodes in an anisotropic energy gap, or (2) widely different magnitudes of multiple isotropic gaps as seen in calculations [30, 31] based on multiple bands. An ARPES measurement [32] on $(\text{Ba},\text{K})\text{Fe}_2\text{As}_2$ reported evidence for multiple gaps.

The absolute value of $\lambda(T \rightarrow 0)$ is about a factor of 3 larger than that observed in $(\text{Ba}_{0.55}\text{K}_{0.45})\text{Fe}_2\text{As}_2$ in our previous measurements [19]. Given that H_{c2} anisotropy is relatively low near T_c , between 3.5 and 2.5 for $H < 14$ T [23], and decreases for higher fields [3], we plot the present results in the $\lambda(T \rightarrow 0)$ versus T_c plot of Fig. 2 (b) without corrections for single-crystal to polycrystal conversion [34]. The resulting point from the present (Ba,K) crystal (red solid square symbol) indicates that the present system has a superfluid density close to those in the 1111 systems with comparable T_c 's, and that a sufficiently doped 122 FeAs system follows the nearly linear relationship between T_c and n_s/m found in the cuprates and 1111 systems. This result disagrees with the H_{c1} measurements on $(\text{Ba},\text{K})\text{Fe}_2\text{As}_2$ [31] which found the superfluid density to have a similar temperature dependence to our results, but the absolute values differed by a factor of 4. As experienced in early studies on various cuprate systems which reported widely scattered values of H_{c1} , the determination of H_{c1} can be affected by flux pinning. This feature might explain the origin of the disagreement.

The superconducting state can also be obtained by applying hydrostatic pressure to the undoped parent compounds of the 122 systems [4, 5]. In particular, the CaFe_2As_2 system shows superconductivity below $T = 10$ K at relatively low pressures p of 3–8 kbar, which are attainable using the available SR piston-cylinder pressure cell. Note that this cell uses Daphne oil as the pressure mediator. We studied static magnetic order of CaFe_2As_2 at ambient pressure and at $p = 3.9, 6.2$ and 9.9 kbar by performing W T F-SR with $W T F = 50$ G. Solid symbols in Fig. 3(a) show the paramagnetic volume fraction, obtained after subtracting the contribution from the pressure cell in which the single crystal specimens were placed with their c -axis oriented parallel to the beam direction. Open circle symbols represent additional results in ambient pressure obtained without the pressure cell. Figure 3(a) demonstrates that static magnetic order sets in at temperatures well above the superconducting T_c in a partial volume fraction both at $p = 3.9$ and 6.2 kbar. The static magnetism disappears at $p = 9.9$ kbar where the superconducting state no longer exists. Figure 3(b) shows the low temperature ($T \rightarrow 0$) values of the volume fraction of the magnetically-ordered region (from W T F data) as well as the muon spin precession frequency in ZF-SR, which is proportional to the size of the ordered Fe moment. We present the resulting pressure-temperature phase diagram of CaFe_2As_2 in Fig. 3(c). The superconducting phase boundary in this figure is based on the reported resistivity results [4]. At this moment, we cannot determine whether the superconductivity exists in the paramagnetic volume alone or in the entire sample volume below T_c . In any case, Figs. 3(a)–(c) indicate that a rather strong magnetism exists in a substantial volume fraction below $T = 50$ – 100 K which is well above the superconducting T_c , as in the cases of the (Ba,K) and (Sr,Na) crystals in ambient pressure.

Resistivity [4] and neutron [35] measurements in applied pressure, the former (the latter) using a liquid (He gas) pressure mediator, have been reported on CaFe_2As_2 single crystals prepared by an identical method to that used for the present specimens [24]. In resistivity studies, a sharp jump was observed at $T = 170$ K at ambient pressure, corresponding to the first-order tetragonal-to-orthorhombic structural phase transition below which magnetic order was detected both by neutrons and muons. With increasing pressure this feature broadens and ordering moves towards lower temperatures, which is qualitatively consistent with the present results in Fig. 3(c). The resistivity anomaly becomes invisible above $p = 4$ kbar, and the neutron magnetic Bragg peak intensity at $T = 50$ K becomes nearly equal to the background level at $p = 6.3$ kbar (Fig. 1(c) in ref. [35]), while SR detected magnetic order continuing to exist at $p = 6.2$ kbar, albeit in a partial volume fraction. A rather sharp structural change detected by neutrons around $p = 3$ kbar does not have a corresponding signature in the

SR data except for an onset of phase separation. At this moment, it is not clear whether these apparent differences are due to (a) different sensitivity of these three probes to magnetic order, as described in more detail in the on-line Supplementary Document C, or (b) to possibly different degrees of the strain gradient between measurements with pressure instruments using liquid and gas mediators, or to both (a) and (b). Further experimental efforts are required for elucidating details of structural and magnetic behaviors, especially in the pressure region of $p = 4$ – 8 kbar.

In Figure 4, we plot the precession frequencies observed in ZF-SR against the Neel temperatures for various 1111 and 122 systems including undoped, doped, and superconducting systems in ambient and applied pressure [14, 18, 19, 36]. Since the Fe-muon hyperfine coupling constants are different only by within 10 % between the 1111 and 122 systems [19], the vertical axis is nearly proportional to the static Fe moment size (see on-line Supplementary Document D for more details). Figure 4 indicates that static magnetism disappears when the system approaches the superconducting state in the 1111 systems, while significantly stronger magnetism (with higher T_N and larger moment size) remains in the 122 systems deep into the superconducting pressure region. This may be related to the more three-dimensional structure of the 122 systems which generally favours magnetic order. Phase separation between volumes with and without static magnetism at the border of a collinear antiferromagnetic state and a non-magnetic spin-gap state was observed in an insulating J_1 - J_2 spin system $\text{Cu}(\text{ClBr})\text{La}(\text{Nb,Ta})_2\text{O}_7$ [37]. Detailed features of the observed SR spectra in this system are remarkably similar to the results in the present 122 systems. This similarity suggests an important role of the J_1 - J_2 frustration played in determining the magnetic behavior of the FeAs-based systems.

Regarding the pairing symmetry, available experimental results on the 1111 and 122 systems are divided between those favoring an isotropic nodeless gap [32, 38] and those supporting line nodes [39]. Some theories for an extended s -wave pairing [40] propose evolution from nodeless behavior to line-node behavior with progressive carrier doping. Multi-gap features can also result in T -dependence different from the BCS s -wave curvature [30, 31]. The present results in Fig. 2(a) represent the first high-statistics SR data of the thermodynamic behavior of the superfluid density obtained in single crystal specimens of the FeAs-based superconductors. The difference between our previous and present results on the two different (Ba,K) crystals, contrasted in Fig. 2(a), may be explained by their different doping levels corresponding to different superfluid densities. It will be important to develop theories of superconducting pairing symmetry including the effect of phase-separated, co-existing static magnetic regions. Figure 2(a) has es-

tablished at least one definite case which does not agree with a single isotropic energy gap. The nearly linear relationship between T_c and the superfluid density (Fig. 2(b)) followed by cuprates, 1111 FeAs, 122 FeAs, and A_3C_{60} systems suggests the existence of an underlying generic principle common to condensation mechanisms of all these exotic superconductors.

We acknowledge financial support from US NSF DMR-05-02706 and 08-06846 (Material World Network) at Columbia, US NSF DMR-07-56568 at U. Tennessee Knoxville, US NSF DMR-08-04173 and Florida State at Florida State U., US DOE under contract No. DE-AC02-07CH11358 at Ames, NSERC and CIFAR (Canada) at McMaster, CNPq on MWN-CIAM program at CBPF (Brazil), NSFC, CAS, and 973 project of MOST (China) at IOP, Beijing, and US-Japan cooperative program at Kyoto U. from JSPS (Japan).

ON-LINE SUPPLEMENTARY DOCUMENT A: SR TIME SPECTRA IN ZF, WTF AND TF

In this section, we briefly show basic features of SR measurements in zero field (ZF), weak transverse field (WTF) and transverse field (TF), together with time spectra obtained on single crystal specimens of $(Ba_{0.5}K_{0.5})Fe_2As_2$ in the present work. Figure 5(a) shows the ZF-SR spectra. The appearance of oscillations below $T = 60$ K indicates an onset of a static internal field from static Fe moments. The amplitude of this signal is proportional to the fraction of muons landing in the region with static magnetic order. The frequency is proportional to the magnitude of the static internal field, and thus to the size of the ordered Fe moments. In the case of Fig. 5(a), the oscillation frequency of 20 MHz signal corresponds to an internal field of about 1.5 kG. The damping of this oscillation is caused by a dephasing process due to an inhomogeneity of the static internal field caused by short-range static spin correlations, or incommensurate magnetism, and/or possible effects of randomness and imperfections. In general, fluctuating internal fields due to dynamic spin fluctuations and/or spin waves can also cause damping of the oscillation through the energy-dissipative $1=T_1$ processes. Static and dynamic origins of the damping can be distinguished by their different responses in SR spectra to application of longitudinal external fields. Long-lived oscillation signals in ZF can be expected for commensurate long-ranged static magnetism, as shown in Figs. 1(a) and 2(a) of ref. [19] for the cases of the parent compounds of the 1111 and 122 FeAs systems.

When a weak, external transverse field (WTF) of typically 30-100 G is applied, muon spins in the paramagnetic or non-magnetic environment exhibit slow coherent precession around the WTF, as shown in Fig. 5(b). In magnetically-ordered regions of most magnetic systems,

a static internal field from surrounding ordered moments at the muon site is much larger than the applied WTF. As a result, those muon spins cannot join in the WTF precession and the signal from the magnetically-ordered region usually disappears within about $t \sim 200$ ns in WTF measurements. This is due to inhomogeneous broadening of the vector sums of the internal plus external fields. The remaining slowly-oscillating signal represents contributions from the other muons in the paramagnetic environment. As shown in Fig. 5(b), it is very straightforward to derive the amplitude of this slow oscillation. Figures 1(b) and 3(a) of the present work and Figs. 1(c) and 3(c) of ref. [19] show the amplitude of such slowly oscillating signals in WTF. This procedure provides another method to estimate volume fractions of the ordered and paramagnetic regions, in addition to the ZF precession signal amplitude which represents the former. The results from the WTF and ZF methods usually agree well, as shown in Fig. 1(c) of ref. [19].

In type-II superconductors below T_c , the application of an external field above H_{c1} leads to the formation of a flux vortex lattice inside the superconductor, which has a well-defined field distribution [6]. This field distribution causes additional damping of the precession signal in both WTF and TF-SR measurements. This feature can be seen in WTF spectra in Fig. 5(b) below $T_c = 37$ K. The optimal value of TF to study the effect of the penetration depth and flux vortex lattice, however, generally ranges between 100 - 3000 G, since it should be above H_{c1} and well below H_{c2} , with the distance between the adjacent flux vortices significantly smaller than the penetration depth. In the present study, we chose to apply $TF = 500$ G, and performed measurements in the field-cooling procedure. Figure 5(c) shows the time spectra of TF-SR, from which we derived the relaxation rate in Fig. 2(a).

ON-LINE SUPPLEMENTARY DOCUMENT B: HIGH PRESSURE INSTRUMENTATION USED IN THE PRESENT WORK

A piston-cylinder-type pressure cell was used to generate hydrostatic pressures up to 10 kbar in the present work. The cylinder is made of a non-magnetic alloy MP35N and has an inside diameter of 7 mm and a wall thickness of 8 mm. Figure 6 shows some photos of this cell and a schematic drawing of the SR spectrometer used in high pressure measurements. The sample space was filled with a pressure-transmitting medium of Daphne oil 7373. The pressure cell was pressurized at room temperature before it was mounted in the cryostat and the pressure was maintained by using CuBe screws. The pressure was generally found to decrease by approximately 3 kbar at low temperatures due to a thermal contraction difference between the cell and the pressure-

transmitting medium. In this paper, we used the low-temperature-range pressure which was calibrated from the pressure dependence of superconducting temperature in Pb.

Previous SR measurements on MnSi [29], performed using this instrument at 0–16 kbar, reproduced the magnetic ordering temperatures and sharp features at phase boundaries reported in prior measurements by other techniques using different pressure cells. Sharp variations of

SR results have also been observed in our unpublished SR work on UGe_2 . Although these observations in other magnetic systems may or may not be generalized to the case of CaFe_2As_2 which exhibits a large change of the unit cell volume in the pressure range of the present work [35], the reproducibility and sharp aspects assure that the pressure cell used in the present work is as good, uniform and accurate as typical piston-cylinder cells currently used in various high pressure experiments in terms of homogeneity and absolute values of the generated pressure.

ON-LINE SUPPLEMENTARY DOCUMENT C : DIFFERENT SENSITIVITY OF MUONS AND NEUTRONS IN DETECTING MAGNETIC ORDER

In magnetic systems that exhibit commensurate long-range, static magnetic order, neutron scattering observes magnetic Bragg peaks, while SR often finds long-lived coherent precession in ZF below the ordering temperature. This was the case for LaOFeAs , as published in refs. [8, 18] which report neutron and SR measurements performed using an identical piece of sintered polycrystalline specimen. Neutron measurements are generally limited by small intensities of magnetic Bragg peaks, especially for the case of polycrystalline specimens having moments smaller than 0.5 Bohr magnetons per unit cell. In contrast, SR has a superb sensitivity for detecting small or random static moments, as even nuclear dipolar moments can be easily detected. In NdOFeAs , neutron studies initially reported the absence of static magnetic order, while SR measurements found a static magnetic order very similar to that of LaOFeAs [19]. The magnetic Bragg peaks in this material were subsequently observed after repeated measurements with higher statistics [41]. This incident demonstrates the potential difficulty in detecting static magnetic order by neutron scattering, even for the case of systems with long-range spin correlations.

For static magnetic order involving short-range or incommensurate or stripe spin correlations, it becomes even more difficult for neutron measurements to detect the onset of ordering, since the intensity is spread in a wider region of momentum space. As an example, here we will compare neutron and SR results obtained in a ceramic polycrystalline specimen of $\text{Ce}(\text{O}_{0.94}\text{F}_{0.06})\text{FeAs}$.

This system is not superconducting, but lies in the border region between the magnetically-ordered and superconducting phases, as elucidated by neutron scattering studies [9]. The Bragg peak intensity for this 6% F-doped system was very low, and static order was detected only below 10 K. In contrast, SR detected static order below $T = 40$ K as shown by the oscillation amplitude in WTF-SR in Fig. 7(a). The asymmetry of 0.2 at high temperatures corresponds to the value expected for fully paramagnetic systems, while the loss of the asymmetry below 40 K indicates a sharp onset of static magnetic order in 100% of the volume fraction. The frequency of the muon precession in ZF-SR (Fig. 7(b)) shows that the ordered moment size is about 0.1 Bohr magnetons.

This apparent difference of ordering behavior found by neutrons and muons can be understood when we look at the spectra of ZF-SR in Fig. 7(c). The spectra at $T = 5$ K exhibits a fast damping corresponding to a very short-ranged character of static Fe spin correlations. The faster damping seen at $T = 2$ K is most likely caused by incommensurate ordering of Ce. These examples on NdOFeAs and $\text{Ce}(\text{O},\text{F})\text{FeAs}$ demonstrate that different magnetic behaviors found by neutrons and muons can be caused by different sensitivities of these probes to static magnetic order.

This general argument provides a possible explanation for the static magnetic order of CaFe_2As_2 found in a wider pressure region in the present SR measurements as compared to that found by neutron scattering studies [35]. An increasingly short-ranged spin correlation is found with increasing pressure by the present studies of CaFe_2As_2 , as demonstrated by the ZF-SR spectra in Fig. 7(d).

ON-LINE SUPPLEMENTARY DOCUMENT D : CONVERSION BETWEEN THE ZF-SR FREQUENCY AND ORDERED FEMOMENT SIZE

Frequencies observed in ZF-SR measurements are generally proportional to the size of the static ordered moment within a given series of magnetic materials having the same crystal structures and an identical muon site location in the unit cell. However, the conversion from the frequency to the Fe moment size is not easy in FeAs-based systems, since the accurate location of the muon site is not known. The argument in Supplementary Doc. C indicates that neutron scattering intensity is not much reliable for this purpose either. In contrast, the hyperfine splitting observed in Mössbauer effect measurements can provide a more reliable estimate of the size of the static Fe moments. As described in ref. [19], comparisons of SR frequencies and Mössbauer hyperfine fields observed in LaOFeAs , BaFe_2As_2 and SrFe_2As_2 [13, 14, 15, 18, 19] indicate that the hyperfine coupling

constants between the muon spin and the Fe moment are nearly equal for the 1111 and 122 systems, with a difference of about 10 %.

Therefore, we plot the SR frequencies in the vertical axis of Fig. 4 without corrections between the 1111 and 122 systems. The absolute value of the moment was scaled based on the Mössbauer results in ref. [13] for BaFe_2As_2 . The resulting Fe moment size, shown in the right-vertical axis of Fig. 4, involves about 10 % error due to the difference between the 1111 and 122 systems. The results of this conversion agree rather well with the estimates from neutron scattering studies which reported 0.36 and 0.8 Bohr magnetons for Fe moments in LaOFeAs [8] and CaFe_2As_2 [12] respectively. Different Mössbauer measurements reported in the literature have adopted different conversion factors between the hyperfine splitting and the Fe moment size [13, 15], resulting in estimates for the ordered moment size in LaOFeAs that differ in magnitude up to 40 %. This ambiguity leads to a systematic error for the absolute moment values in Fig. 4. The relative comparison of the moment size between different systems, however, can be made with the accuracy of $\pm 10\%$, assuming that the muon site does not change among materials within each series (1111 and 122).

author to whom correspondences should be addressed:
E-mail tom.o@brentz.phys.columbia.edu

- [1] Y. Kamihara, T. Watanabe, M. Hirano, H. Hosono, Iron-Based Layered Superconductor $\text{LaO}_{1-x}\text{F}_x\text{FeAs}$ ($x = 0.05-0.12$) with $T_c = 26$ K, *J. Am. Chem. Soc.* 130 (2008) 3296.
- [2] X.H. Chen et al., Superconductivity at 43 K in Samarium-arsenide Oxides $\text{SmFeAsO}_{1-x}\text{F}_x$, *Nature* 453 (2008) 761; G.F. Chen et al., Superconductivity at 41 K and its competition with spin-density-wave instability in layered $\text{CeO}_{1-x}\text{F}_x\text{FeAs}$, *Phys. Rev. Lett.* 100 (2008) 247002; Zhi-An Ren et al., Superconductivity and Phase Diagram in the Iron-based Arsenic-oxides ReFeAsO_1 (Re = rare earth metal) without F-Doping, *Europhys. Lett.* 83 (2008) 17002; H.H. Wen, G. Mu, L. Fang, H. Yang, X. Zhu, Superconductivity at 25 K in hole-doped $(\text{La}_{1-x}\text{Sr}_x)\text{OFeAs}$, *Europhys. Lett.* 82 (2008) 17009; Zhi-An Ren et al., Superconductivity and Phase Diagram in the Iron-based Arsenic-oxides ReFeAsO_1 (Re = rare earth metal) without F-Doping, *Europhys. Lett.* 83 (2008) 17002.
- [3] M. Rotter, M. Tegel and D. Johrendt, Superconductivity at 38 K in the iron arsenide $(\text{Ba}_{1-x}\text{K}_x)\text{Fe}_2\text{As}_2$, arXiv:0805.4630; G.F. Chen et al., Superconductivity in hole-doped $(\text{Sr}_{1-x}\text{K}_x)\text{Fe}_2\text{As}_2$, arXiv:0806.1209 (2008); K. Sasmal et al., Superconductivity up to 37 K in $(\text{A}_{1-x}\text{Sr}_x)\text{Fe}_2\text{As}_2$ with $\text{A}=\text{K}$ and Cs , arXiv:0806.1301 (2008).
- [4] M.S. Torikachvili, S.L. Bud'ko, N. Ni, P.C. Canfield, Pressure Induced Superconductivity in CaFe_2As_2 , *Phys. Rev. Lett.* 101 (2008) 057006.
- [5] P.L. Alireza et al., Superconductivity up to 29 K in SrFe_2As_2 and BaFe_2As_2 at high pressures, arXiv:0807.1896 (2008).
- [6] X.C. Wang et al., The superconductivity at 18 K in Li_xFeAs compounds, arXiv:0806.4688 (2008).
- [7] F.C. Hu et al., Superconductivity in the PbO -type Structure FeSe , arXiv:0807.2369 (2008); Y.M. Izuguchi, F. Tomioka, S. Tsuchida, T. Yamaguchi and Y. Takano, Superconductivity at 27 K in tetragonal FeSe under high pressure, arXiv:0807.4315 (2008).
- [8] C. de la Cruz et al., Magnetic Order versus superconductivity in the Iron-based layered $\text{La}(\text{O}_{1-x}\text{F}_x)\text{FeAs}$ systems, *Nature* 453 (2008) 899.
- [9] J. Zhao et al., Structural and magnetic phase diagram of $\text{CeFeAsO}_{1-x}\text{F}_x$ and its relationship to high-temperature superconductivity, arXiv:0806.2528 (2008).
- [10] H. Chen et al., Coexistence of the spin-density-wave and superconductivity in the $\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$, arXiv:0807.3950 (2008).
- [11] Q. Huang et al., Magnetic order in BaFe_2As_2 , the parent compound of the FeAs -based superconductors in a new structural family, arXiv:0806.2776 (2008).
- [12] A.I. Goldman et al., Lattice and magnetic instabilities in CaFe_2As_2 : A single crystal neutron diffraction study, arXiv:0807.1525 (2008).
- [13] M. Rotter et al., Spin-density-wave anomaly at 140 K in the ternary iron arsenide BaFe_2As_2 , arXiv:0805.4021 (2008).
- [14] A. Jesche et al., Strong coupling between magnetic and structural order parameters in SrFe_2As_2 , arXiv:0807.0632 (2008).
- [15] H.H. Kjauss et al., Commensurate Spin Density Wave in LaOFeAs : A Local Probe Study, arXiv:0805.0264 (2008).
- [16] H. Luetkens et al., Field and Temperature Dependence of the Superfluid Density in $\text{LaO}_{1-x}\text{F}_x\text{FeAs}$ Superconductors: A Muon Spin Relaxation Study, arXiv:0804.3115 (2008); R. Khasanov et al., Muon-spin rotation studies of $\text{SmFeAsO}_{0.85}$ and $\text{NdFeAsO}_{0.85}$ superconductors, arXiv:0805.1923 (2008).
- [17] A.J. Drew et al., Coexistence of magnetic fluctuations and superconductivity in the pnictide high temperature superconductor $\text{SmFeAsO}_{1-x}\text{F}_x$ measured by muon spin rotation, arXiv:0805.1042 (2008).
- [18] J.P. Carbo et al., Static magnetic order and superfluid density of $\text{RE}(\text{O},\text{F})\text{FeAs}$ (RE = La, Nd, Ce) and LaOFeP studied by muon spin relaxation: remarkable similarities with the cuprates, arXiv:0805.2186 (2008).
- [19] A.A. Aczel et al., Muon spin relaxation studies of magnetic order and superfluid density in antiferromagnetic NdOFeAs , BaFe_2As_2 and superconducting $(\text{Ba,K})\text{Fe}_2\text{As}_2$, arXiv:0807.1044 (2008).
- [20] Y.J. Uemura et al., Universal Correlations between T_c and n_s/m (Carrier Density over Effective Mass) in High- T_c Cuprate Superconductors, *Phys. Rev. Lett.* 62 (1989) 2317; Y.J. Uemura et al., Basic Similarities among Cuprate, Bismuthate, Organic, Chevrel-Phase and Heavy-Fermion Superconductors Shown by Penetration-Depth Measurements, *Phys. Rev. Lett.* 66 (1991) 2665; Y.J. Uemura, Twin spin/charge roton mode and superfluid density: Primary determining factor of T_c in high- T_c superconductors observed by neutron, ARPES, and μSR , *Physica B* 374-375 (2006) 1.
- [21] H. Luetkens et al., Electronic phase diagram of the $\text{LaO}1-$

- $x\text{FeAs}$ superconductor, arXiv:0806.3533 (2008).
- [22] A.J.Drew et al., Coexistence of static magnetism and superconductivity in $\text{SmFeAsO}_{1-x}\text{F}_x$ as revealed by muon spin rotation, arXiv:0807.4876 (2008).
- [23] N.Ni et al., Anisotropic thermodynamic and transport properties of single crystalline $(\text{Ba}_{1-x}\text{K}_x)\text{Fe}_2\text{As}_2$ ($x = 0$ and 0.45), Phys. Rev. B 78 (2008) 014507.
- [24] N.Ni et al., First-order structural phase transition in CaFe_2As_2 , Phys. Rev. B 78 (2008) 014523.
- [25] G.F.Chen et al., Breaking rotation symmetry in single crystal SrFe_2As_2 , arXiv:0806.2648 (2008).
- [26] J.E. Sonier, J.H. Brewer, R.F. Kie, SR Studies of the Vortex State in Type-II Superconductors, Rev. Mod. Phys. 72 (2002) 769.
- [27] Muon Science: Muons in Physics, Chemistry and Materials, ed. by S.L. Lee, S.H. Kilcoyne, and R. Cywinski, Inst. of Physics Publishing, Bristol, 1999.
- [28] A.T.Savici et al., Muon spin relaxation studies of incommensurate magnetism and superconductivity in stage-4 $\text{La}_2\text{CuO}_{4.11}$ and $\text{La}_{1.88}\text{Sr}_{0.12}\text{CuO}_4$, Phys. Rev. B 66 (2002) 014524.
- [29] Y.J.Uemura et al., Phase separation and suppression of critical dynamics at quantum phase transitions of MnSi and $(\text{Sr}_{1-x}\text{Ca}_x)\text{RuO}_3$, Nature Physics 3 (2007) 29–35.
- [30] L.Benfatto, M.Capone, S.Caprara, C.Castellani, C.DiCastro, Multiple Gaps and Superfluid Density from Interband Pairing in Iron Oxypnictides, arXiv:0807.4408 (2008).
- [31] C.Ren et al., Evidence for Two Gaps and Breakdown of the Uemura Plot in $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$ Single Crystals, arXiv:0808.0805 (2008).
- [32] H.Ding et al., Observation of Fermi-surface-dependent nodeless superconducting gaps in $\text{Ba}_{0.6}\text{K}_{0.4}\text{Fe}_2\text{As}_2$, arXiv:0807.0419 (2008).
- [33] M.Altarawneh et al., Determination of anisotropic H_{c2} up to 45 T in $(\text{Ba}_{0.55}\text{K}_{0.45})\text{Fe}_2\text{As}_2$ single crystals, arXiv:0807.4488; H.Q.Yuan et al., Nearly Isotropic superconductivity in $(\text{Ba,K})\text{Fe}_2\text{As}_2$, arXiv:0807.3137 (2008).
- [34] P.L.Russo et al., Muon Spin Relaxation Study of Superconducting $\text{Bi}_2\text{Sr}_2-x\text{La}_x\text{CuO}_{6+}$ (Bi_2201), Phys. Rev. B 75 (2007) 054511.
- [35] A.Kreyssig et al., Squeezing the magnetism out of superconducting CaFe_2As_2 , arXiv:0807.3032 (2008).
- [36] see results shown in the on-line Supplementary Document C.
- [37] Y.J.Uemura et al., Quantum evolution from spin-gap to antiferromagnetic state in the frustrated J_1 - J_2 system $\text{Cu}(\text{Cl,Bi})\text{La}(\text{Nb,Ta})_2\text{O}_7$, arXiv:0806.2021 (2008).
- [38] K.Hashimoto et al., Microwave Penetration Depth and Quasiparticle Conductivity in Single Crystal PrFeAsO_{1-y} : Evidence for Fully Gapped Superconductivity, arXiv:0806.3149 (2008).
- [39] M.C.Boyer et al., Scanning tunneling microscopy of the 32 K superconductor $(\text{Sr}_x\text{K}_x)\text{Fe}_2\text{As}_2$, arXiv:0806.4400 (2008); C.Ren et al., Linear Temperature Dependence of the Lower Critical Field H_{c1} in F-Doped LaOFeAs Superconductors, arXiv:0804.1726 (2008); L.Shan et al., Point-Contact Spectroscopy of Iron-Based Layered Superconductor $\text{LaO}_{0.9}\text{F}_{0.1}\text{FeAs}$, arXiv:0803.2405 (2008); H.J.Grafe et al., ^{75}As NMR studies of superconducting $\text{LaO}_{0.9}\text{F}_{0.1}\text{FeAs}$, arXiv:0805.2595 (2008); Y.Nakai et al., Evolution from Itinerant Antiferromagnet to Unconventional Superconductor with Fluorine Doping in $\text{La}(\text{O}_{1-x}\text{F}_x)\text{FeAs}$ Revealed by ^{75}As and ^{139}La Nuclear Magnetic Resonance, arXiv:0805.4795 (2008); H.Mukuda et al., ^{75}As NQR/NMR Studies on Oxygen-deficient Iron-based Oxypnictide Superconductors LaFeAsO_{1-y} ($y = 0, 0.25, 0.4$) and $\text{NdFeAsO}_{0.6}$, arXiv:0806.3238 (2008).
- [40] M.M.Parish, Jiangping Hu, B.A.Bernevig, Experimental consequences of the S -wave $\cos(k_x)\cos(k_y)$ Superconductivity in the Iron-Pnictides, arXiv:0807.4572 (2008).
- [41] Y.Chen et al., Magnetic Order of the Iron Spins in NdOFeAs , arXiv:0807.0662 (2008).

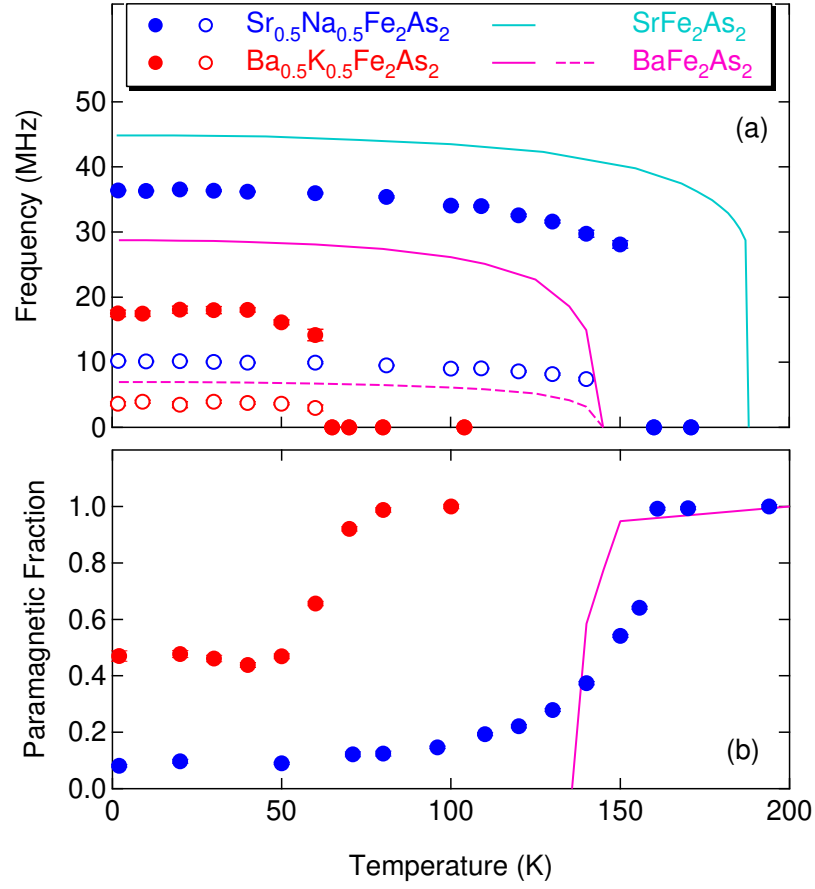


FIG. 1: (color) Temperature dependences of (a) the muon spin precession frequency observed in ZF- SR and (b) the paramagnetic volume fraction determined in W T F- SR measurements in single crystal specimens of $(\text{Ba}_{0.5}\text{K}_{0.5})\text{Fe}_2\text{As}_2$ ($T_c = 37$ K) and $(\text{Sr}_{0.5}\text{Na}_{0.5})\text{Fe}_2\text{As}_2$ ($T_c = 35$ K), which demonstrate the onset of static magnetic order in a partial volume fraction at temperatures well above the superconducting T_c . The results from the present work (solid and open circles) are compared with those of the undoped parent compounds BaFe_2As_2 [19] and SrFe_2As_2 [14] (solid and broken lines).

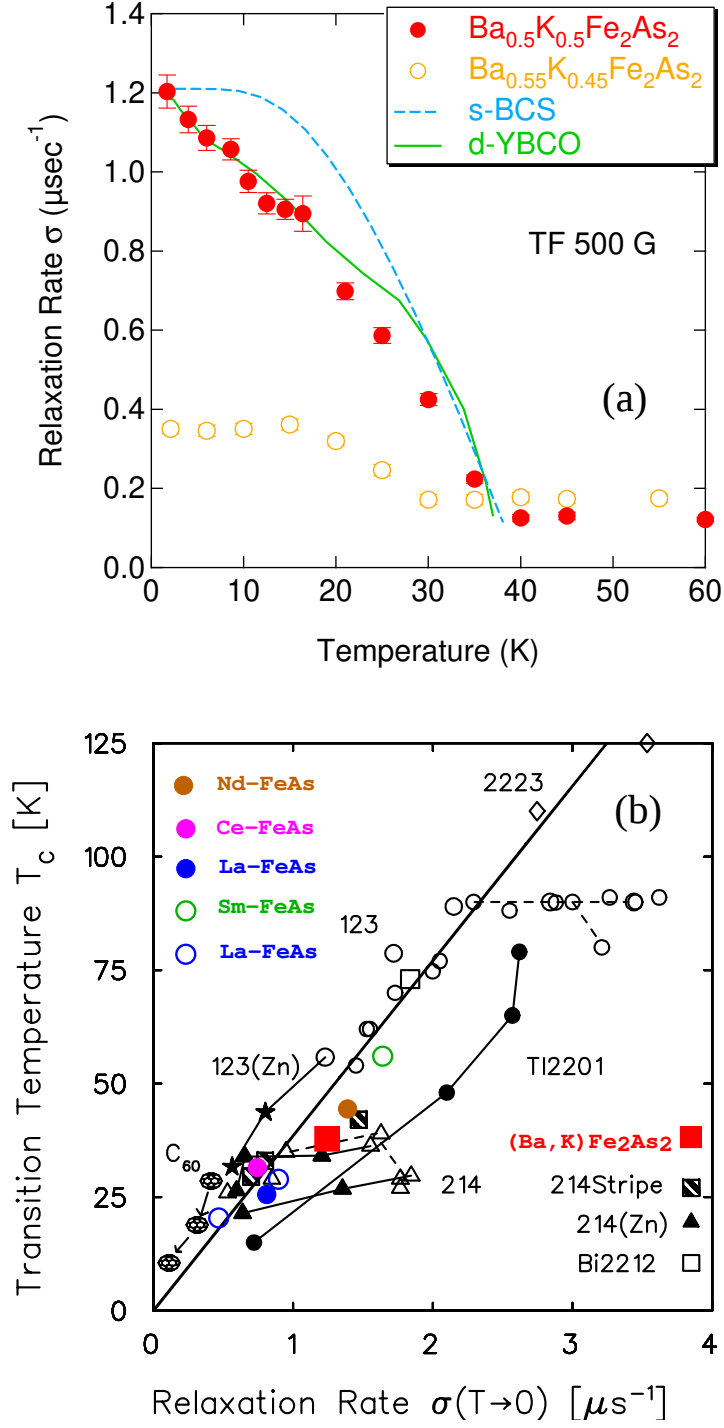


FIG. 2: (color) (a) Temperature dependence of the muon spin relaxation rate observed in a single crystal specimen of $(\text{Ba}_{0.5}\text{K}_{0.5})\text{Fe}_2\text{As}_2$ ($T_c = 37$ K) in TF-SR with TF = 500 G (closed circles, present work), compared with the temperature dependence expected for the isotropic energy gap of BCS s-wave pairing (broken line), scaled results from YBCO [26] (solid line), and our previous results in a different crystal of $\text{Ba}_{0.55}\text{K}_{0.45}\text{Fe}_2\text{As}_2$ [19] (open circles). The superfluid density is observed to be linear in T at low temperatures, which is consistent with an anisotropic energy gap with line nodes or multiple isotropic gaps with widely different magnitudes. (b) A plot of the relaxation rate ($T \rightarrow 0$) versus T_c , including the point for $(\text{Ba}_{0.5}\text{K}_{0.5})\text{Fe}_2\text{As}_2$ from the present work as well as those for the FeAs-based 1111 superconductors published in refs. [16, 18], various cuprates, and A_3C_{60} superconductors [20], which demonstrates a nearly linear relationship between the superfluid density $n_s \propto m$ and T_c followed by all of these exotic superconductors.

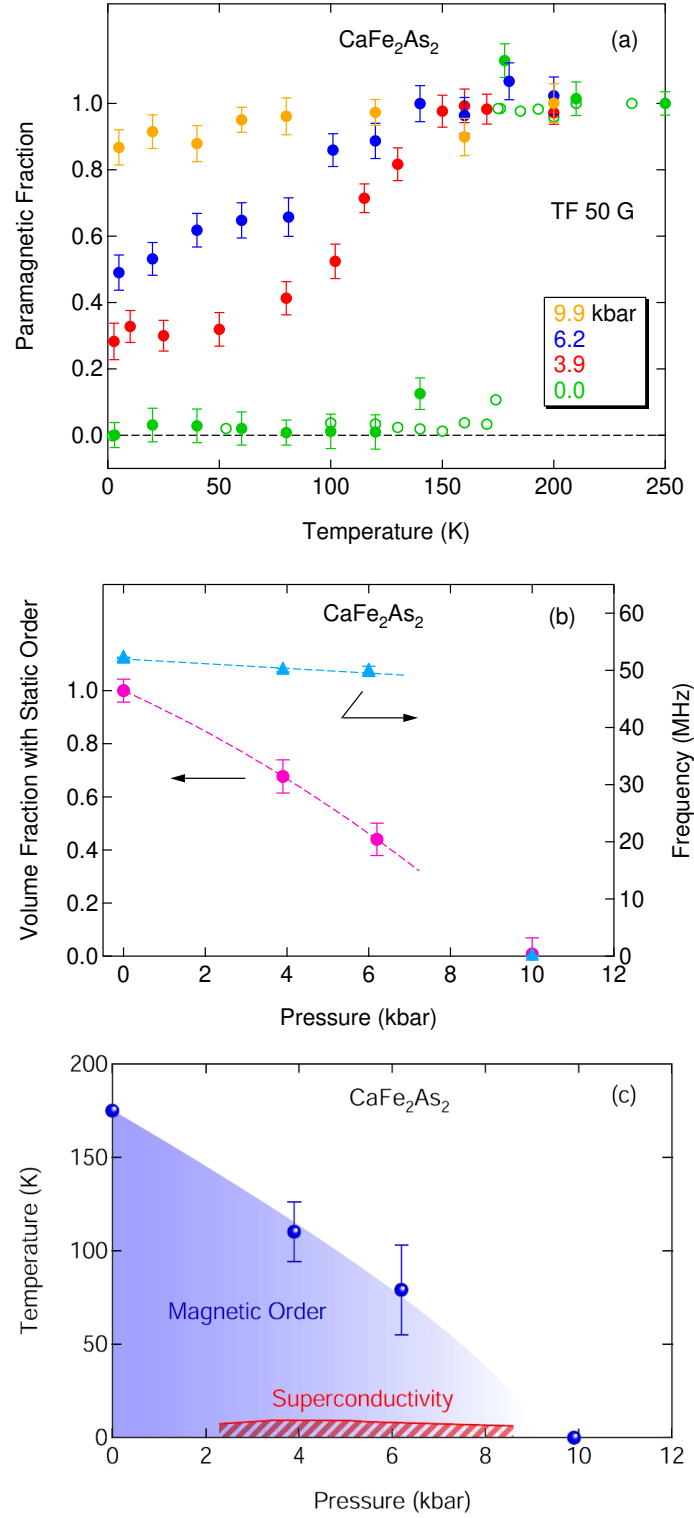


FIG. 3: (color) (a) The volume fraction of regions without static magnetic order in CaFe_2As_2 , as a function of temperature and pressure, determined by W T F - SR measurements with $W T F = 50$ G. The points with closed (open) symbols were obtained in measurements with (without) a pressure cell. (b) Pressure dependence of the volume fraction of the magnetically-ordered region (purple closed circles; left axis) from W T F - SR and the muon spin precession frequency (blue triangles; right axis) from ZF - SR at $T = 2$ K in CaFe_2As_2 . (c) The phase diagram as a function of pressure and temperature in CaFe_2As_2 . These results demonstrate an onset of static magnetic order in a partial volume fraction at temperatures well above the superconducting T_c 's. The T_c values are taken from the reported resistivity results [4]. Upper, middle, and lower temperatures attached to the closed circle symbols for T_N represent temperatures at which the volume fraction with static magnetic order becomes 30, 50, and 70 % of the value at $T = 0$, respectively.

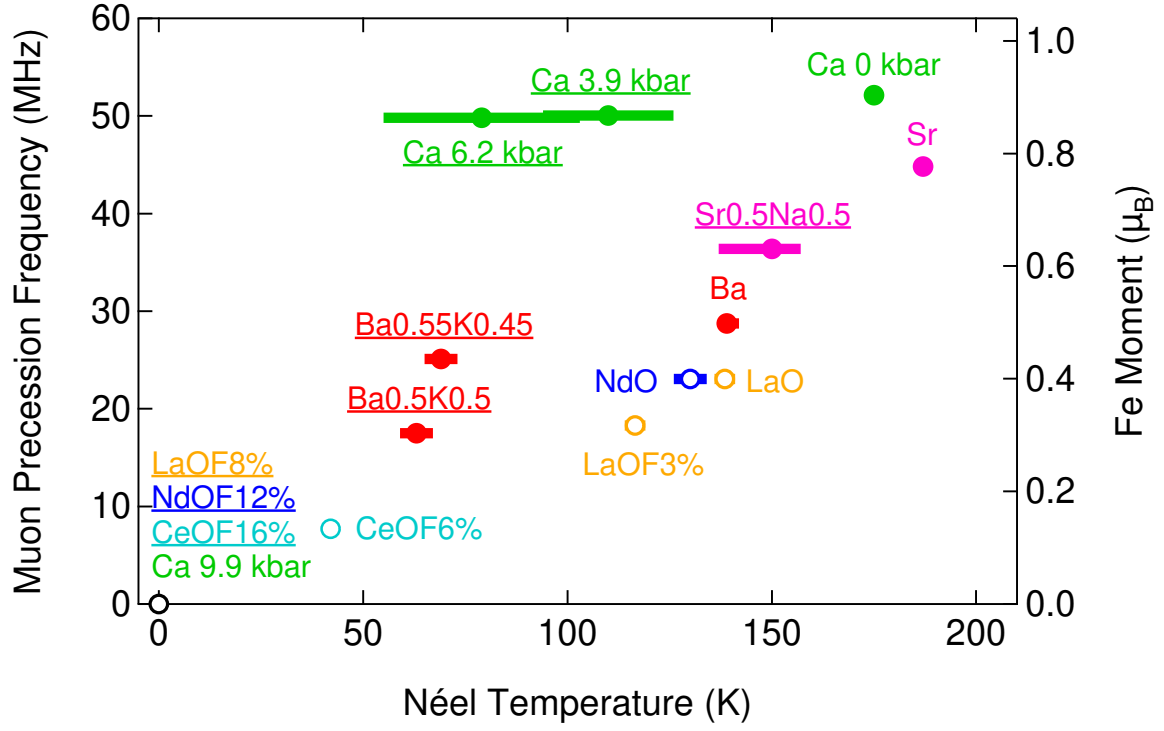


FIG. 4: (color) Plot of the muon spin precession frequency in ZF-SR versus Néel temperature for the 1111 FeAs systems (open symbols; from refs. [18, 36]) and the 122 FeAs systems (filled symbols; present work and refs. [14, 19]). Superconducting compounds are underlined. An estimate of the ordered Fe moment size, based on comparisons of SR and Mössbauer effect results [19], is given in the right axis. Details of the frequency to moment conversion is given in the online Supplementary Document D. The extended bar symbols for the superconducting 122 systems indicate temperatures at which the volume fraction with static magnetic order becomes 30 and 70% of the values at $T = 2$ K. These results demonstrate that the static magnetism is more robust in the 122 systems, which have more three-dimensional crystal structures than the 1111 systems.

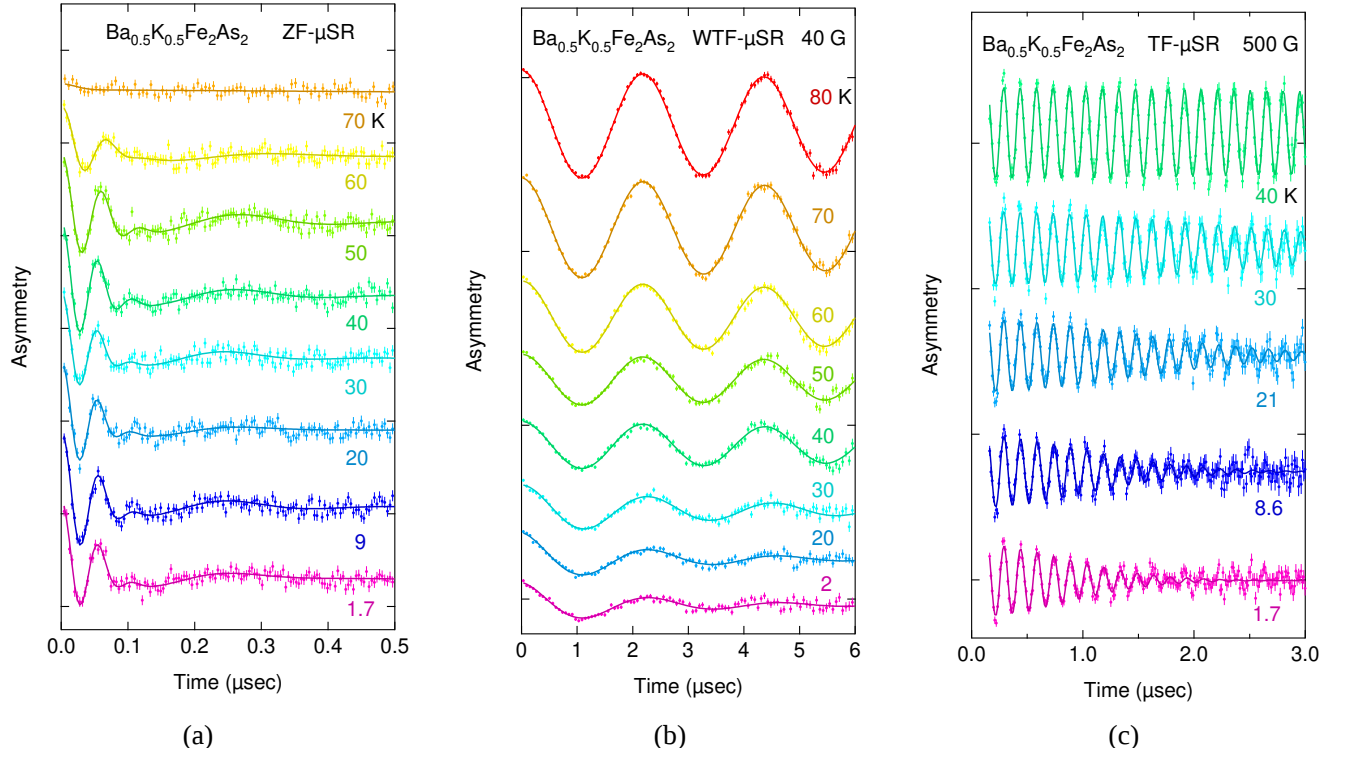


FIG. 5: (color) Figure for the on-line Supplementary Document A
Time spectra of (a) zero-field SR, (b) weak-transverse-field SR, and (c) transverse-field SR observed in a single-crystal specimen of $\text{Ba}_{0.5}\text{K}_{0.5}\text{Fe}_2\text{As}_2$.

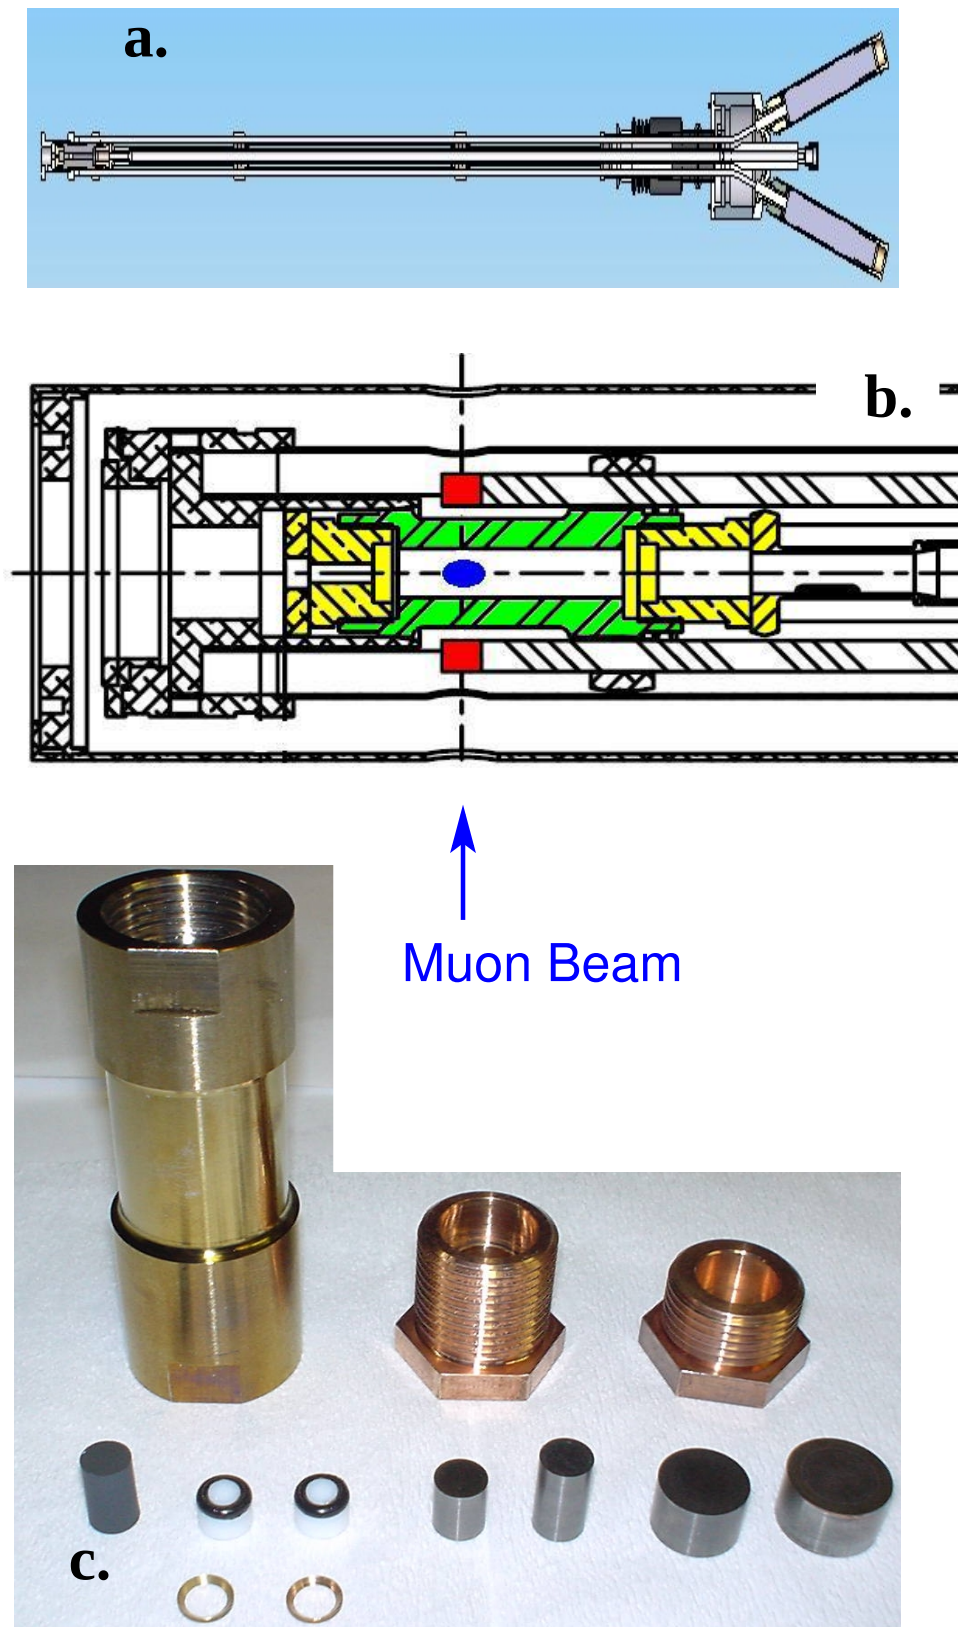


FIG . 6: (color) Figure for the on-line Supplementary Document B

(a) and (b): Schematic drawing of a SR spectrometer at TRIUMF used for measurements with applied pressure. The blue circle in (b) represents the specimen, and the green and yellow regions show the walls of the pressure cell. The red squares show plastic scintillation counters which detect incoming muons and decay positrons. (c) A photograph of the piston-cylinder-type pressure cell used in the present measurements.

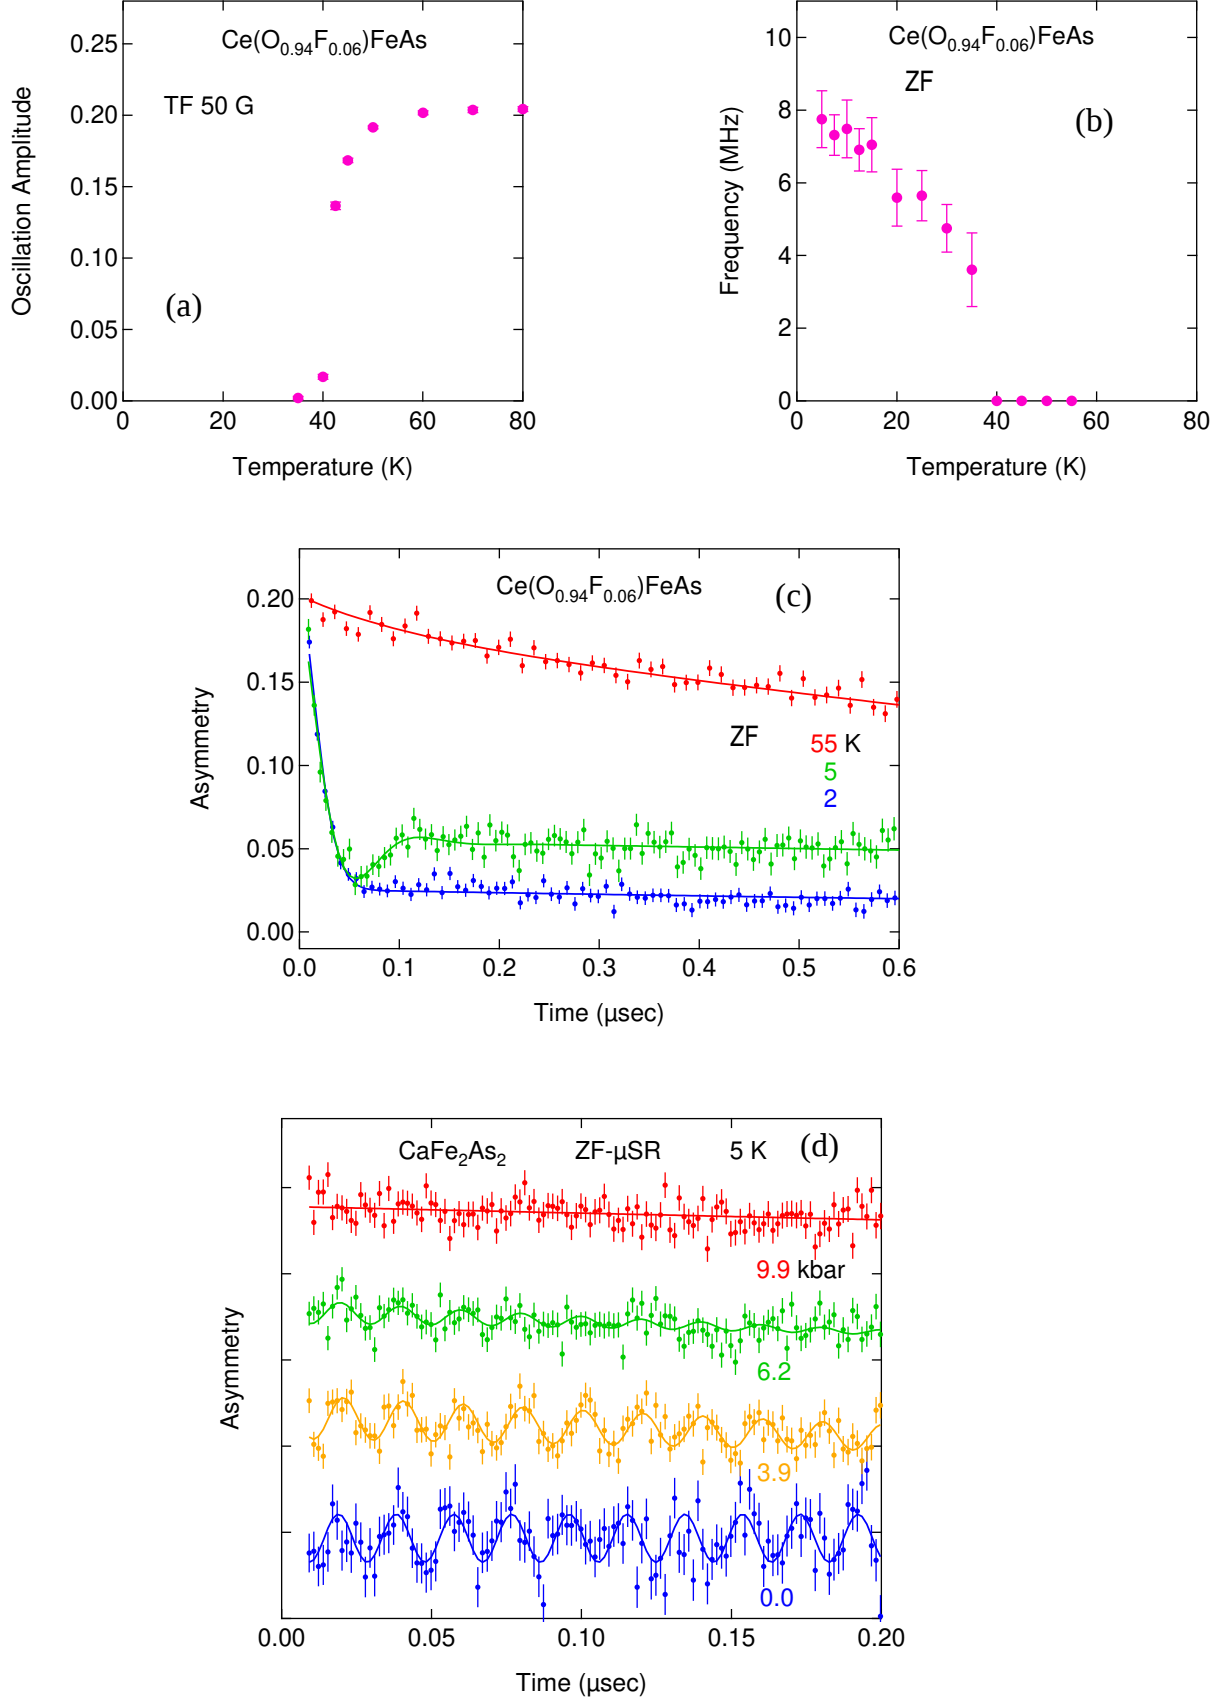


FIG. 7: (color) Figure for the on-line Supplementary Document C

(a) The precession amplitude of muon spins in a weak transverse field (TF) of 50 G, (b) the ZF- μSR precession frequency, and (c) the time spectra of ZF- μSR observed in a polycrystalline specimen of $\text{CeO}_{0.94}\text{F}_{0.06}\text{FeAs}$. (d) shows the time spectra of ZF- μSR measurements from a mosaic single-crystal specimen of CaFe_2As_2 obtained using a pressure cell at $T = 5\text{ K}$ at several different hydrostatic pressures.