

Superconductivity in $\text{SrN}_{1/2}\text{As}_2$ Single Crystals

E. D. Bauer, F. Ronning, B. L. Scott, and J. D. Thompson

Los Alamos National Laboratory, Los Alamos, New Mexico 87545, USA

(Dated: February 20, 2024)

Abstract

The electrical resistivity $\rho(T)$ and heat capacity $C(T)$ on single crystals of $\text{SrN}_{1/2}\text{As}_2$ and $\text{EuN}_{1/2}\text{As}_2$ are reported. While there is no evidence for a structural transition in either compound, $\text{SrN}_{1/2}\text{As}_2$ is found to be a bulk superconductor at $T_c = 0.62$ K with a Sommerfeld coefficient of $\gamma = 8.7$ mJ/molK² and a small upper critical field $H_{c2} \approx 200$ Oe. No superconductivity was found in $\text{EuN}_{1/2}\text{As}_2$ above 0.4 K, but anomalies in ρ and C reveal that magnetic order associated with the Eu^{2+} magnetic moments occurs at $T_m = 14$ K.

PACS numbers: 74.10.+v, 74.25.Bt, 74.70.Dd

The ThCr_2Si_2 structure type is well known for accommodating a superconducting ground state, particularly in the heavy fermion community with superconductors such as CeCu_2Si_2 and URu_2Si_2 . [1] Soon after the discovery of superconductivity in $\text{LaFeAsO}_{1-x}\text{F}_x$ at $T_c = 26$ K with the structure type ZrCuSiAs , [2] it was realized that the related compounds (AFe_2As_2 with $A = \text{Ba, Sr, Ca, Eu}$) in the ThCr_2Si_2 structure are also superconducting either with doping [3, 4, 5, 6, 7] or under pressure. [8, 9, 10]. While systems with Fe_2As_2 planes have the highest T_c 's to date, superconductivity has been found in both structure types with either NiP_2 (Refs. 11, 12) or NiAs_2 (Refs. 13, 14, 15, 16) layers.

Here we report the observation of superconductivity in single crystals of SrNi_2As_2 at $T_c = 0.62$ K, as determined by heat capacity, in the absence of a structural phase transition (below 400 K). Following our initial observation of superconductivity in BaNi_2As_2 , [16] this represents the second superconducting system in the ThCr_2Si_2 structure with NiAs_2 layers. In addition, we report that our EuNi_2As_2 single crystals grown from Pb flux are not superconducting above 0.4 K.

Single crystals of SrNi_2As_2 and EuNi_2As_2 were grown in Pb flux in the ratio $(\text{Sr,Eu})\text{NiAsPb} = 1:2:2:20$. The starting elements were placed in an alumina crucible and sealed under vacuum in a quartz ampoule. The ampoule was placed in a furnace and slowly heated 1050 °C, as described in Ref. 16. The sample was then cooled slowly (5°C hr^{-1}) to 600 °C, at which point the excess Pb flux was removed with the aid of a centrifuge. For SrNi_2As_2 the resulting plate-like crystals were heavily imbedded in a yet unidentified needle-like impurity phase. From single crystal x-ray refinements, the plate-like samples were confirmed to crystallize in the ThCr_2Si_2 tetragonal structure (space group no. 139, $I4/mmm$). The refinement for SrNi_2As_2 [$R(\geq 2) = 3.7\%$] at 124 K yields lattice parameters $a = 4.1374(8)$ Å and $c = 10.188(4)$ Å and fully occupied ($> 98\%$) atomic positions $\text{Sr } 2a(0,0,0)$, $\text{Ni } 4d(0.5,0,0.25)$ and $\text{As } 4e(0,0,z)$ with $z = 0.3634(1)$ consistent with previous reports. [18, 19, 20] The refinement for EuNi_2As_2 [$R(\geq 2) = 5.09\%$] at 124 K gives lattice parameters $a = 4.0964(6)$ Å, $c = 10.029(3)$ Å and fully occupied ($> 98\%$) atomic positions $\text{Eu } 2a(0,0,0)$, $\text{Ni } 4d(0.5,0,0.25)$ and $\text{As } 4e(0,0,z)$ with $z = 0.3674(2)$ also consistent with previous reports. [21, 22]

The in-plane electrical resistivity data for ANi_2As_2 ($A = \text{Ba, Sr, Eu}$) is shown in Fig. 1. All samples exhibit metallic behavior. SrNi_2As_2 is a relatively good metal with a $\text{RRR} (= (300\text{ K})/(4\text{ K}))$ of 11, and a residual resistivity of $7\text{ }\mu\Omega\text{-cm}$. The resistivity of EuNi_2As_2 exhibits

a kink at $T_m = 14$ K associated with magnetic ordering of the Eu^{2+} moments, consistent with previous reports.[22] For $\text{SrN}_{1/2}\text{As}_2$, there is no evidence of a structural transition below 400 K, in contrast to $\text{BaN}_{1/2}\text{As}_2$, which has a clear first order transition at $T_0 = 130$ K. The lack of a phase transition in $\text{SrN}_{1/2}\text{As}_2$ is also provided by the heat capacity data shown in the inset of Fig. 3.[24]

Figure 2 presents the low temperature in-plane resistivity data for $\text{SrN}_{1/2}\text{As}_2$ with fields applied parallel and perpendicular to the c-axis. In zero field, a sharp superconducting transition is observed at $T_c = 0.66$ K, defined as the mid-point resistive anomaly. With increasing magnetic field, the transition remains sharp and is quickly suppressed. The specific heat shown in Fig. 3 confirms the bulk nature of superconductivity in $\text{SrN}_{1/2}\text{As}_2$. The zero resistance state coincides exactly with the onset of the specific heat transition, from which we extract a superconducting transition temperature of $T_c = 0.62$ K by an equal area construction. A fit to the data from 0.7 K to 3 K of $C = T = \gamma + \beta T^2 + \beta' T^4$, a Sommerfeld coefficient $\gamma = 8.7$ mJ/moK² is obtained. Using this value, the ratio of the specific heat jump at T_c to the electronic specific heat is estimated to be $\Delta C = T_c \gamma' \approx 1.0$. From the coefficient $\gamma = 0.67$ mJ/moK⁴, one obtains a Debye temperature $\theta_D = 244$ K.

The magnetic field-temperature H - T phase diagram of $\text{SrN}_{1/2}\text{As}_2$ is shown in Fig. 4 determined from the $\rho(T)$ curves in Fig. 2, along with the data for $\text{BaN}_{1/2}\text{As}_2$ for comparison.[16] For $\text{SrN}_{1/2}\text{As}_2$, the zero-temperature orbital critical field[25] $H_{c2}(0) = -0.7 T_c dH_{c2}/dT_c$ is determined to be 210 Oe and 150 Oe for $H_{k||c}$ and $H_{k||ab}$, respectively. From this, the superconducting coherence length is estimated via $H_{c2}(0) = \xi_0^{-2} \mu_0^2$, [26] yielding $\xi_0^{ab} = 1477$ Å, and $\xi_0^c = 1250$ Å. Values for the Fermi velocity $v_F^{ab} = 7.1 \times 10^6$ cm/s and $v_F^c = 6.0 \times 10^6$ cm/s are obtained from $\xi_0 = 0.18 \lambda_F = k_B T_c$. Surprisingly, while the absolute value of T_c in zero magnetic field is very similar for the two compounds, the anisotropy (H_{c2}^{ab}/H_{c2}^c) of the upper critical field, which is a factor of 2.1 in $\text{BaN}_{1/2}\text{As}_2$, reverses sign ($H_{c2}^c/H_{c2}^{ab} = 1.4$) in $\text{SrN}_{1/2}\text{As}_2$ and the overall magnitude of the upper critical field is nearly an order of magnitude smaller. The differences in the H_{c2} between the two compounds may be due changes in electronic structure resulting from the structural transition in $\text{BaN}_{1/2}\text{As}_2$ that is not present in $\text{SrN}_{1/2}\text{As}_2$.

The specific heat, plotted as C/T , for $\text{EuN}_{1/2}\text{As}_2$ is shown in Fig. 5 in magnetic fields up to 9 T ($H_{||c}$). A sharp anomaly occurs at the magnetic ordering temperature $T_m = 14$ K (consistent with the kink in $\rho(T)$, Fig. 1), as well as a broader hump at 4 K. A magnetic

eld along the c-axis modestly suppresses the transition, consistent with previous reports of antiferromagnetic ordering in polycrystalline samples.[22, 23] There is no indication of superconductivity above 0.4 K in EuNi_2As_2 .

It is interesting that superconductivity with very similar transition temperatures is found both in BaNi_2As_2 [16] and in SrNi_2As_2 , despite the differences in structural parameters caused by the smaller Sr^{2+} ions, as well as the presence of a first order structural transition in BaNi_2As_2 that is possibly also magnetic. Recent theoretical work by Subedi and coworkers[28] indicate that the superconducting properties of the related Ni-analog LaNiPO may be explained within a conventional electron-phonon approach, yielding a low value of $T_c = 2.6$, consistent with experiment; the authors go on to suggest that the FeAs superconductors may be in a separate class from their Ni-based counterparts. However, a scenario has been put forth by Cvetkovic and Tesanovic[29] involving a multiband Fermi surface in the layered FeAs superconductors to produce the large values of T_c may also be an appropriate description of these ANi_2As_2 superconductors as well. Further work is in progress to elucidate the nature of the superconductivity in these Ni-based materials and its relation to the details of the electronic structure.

In conclusion, specific heat and electrical resistivity measurements on SrNi_2As_2 single crystals reveal bulk superconductivity at 0.62 K, which shows no sign of a structural/magnetic anomaly below 400 K. Magnetic ordering associated with the Eu magnetic moments is observed in single crystalline EuNi_2As_2 . No evidence for superconductivity is observed in this compound above 0.4 K.

Acknowledgments

Work at Los Alamos National Laboratory was performed under the auspices of the U.S. Department of Energy.

[1] D. W. Hess, P. S. Riseborough, and J. L. Smith, in *Encyclopedia of Applied Physics* (VCH, New York, 1993), Vol. 7, p. 435.

[2] Y. Kamihara, T. Watanabe, M. Hirano, H. Hosono, *J. Am. Chem. Soc.* **130**, 3296 (2008).

[3] M. Rotter, M. Tegel, D. Johrendt, *arXiv:0805.4630*, (2008).

- [4] G.F.Chen, Z.Li, G.Li, W.Z.Hu, J.Dong, X.D.Zhang, P.Zheng, N.L.Wang, J.L.Luo, arXiv:0806.1209, (2008).
- [5] K.Sasmal, B.Lv, B.Lorenz, A.Gulby, F.Chen, Y.Xue, C.W.Chu, arXiv:0806.1301, (2008).
- [6] G.Wu, H.Chen, T.Wu, Y.L.Xie, Y.J.Yan, R.H.Liu, X.F.Wang, J.J.Ying, X.H.Chen, arXiv:0806.4279, (2008).
- [7] H.S.Jeevan, Z.Hossain, C.Geibel, P.Gegenwart, arXiv:0807.2530, (2008).
- [8] T.Park, E.Park, H.Lee, T.Klimczuk, E.D.Bauer, F.Ronning, J.D.Thompson, J.Phys. Cond.Matter 20, 322204 (2008).
- [9] M.S.Torikachvili, S.L.Budko, N.Ni, P.C.Canfield, , arXiv:0807.0616 (2008).
- [10] P.L.Alireza, J.Gillet, Y.T.ChrisKo, S.E.Sebastian, G.G.Lonzarich, , arXiv:0807.1896 (2008).
- [11] T.Watanabe, H.Yanagi, T.Kamiya, Y.Kamihara, H.Hiramatsu, M.Hirano, H.Hosono, Inorg.Chem. 46, 7719 (2007).
- [12] T.Mine, H.Yanagi, T.Kamiya, Y.Kamihara, M.Hirano, H.Hosono, Solid State Communications 147, 111 (2008).
- [13] T.Watanabe, H.Yanagi, Y.Kamihara, T.Kamiya, M.Hirano, H.Hosono, J. Solid State Chem., doi:10.1016/j.jssc.2008.04.033 (2008).
- [14] L.Fang, H.Yang, P.Cheng, X.Zhu, G.Mu, H.H.Wen, arXiv:0803.3978, (2008).
- [15] Z.Li, G.F.Chen, J.Dong, G.Li, W.Z.Hu, D.Wu, S.K.Su, P.Zheng, T.Xiang, N.L.Wang, J.L.Luo, arXiv:0803.2572, (2008).
- [16] F.Ronning, N.Kurita, E.D.Bauer, B.L.Scott, T.Park, T.Klimczuk, R.Movshovich, J.D.Thompson, J.Phys.: Cond.Matter 20, 342203 (2008).
- [17] Y.Kamihara, H.Hiramatsu, M.Hirano, R.Kawamura, H.Yanagi, T.Kamiya, H.Hosono, J. Am.Chem.Soc. 128, 10012 (2006).
- [18] A.Mewis, A.Distler, Z.Naturforsch.B:Chem.Sci 35, 391 (1980).
- [19] M.Psterer, G.Nagorsen, Z.Naturforsch.B:Chem.Sci 35, 703 (1980).
- [20] M.Psterer, G.Nagorsen, Z.Naturforsch.B:Chem.Sci 38, 811 (1983).
- [21] W.Jeitschko, W.K.Hofmann, L.J.Terbuchte, J.Less Common Met. 137, 133 (1988).
- [22] E.H.ElGhadraoui, J.Y.Pivan, R.Guerin, O.Pena, J.Padiou, M.Sergent, Mater.Res.Bull. 23, 1345 (1988).
- [23] H.Raus, E.Morsen, B.D.Mosel, W.Muller-Warmuth, W.Jeitschko, L.Terbuchte, T.

Vomhof, J. Phys. Chem. Solids. 54, 135 (1993).

[24] Due to the small size of the heat capacity signal, we are unable to properly subtract the addenda. This is particularly evident at high temperatures, where we do not recover the Dulong-Petit value. We believe this is also responsible for the shift of approximately 1 mJ/mol K^2 at low temperatures and a magnetic field of 1 T .

[25] N.R. Werthamer, E. Helfand, P.C. Hohenberg, Phys. Rev. 147, 295 (1966).

[26] See, for example, M. Tinkham, Introduction to Superconductivity, (McGraw-Hill, New York, 1975).

[27] M. Bouvier, P. Lethuillier, D. Schm itt, Phys. Rev. B 43, 13137 (1991).

[28] A. Subedi and D. J. Singh and M. H. Du, arXiv:0806.3875, (2008).

[29] V. Cvetkovic and Z. Tesanovic, arXiv:0804.4678, (2008).

Figures

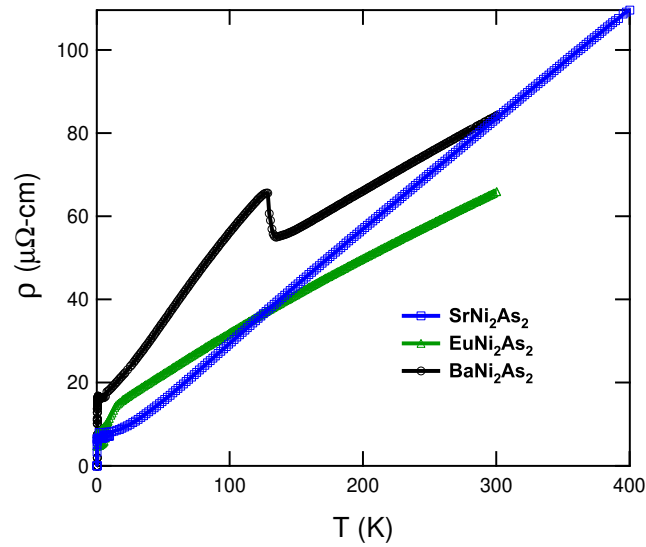


FIG. 1: (color online) In-plane electrical resistivity $\rho(T)$ (K Ω) for selected ANi_2As_2 ($A = \text{Ba}, \text{Sr}, \text{Eu}$) compounds.

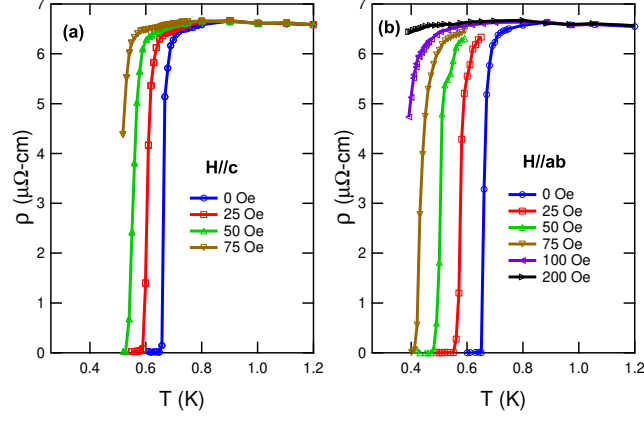


FIG. 2: (color online) Electrical resistivity $\rho(T)$ of SrNi_2As_2 showing the superconducting transition for $H \parallel c$ (a) and $H \parallel ab$ (b). The current was maintained perpendicular to the magnetic field.

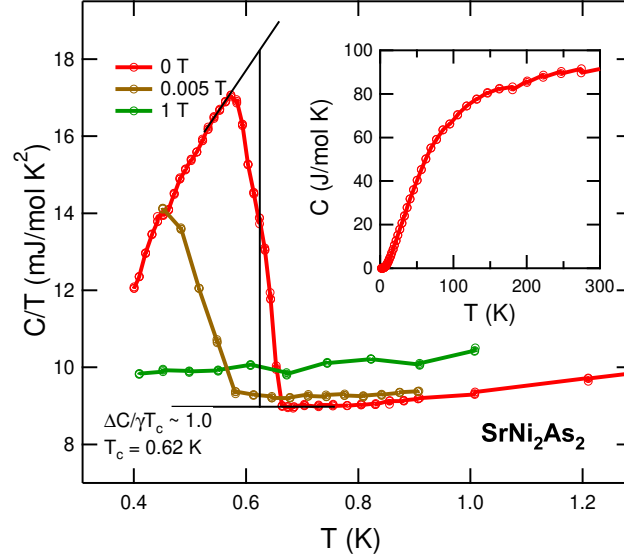


FIG. 3: (color online) Low temperature specific heat C versus temperature T of SrNi_2As_2 [24] for various magnetic fields ($H \parallel c$). The inset displays the high temperature heat capacity with no indication of a first order phase transition at higher temperatures.

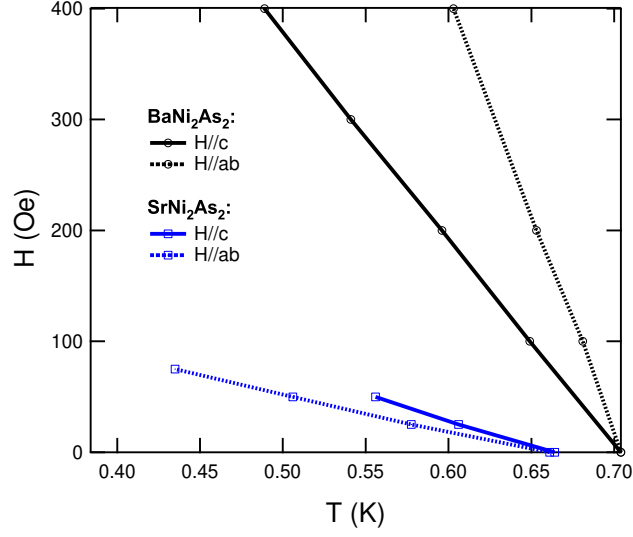


FIG. 4: (color online) Magnetic field-temperature H - T phase diagram of SrNi_2As_2 . The upper critical field H_{c2} for $H \parallel \hat{c}$ and $H \parallel \hat{ab}$ was determined by the resistive midpoint in Fig. 2 (a) and (b). The data for BaNi_2As_2 from Ref. 16 is for the zero resistance state.

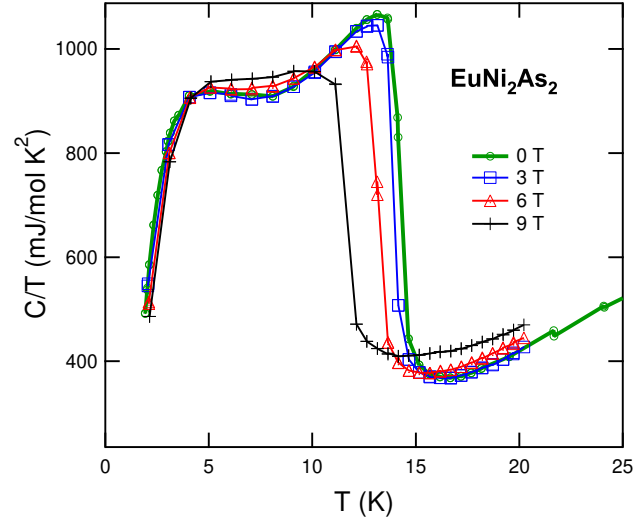


FIG. 5: (color online) Heat capacity data versus temperature for EuNi_2As_2 in zero and applied magnetic field [24]. The magnetic field was applied along the c -axis.