

Quantification of the Heterogeneity of Particle Packings

Iwan Schenker, Frank T. Filser, and Ludwig J. Gauckler

Nonmetallic Materials, Department of Materials, ETH Zurich, Zurich CH-8093, Switzerland

Tomaso Aste

Department of Applied Mathematics, RSPHysSE,
The Australian National University, 0200 Australia
and

School of Physical Sciences, University of Kent,
Canterbury, Kent, CT2 7NH, United Kingdom

Hans J. Herrmann

Computational Physics for Engineering Materials,
Institute for Building Materials, ETH Zurich, Zurich CH-8093, Switzerland

The microstructure of coagulated colloidal particles, for which the inter-particle potential is described by the DLVO theory, is strongly influenced by the particles' surface potential. Depending on its value, the resulting microstructures are either more "homogeneous" or more "heterogeneous", at equal volume fractions. An adequate quantification of a structure's degree of heterogeneity (DOH) however does not yet exist. In this work, methods to quantify and thus classify the DOH of microstructures are investigated and compared. Three methods are evaluated using particle packings generated by Brownian dynamics simulations: (1) the pore size distribution, (2) the density fluctuation method and (3) the Voronoi volume distribution. Each method provides a scalar measure, either via a parameter in a fit function or an integral, which correlates with the heterogeneity of the microstructure and which thus allows for the first time to quantitatively capture the DOH of a granular material. An analysis of the differences in the density fluctuations between two structures additionally allows for a detailed determination of the length scale on which differences in heterogeneity are most pronounced.

PACS numbers: 81.05.Rm, 61.43.-j, 82.70.Gg

I. INTRODUCTION

Colloidal particle packings are suitable model systems for the study of the structural properties of granular materials below the random loose packing limit. For such systems the gravitational force is negligible in comparison to the van der Waals force, electrostatic repulsion or Brownian motion [1, 2]. In the present study, we particularly focus on systems, for which the local arrangement of the particles is the only variable, as opposed to variations in the volume fraction or the particle size distribution for example. Commonly, these microstructures are referred to as "more homogeneous" or "more heterogeneous", which either designates a structure presenting a rather uniform distribution of the particle positions or one having locally denser regions and therefore larger voids. These qualitative terms may be intuitive, however, they do not allow for a sound scientific quantification of the structure's degree of heterogeneity (DOH), which does not yet exist. In this paper, three methods providing the means for such a quantification are presented, analyzed and compared. These methods permit for the first time to explicitly capture the DOH of a par-

ticle packing in form of a quantitative, scalar measure.

Experimentally, the reproducible generation of colloidal particle packings possessing a specific DOH is achieved by the use of an in-situ enzyme-catalyzed destabilization method (Direct Coagulation Casting (DCC), [3, 4]). For volume fractions between 0.2 and 0.6, DCC allows for the coagulation of electrostatically stabilized colloidal suspensions to stable particle structures by either shifting the pH of the suspension to the particles' isoelectric point or by increasing the ionic strength of the suspension without disturbing the particle system. Shifting the pH leads to "more homogeneous" microstructure through diffusion limited aggregation while increasing the ionic strength results in "more heterogeneous" microstructures via reaction rate limited aggregation. The differences in heterogeneity have been observed using various techniques such as diffusing wave spectroscopy [5], static light transmission [5] or cryogenic scanning electron microscopy [6].

Computationally, microstructures with different DOH were successfully reproduced using Brownian dynamics simulations (BD) [6, 7, 8]. Slices of three particle layer thickness through a "homogeneous" and a "heterogeneous" BD-microstructure of identical volume fraction nicely demonstrate the differences between the microstructures (Fig. 1). The microstructure on the left presents a rather uniform distribution of the particle po-

Electronic address: iwan.schenker@alum.niethz.ch

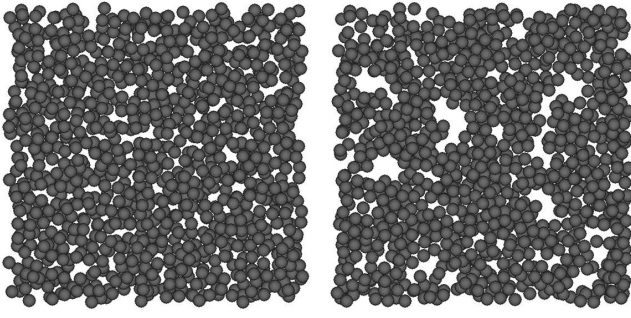


FIG. 1: Slices through a "homogeneous" (left) and a "heterogeneous" (right) particle structure with the same volume fraction of 0.4 resulting from Brownian dynamics simulations [7] (slice thickness: three particle diameters; particle diameter: 0.5 μm).

sitions over the whole slice while the microstructure on the right presents locally more densely packed particles and consequently larger voids. Both structures have an identical overall volume fraction of 0.4.

In preceding works, various characterization methods, such as the radial pair correlation function [7], the bond angle distribution function [7], the triangle distribution function [7] and the Minkowski functionals in conjunction with the parallel-body technique [9] were applied to sets of microstructures generated by BD simulations [8].

The pair correlation function quantifies the amount of structural rearrangement during the coagulation. Its usefulness regarding a distinction between structures with different DOH however is rather limited as the differences between peaks corresponding to characteristic particle separation distances are relatively small [7]. The main advantage of the pair correlation function is its experimental accessibility through scattering techniques such as SESANS [10].

The bond angle distribution function and the triangle distribution function give further information on the local building blocks of the particle network [7]. Particular features, as for example peaks in the respective distribution function allow distinguishing between "more homogeneous" and "more heterogeneous" microstructures. However, as in the case of the pair correlation function, the differences between structures with different DOH are small for both, the bond angle and the triangle distribution function.

The analysis using the Minkowski functionals in conjunction with the parallel-body technique supplies additional information on the structure's morphology resolving microstructural differences on a length scale limited by the largest pore size [9]. This method is computationally intensive and the extension to arbitrary particle shapes is difficult.

Gearing towards a possible correlation between microstructure and mechanical properties "homogeneous" and "heterogeneous" microstructures have recently been analyzed in terms of load bearing sub-structures: Firstly,

regions of closely packed particles and secondly, quasi-linear chains of contacting particles [11]. The locally closed packed regions were analyzed using the common neighbor distribution in conjunction with the dihedral angle distribution. Both methods only showed minor differences between a "homogeneous" and a "heterogeneous" microstructure. In particular, practically the same number of triangles and regular tetrahedrons were found in both structures. Quasi-linear arrangements of contacting particles were quantified using the straight path method, revealing significant microstructural differences between "homogeneous" and "heterogeneous": approximately twice as many paths of length longer or equal to four particles and three times as many paths of length longer or equal to five particles were found in the "heterogeneous" microstructure.

Despite the multitude of microstructural characterization methods that have been applied to colloidal microstructures possessing various DOH, a useful quantification of the microstructures' heterogeneity in form of a scalar measure is lacking. In the present study statistical measures allowing for a quantification of a structure's heterogeneity are provided. The following three methods aiming at this quantification are discussed.

Firstly, the exclusion probability [12] estimates the pore size distribution by randomly probing the pore space. In [13] this method was applied to very dilute simulated colloidal systems and allowed for a clear distinction between particle gel networks with varying textures. The same method, termed spherical contact distribution function [14], was used to investigate the pore size distribution of dense sphere packings as a function of the particle size distribution and the packing generation algorithm.

Secondly, the density fluctuation method considers the fixed particle centers as a point process, and it statistically analyses the fluctuations of the particle center density as a function of length scale. Used comparatively, this method further allows for a detailed analysis of the length scale, on which two structures present the largest differences in terms of heterogeneity.

Finally, the Voronoi volume distribution [15] is used to quantify the distribution of the free volume of our particle packings. In [16] the packing of cohesive particles resulting from simulations using the discrete element method [17] with volume fractions between approximately 0.2 and 0.6 was analyzed. The distribution of Voronoi volumes was shown to broaden with decreasing volume fraction. In [18] the Voronoi volume distribution was determined for a large set of experimental and numerical data covering a wide range of volume fractions. The various distributions were shown to follow a so-called k-gamma function, which was deduced by means of a statistical mechanics approach. The parameter k characterizing the shape of the curve was found to depend very sensitively on the structural organization of the particles.

To the authors' knowledge, none of these methods have yet been applied to particle structures, for which the

TABLE I: DLVO Potential Parameters.

Parameter	Symbol	Value
Hamaker constant of Al_2O_3 in H_2O	A_H	$4.76 \cdot 10^{-20} \text{ J}$
Particle diameter	d_0	$5 \cdot 10^{-7} \text{ m}$
Relative dielectric constant of H_2O	ϵ_r	81
Surface potential	ϕ_0	$0 - 15 \text{ mV}$
Absolute temperature	T	293 K
Valency of ions	z	1
Inverse Debye screening length		10^8 m^{-1}

DOH is the only variable, in opposition to a varying volume fraction or particle size distribution for example.

II. MATERIALS AND METHODS

In the following, the structure characterization methods employed in this work are presented: the pore size distribution, the density fluctuation method and the distribution of Voronoi volumes. These methods are evaluated in terms of their ability to quantify the DOH of microstructures generated by previous BD simulations [7, 8]. In these simulations, the DLVO theory [19] was used to describe the inter-particle potential V^{dlvo} given by the sum of an attractive van der Waals term V^{vdw} (Eq. 1) and an electrostatic repulsion term V^{el} (Eq. 2). Thus, $V^{\text{dlvo}} = V^{\text{vdw}} + V^{\text{el}}$ with,

$$V^{\text{vdw}}(r) = \frac{A_H}{12} \left[\frac{d_0^2}{r^2} - \frac{d_0^2}{r^2} + \frac{d_0^2}{r^2} + 2 \ln \frac{r^2}{r^2} \right] \quad (1)$$

and

$$V^{\text{el}}(r) = \frac{4k_b T}{ze} \tanh \left(\frac{ze}{4k_b T} \phi_0 \right) \frac{1}{d_0 \exp(-\kappa(r - d_0))} \quad (2)$$

respectively. The DLVO parameters are summarized in Table I.

The heterogeneity of the final microstructure was shown to be closely related to the presence and depth of the secondary minimum in the inter-particle potential, which, for fixed values of the Debye screening length, essentially depends on the particles' surface potential ϕ_0 [7, 20].

The microstructures analyzed in this work are labelled according to the surface potential ϕ_0 used during their generation. In particular, the following ϕ_0 -values are used: 0 mV, 12 mV, 13 mV, 14 mV and 15 mV. Additionally, these final microstructures are compared to the initial microstructure, representing a stabilized suspension in which the inter-particle potential is purely repulsive. The volume fraction is fixed at 0.4, the monosized particles have a radius $r_0 = 0.25 \text{ } \mu\text{m}$, all microstructures

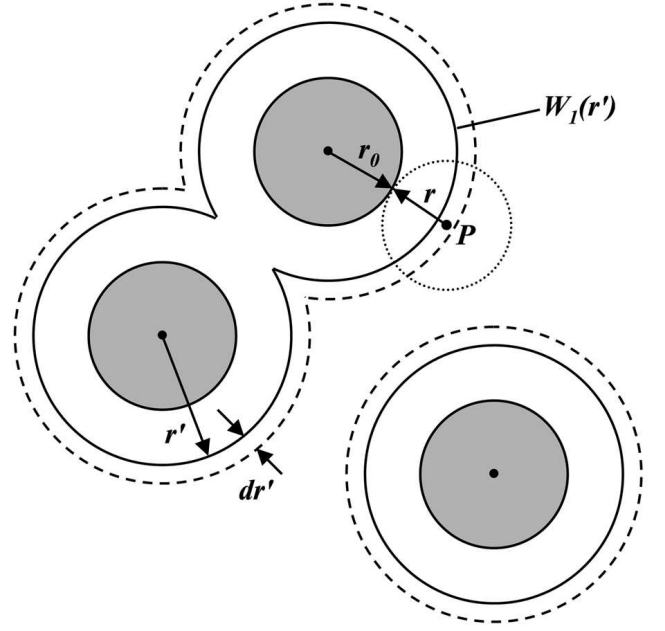


FIG. 2: Particle structure (gray particles) with a test particle inserted at position P.

consist of 8000 particles and are contained in a simulation box with periodic boundary conditions. In particular, the particle interpenetration is much smaller than the length scale of the heterogeneities analyzed in this study. Less than 0.1% of all contacts present an interpenetration above 1.0% of the particle diameter d_0 with a maximum interpenetration of 1.3% d_0 . Please refer to [7, 8] for a more detailed description of the BD-simulations.

A. Pore Size Distribution

The pore size distribution is estimated following the approach described by Torquato et al. [12] using the exclusion probability $E_V(r)$. $E_V(r)$ is defined as the probability of inserting a "test" particle of radius r at some arbitrary position in the pore space of a system of N particles. This is schematically represented in Fig. 2 using a set of particles of radius r_0 (gray) with a test particle of radius r inserted at position P.

In order to estimate $E_V(r)$, a statistically large number of points is randomly placed in the pore space of a given microstructure and the distance to the closest particle surface is determined.

In [9] the relation between $E_V(r)$ and the Minkowski functional $W_1(r)$ was described. The Minkowski functional in conjunction with the parallel body technique considers the point process given by the fixed particle centers. Generally, in three dimensions there are four functionals W_i , where $i = 0, \dots, 3$ with d the spatial dimension, corresponding to the volume, surface, average mean curvatures and connectivity. In particular,

$W_1(r^0) = \frac{1}{3} \int_{\partial A(r^0)} dS$ calculates the surface of the union of spheres located at the particle centers in dependence of their radius $r^0 = r_0 + r$. Schematically, $W_1(r^0)$ is shown in Fig. 2. $W_1(r^0)dr^0$ is the volume between the distance r^0 and $r^0 + dr^0$. The probability of placing an uniformly drawn random test point at a distance $r \in [r^0; r^0 + dr^0]$ is proportional to the volume delimited by r^0 and $r^0 + dr^0$ and therefore $P(r^0 \leq r_0 + r < r^0 + dr^0) = E_V(r)dr^0 / W_1(r^0)dr^0$, which results in $E_V(r_0 + r) / W_1(r^0)$. Thus, given a statistically large number of test points $E_V(r)$ provides a means to estimate $W_1(r^0)$, which has the advantage of being computationally less intensive. A similar Monte Carlo integration is usually performed to calculate $W_0(r^0)$.

B. Density Fluctuations

The density fluctuation method quantifies the local fluctuation of particle centers by subdividing the structure into smaller parts and measuring the average value and the standard deviation of the particle center density. Practically, this is done by dividing the structure into n_c^3 cells using a cubic grid, where n_c is the number of cells along one dimension with $n_c = 2, \dots, n_c^{\max}$, n_c^{\max} being the maximum number of cells under consideration (along one dimension). The density fluctuation method consists in determining the average number of particle centers per cell E_{ppc} and its standard deviation σ_{ppc} as a function of n_c and then calculating the relative fluctuations $\frac{\sigma_{ppc}}{E_{ppc}}$.

Additionally, the density fluctuation method is applied comparatively allowing for a determination of the length scale on which two structures show the largest differences. Therefore, the difference (n_c) given in Eq. (3) is calculated between two structures i and j .

$$(n_c) = \frac{\frac{i}{ppc}}{E_{ppc}^i} - \frac{\frac{j}{ppc}}{E_{ppc}^j} (n_c) \quad (3)$$

If both structures have the same number of particles and identical volume fractions, which is the case for the microstructures investigated in this work, then $E_{ppc}^i = E_{ppc}^j = E_{ppc}$ and Eq. (3) yields Eq. (4).

$$(n_c) = \frac{\frac{i}{ppc}}{E_{ppc}} - \frac{\frac{j}{ppc}}{E_{ppc}} (n_c) \quad (4)$$

is plotted against the cell's edge length $l_c(n_c) = L_{Box}/n_c$ normalized by the particle diameter d_0 , where L_{Box} is the side length of the cubic simulation box.

C. Voronoi Volume Distribution

Formally, for a set of monodispersed spherical particles, the Voronoi volume V_i associated with a particle i

is a polyhedron whose interior consists of all points in space that are closer to the center of particle i than to any other particle center [15]. The Voronoi tessellation thus divides the volume containing a set of particles into a set of space-filling, non-overlapping and convex polyhedrons. In this work, the Quickhull algorithm [21] is used to compute the volumes of the Voronoi polyhedrons. The distribution of the Voronoi volumes describes the deviation of a structure from a perfect crystalline packing, in which case all particles occupy the same volume and the Voronoi volume distribution thus is a delta function. The minimum volume of a Voronoi cell V_{min} is achieved for a regular close packing with $V_{min} = 1.325V_{sphere}$, where V_{sphere} is the volume of a particle. The difference between a particle's Voronoi volume V_i and V_{min} is termed the Voronoi free volume $V_i^f = V_i - V_{min}$.

The distribution of the Voronoi free volume was found to follow gamma-distributions: Kumar and Kumaran for example have shown that the free volume distribution of hard-disk and hard-sphere systems are well described using a two-parameter and a three-parameter gamma-distributions [22].

Aste et al. have deduced the two-parameter gamma-distribution using a statistical mechanics approach [18]. The so-called k -gamma distribution given by Eq. (5) was found to agree very well with a large number of experiments and computer simulations over a wide range of packing fractions.

$$f(V^f; k) = \frac{k^k}{\Gamma(k)} \frac{(V^f)^{k-1}}{(V^f)^k} \exp\left(-k \frac{V^f}{V}\right) \quad (5)$$

The mean Voronoi free volume V^f is a scaling parameter given by $V - V_{min} = (1 - 1.325)V_{sphere}$, where is the volume fraction. The free parameter k characterizing the shape of the curve depends very sensitively on the structural organization of the particles and corresponds to the specific heat in classical thermodynamics. Empirically, k can be computed using $k = \frac{(V^f)^2}{V}$, where $\frac{2}{V}$ is the variance of the free volume distribution. In particular, Eq. (5) was shown to hold for systems at statistical equilibrium as well as for systems out of equilibrium [18].

III. RESULTS AND DISCUSSION

A. Pore Size Distribution

The pore size distribution of the various microstructures is depicted in Fig. 3 in terms of the exclusion probability $E_V(r_p)$ as a function of the pore radius r_p normalized by the particle radius r_0 . A set of 10^6 random test points [23] placed in the structures' pore space was used to estimate $E_V(r_p)$.

All curves for the nanomicrostructures ($\phi = 0 - 15 \text{ mV}$) decrease monotonically towards increasing pore sizes indicating a decreasing probability of finding larger

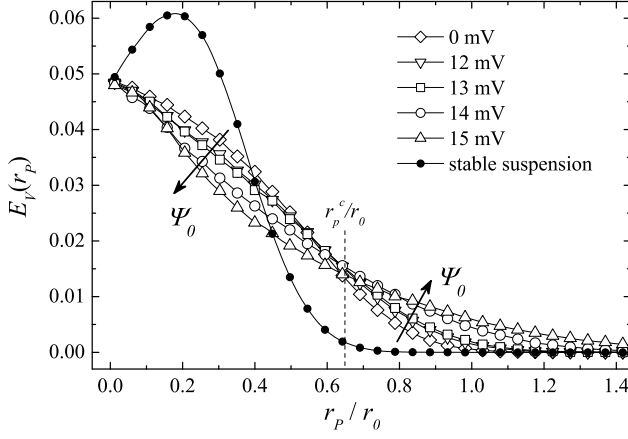


FIG. 3: Pore size distribution for the initial microstructure (stable suspension) and natural microstructures ($\psi_0 = 0 - 15$ mV). B-spline curves serve as guide to the eye.

pores. A particular behavior is found for the stable suspension where the exclusion probability increases with increasing pore size up to a pore radius of $0.18r_0$. This is due to the repulsive inter-particle potential in the case of the stable suspension where consequently, the particles are not in contact. The pore diameter, at which the maximum in the exclusion probability is found, corresponds to the average surface-to-surface distance between neighboring particles.

Remarkably, the various curves for the natural microstructures in Fig. 3 intersect at approximately the same point defining a characteristic pore size r_p^c , found at $0.65r_0$. The probability of finding a pore with a radius below r_p^c decreases for increasing values of ψ_0 while pores with a radius above r_p^c are found with higher probability towards increasing ψ_0 . Indeed, the probability of finding pore radii larger than approximately $1.1r_0$ is negligible in the case of the "most homogeneous" microstructure with $\psi_0 = 0$ mV while pore radii up to $2.4r_0$ are found in the "most heterogeneous" microstructure with $\psi_0 = 15$ mV.

Using the results obtained for the exclusion probability $E_V(r_p)$, the cumulative probability $P(r_p > r)$ of finding pore radii larger than r was calculated using $P(r_p > r) = \int_{r_0 > r_p} E_V(r_0^0)$. The results are shown in Fig. 4.

$P(r_p > r)$ decreases monotonically for all microstructures. The fastest decrease is found for the stable suspension. With increasing ψ_0 the decrease of $P(r_p > r)$ is slower. Comparing the "most and the least heterogeneous" microstructure, with $\psi_0 = 15$ mV and $\psi_0 = 0$ mV, respectively, there is a 1.7 times higher probability of finding pores larger than $0.5r_0$. Towards larger pore radii, the probability ratio increases: finding pores with a radius larger than $0.75r_0$ and $1.0r_0$ is 5.1 times and 60 times, respectively, more probable in the "heterogeneous" than in the "homogeneous" microstructure. Fig. 4 further shows the fit of $P(r_p > r)$ using a complementary error function given by Eq. (6).

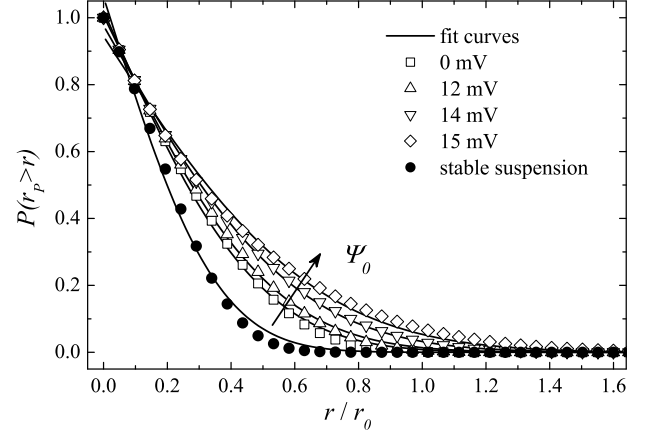


FIG. 4: Probability of finding pores with a radius r_p larger than r vs. r normalized by the particle radius r_0 for the various microstructures (symbols) and corresponding fits using a complementary error function (solid lines).

$$P(r_p > r) = 1 - \text{erf} \left(\frac{r - r_0}{a} \sqrt{\frac{b}{2}} \right) \quad (6)$$

The error function is defined as the cumulative Gaussian distribution: $\text{erf}(x) = \frac{2}{\sqrt{\pi}} \int_0^x \exp(-z^2) dz$. Parameter a is the standard deviation, i.e. the width of the corresponding Gaussian distribution and b is the location of its maximum, i.e. the most probable pore to particle radius ratio.

Table II summarizes the fit parameters a and b obtained for the various microstructures analyzed in this work and the corresponding correlation coefficients R^2 , which for all fits are very close to 1 and thus indicate a good fit. Parameter a is smallest for the initial microstructure and increases towards increasing values of ψ_0 . The increasing values of a reflect the slower decrease of the curves in Fig. 4 and hence the broadening of the distributions towards increasing DOH. The values found for b decrease with increasing ψ_0 representing a shift of the maximum in the Gaussian distribution shown in Fig. 3.

In [12] the following expression for $E_V(r)$ was found for a statistically homogeneous microstructure of impenetrable spheres: $E_V(r) = (1 - \phi) \exp(P_3(r; \phi))$, where

ϕ is the volume fraction and P_3 is a third degree polynomial function in r . This function can be interpreted as a corrected Gaussian distribution which is nicely approximated by Eq. (6) as well ($R^2 = 0.9962$), yielding $a = 0.347$ and $b = 0.0204$. The DOH of this theoretical structure thus lies between the stable suspension and the most homogeneous natural microstructure with $\psi_0 = 0$ mV.

An alternative to the quantification of a structure's heterogeneity by means of the fit parameter a is the calculation of the integral over the cumulative pore size distribution. This scalar measure has the advantage of being statistically more robust. It is also more general in the

TABLE II: Fit parameters a and b , R^2 -values and integrals I_{ps} and I_{df} for the various microstructures.

	a	$b (10^{-2})$	R^2	I_{ps}	I_{df}
stable suspension	0.2651	2.042	0.9952	0.215	20.29
$\phi_0 = 0$ mV	0.3752	0.9013	0.9987	0.291	22.01
$\phi_0 = 12$ mV	0.4053	0.3136	0.9994	0.311	22.31
$\phi_0 = 13$ mV	0.4127	0.1225	0.9996	0.315	22.44
$\phi_0 = 14$ mV	0.4736	-1.415	0.9996	0.352	23.05
$\phi_0 = 15$ mV	0.5377	-3.756	0.9972	0.388	23.71

sense that it is applicable even when the fit with a complementary error function does not yield good results. The integral over the cumulative pore size distribution is labelled I_{ps} and is given by Eq. (7):

$$I_{ps} = \int_{r_0}^{\infty} P(r_p > r) \frac{dr}{r_0} = \frac{r}{r_0} \int_{r_1}^{\infty} P(r_p > r_1) \quad (7)$$

The second equality accounts for the discrete case, where r is the radial resolution of the empirical pore size distribution. The I_{ps} -values for the various microstructures are summarized in Table II. In our case, in which the data can nicely be fitted using Eq. (6), the fit parameter a is proportional to I_{ps} : $a = I_{ps} = 1.31 \pm 0.05$. Thus, a quantification of the DOH by means of a or I_{ps} is equivalent.

B. Density Fluctuations

The density fluctuations for the various microstructures are shown in Fig. 5. Over the whole range of grid spacings, the fluctuations are smallest for the stable suspension and increase for increasing values ϕ_0 . For $n_c = 34$, which corresponds to a grid spacing of 0.64 particle diameter, the density fluctuations of the various microstructures are equal. I_{df} given in Eq. (8) provides an integral measure of the heterogeneity similar to I_{ps} in the previous section, however accounting for the discrete variable n_c .

$$I_{df} = \sum_{n_c < 34}^{\infty} \frac{ppc}{E_{ppc}}(n_c) \quad (8)$$

The I_{df} values for the various microstructures summarized in Table II continuously increase towards increasing values of ϕ_0 and thus measure the DOH of the microstructures.

In the following, two sets of comparisons are performed: Firstly, the various microstructures are compared to the stable suspension. This comparison quantifies the length scale on which structural rearrangements take place during the coagulation. Secondly, the microstructures with $\phi_0 > 0$ mV are compared to the "most homogeneous" microstructure with $\phi_0 = 0$

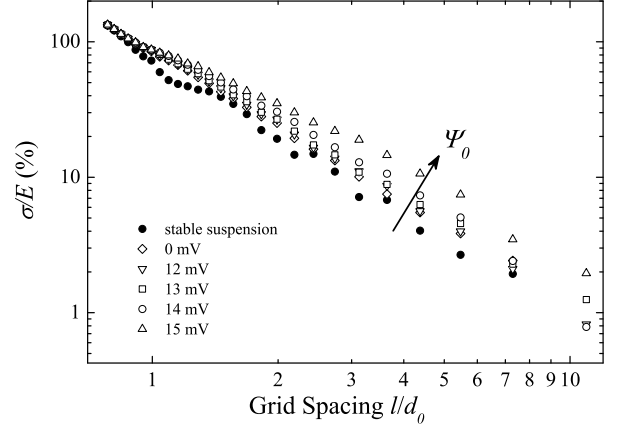


FIG. 5: Relative density fluctuations for the various microstructures and the stable suspension as a function of grid spacing.

mV. This set of comparisons reveals the length scale on which variations in heterogeneity are most pronounced.

The comparison of the various microstructures to the initial, stabilized microstructure is shown in Fig. 6 in terms of (n_c) as given by Eq. (4) where superscripts i and j correspond to a microstructure and to the initial microstructure, respectively. (n_c) is shown as function of the grid spacing l normalized by the particle diameter $d_0 = 2r_0$.

All curves present an identical behavior, which essentially consists of three successive peaks with decreasing height towards a larger grid spacing. The location of the first, second and third peak is slightly above one, at two and at three particle diameters, respectively. The height of the individual peaks increases for increasing values ϕ_0 .

More precisely speaking, the first peak is found at $1.09d_0$ for all microstructures in comparison to the stable suspension. This grid spacing corresponds to a cell number of 8000 and therefore to the case where the average number of particles per cell is exactly one. This case is best reproduced for the stable suspension as for the microstructures the standard deviation is roughly 20 to 27% larger. Physically, this peak is explained by the transition of the inter-particle potential from repulsive to attractive. Indeed, the repulsive potential in the case of the stable suspension causes all particles to occupy approximately the same volume as will be confirmed in Sec. III C by means of the Voronoi volume distribution. The switching of the inter-particle potential from repulsive to attractive causes the particles to form contacts resulting in an average particle separation of one particle diameter, which is smaller than the grid spacing of $1.09d_0$. This increases the probability of finding cells that are either empty or contain more than one particle and thus the standard deviation of the average number of particles per cell is increased.

The peaks at a grid spacing of approximately two and

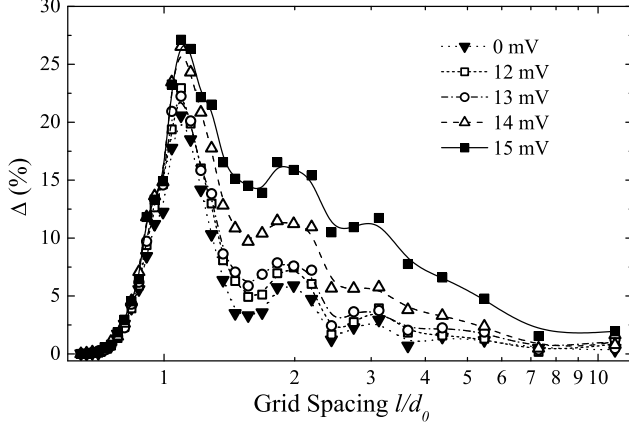


FIG. 6: Relative difference between the density fluctuations of the various nalm microstructures and the stable suspension as a function of grid spacing. B-spline curves serve as guide to the eye.

three particle diameters are considerably less pronounced than the peak at $1.09d_0$. In particular, the differences between the various nalm microstructures are larger than for the first peak. These differences will be elaborated in more detail in the following.

The comparison between the nalm microstructures with $\phi_0 > 0$ mV and the "most homogeneous" microstructure with $\phi_0 = 0$ mV is shown in Fig. 7. Here, superscripts i and j (Eq. (4)) correspond to one of the microstructures with $\phi_0 > 0$ mV and to the microstructure with $\phi_0 = 0$ mV, respectively. Over the whole range of grid spacings, the differences between the density fluctuations increase towards higher values of ϕ_0 . This behavior correlates very well with the increase of porosity for increasing ϕ_0 as already observed in the previous section. Additionally, Fig. 7 reveals that the largest differences in terms of particle density between the "most and least heterogeneous" microstructure ($\phi_0 = 15$ mV and $\phi_0 = 0$ mV, respectively) are found on a length scale between 1.3 and 2.2 particle diameters.

C. Voronoi Volume Distribution

As stated in Sec. II C the distribution of Voronoi volumes $P(v)$ describes the deviation of a given structure from a perfectly crystalline packing, for which $P(v)$ is a delta function and all particles occupy the same volume. For random particle structures $P(v)$ broadens and as will be shown in the following, the width of the distribution can be interpreted as the heterogeneity of a structure.

We've calculated $P(v)$ for the stable suspension and the various nalm microstructures as a function of $v = \frac{V - V_{min}}{V - V_{min}}$, the free volume normalized by the mean free volume (Fig. 8, symbols). The distribution found for the stable suspension is significantly narrower in comparison

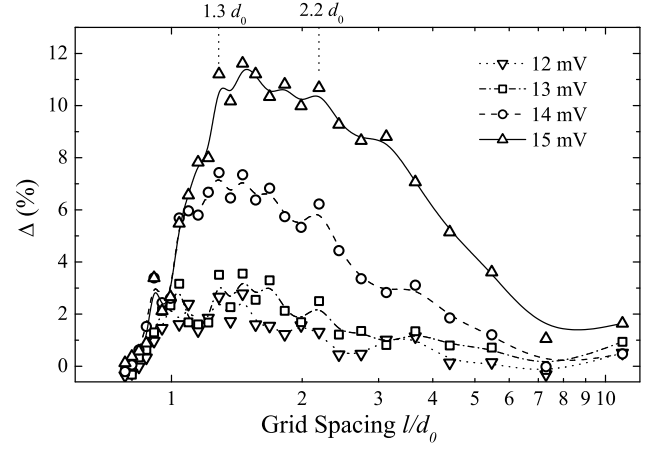


FIG. 7: Relative difference between the density fluctuations of the various microstructures with ($\phi_0 > 0$ mV) and the "most homogeneous" microstructure ($\phi_0 = 0$ mV) as a function of grid spacing. B-spline curves serve as guide to the eye.

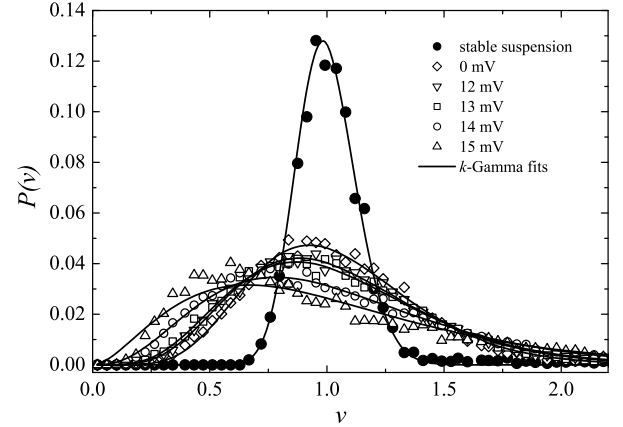


FIG. 8: Voronoi volume distribution $P(v)$ for the various microstructures (symbols) and corresponding fits using the k-gamma distribution (lines).

to the nalm microstructures. In the case of the nalm microstructures, $P(v)$ broadens with increasing value of ϕ_0 indicating that larger fluctuations in Voronoi volumes are found with increasing heterogeneity.

The various microstructures were fitted using the k-Gamma distribution given in Eq. (5). The resulting curves are shown in Fig. 8 (lines) and the corresponding k- and R^2 -values are summarized in Table III. k decreases with increasing heterogeneity and can therefore be used as a measure for the DOH of the microstructures. The R^2 -values close to one indicate good fits. In particular, a very good fit quality was achieved for the stable and the nalm microstructures up to $\phi_0 = 14$ mV. The R^2 -value for the $\phi_0 = 15$ mV microstructure is lower. Indeed, Fig. 8 shows that for the $\phi_0 = 15$ mV microstructure the agreement between the measured distribution and the fit curve for small Voronoi volumes is

TABLE III: k-Gamma results.

	k	R ²
stable suspension	62.3	0.990
$\phi_0 = 0$ mV	8.6	0.995
$\phi_0 = 12$ mV	6.5	0.996
$\phi_0 = 13$ mV	6.0	0.996
$\phi_0 = 14$ mV	4.0	0.994
$\phi_0 = 15$ mV	2.8	0.972

not as good as for the other curves. This might be related to the fact that during the generation of the $\phi_0 = 15$ mV microstructure the energy barrier between primary and secondary minimum in the inter-particle potential was largest. This resulted in a few particle contacts still trapped in the secondary minimum (roughly 7% of the physical contacts). Particles trapped in the secondary minimum have an inter-particle distance of $2.16r_0$ instead of $2r_0$ upon complete coagulation, which may be a reason for the reduced quality towards smaller Voronoi volumes.

IV. SUMMARY AND CONCLUSIONS

In this paper, we have analyzed three distinct microstructural characterization methods. Using these methods, scalar measures were introduced, which for the first time allow quantifying the DOH of particle packings.

The exclusion probability gives an estimate of the pore size distribution by a random probing of the pore space. The "more heterogeneous" microstructures present a considerably broader pore size distribution with a significantly longer tail than the distribution for the "more homogeneous" microstructures. In particular, a continuous broadening is found with increasing heterogeneity. The cumulative exclusion probabilities were shown to follow error functions with parameter a reflecting their width and thus measuring the structures' DOH. Fit parameter a increases with increasing heterogeneity.

The density fluctuation method statistically analyzes the particle center density in dependence of the sampling length scale. The relative density fluctuation as function of the grid spacing presents a clear dependence on the heterogeneity of the microstructure: Over the whole range of grid spacings, the stable suspension exhibits the smallest density fluctuations. These fluctuations increase towards increasing values of ϕ_0 and thus increasing DOH, which is nicely reflected by increasing values of the integral measure I_{df} .

An examination of the differences between the density fluctuations of two structures was found to be particularly useful as it allows determining the

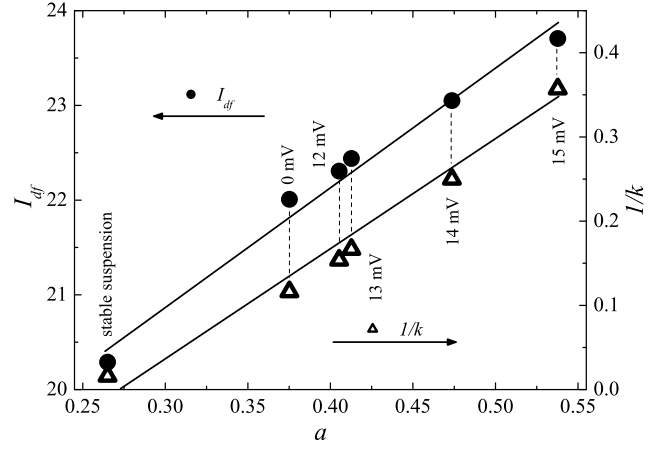


FIG. 9: Interdependence between the measures of the degree of heterogeneity for the various microstructures: I_{df} and l/k as a function of a .

length scale on which the structures present the largest differences in heterogeneity. In the case of the "most heterogeneous" microstructure the largest differences in comparison to the "most homogeneous" one are found on a length scale between 1.3 and 2.2 particle diameters.

The Voronoi volume distribution of the stable suspension is very narrow in comparison to the natural microstructures, for which the distribution broadens with increasing heterogeneity. The various Voronoi volume curves were shown to follow k-gamma distributions. Parameter k , reflecting the width of the distribution and thus the structure's DOH, decreases with increasing heterogeneity.

The behavior of the three parameters a , k and I_{df} is summarized in Fig. 9 showing I_{df} (left scale) and l/k (right scale) as a function of a . The solid lines suggest a pairwise interdependence between I_{df} , l/k and a . Thus, as far as the quantitative characterization of the DOH of the microstructures considered in this work is concerned, all methods, the pore size distribution, the density fluctuation method and the Voronoi volume distribution, can be considered as equivalent in the sense that the knowledge of one parameter permits to determine the others. However, parameter k reflects changes in the DOH more sensitively than a or I_{df} . Indeed, the normalization of k , a and I_{df} with respect to their maximum values reveals that parameter k covers the interval $[0.04; 1.0]$. This interval is significantly larger than the normalized ranges of a and I_{df} , which are $[0.5; 1.0]$ and $[0.86; 1.0]$, respectively.

The interrelation between the three structural characterization methods can be understood as follows: The probability of placing a random point used for the determination of the pore size distribution into the free Voronoi volume of a particle is proportional to the particle's free Voronoi volume. Thus, the broader the distribution of Voronoi volumes, the higher the probability of

inding larger pores, which leads to a longer tail in the exclusion probability as shown in Fig. 3. The relation between the Voronoi volume distribution and the density fluctuation follows similar arguments: A broadening in the Voronoi volume distribution essentially means that there is a broader distribution in the nearest neighbor distances and therefore larger differences in the density fluctuations.

We have applied the methods to a set of monodispersed spherical particle packings representing stable and coagulated colloidal particle structures, but the methods could of course be generalized. The pore size distribution as determined by the Monte Carlo method employed in this work can be applied as it is to any porous media. In this sense, it is the most general method analyzed in this study. The use of an error function however may not necessarily yield good results. In this case the integral measure I_{ps} proposed in Sec. III A could be used or the width of the distribution could be determined empirically. The Voronoi volume distribution generally only requires that the elements constituting a structure are convex and in this case, the empirical distribution can be determined. To the authors' knowledge, the use of the k -gamma distribution has however only been performed in the case of packings of monodispersed, spherical particles. As for the density fluctuation method, we have in this work considered the density of the particle centers. The method may be extended to a determination of the exact portion of the sphere volumes per cell, which however is computationally expensive. An alternative could be a cell-wise Monte Carlo integration of the partial sphere volumes, which would allow for a characterization of arbitrary porous structures using the density fluctuation method.

From an experimental point of view, the methods presented in this study rely on the possibility to determine the particle positions, which in the case of colloidal particles can be obtained using confocal laser microscopy for example [24]. In particular, the pore size distributions measured using mercury porosimetry [25] and estimated using the exclusion probability are not equivalent since the latter overestimates the number of small pores due to the random probing of the pore space.

In this paper, we have introduced three scalar measures, which for the first time allow quantifying and comparing the heterogeneity of packings of spherical particles in terms of a DOH. These measures were calculated using distinct techniques and structural characterization methods. In view of these differences, the very nice correlation between the three DOH measures is remarkable. Indeed, it suggests that the DOH is a microstructure's inherent property and that any of the methods proposed in this work can be used to uniquely characterize and classify it. In terms of sensitivity however, considerable differences between the methods were found. Parameter k reflects differences in the DOH most sensitively, followed by parameter a and finally I_{df} . A further definition of an absolute DOH would require a suitable reference struc-

ture, which for example is either perfectly heterogeneous or perfectly homogeneous under the condition of being random.

Acknowledgments

The authors would like to express their gratitude to Markus Hutter for providing the colloidal microstructure data from the Brownian dynamics simulations. Additionally, Iwan Schenker would like to thank Henning Galinski and Joakim Reuteler for helpful discussions.

-
- [1] J. Visser, *Powder Technol.* 58, 1 (1989).
 - [2] J. N. Israelachvili, *Intermolecular & Surface Forces* (Academic Press, London, 1991), 2nd ed.
 - [3] L. J. Gauckler, T. Graule, and F. Baader, *Mater. Chem. Phys.* 61, 78 (1999).
 - [4] E. Tervoort, T. A. Tervoort, and L. J. Gauckler, *J. Am. Ceram. Soc.* 87, 1530 (2004).
 - [5] H. M. W. Yss, S. Romer, F. Scheold, P. Schurtenberger, and L. J. Gauckler, *J. Colloid Interface Sci.* 241, 89 (2001).
 - [6] H. M. W. Yss, M. Hutter, M. Müller, L. P. Meier, and L. J. Gauckler, *J. Colloid Interface Sci.* 248, 340 (2002).
 - [7] M. Hutter, *J. Colloid Interface Sci.* 231, 337 (2000).
 - [8] M. Hutter, *Brownian Dynamics Simulation of Stable and of Coagulating Colloids in Aqueous Suspension* (Ph.D. thesis no. 13107, ETH Zurich, Switzerland, 1999).
 - [9] M. Hutter, *Phys. Rev. E* 68, 031404 (2003).
 - [10] R. Andersson, L. F. van Heijkamp, I. M. de Schepper, and W. G. Bouwman, *J. Appl. Cryst.* 41, 868 (2008).
 - [11] I. Schenker, F. T. Filser, T. Aste, and L. J. Gauckler, *J. Eur. Ceram. Soc.* 28, 1443 (2008).
 - [12] S. Torquato, B. Lu, and J. Rubinstein, *Phys. Rev. A* 41, 2059 (1990).
 - [13] M. W. Hittle and E. Dickinson, *Mol. Phys.* 96, 259 (1999).
 - [14] A. Bezrukov, M. Bargiel, and D. Stoyan, *Part. Part. Syst. Charact.* 19, 111 (2002).
 - [15] G. Voronoi, *J. reine angew. Math.* 134, 198 (1908).
 - [16] R. Y. Yang, R. P. Zou, and A. B. Yu, *Phys. Rev. E* 65, 041302 (2002).
 - [17] P. A. Cundall and O. D. L. Strack, *Geotechnique* 29, 47 (1979).
 - [18] T. Aste and T. Di Matteo, *Phys. Rev. E* 77, 021309 (2008).
 - [19] W. B. Russel, D. A. Saville, and W. R. Schowalter, *Colloidal Dispersions* (Cambridge University Press, March 1989).
 - [20] H. M. W. Yss, A. M. Delormani, E. Tervoort, and L. J. Gauckler, *AIChE J.* 51, 134 (2005).
 - [21] C. B. Barber, D. P. Dobkin, and H. Huhdanpaa, *ACM Trans. Math. Software* 22, 469 (1996).
 - [22] V. S. Kumar and V. Kumaran, *J. Chem. Phys.* 123, 114501 (2005).
 - [23] M. Matsumoto and T. Nishimura, *ACM Transactions on Modeling and Computer Simulation* 8, 3 (1998).
 - [24] J. C. Crocker and D. G. Grier, *J. Colloid Interface Sci.* 179, 298 (1996).
 - [25] H. Giesche, *Part. Part. Syst. Charact.* 23, 919 (2006).