

# Metal-insulator transition in $\text{Sr}_{2-x}\text{La}_x\text{CoO}_4$ driven by spin-state transition

Hua Wu\*

Laboratory for Computational Physical Sciences (MOE), State Key Laboratory of Surface Physics, and Department of Physics, Fudan University, Shanghai 200433, China

(Dated: today)

We sought the origin of the metal-insulator transition in  $\text{Sr}_{2-x}\text{La}_x\text{CoO}_4$ , using electron-correlation corrected density functional calculations. Our results show that  $\text{Sr}_2\text{CoO}_4$  is in an intermediate-spin (IS,  $t_{2g}^4 e_g^1$ ) state and a strong  $\text{Co}^{4+}$   $3d$ - $\text{O}$   $2p$  hybridization is responsible for its ferromagnetic metallicity. Upon La doping, however, a spin-state transition occurs in  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$ :  $\text{IS Co}^{4+} \times 2 + 1e \rightarrow \text{LS Co}^{4+} (t_{2g}^5) + \text{HS Co}^{3+} (t_{2g}^4 e_g^2)$  (LS: low spin; HS: high spin). Then the spin-state transition suppresses an electron hopping via a spin-blockade and gives rise to the insulating behavior of  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$ . A corresponding superexchange accounts for its ferromagnetism. Thus, spin state could provide a way to tune materials properties.

PACS numbers: 71.30.+h, 75.30.-m, 71.20.-b, 71.70.-d

## I. INTRODUCTION

It is quite common that a ferromagnetic (FM) material is metallic but an antiferromagnetic one is insulating (or semiconducting). Therefore, either a FM insulator or an antiferromagnetic metal seems to be an exception and would be of interest. In electron-correlated transition-metal oxides, charge, spin, orbital, and lattice degrees of freedom often couple to one another and result in abundant electronic and magnetic properties.<sup>1</sup> As a result, exceptions from the above ‘rule’ emerge more than rarely.<sup>2</sup> In this work, we will study such an exception — the FM semiconducting cobaltate  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$ , and the end material of the  $\text{Sr}_{2-x}\text{La}_x\text{CoO}_4$  series,  $\text{Sr}_2\text{CoO}_4$  for a comparison.

$\text{Sr}_{2-x}\text{La}_x\text{CoO}_4$  is a group of interesting materials, which has the  $\text{K}_2\text{NiF}_4$ -type layered structure.  $\text{Sr}_2\text{CoO}_4$  is a FM metal,<sup>3,4</sup> and it could even be a half metal.<sup>5</sup> Upon La doping ( $x=0.5$ ),  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$  turns semiconducting but remains FM.<sup>6,7</sup> With La doping up to  $x=1$ ,  $\text{SrLaCoO}_4$  becomes a paramagnetic insulator.<sup>6-8</sup> It is well known that cobaltates often have a spin-state issue. The spin state depends on Hund exchange, crystal field, and band hybridization, and it has a strong impact on the magnetic and electronic properties of cobaltates. It is this spin-state issue that has brought about a lot of debates in literature. Partially because of this,  $\text{Sr}_{2-x}\text{La}_x\text{CoO}_4$  draw much attention very recently.<sup>9-17</sup>

In this work, using generalized gradient approximation plus Hubbard  $U$  (GGA+ $U$ )<sup>18</sup> calculations, we seek the origin of the metal-insulator transition induced by La doping in  $\text{Sr}_2\text{CoO}_4$ , and pay attention to the FM semiconducting behavior of  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$ . In Fig. 1, we sketch the Co  $3d$  crystal-field levels in  $\text{Sr}_{2-x}\text{La}_x\text{CoO}_4$  with a  $c$ -axis elongated  $\text{CoO}_6$  octahedron. The electronic configurations are shown for an intermediate-spin (IS) state [Fig. 1(a)] and for a low-spin (LS) state [Fig. 1(c)] both relevant to a high-valent  $\text{Co}^{4+}$  ion. Our following GGA+ $U$  calculations find that  $\text{Co}^{4+}$  in  $\text{Sr}_2\text{CoO}_4$  favors the IS state, though somewhat modified compared to Fig. 1(a) due to hybridization effects and on-

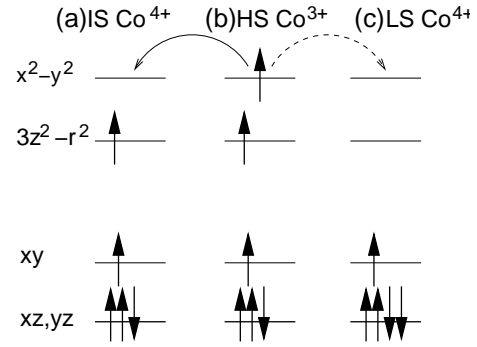


FIG. 1: Electronic configuration of (a) the IS and (c) LS state of a  $\text{Co}^{4+}$  ion in a  $c$ -axis elongated  $\text{CoO}_6$  octahedron (a tetragonal crystal field), and of (b) the HS state of a  $\text{Co}^{3+}$  ion. While the  $x^2-y^2$  electron would readily hop from the HS  $\text{Co}^{3+}$  to IS  $\text{Co}^{4+}$  via Zener’s double exchange, a hopping from the HS  $\text{Co}^{3+}$  to LS  $\text{Co}^{4+}$  is suppressed by a spin blockade. See more in the main text.

site Coulomb interactions, and that a strong Co  $3d$ - $\text{O}$   $2p$  hybridization results in FM metallicity of the compound. In Fig. 1(b), we show a high-spin (HS) state for a  $\text{Co}^{3+}$ , which emerges upon La doping. Here the  $\text{Co}^{3+}$  HS state is conceived, based not only on our very recent work about  $\text{SrLaCoO}_4$ ,<sup>8</sup> but also on a crystal-field scenario (see below). As  $\text{SrLaCoO}_4$  has a  $\text{Co}^{3+}$  HS-LS mixed state,<sup>8,19</sup> less La-doping in  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$  will most probably change the LS  $\text{Co}^{3+}$  into a LS  $\text{Co}^{4+}$  and leave the HS  $\text{Co}^{3+}$  unchanged, in order to maximize Hund exchange. Then  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$  would have the HS  $\text{Co}^{3+}$  and LS  $\text{Co}^{4+}$  ions. In this sense, upon La doping in  $\text{Sr}_2\text{CoO}_4$ , there would be an IS-LS transition of the  $\text{Co}^{4+}$  ions, besides an introduction of the HS  $\text{Co}^{3+}$  ions. As seen below, our calculations indeed confirm this spin-state transition and find it to be the origin of the metal-insulator transition.

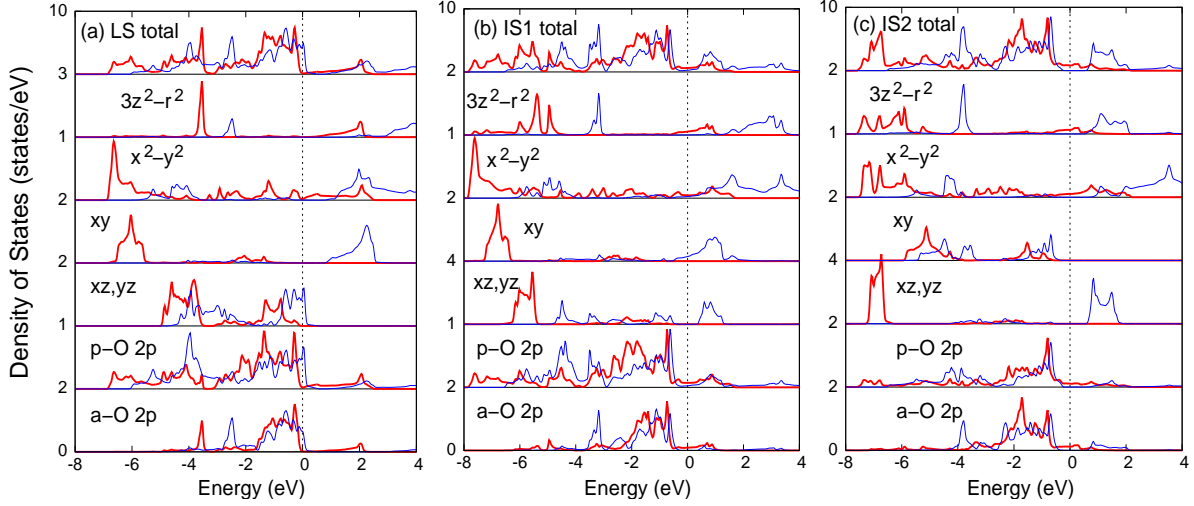


FIG. 2: (Color online) Total density of states (DOS), Co  $3d$ -orbital resolved DOS, planar O (p-O) and apical O (a-O)  $2p$  DOS of FM  $\text{Sr}_2\text{CoO}_4$  in (a) LS, (b) IS1, and (c) IS2 states calculated by GGA+ $U$ . The red (bold) curves stand for the up spin, and the blue (solid) for the down spin. Fermi level is set at zero energy. While the LS and IS1 states are metallic, the IS2 state is half metallic. The IS2 is the ground state, see also Table I.

## II. CALCULATIONS AND DISCUSSION

We carried out GGA+ $U$  calculations, using the full-potential augmented plane wave plus local orbital code (Wien2k).<sup>20</sup> The structural data were taken from Refs. 4 and 7. The muffin-tin sphere radii were chosen to be 2.5, 2.0, and 1.5 Bohr for (Sr,La), Co, and O atoms, respectively. A virtual atom with the atomic number  $Z=38.25$  ( $0.75Z_{\text{Sr}}+0.25Z_{\text{Y}}$ ) was used for the ( $\text{Sr}_{1.5}\text{La}_{0.5}$ ) sites, as Sr and La(Y) ions are in most cases simple electron donors. The plane-wave cut-off energy of 16 Ry was set for the interstitial wave functions, and 1200 (600)  $\mathbf{k}$  points for integration over the Brillouin zone of  $\text{Sr}_2\text{CoO}_4$  (of  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$  with a doubled unit cell). The spin-orbit coupling was included by the second-variational method with scalar relativistic wave functions. The typical value of  $U=5$  eV and Hund exchange of 0.9 eV were used in our GGA+ $U$  calculations to account for the electron correlation of the Co  $3d$  states.<sup>8,19</sup>

### A. $\text{Sr}_2\text{CoO}_4$

We first calculated  $\text{Sr}_2\text{CoO}_4$ . As seen in Table I, our configuration-state constrained GGA+ $U$  calculations find three stable FM solutions, one LS and two IS states. Indeed, the IS states are more stable than the LS state. The LS state is metallic, see Fig. 2(a). The up-spin  $t_{2g}$  ( $xy$  and  $xz/yz$ ) orbitals are fully occupied, and the down-spin  $xz/yz$  are almost fully filled. Note that owing to the high valence of the  $\text{Co}^{4+}$  ion and its negative charge-transfer energy,<sup>21</sup> a strong  $pd\sigma$  hybridization with the ligand oxygens bring about a large occupation on the  $e_g$  ( $3z^2-r^2$  and  $x^2-y^2$ ) orbitals. This accounts for the calculated total spin moment of  $2.03 \mu_B/\text{fu}$  which is in-

creased from the formal LS  $S=1/2$  state. The Co ion has a local spin (orbital) moment of  $1.82$  ( $0.09$ )  $\mu_B$  within its muffin-tin sphere, see Table I.

Starting from the electronic configuration  $t_{2g\uparrow}^3(3z^2-r^2)^1_{\uparrow}(xz+iyz)^1_{\downarrow}$  for the IS1 state, we also get a metallic solution with a total spin moment of  $2.79 \mu_B/\text{fu}$ . The up-spin  $e_g$  bands get almost doubly occupied due to the strong  $pd\sigma$  covalency, and they cross Fermi level together with the down-spin  $xy$  band, see Fig. 2(b). The down-spin  $xz+iyz$  ( $Y_{21}$ ) orbital is fully occupied and well separated from the unoccupied  $xz-iyz$  ( $Y_{2-1}$ ) orbital. It is the  $xz+iyz$  electron that contributes most to the calculated orbital moment of  $1.02 \mu_B$ . The local spin moment is  $2.53 \mu_B$  for the IS1 Co ion.

The most stable IS state is achieved self-consistently from the initial configuration state  $t_{2g\uparrow}^3(3z^2-r^2)^1_{\uparrow}xy^1_{\downarrow}$ . It is FM half metallic, see Fig. 2(c). Only the up-spin  $e_g$

TABLE I: The relative total energies  $\Delta E$  (meV/fu) of FM  $\text{Sr}_2\text{CoO}_4$  (SCO) in one LS and two IS states calculated by GGA+ $U$ , the total spin moment  $M$  and the local spin/orbital moment of Co ions in unit of  $\mu_B$ . A reference to figures is included. The corresponding data are listed for FM  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$  (SLCO). The  $\text{Co}^{3+}$  HS state is marked bold for clarity. Note that in our GGA+ $U$  calculations, the IS  $\text{Co}^{4+}$ -IS  $\text{Co}^{3+}$  state converges to the LS-HS ground state.

SCO	$\Delta E$	$M$ ( $\mu_B/\text{fu}$ )	$\text{Co}^{4+}$ $m_s/m_o$		Fig.
LS	0	2.03	1.82/0.09		2(a)
IS1	-56	2.79	2.53/1.02		2(b)
IS2	-155	3.00	2.61/0.10		2(c)
SLCO	$\Delta E$	$M$ ( $\mu_B/2\text{fu}$ )	$\text{Co}^{4+}$	$\text{Co}^{3+}$	Fig.
IS-HS	0	7.00	2.85/0.13	2.89/0.85	3
LS-HS	-139	5.00	1.70/0.01	2.88/0.84	4

bands cross Fermi level. This solution has an integer spin moment of  $3 \mu_B/\text{fu}$  as expected for the formal IS  $S=3/2$  state. The  $\text{Co}^{4+}$  ion has a local spin (orbital) moment of  $2.61$  ( $0.10$ )  $\mu_B$ , see Table I. This IS2 state is more stable than the LS state by  $155 \text{ meV/Co}$  and than the IS1 state by  $99 \text{ meV/Co}$ . As the  $xy$  singlet is a higher level than the  $xz/yz$  doublet in an elongated tetragonal crystal field, it seems a bit surprising that the IS2 state is more stable than the IS1 state. However, for the almost doubly occupied  $e_g$  orbitals [Figs. 2(b) and 2(c)], the planar  $x^2-y^2$  orbital is itinerant but the  $3z^2-r^2$  orbital is relatively localized. As such, a stronger Coulomb repulsion between the  $3z^2-r^2$  and  $xz/yz$  electrons than that between  $3z^2-r^2$  and  $xy$  makes the filling of the down-spin  $xy$  orbital energetically more favorable than that of the down-spin  $xz/yz$ . Apparently, the FM half-metallic solution of  $\text{Sr}_2\text{CoO}_4$  is due to the significant  $pd\sigma$  hybridization between the IS  $\text{Co}^{4+}$  ions and the planar oxygens. This is because the high-valent  $\text{Co}^{4+}$  ion has a negative charge transfer energy<sup>21</sup> and thus its actual configuration is more like  $\text{Co}^{3+}\underline{L}$ . Indeed, Fig. 2(c) shows almost the  $3d^6$  state of the HS  $\text{Co}^{3+}$  like and the ligand O  $2p$  hole states. Moreover, the planar-O  $2p$  hole state is more itinerant than the apical-O  $2p$ . As a result, the calculated spin moment of  $0.03 \mu_B$  on the planar oxygen is smaller than that of  $0.10 \mu_B$  on the apical oxygen.

### B. $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$

Now we turn to the calculations for the  $\text{Co}^{4+}\text{-Co}^{3+}$  mixed-valent  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$ . As  $\text{Co}^{3+}$  ion has a larger radius than  $\text{Co}^{4+}$ , longer  $\text{Co}^{3+}\text{-O}$  distances would produce a weaker crystal field for  $\text{Co}^{3+}$ , compared with  $\text{Co}^{4+}$ . In this sense,  $\text{Co}^{3+}$  could be in a higher spin state than  $\text{Co}^{4+}$ . Therefore, we first tested the IS  $\text{Co}^{4+}\text{-HS Co}^{3+}$  state as a candidate for  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$ . As seen in Figs. 1(a) and 1(b), the  $x^2-y^2$  electron would readily hop from the HS  $\text{Co}^{3+}$  to IS  $\text{Co}^{4+}$ , giving rise to a FM half-metallic behavior via Zener's double exchange. This picture is indeed supported by our calculations, see Fig. 3: the up-spin  $x^2-y^2$  bands both of the  $\text{Co}^{4+}$  and  $\text{Co}^{3+}$  ions are almost fully occupied but cross Fermi level due to the  $x^2-y^2$  electron hopping and the strong planar  $pd\sigma$  hybridization. This FM half-metallic solution has a total integer spin moment of  $7 \mu_B/2\text{fu}$  as expected for the IS  $\text{Co}^{4+}\text{-HS Co}^{3+}$  FM state ( $S=3/2$  plus  $S=2$ ). The formal HS  $\text{Co}^{3+}$  and IS  $\text{Co}^{4+}$  ions have, mainly due to the  $x^2-y^2$  electron hopping, almost the same local spin moment (being about  $2.9 \mu_B$  each), see Table I. Note, however, that this half-metallic solution disagrees with the experimental semiconducting behavior.<sup>6,7</sup>

Taking into account the above crystal-field scenario, we then calculate the LS  $\text{Co}^{4+}\text{-HS Co}^{3+}$  state, i.e., our calculations now involve a possible spin-state transition of the  $\text{Co}^{4+}$  ion from the IS state in  $\text{Sr}_2\text{CoO}_4$  to the LS state in  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$ . [This spin-state transition is likely upon La doping into  $\text{Sr}_2\text{CoO}_4$ , as the introduced HS  $\text{Co}^{3+}$  ions

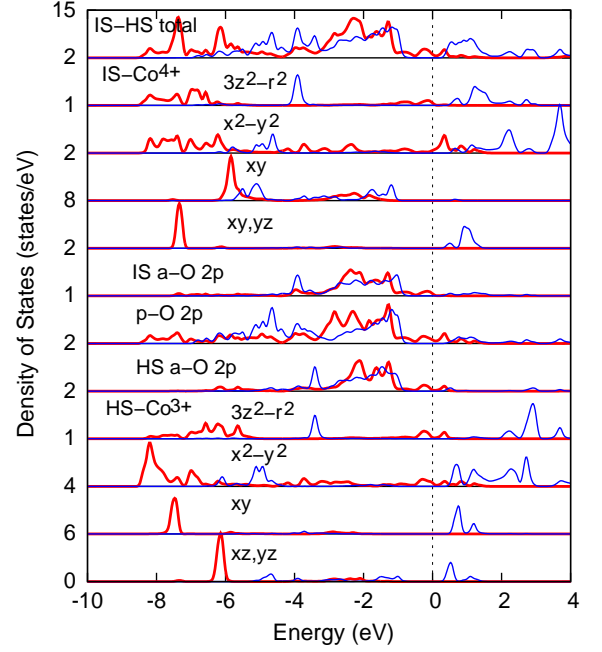


FIG. 3: (Color online) DOS of  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$  in the IS  $\text{Co}^{4+}\text{-HS Co}^{3+}$  state calculated by GGA+ $U$ . It is FM half metallic.

get bigger in size (compared with the IS  $\text{Co}^{4+}$  ions), and then a chemical pressure forces the IS  $\text{Co}^{4+}$  ions transit into the lower-volume LS state.] At a glance, an electron hopping from  $\text{Co}^{3+}$  to  $\text{Co}^{4+}$  is possible, as there could be no change of the electronic configurations (from the initial  $d^6+d^5$  state to the final  $d^5+d^6$  state). However, as seen in Figs. 1(b) and 1(c), the  $x^2-y^2$  electron hopping from HS  $\text{Co}^{3+}$  to LS  $\text{Co}^{4+}$  is actually suppressed, particularly due to the spin-state issue. If such a hopping took place, there would be an energy cost of Hund exchange associated with the change of the spin states from LS-HS to IS-IS. As a result, the LS  $\text{Co}^{4+}\text{-HS Co}^{3+}$  state will be stabilized at it is, and it has no real electron hopping (due to a spin blockade<sup>11,22</sup>) and is thus insulating. However, a virtual hopping of the  $x^2-y^2$  electron forth and back and the local Hund exchange would mediate a superexchange FM in the  $e_g^0e_g^2$  configuration of the LS  $\text{Co}^{4+}\text{-HS Co}^{3+}$  state.

The insulating but FM solution of the LS  $\text{Co}^{4+}\text{-HS Co}^{3+}$  state is indeed confirmed by our calculations, see Fig. 4: it has a small insulating gap of about  $0.3 \text{ eV}$ . The  $\text{Co}^{4+}$   $t_{2g}$  orbitals carry a spin= $1/2$  (on the  $xy$  orbital), and the strong  $pd\sigma$  hybridization brings about a large amount of  $e_g$  occupation and thus increases the local spin moment of the  $\text{Co}^{4+}$  to  $1.7 \mu_B$ , see Table I. The LS  $\text{Co}^{4+}$  ion has a negligible orbital moment of  $0.01 \mu_B$ . For the  $\text{Co}^{3+}$  ion, Co-O valency reduces its local spin moment to  $2.88 \mu_B$ . The total spin moment is  $5 \mu_B/2\text{fu}$  as expected for this LS  $\text{Co}^{4+}\text{-HS Co}^{3+}$  ( $S=1/2$  plus  $S=2$ ) state. In this semiconducting state, besides the localized  $t_{2g}$  and  $3z^2-r^2$  orbitals, the  $x^2-r^2$  orbital also gets localized due to the spin blockade. Then the formal HS  $\text{Co}^{3+}$  ion has

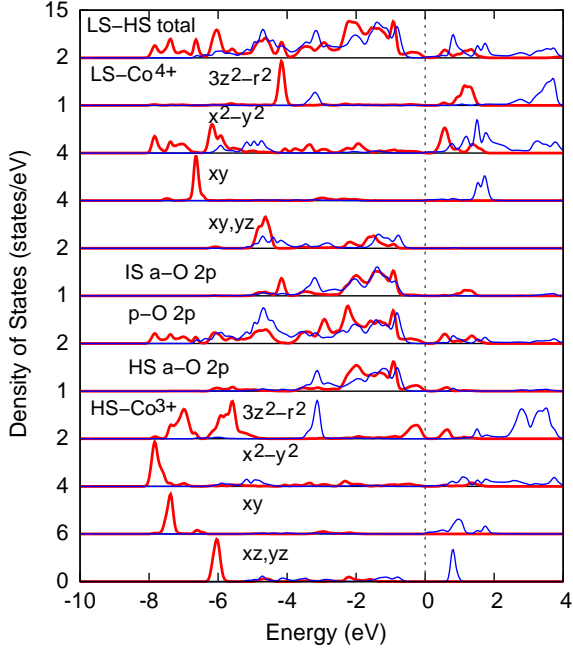


FIG. 4: (Color online) DOS of  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$  in the LS  $\text{Co}^{4+}$ -HS  $\text{Co}^{3+}$  ground state calculated by GGA+ $U$ . It is FM semiconducting.

the configuration state  $t_{2g\uparrow}^3 e_{g\uparrow}^2 (xz+iyz)_{\downarrow}^1$ , i.e., the up-spin orbitals are fully occupied and form a closed subshell, but the rest single electron occupies the lowest crystal-field doublet  $xz/yz$ . As a result, the spin-orbit coupling lifts the orbital degeneracy, produces the  $Y_{21}$  ( $xz+iyz$ ) complex orbital, and gives a large orbital moment of  $0.84 \mu_B$  along the easy-magnetization  $c$ -axis. The importance of spin-orbit coupling was also demonstrated previously when studying the spin-orbital ground state of the perovskite  $\text{LaCoO}_3$ .<sup>23</sup> Thus, in  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$  the total spin and orbital moments sum up to about  $5.8 \mu_B/2\text{fu}$ .

It is important to note that this LS  $\text{Co}^{4+}$ -HS  $\text{Co}^{3+}$  FM state is more stable than the above IS-HS FM state by  $139 \text{ meV/fu}$ . In addition, this LS-HS state brings about a local distortion against the homogeneous Co-O lattice measured so far in polycrystals. Our calculations doing atomic relaxations show that the LS  $\text{Co}^{4+}$  ion has the optimized Co-O bondlengths of  $1.879 \text{ \AA} \times 4$  (in plane) and  $2.011 \text{ \AA} \times 2$  (out of plane). The corresponding values are  $1.911 \text{ \AA} \times 4$  and  $2.061 \text{ \AA} \times 2$  for the HS  $\text{Co}^{3+}$ . Such atomic relaxations help the LS  $\text{Co}^{4+}$ -HS  $\text{Co}^{3+}$  state gain further an elastic energy of  $54 \text{ meV/fu}$  as shown by our calculations. The semiconducting electronic structure turns out to have insignificant changes due to the

atomic relaxations. For example, the local spin and orbital moments of the LS  $\text{Co}^{4+}$  (the HS  $\text{Co}^{3+}$ ) are now  $1.64$  and  $0.01$  ( $2.92$  and  $0.83$ )  $\mu_B$ , respectively (see Table I for a comparison). Moreover, our calculation finds a LS-HS ferrimagnetic solution to be less stable than the LS-HS FM solution by  $34 \text{ meV/fu}$ . The LS-HS ferrimagnetic solution has a total spin moment of  $3 \mu_B/2\text{fu}$  as expected. The constituent LS  $\text{Co}^{4+}$  ( $S = -1/2$ ) has a local spin (orbital) moment of  $-0.42$  ( $-0.01$ )  $\mu_B$ , and the HS  $\text{Co}^{3+}$  ( $S = 2$ ) has  $2.97$  ( $0.84$ )  $\mu_B$ . Furthermore, our calculations show that another possible spin state of  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$ —the IS  $\text{Co}^{4+}$ -IS  $\text{Co}^{3+}$  state is unstable and converges to the present LS-HS FM state. Therefore, the present FM semiconducting LS  $\text{Co}^{4+}$ -HS  $\text{Co}^{3+}$  solution is the ground state of  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$ .

This FM semiconducting ground-state solution agrees with the experiments.<sup>6,7</sup> Moreover, using the LS  $\text{Co}^{4+}$ -HS  $\text{Co}^{3+}$  state ( $S=\frac{1}{2}$  and  $S=2$  plus  $L=1$ ), we estimate the effective magnetic moment

$$\mu_{eff} = \sqrt{0.5 \times 4 \times \frac{1}{2} \times \frac{3}{2} + 0.5 \times (4 \times 2 \times 3 + 1 \times 1 \times 2)} \approx 3.8 \mu_B/\text{Co}.$$

Taking a covalency reduction, this value is in good agreement with the measured one of  $3.5 \mu_B$ .<sup>6</sup> Although the predicted magnetic moment of  $2.9 \mu_B/\text{fu}$  (i.e., the above  $5.8 \mu_B/2\text{fu}$ ) along the easy-magnetization  $c$ -axis (of a single crystal, ideally) is much bigger than the measured  $1.5 \mu_B$ ,<sup>6</sup> using of the polycrystals so far in the experiments would most probably account for the large reduction. The predicted LS-HS state, a big orbital moment along the  $c$ -axis, and the local Co-O distortions in  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$  call for further studies on a single crystal.

### III. CONCLUSION

In summary, using GGA+ $U$  calculations, we find that while  $\text{Sr}_2\text{CoO}_4$  in the  $\text{Co}^{4+}$  IS ground state is a FM half-metal,  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$  has the LS  $\text{Co}^{4+}$ -HS  $\text{Co}^{3+}$  ground state. It is the  $\text{Co}^{4+}$  IS-LS transition that suppresses an electron hopping via a spin blockade and thus drives a metal-insulator transition in  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$ . Moreover, the present spin-state picture consistently accounts for the FM behavior of metallic  $\text{Sr}_2\text{CoO}_4$  via a  $pd\sigma$  hybridization and that of semiconducting  $\text{Sr}_{1.5}\text{La}_{0.5}\text{CoO}_4$  via a superexchange. Thus, spin state could provide a way to tune materials properties.

This work was supported by the NSF of China and WHMFC (WHMFCKF2011008).

\* Email address: wuh@fudan.edu.cn

<sup>1</sup> M. Imada, A. Fujimori, and Y. Tokura, Rev. Mod. Phys. **70**, 1039 (1998).

<sup>2</sup> A. C. Komarek, S. V. Streltsov, M. Isobe, T. Möller, M. Hoelzel, A. Senyshyn, D. Trots, M. T. Fernández-Díaz, T. Hansen, H. Gotou, T. Yagi, Y. Ueda, V. I. Anisimov, M.

- Grüninger, D. I. Khomskii, and M. Braden, Phys. Rev. Lett. **101**, 167204 (2008).
- <sup>3</sup> J. Matsuno, Y. Okimoto, Z. Fang, X. Z. Yu, Y. Matsui, N. Nagaosa, M. Kawasaki, and Y. Tokura, Phys. Rev. Lett. **93**, 167202 (2004).
  - <sup>4</sup> X. L. Wang and E. Takayama-Muromachi, Phys. Rev. B **72**, 064401 (2005).
  - <sup>5</sup> S. K. Pandey, Phys. Rev. B **81**, 035114 (2010).
  - <sup>6</sup> Y. Shimada, S. Miyasaka, R. Kumai, and Y. Tokura, Phys. Rev. B **73**, 134424 (2006).
  - <sup>7</sup> A. V. Chichev, M. Dlouhá, S. Vratislav, K. Knížek, J. Hejtmánek, M. Maryško, M. Veverka, Z. Jiráček, N. O. Golosova, D. P. Kozlenko, and B. N. Savenko, Phys. Rev. B **74**, 134414 (2006).
  - <sup>8</sup> H. Wu, Phys. Rev. B **81**, 115127 (2010).
  - <sup>9</sup> N. Hollmann, M. W. Haverkort, M. Cwik, M. Benomar, M. Reuther, A. Tanaka, and T. Lorenz, New J. Phys. **10**, 023018 (2008).
  - <sup>10</sup> M. Cwik, M. Benomar, T. Finger, Y. Sidis, D. Senff, M. Reuther, T. Lorenz, and M. Braden, Phys. Rev. Lett. **102**, 057201 (2009).
  - <sup>11</sup> C. F. Chang, Z. Hu, H. Wu, T. Burnus, N. Hollmann, M. Benomar, T. Lorenz, A. Tanaka, H.-J. Lin, H. H. Hsieh, C. T. Chen, and L. H. Tjeng, Phys. Rev. Lett. **102**, 116401 (2009).
  - <sup>12</sup> H. Wu and T. Burnus, Phys. Rev. B **80**, 081105(R) (2009).
  - <sup>13</sup> L. M. Helme, A. T. Boothroyd, R. Coldea, D. Prabhakaran, C. D. Frost, D. A. Keen, L. P. Regnault, P. G. Freeman, M. Enderle, and J. Kulda, Phys. Rev. B **80**, 134414 (2009).
  - <sup>14</sup> C. Tealdi, C. Ferrara, L. Malavasi, P. Mustarelli, C. Ritter, G. Chiodelli, and Y. A. Diaz-Fernandez, Phys. Rev. B **82**, 174118 (2010).
  - <sup>15</sup> P. Babkevich, D. Prabhakaran, C. D. Frost, and A. T. Boothroyd, Phys. Rev. B **82**, 184425 (2010).
  - <sup>16</sup> N. Hollmann, M. W. Haverkort, M. Benomar, M. Cwik, M. Braden, and T. Lorenz, Phys. Rev. B **83**, 174435 (2011).
  - <sup>17</sup> M. Merz, D. Fuchs, A. Assmann, S. Uebe, H. v. Löhneysen, P. Nagel, and S. Schuppler, Phys. Rev. B **84**, 014436 (2011).
  - <sup>18</sup> V. I. Anisimov, I. V. Solov'yev, M. A. Korotin, M. T. Czyżyk, and G. A. Sawatzky, Phys. Rev. B **48**, 16929 (1993).
  - <sup>19</sup> J. Wang, W. Zhang, and D. Y. Xing, Phys. Rev. B **62**, 14140 (2000); J. Wang, Y. C. Tao, W. Zhang, and D. Y. Xing, J. Phys.: Condens. Matter **12**, 7425 (2000).
  - <sup>20</sup> P. Blaha, K. Schwarz, G. Madsen, D. Kvasnicka, and J. Luitz, **WIEN2k**, 2001. ISBN 3-9501031-1-2.
  - <sup>21</sup> R. H. Potze, G. A. Sawatzky, and M. Abbate, Phys. Rev. B **51**, 11501 (1995).
  - <sup>22</sup> A. Maignan, V. Caignaert, B. Raveau, D. Khomskii, and G. Sawatzky, Phys. Rev. Lett. **93**, 026401 (2004).
  - <sup>23</sup> Z. Ropka and R. J. Radwanski, Phys. Rev. B **67**, 172401 (2003).