

## Comment on “Tuning the Magnetic Dimensionality by Charge Ordering in the Molecular TMTTF Salts”

Yoshimi *et al.* [1] have attempted to explain the pressure( $P$ )-dependent behavior of Fabre salts which exhibit charge order (CO), antiferromagnetic (AFM), and spin-Peierls (SP) phases. Experiments find two AFM phases [2, 3], AFM<sub>1</sub> at large  $P$  and AFM<sub>2</sub> at small  $P$ . Yoshimi *et al.* suggest that there also exist two distinct zero-temperature SP phases, SP<sub>1</sub> and SP<sub>2</sub>. Here we point out that the occurrence of two distinct SP phases contradicts experiments [2, 3], and is found in [1] because of unrealistic model parameters.

Experiments [2, 3] emphasize *co-operative interaction* between the ferroelectric charge order (FCO) and AFM<sub>2</sub> phases. In the experimental phase diagram [2, 3]  $T_{CO}$  and the Néel temperature in the AFM<sub>2</sub> phase both decrease with  $P$ . Thus charge occupancies in the FCO and AFM<sub>2</sub> phases are likely the same. In contrast,  $P$  *increases* [2, 3] the SP transition temperature, indicating that FCO and SP<sub>2</sub> phases *compete*. No CO was detected for  $P > 0.5$  GPa in (TMTTF)<sub>2</sub>SbF<sub>6</sub> [2, 3], in the  $P$  region where the SP<sub>2</sub> phase occurs at lower temperature. It is then unlikely that SP<sub>2</sub> and FCO coexist at zero temperature.

The hopping parameters used by the authors in their model calculations are realistic. Their choice of Coulomb interactions is however unrealistic. The onsite Coulomb interaction assumed,  $U/t_{a2}=4$ , is too small—in the purely electronic one dimensional model no CO occurs for this  $U$  [4, 5]. The assumed intersite Coulomb interactions  $V_b = 0$  and  $V_q = V_a$ , are also unrealistic. Given the lattice geometry (see Fig. 1) it is highly unlikely that  $V_b \ll V_q$ , and with large interchain separation  $V_q = V_a$  is equally unrealistic.  $4 \lesssim U \lesssim 8$  and  $V_b \simeq V_q \ll V_a$  is more appropriate.

We repeated the calculations with more realistic  $V_a = V$ ,  $V_b = V_q = 0$ , and  $4 \leq U \leq 8$ . For these parameters, the intra-dimer charge structure factor ( $C_{-}(\mathbf{q})$  in [1]) peaks at several  $\mathbf{q}$  values, indicating comparable energies for both FCO and the checkerboard pattern CO, in agreement with experiments [6]. Peaks in  $S_{\pm}(\mathbf{q})$  remain at the same  $\mathbf{q}$  values as in Fig. 2 of [1]. We conclude that the  $V_{ij}$  assumed in [1] is *not* required to explain coexisting FCO/AFM order in the AFM<sub>2</sub> state.

We also repeated (see Fig. 1) the  $8 \times 2$  calculations with these parameters. We have three main observations: (i) for  $V_a = V$ ,  $V_b = V_q = 0$ , we find a phase diagram similar to that in [1], but with FCO entering at larger  $V$  as expected [4, 5]. The choice  $V_q = V$ ,  $V_b = 0$  is also *not* required to realize the FCO phase; FCO can be stabilized by antiferromagnetic superexchange along the  $t_b$  bonds; (ii) As  $U$  increases the FCO+SP phase narrows; (iii) For both these and the parameters assumed in [1], the width of the FCO+SP phase is *directly proportional to the strength of the inter-site electron phonon coupling* (larger  $K_1$  gives weaker coupling). Uncondi-

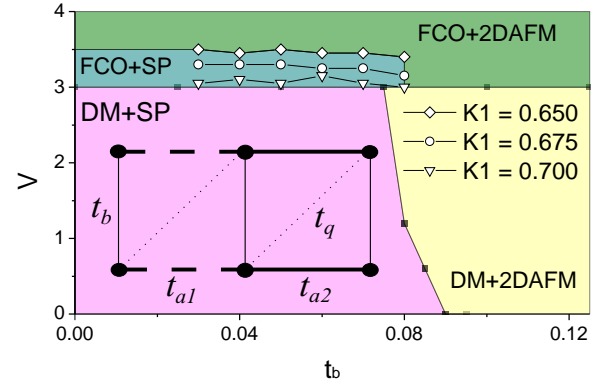


FIG. 1: (color online)  $8 \times 2$  phase diagram for  $U = 6$ ,  $V_a = V$ , and  $K_2 = 1$ . The inset shows the lattice structure assumed by [1]. As  $K_1$  increases the size of the FCO+SP phase shrinks. Other points do not significantly change with  $K_1$ .

tional transitions in the thermodynamic limit occur in the limit of  $0^+$  phonon coupling. Importantly, point (iii) was not discussed in [1], and together with (ii) suggests that in the thermodynamic limit the FCO+2DAFM and DM+SP phases may share a common border.

To understand the phase diagram one must consider thermodynamics. For large Coulomb interactions the free energy is dominated by spin excitations. We have previously shown that the same DM+SP ground state can have two kinds of soliton spin excitations, (i) with local CO, or (ii) with uniform charge but local bond distortion [7]. In this picture, to the left of the line bisecting the SP phase [2] soliton excitations with local CO dominate at finite  $T$ ; to the right occur excitations with uniform site charges. A unique SP *ground state* is expected at all pressures between AFM<sub>1</sub> and AFM<sub>2</sub>. We acknowledge support from the Department of Energy grant DE-FG02-06ER46315.

A. B. Ward<sup>1</sup>, R. T. Clay<sup>1</sup>, and S. Mazumdar<sup>2</sup>

<sup>1</sup>Department of Physics & Astronomy  
HPC<sup>2</sup> Center for Computational Sciences  
Mississippi State University  
Mississippi State, MS 39762-5167

<sup>2</sup>Department of Physics  
University of Arizona  
Tucson, AZ 85721

- [1] K. Yoshimi, H. Seo, S. Ishibashi, and S. E. Brown, Phys. Rev. Lett. **108**, 096402 (2012).
- [2] W. Yu et al., Phys. Rev. B **70**, 121101 (2004).
- [3] F. Iwase, K. Sugiura, K. Furukawa, and T. Nakamura, Phys. Rev. B **84**, 115140 (2011).
- [4] R. T. Clay, S. Mazumdar, and D. K. Campbell, Phys. Rev. B **67**, 115121 (2003).
- [5] H. Seo, J. Merino, H. Yoshioka, and M. Ogata, J. Phys. Soc. Jpn. **75**, 051009 (2006).
- [6] T. Nakamura, J. Phys. Soc. Jpn. **72**, 213 (2003).
- [7] R. T. Clay, R. P. Hardikar, and S. Mazumdar, Phys. Rev. B **76**, 205118 (2007).