

# Nodal Landau Fermi-Liquid Quasiparticles in Overdoped $\text{La}_{1.77}\text{Sr}_{0.23}\text{CuO}_4$

C. G. Fatuzzo,<sup>1</sup> Y. Sassa,<sup>2</sup> M. Månsson,<sup>2,3</sup> S. Pailhès,<sup>4,5</sup> O. J. Lipscombe,<sup>6</sup> S. M. Hayden,<sup>6</sup> L. Patthey,<sup>7</sup> M. Shi,<sup>7</sup> M. Grioni,<sup>1</sup> H. M. Rønnow,<sup>1</sup> J. Mesot,<sup>1,2,4</sup> O. Tjernberg,<sup>3</sup> and J. Chang<sup>1,7,4</sup>

<sup>1</sup>*Institute for Condensed Matter Physics, École Polytechnique Fédérale de Lausanne (EPFL), CH-1015 Lausanne, Switzerland*

<sup>2</sup>*Laboratory for Solid State Physics, ETH Zürich, CH-8093 Zürich, Switzerland*

<sup>3</sup>*KTH Royal Institute of Technology, Materials Physics, S-164 40 Kista, Sweden*

<sup>4</sup>*Laboratory for Neutron Scattering, Paul Scherrer Institut, CH-5232 Villigen, Switzerland*

<sup>5</sup>*LPMC, CNRS, UMR 5586, Université Lyon 1, F-69622 Villeurbanne, France*

<sup>6</sup>*H. H. Wills Physics Laboratory, University of Bristol, Bristol, BS8 1TL, United Kingdom*

<sup>7</sup>*Swiss Light Source, Paul Scherrer Institut, CH-5232 Villigen PSI, Switzerland*

Nodal angle resolved photoemission spectra taken on overdoped  $\text{La}_{1.77}\text{Sr}_{0.23}\text{CuO}_4$  are presented and analyzed. It is proven that the low-energy excitations are true Landau Fermi-liquid quasiparticles. We show that momentum and energy distribution curves can be analyzed self-consistently without quantitative knowledge of the bare band dispersion. Finally, by imposing Kramers-Kronig consistency on the self-energy  $\Sigma$ , insight into the quasiparticle residue is gained. We conclude by comparing our results to quasiparticle properties extracted from thermodynamic, magneto-resistance, and high-field quantum oscillation experiments on overdoped  $\text{Tl}_2\text{Ba}_2\text{CuO}_{6+\delta}$ .

## I. INTRODUCTION

The extent to which Landau Fermi-liquid theory, and its concept of quasiparticles<sup>1</sup>, applies to the normal state of cuprates is still under debate<sup>2,3</sup>. Evidence for Landau Fermi-liquid quasiparticles has been reported by resistivity experiments on highly overdoped  $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$  (LSCO)<sup>4</sup>. More recently, unambiguous proof has been given by high-field quantum oscillation experiments<sup>5–9</sup> on both overdoped and underdoped cuprates. It is, however, puzzling that no evidence of Landau Fermi-liquid quasiparticle excitations has been found from angle resolved photoemission spectroscopy (ARPES), that is a direct probe of the Green's function:  $-(1/\pi)\text{Im}G(k, \omega)$ <sup>10</sup>. Although the “quasiparticles” terminology is widely used to describe the excitations of the photoemission spectra, it has never been proven by ARPES that the low-energy excitations in the cuprates are indeed true Landau Fermi-liquid quasiparticles. A direct spectroscopic proof of true Landau Fermi-liquid quasiparticles in the cuprates is therefore important.

This paper has two main objectives. The first is to prove that the nodal excitations observed in overdoped LSCO by ARPES are genuine Landau Fermi-liquid quasiparticles. The second is to discuss the nodal bare band velocity,  $v_b$ , and the nodal quasiparticle residue  $Z \equiv (1 - \partial\Sigma'/\partial\omega)^{-1}$ , where  $\Sigma$  is the self-energy. Perhaps the most compelling spectroscopic proof of Landau quasiparticles is the demonstration of a low-energy self-energy that has (1) the form  $\Sigma'' \propto i\omega$ <sup>211</sup> and (2)  $-Z\Sigma'' < |\omega|$ <sup>12,13</sup>. Proving this requires full knowledge about  $\Sigma$  and insight into the bare band  $\varepsilon_b$ , that is not straightforward to derive from an APRES spectrum<sup>14</sup>. Here, we however present an experimental case where  $Z\Sigma''$  can be evaluated without quantitative knowledge of  $\varepsilon_b$ . In this specific case, it is therefore possible to prove the existence of true Landau Fermi-liquid quasiparticle excitations.

## II. METHODS

Nodal ARPES spectra of overdoped  $\text{La}_{1.77}\text{Sr}_{0.23}\text{CuO}_4$  ( $T_c = 25\text{K}$ )<sup>22,23</sup> were recorded at the surface and interface spectroscopy (SIS) beam line<sup>19</sup> of the Swiss Light Source (SLS) at the Paul Scherrer Institute, Switzerland. High quality nodal spectra were obtained after cleaving<sup>21</sup> at  $T = 15\text{K}$  under ultra-high vacuum conditions ( $p \sim 10^{-11}\text{ mbar}$ ). Using 55 eV circular polarized photons and a SCIENTA 2002 electron analyzer, angular and energy resolutions corresponding to  $0.15^\circ$  (FWHM) and  $\sigma = 9\text{ meV}$  (standard Gaussian deviation) were achieved. A detailed description of the experimental conditions can be found in Ref. 20.

## III. RESULTS

Fig. 1(a) shows a colormap  $-I$  vs  $(k, \omega)$  – of ARPES spectra recorded close to the nodal direction of overdoped  $\text{La}_{1.77}\text{Sr}_{0.23}\text{CuO}_4$ . A selection of corresponding momentum distribution curves (MDC) and energy distribution curves (EDC) are displayed in Fig. 1(b,c). We start by discussing the MDCs. As this paper focuses entirely on the low-energy excitations, MDCs are only shown up to the energy scale (80 meV) of the nodal kink shown in the inset of Fig. 1(c). In this energy interval, the MDC line shapes are symmetric peaks on a constant background. Therefore, data at constant  $\omega$  were analyzed using a Lorentzian function  $I_0\Gamma/[(\omega - \varepsilon_k)^2 + \Gamma^2]$ , where  $\Gamma$  is the linewidth (Fig. 2a),  $\varepsilon_k$  is the peak position (Fig. 2b), and  $I_0$  is an amplitude (Fig. 3). The observed nodal excitations disperse with a Fermi velocity  $v_F = 1.62(2)\text{ eV\AA}$  [Fig. 2(b)], consistently with previous reports on LSCO<sup>24,25</sup>. The half-width half-maximum,  $\Gamma$ , is plotted as a function of excitation energy squared  $\omega^2$  in Fig. 2(a). We find that, for  $\omega < \omega_c = 0.18 \pm 0.2\text{ eV}$ , the linewidth is well described by  $\Gamma = \Gamma(0) + \eta\omega^2$  with



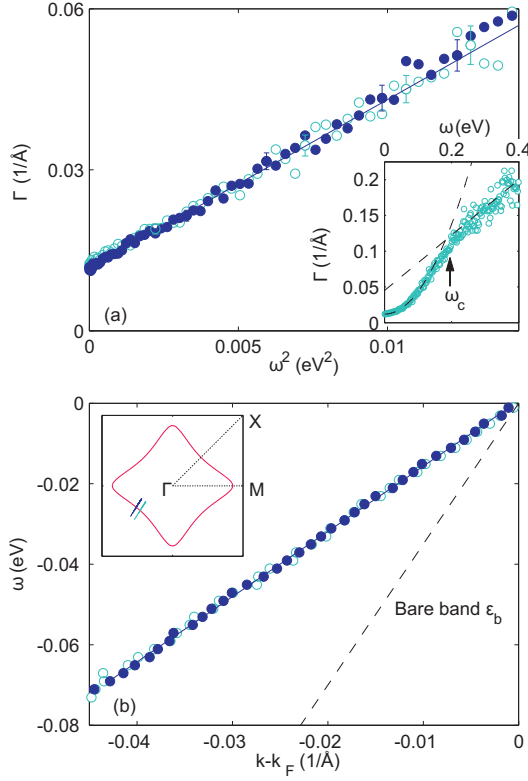


FIG. 2: (a) Linewidth  $\Gamma$  of the momentum distribution curves plotted versus excitation energies squared ( $\omega^2$ ), for the two cuts shown in the inset of (b). Inset of (a) shows  $\Gamma$  vs  $\omega$ . The deviation from  $\omega^2$  dependence defines the energy scale  $\omega_c$  – indicated by the arrow. (b) Nodal dispersions extracted from MDC analysis for the two cuts shown in the inset. The dashed line indicates the bare-band extracted by assuming Kramers-Kronig consistency of the self-energy  $\Sigma$ , see text. The inset shows the Fermi surface of LSCO  $x = 0.23$  and the two cuts along which the spectra were recorded.

part of the spectral function and featureless weight to the incoherent part. Here we focus on the low-energy part of the spectra, where the coherent spectral weight is dominating.

To make progress, two justified assumptions are made. First, it is assumed that the experimentally unknown bare band can be linearized ( $\epsilon_b \simeq v_b(k - k_F)$ ) near the Fermi level. Already the observed normalized band (extracted from the MDC analysis) can, to a very good approximation, be described by  $\epsilon_k = v_F(k - k_F)$ , with  $v_F = 1.62 \text{ eV}\text{\AA}$  [Fig. 2(b)]. The bare band is expected to have an even larger band velocity – LDA calculations suggest for example  $v_b \simeq 3.5 \text{ eV}\text{\AA}$ <sup>29</sup>. For the excitation energies discussed here, curvature effects of the bare band are therefore expected to be negligibly small. Secondly, we assume that the self-energy,  $\Sigma$ , is locally momentum independent. Globally this assumption is not correct – the self-energy varies strongly as one approaches the anti-nodal region<sup>20</sup>. However, locally, in the vicinity of the

nodal region, this is a good approximation. As shown in Fig. 2, both the band velocity and MDC linewidth are essentially identical for the two different nodal cuts. Another indication that  $\Sigma$  is momentum independent stems from the symmetric MDC lineshape shown in Fig. 1b. A  $k$ -dependence of  $\Sigma$  along the cut-direction would lead to an asymmetric lineshape. As this is not observed, it is concluded that  $\Sigma$  is locally independent of momentum both along and perpendicular to the cut direction.

It is thus possible to rewrite the coherent part of the spectral function as:

$$A_{coh}(k, \omega) = \frac{-1}{\pi} \frac{\Sigma''(\omega)}{(\omega - \Sigma'(\omega) - v_b(k - k_F))^2 + \Sigma''(\omega)^2}. \quad (2)$$

Notice that this is nothing else than a Lorentzian function in momentum space, with half-width half-maximum  $\Gamma$  given by  $\Gamma(\omega) = -\Sigma''(\omega)/v_b$ . Experimentally, it is found that  $\Gamma \propto \omega^2$  (see Fig. 2). Therefore, consistently with true Fermi liquid quasiparticle excitations, we conclude that  $\Sigma'' \propto \omega^2$ .

A Kramers-Kronig consistent self-energy with  $\Sigma'' \propto \omega^2$  has  $\Sigma' \simeq -\gamma\omega$  in the low-energy limit. The unknown constant  $\gamma$  is sometimes referred to as the quasiparticle renormalization factor<sup>30</sup>. If consistency between MDC and EDC poles (dispersions) is enforced, then  $1/(1 + \gamma) = v_F/v_b = Z$ . The coherent spectral function can consequently be re-written as:

$$A_{coh}(k, \omega) = \frac{Z}{\pi} \frac{v_F \Gamma}{(\omega - v_F(k - k_F))^2 + (v_F \Gamma)^2}, \quad (3)$$

where both  $v_F$  and  $\Gamma$  are known from the MDC analysis. The only unknown parameter,  $v_b$ , is a prefactor. It is therefore possible to model the EDC lineshape without quantitative knowledge of the bare band  $\epsilon_b$ , and with the peak amplitude as the only free parameter – see solid lines in Fig. 1(c). In the displayed energy interval, a consistent description of both EDCs and MDCs were obtained from  $A_{coh}(k, \omega)$ .

Because  $Z = v_F/v_b$  and  $\Sigma'' = -\eta v_b \omega^2$ , the product  $Z\Sigma'' = -v_F \eta \omega^2$  can be evaluated without quantitative knowledge of the bare band velocity. The condition for coherent quasiparticle excitations is  $-Z\Sigma'' < |\omega|$ <sup>12,13</sup>. Using the experimental values of  $v_F$  and  $\eta$ , we find that Landau quasiparticles are coherent for  $\omega < 1/v_F \eta \sim 0.19 \text{ eV}$ . This energy scale is comparable to  $\omega_c$  – the energy scale below which  $\Sigma'' \propto \omega^2$  – and hence re-enforces the interpretation of  $\omega_c$  as an energy scale related to the break down of Landau Fermi-liquid quasiparticle excitations<sup>20</sup>.

Finally, we discuss the Kramers-Kronig relation between  $\Sigma'$  and  $\Sigma''$ :

$$\begin{aligned} \Sigma' &= \frac{\mathcal{P}}{\pi} \int_{-\omega_c}^{\omega_c} \frac{\Sigma''(\omega')}{\omega' - \omega} d\omega' \pm \frac{\mathcal{P}}{\pi} \int_{\pm\omega_c}^{\pm W} \frac{\Sigma''(\omega')}{\omega' - \omega} d\omega' \\ &= \Sigma'_{qp} + \Sigma'_{nqp} \end{aligned} \quad (4)$$

where  $\mathcal{P}$  is the principal value and  $W$  is the band width. To first order, the quasiparticle part yields  $\Sigma'_{qp} \simeq \gamma_{qp}\omega$

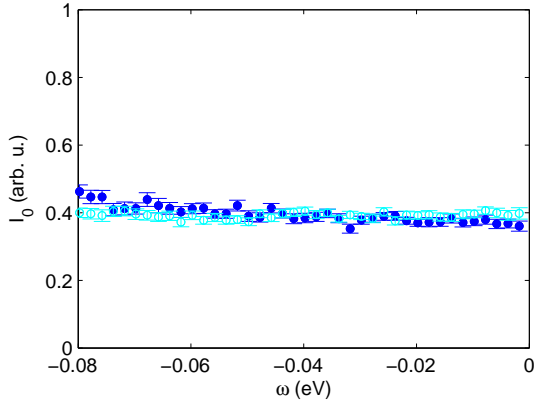


FIG. 3: Amplitude  $I_0$ , in arbitrary units, versus excitation energy  $\omega$  for the two cuts in the inset of Fig. 2b. Correction by the Fermi-Dirac distribution only influence the data points near the Fermi level.

where  $\gamma_{qp} = 2v_b\eta\omega_c/\pi$ . To gain insight into  $\Sigma'_{nqp}$ , we define  $Z_i(\omega) = (1 - \partial\text{Re}\Sigma_i/\partial\omega)^{-1}$  so that  $Z(\omega) = Z_{qp}(\omega) + Z_{nqp}(\omega)$ . As  $Z(\omega) \sim I_0(\omega)$  varies weakly with excitation energies (see Fig. 3), we infer that  $Z_{nqp}$  (to first order) is  $\omega$ -independent. Hence  $\text{Re}\Sigma_{nqp}(\omega) = \gamma_{nqp}\omega$  and  $Z = 1/(1 + \gamma_{qp} + \gamma_{nqp})$ . As long as the detailed high-energy part of  $\text{Im}\Sigma(\omega)$  is unknown, it is not possible to directly extract  $\Sigma'_{nqp} = \gamma_{nqp}\omega$ . This is known as the "tail" problem<sup>14</sup>. The linear  $\omega$ -dependence at high-energies, shown in the inset of Fig. 2, yields  $\gamma_{nqp} \sim \ln(C/\omega_c)$  where  $C$  is an unknown constant. Hence  $\gamma_{nqp}$  diverges only logarithmically in the limit  $\omega_c \rightarrow 0$ <sup>20</sup>. On the other hand, for large  $\omega_c$  the role of  $\gamma_{nqp}$  will be less important. As  $\omega_c = 0.18$  eV is a large energy scale, corresponding to a temperature scale of the order 1000 K, we hypothesize that  $\gamma_{nqp} \ll 1$ . In that case,  $Z \simeq 1/(1 + \gamma_{qp}) = v_F/v_b$  and hence  $v_b = \pi v_F/(\pi - 2\eta\omega_c v_F) = 3.8$  Å. This is consistent with the nodal LDA Fermi velocity  $v_{LDA} = 3.5$  eVÅ<sup>29</sup> calculated for LSCO and with values of  $v_b$  derived from a numeric self-consistent method<sup>14</sup>. The consistent values of  $v_b$  further support the conjecture that  $\gamma_{nqp} \ll 1$ .

The quasiparticle mass is given by  $m_b/m^* = Z\hat{Z}$ , where  $m_b$  is the bare mass and  $\hat{Z} = 1 + (m_b/\hbar^2 k_F)\partial\Sigma'(k, 0)/\partial k$ <sup>17,31</sup>. Since the self-energy is locally independent of momentum, the nodal quasiparticle mass is given by  $m^* = m_b/Z \simeq 2.4m_b$ . This is comparable to the momentum averaged val-

ues  $m^* \simeq 3m_b$  extracted from quantum oscillation<sup>6,17</sup> and electronic specific heat experiments on overdoped  $\text{Ti}_2\text{Ba}_2\text{CuO}_{6+\delta}$  (Ti2201)<sup>15</sup>. Remarkably, a Fermi-liquid cut-off energy scale  $\omega_c \sim 0.2$  eV was extracted<sup>32,33</sup> from angle-dependent magneto-resistance measurements on overdoped Ti2201<sup>16</sup>. This is in good agreement with nodal ARPES spectra recorded on LSCO  $x = 0.23$ <sup>20</sup>. On LSCO, no quantum oscillation or angle-dependent magneto-resistance experiments exist. Insight into the average quasiparticle mass of overdoped LSCO stems, therefore, alone from specific heat measurements<sup>34</sup>. Compared to Ti2201<sup>15</sup>, a somewhat larger Sommerfeld constant  $\gamma_{el} \simeq 12$  mJ/(mole K<sup>2</sup>) is found for overdoped LSCO  $x \simeq 0.23$ <sup>34</sup>, suggesting a larger average quasiparticle mass. This is not necessarily inconsistent with the ARPES data. The Fermi-liquid cut-off energy scale,  $\omega_c$ , softens rapidly as a function of Fermi surface angle, and the quasiparticle scattering is globally dependent on momentum<sup>20</sup>. This implies (1) that the contribution from non-Fermi liquid excitations will become increasingly important and (2) that  $\hat{Z} < 1$  on certain portions of the Fermi surface. Both effects would lead to larger quasiparticle masses.

## V. CONCLUSIONS

In summary, we have proven that the nodal single particle excitations observed by ARPES in overdoped LSCO are indeed true Landau Fermi liquid quasiparticle excitations. This result, together with consistent MDC and EDC analysis, was obtained without knowing the exact bare band. From Kramers-Kronig consistency of the quasiparticle self-energy  $\Sigma$ , insight into the bare band  $\epsilon_b$  and the real part of the self-energy  $\Sigma'$  were obtained. An estimate of the nodal quasiparticle residue  $Z = 0.42(7)$  allowed comparison to quasiparticle masses obtained from thermodynamic and high-field quantum oscillation experiments on overdoped  $\text{Ti}_2\text{Ba}_2\text{CuO}_{6+\delta}$  compounds<sup>6</sup>.

*Acknowledgments:* This work was supported by the Swiss NSF (through NCCR, MaNEP, and grant Nos. 200020-105151 and PZ00P2-142434), the Ministry of Education and Science of Japan, and the Swedish Research Council. The experimental work was performed at the SLS of the Paul Scherrer Institut, Villigen PSI, Switzerland. We thank the X09LA beamline<sup>19</sup> staff for their technical support.

<sup>1</sup> D. Pines and P. Nozières, *The theory of quantum liquids* (W. A. Benjamin, 1966).

<sup>2</sup> S. I. Mirzaei, D. Stricker, J. N. Hancock, C. Berthod, A. Georges, E. van Heumen, M. K. Chan, X. Zhao, Y. Li, M. Greven, et al., PNAS **110**, 5774 (2013).

<sup>3</sup> N. Barišić, M. K. Chan, Y. Li, G. Yu, X. Zhao, M. Dressel, A. Smontara, and M. Greven, PNAS **110**, 12235 (2013).

<sup>4</sup> S. Nakamae, K. Behnia, N. Mangkorntong, M. Nohara, H. Takagi, S. J. C. Yates, and N. E. Hussey, Phys. Rev. B **68**, 100502 (2003).

<sup>5</sup> N. Doiron-Leyraud, C. Proust, D. LeBoeuf, J. Levallois, J.-B. Bonnemaison, R. Liang, D. A. Bonn, W. N. Hardy, and L. Taillefer, Nature **447**, 565 (2007).

<sup>6</sup> B. Vignolle, A. Carrington, R. A. Cooper, M. M. J. French,



- A. P. Mackenzie, C. Jaudet, D. Vignolles, C. Proust, and N. E. Hussey, *Nature* **455**, 952 (2008).
- <sup>7</sup> S. E. Sebastian, N. Harrison, and G. G. Lonzarich, *Rep. Prog. Phys.* **75**, 102501 (2012).
  - <sup>8</sup> B. Vignolle, D. Vignolles, D. LeBoeuf, S. Lepault, B. Ramshaw, R. Liang, D. A. Bonn, W. N. Hardy, N. Doiron-Leyraud, A. Carrington, et al., *C. R. Physique* **12**, 446 (2011).
  - <sup>9</sup> Neven Barišić, Sven Badoux, Mun K. Chan, Chelsey Dorow, Wojciech Tabis, Baptiste Vignolle, Guichuan Yu, Jérôme Béard, Xudong Zhao, Cyril Proust and Martin Greven, *Nat. Phys.* **9**, 761-764 (2013).
  - <sup>10</sup> A. Damascelli, Z. Hussain, and Z.-X. Shen, *Rev. Mod. Phys.* **75**, 473 (2003).
  - <sup>11</sup> Jacko, A. C., Fjærestad, J. O., and Powell, B. J., A unified explanation of the Kadowaki-Woods ratio in strongly correlated metals. *Nat. Phys.* **5**, 422-425 (2009).
  - <sup>12</sup> Jernej Mravlje, Markus Aichhorn, Takashi Miyake, Kristjan Haule, Gabriel Kotliar and Antoine Georges, *Phys. Rev. Lett.* **106**, 096401 (2011).
  - <sup>13</sup> Xiaoyu Deng, Jernej Mravlje, Rok Žitko, Michel Ferrero, Gabriel Kotliar and Antoine Georges, *Phys. Rev. Lett.* **110**, 086401 (2013).
  - <sup>14</sup> A. A. Kordyuk, S. V. Borisenko, A. Koitzsch, J. Fink, M. Knupfer, and H. Berger, *Phys. Rev. B* **71**, 214513 (2005).
  - <sup>15</sup> J. Loram, K. Mirza, J. Wade, J. Cooper, and W. Liang, *Physica C: Superconductivity* **235240**, Part 1, 134 (1994).
  - <sup>16</sup> M. Abdel-Jawad, M. Kennett, L. Balicas, A. Carrington, A. Mackenzie, R. H. McKenzie, and N. Hussey, *Nat. Phys.* **2**, 821 (2006).
  - <sup>17</sup> P. M. C. Rourke, A. F. Bangura, T. M. Benseman, M. Matusiak, J. R. Cooper, A. Carrington, and N. E. Hussey, *New Journal of Physics* **12**, 105009 (2010).
  - <sup>18</sup> There are at least two ways to mimic the effect of instrumental resolution. One is to use the measured  $\Gamma_0$  and the width of the Fermi step that already include instrumental resolution. Another method is to use  $\Gamma_0(\text{intrinsic}) = (\Gamma_0^2 - \Gamma_k(\text{res})^2)^{0.5}$ , where  $\Gamma_k(\text{res})$  is the momentum resolution, a Fermi step defined by  $k_B T$  and then convolve this with the instrumental resolution. Both methods were tried with essentially identical results.
  - <sup>19</sup> L. P. U. Flechsig and T. Schmidt, *AIP Conf. Proc.* **705**, 316 (2004).
  - <sup>20</sup> J. Chang, M. Månsson, S. Pailhès, T. Claesson, O. J. Lipscombe, S. M. Hayden, L. Patthey, O. Tjernberg, and J. Mesot, *Nat. Comm.* **4**, 2559 (2013).
  - <sup>21</sup> M. Månsson, T. Claesson, U. O. Karlsson, O. Tjernberg, S. Pailhès, J. Chang, J. Mesot, M. Shi, L. Patthey, N. Momono, et al., *Rev. Sci. Instrum.* **78**, 076103 (2007).
  - <sup>22</sup> O. Lipscombe, S. M. Hayden, B. Vignolle, D. F. McMorro and T. G. Perring, *Phys. Rev. Lett.* **99**, 067002 (2007)
  - <sup>23</sup> Chang, J., et al., *Phys. Rev. B* **85**, 134520 (2012).
  - <sup>24</sup> X. J. Zhou, T. Yoshida, A. Lanzara, P. V. Bogdanov, S. A. Kellar, K. M. Shen, W. L. Yang, F. Ronning, T. Sasagawa, T. Kakeshita, et al., *Nature* **423**, 398 (2003).
  - <sup>25</sup> T. Yoshida, X. J. Zhou, D. H. Lu, S. Komiya, Y. Ando, H. Eisaki, T. Kakeshita, S. Uchida, Z. Hussain, Z.-X. Shen, et al., *J. Phys.: Cond. Matt.* **19**, 125209 (2007).
  - <sup>26</sup> J. Chang, M. Shi, S. Pailhès, M. Månsson, T. Claesson, O. Tjernberg, A. Bendounan, Y. Sassa, L. Patthey, N. Momono, et al., *Phys. Rev. B* **78**, 205103 (2008).
  - <sup>27</sup> E. Abrahams and C. M. Varma, *PNAS* **97**, 5714 (2000).
  - <sup>28</sup> G.-H. Gweon, B. S. Shastry, and G. D. Gu, *Phys. Rev. Lett.* **107**, 056404 (2011).
  - <sup>29</sup> E. Pavarini, I. Dasgupta, T. Saha-Dasgupta, O. Jepsen, and O. K. Andersen, *Phys. Rev. Lett.* **87**, 047003 (2001).
  - <sup>30</sup> J. Geck et al., *Phys. Rev. Lett.* **99**, 046403 (2007)
  - <sup>31</sup> C. Varma, Z. Nussinov, and W. van Saarloos, *Physics Reports* **361**, 267 (2002).
  - <sup>32</sup> J. Kokalj and R. H. McKenzie, *Phys. Rev. Lett.* **107**, 147001 (2011).
  - <sup>33</sup> J. Kokalj, N. E. Hussey, and R. H. McKenzie, *Phys. Rev. B* **86**, 045132 (2012).
  - <sup>34</sup> N. Momono, M. Ido, T. Nakano, M. Oda, Y. Okajima, and K. Yamaya, *Physica C: Superconductivity* **233**, 395 (1994).