

# Interaction Effects on the Magneto-optical Response of Magnetoplasmonic Dimers

N. de Sousa

*Departamento de Física de la Materia Condensada,  
Universidad Autónoma de Madrid, E-28049 Madrid, Spain*

L. S. Froufe-Pérez

*Instituto de Estructura de la Materia,  
CSIC, Serrano 121, E-28006 Madrid, Spain*

G. Armelles, A. Cebollada, M. U. González, F.

García, D. Meneses-Rodríguez, and A. García-Martín\*

*IMM-Instituto de Microelectrónica de Madrid (CNM-CSIC),  
Issac Newton 8, PTM, E-28760 Tres Cantos, Madrid, Spain*

## Abstract

The effect that dipole-dipole interactions have on the magneto-optical (MO) properties of magnetoplasmonic dimers is theoretically studied. The specific plasmonic versus magnetoplasmonic nature of the dimer's metallic components and their specific location within the dimer plays a crucial role on the determination of these properties. We find that it is possible to generate an induced MO activity in a purely plasmonic component, even larger than that of the MO one, therefore dominating the overall MO spectral dependence of the system. Adequate stacking of these components may allow obtaining, for specific spectral regions, larger MO activities in systems with reduced amount of MO metal and therefore with lower optical losses. Theoretical results are contrasted and confirmed with experiments for selected structures.

PACS numbers: 78.20.Ls, 73.20Mf, 78.66.Bz

---

\* a.garcia.martin@csic.es

Smart nanoscale systems are able to interact with light in an intricate fashion, [1] which is strongly dependent on the internal electromagnetic interaction between the constituent elements of the system. Plasmonic structures composed by a number of individual elements, for example, give rise to Fano resonance effects that induce Electromagnetically Induced Transparency (EIT). [2–8] Similar phenomena have also been found in magnetoplasmonic nanosystems,[9] those sharing magnetic and plasmonic functionalities and that therefore allow a further degree of freedom, namely the external control of the system response. [10–14] By an adequate design of their internal structure, it is possible to obtain configurations which provide enhanced MO activity upon plasmon resonance excitation, [15–18] which allow probing the EM field distribution inside a metallic nanoelement, [19] or which yield high MO activity and low optical losses with MO figures of merit comparable with those of garnet structures.[13] Furthermore, in dimers where one of the elements is purely plasmonic and the other is of magnetoplasmonic nature, interaction effects cause the magnetoplasmonic component to induce MO activity in the plasmonic one (which intrinsically lacks MO activity).[20] For specific inter-element distances, which determines the interaction between them, this brings as a consequence the equivalent of the EIT in the MO spectrum of the system, *i.e.* a cancelation of the MO activity in a narrow spectral range due to the competition between the intrinsic MO contribution of the magnetoplasmonic component and the induced MO contribution of the plasmonic one.[20] As this effect exhibits a narrow spectral feature in the MO response, it may find applications in sensing and telecommunication areas, and a complete understanding will help to the development of novel sensing and biosensing architectures as well as MO devices.

In this context, these induced MO activity effects and its influence on the overall MO activity of the system for specific ranges of interaction lead to consider additional issues where the electromagnetic interaction between these elements is relevant but remains unaddressed. For example: Is it possible to devise a configuration for which the MO activity induced in the non MO-active element is even larger than that of the MO active one? Even more, does the MO response depend in a continuous, gradual fashion with the amount of MO active component? Moreover, in systems where both components are MO active, does the MO response behaves simply as the sum of those of the two components?

With this in mind, the goal of this work is to consider theoretically and experimentally these issues by presenting a detailed study of the interaction effects in a model sys-

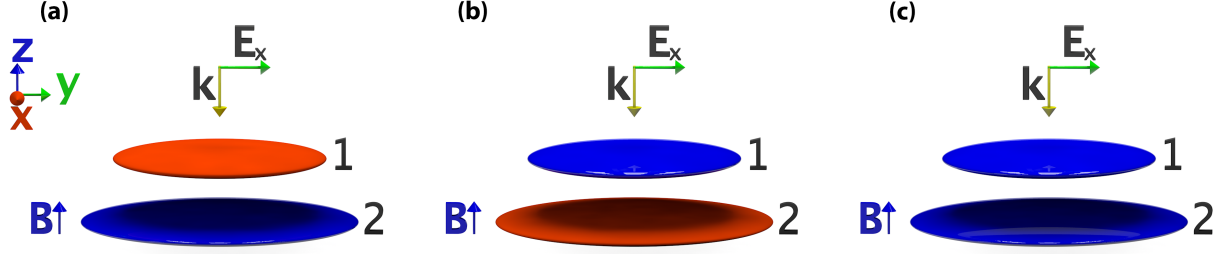


FIG. 1. Color online. Schematic representation of the studied configurations.

(a) The lower dipole is MP whereas the upper one is P, (b) the lower dipole is P whereas the upper disk is MP, (c) both disks are MP.

tem formed by two coupled nanodisks separated by a dielectric in a nanopillar geometry when the plasmonic or magnetoplasmonic nature of the nanodisk components is changed. Namely, we present results for three different geometries: first assuming that the bottom disk is magnetoplasmonic and the top one is plasmonic; second the inverse situation (i.e. top magnetoplasmonic, bottom plasmonic); and finally the case in which both nanodisks are magnetoplasmonic in nature. For the theoretical description we will follow two approaches, an analytic one in which each disk is considered as a point dipole (with the proper polarizability) and a numerical one based on FDTD techniques in which the real internal structure of the disks is taken into account. The first, simple approach allows distinguishing the contribution of each of the elements separately, giving detailed information about the underlying physics. The second, full numerical approach, permits the validation of the obtained insights. These theoretical results will be contrasted with experimental data of equivalent systems obtained by hole mask colloidal lithography and evaporation.

The geometry is similar to that previously considered in Refs. [6, 13, 20], where two metallic disks (each one can be magneto-optically active) are vertically aligned and separated by a dielectric spacer. We approximate each disk by an oblate spheroid with an aspect ratio that corresponds to dimensions of previously fabricated disks (see Fig. 1). Since the actual fabricated structures have a truncated cone shape, the aspect ratio of the bottom dipole must be larger than that of the top one. For non-magneto-optical, plasmonic dipoles (P) we consider a diagonal, isotropic, dispersive dielectric tensor (Au). For the magnetoplasmonic (MP) dipole we consider an average medium that combines the dielectric tensor

of a noble metal and that of a ferromagnetic one (Au and Co in this case) giving rise to a non-diagonal dielectric tensor. The non-zero off-diagonal elements depend on the relative orientation of the geometry, of the exciting radiation and of the magnetic field. In our case the external magnetic field is aligned perpendicular to the dipoles (i.e. aligned along the stacking direction, see Fig. 1), which corresponds to the so called polar Kerr configuration, and the dielectric tensor of the MP dipole presents the form:

$$\boldsymbol{\epsilon} = \begin{pmatrix} \epsilon_d & \epsilon_M & 0 \\ -\epsilon_M & \epsilon_d & 0 \\ 0 & 0 & \epsilon_d \end{pmatrix}. \quad (1)$$

Depending of the amount of Co within the MP disk, the elements of the dielectric tensor read as:

$$\epsilon_d = (1 - \nu) \epsilon_{d,Au} + \nu \epsilon_{d,Co}; \quad \epsilon_M = \nu \epsilon_{M,Co} \quad (2)$$

where  $\nu = \frac{V_{Co}}{V_{Co} + V_{Au}}$  is the Co relative amount in each dipole.

Once the dielectric tensor is known, we can obtain the static polarizability of a dipole, that, considered as an oblate particle in air, is given by:[21]

$$\tilde{\alpha}_0 = 4\pi a^2 c \frac{\boldsymbol{\epsilon} - \mathbb{I}}{3\mathbb{I} + 3\mathbf{L}(\boldsymbol{\epsilon} - \mathbb{I})}, \quad (3)$$

where  $a$  and  $c$  are the in-plane and out of plane dimensions of the oblate spheroids (see Fig. 1),  $\boldsymbol{\epsilon}$  is the dielectric tensor of the material and  $\mathbf{L}$  the geometrical tensor. To insure the optical theorem is fulfilled, we apply the radiative correction to the static polarizability:[22]

$$\tilde{\alpha} = \frac{\tilde{\alpha}_0}{\mathbb{I} - i \frac{k^3}{6\pi} \tilde{\alpha}_0}. \quad (4)$$

Sometimes it is convenient to work with scaled magnitudes, so that polarizability  $\tilde{\alpha}$ , polarization  $\tilde{p}$  and green tensor  $\tilde{G}$ , become  $\alpha_i = (k^3/4\pi)\tilde{\alpha}_i$ ,  $p_i = (k^3/4\epsilon_0\pi)\tilde{p}_i$ ,  $G = (4\pi/k)\tilde{G}$ . Once we have the polarizability for oblate particles, we are able to describe each disk as a single dipole. Its properties (material, shape and dimensions) are embedded in the polarizability. From coupled dipole theory we know that the interaction between dipoles is mediated by the Green tensor  $G$ . If an incident planar wave, with wavenumber  $k$  and with electric polarization in the plane of the dipoles, is used to excite the system (see Fig. 1) the

two dipoles can be described in the x-y plane as:

$$\begin{aligned}\mathbf{p}_1 &= \boldsymbol{\alpha}_1 [\mathbf{E}_{0,1} + G(\mathbf{r}_1, \mathbf{r}_2) \mathbf{p}_2] \\ \mathbf{p}_2 &= \boldsymbol{\alpha}_2 [\mathbf{E}_{0,2} + G(\mathbf{r}_2, \mathbf{r}_1) \mathbf{p}_1],\end{aligned}\tag{5}$$

where the Green tensor and the polarizability, in this case, are

$$\begin{aligned}G(\mathbf{r}_1, \mathbf{r}_2) &= G(\mathbf{r}_2, \mathbf{r}_1) = \mathcal{G} \mathbb{I}_{2 \times 2} = \frac{e^{ikr}}{kr} \left( \frac{(kr)^2 + ikr - 1}{(kr)^2} \right) \mathbb{I}_{2 \times 2}, \\ \alpha_i &= \begin{pmatrix} \alpha_i & \alpha_{iM} \\ -\alpha_{iM} & \alpha_i \end{pmatrix}\end{aligned}\tag{6}$$

where  $r$  is the distance between the two dipoles.

The general solution of that system of Eqs. under the influence of a plane wave linearly polarized along the x-axis, and amplitude  $E_0$  at dipole 1 is given by:

$$\begin{aligned}p_{1x} &= \frac{E_0}{\mathcal{D}} [\alpha_1 + \mathcal{G}e^{-ikr}(\alpha_2\alpha_1 - \alpha_{2M}\alpha_{1M}) - \mathcal{G}^2\alpha_2D_1 - \mathcal{G}^3e^{-ikr}D_1D_2] \\ p_{2x} &= \frac{E_0}{\mathcal{D}} [e^{-ikr}\alpha_2 + \mathcal{G}(\alpha_2\alpha_1 - \alpha_{2M}\alpha_{1M}) - \mathcal{G}^2e^{-ikr}\alpha_1D_2 - \mathcal{G}^3D_1D_2] \\ p_{1y} &= \frac{E_0}{\mathcal{D}} [-\alpha_{1M} - \mathcal{G}e^{-ikr}(\alpha_1\alpha_{2M} + \alpha_2\alpha_{1M}) - \mathcal{G}^2\alpha_{2M}D_1] \\ p_{2y} &= \frac{E_0}{\mathcal{D}} [-e^{-ikr}\alpha_{2M} - \mathcal{G}(\alpha_1\alpha_{2M} + \alpha_2\alpha_{1M}) - \mathcal{G}^2e^{-ikr}\alpha_{1M}D_2],\end{aligned}\tag{7}$$

where  $\mathcal{D} = 1 - 2\mathcal{G}^2(\alpha_2\alpha_1 - \alpha_{2M}\alpha_{1M}) + \mathcal{G}^4D_1D_2$ , and  $D_i = \alpha_i^2 + \alpha_{iM}^2$ . Note that the y-component of both dipoles is not zero when at least one of the dipoles is MO active.

For the particular geometry we are analyzing, the external magnetic field produces a change in the polarization state of the reflected light, and the magneto-optical activity (MOA) of the whole system, defined as the modulus of the complex Kerr rotation, can be written as :

$$\text{MOA} = |\theta + i\phi| = \text{atan} \left| \frac{E_y^R}{E_x^R} \right| \approx \left| \frac{p_{1,y} + p_{2,y}}{p_{1,x} + p_{2,x}} \right| = \frac{(|p_{1,y}|^2 + |p_{2,y}|^2 + 2|p_{1,y}||p_{2,y}|\cos(\Delta))^{\frac{1}{2}}}{(|p_{1,x}|^2 + |p_{2,x}|^2 + 2|p_{1,x}||p_{2,x}|\cos(\Gamma))^{\frac{1}{2}}}.\tag{8}$$

From the interaction point of view there are three different regimes that are determined by the distance between the interacting dipoles: strong interaction (very close dipoles), weak interactions (very far away objects) and medium interaction (intermediate distance). We will concentrate on the most interesting case of medium interactions,[20] and will analyze two

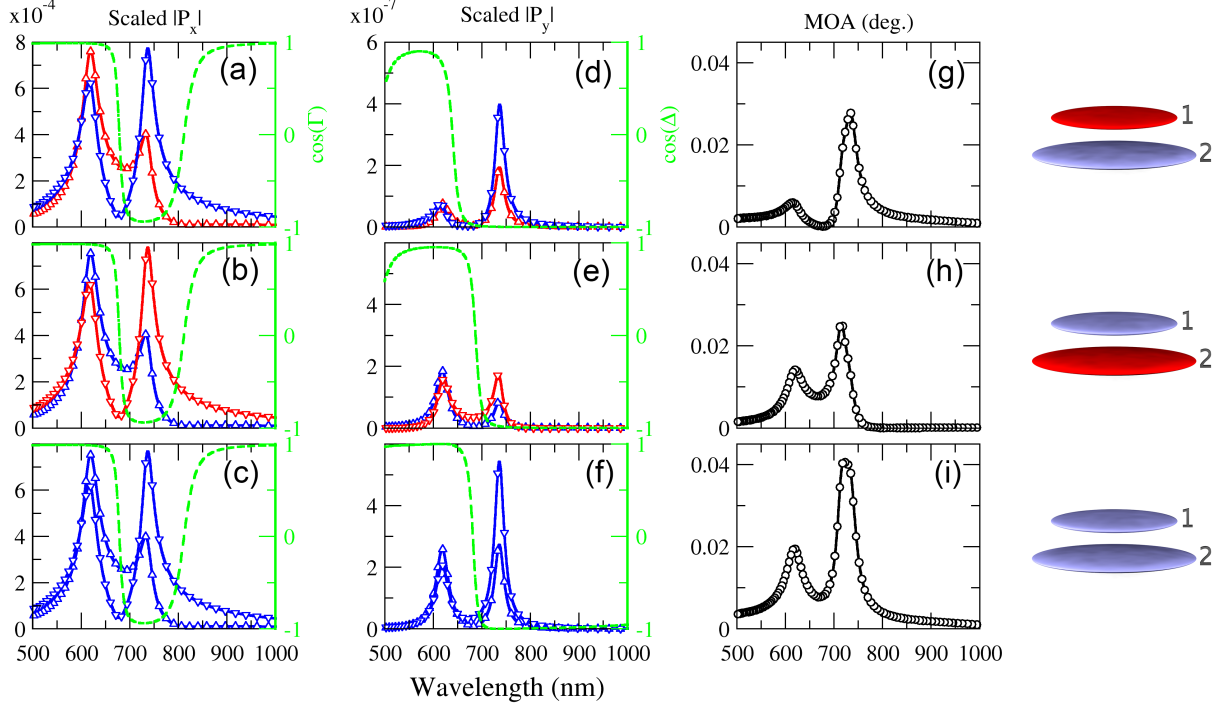


FIG. 2. Color online. Dipole contributions, and MOA for 0.1% Co concentration. (a)-(c) x-component of the scaled dipole (left axis) and the cosine of the relative phase between them (right axis), (d)-(f) y-component of the scaled dipole (left axis), and their relative phase (right axis), (g)-(i) magneto-optical activity. The upper panels represent the situation where the MP dipole is at the bottom, the medium panels are when the MP dipole is at the top, the lower panels when both are MP. Triangle-up for the top dipole, and triangle down for the bottom dipole.

situations: one in which the amount of Co in the magneto-optical disk is very small (0.1%) and a second one where it is comparable to the Au amount (25%). For the analysis, the aspect ratios of the dipoles are  $a/c = 13$  and  $10$  for the bottom and top dipoles respectively.

Let us start with the case of very small Co concentration (0.1%) in the MP dipole. In Fig. 2 we show the modulus of the components of the dipole along  $x$ , the polarization direction of the incident beam ( $p_{i,x}$ ), and along  $y$  direction ( $p_{i,y}$ ), as well as that of the complex Kerr rotation (MO activity, MOA) calculated with this simple analytical model for the situations where the MP dipole is at the bottom, top and in both positions of the structure. The cosine of relative phases between the  $p_{i,x}$  ( $\cos \Gamma$  in Fig. 2 (a)-(c)) and  $p_{i,y}$  ( $\cos \Delta$  in Fig. 2(d)-(f)) components of the upper and lower disks (dashed curves) are also shown, with limit values

of 1 and -1 for in-phase and out-of-phase oscillations, respectively.

Considering first the x-component of the dipoles (Fig. 2 (a)-(c)), and due to the low Co concentration, there is no noticeable difference between the three situations. All cases show two characteristic low- (740 nm) and high- (620nm) energy modes of antisymmetric and symmetric nature respectively, [6, 13, 20] as directly concluded by the obtained relative phase between the two dipoles. The abrupt change in sign of the cosine occurs exactly at the minimum in magnitude of both dipoles. For energies below roughly 760 nm the phase gradually changes again, going back to an in-phase configuration for wavelengths larger than 820 nm. Regarding the relative contribution of both disks to these  $p_x$  spectral features, the low energy mode has a stronger component originating from the bottom disk (down-triangles) than from the top one, (up-triangles), since it has a lower aspect ratio. The situation is reversed for the high energy peak, even though the difference between the contributions of the two dipoles is smaller.

Beyond the purely optical properties, fully understandable by simply considering  $p_x$ , the direct consequence of the application of a magnetic field is the generation of a y-component in the dipole [20, 23] (Fig. 2(d)-(f)). Contrary to what is observed in the x-component, now different results are obtained depending on the specific position of the MP active dipole.

Let us examine each situation individually. When the MP dipole is at the bottom, a y-component is observed not only in this dipole, but also in the P top one, which is due to the interaction between the dipoles. This y-component is stronger for the bottom MP dipole in the low energy region, but they are similar in the high energy region. Even more, in the spectral region where the x-component of the MP dipole is minimum, the y-component of *both* dipoles is almost zero, even though the x-component of the P dipole in the same intermediate region is not negligible. This is simply due to the fact that the y-component is originated by the magnetic field induced rotation of the MP dipole, which in turn induces the rotation of the upper P dipole. Thus, a y-component dipole can be originated *only* if the x-component of the MP active dipole is not zero. Additionally, the relative phases between the two dipoles along the y-axes show essentially the same symmetric/antisymmetric configuration for the corresponding high/low energy modes compared to those for the x-components, even though now they do not return to in-phase values for energies below 800 nm. The presence of  $p_y$  is directly related to the presence of MO activity in the system (Fig. 2 (g)). Indeed, as shown in Eq. 8, this magnitude is basically the modulus of the sum of the

y-components of the top and bottom dipoles divided by that of the x-components. Therefore, the spectral dependence of MOA can be understood in simple terms considering these four dipole components, taking into account their relative phases. So, in this first considered case with the bottom MP dipole, the high energy peak results from the addition of both (top and bottom dipoles) y-components, while the low energy one results from the corresponding difference, since in this energetic range the y-components are in phase opposition.

If we consider now the situation where the MP dipole is on the top of the structure, the results are very different. Strikingly, here the obtained y-component in the low energy region is larger for the P dipole than for the MP one, while both components are similar for the high energy region. This means that the contribution to the MOA (Fig. 2 (h)) coming from the P dipole in the low energy region is actually stronger than that of the MP one. This is simply due to the larger x-component of the P dipole in the low energy region, which also explains why the y-components in the high energy region are of similar magnitude for both MP and P dipole in the previous case. On the other hand, regarding the intermediate spectral region, and due to the non vanishing x-component of the MP dipole in this range, both the y-components (especially of the P dipole) and the MOA are not zero.

Finally, if both disks have MO component the intensity of the  $p_y$  components increases for both dipoles and within each mode they follow the same trend as the corresponding x-component. Besides, for all the energy regions the intensity of the MOA is larger than that of the other two configurations.

Going towards a more realistic situation, with larger Co amounts in the MP dipoles, in Fig. 3 we show theoretical calculations equivalent to those shown in Fig. 2 but using the dipole model with a 25% Co content in the different MP dipoles. As it can be seen in Fig. 3(a)-(c), and contrary to what was observed for low Co concentrations, now the  $p_x$  components are very different depending on the specific position MP dipole. The effect of increasing the Co amount is both to broaden the peaks and to change their absolute and relative intensities, as well as their energetic position, both for  $p_x$  and  $p_y$  components. Due to the much larger amount of Co (250 times more Co) in this case, the magnitudes of the  $p_x$  and  $p_y$  components are now very different (between a factor of 2 to 4 reduction in the x-component due to the increased losses, and roughly one order of magnitude larger in the y-component due to the much larger amount of MO material). Even more, for this concentration, all these effects also depend on the specific location of the MP dipole.



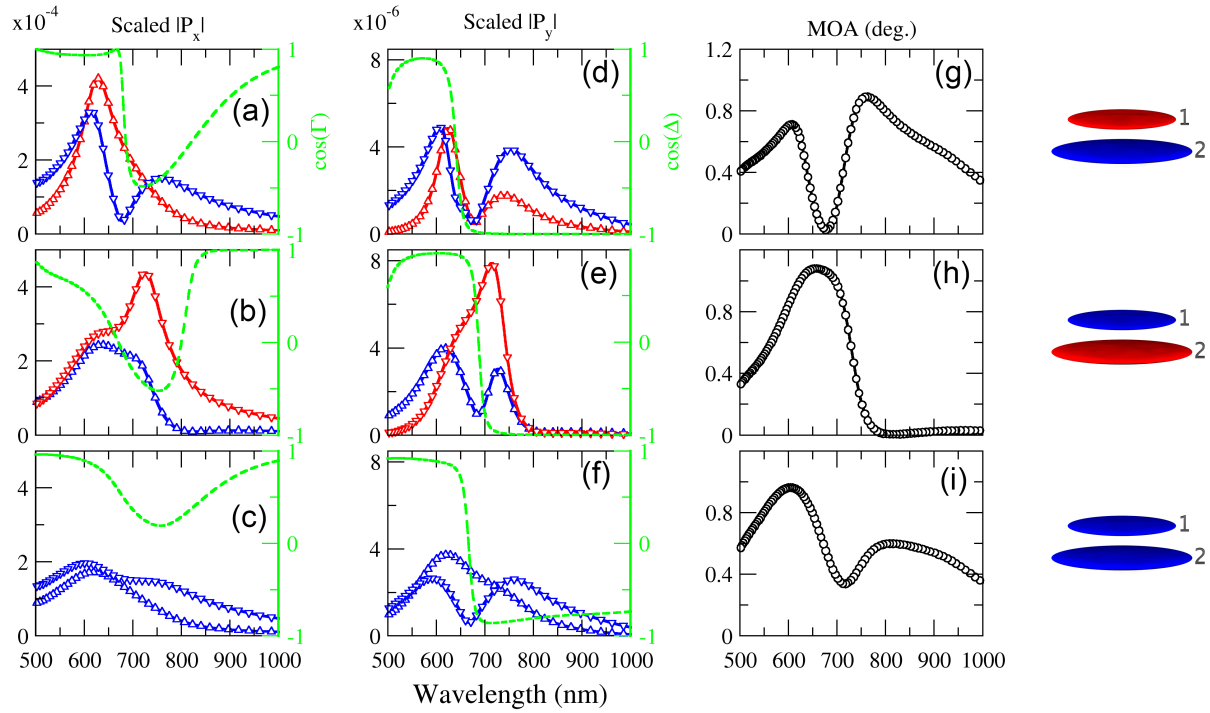


FIG. 3. Color online. Dipole contributions, and MOA for 25% Co concentration. (a)-(c) x-component of the scaled dipole (left axis) and the cosine of the relative phase between them (right axis), (d)-(f) y-component of the scaled dipole (left axis), and their relative phase (right axis), (g)-(i) magneto-optical activity. The upper panels represent the situation where the MP dipole is at the bottom, the medium panels are when the MP dipole is at the top, the lower panels when both are MP. Triangle-up for the top dipole, and triangle down for the bottom dipole

For the configuration with the MP dipole at the bottom, the low energy peak in the MOA has a stronger component due to the bottom dipole (as seen in the low Co concentration case) and the increase of the Co amount brings as a consequence both a reduction of the relative intensity for the x-component and a broadening for both x- and y-components. However, the high energy peak, with a stronger contribution from the upper P dipole, is less affected since no Co is present in it. Again, a minimum in the y-component in the intermediate energy region yields a minimum in the MO activity. Regarding the relative phases, for the  $p_x$  components it is clear now that they do not reach the perfect out-of phase configuration, indicating that now the nature of the modes is not purely but only partially antisymmetric. This is due to the sizeable amount of Co present in the dipoles, which enhances the losses

of the system and affects the retardation between the two coupled dipole x-components. However, for the y-components, the phase basically reproduces the same behavior observed for the very low concentration limit.

Going now to the situation where the MP dipole is in the upper part, the most affected peak (for all  $p_x$ ,  $p_y$  and MOA) due to the incorporation of Co is the high energy one, since it is the one which carries a stronger part of the upper dipole. We therefore observe a change in the relative intensity with respect to the case with the MP dipole in the bottom. Remarkably, in this situation the y-component of the P dipole is much larger than that of the MP one in the low energy part of the spectrum, due to the interaction effects and to the very large x-component of this P dipole. Now, due to both the broadening and spectral overlapping of the y-components of both top and bottom dipoles, only one broad peak is observed in the MOA. This peak is mainly originated by the induced y-component in the bottom dipole, which is not MO active. Regarding the phase of the y-component, it is worth noticing that it is again exactly the same as for the low Co concentration, i.e. it does not depend on the Co concentration. If one considers Eq. 7, and makes either  $\alpha_{1M}$  or  $\alpha_{2M}$  equal to zero, the ratio between the y-components of the P and MP dipoles becomes  $p_{y,NMO}/p_{y,MO} = \mathcal{G}\alpha_{NMO}$ , i.e. it does not depend on the MO active element, and thus the relative phase does not depend on the Co content.

Finally, when both dipoles are MP, the larger amount of Co implies that the total losses are even larger, and therefore the peaks in the x-components are weaker and broader. The direct consequence of this reduction in the x-components is that the y-components are also somehow weaker and broader compared to the other two cases with only one MP dipole. Now, for the x-component the two peaks overlap for the bottom dipole and only one broad peak is observed for the top one, which is also the same behavior basically observed for the y-component. Regarding the MOA, two well distinguishable peaks are observed and, surprisingly, the low energy one yields lower MO activity than the corresponding peak for the other two cases (only one MP dipole), contrary to what was observed for low Co concentration. This is due to the smaller difference of intensities between the y-components of the two dipoles in this case and to the fact that in this spectral region they are out-of-phase. Briefly, this complex behavior of relative intensities and phases induces a smaller MOA even when more MP components are present in this dimer.

Let us summarize the preceding discussion. When two dipoles interact, one of them

presenting MO activity (MP dipole), this MP dipole can induce MOA in the non-MO active (purely plasmonic, P) one. The induced MOA can be even much larger than the intrinsic one (see low energy region of Figs. 2e and 3e). This occurs in the spectral region of the resonance of the P dipole. On the other hand, if the system is composed of two MP, lossy dipoles (high Co content), the resulting MOA response can be much lower than that obtained when only one dipole is MP (see Figs. 3g-i). This has important consequences in real magnetoplasmonic systems composed of noble metals and ferromagnetic metals. One would naively think that the MOA is to be enhanced by increasing the number of MP components, but then the losses will increase in parallel. Our results show that an adequate stacking of the system components may allow devising structures with higher MO activity using overall lower amounts of ferromagnetic content.

Despite the simplicity of the two interacting dipoles model, it describes quite well the outcome of the interaction between disks in magnetoplasmonic dimers. For example, in Fig. 4 we present the experimental MO activity for three different samples. They consist of a layer of two metallic disks separated by 20nm of SiO<sub>2</sub> deposited on a glass substrate. The three samples have a homogeneous distribution of the disks, with a filling factor of 15%. The diameter of the disks ranges from 130nm to 150nm. They were obtained by hole mask colloidal lithography, metal evaporation and lift off. [24] The internal structure of the disks is presented in the rightmost panel of Fig. 4. The disks dimensions are the same as those of the disks in Ref. [20]. In sample a, the bottom disk consists of a Au/Co multilayer (MP) and the top one is a Au disk (P); in sample b, the top disk is a Au/Co multilayer (MP) and the bottom one a Au disk (P); and finally, in sample c, both disks are Au/Co multilayers (MP).

As it can be observed, when the bottom disks are magnetoplasmonic, samples a and c, the MOA spectrum has two peaks. Despite the lower Co contents of sample a, the lower energy peak has a higher intensity in this sample than in sample c, where the two disks are magnetoplasmonic. Moreover, the MOA spectrum of sample b has only one peak, whose intensity is also greater than the intensity of the low energy peak of sample c. Additionally, in Fig. 4 we also present a FDTD theoretical calculation which takes into account the internal structure of the disks. As it can be observed, these calculations reproduce quite well the experimental behavior, and the results are also equivalent to those obtained with the previously exposed analytical approach for intermediate interactions (Fig. 3). The

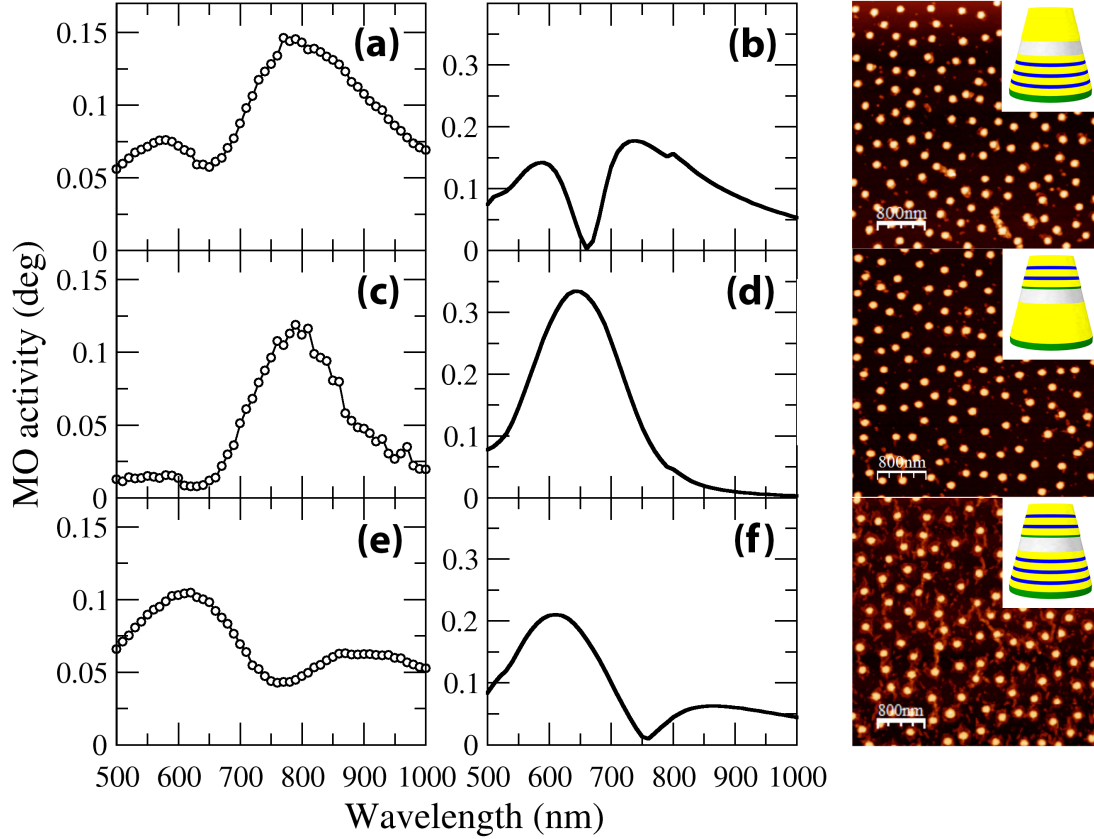


FIG. 4. Color online. Experimental results (a) and numerical simulations (b) of the MO activity when the MP disk is at the bottom, (c),(d) are the same but when the MP disk is at the top, and (e),(f) when both are MP. In the rightmost panel we show AFM images of the three experimental samples where the density of disks (about 15% coverage) and homogeneity can be seen. The images show that the disk diameter ranges from 130nm to 150nm. Also is represented a scheme of the structures. In green we depict the Ti adhesive layer, in blue the Co layers, grey is the  $\text{SiO}_2$  and yellow are the gold layers. The three different systems are constituted by two metallic disks separated by 20nm of  $\text{SiO}_2$ . For the configuration with the MP disk at the bottom (top panels), the MP disk is composed of a 2nm Ti layer followed by a 4nm Au layer and three sequential combinations of 2nm Co/4nm Au layers. The disk at the top is composed by 16nm Au. For the configuration with MP disk at the top, the MP disk is composed by an initial 1nm layer of Ti then 4nm Au layer and two sequences of 2nm Co/4nm Au layers. The disk at the bottom is composed by 22nm of gold. When both disks are MP, they consist of those Au/Co sequences employed in the other two situations.

numerical calculations have been made using 130nm for the diameter of base of the cone and 100nm for the top in all cases. An increase in these numbers would cause a red shift of the peaks.

In conclusion, we have analyzed the effect of electromagnetic interactions on the MO response of magnetoplasmonic dimers composed of two metallic disks separated by a dielectric. The MO response strongly depends on the plasmonic versus magnetoplasmonic nature of the two disks, observing for specific configurations that the MO response can be dominated by the induced MOA of the purely plasmonic disk. On the other hand, the MO activity of a system with only one of the disks containing material with intrinsic MO can be even larger than that of a system composed of two MP disks. A simple analytical model of two interacting point dipoles allows us to fully describe separately the contribution of each disk to the optical and MOA of the system, along with the relative phases of the dipoles responsible for these activities. Experimental results and numerical calculations fully support the analytical calculations results.

## ACKNOWLEDGMENTS

We acknowledge H. Feng for his assistance in the growth of some of the studied samples. Funding from Spanish Ministry of Economy and Competitiveness through grants “FUNCOAT” CONSOLIDER CSD2008– 00023, and MAPS MAT2011–29194- C02–01, and from Comunidad de Madrid through grants “NANOBIOMAGNET” S2009/MAT-1726 and “MICROSERES-CM” S2009/TIC-1476 is acknowledged. L.S. F.-P. acknowledges support from the European Social Fund and CSIC through a JAE-Doc grant.

- 
- [1] M. Aeschlimann, M. Bauer, D. Bayer, T. Brixner, F. J. García de Abajo, W. Pfeiffer, M. Rohmer, C. Spindler, and F. Steeb, *Nature* **446**, 301 (2007).
  - [2] M. Hentschel, M. Saliba, R. Vogelgesang, H. Giessen, A. P. Alivisatos, and N. Liu, *Nano Letters* **10**, 2721 (2010).
  - [3] J. B. Lassiter, H. Sobhani, J. A. Fan, J. Kundu, F. Capasso, P. Nordlander, and N. J. Halas, *Nano Letters* **10**, 3184 (2010).

- [4] K.-H. Su, Q.-H. Wei, X. Zhang, J. Mock, D. R. Smith, and S. Schultz, *Nano Letters* **3**, 1087 (2003).
- [5] W. Rechberger, A. Hohenau, A. Leitner, J. Krenn, B. Lamprecht, and F. Aussenegg, *Optics Communications* **220**, 137 (2003).
- [6] A. Dmitriev, T. Pakizeh, M. Käll, and D. S. Sutherland, *Small* **3**, 294 (2007).
- [7] L. V. Brown, H. Sobhani, J. B. Lassiter, P. Nordlander, and N. J. Halas, *ACS Nano* **4**, 819 (2010).
- [8] C. Wadell, T. J. Antosiewicz, and C. Langhammer, *Nano Letters* **12**, 4784 (2012).
- [9] G. Armelles, A. Cebollada, A. García-Martín, and M. U. González, *Advanced Optical Materials* **1**, 10 (2013).
- [10] V. V. Temnov, G. Armelles, U. Woggon, D. Guzatov, A. Cebollada, A. Garcia-Martin, J. M. Garcia-Martin, T. Thomay, A. Leitenstorfer, and R. Bratschitsch, *Nature Photonics* **4**, 107 (2010).
- [11] V. I. Belotelov, I. A. Akimov, M. Pohl, V. A. Kotov, S. Kasture, A. S. Vengurlekar, A. V. Gopal, D. R. Yakovlev, A. K. Zvezdin, and M. Bayer, *Nature Nanotechnology* **6**, 370 (2011).
- [12] V. Bonanni, S. Bonetti, T. Pakizeh, Z. Pirzadeh, J. Chen, J. Nogués, P. Vavassori, R. Hillenbrand, J. Åkerman, and A. Dmitriev, *Nano Letters* **11**, 5333 (2011).
- [13] J. C. Bantón, D. Meneses-Rodríguez, F. García, M. U. González, A. García-Martín, A. Cebollada, and G. Armelles, *Advanced Materials* **24**, OP36 (2012).
- [14] J. Y. Chin, T. Steinle, T. Wehler, D. Dregely, T. Weiss, V. I. Belotelov, B. Stritzker, and H. Giessen, *Nature Communications* **4**, 1599 (2013).
- [15] J. B. González-Díaz, A. García-Martín, J. M. García-Martín, A. Cebollada, G. Armelles, B. Sepúlveda, Y. Alaverdyan, and M. Käll, *Small* **4**, 202 (2008).
- [16] P. K. Jain, Y. Xiao, R. Walsworth, and A. E. Cohen, *Nano Letters* **9**, 1644 (2009).
- [17] L. Wang, C. Clavero, Z. Huba, K. J. Carroll, E. E. Carpenter, D. Gu, and R. A. Lukaszew, *Nano Letters* **11**, 1237 (2011).
- [18] H. Marinchio, J. J. Sáenz, and R. Carminati, *Physical Review B* **85**, 245425 (2012).
- [19] D. Meneses-Rodríguez, E. Ferreira-Vila, P. Prieto, J. Anguita, M. U. González, J. M. García-Martín, A. Cebollada, A. García-Martín, and G. Armelles, *Small* **7**, 3317 (2011).
- [20] G. Armelles, A. Cebollada, A. García-Martín, M. González, F. García, D. Meneses-Rodríguez, N. de Sousa, and L. Froufe-Pérez, *Optics Express* **21**, 27356 (2013).

- [21] C. F. Bohren and D. R. Huffman, *Absorption and Scattering of Light by Small Particles* (Wiley, Weinheim, Germany, 1983).
- [22] S. Albaladejo, R. Gomez-Medina, L. S. Froufe-Perez, H. Marinchio, R. Carminati, J. F. Torrado, G. Armelles, A. Garcia-Martin, and J. J. Saenz, *Optics Express* **18**, 3556 (2010).
- [23] B. Sepúlveda, J. B. González-Díaz, A. García-Martín, L. M. Lechuga, and G. Armelles, *Physical Review Letters* **104**, 147401 (2010).
- [24] H. Fredriksson, Y. Alaverdyan, A. Dmitriev, C. Langhammer, D. S. Sutherland, M. Zäch, and B. Kasemo, *Advanced Materials* **19**, 4297 (2007).