

Magnetic properties of epitaxial Fe_3O_4 films with various crystal orientations and TMR effect in room temperature

Taro Nagahama,^{1, a)} Yuya Matsuda,¹ Kazuya Tate,¹ Shungo Hiratani,¹ Yusuke Watanabe,¹ Takashi Yanase,¹ and Toshihiro Shimada¹

Graduate School of Engineering, Hokkaido University, Kita13 Nishi8, Kitak-ku, Sapporo, 060-8628, Japan

(Dated: 28 October 2018)

Fe_3O_4 is a ferrimagnetic spinel ferrite that exhibits electric conductivity at room temperature (RT). Although the material has been predicted to be a half metal according to ab-initio calculations, magnetic tunnel junctions (MTJs) with Fe_3O_4 electrodes have demonstrated a small tunnel magnetoresistance effect. Not even the sign of the TMR ratio has been experimentally established. Here, we report on the magnetic properties of epitaxial Fe_3O_4 films with various crystal orientations. The films exhibited apparent crystal orientation dependence on hysteresis curves. In particular, $\text{Fe}_3\text{O}_4(110)$ films exhibited in-plane uniaxial magnetic anisotropy. With respect to the squareness of hysteresis, $\text{Fe}_3\text{O}_4(111)$ demonstrated the largest squareness. Furthermore, we fabricated MTJs with $\text{Fe}_3\text{O}_4(110)$ electrodes, and obtained an TMR effect of -12% at RT. The negative TMR ratio corresponded to the negative spin polarization of Fe_3O_4 predicted from band calculations.

^{a)}nagahama@eng.hokudai.ac.jp

Half metals that have 100% spin polarization (P) at the Fermi level are key materials to fabricate spintronic devices because their high spin polarization enables very large magnetoresistance effects. The most impressive case is in magnetic tunnel junctions (MTJs) with epitaxial MgO tunnel barriers^{1,2}. As transport in MgO-MTJs is dominated by coherent tunneling of Δ_1 electrons with 100% spin polarization, the TMR ratio has reached 600% at RT³. Such a large TMR ratio has allowed us to fabricate highly functional spintronic devices like magnetoresistive random access memories (MRAMs). However, MTJs with MgO have stringent limitations where the crystal orientation should be bcc (001) due to band structure matching between MgO and the electrodes. Half metal is the solution to large TMR ratios without restricting the crystal structure or orientation. Thus far, many oxide materials have been proposed as candidates for half metals, e.g., CrO_2 ⁴, $\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3$ ⁵, and Fe_3O_4 ⁶. Of these materials, Fe_3O_4 has been considered to be the most promising as a half metal because of its high Curie temperature of 858 K, which is an advantage in applications to spintronic devices that require high Tc. The crystal structure is an inverse spinel with Fe^{3+} cations occupying tetrahedral sites (A sites) and Fe^{3+} and Fe^{2+} cations occupying octahedral sites (B sites). The magnetic couplings between A and B sites are antiferromagnetic and the couplings at A-A or B-B are ferromagnetic; consequently, it is a ferrimagnetic material. As Fe_3O_4 exhibits good electric conductivity at RT due to the hopping of electrons between Fe^{2+} and Fe^{3+} on the B sites⁷, the conduction electrons are 100% spin polarized. As hopping is frozen on cooling, conductivity greatly decreases at low temperature, which is known as Verwey transition. The transition temperature, T_v , is 120K⁸. The saturation magnetization of bulk Fe_3O_4 is 510 emu/cc⁹. According to Julliere's formula¹⁰, MTJs with Fe_3O_4 electrodes are expected to exhibit very high TMR ratios due to large spin polarization. To date, researchers have fabricated MTJs with Fe_3O_4 and measured magnetoresistance; however, the TMR ratios have been small. Although the reason for this is not completely understood, such small TMR ratios can be attributed to imperfect antiparallel magnetic states in MTJs¹¹. The magnetization process of Fe_3O_4 films should be improved to achieve clear parallel and antiparallel magnetic configurations. We prepared epitaxial Fe_3O_4 films with various crystal orientations, and investigated their crystalline qualities and magnetic properties. We also fabricated MTJs with Fe_3O_4 electrodes and observed a negative TMR effect of -12%.

The Fe_3O_4 thin films were prepared with three crystal orientations of (001), (110), and

(111) by using a molecular beam epitaxy (MBE) system. The sample structures were:

- 1) an MgO(001) substrate/MgO (20 nm)/Fe₃O₄ (60 nm),
- 2) an MgO(110) substrate/MgO (20 nm)/Fe₃O₄ (60 nm), and
- 3) an Al₂O₃(0001) substrate/Pt (20 nm)/Fe₃O₄ (60 nm).

Following the deposition of MgO or Pt buffer layers, Fe₃O₄ thin film was formed by reactive deposition at a temperature (T_{sub}) of 300°C in an O₂ atmosphere of 4×10^{-4} Pa. Then, the films were annealed at 600°C for 30 min in an O₂ atmosphere. The partial pressure of O₂ gas was 1×10^{-4} Pa during annealing. All the samples were fabricated under the same growth conditions to enable the quality of Fe₃O₄ films to be compared. Epitaxial growth was observed with reflection high energy electron diffraction (RHEED) and the surface morphology was observed with atomic force microscopy (AFM). We also investigated the magnetization process at RT with a vibrating sample magnetometer (VSM).

Figs. 1 (a) and (b) show the RHEED patterns of Fe₃O₄(100) before and after O₂ annealing at 600°C for 30 min. The electron beam was incident along [100]. Fig. 1 (c) is an atomic force micrograph (AFM) of Fe₃O₄(100) after annealing. A streak RHEED pattern can be observed in Fig. 1 (a) meaning the Fe₃O₄ film grew epitaxially. In addition, p(1x1) surface reconstruction was observed^{12,13}. The streak pattern sharpened after annealing at 600°C in the O₂ atmosphere, as can be seen from Fig. 1 (b). A step-terrace structure can be confirmed from the AFM in Fig. 1 (c). The roughness average, R_a , was 0.12 nm, and the terrace width was 200 nm.

Figs. 1 (d)-(f) show the RHEED patterns and AFMs of Fe₃O₄(110) grown on MgO(110). The incident electron beam direction was [-110]. A spotty pattern was obtained before annealing due to the island growth of Fe₃O₄ (110). However, the surface flatness was improved dramatically by O₂ annealing at 600°C, as can be seen from the RHEED pattern in Fig. 1 (e). The surface in the AFM of Fe₃O₄(110) after annealing in Fig. 1 (f) had anisotropic shapes along [100], which seemed to originate from the anisotropy of the MgO(110) substrate. R_a was estimated to be 0.39 nm.

Finally, Figs. 1 (g)-(i) show RHEED patterns and AFMs of Fe₃O₄(111). The direction of the incident electron beam was [11-20]. Fig. 1(g) shows RHEED patterns of as-deposited Fe₃O₄(111). It shows streak patterns that indicate a flat surface and surface reconstruction. Terrace and step structures can be observed in the AFM of Fe₃O₄(111) after annealing in Fig. 1 (i); however, islands with a diameter of 200 nm and height of several tens of nanometers

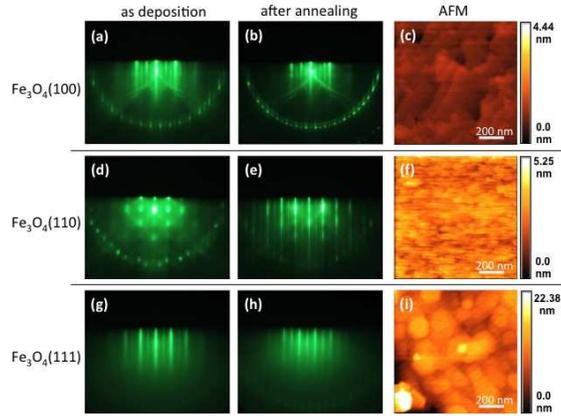


FIG. 1. RHEED patterns and AFMs of epitaxial Fe_3O_4 (60 nm) films. RHEED patterns were taken after deposition at 300°C and annealing at 600°C . AFM observations were carried out after annealing. (a), (b), and (c) are for $\text{MgO}(100)/\text{Fe}_3\text{O}_4(100)$ (60 nm). (d), (e), and (f) are for $\text{MgO}(110)/\text{Fe}_3\text{O}_4(110)$ (60 nm). (g), (h), and (i) are for $\text{Al}_2\text{O}_3(0001)/\text{Pt}(111)$ (20 nm)/ $\text{Fe}_3\text{O}_4(111)$ (60 nm).

were observed on the surface (not shown) in the AFM of a large area. The R_a was estimated at 2.40 nm, which was one order of magnitude larger than the other crystal orientations. The large roughness could be attributed to the lattice mismatch between Fe_3O_4 and the Pt buffer layer¹⁴. As the lattice constant of Fe_3O_4 was 0.8397 nm and that of MgO was 0.421 nm, the lattice mismatch was about 0.3%. However, as the lattice constant of Pt was 0.392 nm, Fe_3O_4 lattice mismatch to the Pt buffer layer was 6.6%. Such large lattice mismatch could give rise to a larger surface roughness for $\text{Fe}_3\text{O}_4(111)$ than that for $\text{Fe}_3\text{O}_4(100)$.

The magnetization curves at RT for the Fe_3O_4 films are plotted in Fig. 2. The magnetic field was applied in plane. The diamagnetic components of the substrates were subtracted under the assumption that the magnetizations of the Fe_3O_4 were saturated at 5 kOe, which is the maximum field of VSM. The magnetization curve of Fe_3O_4 (100) is in Fig. 2 (a). The saturation magnetization (M_s) was 330 emu/cc, the remanent magnetization (M_r) was 100 emu/cc, and the coercive field (H_c) was 80 Oe. The remanent magnetization ratio (M_r/M_s) was 0.30. Fig. 2(b) plots the magnetization curves of Fe_3O_4 (110) where the directions of the magnetic field were [001] and [-110]. The saturation magnetization was 185 emu/cc for both magnetic field directions. M_r , H_c , and M_r/M_s in the magnetic field along [001] were

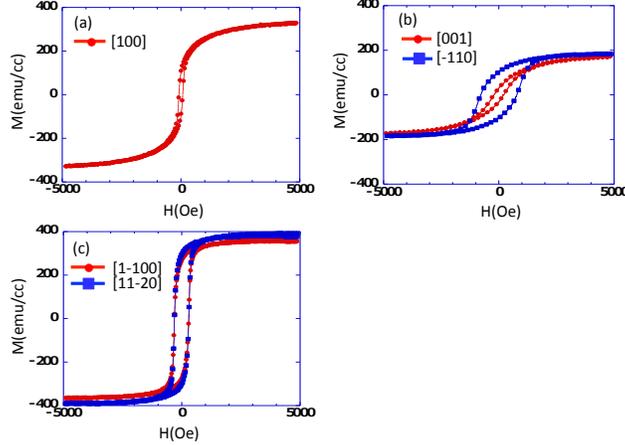


FIG. 2. Hysteresis curves obtained from VSM measurements at RT for epitaxial Fe_3O_4 films with various crystal orientations. (a) is $\text{Fe}_3\text{O}_4(100)$, (b) is $\text{Fe}_3\text{O}_4(110)$, and (c) is $\text{Fe}_3\text{O}_4(111)$. Directions of magnetic fields are given in plots.

30 emu/cc, 210 Oe, and 0.16, and those for $[-110]$ were 100 emu/cc, 780 Oe, and 0.54. The magnetization process strongly depended on the directions of the magnetic field, viz., the squareness and M_r/M_s were larger for the $[-110]$ magnetic field than those for $[100]$. Nevertheless, the films had an anisotropic shape along the $[100]$ direction, as shown in Fig. 1(f), and the films had a larger remanent ratio in the $[-110]$ direction. Therefore, the anisotropy in Fig. 2 (b) was attributed to the magneto-crystalline anisotropy in Fe_3O_4 . Saturation magnetization was 390 emu/cc, remanent magnetization was 290 emu/cc, and coercivity was 300 Oe in the magnetization curve of $\text{Fe}_3\text{O}_4(111)$. The remanent magnetization ratio was approximately 0.74, which was the largest value in the three crystal directions. The magnetic process was almost independent of the field directions. These values are summarized in Table 1. All the films exhibited smaller saturated magnetizations than the value for bulk Fe_3O_4 of 510 emu/cc. The reason for this is that the external field was not sufficient to saturate the magnetic moments in the Fe_3O_4 films. According to previous studies, Fe_3O_4 thin films contain considerable numbers of antiphase boundaries (APBs)¹⁵ that make the Fe_3O_4 hard to saturate magnetically due to antiferromagnetic coupling at the APBs.

We fabricated the MTJs with $\text{Fe}_3\text{O}_4(110)$ electrodes, and measured the tunnel magnetoresistance effect. The film structure was $\text{MgO}(110)/\text{NiO}(110)$ (5 nm)/ $\text{Fe}_3\text{O}_4(110)$ (60 nm)/ Al_2O_3 (2.4 nm)/Fe (5 nm)/Co (10 nm)/Au (30 nm). The NiO layer was inserted to suppress the diffusion of Mg from the substrates. Junctions of $10 \times 10 \mu\text{m}^2$ were fabricated

TABLE I. Magnetic characteristics of Fe_3O_4 films with various crystal orientations.

	M_s (emu/cc)	M_r (emu/cc)	H_c (Oe)	M_r/M_s
$\text{Fe}_3\text{O}_4(100)$	330	100	80	0.30
$\text{Fe}_3\text{O}_4(110)$ H//[001]	185	30	210	0.16
$\text{Fe}_3\text{O}_4(110)$ H//[-110]	185	100	780	0.54
$\text{Fe}_3\text{O}_4(111)$	390	290	300	0.74

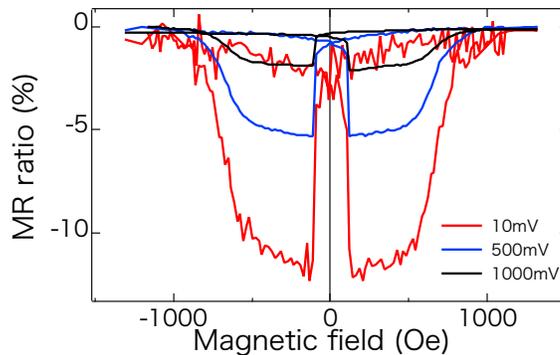


FIG. 3. TMR curve for MTJ of $\text{MgO}(110)/\text{NiO}(110)$ (5 nm)/ $\text{Fe}_3\text{O}_4(110)$ (60 nm)/ Al_2O_3 (2.4 nm)/Fe (5 nm)/Co (10 nm)/Au (30 nm) at RT. Red, blue, and black lines are TMRs with bias voltages of 10, 500, and 1000 mV.

by photolithography, Ar ion milling, and sputtering. The junctions demonstrated a clear TMR effect of -12% at RT, as shown in Fig. 3. The negative MR agreed with the ab-initio calculations that predicted negative spin polarization in Fe_3O_4 . To the best of our knowledge, these are the first experimental results of a negative MR ratio with an AlO barrier and Fe_3O_4 electrodes¹⁶¹⁷¹⁸¹⁹²⁰. The polarization of Fe_3O_4 deduced from the MR ratio based on Julliere's formula was -16%, in which the polarization of Fe/ Al_2O_3 was assumed to be 40%²¹. Although the polarization was much smaller than the predicted value, -16% is of the same order as the reported values using various barrier materials²²²³.

Fe_3O_4 epitaxial films with various crystal orientations were fabricated by reactive MBE and all the films grew epitaxially. The Fe_3O_4 (110) films exhibited clear uniaxial magnetic anisotropy that originated from crystal anisotropy. The squareness of the hysteresis curves strongly depended on the crystal orientation. A negative MR ratio of -12% was observed in

the MTJs with $\text{Fe}_3\text{O}_4(110)$ electrodes. Although the absolute value was small, the negative MR agreed with the theoretical predictions.

We would like to express our gratitude to Prof. Yamamoto's group for the cooperation in microfabrications. This work was supported by JSPS KAKENHI Grant-in-Aid for Young Scientists (A) Grant Number 23686006 and the Collaborative Research Program of Institute for Chemical Research, Kyoto University (grant 2014-75).

REFERENCES

- ¹S. Yuasa, T. Nagahama, A. Fukushima, Y. Suzuki, and K. Ando, "Giant room-temperature magnetoresistance in single-crystal fe/mgo/fe magnetic tunnel junctions," *Nature materials* **3**, 868–871 (2004).
- ²S. S. Parkin, C. Kaiser, A. Panchula, P. M. Rice, B. Hughes, M. Samant, and S.-H. Yang, "Giant tunnelling magnetoresistance at room temperature with mgo (100) tunnel barriers," *Nature materials* **3**, 862–867 (2004).
- ³S. Ikeda, J. Hayakawa, Y. Ashizawa, Y. Lee, K. Miura, H. Hasegawa, M. Tsunoda, F. Matsukura, and H. Ohno, "Tunnel magnetoresistance of 604% at 300 k by suppression of ta diffusion in cofeb/mgo/cofeb pseudo-spin-valves annealed at high temperature," *Applied Physics Letters* **93**, 082508–082508 (2008).
- ⁴J. M. D. Coey and M. Venkatesan, "Half-metallic ferromagnetism: Example of cro_2 (invited)," *Journal of Applied Physics* **91**, 8345–8350 (2002).
- ⁵B. Nadgorny, I. I. Mazin, M. Osofsky, R. J. Soulen, P. Broussard, R. M. Stroud, D. J. Singh, V. G. Harris, A. Arsenov, and Y. Mukovskii, "Origin of high transport spin polarization in $\text{la}_{0.7}\text{sr}_{0.3}\text{mno}_3$: Direct evidence for minority spin states," *Phys. Rev. B* **63**, 184433 (2001).
- ⁶A. Yanase and K. Siratori, "Band structure in the high temperature phase of fe_3o_4 ," *Journal of the Physical Society of Japan* **53**, 312–317 (1984).
- ⁷G. F. Dionne, *Magnetic Oxides* (Springer, 2010).
- ⁸E. Verwey, "Electronic conduction of magnetite (fe_3o_4) and its transition point at low temperatures," *Nature* **144**, 327–328 (1939).
- ⁹S. Chikazumi, *Physics of Ferromagnetism 2e*, 94 (Oxford University Press, 2009).
- ¹⁰M. Julliere, "Tunneling between ferromagnetic films," *Physics Letters A* **54**, 225 – 226 (1975).

- ¹¹C. Tiusan, T. Dimopoulos, K. Ounadjela, and M. Hehn, “Field-dependent domain structure evolution in artificial ferrimagnets analyzed by spin-polarized tunnel transport in magnetic tunnel junctions,” *Physical Review B* **64**, 104423 (2001).
- ¹²S. A. Chambers, S. Thevuthasan, and S. A. Joyce, “Surface structure of mbe-grown $\text{Fe}_3\text{O}_4(001)$ by x-ray photoelectron diffraction and scanning tunneling microscopy,” *Surface science* **450**, L273–L279 (2000).
- ¹³G. Tarrach, D. Bürgler, T. Schaub, R. Wiesendanger, and H.-J. Güntherodt, “Atomic surface structure of $\text{Fe}_3\text{O}_4(001)$ in different preparation stages studied by scanning tunneling microscopy,” *Surface science* **285**, 1–14 (1993).
- ¹⁴S. A. Chambers, “Epitaxial growth and properties of thin film oxides,” *Surface Science Reports* **39**, 105 – 180 (2000).
- ¹⁵D. Margulies, F. Parker, M. Rudee, F. Spada, J. Chapman, P. Aitchison, and A. Berkowitz, “Origin of the anomalous magnetic behavior in single crystal Fe_3O_4 films,” *Physical review letters* **79**, 5162 (1997).
- ¹⁶K.-i. Aoshima and S. X. Wang, “ Fe_3O_4 and its magnetic tunneling junctions grown by ion beam deposition,” *Journal of Applied Physics* **93**, 7945–7956 (2003).
- ¹⁷H. Matsuda, M. Takeuchi, H. Adachi, M. Hiramoto, N. Matsukawa, A. Odagawa, K. Setsumi, and H. Sakakima, “Fabrication and magnetoresistance properties of spin-dependent tunnel junctions using an epitaxial Fe_3O_4 film,” *Japanese Journal of Applied Physics* **41**, L387–L390 (2002).
- ¹⁸M. Opel, S. Gepraegs, E. P. Menzel, A. Nielsen, D. Reisinger, K.-W. Nielsen, A. Brandlmaier, F. D. Czeschka, M. Althammer, M. Weiler, *et al.*, “Novel multifunctional materials based on oxide thin films and artificial heteroepitaxial multilayers,” *physica status solidi (a)* **208**, 232–251 (2011).
- ¹⁹P. Seneor, A. Fert, J.-L. Maurice, F. Montaigne, F. Petroff, and A. Vaurès, “Large magnetoresistance in tunnel junctions with an iron oxide electrode,” *Applied Physics Letters* **74**, 4017–4019 (1999).
- ²⁰C. Park, Y. Shi, Y. Peng, K. Barmak, J.-G. Zhu, D. Laughlin, and R. M. White, “Interfacial composition and microstructure of Fe_3O_4 magnetic tunnel junctions,” *Magnetics, IEEE Transactions on* **39**, 2806–2808 (2003).
- ²¹R. Meservey and P. Tedrow, “Spin-polarized electron tunneling,” *Physics Reports* **238**, 173–243 (1994).

- ²²G. Hu and Y. Suzuki, “Negative spin polarization of Fe_3O_4 in magnetite/manganite-based junctions,” *Physical review letters* **89**, 276601 (2002).
- ²³L. Alldredge, R. Chopdekar, B. Nelson-Cheeseman, and Y. Suzuki, “Spin-polarized conduction in oxide magnetic tunnel junctions with magnetic and nonmagnetic insulating barrier layers,” *Applied physics letters* **89**, 182504–182504 (2006).