Superconductivity at 4K in Pd deficient layered Ta₂Pd_xS₆

Brajesh Tiwari¹, Babu Baijnath Prasad^{1,2}, Rajveer Jha¹, Dharmendra Kumar Singh¹ and V.P.S. Awana^{1,*}

¹National Physical Laboratory, New Delhi-110012, India ²Sri Murli Manohar Town Post Graduate College Ballia. 277001, India

Strong spin-orbit coupled 4d and 5d transition metal based compounds such as $(Nb/Ta)_2Pd_x(S/Se/Te)_y$ have gained renewed research interests due to their superconducting properties, exotic such as exceptionally large upper critical fields, being surpassing the Pauli paramagnetic limit, H_p~1.84T_c, their multi band nature and pressure independent superconducting transition temperature (T_c) [1-8]. In a very recent experimental observations Lu et. al [6] first reported that Ta₂Pd_xS₅ exhibit metal to superconducting transition at around 6K with three times higher upper critical field, $H_{c2}(0)$, to that as constrained by Pauli paramagnetic limit. This is theoretically explained by considering the multiband superconductivity in strong coupling regime [7].

The $Ta_2Pd_xS_6$ compounds were first synthesized and characterized in mid 1980's [9,10]. Following the reports available [1-8] on superconductivity of (Nb/Ta)Pd(S/Se/Te) compounds. the identification of right phase and composition of them seems to be the major issue yet. Further, the role of Pd-centered square planer structure needs to be probed in detail to comprehend the extraordinary physical properties in Pd-based chalcogenide superconductor [1-8].

Here in this short note, we report on the low dimensional 4d and 5d transition metals-chalcogenide based compounds i.e.. $Ta_2Pd_xS_6$, showing semiconducting to superconducting transition around 4K with upper critical field outside Pauli paramagnetic limit. On the other hand in Ta₂Pd_xS₅ phase, a metallic normal state with T_c~ 6K is seen [6]. It seems couple of different superconducting phases do exist in these new set of compounds. Our short note in this regards is thought provoking, asking to explore various unearthed possible superconducting phases in $(Nb/Ta)_2Pd_x(S/Se/Te)_y$ systems.

In this study, we focus on the polycrystalline samples with nominal composition $Ta_2Pd_xS_6$; x=0.97, 0.94. The stoichiometric ratio of elemental powder of Ta, Pd and S in 2:x:6 were mixed thoroughly in Arcontrolled glove-box and pelletized by uniaxial 100 kg/cm² stress. The pellets were sealed separately in evacuated quartz tubes and heated to 800°C and 850°C for 24h with intermediate grinding. The obtained samples are used for structural and transport

measurements. The structure of the samples were identified by Rietveld refinement of powder XRD pattern recorded using Rigaku made machine with Cu K α (λ =1.54Å) x-ray source. Resistivity of bulk samples were measured by standard linear four probe method on Quantum Design make Physical Property Measurement System (PPMS).

Figure 1(a) shows the XRD patterns for $Ta_2Pd_{0.97}S_6$ and $Ta_2Pd_{0.94}S_6$ and their corresponding Rietveld refinements with two of their monoclinic phases with space group C2/m having two different stoichiometries i.e., $Ta_2Pd_xS_6$ and $Ta_2Pd_xS_5$ (x=0.97 and 0.94).

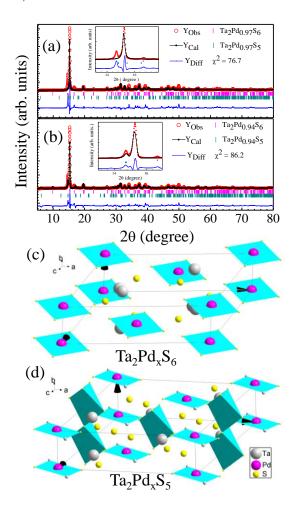


Figure 1 (Color online). Rietveld refinement for powder XRD patterns of compounds (a) $Ta_2Pd_{0.97}S_6$ and (b) $Ta_2Pd_{0.94}S_6$ with monoclinic space group C2/m. The XRD patterns are refined simultaneously for the two different crystal structures (c) $Ta_2Pd_xS_6$ (magenta bars) and (d) $Ta_2Pd_xS_5$ (cyan bars), respectively.

It is observed that though the samples were not single phase, the major phase (> 80% by volume fraction) in these samples belongs to composition Ta₂Pd_xS₆, along with minor Ta₂Pd_xS₅ phase. The corresponding crystal structures are shown in figure 1(b) and (c) respectively. The obtained lattice parameters for Ta₂Pd_{0.94}S₆ phase are a=11.79Å, b=3.27Å, c=9.93Å, $\beta=115.6^{\circ}$ while for Ta₂Pd_{0.94}S₅ the same are a=12.31Å, b=3.29Å, c=14.56Å, $\beta=102.7^{\circ}$. A small increase in *a* and *c* lattice parameters is found for Ta₂Pd_{0.97}S₆, which are close to earlier reported values for the same phase [10].

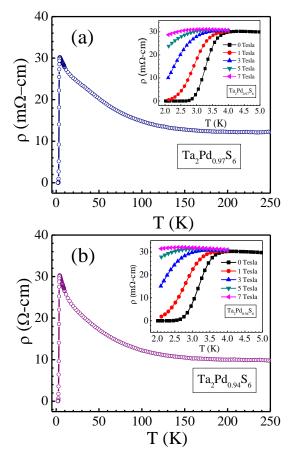


Figure 2 (Color online). Temperature (T) dependences of resistivity (ρ) for compounds (a) Ta₂Pd_{0.97}S₆ and (b) Ta₂Pd_{0.94}S₆, whereas insets show ρ verses T at different applied magnetic fields upto 7 Tesla, respectively.

Figure 2 shows the temperature dependences of electrical resistivity for compounds (a) $Ta_2Pd_{0.97}S_6$ and (b) Ta₂Pd_{0.94}S₆ down to 2 K. A clear semiconducting normal state can be observed in variance to recent report by Lu et.al [6] which observed metallic normal state in Ta₂Pd_xS₅ stoichiometry. $Ta_2Pd_{0.97}S_6$ (and $Ta_2Pd_{0.94}S_6$) shows superconducting $T_c^{onset} =$ transition with onset temperature 3.96K (3.76K) and estimated dH_{c2}/dT based on 90% criteria of normal state resistivity is -4.43Tesla/K (and -3.53Tesla/K). The estimated H_{c2} (0) is 12Tesla (and 9.2Tesla), which is clearly above Pauli's paramagnetic limit of 7.3Tesla for these 4K superconductors. For the determination of upper critical field we used the formula $H_{c2}(0) = -0.69T_c \left(\frac{dH_{c2}}{dT}\right)_{T=T_c}$ based on model developed by Werthamer Helfand and Hohenberg (WHH) true for BCS type superconductors [11]. These observations suggest entirely different and a new superconducting phase in Pd-based compound Ta₂Pd_xS₆. The detailed study is underway on role of sulfur stoichiometry on the structure and physical properties of Ta₂Pd_xS_{6- δ} based superconductors.

In summary, we have synthesized Pd-deficient monoclinic compounds with major $Ta_2Pd_xS_6$ stoichiometry. We have shown by temperature dependent resistivity measurements that $Ta_2Pd_xS_6$ have normal state semiconducting to superconducting transition at about 4 K. It is observed that these compounds are rather robust against external magnetic field. Observation of superconductivity in heavy transition metal-based chalcogenide may add to new dimensions in superconducting research.

Acknowledgement: Authors would like to thank their Director NPL India and for financial support by *DAE-SRC* scheme on search for new superconductors. BBP thanks IASs, India for summer research fellowship.

References:

[1]. Q. Zhang, G. Li, D. Rhodes, A. Kiswandhi, T. Besara, B. Zeng, J. Sun, T. Siegrist, M. D. Johannes, and L. Balicas, *Sci. Rep.*, **3**, 1446 (2013).

- [2]. R. Jha, B. Tiwari, P. Rani, H. Kishan and V. P. S. Awana, *J. Appl. Phys.* **115**, 213903 (2014).
- [3]. C. Q. Niu, J. H. Yang, Y. K. Li, B. Chen, N. Zhou, J. Chen, L. L. Jiang, B. Chen, X. X. Yang, C. Cao, J. Dai, and X. Xu *Phys. Rev. B*, **88**, 104507 (2013)
- [4]. H. Yu, M. Zuo, L. Zhang, S. Tan, C. Zhang and Y. Zhang, J. Am. Chem. Soc., **135** (35), 12987 (2013).
- [5]. S. Khim, B. Lee, Ki-Y. Choi, B.-Gu Jeon, D. H. Jang, D. Patil, S. Patil, R. Kim, E. S. Choi, S. Lee, J. Yu and K. H. Kim, *New J. of Phys.*, **15**, 123031(2013).
- [6]. Y. Lu, T. Takayama, A. F. Bangura, Y. Katsura, D. Hashizume and H. Takagi, *J. Phys. Soc. Jpn.*, **83**, 023702 (2014).
- [7]. D. J. Singh, Phys. Rev. B, 88, 174508 (2013).
- [8]. W. H. Jiao, Z. T. Tang, Y. L. Sun, Y. Liu, Q. Tao,
 C. M. Feng, Y. W. Zeng, Z. A. Xu and G. H. Cao J.
 Am. Chem. Soc., 136 (4), 1284 (2014).
- [9]. P. J. Squattritto, S. A. Sunshine and J. A. Ibers, J. Solid State Chem. **64**, 261 (1986).
- [10]. D. A. Keszler, P. J. Squattrito, N. E. Brese, J. A. Ibers, S. Maoyu, and L. Jiaxi, *Inorg. Chem.*, **24**, 3063 (1985).

[11]. N. R. Werthamer, E. Helfand, and P. C. Hohenberg, *Phys. Rev.*, **147**, 295 (1966).