

Nickel-Titanium double perovskite: A three-dimensional spin-1 Heisenberg antiferromagnet

M. Karolak, M. Edelmann and G. Sangiovanni

*Institut für Theoretische Physik und Astrophysik,
Universität Würzburg, Am Hubland, D-97074 Würzburg, Germany*

(Dated: March 2, 2022)

The double perovskite $\text{La}_2\text{NiTiO}_6$ is identified as a three-dimensional $S=1$ quantum magnet. By means of Density Functional Theory we demonstrate that this material is a high-spin d -electron system deep in the Heisenberg limit and establish that its paramagnetic Mott phase persists down to low temperatures (experimental Néel temperature $T_N \sim 25\text{K}$) not because of frustration effects but rather for strong local fluctuations of the magnetic order parameter. Our many-body calculations on an *ab initio*-derived multi-orbital basis predict indeed a kinetic energy gain when entering the magnetically ordered phase. $\text{La}_2\text{NiTiO}_6$ emerges thus as a paradigmatic realization of a Hund's coupling-driven Mott insulator. Its peculiar properties may turn out to be instrumental in the ongoing chase after correlated topological states of matter.

PACS numbers: 71.27.+a, 71.10.Fd, 71.15.Mb, 75.10.Dg

I. INTRODUCTION

Nickel (Ni) in d^8 configuration has been attracting growing attention for the possibility to realize the “Haldane” $S=1$ spin-chain^{1–6}. In compounds like CsNiCl_3 or NiTa_2O_6 the Ni atoms are connected via small hopping integrals t along specific one-dimensional paths and charge fluctuations are strongly suppressed by the large on-site Hubbard repulsion U . This allows for a theoretical description in terms of the 1D-Heisenberg model with an antiferromagnetic superexchange coupling $J \propto t^2/U$. In two dimensions the interest in $S=1$ quantum antiferromagnets has been somewhat hidden by the widely investigated spin-1/2 t - J model, related to the physics of underdoped high- T_c cuprates. Ni is again present in some of the $S=1$ bulk materials with strong 2D character, such as La_2NiO_4 or K_2NiF_4 ^{7–11}. In an interesting recent proposal Chen, *et al.* suggested to artificially design a 2D spin-1 Mott insulator upon heterostructuring Ni and Ti single perovskites¹².

In 3D spin-1 quantum magnets are found in pyrochlore compounds, such as ZnV_2O_4 or MgV_2O_4 ^{13–15}, where the absence of magnetic ordering down to very low temperatures is, however, due to frustration rather than to the strong-coupling regime in U . Some face-centered cubic (fcc) transition-metal oxides with $S=1$ are described in terms of spin-only models with nearest- (90°) and next-nearest neighbor (180°) exchange couplings J_1 and J_2 , respectively. While this is fully justified for NiS_2 ^{16,17}, which belongs to the family of frustrated magnets ($J_2/J_1 \approx 0.5$), NiO ¹⁸ and KNiF_3 ¹⁹, together with d^2 -vanadates^{20,21}, are actually quite far from the strong-coupling Heisenberg limit, due to the significant hybridization between the transition-metal ions and the “bridging” ligand atoms. Charge fluctuations indeed still play a role as also reflected by the relevant d -electron bandwidth, which in these compounds hardly gets smaller than $\sim 1.5\text{--}2.0\text{eV}$. As a matter of fact, the majority of the spin-1 three-dimensional transition-metal

compounds that we know of, fall into one or both of the following categories: materials with relatively high magnetic ordering temperatures and pretty far from a true strong-coupling Heisenberg limit, or quantum magnets where long-range order is suppressed by sizable geometrical frustration. The examples that are lacking for $S=1$ in 3D are those of nearly unfrustrated cases with small values of the ratio t/U , i.e. the repulsive counterpart of phase-fluctuation driven Bose-Einstein physics. In such materials, the strong coupling regime would determine the low magnetic ordering temperatures $T_N \propto J$.

Here we demonstrate that the Nickel double perovskite $\text{La}_2\text{NiTiO}_6$ is a perfect realization of the latter class of systems. As we show in our calculation, the reason why this $S=1$ quantum antiferromagnet is deep into the Heisenberg limit comes from its distinctive hierarchy of magnetic exchange couplings: $J_2 \gg J_1$. $\text{La}_2\text{NiTiO}_6$ can therefore be very well described by $S=1$ spins living on a weakly frustrated three-dimensional fcc lattice^{23–25}. In order to fully describe the residual charge fluctuations, which in spin-1 systems may be relevant due to the importance of biquadratic effects as well as three-body interactions^{30–33}, we also go beyond the bilinear spin-only description and investigate the antiferromagnetic (AFM) phase in the “full” Hubbard model. This allows us to make a thermodynamic analysis of $\text{La}_2\text{NiTiO}_6$ revealing a kinetic-energy driven ordering mechanism.

The low value of the Néel temperature $T_N \sim 25\text{K}$ ³⁶ in $\text{La}_2\text{NiTiO}_6$ has the interesting consequence that its paramagnetic Mott insulating state can be observed in an unusually extended range of temperatures. Even though its properties as a Mott insulator have not been discussed hitherto, it is important to stress that $\text{La}_2\text{NiTiO}_6$ can actually be synthesized, as described in Refs. 34–38. Here we connect its features as a high-spin paramagnet with the peculiar electronic structure: a half-filled e_g manifold at the Fermi level which is extremely narrow and uncommonly well separated from any other band. The origin of this lies in the isotropic reduction of the hoppings in

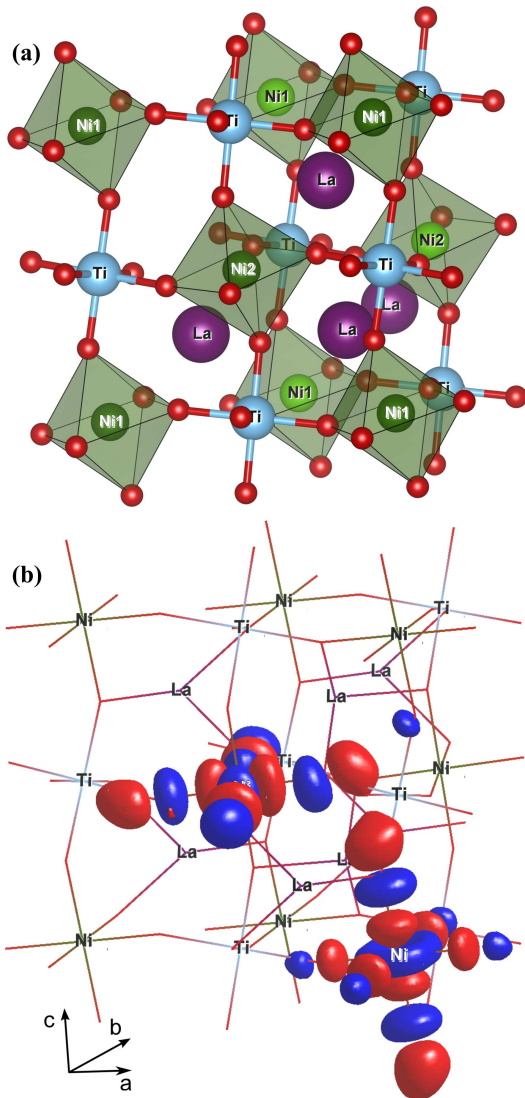


FIG. 1. (color online) (a) Crystal structure of $\text{La}_2\text{NiTiO}_6$. (b) Isosurfaces of Wannier functions obtained by projection of only the Ni e_g bands. The upper left one is mainly of x^2-y^2 character and the lower right mainly of $3z^2-r^2$ character. The coordinate system gives the directions used in Tab. I and also applies to panel (a).

all three spatial directions, something hardly possible to achieve artificially but that nature does very effectively, replacing the Ni-O-Ni bonds characteristic of other $S=1$ materials with longer Ni-O-Ti-O-Ni ones. This class of d^8 - d^0 double perovskites can open new directions in oxide engineering: by considering also heavier elements of the Ni group and upon splitting the e_g bands by heterostructuring or strain a correlation-driven band inversion can be realized, as in recent theoretical proposals for interacting topological insulators^{39–43}.

II. ELECTRONIC STRUCTURE

$\text{La}_2\text{NiTiO}_6$ crystallizes in a double perovskite structure with a small monoclinic distortion ($P2_1/n$ space group), as determined from neutron powder diffraction experiments^{36–38}. Structural relaxation within Density Functional Theory (DFT) using the GGA (PBE)⁴⁴ functional results only in minor changes to the experimentally measured structure. The Ni-Ni distances along the a and b axes are 7.85 Å, while along c the distance is 7.83 Å. The Ni/TiO₆ octahedra display a very small Jahn-Teller distortion (the lengths of the Ni/Ti-O bonds differ by at most 0.4%) and show an alternating tilting (see Fig. 1a).

For the paramagnetic calculations we consider a unit cell containing two formula units whereas the magnetic cell contains four. The locally equivalent Ni atoms form an fcc lattice comprised of intertwined simple tetragonal sublattices (denoted as “1” and “2” in Fig. 1a). One “face” of the fcc lattice formed by the darker green (darker grey) Ni atoms is shown in Fig. 1a. A face with Ni1 corners has a Ni2 in the center and vice versa.

The electronic structure was calculated with GGA using the VASP code⁴⁵. Nominally Ni is in a $3d^8$ configuration and Ti in $3d^0$. In DFT $\text{La}_2\text{NiTiO}_6$ is a metal, with two degenerate Ni e_g bands crossing the Fermi level, as shown in Figs. 2a and b. Due to the presence of the inactive Ti “spacers” the Ni e_g bands are remarkably narrow. The corresponding value of the bandwidth $W_{e_g} \sim 0.8$ eV is indeed substantially smaller than that of NiS_2 ^{17,46,47}, of NiO ⁴⁸ and of other $S=1$ three-dimensional compounds. The t_{2g} manifold of Ni lies 1 eV below the Fermi level and, approximately 1 eV further below, one finds the upper edge of the O $2p$ bands. The states close to the Fermi level are predominantly of Ni e_g character and are furthermore well separated from the other bands.

Subsequently we extracted maximally-localized Wannier functions (MLWF)⁴⁹ from the O $2p$, the Ni $3d$ as well as the Ti t_{2g} bands using the WANNIER90 package⁵⁰. Due to the tilting and rotation of the octahedra the straightforward MLWF construction produces a basis that retains considerable on-site mixing between the Ni t_{2g} and e_g orbitals (see inset of Fig. 2a). This local t_{2g} - e_g hybridization is just a consequence of this specific choice of orbital representation, therefore we have performed a unitary transformation after the MLWF procedure⁵¹. The usual choices here are a rotation into the so-called “crystal field basis” or into a basis that renders the DFT occupancy matrix $\rho_{ij} = \langle c_i^\dagger c_j \rangle$ diagonal on each atom, see e.g. Refs. 51 and 52. In light of a subsequent dynamical mean field theory (DMFT) calculations using a quantum Monte Carlo solver we have decided to block diagonalize the occupancy matrix, since this treatment yields in our case smaller off-diagonal elements in the frequency-dependent non-interacting Green’s function $G^0(i\omega_n)$ as the crystal field basis. We quantify the off-diagonal elements in $G^0(i\omega_n)$ by the average of the absolute values

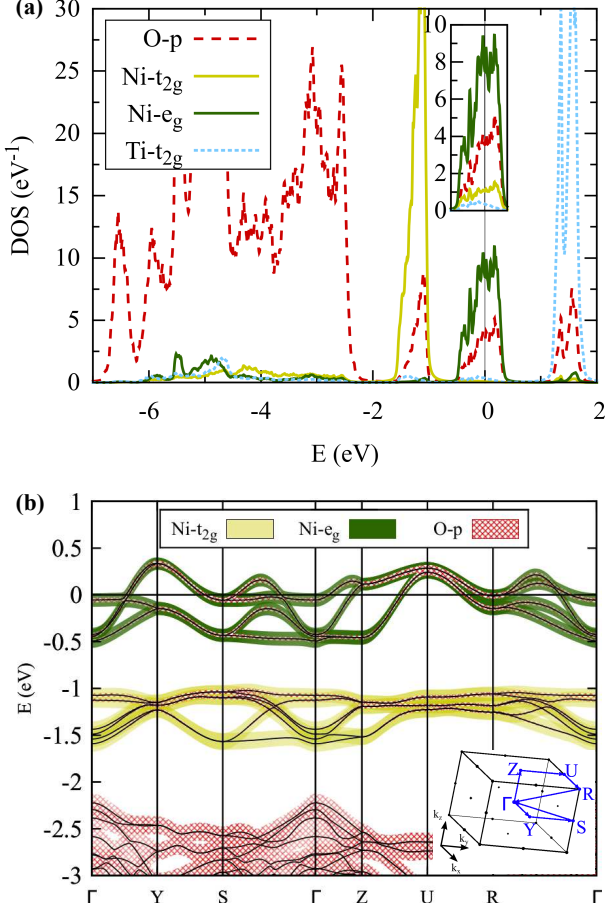


FIG. 2. (color online) (a) Orbitaly resolved density of states (Fermi level at $E=0$) (b) Fat band electronic structure for a cell containing two formula units. The thickness of the bands denotes the corresponding orbital character. In both panels the Wannier functions that have been used are those that diagonalize the occupancy matrix spanning Ni d , Ti t_{2g} and O p states (see text). In this basis the character mixture between the t_{2g} and e_g states of Ni is almost absent, in contrast to the MLWF basis, an example of which is shown, for the DOS, in the inset to panel (a).

of the off-diagonal elements, i.e.

$$\overline{|G^0(i\omega_n)|} = \frac{1}{N_{\text{od}}} \sum_{m>m'} |G_{mm'}^0(i\omega_n)|, \quad (1)$$

where N_{od} is the number of off-diagonal elements in the upper triangle of the matrix. We find the largest values at the first Matsubara frequency, for the crystal field basis and inverse temperature of $\beta = 40\text{eV}^{-1}$ the value is $\overline{|G^0(i\omega_0)|} = 0.06\text{eV}^{-1}$, while for the diagonal occupancy matrix the same is more than a factor of five smaller at 0.01eV^{-1} . The orbital character shown in the density of states in Fig. 2a and the band structure in Fig. 2b was computed using this basis.

Because of the separation of the states close to the Fermi level from the other bands and their predominant Ni e_g character we construct a low-energy model using

only these bands, projecting onto MLWFs spanning this subspace. This results in two orbitals sitting on Ni that are warped from the atomic shape by hybridization with O and Ti, an $x^2 - y^2$ -like and a $3z^2 - r^2$ -like Wannier function, whose isosurfaces are shown in Fig. 1b. In this case no additional basis transformation was necessary, since the MLWFs are already locally orthogonal. This two band model is used for most of the DFT+DMFT calculations presented here. A larger basis containing the full Ni d and the O p shell was also considered within DFT+DMFT for assessing the validity of the two band description, see Section IV.

The calculated Ni-Ni hopping amplitudes in this e_g -only model for the $3z^2 - r^2$ - and $x^2 - y^2$ -like orbitals, effectively containing the hybridization to O and Ti, are shown in Tab. I. We label the orbitals as $|1\rangle \sim 3z^2 - r^2$ and $|2\rangle \sim x^2 - y^2$ on Ni1 and analogously $|3\rangle, |4\rangle$ on Ni2. The hopping amplitude between orbitals $|i\rangle$ and $|j\rangle$ in a given direction is given by $t_{i,j}$. The overall Ni-Ni hopping is small, the element $t_{1,1}$ along the c axis being the largest (-97meV). Along the same direction the $x^2 - y^2$ hardly contributes. In the ab -plane the situation is more evenly distributed among the two orbitals but the sum of the squares of all hoppings is similar to the same quantity along c (as shown in Eq. 3 $\sum_{mm'} |t_{mm'}|^2$ determines the super-exchange coupling). For Ni-Ni 90° bonds there are two possible paths, either inter- or intra-sublattice hoppings, i.e. either Ni1-Ni2 or Ni1-Ni1, respectively. The most important outcome of the Wannier projection is that the next-nearest-neighbor Ni-Ni 180° hoppings are a factor of 4 to 10 larger than the nearest-neighbor 90° ones.

III. SPIN-ONLY MODEL

The Wannier projection allows us to derive a bilinear Heisenberg Hamiltonian $\mathcal{H}_{\text{Heis.}}$, with which we can give a first description of the physics of $\text{La}_2\text{NiTiO}_6$. To this aim, we downfold^{52,53} our *ab initio* e_g model with two electrons onto the subspace of singly occupied orbitals. The intermediate configurations generated by one Ni-Ni hopping process contain only one intra-orbital double occupation, as sketched in Fig. 3. The local interaction considered in the direct exchange model is of Kanamori type^{54,55}, the fully $\text{SU}(2)$ -symmetric interaction Hamiltonian reads

$$\begin{aligned} \mathcal{H}_{\text{Kan.}} = & U \sum_m n_{m,\uparrow} n_{m,\downarrow} \\ & + \sum_{m>m'} \sum_{\sigma} [U' n_{m,\sigma} n_{m',-\sigma} + (U' - J_{\text{H}}) n_{m,\sigma} n_{m',\sigma}] \\ & + \frac{1}{2} J_{\text{H}} \sum_{m \neq m'} \sum_{\sigma} \left(c_{m,\sigma}^\dagger c_{m',-\sigma}^\dagger c_{m,-\sigma} c_{m',\sigma} \right. \\ & \left. - c_{m,\sigma}^\dagger c_{m',-\sigma}^\dagger c_{m',\sigma} c_{m,-\sigma} \right) \end{aligned} \quad (2)$$

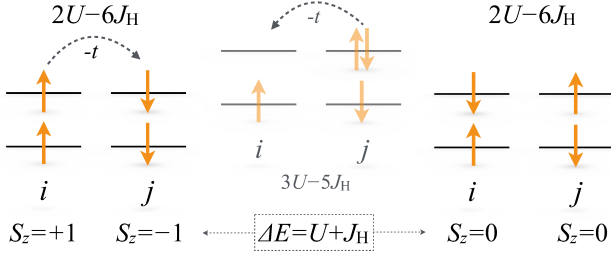


FIG. 3. (color online) Sketch of a spin-spin off-diagonal term of $\mathcal{H}_{\text{Heis.}}$ between neighboring sites i and j . Even though the two e_g orbitals are shown on two different levels for the sake of clarity, we stress that they are in fact degenerate. The final state is actually the triplet combination which, for simplicity, is represented as just one state.

with the number operator $n_{m,\sigma} = c_{m,\sigma}^\dagger c_{m,\sigma}$, where $c_{m,\sigma}^\dagger$ ($c_{m,\sigma}$) creates (annihilates) an electron with spin σ in orbital m . Furthermore, we used $U' = U - 2J_H$, where U represents the Hubbard repulsion and J_H the Hund's coupling.

The two electrons on each Ni give rise to $S=1$ as well as $S=0$ configurations which, in the low-energy subspace, are mutually coupled. However, as we will see later in our dynamical mean field theory calculation, the two electrons are strongly affected by the Hund's coupling J_H and yield an effective local moment close to the maximum possible value. Hence, the singlet can be discarded from our analysis. The resulting $S=1$ Heisenberg Hamiltonian reads

$$\mathcal{H}_{\text{Heis.}} = \frac{1}{U + J_H} \left(\sum_{mm'} |t_{mm'}|^2 \right) \sum_{ij} (\mathbf{S}_i \cdot \mathbf{S}_j - 1). \quad (3)$$

One of the processes responsible for the spin off-diagonal terms is shown in Fig. 3, where also the energies of the initial/final and intermediate states are given. The initial and intermediate configurations are eigenstates of the Kanamori Hamiltonian. The final state is actually the triplet combination which, for simplicity, is represented as just one state in our sketch.

Using typical interaction values for Ni ($U = 5$ eV and $J_H = 0.8$ eV⁵⁹) we get $J_2 \simeq 1.6$ meV and $J_1 \simeq 0.3$ meV (or smaller, depending on which 90° bond is considered). This value of U is moderate, since, for example, in NiO $U = 8$ eV⁶⁰. This small value of the ratio $J_1/J_2 \sim 0.2$ – a direct consequence of the small nearest-neighbor hoppings – corresponds to a very weak degree of frustration. The 180° Ni-Ni bonds are not strongly disturbed by the nearest-neighbor ones and form four interpenetrating antiferromagnetic simple cubic sublattices. The magnetic ordering vector of this so-called AF-II phase, which in mean-field is stable for $J_1 < 2J_2$, is $[1/2, 1/2, 1/2]$ ^{23–25}. We have performed GGA+U calculations and found that the AF-II (Type A) order has indeed the lowest energy, in agreement with experiments^{26,36}.

| abc | hopping amplitude t_{ij} (meV) | | | | $\sum_{i,j} t_{ij}^2$ (meV ²) |
|-------|----------------------------------|-------------|-------------|-------------|---|
| | (1 1) | (1 2) | (2 1) | (2 2) | |
| 0 0 1 | -97 | -3 | -3 | 0 | 9427 |
| 0 1 0 | -27 | 44 | 44 | -70 | 9501 |
| 1 0 0 | -22 | -42 | -42 | -77 | 9941 |
| <hr/> | | | | | |
| | (3 3) | (3 4) | (4 3) | (4 4) | |
| 0 0 1 | -97 | -3 | -3 | 0 | 9427 |
| 0 1 0 | -22 | -42 | -42 | -77 | 9941 |
| 1 0 0 | -27 | 44 | 44 | -70 | 9501 |
| <hr/> | | | | | |
| | (1 3) | (1 4) | (2 3) | (2 4) | |
| 0 1 1 | -27 | 25 | -19 | -4 | 1731 |
| 1 0 1 | -27 | 25 | -19 | -4 | 1731 |
| 0 1 1 | -24 | 26 | -18 | 0 | 1576 |
| 1 0 1 | -24 | 26 | -18 | 0 | 1576 |
| <hr/> | | | | | |
| | (1 1)/(3 3) | (1 2)/(3 4) | (2 1)/(4 3) | (2 2)/(4 4) | |
| 1 1 0 | 11 | 2 | 2 | -46 | 2245 |
| 1 1 0 | 12 | 3 | 3 | -26 | 838 |

TABLE I. Hopping parameters between two Ni atoms within the crystal as obtained via Wannier projection. The first column indicates the direction of the Ni-Ni bond via $\mathbf{v} \propto a\mathbf{a} + b\mathbf{b} + c\mathbf{c}$. The numbers in parentheses refer to the indices i, j by $|1\rangle \sim 3z^2 - r^2$ and $|2\rangle \sim x^2 - y^2$ on Ni1 and analogously $|3\rangle, |4\rangle$ on Ni2. Only hopping amplitudes between nearest and next-nearest Ni atoms are given here.

IV. DFT+DMFT CALCULATION

In order to go beyond the spin-only bilinear Heisenberg model above, we solve the “full” multi-orbital Hubbard model in the Wannier basis using dynamical mean field theory^{27–29}. In the following we present calculations for the e_g -only basis with the SU(2)-symmetric Kanamori interaction. The result is that $\text{La}_2\text{NiTiO}_6$ is a Mott insulator in DFT+DMFT. We have also tried larger basis-sets, in particular a dp -model containing Ni e_g , Ni t_{2g} and O p bands. The DFT+DMFT result turns out to be robust against the choice of the low-energy model, in contrast to many other transition-metal oxides for which DFT+DMFT gives qualitatively different outcomes depending on the basis set⁵⁶. In selected cases we performed calculations for an enlarged model containing the full Ni d and the O p shells, using density-density (only the first two lines of Eq. 2) as well as Kanamori interaction. As a result we find that the system is still a Mott insulator with a Ni d occupation of about 8.5 electrons, i.e. 2.4 electrons in the e_g states. We note in passing that this robustness of $\text{La}_2\text{NiTiO}_6$ against the choice of basis set makes it an ideal testbed material for the derivation of low-energy models for e_g orbitals, in the same way as SrVO_3 is very often used for t_{2g} bands. $\text{La}_2\text{NiTiO}_6$ has the additional interesting property of a much stronger effect of the Hund coupling J_H because of the half-filled, narrow e_g bands.

The DFT+DMFT solution of $\text{La}_2\text{NiTiO}_6$ for the e_g -only model demonstrates that, in a wide range of interaction parameters relevant for Ni ($U = 4$ eV to 7 eV and $J_H = 0.6 - 1.0$ eV), the local moment is very close to the maximum value of $S_{\text{eff}} = 1$. By calculating $\langle S_z^2 \rangle$ we indeed find its maximum value of $2/3$, because the inter-orbital “Hund” double occupancies $d_H = \langle n_{1,\uparrow} n_{2,\uparrow} \rangle$

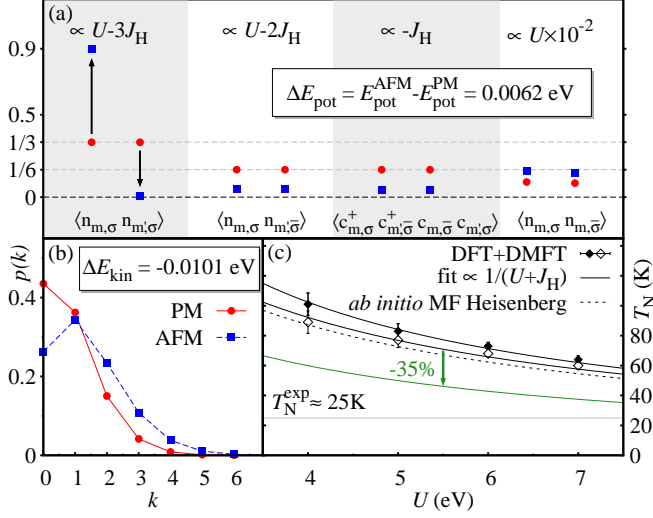


FIG. 4. (color online) Energetic balance for $U = 4$ eV, $J_H = 0.6$ eV and $\beta = 200$ (eV) $^{-1}$. (a) Different contributions to the potential energy of the paramagnetic and antiferromagnetic phases (red dots and blue squares, respectively). The two sets of data given per quantity correspond to the two spin orientations. The error bars are not visible as they are smaller than the symbol size. The potential energy of the AFM solution is larger than that of the PM one (potential energy loss). (b) Histogram of the expansion order of the QMC diagrams contributing to the fermionic trace for the two phases. Its average is proportional to the kinetic energy. The shift towards higher expansion orders for the AFM solution indicates a kinetic energy gain. In (c) T_N calculated within DFT+DMFT for the e_g -only model is reported with diamonds (full and empty symbols correspond to $J_H = 0.6$ and 1.0 eV, respectively). Fits to the data (black solid lines) yield a prefactor of the $1/(U + J_H)$ behavior which is very close to the estimate obtained from the mean-field solution of a Heisenberg model with the hopping values from Table I (black dashed line, for $J_H = 1.0$ eV). From Ref. 23 we estimated the reduction of the mean-field value, due to spatial fluctuations (line indicated by the arrow).

and the “anti-Hund” ones $d_{\text{anti-H}} = \langle n_{1,\uparrow} n_{2,\downarrow} \rangle$ are given by their “saturation” values of $1/3$ and $1/6$, respectively (see Fig. 4a). In the paramagnetic phase we therefore have $\langle S^2 \rangle = 3\langle S_z^2 \rangle = 2 = S_{\text{eff}}(S_{\text{eff}} + 1)$ with the SU(2)-symmetric Kanamori interaction. Hence $S_{\text{eff}} = 1$ and, as we only consider its spin-dependent contribution ($g = 2$), the corresponding local moment is $m \approx 2.83\mu_B$.

So far we have used DFT+DMFT to analyze the paramagnetic phase of $\text{La}_2\text{NiTiO}_6$. Being a mean-field theory, DMFT allows us to follow it down to zero temperature or, alternatively, to calculate the Néel temperature and switch to the magnetically ordered solution below T_N . The values of T_N calculated in our *ab initio* e_g -only model for different values of $U = 4$ eV to 7 eV are shown by the full and empty diamonds in Fig. 4c for $J_H = 0.6$ eV and 1.0 eV, respectively.

Before making a close comparison between the DMFT results and the experimental T_N some considerations are in order: Even if DFT+DMFT is well known for giving

accurate results for three-dimensional transition-metal oxides, the quantitative corrections due to spatial fluctuations are still sizeable in 3D. The reduction of T_N is one of the most evident of these corrections. Indeed, even if not as dramatic as in 2D, where the single-site DMFT T_N is finite instead of zero as predicted by the Mermin-Wagner theorem, this reduction has been quantified by means of a diagrammatic extensions of DMFT to be $\sim 30\%$ in the intermediate-to-strong coupling regime⁵⁷.

In our specific case, we can also rely on random-phase calculations and on spin-wave theory to evaluate the effect of non-local correlations. For our value of the J_1/J_2 ratio the random-phase approximation predicts for the fcc case with $S=1$ a reduction of T_N of about 35% compared to mean-field²³, in line with the above-mentioned result. The solid line indicated by the arrow in Fig. 4c represents the DFT+DMFT results taking into account the 35% reduction. This line gets quite close to the experimental value, especially for the largest values of U considered. The most plausible reason for an additional reduction of the theoretical T_N is the presence of a few percents of Ni-Ti anti-site disorder, as reported in Ref. 36–38.

Before switching to the thermodynamics of the magnetic transition, let us also comment on the dashed line in Fig. 4c. This shows the behavior with U of the mean-field Néel temperature of a $S=1$ Heisenberg model on an fcc lattice ($k_B T_N = 4J_2$, see Ref. 23), where in the expression for J_2 the hopping values estimated from our DFT analysis have been used (as in Eq. 3). The almost perfect agreement with T_N from the full DFT+DMFT calculation shows that it makes perfect sense to identify the single-site DMFT result with the mean-field Heisenberg outcome.

In order to prove that the physics of $\text{La}_2\text{NiTiO}_6$ is actually that of a strong-coupling Heisenberg antiferromagnet, we perform a thermodynamic analysis. The smoking gun ruling out possible intermediate-coupling physics is a lower total energy for the AFM phase realized through a kinetic energy gain and a loss in potential energy^{58,64,65,69}. Our results very clearly indicate a kinetic energy gain, as shown in Fig. 4b. This is calculated from the first moment of $h(k)$, the histogram of the expansion order of the continuous-time hybridization-expansion quantum Monte Carlo solver^{61,62}. A shift toward larger expansion orders indicates a gain in kinetic energy for the AFM phase ($\Delta E_{\text{kin}} = E_{\text{kin}}^{\text{AFM}} - E_{\text{kin}}^{\text{PM}} < 0$). At the same time, as shown in Fig. 4a, where the local terms of the multi-orbital Hubbard Hamiltonian are separately analyzed, we detect a potential energy loss ($\Delta E_{\text{pot}} = E_{\text{pot}}^{\text{AFM}} - E_{\text{pot}}^{\text{PM}} > 0$), ruling out intermediate-coupling physics. Our analysis reveals that the potential energy loss is almost entirely given by the corresponding increase in d_U , the intra-orbital double occupancies by going from PM to AFM. As shown in Fig. 4a, the “Hund” inter-orbital double occupancies d_H (proportional to $U - 3J_H$), the “anti-Hund” ones, $d_{\text{anti-H}} (\propto U - 2J_H)$ and the “spin-flip” term $d_K (\propto -J_H)$, are close to

compensating each other. Since the pair-hopping terms hardly contribute, the potential energy loss reads $\Delta E_{\text{pot}} = 2[(U - 3J_H)\Delta d_H + (U - 2J_H)\Delta d_{\text{anti-H}} + J_H\Delta d_N + U\Delta d_U]$, where Δd indicates the total difference in the respective quantity summed over spin and orbital indices. Indeed it is almost entirely given by the corresponding change in d_U : $\Delta E_{\text{pot}} \approx 2U\Delta d_U$.

This is a precise consequence of the strong-coupling physics: the disordered phase has preformed localized moments that slightly delocalize upon entering the ordered phase because they gain coherence. At the same time, the length of the (unordered) local moment (whose square is $\propto \langle S^2 \rangle$ ⁶⁶) changes only slightly by going from the PM to the AFM phase: the latter is $\sim 0.002\mu_B$ shorter than the former.

V. CONCLUSIONS

We have shown that $\text{La}_2\text{NiTiO}_6$ is a Hund's coupling-driven Mott insulator, far in the strong-coupling limit. The peculiar properties of this double perovskite come from the presence of inactive d^0 Ti-“spacers” which enlarge the Ni-Ni bonds isotropically in all directions, drastically reducing the relevant bandwidth. The proper low-energy spin-spin model is a Heisenberg Hamiltonian with next-nearest-neighbor exchange coupling J_2 equal to about 1.6 meV and nearest-neighbor coupling J_1 a factor of 4-5 smaller. On an fcc lattice like the present one, this implies that frustration effects are almost absent and the very low value of T_N is a consequence of the strong local fluctuations of the order parameter. We demonstrate the strong coupling nature of $\text{La}_2\text{NiTiO}_6$ by a direct analysis of the energetic balance within DFT+DMFT. This prediction can be tested, for instance, by looking for the presence of spin-polarons in photoemission as well as in

optical conductivity measurements⁶⁷⁻⁶⁹ which should be visible due to the pronounced three-dimensional character.

Our results unveil a new family of double perovskites – $\text{La}_2\text{NiTiO}_6$ being its first member – that, due to the dramatic reduction of the bandwidth can be very interesting for oxide engineering. One promising direction is to try to split the two e_g bands with strain or upon heterostructuring. This can be achieved because, despite the very isotropic J_2 , the 180° hoppings of the $3z^2 - r^2$ - and of the $x^2 - y^2$ -orbitals are not symmetric under rotations of the crystal axes. It should therefore be possible to induce a splitting which, due to the hybridization between the two e_g -orbitals, may result in a gap of inverted orbital character at specific points of the Brillouin zone. The resulting band structure can in fact be ideal for the realization of a correlated topological insulator, with two d electrons in two entangled orbitals forming a large local moment (hence more easily detectable in an experiment). If the $x^2 - y^2/3z^2 - r^2$ splitting turns out to be externally tunable, this class of d^8 - d^0 double perovskites could become tremendously attractive from this point of view. By substituting Ni with heavier isoelectronic elements the spin-orbit coupling can also help in the opening of the hybridization gap necessary to realize a correlated topological insulator.

ACKNOWLEDGMENTS

We thank A. Toschi for enlightening suggestions, Y. Motome, A. Katanin, R. Claessen, M. Sing, J. Kuneš, M. Capone, G. Giovannetti for useful comments and A. Hausoel for his great work on the “w2dynamics” code. This work has been funded by the Deutsche Forschungsgemeinschaft through the research units FOR 1162 (M.K.) and FOR 1346 (G.S.).

-
- ¹ F. D. Haldane, Phys. Rev. Lett. **50**, 1153 (1983)
 - ² I. Affleck, T. Kennedy, E. H. Lieb and H. Tasaki, Phys. Rev. Lett. **59**, 799 (1987)
 - ³ W. Buyers, R. Morra, R. Armstrong, M. Hogan, P. Gerlach and K. Hirakawa, Phys. Rev. Lett. **56**, 371 (1986)
 - ⁴ S. R. White and D. A. Huse, Phys. Rev. B **48**, 3844 (1993)
 - ⁵ O. Golinelli, Th. Jolicœur and R. Lacaze, Phys. Rev. B **50**, 3037 (1994)
 - ⁶ E. Čížmár, *et al.*, New Jour. of Phys. **10**, 033008 (2008)
 - ⁷ R. J. Birgeneau, J. Als-Nielsen and G. Shirane, Phys. Rev. B **16**, 280 (1977)
 - ⁸ M. Greven, R. J. Birgeneau, Y. Endoh, M. A. Kastner, M. Matsuda and G. Shirane, Z. Phys. B **96**, 465 (1995)
 - ⁹ P. Khuntia and A. V. Mahajan, J. Phys.: Condens. Matter **22**, 296002 (2010)
 - ¹⁰ Y. Tsujimoto, *et al.*, Chem. Mater. **22**, 4625 (2010)
 - ¹¹ R. J. Birgeneau, Phys. Rev. B **41**, 2514 (1990)
 - ¹² H. Chen, A. J. Millis and C. A. Marianetti, Phys. Rev. Lett. **111**, 116403 (2013)
 - ¹³ Y. Yamashita and K. Ueda, Phys. Rev. Lett. **85**, 4960 (2000)
 - ¹⁴ A. J. García-Adeva and D. L. Huber, Phys. Rev. Lett. **85**, 4598 (2000)
 - ¹⁵ J. S. Gardner, M. J. Gingras and J. E. Greedan, Rev. Mod. Phys. **82**, 53 (2010)
 - ¹⁶ M. Matsuura, Y. Endoh, H. Hiraka, K. Yamada, A. S. Mishchenko, N. Nagaosa and I. V. Solovyev, Phys. Rev. B **68**, 094409 (2003)
 - ¹⁷ A. Perucchi, C. Marini, M. Valentini, P. Postorino, R. Sopracase, P. Dore, P. Hansmann, O. Jepsen, G. Sangiovanni, A. Toschi, K. Held, D. Topwal, D. D. Sarma and S. Lupi, Phys. Rev. B **80**, 073101 (2009)
 - ¹⁸ J. Kuneš, V. I. Anisimov, S. L. Skornyakov, A. V. Lukoyanov and D. Vollhardt, Phys. Rev. Lett. **99**, 156404 (2007)
 - ¹⁹ R. L. Martin and F. Illas, Phys. Rev. Lett. **79**, 1539 (1997)
 - ²⁰ M. De Raychaudhury, E. Pavarini and O. K. Andersen, Phys. Rev. Lett. **99**, 126402 (2007)
 - ²¹ The same is true, for instance, for the d^3 perovskites

- SrMnO₃ and SrTcO₃²².
- ²² J. Mravlje, M. Aichhorn and A. Georges, Phys. Rev. Lett. **108**, 197202 (2012)
 - ²³ M. E. Lines, Phys. Rev. **139**, A1304 (1965)
 - ²⁴ T. Yildirim, A. B. Harris and E. F. Shender, Phys. Rev. B **58**, 3144 (1998)
 - ²⁵ A. N. Ignatenko, A. A. Katanin and V. Yu. Irkhin JETP Lett. **87**, 555 (2008)
 - ²⁶ M. Edelmann, Master Thesis, University of Würzburg, (2014) (unpublished)
 - ²⁷ W. Metzner and D. Vollhardt, Phys. Rev. Lett. **62**, 324 (1989)
 - ²⁸ A. Georges and G. Kotliar, Phys. Rev. B **45**, 6479 (1992)
 - ²⁹ A. Georges, G. Kotliar, W. Krauth, and M. J. Rozenberg, Rev. Mod. Phys. **68**, 13 (1996)
 - ³⁰ B. Sutherland, Phys. Rev. B **12**, 3795 (1975)
 - ³¹ A. Yoshimori and S. Inagaki, Jour. Phys. Soc. Jap. **50**, 769 (1981)
 - ³² F. Alet, S. Capponi, H. Nonne, P. Lecheminant and I. P. McCulloch, Phys. Rev. B **83**, 060407(R) (2011)
 - ³³ F. Michaud and F. Mila, Phys. Rev. B **88**, 094435 (2013)
 - ³⁴ R. Roy, J. Am. Ceram. Soc. **37**, 581 (1954)
 - ³⁵ V. J. Fratello, G. W. Berkstresser, C. D. Brandle and A. J. Ven Graitis, J. of Cryst. Growth **166**, 878 (1996)
 - ³⁶ E. Rodríguez, M. L. López, J. Campo, M. L. Veiga and C. Pico, J. Mater. Chem. **12**, 2798 (2002)
 - ³⁷ J. C. P. Flores, C. Ritter, D. Pérez-Coll, G. C. Mather, F. García-Alvarado and U. Amador, J. Mater. Chem. **21**, 13195 (2011)
 - ³⁸ W. Z. Yang, X. Q. Liu, Y. Q. Lin and X. M. Chen, J. of Appl. Phys. **111**, 084106 (2012)
 - ³⁹ S. Raghu, X.-L. Qi, C. Honerkamp and S.-C. Zhang, Phys. Rev. Lett. **100**, 156401 (2008)
 - ⁴⁰ D. Pesin and L. Balents, Nature Phys. **6**, 376 (2010)
 - ⁴¹ L. Fu, Phys. Rev. Lett. **106**, 106802 (2011)
 - ⁴² A. Rüegg, C. Mitra, A. A. Demkov and G. A. Fiete, Phys. Rev. B **88**, 115146 (2013)
 - ⁴³ J. C. Budich, B. Trauzettel and G. Sangiovanni, Phys. Rev. B **87**, 235104 (2013)
 - ⁴⁴ J. P. Perdew, K. Burke and M. Ernzerhof, Phys. Rev. Lett. **77**, 3865 (1996)
 - ⁴⁵ G. Kresse and J. Hafner, Jour. of Phys.: Condensed Matter, **6**, 8245 (1994); G. Kresse and D. Joubert, Phys. Rev. B **59**, 1758 (1999)
 - ⁴⁶ C. Schuster, <http://arxiv.org/abs/0911.3303> (unpublished); C. Schuster, M. Gatti and A. Rubio, Eur. Phys. J. B **85** (2012)
 - ⁴⁷ J. Kuneš, *et al.*, Phys. Rev. B **81**, 035122 (2010)
 - ⁴⁸ L. F. Mattheiss, Phys. Rev. B **5**, 290 (1972)
 - ⁴⁹ N. Marzari, A. A. Mostofi, J. R. Yates, I. Souza and D. Vanderbilt, Rev. Mod. Phys. **84**, 1419 (2012)
 - ⁵⁰ A. A. Mostofi, J. R. Yates, Y.-S. Lee, I. Souza and D. Vanderbilt and N. Marzari, Computer Physics Communications **178**, 685 (2008)
 - ⁵¹ F. Lechermann, A. Georges, A. Poteryaev, S. Biermann, M. Posternak, A. Yamasaki, and O. K. Andersen, Phys. Rev. B **74**, 125120 (2006).
 - ⁵² E. Pavarini, A. Yamasaki, J. Nuss and O. K. Andersen, New J. Phys. **7**, 188 (2005).
 - ⁵³ P.-O. Löwdin, J. Chem. Phys. **19**, 1396, (1951).
 - ⁵⁴ J. Kanamori, Prog. Theo. Phys. **30**, 275, (1963).
 - ⁵⁵ A. Georges, L. de Medici and J. Mravlje, Annu. Rev. Condens. Matter Phys. **4**, 137 (2013) .
 - ⁵⁶ M. Aichhorn, L. Pourovskii, V. Vildosola, M. Ferrero, O. Parcollet, T. Miyake, A. Georges, and S. Biermann, Phys. Rev. B **80**, 085101 (2009); X. Wang, M. J. Han, L. de' Medici, H. Park, C. A. Marianetti and A. J. Millis, Phys. Rev. B **86**, 195136 (2012) M. J. Han, X. Wang, C. A. Marianetti and A. J. Millis, Phys. Rev. Lett. **107** 206804 (2011); N. Parragh, G. Sangiovanni, P. Hansmann, S. Hummel, K. Held and A. Toschi, Phys. Rev. B **88**, 195116 (2013); P. Hansmann, N. Parragh, A. Toschi, G. Sangiovanni and K. Held, New J. Phys. **16**, 033009 (2014).
 - ⁵⁷ G. Rohringer, A. Toschi, A. Katanin and K. Held, Phys. Rev. Lett. **107**, 256402 (2011).
 - ⁵⁸ A. Toschi, M. Capone and C. Castellani, Phys. Rev. B **72**, 235118 (2005).
 - ⁵⁹ E. Şaşoğlu, C. Friedrich and S. Blügel, Phys. Rev. B **83**, 121101(R) (2011).
 - ⁶⁰ V. I. Anisimov, J. Zaanen, and O. K. Andersen, Phys. Rev. B **44**, 943 (1991).
 - ⁶¹ P. Werner, A. Comanac, L. de' Medici, M. Troyer, and A. J. Millis, Phys. Rev. Lett. **97**, 076405 (2006); P. Werner and A. J. Millis, Phys. Rev. B **74**, 155107 (2006); K. Haule, Phys. Rev. B **75**, 155113 (2007); E. Gull, A. J. Millis, A. I. Lichtenstein, A. N. Rubtsov, M. Troyer and P. Werner, Rev. Mod. Phys. **83**, 349 (2011).
 - ⁶² For our calculations we have used the Würzburg-Vienna code package "w2dynamics"⁶³.
 - ⁶³ N. Parragh, A. Toschi, K. Held, G. Sangiovanni, Phys. Rev. B, **86** 155158 (2012).
 - ⁶⁴ E. Gull, P. Werner, X. Wang, M. Troyer and A. J. Millis, Eur. Phys. Lett. **84**, 37009 (2008).
 - ⁶⁵ T. Schäfer, F. Geles, D. Rost, G. Rohringer, E. Arrigoni, K. Held, N. Blümer, M. Aichhorn and A. Toschi <http://arxiv.org/abs/1405.7250> (2014)
 - ⁶⁶ $\langle S_z^2 \rangle = 1/4 n_{\text{tot}} - d_U + d_H - d_{\text{anti-H}}$, $\langle S_x^2 \rangle = 1/4 n_{\text{tot}} - d_U - d_N$, $\langle S_x^2 \rangle + \langle S_y^2 \rangle + \langle S_z^2 \rangle = 3/4 n_{\text{tot}} - 3d_U + d_H - d_{\text{anti-H}} - 2d_N$.
 - ⁶⁷ R. Strack and D. Vollhardt, Phys. Rev. B **46**, 13852 (1992)
 - ⁶⁸ G. Sangiovanni, *et al.*, Phys. Rev. B **73**, 205121 (2006)
 - ⁶⁹ C. Taranto, G. Sangiovanni, K. Held, M. Capone, A. Georges and A. Toschi, Phys. Rev. B **85**, 085124 (2012)