

Symmetry of the Excitations in the Hidden Order State of URu₂Si₂

J. Buhot, M.-A. Méasson,^{*} Y. Gallais, M. Cazayous, and A. Sacuto
*Laboratoire Matériaux et Phénomènes Quantiques, UMR 7162 CNRS,
 Université Paris Diderot, Bât. Condorcet 75205 Paris Cedex 13, France*

G. Lapertot and D. Aoki
*Univ. Grenoble Alpes, INAC-SPSMS, F-38000 Grenoble, France and
 CEA, INAC-SPSMS, F-38000 Grenoble, France*
 (Dated: March 2, 2022)

We have performed polarized electronic Raman scattering on URu₂Si₂ single crystals at low temperature down to 8 K in the hidden order state and under magnetic field up to 10 T. The hidden order state is characterized by a sharp excitation at 1.7 meV and a gap in the electronic continuum below 6.8 meV. Both Raman signatures are of pure A_{2g} symmetry. By comparing the behavior of the Raman sharp excitation and the neutron resonance at $\mathbf{Q}_0=(0,0,1)$, we provide new evidence, constrained by selection rules of the two probes, that the hidden order state breaks the translational symmetry along the c axis such that Γ and Z points fold on top of each other. The observation of these distinct Raman features with a peculiar A_{2g} symmetry as a signature of the hidden order phase places strong constraints on current theories of the hidden order in URu₂Si₂.

For almost three decades [1], the identity of the ordered phase found in URu₂Si₂ at temperature below $T_0=17.5$ K has eluded researchers [2, 3] despite intensive experimental and theoretical investigations. The second order transition to this so-called hidden order (HO) appears clearly in the thermodynamic and transport quantities [1, 4–7]. This unique electronic state is not a simple long-range magnetic (dipolar) order since the associated tiny magnetic moment measured in the HO state cannot account for the large entropy release during the transition [8]. Nevertheless, the HO changes to a simple antiferromagnetic with a simple tetragonal structure under a small applied pressure of 0.5 GPa [9–11]. Many interesting theories have been proposed to explain the nature of HO, among which multipolar orders from quadrupolar to dotriacontapolar [12–16], local currents [17, 18], unconventional density wave [19, 20] modulated spin liquid [21, 22], dynamical symmetry breaking [23] and hastatic order [24] for the most recent ones. Yet a complete understanding of the nature of the hidden order has not been reached.

A wide variety of experimental studies have succeeded in revealing salient features of the HO state. Inelastic neutron measurements [8, 25, 26] observe two magnetic excitations with a commensurate wave vector $\mathbf{Q}_0=(1,0,0)\equiv(0,0,1)$ and an incommensurate wave vector $\mathbf{Q}_1=(1.4,0,0)$ at 1.7 meV and 4.8 meV, respectively. The first one has been demonstrated to be a major signature of the HO state [27]. It is well accepted [6, 28] that a partial Fermi-surface gapping with a strong reduction of the carriers number occurs at T_0 and accordingly, the electronic structure abruptly reconstructs at T_0 [29–32]. It persists in the antiferromagnetic state under pressure [33] suggesting similar Brillouin zone folding in both states. Besides, a recent set of experiments have identified a four-fold symmetry breaking upon entering the HO state [34–

36], steering some controversy [37] [38]. Preliminary connections between the fingerprints of the HO transition have been made. The electronic structure of the HO is consistent with a periodicity given by the commensurate wave vector \mathbf{Q}_0 [39] and part of the gapping of the incommensurate spin fluctuations was related to the loss of entropy at the HO transition [26]. However, these relationships remain indirect. Additionally, the question of the symmetry of the novel excitations emerging from the HO state has not been addressed experimentally.

In this letter using electronic Raman spectroscopy, we report clear Raman signatures of the HO state, i.e. a gap below ~ 55 cm⁻¹ (6.8 meV) and a sharp excitation deep inside the gap at 14 cm⁻¹ (1.7 meV). Both signatures are observed only in the A_{2g} symmetry, which indicates a direct intimate relationship between them. They emerge from a broad A_{2g} quasi-elastic continuum which persists up to 300 K. Given the peculiarity of the A_{2g} symmetry itself, our results give new and strong constraints on the nature of the HO state. We further demonstrate that the sharp Raman excitation tracks the resonance at $\mathbf{Q}_0=(0,0,1)$ detected by inelastic neutron scattering (INS) [25] in the HO state as a function of temperature and magnetic field, indicating that both excitations have the same origin even if measured at different wave vector transfer. This brings a new and robust evidence for a Brillouin zone folding which places the Z point on top of the Γ point as expected in a transition between a body center tetragonal (bct) and a simple tetragonal (st) phase.

Polarized Raman experiments have been carried out using a solid state laser emitting at 561 nm and a Jobin Yvon T64000 triple subtractive grating spectrometer equipped with a nitrogen cooled CCD camera. Single crystals of URu₂Si₂ were grown by the Czochralski method using a tetra-arc furnace [40]. Three samples

from the same batch with a residual resistivity ratio of ~ 50 and freshly cleaved along the (ab) plane have been measured. Temperature and magnetic field dependencies have been performed in a closed-cycle ^4He cryostat with sample in high vacuum and a ^4He pumped cryostat with the sample in exchange gas, respectively [41]. By combining different incident and scattered light polarizations and sample geometry, we have extracted the A_{1g} , B_{1g} , B_{2g} and A_{2g} symmetries of the D_{4h} point group (space group $n^\circ 139$) [46].

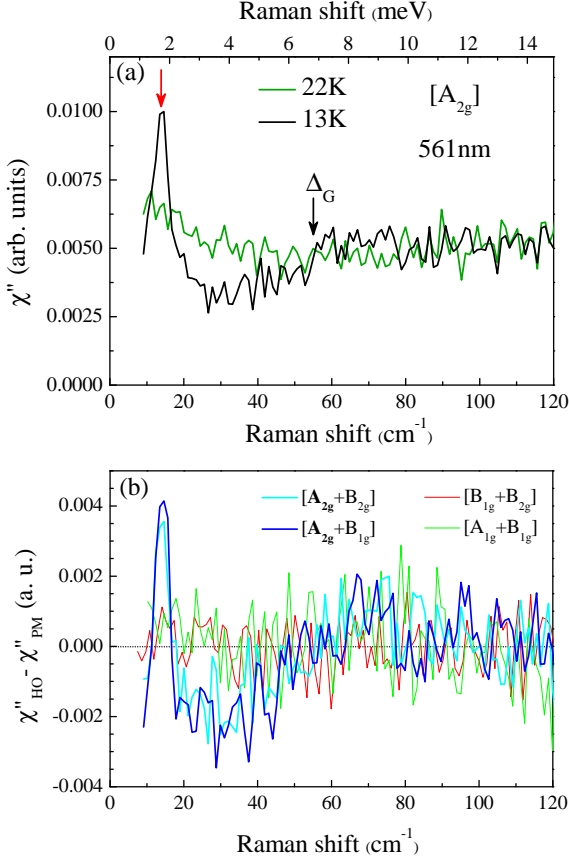


FIG. 1. (Color online) (a) Raman spectra of URu_2Si_2 in the pure A_{2g} symmetry in the hidden order (HO) phase (13 K) and in the paramagnetic phase (22 K). In the HO, a sharp peak at 14 cm^{-1} , indicated by the red arrow, is superimposed on a gap below $\Delta_G \sim 55 \text{ cm}^{-1}$. (b) Subtracted Raman responses in the hidden order phase and the paramagnetic phase for all probed symmetries. All spectra have been measured with the same laser power. Those containing the B_{1g} response have been normalized to the intensity of the B_{1g} phonon.

Figure 1(a) shows the low-frequency Raman spectra of URu_2Si_2 in the pure A_{2g} symmetry [47]. Upon entering the HO state, a gap opens below $\Delta_G \sim 55 \text{ cm}^{-1}$ and a sharp excitation emerges at $\sim 14 \text{ cm}^{-1}$ deep inside the gap. The subtraction of the Raman responses in the paramagnetic (PM) and HO state in various symmetries

is reported Figure 1(b). Within our accuracy, no feature can be detected in the other probed symmetries [48][49]. The HO state is thus characterized by two Raman signatures of pure A_{2g} symmetry. The A_{2g} symmetry is intriguing. It is equivalent to the C_{4h} subgroup of the D_{4h} space group and transforms as $xy(x^2 - y^2)$ or R_z [51]. This symmetry is usually associated with time reversal and/or chiral symmetry breaking excitations [53–56]. Among the large families of compounds belonging to the D_{4h} space group, including the cuprates and the Fe-based superconductors, few measurements only have reported a sizeable A_{2g} Raman response [57].

The energy of the gap is consistent with previous optical conductivity measurements [28, 58–60]. In addition, the gaps Δ_G extracted from the resistivity ($\sim 56 \text{ cm}^{-1}$) [61] and from heat capacity measurements ($\sim 88 \text{ cm}^{-1}$) [62, 63] are in the same energy range than our findings. Scanning tunneling microscopy experiments also report a gap of $\sim \pm 4 \text{ meV}$, i.e. $\Delta_G \simeq 65 \text{ cm}^{-1}$ [64, 65].

We note that Raman scattering is also sensitive to double excitations processes, such as double phonon or two-spin excitations with $\pm \mathbf{Q}$ transferred wave-vectors. A double excitation process involving the resonance at $\pm \mathbf{Q}_1$ would be measured at $\sim 75 \text{ cm}^{-1}$, in the energy range of the Raman gap. However, we can rule out this interpretation because the \mathbf{Q}_1 resonance strongly shifts to lower energy with increasing temperature. It has been reported to be inelastic above T_0 reaching $\sim 2.5 \text{ meV}$ at 20 K, i.e. 40 cm^{-1} for a double excitation [8, 66] whereas the A_{2g} Raman gap depletion vanishes at T_0 while its energy remains roughly constant up to T_0 [67]. This comparison, as well as the observation of a similar gap by optical conductivity measurements, suggests that the depletion is not linked to the resonance at \mathbf{Q}_1 but to a gapped electron-hole excitations continuum as expected from a reconstruction of the Fermi surface inside the HO state [23, 29–31]. We provide here a new information on this electron-hole excitations continuum, i.e. it has the pure A_{2g} symmetry. From that, we surmise that the gap occurs in a continuum involving quasi-particles with strong spin-orbit character as described in [68].

Below the gap, the A_{2g} peak is sharp with a full width at half maximum (FWHM) of $\sim 1 \text{ cm}^{-1}$ at $\sim 10 \text{ K}$, showing it is a long lived excitation. Figure 2(a) presents the temperature dependence of its position and FWHM. Its energy and width are almost constant up to $\sim 15 \text{ K}$. It abruptly drops to zero near T_0 with a temperature dependence stronger than expected for a mean field transition. It also broadens when approaching T_0 . We also report the energy E_0 and FWHM of the neutron resonance at $\mathbf{Q}_0=(0,0,1)$, the up-to-now major signature of the HO phase [25, 27]. The A_{2g} Raman peak closely tracks the neutron resonance which strongly suggests that the same excitation is coupled to both probes. In addition, as shown figure 2(b) the peak hardens slightly

under magnetic field up to 10 T [69] which is qualitatively consistent with the magnetic field dependence of the neutron resonance [71]. Raman spectroscopy probes the Γ point, i.e. the total transferred wave vector $\mathbf{Q} = 0$. The feature observed at 1.7 meV by neutron scattering is measured at the Z point, i.e. at $\mathbf{Q}_0 = (0,0,1)$. Measuring the same excitation at the Γ and Z points can be explained by invoking a Brillouin zone folding along the c axis which occurs upon entering the HO state, as a bct to st transition would produce (Cf. Figure 2(c)). The same conclusion was previously made from the comparison between the Fermi surfaces at ambient pressure and under pressure in the antiferromagnetic state [33] as well as from the comparison between photoemission spectroscopy (ARPES) data at the Γ and the Z points [30–32, 72, 73]. The conclusion drawn here is robust as it results from measurements at zero magnetic field and zero applied pressure. Most of all it is based on the observation of a major signature of the HO state at different \mathbf{Q} vectors.

Interestingly, the finite Raman response in the A_{2g} symmetry is not limited to the HO state. Indeed, as reported by Cooper et al. [74], already at 300 K, URu_2Si_2 exhibits a A_{2g} quasi-elastic peak (QEP) with a overdamped Lorentzian line shape. As shown Figure 3(a), the quasi-elastic contribution sharpens with decreasing temperature before collapsing in the HO state. The FWHM, calculated with a simple relaxation model [74], is reported in Figure 3(b). After a Korringa-like linear temperature dependence down to ~ 100 K, it exhibits a plateau-like behavior between ~ 100 K and ~ 50 K before decreasing three times faster down to 20 K. The plateau is thus limited to the Kondo regime with an increase of the lifetime of the A_{2g} excitations most probably below the Kondo coherence temperature. Via the Kramers-Kronig relation [75], the A_{2g} static susceptibility $\chi_0^{A_{2g}}$ can be extracted as $\int \chi_{A_{2g}}''(\omega)/\omega d\omega$ with integration spanning from 8 to 100 cm^{-1} , above which all spectra are on top of each other. As shown in Figure 3(b), the A_{2g} static susceptibility exhibits a temperature dependence very reminiscent to the dc magnetic susceptibility along the c axis [76], suggesting a link between the A_{2g} degree of freedom and the magnetic susceptibility. The temperature dependence of this last one has been tentatively explained considering various crystalline electric field (CEF) schemes [77]. A similar Raman quasi-elastic response has already been discussed in the context 4f and 5f system, where it was attributed to either spin fluctuations or localized CEF excitations like in UBe_{13} [78]. In URu_2Si_2 , a tempting simple interpretation of the A_{2g} QEP would be to consider a CEF excitation between very broad (and partially delocalized) levels. Indeed, simple local CEF excitations on the U atoms can have a A_{2g} symmetry, with different ground state and with an even or odd number of localized electrons [79].

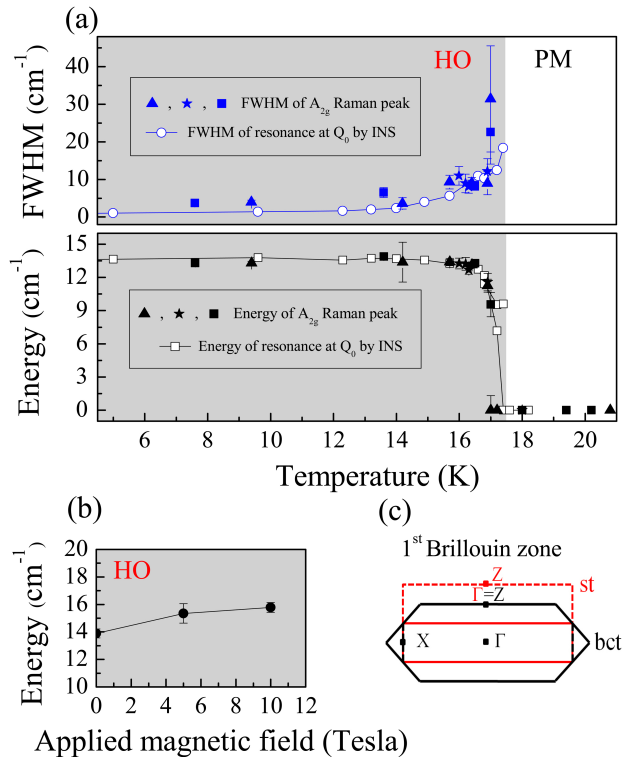


FIG. 2. (Color online) (a) Temperature dependence of the energy and full width at half maximum (FWHM) (after deconvolution from the resolution of the spectrometer (2 cm^{-1})) of the sharp A_{2g} Raman peak (full symbols) and of the resonance at $\mathbf{Q}_0 = (0,0,1)$ measured by inelastic neutron scattering (INS) (open symbols) [25]. The full symbols (stars, triangle, square) are extracted from various measurements on different samples from the same batch. The grey area corresponds to the temperature range of the HO phase. Both features are due to the same excitation probed by different techniques. The folding sketched in (c) would explain the observation of the same excitation at different \mathbf{Q} wave vectors. (b) Magnetic field dependence of the energy of the sharp A_{2g} Raman peak. The magnetic field is applied at $30 \pm 5^\circ$ of the c axis. (c) Sketch of the first Brillouin zone in the paramagnetic state (body centered tetragonal, bct) and the folded one to the simple tetragonal (st) structure which folds the Z point to the Γ point.

Following this interpretation, a global and simple scenario, reminiscent of the results obtained across the metal-insulator transition of the skutterudite $\text{PrRu}_4\text{P}_{12}$ [81], can be given. The A_{2g} QEP as well as the sharp A_{2g} peak in the HO state are due to CEF excitations while the gap Δ_G is associated to the gapped itinerant electron-hole continuum. Because CEF excitations are coupled to itinerant carriers, the QEP is strongly damped and quasi-elastic above T_0 . At the HO transition, A_{2g} decaying channels are quenched at low energy due to the opening of the A_{2g} gap in the electronic continuum and consequently, the CEF excitation becomes long-lived. By the same process the CEF excitation becomes gapped

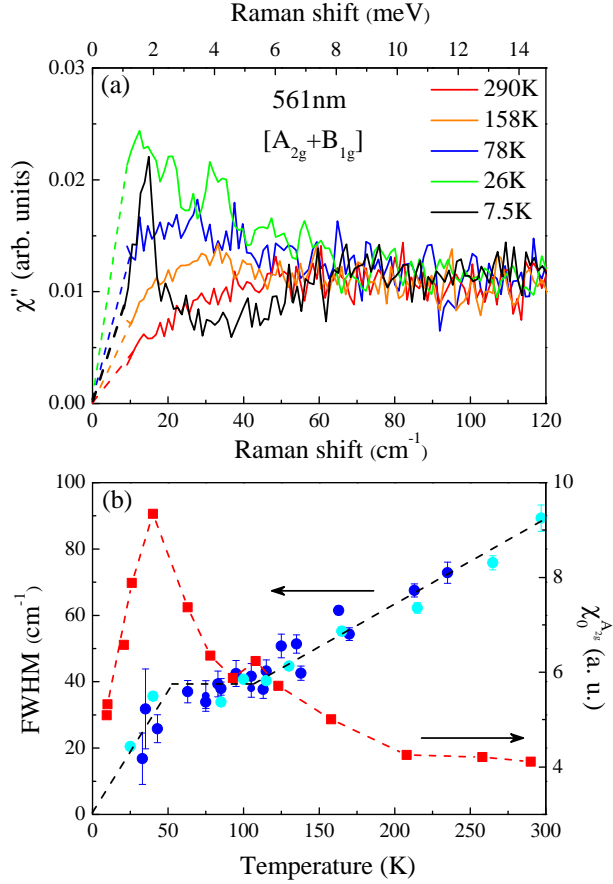


FIG. 3. (Color online) (a) Raman susceptibility in the $A_{2g}+B_{1g}$ symmetry from 7.5 K to 300 K. (b) Left axis: Full width of the quasi-elastic response (Cf. text) (blue filled circles) versus temperature. Right axis: Raman static susceptibility $\chi_0^{A_{2g}}$ (red filled squares) versus temperature (Cf. text). Dashed lines are guide for the eyes.

(inelastic) because of the associated loss of hybridization with delocalized quasiparticle continuum in the HO state. In this picture, the dual character of the phase transition in URu₂Si₂ appears naturally, with the gap Δ_G observed in the Raman continuum, directly linked to the itinerant nature of the 5f electrons and the CEF excitation observed as the Raman sharp peak, associated with their local character. Within this scenario, a close relationship between the signatures of the itinerant and localized character of the HO state can be made, through the similarity of their A_{2g} symmetry.

Now, we discuss alternative explanations for each signature, the QEP and the sharp peak, independently. We inferred that the A_{2g} gap is a gapped electron-hole excitation continuum. As already noted above, the opening of this gap will help any excitation inside the gap to become long-lived and sharp. In this context, the peculiar A_{2g} symmetry may emerge from local current loop exci-

tations, which could give rise to the A_{2g} peak in the HO state. Indeed similar anomalous orbital motion of charge carriers have been shown to have the A_{2g} symmetry [53] based on a Raman experiment in the insulating cuprates [54]. This hypothesis has also been recently brought up for URu₂Si₂ [3, 68]. As for the QEP observed above T_0 , in a pure itinerant picture perspective, a Drude-like Raman response of electron-hole excitations may explain it. We would need then to account for the strong spectral weight in the A_{2g} symmetry. This would certainly require to go beyond the effective mass approximation [57] by taking into account the resonant contributions for the Raman vertex calculation [53, 82] [83].

In conclusion, we have reported two Raman features of pure A_{2g} symmetry, a sharp peak at 14 cm⁻¹ and a low energy gap at ~ 55 cm⁻¹, as signatures of the hidden order state in URu₂Si₂. Additionally, by performing accurate temperature and magnetic field dependencies of the sharp Raman peak, we have shown that the sharp peak matches the neutron resonance at \mathbf{Q}_0 . This brings new and robust evidence of the Brillouin zone folding along c axis upon entering the HO state, consistent with a switch from body center tetragonal to simple tetragonal. Theoretical investigations, most probably accounting for both the local and the itinerant character of the quasiparticle in URu₂Si₂, are necessary to reach a global scenario of these Raman signatures of peculiar A_{2g} symmetry and to conclude about the associated HO order parameter.

This work was supported by the Labex SEAM (Grant No. ANR-11-IDEX-0005-02) and by the french Agence Nationale de la Recherche (ANR PRINCESS). We thanks F. Bourdarot, S. Burdin, C. Pepin, G. Knebel, I. Paul, D. Khveshchenko, G. Blumberg, G. Kotliar, H. Harima and P. Oppeneer for very fruitful discussions.

* marie-aude.measson[at]univ-paris-diderot.fr

- [1] T. T. M. Palstra, A. A. Menovsky, J. van den Berg, A. J. Dirkmaat, P. H. Kes, G. J. Nieuwenhuys, and J. A. Mydosh, *Physical Review Letters* **55**, 2727 (1985).
- [2] J. A. Mydosh and P. M. Oppeneer, *Reviews of Modern Physics* **83**, 1301 (2011).
- [3] J. Mydosh and P. Oppeneer, *Philosophical Magazine* (2014).
- [4] W. Schlabit, J. Baumann, B. Pollit, U. Rauchschwalbe, H. M. Mayer, U. Ahlheim, and C. D. Bredl, *Zeitschrift für Physik B Condensed Matter* **62**, 171 (1986).
- [5] K. Behnia, R. Bel, Y. Kasahara, Y. Nakajima, H. Jin, H. Aubin, K. Izawa, Y. Matsuda, J. Flouquet, Y. Haga, Y. Onuki, and P. Lejay, *Physical Review Letters* **94**, 156405 (2005).
- [6] J. Schoenes, C. Schonenberger, J. J. M. Franse, and A. A. Menovsky, *Physical Review B* **35**, 5375 (1987).
- [7] A. de Visser, F. E. Kayzel, A. A. Menovsky, J. J. M. Franse, J. van den Berg, and G. J. Nieuwenhuys, *Physical Review B* **34**, 8168 (1986).
- [8] C. Broholm, H. Lin, P. T. Matthews, T. E. Mason,

- W. J. L. Buyers, M. F. Collins, A. A. Menovsky, J. A. Mydosh, and J. K. Kjems, *Physical Review B* **43**, 12809 (1991).
- [9] H. Amitsuka, K. Matsuda, I. Kawasaki, K. Tenya, M. Yokoyama, C. Sekine, N. Tateiwa, T. Kobayashi, S. Kawarazaki, and H. Yoshizawa, *Journal of Magnetism and Magnetic Materials* **310**, 214 (2007).
- [10] N. P. Butch, J. R. Jeffries, S. Chi, J. B. Leão, J. W. Lynn, and M. B. Maple, *Physical Review B* **82**, 060408 (2010).
- [11] E. Hassinger, G. Knebel, K. Izawa, P. Lejay, B. Salce, and J. Flouquet, *Physical Review B* **77**, 115117 (2008).
- [12] H. Kusunose and H. Harima, *Journal of the Physical Society of Japan* **80**, 084702 (2011).
- [13] E. Ressouche, R. Ballou, F. Bourdarot, D. Aoki, V. Simonet, M. T. Fernandez-Diaz, A. Stunault, and J. Flouquet, *Physical Review Letters* **109**, 067202 (2012).
- [14] K. Haule and G. Kotliar, *Nature Physics* **5**, 796 (2009).
- [15] H. Ikeda, M.-T. Suzuki, R. Arita, T. Takimoto, T. Shibauchi, and Y. Matsuda, *Nature Physics* **8**, 528 (2012).
- [16] J. G. Rau and H.-Y. Kee, *Physical Review B* **85**, 245112 (2012).
- [17] P. Chandra, P. Coleman, J. A. Mydosh, and V. Tripathi, *Nature* **417**, 831 (2002).
- [18] S. Fujimoto, *Physical Review Letters* **106**, 196407 (2011).
- [19] P. S. Riseborough, B. Coqblin, and S. G. Magalhães, *Physical Review B* **85**, 165116 (2012).
- [20] T. Das, *Physical Review B* **89**, 045135 (2014).
- [21] C. Pépin, M. R. Norman, S. Burdin, and A. Ferraz, *Physical Review Letters* **106**, 106601 (2011).
- [22] C. Thomas, S. Burdin, C. Pépin, and A. Ferraz, *Physical Review B* **87**, 014422 (2013).
- [23] S. Elgazzar, J. Ruzs, M. Amft, P. M. Oppeneer, and J. A. Mydosh, *Nature Materials* **8**, 337 (2009).
- [24] P. Chandra, P. Coleman, and R. Flint, *Nature* **493**, 621 (2013).
- [25] F. Bourdarot, E. Hassinger, S. Raymond, D. Aoki, V. Taufour, L.-P. Regnault, and J. Flouquet, *Journal of the Physical Society of Japan* **79**, 064719 (2010).
- [26] C. R. Wiebe, J. A. Janik, G. J. MacDougall, G. M. Luke, J. D. Garrett, H. D. Zhou, Y.-J. Jo, L. Balicas, Y. Qiu, J. R. D. Copley, Z. Yamani, and W. J. L. Buyers, *Nature Physics* **3**, 96 (2007).
- [27] A. Villaume, F. Bourdarot, E. Hassinger, S. Raymond, V. Taufour, D. Aoki, and J. Flouquet, *Physical Review B* **78**, 012504 (2008).
- [28] D. A. Bonn, J. D. Garrett, and T. Timusk, *Physical Review Letters* **61**, 1305 (1988).
- [29] A. F. Santander-Syro, M. Klein, F. L. Boariu, A. Nuber, P. Lejay, and F. Reinert, *Nature Physics* **5**, 637 (2009).
- [30] R. Yoshida, Y. Nakamura, M. Fukui, Y. Haga, E. Yamamoto, Y. Onuki, M. Okawa, S. Shin, M. Hirai, Y. Muraoka, and T. Yokoya, *Physical Review B* **82**, 205108 (2010).
- [31] F. L. Boariu, C. Bareille, H. Schwab, A. Nuber, P. Lejay, T. Durakiewicz, F. Reinert, and A. F. Santander-Syro, *Physical Review Letters* **110**, 156404 (2013).
- [32] J.-Q. Meng, P. M. Oppeneer, J. A. Mydosh, P. S. Riseborough, K. Gofryk, J. J. Joyce, E. D. Bauer, Y. Li, and T. Durakiewicz, *Physical Review Letters* **111**, 127002 (2013).
- [33] E. Hassinger, G. Knebel, T. D. Matsuda, D. Aoki, V. Taufour, and J. Flouquet, *Physical Review Letters* **105**, 216409 (2010).
- [34] R. Okazaki, T. Shibauchi, H. J. Shi, Y. Haga, T. D. Matsuda, E. Yamamoto, Y. Onuki, H. Ikeda, and Y. Matsuda, *Science* **331**, 439 (2011).
- [35] S. Tonegawa, K. Hashimoto, K. Ikada, Y.-H. Lin, H. Shishido, Y. Haga, T. D. Matsuda, E. Yamamoto, Y. Onuki, H. Ikeda, Y. Matsuda, and T. Shibauchi, *Physical Review Letters* **109**, 036401 (2012).
- [36] S. Tonegawa, S. Kasahara, T. Fukuda, K. Sugimoto, N. Yasuda, Y. Tsuruhara, D. Watanabe, Y. Mizukami, Y. Haga, T. D. Matsuda, E. Yamamoto, Y. Onuki, H. Ikeda, Y. Matsuda, and T. Shibauchi, *Nature Communications* **5**, 5188 (2014).
- [37] S. Kambe, Y. Tokunaga, H. Sakai, T. D. Matsuda, Y. Haga, Z. Fisk, and R. E. Walstedt, *Physical Review Letters* **110**, 246406 (2013).
- [38] H. Amitsuka, *Workshop on hidden order, superconductivity and magnetism in URu₂Si₂*, Leiden (2013).
- [39] P. M. Oppeneer, J. Ruzs, S. Elgazzar, M.-T. Suzuki, T. Durakiewicz, and J. A. Mydosh, *Physical Review B* **82**, 205103 (2010).
- [40] D. Aoki, F. Bourdarot, E. Hassinger, G. Knebel, A. Miyake, S. Raymond, V. Taufour, and J. Flouquet, *Journal of Physics: Condensed Matter* **22**, 164205 (2010).
- [41] See Supplemental Material [<http://link.aps.org/supplemental/...>], which includes Refs. [42–45], for details about the laser heating estimation.
- [42] R. Hackl, R. Kaiser, and S. Schicktzan, *Journal of Physics C: Solid State Physics* **16**, 1729 (1983).
- [43] A. A. Maksimov, A. V. Puchkov, I. I. Tartakovskii, V. B. Timofeev, D. Reznik, and M. V. Klein, *Solid State Communications* **81**, 407 (1992).
- [44] A. Mialitsin, *Raman scattering from layered superconductors: effects of charge ordering, two-band superconductivity, and structural disorder.*, Ph.D. thesis, New Brunswick Rutgers (2010).
- [45] F. G. Aliev, V. Kovachik, V. V. Moshchalkov, V. V. Pryadun, N. E. Alekseevskii, A. V. Mitin, N. Agrait, S. Vieira, and R. Villar, *Journal of low temperature physics* **85**, 359 (1991).
- [46] W. Hayes and R. Loudon, *Scattering of Light by Crystals*, Dover Books on Physics (Dover Publications, 2004).
- [47] See Supplemental Material [<http://link.aps.org/supplemental/...>] for details about the extraction of the pure A_{2g} symmetry.
- [48] See Supplemental Material [<http://link.aps.org/supplemental/...>] for details about the measurements of the Raman response in other symmetries.
- [49] We are aware of a parallel Raman study by the group of G. Blumberg with similar results [50] interpreted in the context of the theory developed by Haule and Kotliar [14].
- [50] H.-H. Kung, R. E. Baumbach, E. D. Bauer, V. K. Thorsmølle, W.-L. Zhang, K. Haule, J. A. Mydosh, and G. Blumberg, *arXiv:1410.6398 [cond-mat]* (2014).
- [51] See Supplemental Material [<http://link.aps.org/supplemental/...>], which includes Ref. [52], for details about the A_{2g} symmetry.
- [52] H. Harima, K. Miyake, and J. Flouquet, *Journal of the Physical Society of Japan* **79**, 033705 (2010).
- [53] D. V. Khveshchenko and P. B. Wiegmann, *Physical Review Letters* **73**, 500 (1994).
- [54] R. Liu, D. Salamon, M. V. Klein, S. L. Cooper, W. C. Lee, S.-W. Cheong, and D. M. Ginsberg, *Physical Review Letters* **71**, 3709 (1993).

- [55] S. Yoon, M. Rübhausen, S. L. Cooper, K. H. Kim, and S. W. Cheong, Physical review letters **85**, 3297 (2000).
- [56] P. E. Sulewski, P. A. Fleury, K. B. Lyons, and S.-W. Cheong, Physical Review Letters **67**, 3864 (1991).
- [57] T. P. Devereaux and R. Hackl, Review of Modern Physics **79**, 175 (2007).
- [58] W. T. Guo, Z. G. Chen, T. J. Williams, J. D. Garrett, G. M. Luke, and N. L. Wang, Physical Review B **85**, 195105 (2012).
- [59] U. Nagel, T. Uleksin, T. Room, R. P. S. M. Lobo, P. Lejay, C. C. Homes, J. S. Hall, A. W. Kinross, S. K. Purdy, T. Munsie, T. J. Williams, G. M. Luke, and T. Timusk, Proceedings of the National Academy of Sciences **109**, 19161 (2012).
- [60] J. S. Hall, U. Nagel, T. Uleksin, T. Room, T. Williams, G. Luke, and T. Timusk, Physical Review B **86**, 035132 (2012).
- [61] M. W. McElfresh, J. D. Thompson, J. O. Willis, M. B. Maple, T. Kohara, and M. S. Torikachvili, Physical Review B **35**, 43 (1987).
- [62] M. B. Maple, J. W. Chen, Y. Dalichaouch, T. Kohara, C. Rossel, M. S. Torikachvili, M. W. McElfresh, and J. D. Thompson, Physical Review Letters **56**, 185 (1986).
- [63] R. A. Fisher, S. Kim, Y. Wu, N. E. Phillips, M. W. McElfresh, M. S. Torikachvili, and M. B. Maple, Physica B: Condensed Matter **163**, 419 (1990).
- [64] P. Aynajian, E. H. da Silva Neto, C. V. Parker, Y. Huang, A. Pasupathy, J. Mydosh, and A. Yazdani, Proceedings of the National Academy of Sciences **107**, 10383 (2010).
- [65] A. R. Schmidt, M. H. Hamidian, P. Wahl, F. Meier, A. V. Balatsky, J. D. Garrett, T. J. Williams, G. M. Luke, and J. C. Davis, Nature **465**, 570 (2010).
- [66] F. Bourdarot, S. Raymond, and L.-P. Regnault, Philosophical Magazine (2014).
- [67] See Supplemental Material [<http://link.aps.org/supplemental/...>] for details about the temperature dependence of the spectral weight of the A_{2g} features.
- [68] P. M. Oppeneer, S. Elgazzar, J. Rusz, Q. Feng, T. Durakiewicz, and J. A. Mydosh, Physical Review B **84**, 241102 (2011).
- [69] See Supplemental Material [<http://link.aps.org/supplemental/...>], which includes Ref. [70], for details about the magnetic field dependence of the Raman peak.
- [70] S. A. M. Mentink, T. E. Mason, S. Sullow, G. J. Nieuwenhuys, A. A. Menovsky, J. A. Mydosh, and J. A. A. J. Perenboom, Physical Review B **53**, R6014 (1996).
- [71] F. Bourdarot, B. Fak, K. Habicht, and K. Prokes, Journal of Magnetism and Magnetic Materials **272-276**, E31 (2004).
- [72] R. Yoshida, K. Tsubota, T. Ishiga, M. Sunagawa, J. Sonoyama, D. Aoki, J. Flouquet, T. Wakita, Y. Mu-raoka, and T. Yokoya, Scientific Reports **3**, 02750 (2013).
- [73] C. Bareille, F. L. Boariu, H. Schwab, P. Lejay, F. Reinert, and A. F. Santander-Syro, Nature Communications **5**, 4326 (2014).
- [74] S. L. Cooper, M. V. Klein, Z. Fisk, and J. L. Smith, Physical Review B **34**, 6235 (1986).
- [75] Y. Gallais, R. M. Fernandes, I. Paul, L. Chauvière, Y.-X. Yang, M.-A. Méasson, M. Cazayous, A. Sacuto, D. Colson, and A. Forget, Physical Review Letters **111**, 267001 (2013).
- [76] T. T. M. Palstra, A. A. Menovsky, G. J. Nieuwenhuys, and J. A. Mydosh, Journal of Magnetism and Magnetic Materials **54**, 435 (1986).
- [77] P. Santini and G. Amoretti, Physical Review Letters **73**, 1027 (1994).
- [78] S. L. Cooper, M. V. Klein, Z. Fisk, and J. L. Smith, Physical Review B **37**, 2251 (1988).
- [79] See Supplemental Material [<http://link.aps.org/supplemental/...>], which includes Ref. [80], for details about the CEF excitations selection rules.
- [80] G. F. Koster, *Properties of the thirty-two point groups* (M.I.T. Press, Cambridge, 1963).
- [81] K. Iwasa, L. Hao, K. Kuwahara, M. Kohgi, S. R. Saha, H. Sugawara, Y. Aoki, H. Sato, T. Tayama, and T. Sakakibara, Physical Review B **72**, 024414 (2005).
- [82] A. M. Shvaika, O. Vorobyov, J. K. Freericks, and T. P. Devereaux, Physical Review B **71**, 045120 (2005).
- [83] Indeed, in the effective mass approximation, the electron-hole excitations continuum is not A_{2g} active except by considering an unlikely electronic band structure on which $\frac{\partial^2 E}{\partial k_x \partial k_y} \neq \frac{\partial^2 E}{\partial k_y \partial k_x}$ in some k-space region of the Fermi surface.

Supplemental Material : Symmetry of the Excitations in the Hidden Order State of URu₂Si₂

J. Buhot, M.A. Méasson, Y. Gallais, M. Cazayous, and A. Sacuto
*Laboratoire Matériaux et Phénomènes Quantiques, UMR 7162 CNRS,
 Université Paris Diderot, Bât. Condorcet 75205 Paris Cedex 13, France*

G. Lapertot and D. Aoki
*Univ. Grenoble Alpes, INAC-SPSMS, F-38000 Grenoble, France and
 CEA, INAC-SPSMS, F-38000 Grenoble, France*
 (Dated: March 2, 2022)

EXPERIMENTAL DETAILS

Laser heating estimation

The focused laser light used for Raman experiment induces a local heating on the crystal surface. To study the hidden order of URu₂Si₂, we aimed to reach with certainty the HO state below T₀=17.5 K and to track accurately the temperature dependence of various features. Therefore, we used a low laser power, and we took special care to estimate the laser heating. For each experiment, the laser heating was estimated for a given bath temperature by using the method reported in [1]. Then, the temperature dependence of this laser heating was determined, as quoted in [2, 3], by considering the temperature dependence of the thermal conductivity of URu₂Si₂ along the c axis [4, 5]. For a spot light of $\sim 50\mu\text{m}$ of diameter focused on samples in vacuum, the laser heating is ~ 2 K/mW for a bath temperature of 4 K and ~ 1 K/mW for a bath temperature of 30 K. The reported temperatures are estimated to have an accuracy of ± 1 K.

Extraction of the pure A_{2g} symmetry

For the D_{4h} space group, there is no configuration of incident and scattered polarizations of light which provides a pure A_{2g} Raman response. Nevertheless, we were able to extract a pure A_{2g} signal using simple operations between Raman responses of mixed symmetries. We have added the following contributions:

$$[A_{2g} + B_{1g}] + [A_{2g} + B_{2g}] = [2A_{2g} + B_{1g} + B_{2g}] \quad (1)$$

Thanks to the use of circular polarizations, we have access to the symmetries:

$$[B_{1g} + B_{2g}] \quad (2)$$

Thus, by removing the contribution (2) from the contribution (1), we obtained a pure A_{2g} signal.

SYMMETRY DEPENDENCE OF THE RAMAN SIGNAL

Figure 1 shows the Raman spectra of URu₂Si₂ in all symmetries, i.e. mixtures of A_{1g}, B_{1g}, A_{2g} and B_{2g}, when the polarizations of light are within the (a,b) plane. Only the E_g symmetry cannot be probed in this configuration. The measurements were done in the hidden order state (HO) (10.5 K and 13 K) and in the paramagnetic (PM) state (22 K and 23 K). In the HO state, the [A_{2g}+B_{2g}] and the [A_{2g}+B_{1g}] symmetries responses exhibit a gap opening below 55 cm⁻¹ and a sharp excitation at ~ 14 cm⁻¹ deep inside the gap (See Figure 1 (a) and (e)). These features are not observed in the other symmetries, i.e. [A_{1g}+B_{2g}], [B_{1g}+B_{2g}] and [A_{1g}+B_{1g}] contributions (See Figure 1 (b), (c), (d), respectively). Therefore, we concluded that the two signatures of the HO state have A_{2g} symmetry [6]. For comparison, the spectra were reported without any normalization, and they were measured with the same laser power and the same optical set-up (except for the insertion of polarizers). We also checked that in the [B_{1g}+B_{2g}] symmetry the Raman response is the same at 35 K as at 13 K and at 22 K. For comparison, we presented a large energy scale in the insets of the Figure 1, in order to show the phonon mode intensities. The A_{1g} and B_{1g} phonon modes are visible here. For some symmetries, a leakage of the phonon modes due to the crystal misalignment is observed (See insets of Figure 1 (a) and (c)). Within our accuracy, there is no signature of charge nematic fluctuations [7], neither in B_{1g} nor in B_{2g} symmetry. We cannot provide any additional evidence for the fourfold symmetry breaking reported by torque [8] and by cyclotron resonance experiments [9].

TEMPERATURE DEPENDENCE OF THE RAMAN SIGNATURES OF THE HIDDEN ORDER STATE

Figure 2 shows the [A_{2g}+B_{1g}] Raman response of URu₂Si₂ at various temperatures below 25 K. As shown in panel (a), the A_{2g} Raman gap closes abruptly near

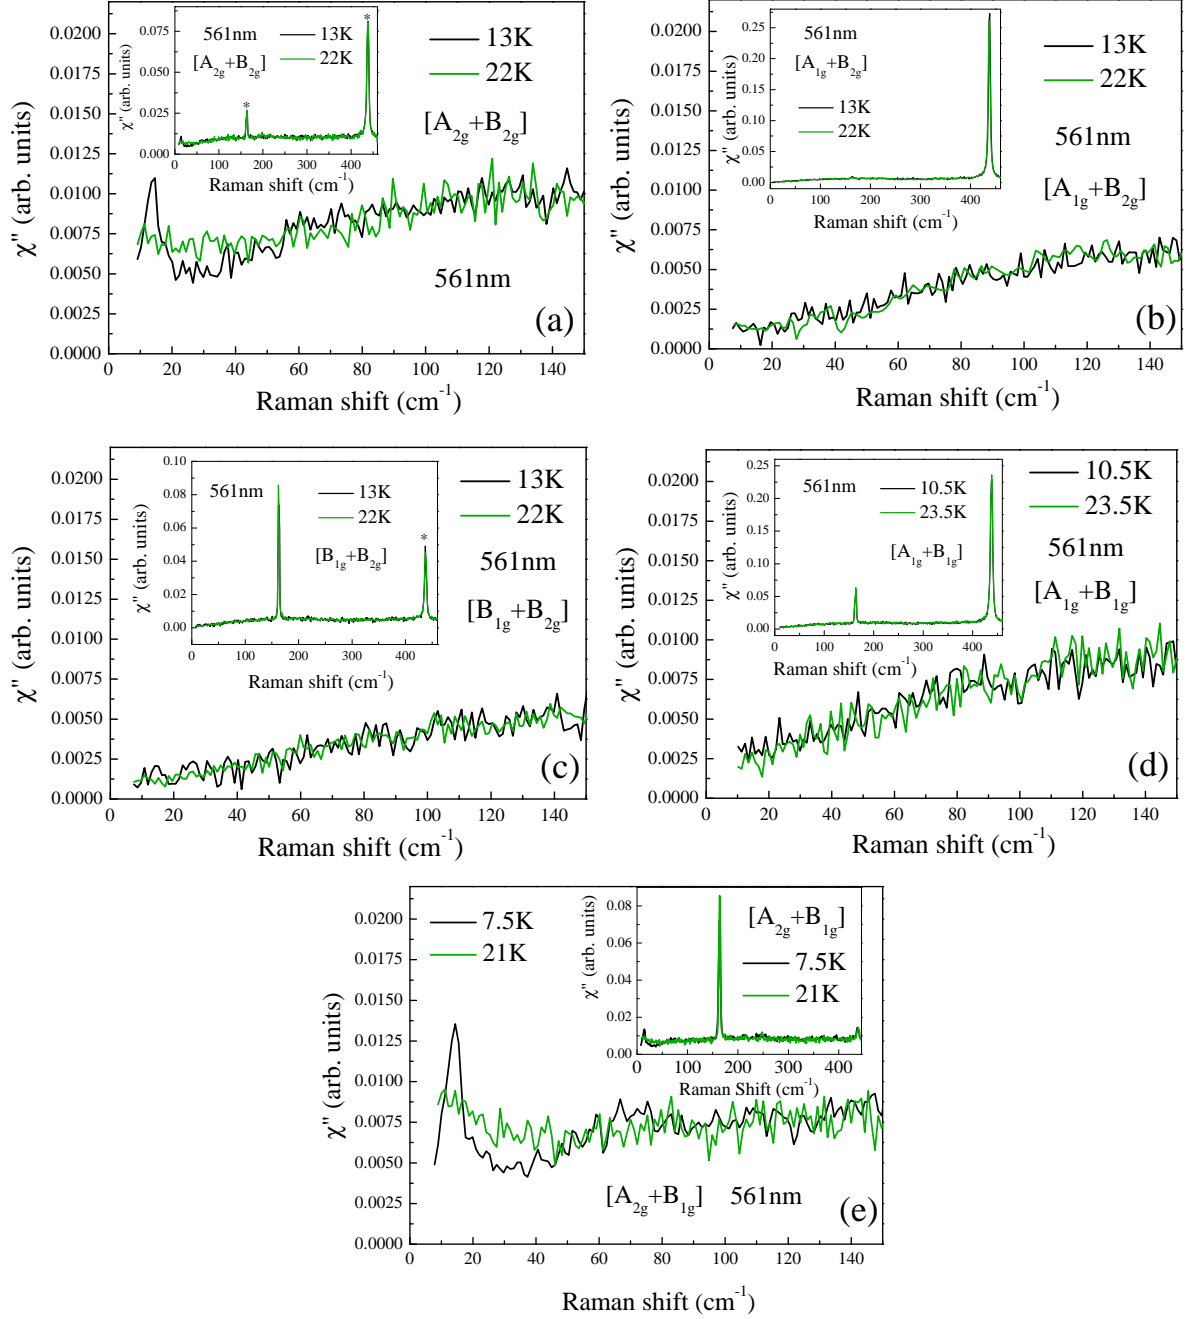


FIG. 1. (Color online) Raman spectra of URu_2Si_2 in the HO phase (black line) and in the PM phase (green line) in the $A_{2g}+B_{2g}$ (a), $A_{1g}+B_{2g}$ (b), $B_{1g}+B_{2g}$ (c), $A_{1g}+B_{1g}$ (d) and $A_{2g}+B_{1g}$ symmetries (e). All spectra have been measured with the same laser power and the same optical set-up. Large energy range with the same intensity scale is shown in the insets for each symmetries. Leakage of phonon modes are marked by a black star.

T_0 , with a filling of the gap starting above 17.2 K. The energy of the gap remains roughly constant until it closes completely. Figure 2(b) and (c) present the spectra focused on the A_{2g} peak with data measured on a sample in vacuum (also presented Figure 2(a)), and with data measured during another experiment with sample in exchange gas, respectively. The A_{2g} peak continuously loses

spectral weight and already starts to soften while the gap is still fully open, as evidenced in Figure 2(b). Above about 16.5 K, the A_{2g} peak abruptly softens and broadens. The peaks are fitted with a Voigt profile which takes into account the resolution of the spectrometer. The values of the position and FWHM extracted from these fits are reported in Figure 2 of the Letter as full squares and

triangles for sample in vacuum and in exchange gas, respectively.

We evaluated the spectral weights of the sharp peak and the gap depletion in the HO state and the total spectral weight by integrating $\chi''(\omega)$. The spectral weight of the sharp peak smoothly decreases with decreasing temperature (See figure 3(a)). The integration of the magnetic resonance at \mathbf{Q}_0 measured by INS is also reported figure 3(a). The T-dependence of the two spectral weights roughly follows the same trend. Discussing a precise temperature dependence (BCS type) of the Raman peak is beyond our accuracy. As clearly shown in figure 3(b), the total spectral weight is neither conserved in the HO state between the gap and the sharp peak nor between the HO state and the PM state. We conclude that no clear spectral weight transfer exists between the gap and the peak. We observed the closing of the gap at $18 \text{ K} \pm 1 \text{ K}$, while the peak becomes broader and quasi-elastic.

MAGNETIC FIELD DEPENDENCE OF THE HO SIGNATURES

The magnetic field dependence of the Raman response has been performed in a ^4He pumped cryostat with the sample in exchange gas using circular polarizations. As shown Figure 4, the peak hardens slightly under magnetic field up to 10 T which is qualitatively consistent with the magnetic field dependence of the neutron resonance E_0 [11]. The peak does not broaden under magnetic field. The A_{2g} gap remains open under magnetic field up to 10 T without any significative shift in energy, as expected from the resistivity measurements under magnetic field [12].

A_{2g} SYMMETRY

Two distinct signatures of the HO state, namely the gap and the sharp peak, are reported to have a well-defined symmetry A_{2g} . The A_{2g} transforms like the function $ixy(x^2 - y^2)$ (See Figure 5) or R_z (axial vector along z axis). It respects the 4-fold symmetry C_4 and the inversion center symmetry I . It lacks the two-fold axis symmetries C_2 (axis x and y) and C_2'' (axis (110)) and the reflections σ_v (planes xz and yz) and σ_d (planes $\perp(110)$ and $\perp(1\bar{1}0)$). Stereographic projection of the elementary A_{2g} symmetries is shown Figure 5. The A_{2g} symmetry is equivalent to the C_{4h} subgroup of the D_{4h} group.

We emphasize that the order parameter of the HO state does not *necessarily* have the same A_{2g} symmetry as the Raman signatures.

Now, we discuss the Raman selection rules in the space group of URu_2Si_2 , i.e. $n^\circ 139$, and in the 4 space groups selected by Harima et al. [13]. All the space groups se-

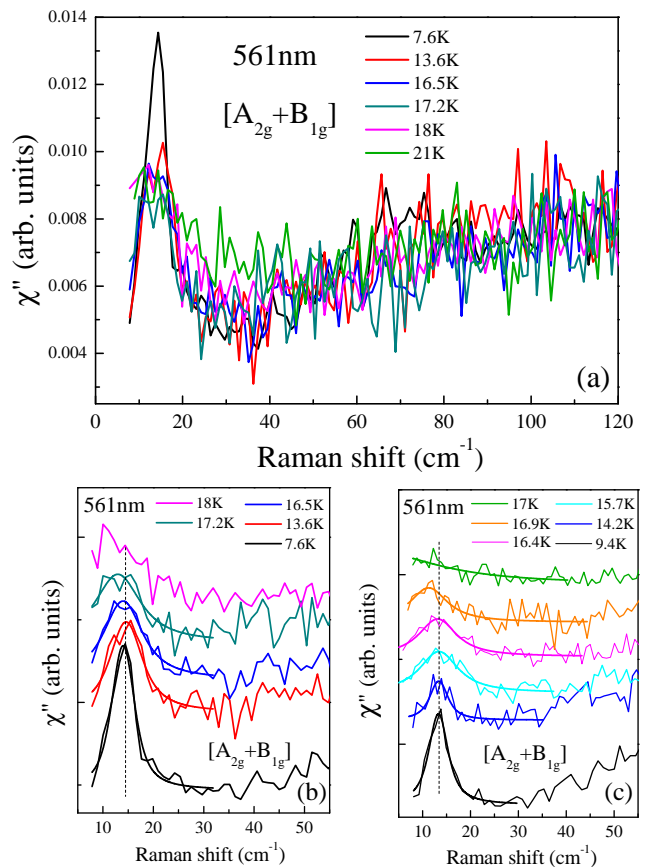


FIG. 2. (Color online) Raman spectra of URu_2Si_2 in the $A_{2g}+B_{1g}$ symmetry at several temperatures across the hidden order transition. All the temperatures are estimated at $\pm 1 \text{ K}$. (a) and (b) Data extracted from an experiment with sample in vacuum. (c) Data extracted from an experiment with sample in exchange gas. In (b) and (c), the spectra focused on the A_{2g} peaks are shifted for clarity. The lines are fits done with a Voigt function taking into account the resolution of the spectrometer.

lected by Harima et al [13] ($n^\circ 126, 128, 134, 136$) as possible candidate for the space group of the HO state have the point symmetry D_{4h} . Then, the selection rules for the phonons are the same inside the HO state than in the PM state (group $n^\circ 139$). However, the local point symmetry at the Uranium site depends on the space group as shown Table I. This will change the irreducible representations and then the selection rules for any local excitations based on the Uranium sites. Table I gives the mapping of the representations (of the PM state) into the representations of the new local point group (of the HO state). For the space groups $n^\circ 126$ and 134 , the mapping of the irreducible representations is equivalent to the one in the space group $n^\circ 139$. Thus the Raman matrices and the selection rules are the same, including the ones for crystalline electric field (CEF) excitations. However for the space groups $n^\circ 128$ and 136 , the irreducible rep-

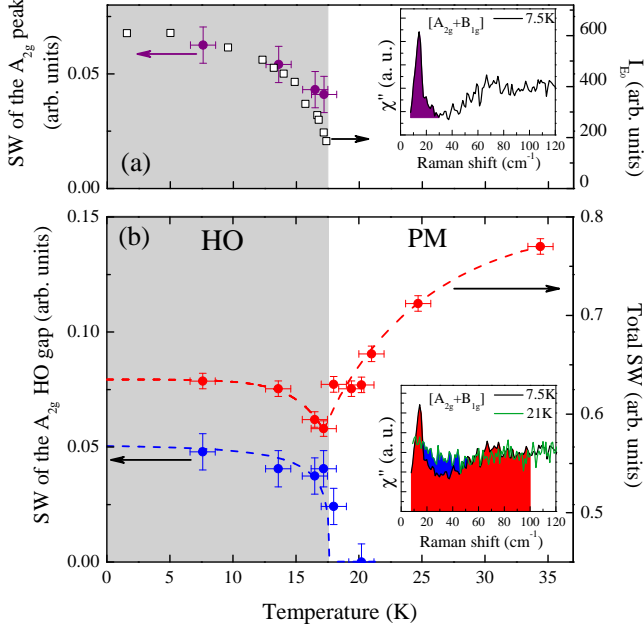


FIG. 3. (Color online) (a) Spectral weight of the A_{2g} sharp Raman peak and integrated imaginary part of the neutron dynamical spin susceptibility at \mathbf{Q}_0 , I_{E_0} [10] versus temperature. Inset: illustration of the calculation of the spectral weight of the Raman peak. (b) Spectral weight of the HO gap calculated just above the A_{2g} peak and total spectral weight up to 100 cm^{-1} . The A_{2g} spectral weight is not conserved. The gap closes abruptly near T_0 . Inset: illustration of the calculation of the spectral weights.

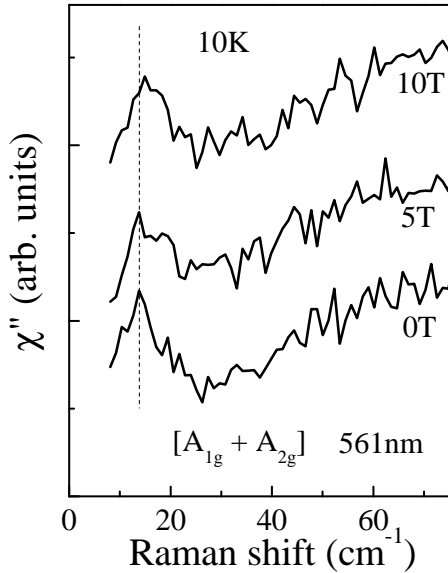


FIG. 4. (Color online) (a) Raman spectra of URu_2Si_2 in the $A_{2g} + A_{1g}$ symmetry in the HO state (10 K) at 0, 5 and 10 T. Data have been shifted for more clarity and the same background has been subtracted from the raw data. The A_{2g} sharp peak slightly hardens and the A_{2g} gap is roughly stable with increasing magnetic field.

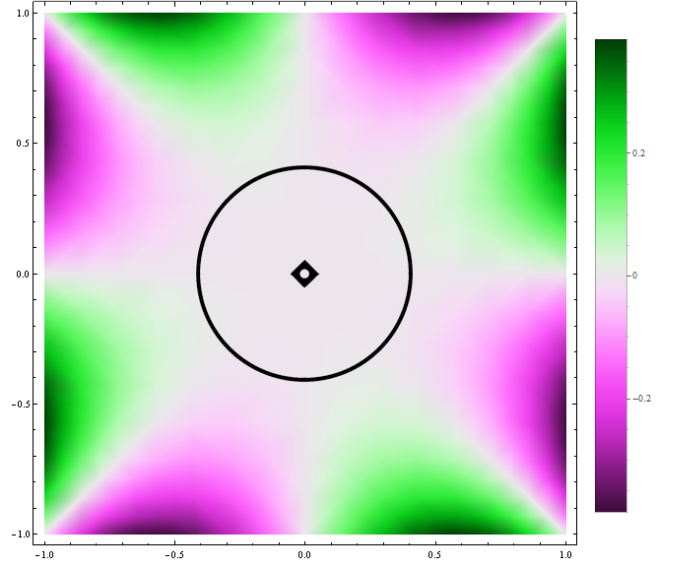


FIG. 5. (Color online) Representation of the A_{2g} function $xy(x^2 - y^2)$. Middle: Stereographic projection of the A_{2g} symmetries (equivalent to the C_{4h} subgroup of the D_{4h} group).

representations are different and the selection rules for local excitations on the Uranium sites have to be revisited.

Next, assuming that the A_{2g} peak is due to a local excitation on the Uranium site such as a CEF excitation, if the HO state is described by the space groups n° 136, a A_{2g} Raman signal would be accompanied by a signal in the B_{2g} symmetry (note here that the symmetries we used are the ones of the D_{4h} point group). For the space group n° 128 we would expect a non zero Raman signal in the A_{1g} symmetry together with the A_{2g} one [14]. The relative intensity of these signals depends on the Raman matrices and cannot be assessed by symmetry arguments alone. For the space groups n° 126 and 134, the Raman response in the A_{2g} channel is independent of the ones in all others symmetries, i.e. we do not expect, a priori, a signal in another symmetry.

We discuss now the selection rules for particular excitations, i.e. the CEF excitations. Table II provides all the CEF excitations that give rise to a signal in the A_{2g} channel. In both cases, with an even (simple representation) or odd (double representation) number of localized electrons, some CEF excitations are active in the A_{2g} symmetry. These results are extracted from the multiplication tables of the irreducible representations [15] and are independent on the respective positions in energy of the CEF levels. Some of the CEF transitions reported in table II are also active in few additional symmetries (see [15]).

Space group	n°139 (D_{4h})	n°126 (D_{4h})	n°128 (D_{4h})	n°134 (D_{4h})	n°136 (D_{4h})
Local Point symmetry at U	D_{4h}	D_4	C_{4h}	D_{2d}	D_{2h}
Irreducible Representations (simple)	$\Gamma_1^+ (A_{1g})$	$\Gamma_1 (A_1)$	$\Gamma_1^+ (A_g)$	$\Gamma_1 (A_1)$	$\Gamma_1^+ (A_g)$
	$\Gamma_2^+ (A_{2g})$	$\Gamma_2 (A_2)$	$\Gamma_1^+ (A_g)$	$\Gamma_2 (A_2)$	$\Gamma_3^+ (B_{1g})$
	$\Gamma_3^+ (B_{1g})$	$\Gamma_3 (B_1)$	$\Gamma_2^+ (B_g)$	$\Gamma_3 (B_1)$	$\Gamma_1^+ (A_g)$
	$\Gamma_4^+ (B_{2g})$	$\Gamma_4 (B_2)$	$\Gamma_2^+ (B_g)$	$\Gamma_4 (B_2)$	$\Gamma_3^+ (B_{1g})$
	$\Gamma_5^+ (E_g)$	$\Gamma_5 (E)$	$\Gamma_3^+ (^1E_g) \oplus \Gamma_4^+ (^2E_g)$	$\Gamma_5 (E)$	$\Gamma_2^+ (B_{2g}) \oplus \Gamma_4^+ (B_{3g})$
Irreducible Representations (double)	Γ_6^+	Γ_6	$\Gamma_5^+ \oplus \Gamma_6^+$	Γ_6	Γ_5^+
	Γ_7^+	Γ_7	$\Gamma_7^+ \oplus \Gamma_8^+$	Γ_7	Γ_5^+

TABLE I. Mapping of the irreducible representations of the point group D_{4h} (space group of URu_2Si_2 and local point symmetry at the Uranium site in URu_2Si_2) into the irreducible representations of the new local point groups upon reduction of symmetry. The new local point groups define the symmetry at the Uranium site associated with the 4 space groups selected by Harima et al.[13] as candidate for the HO state. Are shown the irreducible representations in the simple and double representation. The local point symmetry is relevant for the selection rules of localized excitations on the Uranium site such as CEF excitations.

Space group	n°139 (D_{4h})	n°126 (D_{4h})	n°128 (D_{4h})	n°134 (D_{4h})	n°136 (D_{4h})
Local Point symmetry at U	D_{4h}	D_4	C_{4h}	D_{2d}	D_{2h}
Possible A_{2g} CEF transitions	$\Gamma_1^+ \rightleftharpoons \Gamma_2^+$	$\Gamma_1 \rightleftharpoons \Gamma_2$	$\Gamma_1^+ \rightleftharpoons \Gamma_1^+$	$\Gamma_1 \rightleftharpoons \Gamma_2$	$\Gamma_1^+ \rightleftharpoons \Gamma_3^+$
	$\Gamma_3^+ \rightleftharpoons \Gamma_4^+$	$\Gamma_3 \rightleftharpoons \Gamma_4$	$\Gamma_2^+ \rightleftharpoons \Gamma_2^+$	$\Gamma_3 \rightleftharpoons \Gamma_4$	
	$\Gamma_5^+ \rightleftharpoons \Gamma_5^+$	$\Gamma_5 \rightleftharpoons \Gamma_5$	$\Gamma_3^+ \rightleftharpoons \Gamma_4^+$	$\Gamma_5 \rightleftharpoons \Gamma_5$	$\Gamma_2^+ \rightleftharpoons \Gamma_4^+$
	$\Gamma_6^+ \rightleftharpoons \Gamma_6^+$	$\Gamma_6 \rightleftharpoons \Gamma_6$	$\Gamma_5^+ \rightleftharpoons \Gamma_6^+$	$\Gamma_6 \rightleftharpoons \Gamma_6$	$\Gamma_5^+ \rightleftharpoons \Gamma_5^+$
	$\Gamma_7^+ \rightleftharpoons \Gamma_7^+$	$\Gamma_7 \rightleftharpoons \Gamma_7$	$\Gamma_7^+ \rightleftharpoons \Gamma_8^+$	$\Gamma_7 \rightleftharpoons \Gamma_7$	

TABLE II. List of the CEF excitations localized on the Uranium atoms and Raman active in the A_{2g} symmetry, for each space groups described in Table I. Some of these excitations are active in other symmetries (see the multiplication tables [15]).

-
- [1] R. Hackl, R. Kaiser, and S. Schicktzan, Journal of Physics C: Solid State Physics **16**, 1729 (1983).
[2] A. A. Maksimov, A. V. Puchkov, I. I. Tartakovskii, V. B. Timofeev, D. Reznik, and M. V. Klein, Solid State Communications **81**, 407 (1992).
[3] A. Mialitsin, *Raman scattering from layered superconductors: effects of charge ordering, two-band superconductivity, and structural disorder.*, Ph.D. thesis, New Brunswick Rutgers (2010).
[4] K. Behnia, R. Bel, Y. Kasahara, Y. Nakajima, H. Jin, H. Aubin, K. Izawa, Y. Matsuda, J. Flouquet, Y. Haga, Y. Onuki, and P. Lejay, Physical Review Letters **94**, 156405 (2005).
[5] F. G. Aliev, V. Kovachik, V. V. Moshchalkov, V. V.

- Pryadun, N. E. Alekseevskii, A. V. Mitin, N. Agrait, S. Vieira, and R. Villar, Journal of low temperature physics **85**, 359 (1991).
[6] We are aware of parallel study by G. Blumberg et al. who reports peaks in the A_{2g} and A_{1g} symmetry. Within our experimental accuracy (noise $\sim 1/5$ of the A_{2g} peak), we cannot resolve any peak in the A_{1g} symmetry.
[7] Y. Gallais, R. M. Fernandes, I. Paul, L. Chauvière, Y.-X. Yang, M.-A. Méasson, M. Cazayous, A. Sacuto, D. Colson, and A. Forget, Physical Review Letters **111**, 267001 (2013).
[8] R. Okazaki, T. Shibauchi, H. J. Shi, Y. Haga, T. D. Matsuda, E. Yamamoto, Y. Onuki, H. Ikeda, and Y. Matsuda, Science **331**, 439 (2011).
[9] S. Tonegawa, K. Hashimoto, K. Ikada, Y.-H. Lin, H. Shishido, Y. Haga, T. D. Matsuda, E. Yamamoto, Y. Onuki, H. Ikeda, Y. Matsuda, and T. Shibauchi,

- Physical Review Letters **109**, 036401 (2012).
- [10] F. Bourdarot, E. Hassinger, S. Raymond, D. Aoki, V. Taufour, L.-P. Regnault, and J. Flouquet, Journal of the Physical Society of Japan **79**, 064719 (2010).
 - [11] F. Bourdarot, B. Fak, K. Habicht, and K. Prokes, Journal of Magnetism and Magnetic Materials **272-276**, E31 (2004).
 - [12] S. A. M. Mentink, T. E. Mason, S. Sullow, G. J. Nieuwenhuys, A. A. Menovsky, J. A. Mydosh, and J. A. A. J. Perenboom, Physical Review B **53**, R6014 (1996).
 - [13] H. Harima, K. Miyake, and J. Flouquet, Journal of the Physical Society of Japan **79**, 033705 (2010).
 - [14] H.-H. Kung, R. E. Baumbach, E. D. Bauer, V. K. Thorsmølle, W.-L. Zhang, K. Haule, J. A. Mydosh, and G. Blumberg, arXiv:1410.6398 [cond-mat] (2014).
 - [15] G. F. Koster, *Properties of the thirty-two point groups* (M.I.T. Press, Cambridge, 1963).