

Superconductivity in $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ and $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$: A comparative study

Om Prakash, A. Thamizhavel, S. Ramakrishnan

Department of Condensed Matter Physics and Material Science, Tata Institute of Fundamental Research, Mumbai-400005, India

E-mail: op1111shukla@gmail.com

Abstract. A variety of unconventional superconductors have low carrier density as a common factor. However, the underlying mechanism of superconductivity in such low carrier density systems is not well understood. Besides, small carrier density is an unfavourable component for conventional superconductivity as described by the Bardeen-Cooper-Schrieffer (BCS) theory. Therefore, studying low carrier density systems can lead to a better understanding in such systems. In this paper, we report superconductivity property studies in low carrier density systems, $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ and $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$, using various experimental techniques. Single crystals of $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ and $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$ have been grown using the Czochralski crystal pulling method in a tetra-arc furnace. The x-ray diffraction experiment reveals that both compounds crystallize in cubic structure (space group $Pm\bar{3}n$, no. 223). The transport, magnetization and heat capacity measurements show that $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ single crystal undergoes a superconducting transition at 2.85 K, whereas, $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$ becomes superconductor at 3.1 K.

1. Introduction

A variety of unconventional superconductors present low density of the charge carriers as a common factor, implying that it could be the basis for a unifying picture to understand the superconductivity in such exotic systems. Low density of charge carriers is one of the characteristic features which is shared by cuprates, fullerenes and MgB_2 [1, 2, 3]. This is quite surprising since low carrier density is an unfavourable element for superconductivity within the conventional framework of BCS [4] or Migdal–Eliashberg [5, 6] theories. Moreover, a small superfluid density, is unavoidably related to poor screening and strong electronic correlations, ingredients which are expected to be also detrimental for conventional superconductivity. On these grounds it is hard to understand why these low carrier materials are the best superconductors. As far as the superconductivity exhibited by inter-metallic compounds is concerned, the role of electron-phonon interaction cannot be overlooked. However, one may have to look beyond the conventional framework of BCS or Migdal–Eliashberg theories in order to understand the unconventional superconductivity in these compounds. From the experimental side, it is important to look for new superconducting materials with low carrier density.

2. Experimental Details

Single crystals of $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ and $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$ have been grown using Czochralski crystal pulling method in a tetra-arc furnace under high purity argon atmosphere. Stoichiometric amount of $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ and $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$ (10 g each) was taken and melted 4-5 times in the tetra-arc furnace

to make a homogeneous polycrystalline mixture. Single crystals were pulled using a tungsten seed rod at the rate of 10 mm/h for about 6 h to get 5-6 mm long and 3-4 mm thick crystals. The phase purity was characterized by powder X-ray diffraction using PANalytical X-ray diffractometer. Single crystals were oriented along the crystallographic direction [100] using Laue back reflection using Huber Laue diffractometer and cut to desired shape and dimensions using a spark erosion cutting machine. Resistivity measurements were done in a home made setup using standard four-probe technique. Magnetization measurements were done in commercial SQUID magnetometer (MPMS5, Quantum Design, USA) and heat capacity measurements were done using PPMS.

3. Results and Discussion

The crystal structure of $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ is shown in Fig. 1. Both compounds have same crystal structure and cubic symmetry ($Pm\bar{3}n$, space group # 223). Rietveld analysis [7] of the Powder X-ray diffraction (PXRD) of $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ is shown in Fig. 2. The temperature dependence of resistivity $\rho(T)$ from 300 to 2K for $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ and $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$ are shown in Fig. 3. A semi-metallic behaviour ($\frac{d\rho}{dT} < 0$) can be observed in the normal state resistivity data of both the compounds. The magnetoresistance data for $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ and $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$ is shown in Fig. 4.

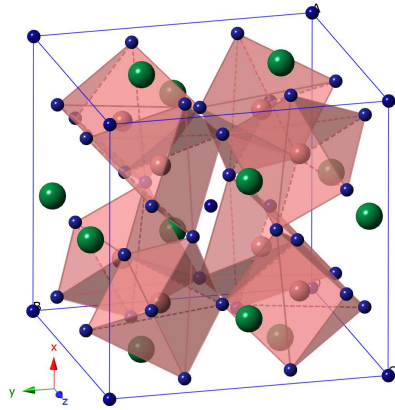


Figure 1. Crystal structure of $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$. Yttrium atoms are shown in green in 6d position, Ruthenium are shown in light pink in 8e position and Germanium are shown in dark blue in 2a and 24k Wyckoff positions.

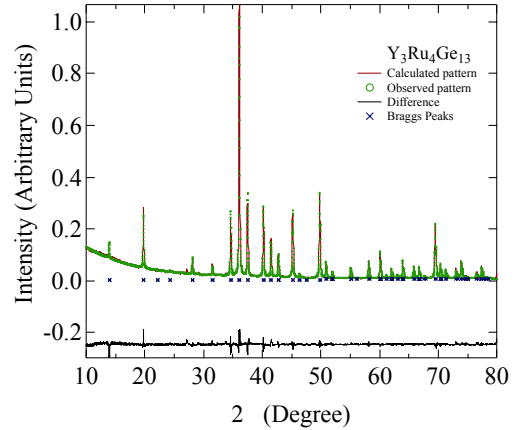


Figure 2. Rietveld analysis of the powder XRD pattern of $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$. No impurity peaks are observed indicating single phase nature of the compound. Similar PXRD pattern is also observed for $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$.

The width of the superconducting transition increases with increasing magnetic field. The transition temperature is taken at the point where resistivity becomes half of its normal state value. The temperature dependence of the upper critical field for $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ and $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$ is shown in Fig. 5. We estimate the orbital upper critical field, $\mu_0 H_{c2}(0)$, for both the compounds using Werthamer-Helfand-Hohenberg (WHH) expression[8], $\mu_0 H_{c2}(0) = -0.693 T_c \frac{dH_{c2}}{dT} \big|_{T=T_c}$ in the dirty limit for type-II superconductors. A nearly linear relationship is observed in Fig. 5 between $\mu_0 H_{c2}$ and T_c in the proximity of the transition temperature (T_c at $H = 0$) for both the compounds but the linear trend is more prominent for $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$. The slope $\frac{dH_{c2}}{dT} \big|_{T=T_c}$ is used to calculate $\mu_0 H_{c2} = 4.63 \pm 0.09$ T for $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ and $\mu_0 H_{c2} = 5.68 \pm 0.12$ T for $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$ using the WHH formula in the dirty limit. The value of $\mu_0 H_{c2}$ is smaller than the weak coupling Pauli paramagnetic limit $\mu_0 H^{\text{Pauli}} = 1.82 T_c = 5.09$ T for $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ and

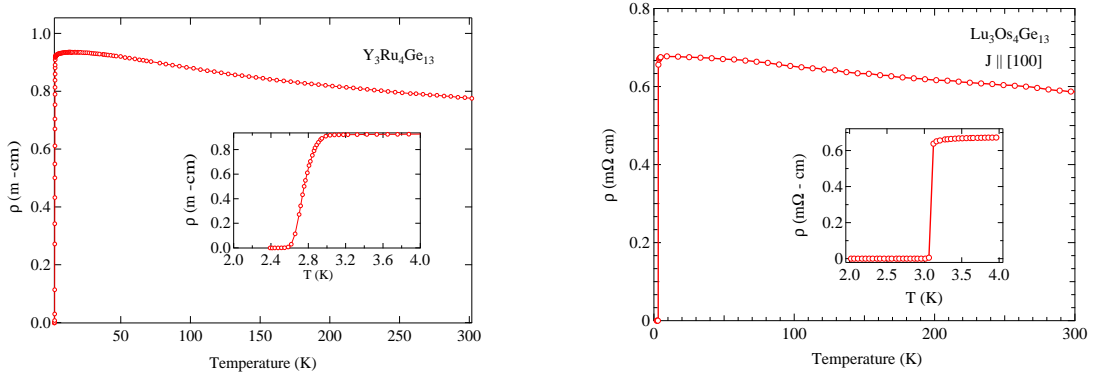


Figure 3. The temperature dependence of the electrical resistivity (ρ) along the (100) directions of cubic (Pm3n) $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ and $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$. Insets show the low temperature data indicating superconducting transition in both compounds. Resistivity data from 2 to 300K clearly shows the semi-metallic nature of both the compounds.

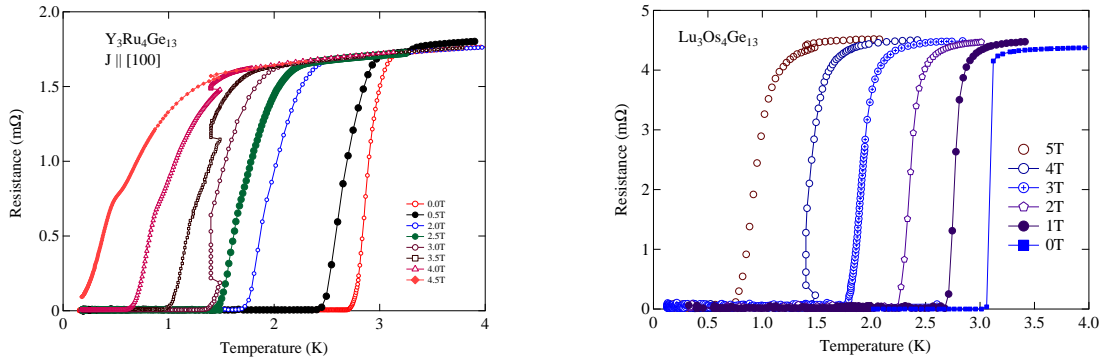


Figure 4. The resistance vs temperature data at different magnetic fields for $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ and $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$. With the increase in applied magnetic field the superconducting transition becomes slightly broader for both compounds. The temperature dependence of the upper critical field ($\mu_0 H_{c2}(T)$) is extracted from these measurements.

$\mu_0 H^{\text{Pauli}} = 5.80$ T for $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$. The upper critical field value $\mu_0 H_{c2}(0)$ can be used to estimate the Ginzburg-Landau coherence length $\xi(0)_{GL} = \sqrt{\Phi_0/2\pi H_{c2}(0)} = 80.4 \pm 0.5 \text{ \AA}$ for $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ and $\xi(0)_{GL} = 76.1 \pm 0.7 \text{ \AA}$ for $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$, where $\Phi_0 = hc/2e$ is the magnetic flux quantum.

The DC-magnetisation data of both compounds is shown in Fig. 6 indicating diamagnetic transitions of $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ at 2.8 K and $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$ at 3.1 K. Very similar values of T_c from both resistivity and susceptibility data confirm that our single crystals are of very high quality. Large vortex pinning can be observed in the field cooled (FC-Meissner) data in shown in Fig. 6.

The characterisation of the superconducting transition using heat capacity measurements is shown in Fig. 7. The specific heat jump at the thermodynamic transition confirm the bulk superconductivity in both the compounds. The low temperature normal state specific heat can be well fitted with $\frac{C}{T} = \gamma + \beta T^2$, where γT represents the electronic contribution and βT^3 describe the lattice-phonon contributions to the specific heat in the normal state. Fitting the above formula give electronic specific heat coefficient $\gamma = 7.08 \frac{\text{mJ}}{\text{molK}^2}$ ($\gamma = 25.4 \frac{\text{mJ}}{\text{molK}^2}$) and the

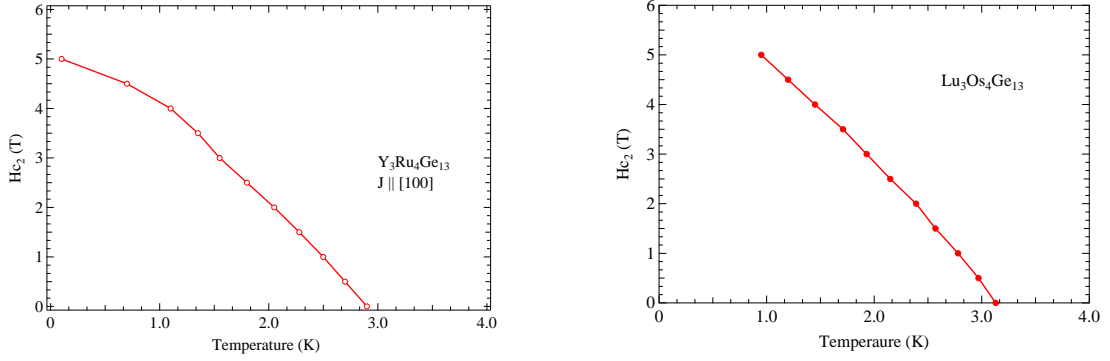


Figure 5. $\mu_0 H_{c2}$ as a function of temperature for $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ and $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$. The upper critical field $\mu_0 H_{c2}$ increases linearly as the temperature is lowered in the vicinity of the transition temperature T_c for both compounds, though the linear dependence is more prominent for $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$.

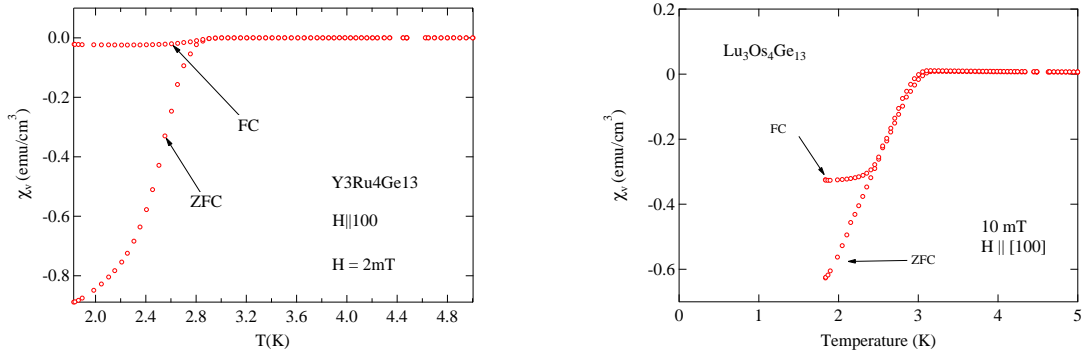


Figure 6. DC magnetic susceptibility as a function of temperature for magnetic field $H \parallel [100]$ direction for $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ and $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$. The superconducting transition temperatures determined from susceptibility measurements are in excellent agreement with the resistivity data reflecting the high quality of the single crystals. The ZFC and FC susceptibility data indicate significant amount of pinning of vortices in both the compounds.

phonon/lattice contributions $\beta = 3.52 \frac{mJ}{molK^4}$ ($\beta = 2.30 \frac{mJ}{molK^2}$) for $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ ($\text{Lu}_3\text{Os}_4\text{Ge}_{13}$). The ratio $\frac{\Delta C}{\gamma T_c}$ can be used to measure the strength of the electron-phonon coupling. The specific heat jump $\frac{\Delta C}{T_c}$ is $6.07 \frac{mJ}{molK^2}$ ($29 \frac{mJ}{molK^2}$), setting the value of $\frac{\Delta C}{\gamma T_c} = 0.85$ ($\frac{\Delta C}{\gamma T_c} = 1.15$) for $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$ ($\text{Lu}_3\text{Os}_4\text{Ge}_{13}$). These values are smaller than the weak-coupling limit of 1.43 for a conventional BCS superconductor, suggesting that these two compounds are moderately electron-phonon coupled superconductor.

The comparison among the normal and superconducting state parameters of the both compounds is shown in Table-1. We also notice from Table-1 that value of γ is larger in $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$ suggesting stronger electronic correlations in $\text{Lu}_3\text{Os}_4\text{Ge}_{13}$ as compared to electronic correlations in $\text{Y}_3\text{Ru}_4\text{Ge}_{13}$.

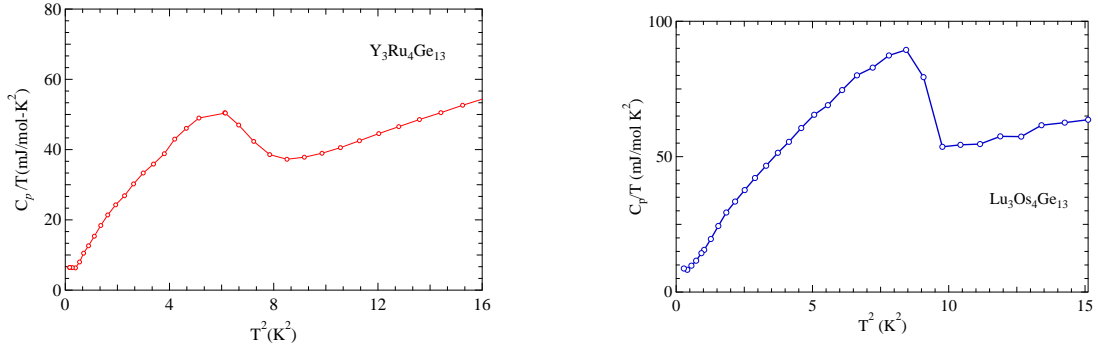


Figure 7. C/T vs T^2 data for $Y_3Ru_4Ge_{13}$ and $Lu_3Os_4Ge_{13}$ respectively. Large jump in heat capacity confirms bulk superconductivity in both the compounds.

Table 1. Normal and superconducting state parameters of $Y_3Ru_4Ge_{13}$ and $Lu_3Os_4Ge_{13}$

Parameters	$Y_3Ru_4Ge_{13}$	$Lu_3Os_4Ge_{13}$
T_c (K)	2.85	3.1
γ (mJ/mol K ²)	7.1	25.4
Θ_D (K)	223	257
$\Delta C_{el}/\gamma T_c$	0.85	1.15
$\mu_0 H_{c2}$ (T)	4.63	5.68
$\xi(0)_{GL}$ (Å)	80.4	78

4. Conclusion

We have grown single crystals and characterised the superconducting properties of two semi-metallic compounds $Y_3Ru_4Ge_{13}$ and $Lu_3Os_4Ge_{13}$. A bulk superconducting transition is confirmed and characterised through electrical transport, magnetisation and heat capacity measurements on the single crystals. The magnetic susceptibility measurements show large pinning of vortices in both the compounds. The analysis of the low temperature heat capacity data suggests that both these compounds are moderately electron-phonon coupled type-II superconductors.

References

- [1] Fleming R M, Ramirez A P, Rosseinsky M J, Murphy D W, Haddon R C, Zahurak S M and Makhija A V 1991 *Nature* **352** 787–788 URL <http://dx.doi.org/10.1038/352787a0>
- [2] Holczer K, Klein O, Huang S m, Kaner R B, Fu K j, Whetten R L and Diederich F 1991 *Science* **252** 1154–1157 URL <http://www.sciencemag.org/content/252/5009/1154>
- [3] Nagamatsu J, Nakagawa N, Muranaka T, Zenitani Y and Akimitsu J 2001 *Nature* **410** 63–64 ISSN 0028-0836 URL <http://dx.doi.org/10.1038/35065039>
- [4] Bardeen J, Cooper L N and Schrieffer J R 1957 *Phys. Rev.* **108**(5) 1175–1204 URL <http://link.aps.org/doi/10.1103/PhysRev.108.1175>
- [5] Migdal A 1958 *Soviet Physics JETP* **34**(7)
- [6] Eliashberg G 1960 *Soviet Physics JETP* **11**(3)
- [7] Carvajal 1993 *Physica B: Condensed Matter* **192** 55 – 69 ISSN 0921-4526 URL <http://www.sciencedirect.com/science/article/pii/092145269390108I>
- [8] Werthamer N R, Helfand E and Hohenberg P C 1966 *Phys. Rev.* **147**(1) 295–302 URL <http://link.aps.org/doi/10.1103/PhysRev.147.295>