

Graphyne on metallic surfaces: an improved graphene

P. Lazić¹ and Ž. Crljen^{1,2}

¹*Theoretical Physics Division, R. Bošković Institute, Zagreb, Croatia*

²*Faculty of Sciences, University of Split, Split, Croatia*

(Dated: March 3, 2022)

We showed how a structural modification of graphene, which gives a carbon allotrope graphyne, can induce an energy gap at the K point of the Brillouin zone. Upon adsorption on metallic surfaces, the same mechanism is responsible for the further modification of the energy gap which occurs via the charge transfer mechanism. We performed the calculation based on the density functional theory with the novel non-local vdW-DF correlation of the adsorption of graphyne on Cu(111), Ni(111) and Co(0001) surfaces and showed the dependence of the gap change on the charge transfer in the system. The binding of graphyne appears to be stronger than of graphene on the same surfaces.

PACS numbers: 71.15.Mb, 73.22.-f, 73.22.Pr, 73.61.Ph

Keywords: Density functional calculations; Graphyne; Graphene; Nanostructure

I. INTRODUCTION

Carbon nanostructures, and graphene in particular, are becoming unavoidable materials in the growing field of nanoelectronics. The experimental realization^{1,2} of a single layer graphene has boosted a tremendous interest in its physical properties. The most prominent feature of this two-dimensional material is its exceptional electronic structure with linear band dispersion in the vicinity of the Dirac point. Graphene shows a huge mobility of charge carriers, high conductivity of electrons and holes and a ballistic charge transport, what makes it a promising candidate for a number of applications in nanoscale electronic devices.

However, what seems to be a graphene strongest side is also its weakest point. Namely, graphene band structure has no band gap what makes it unusable in building some of basic electronic elements. Graphene field-effect-transistor, for example, cannot be turned off effectively due to the absence of a bandgap. Creating a bandgap in graphene is one of the most important research topics in graphene community since it may ultimately enable new applications in electronics, nanospintronics, and infrared nanophotonics. A number of approaches have been proposed or implemented to create a bandgap in graphene already, such as using graphene-substrate interaction³, lateral confinement⁴, uniaxial strain⁵ and breaking the inversion symmetry in bilayer graphene^{6,7}.

Here, an alternative approach is proposed, the use of another allotrope of carbon instead, a graphyne. Our presentation is organized as follows. The motivation for our studies is further supported in section II where the freestanding graphyne is discussed. In section III we report for the first time the graphyne adsorption on three representative metallic surfaces showing the features of binding of graphyne on Co(0001), Ni(111) and Cu(111). Finally, in section IV we give conclusions and perspectives of graphyne.

II. FREE STANDING GRAPHYNE

Graphyne, shown in Fig.1(b), is a result of a structural change in the two dimensional graphene plane which opens a gap at the K point, i.e. lifts the degeneracy caused by the symmetry of the hexagonal structure. It can be easily understood by making a comparison with the one-dimensional linear polymer chain consisting of strongly interacting coplanar p_z orbitals, each of which contributes one electron to the resultant continuous π -electron system. The chain should behave essentially as a one-dimensional metal with a half-filled conduction band and show Peierls distortion and a metal-insulator transition. By introducing a bond alternation (alternating single long and double short bonds) and consequently doubling the lattice constant such a chain can efficiently lower its energy. This reduces the extent of electronic

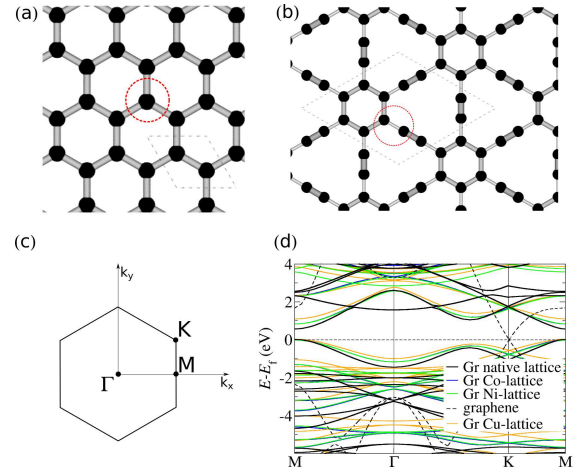


FIG. 1. (Color online). Structure and energy bands. (a) Graphene, (b) Graphyne, (c) Reciprocal lattice, (d) Energy bands for different lattice constant (see text). Circles in (a) and (b) denote the substitution in graphene that creates graphyne.

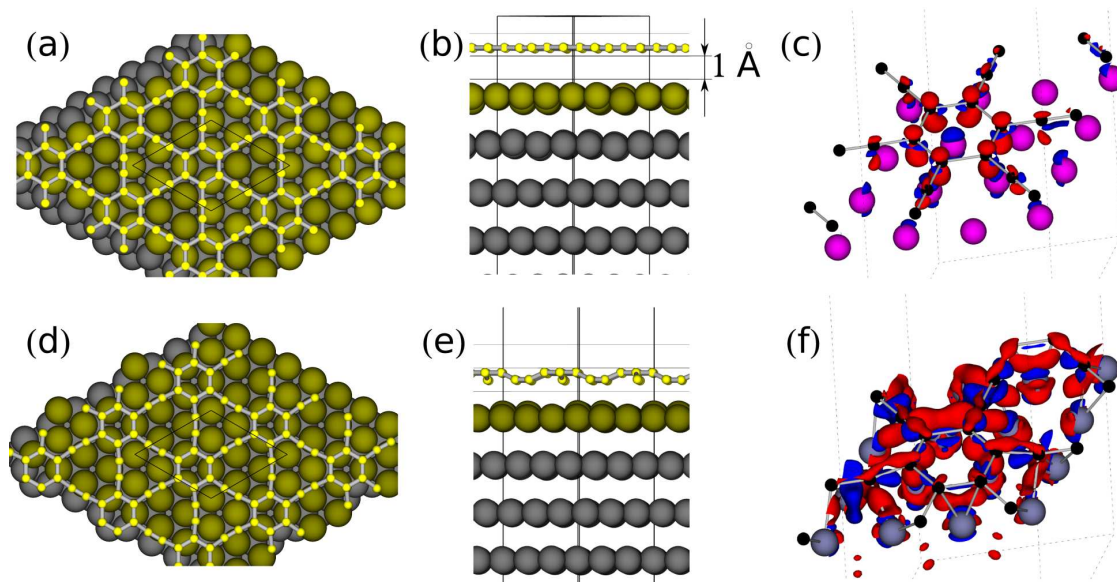


FIG. 2. (Color online). Graphyne adsorbed on Cu(111) in top row and Ni(111) in bottom row, (a) and (d) top view, (b) and (e) side view, (c) and (f) charge rearrangement (isosurface of $0.04 \text{ e}/\text{\AA}^3$ plotted, depletion in blue, accumulation in red), angle view, only the top layer of surface atoms are plotted.

delocalization that can take place along the backbone but opens an energy gap in the electronic structure of the polymer. In a graphene each carbon atom, too, has one out of plane p_z orbital with one electron. The peculiarity of graphene, dictated by the backbone hexagonal structure, is that each atom is surrounded with three equivalent neighbors and cannot make such a transition with bond alternation. The periodic crystal potential is such that it causes a band splitting at the Γ and M symmetry points but degeneracy (zero bandgap) at the K points of the first Brillouin zone making graphene a zero bandgap semiconductor as shown in Fig.1(d).

One way to lift that degeneracy is then to introduce an inequivalent neighbor to the hexagonal atom. In a π conjugated system this is easy to achieve by forcing a single bonding to the neighboring atom, as discussed for the case of a linear polymer. In Fig.1(b) it is achieved by introducing an acetylene in the hexagonal structure. The p_z orbitals of the acetylene atoms are involved in a triple bond and acetylene atom can only form a single bond with the hexagonal atom. The consequence of the formation of a single bond is thus an inequivalent neighbor, the change of the periodicity of the system and lifting of the degeneracy at the K points. The resulting graphyne has a high electron density at the Fermi level like the graphene, but most importantly it has a well defined direct bandgap of 1.1 eV at the M point of the Brillouin zone as displayed in Fig.1(d).

Graphyne and similar non-natural carbon allotropes can be assumed to be chemically stable⁸, in spite of having a triple bond in their structure. Finite building blocks have been synthesized^{9,10} and steps towards a preparation have been developed^{9,11}. In fact, a graphdiyne, an

allotrope with diacetylenic linking chain, has already been synthesized^{12,13} but only as a multi-layer film and a nanowire with the diameter of 30 nm. There is no report of a free standing or supported monolayer material.

The calculation of the band structure of single layer graphyne and graphdiyne have been reported^{14–17}, but to the best of our knowledge the adsorbed monolayer on any surface has not yet been investigated.

III. GRAPHYNE ON METALLIC SURFACES

Support of surfaces and coupling to metal contacts play a fundamental role in technological applications and may bring a new property resulting in novel devices. In spintronics a hybrid structure of graphene and ferromagnetic surfaces, for example, brings a promise for a spin-filtering device¹⁸. In that respect graphyne as a semiconductor with different charge distribution locally is a new element, possibly a new building block in nanoelectronics.

The change it brings can be best verified investigating its adsorption on transition metal surfaces. We choose Cu(111), Ni(111) and Co(0001) surfaces, studied a lot in the context of graphene adsorption^{19–21}, as they provide the possibility for physisorption and chemisorption due to a hybridization of carbon orbitals with metallic states. Graphyne is expected to have a large polarizability²², which together with the polarizability of metallic surfaces may result in a significant van der Waals interaction. To calculate the structure and electronic properties we use the state of the art approach of density functional theory (DFT) as implemented in the VASP 5.1. computer code²³ and vdW-DF correlation^{24,25} with the

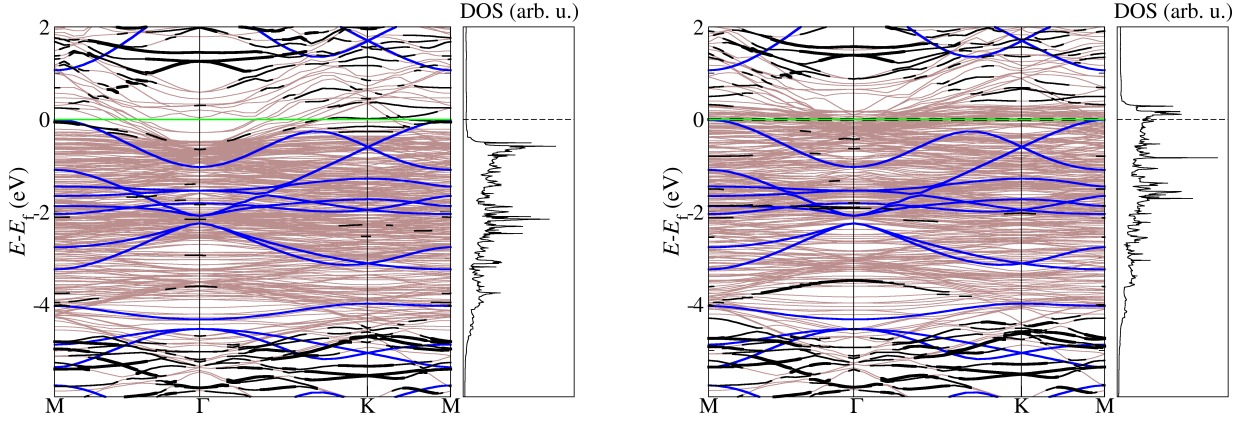


FIG. 4. (Color online). Energy bands of graphyne/Ni(111) and density of states of clean Ni for majority (left) and minority spin (right). The thickness of black lines show projection weight on carbon atoms. Blue lines - free standing graphyne.

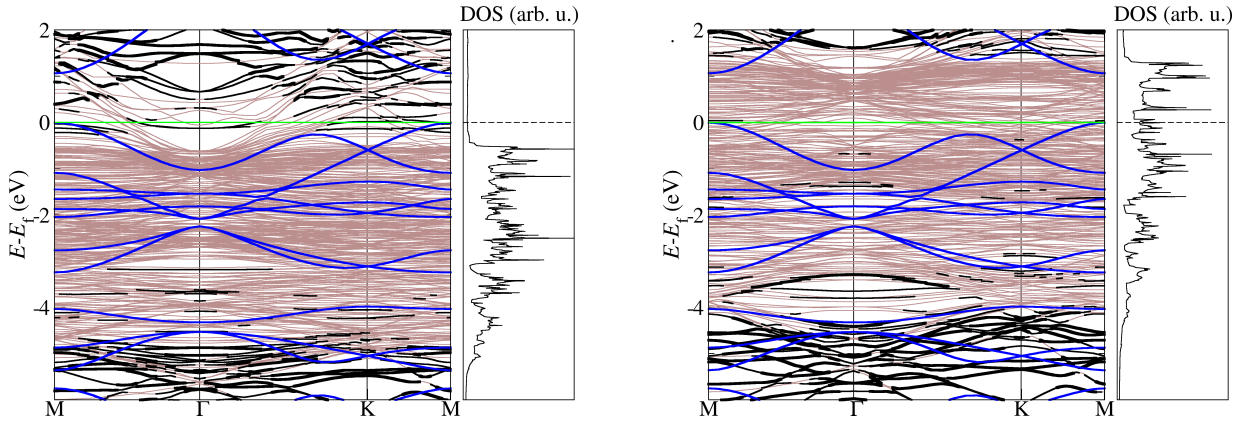


FIG. 5. (Color online). Energy bands of graphyne/Co(0001) and density of states of clean Co for majority (left) and minority spin (right). The thickness of black lines show projection weight on carbon atoms. Blue lines - free standing graphyne.

is particularly strong in the range of the metal d -band energy region, where the graphyne states are virtually dispersed over the band. Comparing the thicker band lines with the lines of free standing graphyne we conclude on relative downshift of graphyne's levels and crossing at Fermi level which renders graphyne metallic rather than semiconducting.

On Ni(111) surface due to its ferromagnetic property different electronic structures are induced for majority and minority spin states as seen in Fig.4. The overall downshift of graphyne's levels for both spins appears, similar to the Cu(111) surface. Due to the fact that the d -band straddles the Fermi level the level repulsion of hybridized and unoccupied graphyne states gives no crossing at the Fermi level and the majority spin states around the Fermi level are mostly metallic d -states. There are pronounced gaps at K and M points of the Brillouin zone. On the ferromagnetic Co(0001) surface, shown in Fig.5, the band structures are very similar to those on Ni(111) surface taking the fact that the d -band of cobalt is wider.

One notices that the length of a triple carbon bond, given in Table I, is longer in adsorbed than in free stand-

ing graphyne ($d = 1.225 \text{ \AA}$) and increasing from 1.309 \AA for Cu to 1.383 \AA for Ni and 1.401 \AA for Co surfaces. The increase is accompanied with the accumulation of charges between acetylenic and hexagonal carbon atom as mentioned before. According to our discussion in section II, it implies the change of the bonding with hexagonal carbon tending to a more symmetric bonding between hexagonal atoms and its neighbors and consequently should be followed by the reduction of energy gaps at the K points. Indeed, the inspection of the structure of energy bands in Fig. 3., 4. and 5. supports the conclusion. The structure is partly blurred by the hybridization induced rather strong redistribution of energy levels in the vicinity of Fermi level, but apparently the energy gap is the most reduced at the K points and the reduction of the gap is increasing from Cu(111) to Ni(111) and Co(0001) surfaces.

IV. CONCLUSIONS

We have shown how a structural modification of graphene induces an energy gap and that the gap of the new allotrope graphyne can be modulated via the charge transfer upon adsorption on different metallic surfaces. As a semiconductor with the density of states comparable to that of graphene, a graphyne can become a valuable material in the field of nanoelectronics. We have calculated the adsorption of graphyne on Cu, Ni and Co surfaces using a DFT method with a selfconsistent implementation of vdW-DF functional which explicitly in-

cludes nonlocal correlations. The binding of graphyne appears to be several times stronger than of graphene on the same surfaces and a way above typical thermal fluctuations at room temperature ($\sim 25\text{meV}$), what makes a graphyne less prone to desorption. In conclusion our results show that a graphyne can complement and even overcome the graphene as a building block in future nanoelectronic components.

ACKNOWLEDGMENTS

This work was supported in part by the Croatian Ministry of Science under Contract No. 098-0352828-3118.

-
- ¹ K. S. Novoselov, A. K. Geim, S. V. Morozov, D. Jiang, Y. Zhang, S. V. Dubonos, I. V. Grigorieva, and A. A. Firsov, *Science* **306**, 666 (2004).
 - ² K. S. Novoselov, A. K. Geim, S. V. Morozov, D. Jiang, M. I. Katsnelson, I. V. Grigorieva, S. V. Dubonos, and A. A. Firsov, *Nature* **438**, 197 (2005).
 - ³ S. Y. Zhou, G. H. Gweon, A. V. Fedorov, P. N. First, W. A. de Heer, D. H. Lee, F. Guinea, A. H. Castro Neto, A. Lanzara, *Nature Mat.* **6**, 770 (2007).
 - ⁴ Y. W. Son, M. L. Cohen, and S. G. Louie, *Phys. Rev. Lett.* **97**, 216803 (2006).
 - ⁵ V. M. Pereira, A. H. Castro Neto, N. M. R. Peres, *Phys. Rev. B* **80**, 045401 (2009).
 - ⁶ F. Xia, D. B. Farmer, Y. Lin and P. Avouris, *Nano Letters* **10**, 715 (2010).
 - ⁷ Y. Zhang, T. Tang, C. Girit, Z. Hao, M. C. Martin, A. Zettl, M. F. Crommie, Y. R. Shen, F. Wang, *Nature* **459**, 820 (2009).
 - ⁸ G. Luo, X. Qian, H. Liu, R. Qin, J. Zhou, L. Li, Z. Gao, E. Wang, W.-N. Mei, J. Lu, Y. Li, and S. Nagase, *Phys. Rev. B* **84**, 075439 (2011).
 - ⁹ M. M. Haley, *Pure Appl. Chem.* **80**, 519 (2008).
 - ¹⁰ F. Diederich and M. Kivala, *Adv. Mater.* **22**, 803 (2010).
 - ¹¹ M. Gholami, F. Melin, R. McDonald, M. J. Ferguson, L. Echegoyen, and R. R. Tykwinski, *Angew. Chem., Int. Ed.* **46**, 9081 (2007).
 - ¹² G. X. Li, Y. L. Li, H. B. Liu, Y. B. Guo, Y. J. Li, and D. B. Zhu, *Chem. Comm.* **46**, 3256 (2010).
 - ¹³ X. Qian, Z. Ning, L. Yuliang, H. Liu, C. Ouyang, Q. Chen and L. Yongjun, *Dalton Trans.*, **41**, 730 (2012).
 - ¹⁴ V. R. Coluci, S. F. Braga, S. B. Legoas, D. S. Galvao, and R. H. Baughman, *Phys. Rev. B* **68**, 035430 (2003).
 - ¹⁵ N. Narita, S. Nagai, S. Suzuki, and K. Nakao, *Phys. Rev. B* **58**, 11 009 (1998).
 - ¹⁶ M. Long, L. Tang, D. Wang, Y. Li, and Z. Shuai, *ACS Nano* **5**, 2593 (2011).
 - ¹⁷ L. D. Pan, L. Z. Zhang, B. Q. Song, S. X. Du, and H.-J. Gao, *Appl. Phys. Lett.* **98**, 173102 (2011).
 - ¹⁸ V. M. Karpan, G. Giovannetti, P. A. Khomyakov, M. Taliana, A. A. Starikov, M. Zwierzycki, J. van den Brink, G. Brocks, and P. J. Kelly, *Phys. Rev. Lett.* **99**, 176602 (2007).
 - ¹⁹ M. Vanin, J.J. Mortensen, A.K. Kelkkanen, J.M. Garcia-Lastra, K.S. Thygesen and K.W. Jacobsen, *Phys. Rev. B* **81**, 081408 (2010).
 - ²⁰ C. Busse, P. Lazić, R. Djemour, J. Coraux, T. Gerber, N. Atodiresei, V. Caciuc, R. Brako, A. T. N'Diaye, S. Blügel, J. Zegenhagen, and T. Michely, *Phys. Rev. Lett.* **107**, 036101 (2011).
 - ²¹ F. Mittendorfer, A. Garhofer, J. Redinger, J. Klimeš, J. Harl, and G. Kresse, *Phys. Rev. B* **84** 201401(R), (2011).
 - ²² Graphene is known to have large polarizability. The conductivity of graphdiyne is $2.516 \times 10^{-4} \text{Sm}^{-1}$, and its large polarizability has been reported in Ref.8.
 - ²³ G. Kresse and J. Furthmüller, *Phys. Rev. B* **54** 11169, (1996).
 - ²⁴ M. Dion, H. Rydberg, E. Schröder, D. C. Langreth, and B. I. Lundqvist, *Phys. Rev. Lett.* **95** 109902, (2005).
 - ²⁵ M. Dion, H. Rydberg, E. Schröder, D. C. Langreth, and B. I. Lundqvist, *Phys. Rev. Lett.* **92** 246401, (2004).
 - ²⁶ J. Klimeš, D. R. Bowler, and A. Michaelides, *J. Phys.: Condens. Matter*, **22**, 022201 (2010).
 - ²⁷ J. Klimeš, D. R. Bowler, and A. Michaelides, *Phys. Rev. B* **83**, 195131 (2011).
 - ²⁸ G. Román-Pérez, and J. M. Soler, *Phys. Rev. Lett.* **103**, 096102, (2009).
 - ²⁹ Adjusting the lattice constant of adsorbate or substrate is a common practice in calculation of graphene adsorption. It significantly reduces the computational cost, but for some substrates the binding may depend strongly on the choice, see Ref. 31. In reality graphene compensates over large distances with a moire pattern. Graphyne is more prone to chemisorption and large distance rearrangements are not probable.
 - ³⁰ T. Olsen, and K. S. Thygesen, *Phys. Rev. B* **87**, 075111 (2013).
 - ³¹ T. Olsen, J. Yan, J. J. Mortensen, and K. S. Thygesen, *Phys. Rev. Lett.* **107**, 156401 (2011).
 - ³² G. M. Sipahi, I. Žutić, N. Atodiresei, R. K. Kawakami, and P. Lazić, *J. Phys.: Condens. Matter*, **26**, 104204 (2014)