

Probing the Hotspot Interaction Length in NbN Nanowire Superconducting Single Photon Detectors

J.J. Renema,* Q. Wang, M.P. van Exter, and M.J.A. de Dood
Leiden Institute of Physics, Leiden University, Niels Bohrweg 2, 2333 CA Leiden, Netherlands

R. Gaudio* and A. Fiore
*COBRA Research Institute, Eindhoven University of Technology,
P.O. Box 513, 5600 MB Eindhoven, Netherlands*

We measure the maximal distance at which two absorbed photons can jointly trigger a detection event in NbN nanowire superconducting single photon detector (SSPD) microbridges by comparing the one-photon and two-photon efficiency of bridges of different overall lengths, from 0 to 400 nm. We find a length of 23 ± 2 nm. This value is in good agreement with the size of the quasiparticle cloud at the time of the detection event.

Nanowire superconducting single photon detectors (SSPDs) [1] are a crucial technology for a variety of applications [2]. These devices consist of a thin superconducting film which detects photons when biased to a significant fraction of its critical current. Although details of the microscopic mechanism are still in dispute [3], the present understanding of this process in NbN SSPDs is as follows [4–14]: after the absorption of a photon, a cloud of quasiparticles is created, which is known as a hotspot. This cloud diffuses, spreading out over some area of the wire. This causes the redistribution of bias current, which triggers a vortex unbinding from the edge of the wire, if the applied bias current is such that the current for vortex entry is exceeded. The transition of a vortex across the wire creates a normal-state region, which grows under the influence of Joule heating from the bias current, leading to a measureable voltage pulse and a detection event [15].

Recently, applications of these detectors have been demonstrated or proposed which rely on the ability of such devices to operate as multiphoton detectors, such as multiphoton subwavelength imaging [16], ultrasensitive higher order autocorrelation [17] and near-field multiphoton sensing [18]. These applications make use of the fact that when biased at lower currents than required for single-photon detection, the detector responds only when several photons are absorbed simultaneously. This multiphoton response has moreover proven to be of great significance in investigating the question of the working mechanism of such devices.

For these multiphoton applications to work, the two photons must be absorbed within some given distance of each other, which we will refer to as the *hotspot interaction length* s . This length determines the efficiency of an SSPD in the multiphoton regime: photons which are absorbed far away from each other along the wire will not be able to jointly cause a detection event, resulting in a reduction of the two-photon detection probability.

In this work, we use this effect to measure the hotspot interaction length. Our experiment is based on comparing

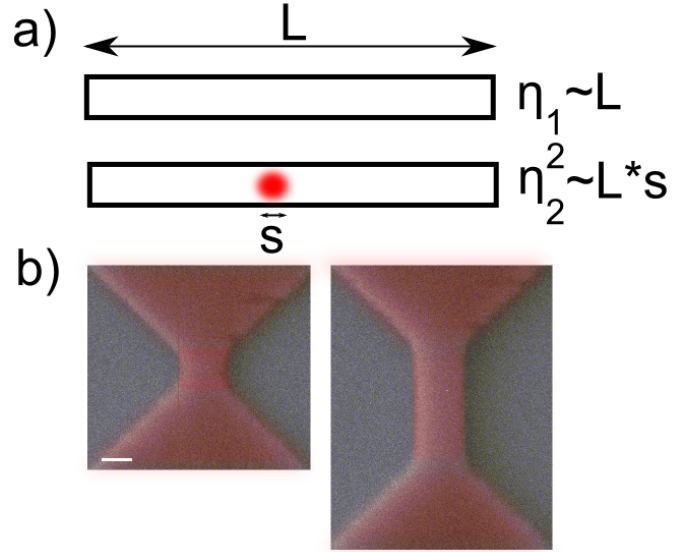


Figure 1. *a)* Sketch of the experiment. Top panel: a nanowire of length L is illuminated uniformly, and the current of the nanowire is set to be in the single-photon regime. Photon absorption at any point in the wire is sufficient to cause a detection event. In the bottom panel, the detector is in the two-photon regime, and a detection is observed only if the second photon is absorbed in the region (red spot) where an excess quasiparticle concentration has been created by the first photon. *b)* False color SEM images of two nanowires, of $L = 100$ nm and $L = 400$ nm, respectively.

the efficiency in the one-photon and two-photon regime of a series of uniformly illuminated nanowires of different lengths. We rely on quantum detector tomography [19] (QDT) to find the bias currents at which the one and two-photon regimes occur. We experimentally find a hotspot interaction length of $s = 23 \pm 2$ nm. We find that the tapers leading into our nanowires are photodetecting over a length of approximately 35 ± 6 nm on each side.

We interpret these results in terms of the diffusion-based vortex crossing model of the detection event. We show that the measured hotspot interaction length cor-

responds to the computed size of the quasiparticle cloud at the moment of a detection event, which demonstrates the agreement between our experiment and our numerical model. Finally, we discuss the implications of these results for multiphoton-based SSPD applications.

The detectors used in this experiment were patterned from a single film (5 nm NbN on GaAs) to ensure that the properties of the wires are as similar as possible. The film is deposited at a temperature of 400 °C, which was found to give the optimal critical current for NbN on GaAs, and a film critical temperature of 9.6 K. The detectors were patterned using conventional e-beam lithography and reactive-ion etching in an SF₆ / Ar plasma. We fabricated 16 detectors of each length, with lengths of $L = 0, 100, 200$ and 400 nm. The width of all detectors was nominally identical, at 150 nm.

For this experiment, it is crucial that the entire area of the detector is active. It is known that the critical current of SSPDs shows variations[20]; NbN nanowires are inhomogeneous on a length scale below 100 nm due to some sort of defects or intrinsic inhomogeneities, which manifest themselves as a reduced value of the critical current [21]. To avoid comparing dissimilar detectors, we measured the critical current of our devices and selected one for each length with critical currents between 27.4 and $27.9 \mu\text{A}$. This value is consistent with earlier samples [4, 16, 21, 22], including bridge samples (nanodetectors) which have a very low probability of containing a defect.

To characterize these detectors optically, we perform QDT [19, 22–24]. QDT relies on illuminating the detector with a set of known probe states. By measuring the count rate as a function of bias current and combining this with knowledge of the photon number distribution in each probe state, we can measure the probability of a detection event given n incident photons. Our modified tomography protocol [22] makes use of model selection to derive from the observed counting statistics both a linear efficiency η , and a series of nonlinear parameters $\{p_n\}$, which correspond to the detection probability of n photons.

We used a Ti:Sapphire laser with a wavelength of $\lambda = 800$ nm to perform detector tomography. This laser is well suited for this experiment, because it has a pulse duration of approximately 100 fs. In this way we avoid introducing the temporal response of the device into the problem: our pulse duration is sufficiently short to act as a delta-like excitation compared to all relevant timescales compared to the lifetime of an excitation in an SSPD of a few tens of ps [17]. The laser is attenuated by a $\lambda/2$ plate between two polarizers. The second polarizer was set so as to maximize the count rate in the device, which aligns the polarization of the light with the direction of current flow, resulting in almost uniform illumination across the wire [13]. The spot size was chosen to be much larger than the length of the wire, to ensure uniform illumination along the wire length.

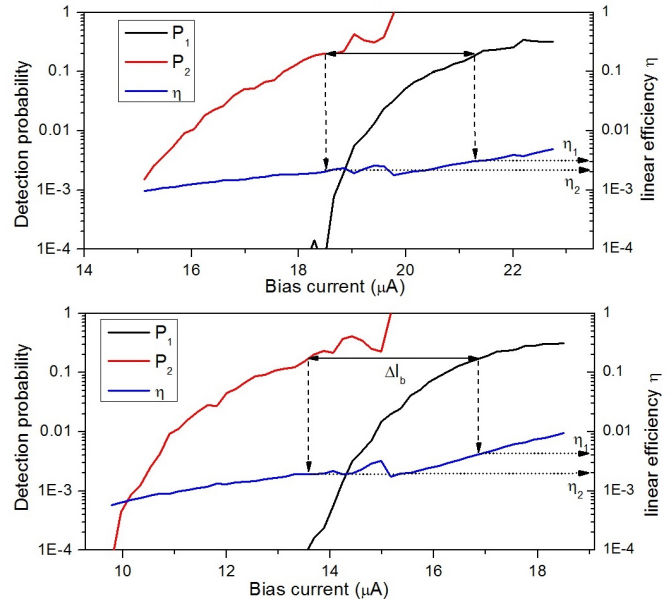


Figure 2. Full tomographic characterization of the $L = 0$ nm sample (*top*) and the $L = 400$ nm sample (*bottom*). The black and red lines show the nonlinear detection probabilities for single photons (p_1) and photon pairs (p_2), respectively. The blue line shows the linear efficiency η . The dashed lines show how we obtain the ratio of efficiencies in the one- and two-photon regime η_1/η_2 .

Figure 2 shows two typical experimental results, for the $L = 0$ and $L = 400$ nm wires. The results on these two devices are almost identical, apart from the linear efficiency parameter η , which falls off faster for the longer wire. We conclude that the reduced detection probability in the two-photon regime manifests itself as a reduction in the linear efficiency. This is to be expected, considering that one can interpret the reduction of the two-photon detection efficiency geometrically: one of the two photons sets the area into which the other has to be absorbed (see Figure 1). We therefore conclude that the conjectured reduction in efficiency occurs and manifests itself (in our parametrization) as a reduction of η .

To extract the hotspot interaction length from these measurements, we consider the detection efficiencies in both photon regimes in detail. For the one-photon regime, we expect $\eta_1 = CL$, where C denotes the absorption probability per unit length of wire. For the two-photon regime, we expect $\eta_2^2 = C^2 Ls$, representing the fact that the second photon has to be absorbed within a distance s from the first[25]. Therefore, we find:

$$L/s = (\eta_1/\eta_2)^2. \quad (1)$$

We find that the change in η is gradual with decreasing bias current. Therefore, we compare equivalent points in the two photon regimes. We start by finding the value of ΔI_b such that $p_2(I_b) = p_1(I_b + \Delta I_b)$, as shown in

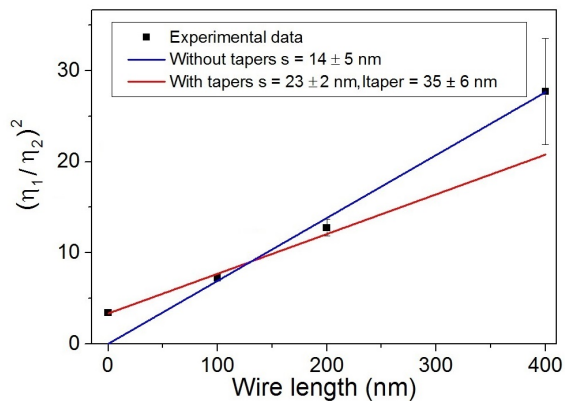


Figure 3. Ratio of linear efficiencies η_1/η_2 for the one and two-photon regimes, derived from tomography as shown in the previous figure. The blue line shows a fit which does not take into account photodetection events in the tapers leading to the wire. The straight lines are fits to the data that either neglect (blue line) or include (red line) an additional taper. From that fit, we find $s = 23$ nm, $L_{\text{taper}} = 36$ nm.

Fig 2. We then take the ratio of efficiencies $\eta_1/\eta_2 = \eta(I_b + \Delta I_b)/\eta(I_b)$. We find that for currents where $p_{1,2} \gtrsim 0.15$, the resulting ratio is independent of bias current. This enables us to associate one value of η_1/η_2 with each device.

Figure 3 shows the resulting values of η_1/η_2 for $L = 0 - 400$ nm, from which we extract s . The point at $L = 0$ is of note: for this nanobridge, we find a value of $\eta_1/\eta_2 = 1.6$. This is consistent with our earlier measurements[22] but not with our model, which would unphysically predict $\eta_2 = \eta_1 = 0$, as it neglects the possibility that photons absorbed close to the end of the wire can trigger a detection. We model this effect by substituting $L_{\text{eff}} = L + 2L_{\text{taper}}$, into eq. 1. Using this modified wire length, we find values of $s_{hs} = 23 \pm 2$ nm and $L_{\text{taper}} = 35 \pm 6$ nm. The observed value of L_{taper} is in reasonable agreement with earlier estimates of the active area of such nanobridges, which found $L_{\text{taper}} \approx 50$ nm[16, 22].

As a sanity check, we must consider that this experiment relies on the assumption that the properties of the superconducting wire are identical at both currents. To evaluate whether this is the case, we consider the superconducting energy gap and the available number of superconducting electrons. Both of these depend on the applied bias current [26, 27]. We find that the density of superconducting electrons varies by 4% over the range of currents in which we performed this experiment, and that the superconducting gap varies by 1.4%. Given that these values are much smaller than the margin of error of our experiment, this justifies the assumption of constant superconducting properties.

It should be noted that the efficiency changes smoothly across the one and two-photon regime. In the simplest

interpretation, one would expect the linear efficiency to jump from η_1 to η_2 when the current is decreased from the one-photon regime to the two-photon regime. However, as we have shown previously [13], different points along the cross-sections of the wire become photodetecting at different bias currents. We conjecture that this effect leads to the smearing-out of the transition between the one- and two-photon regimes.

We note that the length scale which we have found is much smaller than the width of the wire. We have assumed that photons which are absorbed at the same cross-section of the wire are equivalent to a $d = 0$ detection event, i.e. to a photon with double the energy. We have observed previously[4] that a single photon of energy $2E$ has the same detection probability as two photons of energy E . Our assumption is justified from theory: across the wire, current continuity enforces an almost instantaneous[7], long-range interaction between the two hotspots.

At this point, we have not attached any interpretation in terms of detector physics to our observed length scale. To answer this question, we perform a series of numerical simulations in COMSOL of current continuity and quasiparticle diffusion, similar to those reported on refs [7, 13]. We have made three simplifications compared to these references. First, we have approximated the process of hot electron to QP conversion as an exponentially decaying source of QP located at the photon absorption site. Second, we have ignored the nonlinear interaction between the condensate velocity and the number of quasiparticles, which amounts to taking the limit of low quasiparticle densities, and equivalently, low photon energies. This later approximation is somewhat justified by the fact that we are in the regime where the energy-current relation is linear [4]. Finally, we only consider photon absorption events in the center of the wire.

Figure 4 shows that the length scale which we have measured in our experiment is that of quasiparticle diffusion at the time of the detection event. We plot the maximum value of the current along the edge of the wire (in units of the applied bias current), which is the quantity that is known to determine whether a detection event occurs [7], as a function of photon separation d . By finding where and when the current density along the wire is maximal, we can identify the position and time of the photodetection event. In the four insets, we plot the distribution of quasiparticles at the timestep when the maximum edge current is achieved and we indicate the position where this happens with a double red arrow. The edge current is roughly constant up to $d_{hs} \approx 20$ nm, and then starts to roll off. The point where this rolloff happens occurs when the quasiparticle clouds no longer significantly overlap. We therefore identify the observed hotspot interaction length with the size of the QP cloud. This result enables us to convert the observed length scale into a timescale, since the diffusion constant for quasipar-

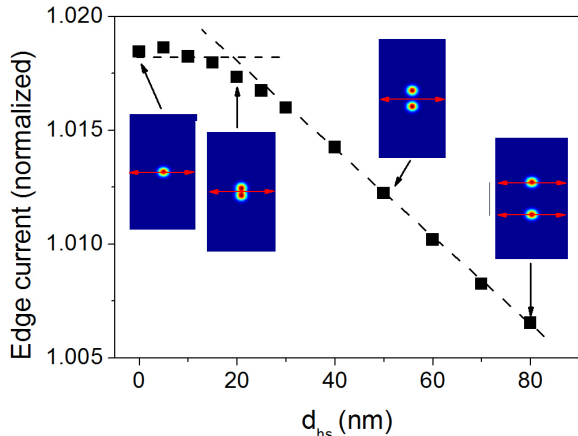


Figure 4. Simulated edge current as a function of photon absorption separation, normalized to the applied bias current. The dashed lines are guides to the eye. The insets show the quasiparticle distribution at the moment of maximum edge current, which we associate with the detection event. The arrows indicate the point where the edge current is maximal.

ticles is known[7] to be $D = 0.4 - 0.6 \text{ cm}^2/\text{s}$. Using the relation $s = \sqrt{Dt}$, we find a value of $t_{det} = 2.7 \pm 0.6 \text{ ps}$. This is in good agreement with the value predicted in ref [7]. At a range of $d = 20 - 60 \text{ nm}$, the two absorbed photons still interact through the current continuity condition. Essentially, the current crowding caused by the first QP cloud has not healed before the current encounters the second QP cloud. However, this length scale is not visible in Fig 4: the edge current decreases smoothly from $d \approx 20 \text{ nm}$ onwards. We therefore conclude that it is the length scale set by the QP cloud and not by current crowding that determines the hotspot interaction length.

We discuss the implications of this result for the use of SSPDs in multiphoton sensing. Increasing the length of the wire will increase the probability of multiphoton events, but each $\sim 20 \text{ nm}$ long segment of the wire will essentially act as a separate multiphoton detector. This means that the efficiency of such devices will be low: for a typical $100 \mu\text{m}$ long SSPD, the overall detection probability in the two-photon regime would be 10^{-4} lower than in the single-photon regime, and correspondingly for higher photon regimes. This demonstrates that the only way to obtain highly efficient multiphoton detection in SSPDs is to go to far-subwavelength focussing, perhaps by the use of nano-antennas.

Recently, a similar experiment was performed on WSi [28]. In this experiment, it was found that the experimental data on two-photon pump-probe measurements [29, 30] could be well explained by a static hotspot of $s > 100 \text{ nm}$. It is possible that self-confinement of the hotspot plays a larger role in WSi than in NbN due to the larger fraction of Cooper pairs which are destroyed in the former material. This would be the first evidence

of a qualitative difference in the detection mechanism between NbN and WSi SSPDs.

Finally, we propose an application for the present work. If the experiment presented here is performed on wires which are longer than the size of the impinging optical beam, the diameter of the optical beam takes the role of the wire length L . If the overall shape of the beam is known (e.g. that it is Gaussian), this enables measurement of the beam diameter with an accuracy far below the diffraction limit.

In conclusion, we have observed that the size of an excitation in NbN SSPDs is approximately 23 nm . We have shown that this number can be interpreted as the size of the quasiparticle cloud at the moment of detection. This observation is consistent with the predictions of the diffusion-based vortex crossing model.

We thank Eduard Driessen, Alexander Kozorezov, Denis Vodolazov, Martin Stevens, Francesco Marsili and Andreas Engel for useful discussions. This work is part of the research programme of the Foundation for Fundamental Research on Matter (FOM), which is financially supported by the Netherlands Organisation for Scientific Research (NWO) and is also supported by NanoNextNL, a micro- and nanotechnology program of the Dutch Ministry of Economic Affairs, Agriculture and Innovation (EL&I) and 130 partners. JJR acknowledges support of Dirk Bouwmeester's NWO Spinoza award.

* These authors contributed equally to this work

- [1] G. N. Goltsman, O. Okunev, G. Chulkova, A. Lipatov, A. Semenov, K. Smirnov, B. Voronov, A. Dzardanov, C. Williams, and Roman Sobolewski. Picosecond superconducting single-photon optical detector. *Appl. Phys. Lett.*, 79(6):705, 2001.
- [2] C.M. Natarajan, M.G. Tanner, and R. Hadfield. Superconducting nanowire single-photon detectors: physics and applications. *Supercond. Sci. Technol.*, 25(6):063001, 2012.
- [3] Andreas Engel, Jelmer Renema, Konstantin Ilin, and Alexander Semenov. Detection mechanism of superconducting nanowire single-photon detectors. *Supercond. Sci. Technol.*, 28 11, 2015.
- [4] J. J. Renema, R. Gaudio, Q. Wang, Z. Zhou, A. Gaggero, F. Mattioli, R. Leoni, D. Sahin, M. J. A. de Dood, A. Fiore, and M. P. van Exter. Experimental test of theories of the detection mechanism in a nanowire superconducting single photon detector. *Phys. Rev. Lett.*, 112:117604, 2014.
- [5] D. Y. Vodolazov. Saddle point states in two-dimensional superconducting films biased near the depairing current. *Phys. Rev. B.*, 85:174507, 2012.
- [6] A. N. Zotova and D. Y. Vodolazov. Photon detection by current-carrying superconducting film: A time-dependent Ginzburg-Landau approach. *Phys. Rev. B*, 85:024509, 2012.
- [7] Andreas Engel and Andreas Schilling. Numerical analysis of detection-mechanism models of superconducting

- nanowire single-photon detector. *J. Appl. Phys.*, 114(21), 2013.
- [8] J. J. Renema, G. Frucci, Z. Zhou, F. Mattioli, A. Gaggero, R. Leoni, M. J. A. de Dood, A. Fiore, and M. P. van Exter. Universal response curve for nanowire superconducting single-photon detectors. *Phys. Rev. B*, 87:174526, 2013.
- [9] R. Lusche, A. Semenov, K. Il'in, M. Siegel, Y. Korneeva, A. Trifonov, A. Korneev, G. Goltsman, D. Vodolazov, and H.-W. Hübers. Effect of the wire width on the intrinsic detection efficiency of superconducting-nanowire single-photon detectors. *J. Appl. Phys.*, 116(4), 2014.
- [10] A.N. Zotova and D.Y. Vodolazov. Intrinsic detection efficiency of superconducting single photon detector in the modified hot spot model. *Supercond. Sci. Technol.*, 27:125001, 2014.
- [11] D. Y. Vodolazov. Current dependence of the red boundary of superconducting single-photon detectors in the modified hot-spot model. *Phys. Rev. B*, 90:054515, 2014.
- [12] Andreas Engel, Julia Lonsky, Xiaofu Zhang, and Andreas Schilling. Detection mechanism in SNSPD: Numerical results of a conceptually simple, yet powerful detection model. *IEEE Trans. Appl. Supercond.*, 25:2200407, 2015.
- [13] J. J. Renema, Q. Wang, R. Gaudio, I Komen, K. op 't Hoog, D. Sahin, A. Schilling, M. P. van Exter, A. Fiore, A. Engel, and M. J. A de Dood. Position-dependent local detection efficiency in a nanowire superconducting single-photon detector. *Nano Lett.* 15:4541, 2015.
- [14] A. G. Kozorezov, C. Lambert, F. Marsili, M. J. Stevens, V. B. Verma, J. A. Stern, R. Horansky, S. Dyer, S. Duff, D. P. Pappas, A. Lita, M. D. Shaw, R. P. Mirin, and Sae Woo Nam. Quasiparticle recombination in hotspots in superconducting current-carrying nanowires. *Phys. Rev. B*, 92:064504, Aug 2015.
- [15] Andrew J. Kerman, Eric A. Dauler, William E. Keicher, Joel K. W. Yang, Karl K. Berggren, G. Goltsman, and B. Voronov. Kinetic-inductance-limited reset time of superconducting nanowire photon counters. *Appl. Phys. Lett.*, 88(11):111116, 2006.
- [16] David Bitauld, Francesco Marsili, Alessandro Gaggero, Francesco Mattioli, Roberto Leoni, Saeedeh Jahanmirinejad, Francis Lévy, and Andrea Fiore. Nanoscale optical detector with single-photon and multiphoton sensitivity. *Nano Lett.*, 10(8):2977–81, 2010.
- [17] Zili Zhou, Giulia Frucci, Francesco Mattioli, Alessandro Gaggero, Saeedeh Jahanmirinejad, Thang Ba Hoang, and Andrea Fiore. *Phys. Rev. Lett.*, 110:133605, 2013.
- [18] Qiang Wang and Michiel J.A. de Dood. An absorption-based superconducting nano-detector as a near-field optical probe. *Opt. Express*, 21:3682, 2013.
- [19] J. S. Lundeen, A. Feito, H. Coldenstrodt-Ronge, K. L. Pregnell, Ch. Silberhorn, T. C. Ralph, J. Eisert, M. B. Plenio, and I. A. Walmsley. Tomography of quantum detectors. *Nat. Phys.*, 5(1):27–30, 2008.
- [20] Andrew J. Kerman, Eric. A. Dauler, Joel K. W. Yang, Kristine M. Rosfjord, Vikas Anant, Karl K. Berggren, Gregory N. Goltsman, and Boris M. Voronov. Constriction-limited detection efficiency of superconducting nanowire single-photon detectors. *Appl. Phys. Lett.*, 90(10):101110, 2007.
- [21] R. Gaudio, K.P.M. op 't Hoog, Z. Zhou, D. Sahin, and A. Fiore. Inhomogeneous critical current in nanowire superconducting single-photon detectors. *Appl. Phys. Lett.*, 105:222602, 2014.
- [22] J. J. Renema, G Frucci, Z Zhou, F Mattioli, A Gaggero, R Leoni, M. J. A. de Dood, A Fiore, and M. P. van Exter. Modified detector tomography technique applied to a superconducting multiphoton nanodetector. *Opt. Express*, 20(3):2806–2813, 2012.
- [23] J S Lundeen, K L Pregnell, A Feito, B J Smith, W Mauerer, Ch Silberhorn, J Eisert, M B Plenio, and I A Walmsley. A proposed testbed for detector tomography. *J. Mod. Optic.*, 56(2-3), 2009.
- [24] Q. Wang, J. J. Renema, A. Gaggero, F. Mattioli, R. Leoni, M. P. van Exter, and M. J. A. de Dood. How noise affects quantum detector tomography. *J. Appl. Phys.*, 118(13), 2015.
- [25] Throughout this work, all efficiencies are defined as single-photon efficiencies.
- [26] M. Tinkham. *Introduction to superconductivity*. McGraw-Hill, 1996.
- [27] A. Anthore, H. Pothier, and D Esteve. Density of states in a superconductor carrying a supercurrent. *Phys. Rev. Lett.*, 90:127001, 2003.
- [28] M.J. Stevens, F. Marsili, A. Kozorezov, V.B. Verma, C. Lambert, R. Horansky, A. Lita, M.D. Shaw, R.P. Mirin, and S.W. Nam. Detector tomography as a probe of hotspot size in snspsds. *Single Photon Workshop*.
- [29] Francesco Marsili, Martin J Stevens, Alexander Kozorezov, Varun B Verma, Colin Lambert, Jeffrey A Stern, Robert Horansky, Shellee D Dyer, Matthew D Shaw, Richard P Mirin, et al. Hotspot dynamics in current carrying wsi superconducting nanowires. In *CLEO: QELS Fundamental Science*, pages FM4B–7. Optical Society of America, 2014.
- [30] F. Marsili, M. Stevens, A. Kozorezov, V.B. Verma, C. Labert, J.A. Stern, R. Horansky, S. Dyer, S. Duff, D.P. Pappas, A. Lita, M.D. Shaw, R.P. Mirin, and S.W. Nam. Hotspot relaxation dynamics in a current carrying superconductor. *Phys. Rev. B*, 93:094518, 2016.