

Stability of Room Temperature Compensated Half-Metallicity in Cr-based Inverse-Heusler Compounds

Hyo-Sun Jin^a, Kwan-Woo Lee^{a,b,*}

^aDepartment of Applied Physics, Graduate School, Korea University, Sejong 30019, Korea

^bDivision of Display and Semiconductor Physics, Korea University, Sejong 30019, Korea

Abstract

Using three correlated band approaches, namely the conventional band approach plus on-site Coulomb repulsion U , the modified Becke-Johnson functional, and hybrid functional, we have investigated inverse-Heusler ferrimagnets Cr_2CoZ ($Z=\text{Al, Ga, In}$). These approaches commonly indicate that the Cr_2CoAl synthesized recently is a precise compensated half-metal (CHM), whereas Cr_2CoGa and Cr_2CoIn are ferrimagnets with a small moment. This is also confirmed by the fixed spin moment approach. Analysis of the Bader charge decomposition and the radial charge densities indicates that this contrast is due to chemical differences among the Z ions. Additionally, in Cr_2CoAl , changing the volume by $\pm 5\%$ or the ratio of c/a by $\pm 2\%$ does not alter the CHM state, suggesting that this state is robust even under application of moderate pressure or strain. Considering the observed high Curie temperature of 750 K, our results suggest that Cr_2CoAl is a promising candidate for robust high T_C CHMs. Furthermore, the electronic structure of the CHM Cr_2CoAl is discussed.

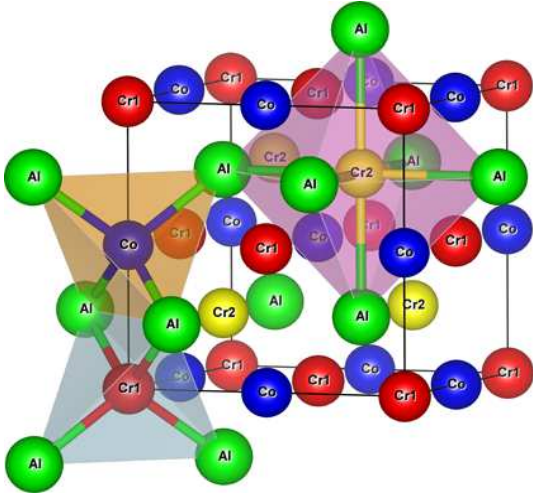


Figure 1: Inverse Heusler XA (or X_α) structure of Cr_2CoAl , consisting of Cr1-Al_4 and Co-Al_4 tetrahedra, and Cr2-Al_6 octahedra. The Cr1-Cr2-Co-Al sequence appears along the diagonal direction. Here, the two tetrahedra are edge-shared with each other, and face-shared with the octahedra. In the ground state, the spin moment of Cr1 ion is antialigned to that of both Cr2 and Co ions.

1. Introduction

The compensated half-metal (CHM), also called the half-metal antiferromagnet,[1] is a half-metal, which has one metallic and the other insulating spin channels, with the precisely compensated net moment. It is expected that

this character have many advantages in spintronics applications which feature zero stray field and high ordering temperatures. Although CHMs have been proposed in diverse crystal structures,[2] perovskite- or Heusler-related systems have been regarded as the most promising candidates. [2, 3, 4, 5, 6, 7] Recently, Felser and coworkers realized CHM in the Heusler Mn_3Ga , in which a small band overlap was observed,[7] by substitution of some Mn ions with Pt ions.[8] Kurt *et al.* also observed the CHM in Ru-doped Mn_2Ga thin films.[9] However, realization of CHM has been very limited and the ordering temperature has remained relatively low.

In this paper, we investigated the inverse-Heusler compounds of the type X_2YZ with a $X-X-Y-Z$ sequence along the diagonal direction in a cubic (the full-Heusler compounds have a $X-Y-X-Z$ sequence), as visualized in the structure of Cr_2CoAl shown in Fig. 1. Using the conventional band theory, Meinert and Geisler calculated formation energies and magnetic moments of several inverse-Heusler systems, and predicted the formation of ferrimagnetic states with a tiny moment.[10] Based on this theoretical suggestion, a few compounds including Cr_2CoGa and Cr_2CoAl have been synthesized and experimentally investigated. Jamer *et al.* recently synthesized Cr_2CoAl and observed a high Curie temperature $T_C \approx 750$ K,[11] which was much higher than that in the CHM $\text{Mn}_{3-x}\text{Pt}_x\text{Ga}$ whose T_C was below 300 K.[8] The x-ray magnetic circular dichroism measurements indicated a tiny net moment resulting from an antialigned configuration of Cr and Co moments, but due to some impurity phases in the sample it remained unclear whether the net

*corresponding author

Email address: mckwan@korea.ac.kr (Kwan-Woo Lee)

Table 1: Calculated total and local magnetic moments (in units of μ_B) of Cr_2YZ ($Y = \text{Co, Fe}$; $Z = \text{Al, Ga, In, Ge}$), using GGA, +U, +mBJ, and +EECE approaches. Here, GGA+U results are given only for $U_{eff} = 3$ eV for Cr and 4 eV for Fe and Co. The CHM character remains unchanged even as the strength of U_{eff} is varied in the region of 3 – 5 eV (see text for details). Small values of Z ions and interstitial contributions in each compound are not given below. For the Cr_2CoIn unsynthesized yet, our optimized lattice parameter, which is similar to the previously reported value,[10] is provided.

Compounds	Lattice constants (Å)	Experiments			Our calculations			
		T_C (K)	Moments (μ_B)	Method	Moments (μ_B)			
					Cr1	Cr2	Y	total
Cr ₂ FeGe	$a = 4.629$, $c = 12.414$ [12]		0.71	GGA	-2.38	1.95	2.08	1.4
				+ U	-2.21	1.73	1.7	0.97
				+mBJ	-2.98	2.01	2.21	0.79
				+EECE	-3.04	2.25	3.17	2.09
Cr ₂ CoGa	$a = 5.79$ [13, 14]	~ 320	0.26 – 0.31	GGA	-1.9	1.68	0.42	0.07
				+ U	-1.9	1.15	0.97	0.00
				+mBJ	-2.35	1.68	1.0	0.04
				+EECE	-3.02	2.08	1.36	0.06
	$a = 5.63$, $c = 5.88$ [15]	440 – 750	0.21 – 0.46	GGA	-1.6	1.44	0.34	0.07
				+ U	-1.6	0.97	0.82	0.00
				+mBJ	-2.14	1.54	0.9	0.04
				+EECE	-2.87	1.98	1.27	0.04
Cr ₂ CoIn	$a = 5.990$	–	–	GGA	-2.44	2.14	0.58	0.13
				+ U	-2.41	1.42	1.22	0.00
				+mBJ	-2.85	2.07	1.21	0.12
				+EECE	-3.34	2.49	1.54	0.32
Cr ₂ CoAl	$a = 5.794$ [11]	750	low-moment	GGA	-1.76	1.59	0.33	0.01
				+ U	-1.75	1.15	0.85	0.00
				+mBJ	-2.12	1.65	0.77	0.00
				+EECE	-2.96	2.16	1.23	0.00

moment was tiny or exactly zero. Additionally, several research groups have observed that the magnetic moment in Cr_2CoGa , a promising CHM candidate with high T_C , is very sensitive to the synthesizing conditions.[12, 13, 14, 15] It may be due to antisite disorder, which often occurs in the Heusler compounds. These findings necessitate a fine *ab initio* calculation, including correlation effects not considered previously but which are often crucial in transition metal compounds, to clarify the magnetic ground states. Besides, for further experimental researches it will be useful to investigate how the CHM state is robust under external conditions such as strain and pressure.

Here, we performed fine *ab initio* calculations with very dense k -meshes, using correlated band theories of the generalized gradient approximation plus U (GGA+U),[16] the Tran and Blaha modified Becke-Johnson functional (mBJ), [17, 18] and the hybrid functional[19]. Our results indicate that Cr_2CoAl is the most promising candidate of an exact CHM, which is also affirmed by the fixed spin moment approach.[20] We also investigate the stability of this state under pressure or strain. Moreover, we address the electronic structure of the CHM state, which is not reported till now.

2. Structure and calculation

In the cubic inverse Heusler X_2YZ structure (space group: $F\bar{4}3m$, No. 216), two types of X ions lie at $4a$ (0,0,0) and $4c$ ($\frac{1}{4}, \frac{1}{4}, \frac{1}{4}$). The Y and Z ions lie at $4b$ ($\frac{1}{2}, \frac{1}{2}, \frac{1}{2}$) and $4d$ ($\frac{3}{4}, \frac{3}{4}, \frac{3}{4}$), respectively. Some of the inverse Heusler compounds, such as Cr_2FeGe and Cr_2CoGa , show a tetragonal distortion. In the tetragonal structure (space group: $I4m2$, No. 119), X ions lie at $2b$ (0, 0, $\frac{1}{2}$) and $2d$ (0, $\frac{1}{2}, \frac{3}{4}$) and the Y and Z ions at $2a$ (0, 0, 0) and $2c$ (0, $\frac{1}{2}, \frac{1}{4}$), respectively. The lattice parameters used in this study are given in Table 1. For all compounds, experimentally obtained values were used in our calculations, except for Cr_2CoIn which has not been synthesized yet. Note that our optimized parameters were found to be within 3.5% of the experimental values, so that very little deviation occurred in the magnetic properties.

Our calculations were carried out with the Perdew-Burke-Ernzerhof GGA as the exchange-correlation functional, [21] implemented in the accurate all-electron full-potential code WIEN2K[22, 23] Correlation effects in the GGA+U approach were treated by the around mean field double-counting scheme,[16] which is often proper for the moderate correlated systems such as the present systems.[24] In these calculations, we varied the effective on-site Coulomb repulsion parameter $U_{eff} = U - J$ in the range of 3 – 5 eV for the Cr, Fe, and Co ions, as commonly applied.[5,

25, 26, 27, 28] Here, J is an intra exchange integral. Additionally, two other correlated band approaches of the hybrid functional[19] and the mBJ[17], implemented in WIEN2K, were used to confirm our GGA+U results. In the hybrid functional approach, the exact exchange for correlated electrons functional (EECE) for treating correlated electron systems was chosen with a common 25% of local density exchange replaced by the exact on-site exchange.[29] All results obtained here are very consistent, although there are subtle differences in some cases. As expected, spin-orbit coupling was excluded, since our preliminary calculations showed negligible effects due to this in these systems.

In the WIEN2K, the basis was determined by $R_{mt}K_{max} = 7$ and the augmented atomic radii of 2.28 – 2.5 a.u. for X and Y ions and 2.18 – 2.39 a.u. for Z ions. A very dense k -mesh containing up to $30 \times 30 \times 30$ points was used to check the convergence of the tiny moment character as a more careful treatment was required near the Fermi level E_F .

3. Results

3.1. Magnetic states in the correlated region

Recently, several ferrimagnetic (FI), transition metal-based inverse-Heusler compounds with low moments have been synthesized or theoretically proposed. However, as mentioned in the section of Introduction, the low moment character remains ambiguous. In the experimental point of view, the observed moments are very sensitive to the experimental conditions. In the theoretical point of view, the correlation effects usually relevant to transition metal based compounds have been excluded in the existing calculations. We now investigate these compounds through fine calculations, using the three correlated band approaches based on the density functional theory, with a very dense k -mesh. The results are given in Table 1.

We first address the tetragonal Cr_2FeGe with the observed net moment of $0.71 \mu_B$, [12] as a test system to check whether our approaches are reasonable for the Cr-based compounds. The spin of Cr1 ions is antialigned to both the spins of Cr2 and Fe ions, but the moment obtained from GGA is larger than the observed value by a factor of 2. On the other hand, inclusion of correlation using GGA+U and +mBJ approaches yields very similar moments in the range of $0.79 - 0.97 \mu_B$ as those obtained from the experiment. As expected, these results affirm the crucial role of correlation in such Cr-based compounds. Note that the GGA+EECE shows a substantially enhanced moment in Cr_2FeGe , whereas in the other compounds studied here the results of all three approaches are very similar.

Next, we investigate the FI Cr_2CoGa , which is experimentally the most well-studied among all three so far. Cr_2CoGa has both cubic and tetragonal phases with similar magnetic moments.[13, 14, 15] However, the observed Curie temperature T_C (in the range of 440 – 750 K) and

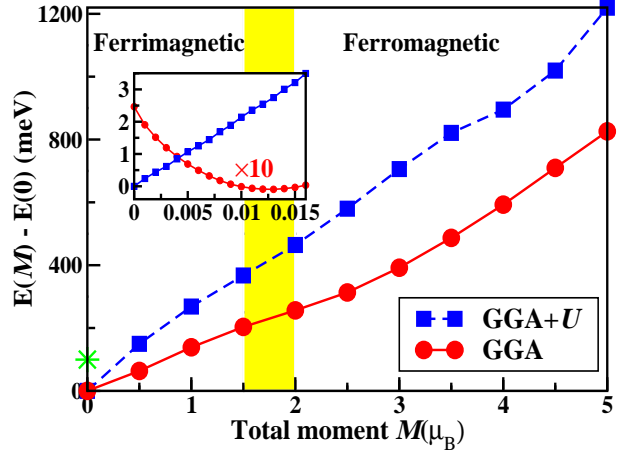


Figure 2: For Cr_2CoAl , change in energy versus fixed spin moment M (in units of μ_B per formula unit) in GGA and GGA+U. Ferrimagnetic state (FI) is favored over ferromagnetic state (FM) for $M \leq 1.5\mu_B$, while FM dominates FI for $M \geq 2\mu_B$. In the shaded region of $1.5 < M < 2.0$, both states coexist. The symbol * denotes the energy of the nonmagnetic state. Here $U_{eff} = 3$ eV for Cr and 4 eV for Co are used. $E(0)$ is the energy of the CHM state. Inset: Blowup plots below $M \sim 0.2\mu_B$, indicating that CHM is the ground state in GGA+U. In the Inset, the energies of GGA are enhanced by a factor of 10 for a better visualization.

moment ($0.21 - 0.46 \mu_B$) are sensitive to the synthesizing conditions.[15] Consistently with the experiments, in all our calculations the spin of Cr1 ions is antialigned to both the spins of Cr2 and Co ions, leading to a tiny net moment, but is not exactly compensated. The small moment of Cr_2CoGa is negligibly affected by the correlation. So, both experiments and calculations consistently indicate that Cr_2CoGa is not an exact CHM.

Further, the magnetic properties of the two isostructural compounds namely, cubic Cr_2CoIn and Cr_2CoAl are evaluated. For Cr_2CoIn , which has not been synthesized so far, only GGA+U produces a precise CHM state, whereas all other results show a small net moment of $0.12 - 0.32 \mu_B$. In the case of Cr_2CoAl , in the GGA calculations a Fermi energy E_F -crossing bands around the Γ -point appear in the spin-down channel (see below). Consequently, a small moment of $0.01 \mu_B$ results which is consistent with the findings of an earlier study.[10] Considering correlation effects, the bands are completely filled, resulting in half-metallic (see below). In this state, the net moment of Cr_2CoAl is exactly compensated. The origin of this distinction among these compounds will be identified below. Note that triple nodal points near the Fermi energy in the spin-up lead to a nontrivial topological feature, as will be addressed elsewhere.[30]

3.2. Studies of fixed spin moment of Cr_2CoAl

We performed fixed spin moment (FSM) calculations to confirm the CHM character of Cr_2CoAl . Figure 2 shows the plot of energy increment $\Delta E = E(M) - E(0)$, relative to the energy $E(0)$ of the CHM state, versus fixed spin moment M in both GGA and GGA+U methods. The

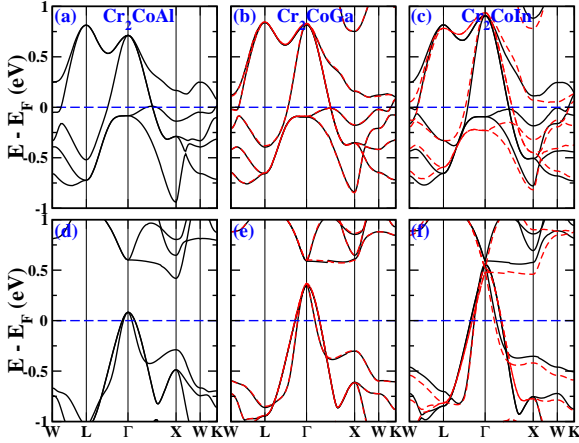


Figure 3: Comparison of band structures in GGA. Top and bottom lines are for the majority and minority spin channels, respectively. The (black) solid lines are for the original structures, and the (red) dashed lines are for the identical structure with Cr_2CoAl . Since difference in structure between Cr_2CoAl and Cr_2CoGa is small, the change in structure leads to no distinguishable variation, as shown in (b) and (e). Even for the identical structure, substantial differences among these three systems are clearly visible in the spin-down channels.

Table 2: Bader charges of Cr_2CoZ ($Z=\text{Al, Ga, In}$) obtained from GGA and GGA+U.

Method		Charges			
		Cr1	Cr2	Co	Z
GGA	Al	+0.37	-0.28	+1.33	-1.42
	Ga	-0.29	-0.39	+0.52	+0.16
	In	-0.28	-0.42	+0.57	+0.14
+U	Al	+0.40	-0.22	+1.23	-1.41
	Ga	-0.36	-0.25	+0.36	+0.25
	In	-0.37	-0.27	+0.37	+0.25

nonmagnetic state has a higher energy by approximately 100 meV than the CHM energy $E(0)$ as obtained from both GGA and GGA+U. Except for the low moment region, both the GGA and GGA+U results show a similar behavior in which the energy increases monotonically with increase in M . The inset of Fig. 2 shows a magnified view of the low moment region where the ground state in GGA appears at $M \approx 0.012\mu_B$, consistent with the self-consistent results. However, in the GGA+U, at the region the energy difference ΔE linearly increases from the value at $M = 0$. The linear behavior of the energy increment is testimony to the character of CHMs or half-metals.[4]

3.3. Effects of pressure and strain on magnetic state

To investigate the impact of pressure and the stability of the CHM state in Cr_2CoAl , we first vary the volume by $\pm 5\%$ of the experimental value. Remarkably, the net moment remains unchanged in all correlated calculations within this range of volume, except in the EECE case which showed a tiny moment of less than few hundredths of a μ_B when the volume was enhanced by more than 3%.

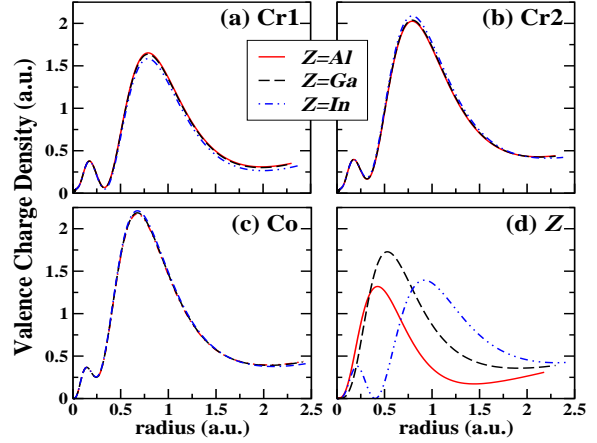


Figure 4: Radial charge densities $4\pi r^2 \rho(r)$ of each ion in Cr_2CoZ compounds versus distance from the each ion nucleus, in a.u. The significant difference in the charge distribution among the Z ions substantially varies that of that Cr1 and Cr2 ions, while that of the Co ion is affected somewhat.

Second, the ratio of in-plane and out-of-plane lattice constants is varied to inspect the effect of strain. A small strain does not lead to changing the moment, but a larger strain by over $\pm 2\%$ induces a tiny moment of about a few thousandths μ_B . This is consistent with the tiny difference in the magnetic moments between the cubic and tetragonal Cr_2CoGa . It is worthy to be noted that the magnetic moment of Cr_2CoIn also remains nearly unchanged, when compressing the volume by 5% or applying a strain. These results indicate that the magnetic states are very robust under application of pressure or strain.

3.4. Identifying differences

These differences among the three Cr-based inverse-Heusler compounds can be clarified in two ways. The difference in ionic sizes of Z atoms leads to structural differences. We first compared band structures with the same structure of Cr_2CoAl to show effects of pure chemical difference. As shown in Fig. 3, even in the identical structure distinctions among band structures of these three systems are very evident near E_F , indicating small effects of structural difference. This suggests that applying pressure is not a useful tool to achieve a CHM state in the system, as mentioned above.

Next, we calculated the Bader charges from the WIEN2K code, given in Table 2. Remarkably, the Al ion is much more ionic than the Ga and In ions. This is also observed in the radial charge density, which is a more efficient way to analyze differences in ionic charges.[31] As shown in Fig. 4, the charge of the Al ion is distributed more closely to the nucleus than that of the other Z ions. This difference in the charge distribution of Z ions affects the charge distribution of Cr1 and Cr2 ions, resulting in considerable variations of their local magnetic moments in each compound. (See Table 1.) These results confirm that the chemical differences among Z atoms, rather than the structure, lead to

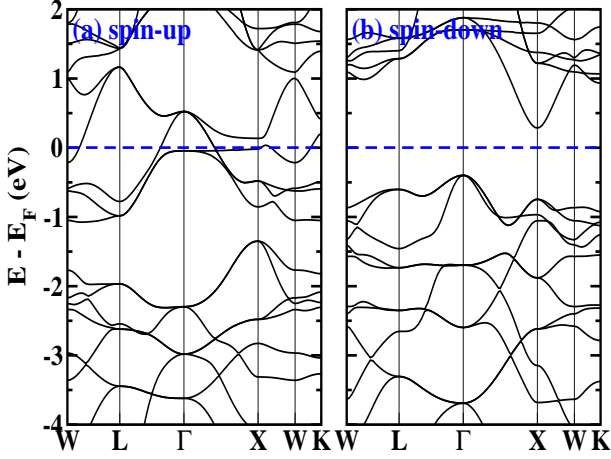


Figure 5: (a), (b) Spin-resolved GGA+U band structures, showing a half-metallic character. Here $U_{eff} = 3$ eV for Cr and 4 eV for Co are used. The horizontal dashed line indicates the Fermi level E_F , which is set to zero.

distinctions in the magnetic properties. One may expect to achieve an exact CHM state in Cr_2CoGa and Cr_2CoIn by some Al-doping, so requiring more research.

3.5. Electronic structures of Cr_2CoAl

Finally, we address the electronic structures of the CHM Cr_2CoAl in the correlated regime, which were not reported before. There are some distinguishing features of the band structures obtained here by the three different correlated band approaches, but they are very similar to each other as a whole. Therefore, only the GGA+U results are presented here, unless mentioned otherwise.

Consistent with the FSM results, the CHM state is energetically favored over the nonmagnetic state by 100 meV per formula unit. Our trials to obtain a ferromagnetic state are always converged into a FI state, indicating that the latter is much more stable.

The spin-resolved band structures of the GGA+U are illustrated in Figs. 5 (a) and (b). As depicted in Fig. 6, Cr_2CoAl shows a hybridization feature very similar to what has been earlier discussed in other inverse-Heusler compounds.[32] The d orbitals of Cr1-Co ions lead to $\{t_{2g}, e_g\}$ manifolds and nonbonding $\{t_{1u}, e_u\}$ orbitals. These 10 orbitals are hybridized with the Cr2 d orbitals, resulting in bonding $\{t_{2g}, e_g\}$, antibonding $\{t_{2g}^*, e_g^*\}$, and nonbonding $\{t_{1u}, e_u\}$ manifolds. In the minority channel, an indirect gap of 1 eV appears between the t_{1u} and e_u manifolds. In the majority channel, a mixture of the t_{1u} and e_u , separated from the other orbitals, is partially filled, indicating a half-metallic character. Notably, in the metallic channel, a nearly flat band appears to cross over E_F along the $\Gamma - X$ line, as often observed in perovskites without $dd\delta$ hopping.[25] This band leads to two interesting features in the density of states (DOS) and fermiology. As shown in the GGA+U total and atom-resolved DOSs of Fig. 6, E_F pinpoints a pseudogap, resulting in a tiny DOS at E_F . As pictured in Fig. 7 (b), rod-like hole Fermi surfaces

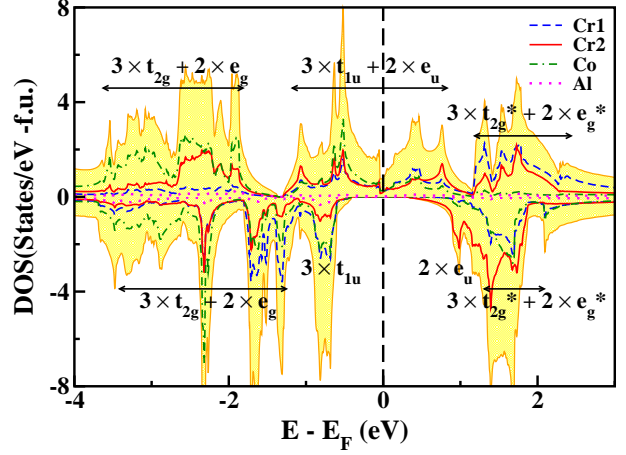


Figure 6: Total and atom-resolved densities of states (DOSs) in GGA+U with $U_{eff} = 3$ eV for Cr and 4 eV for Co. The symbols represent the hybridization feature. The total DOS, (yellow) shaded region, $N(E_F)$ at E_F is 0.047 states/eV per formula unit.

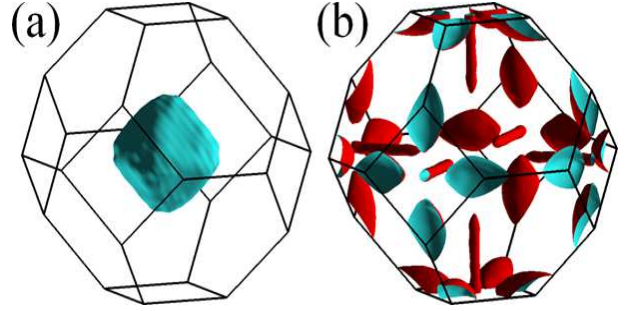


Figure 7: GGA+U Fermi surfaces, which possess (a) holes and (b) electrons

(FSs) appear along the X to Γ line. Additionally, there are Γ -centered hole and W -centered elliptical electron FSs, given in Fig. 7. The presence of the pseudogap close to E_F in the metallic channel may lead to unusual transport phenomena like ultrafast demagnetization.[33]

Although the topological properties are not covered here, it is worthy to be noted that the metallic channel shows remarkable features, seemingly related with topological characters, near the Fermi energy E_F . As in the full Heusler Co_2MnGa ,[34] a crossing between the nearly flat band and two-fold bands appears just below E_F along the $\Gamma - X$ line. (See Fig. 5(a).) In the Co_2MnGa , four-bands involved this crossing lead to a hopf-link semimetallic state. Instead, in the inverse Heusler compounds, this crossing leads to six triple points due to lack of inversion symmetry along the $\langle 100 \rangle$ in the BZ, implying another interesting topological character. Recently, Shi *et al.* also suggested a Weyl semimetallic state in the inverse Heusler FI Ti_2MnAl . [35] These interesting topological properties will be discussed elsewhere.[30]

4. Summary

We have investigated a few Cr-based inverse-Heusler compounds Cr_2CoZ ($Z=\text{Al, Ga, In}$) through fine electronic structure calculations based on three correlated band approaches, which have been used widely, in the hope of finding promising candidates for compensated half-metals (CHMs)

In these systems, our results show energetically most favored ferrimagnetic state, in which the spin of one of the two Cr ions is antialigned to that of the other Cr and Co ions. In contrast to the other systems showing small moments, the net moment of Cr_2CoAl is precisely compensated. This is also confirmed by the fixed spin moment approach. Through analysis of the radial charge distribution, we show that this distinction is due to chemical differences among the Z ions, implying that a precise CHM state would be also obtained by substitution of Al in Cr_2CoGa and Cr_2CoIn . Our results also suggest that the CHM state of Cr_2CoAl is robust under pressure or strain. Therefore, considering the observed high T_C , Cr_2CoAl would be a promising candidate for robust compensated half-metals with a high T_C , requiring more experimental research.

5. Acknowledgments

This research was supported by NRF of Korea Grant No. NRF-2016R1A2B4009579.

6. References

References

- [1] H. van Leuken and R. A. de Groot, Phys. Rev. Lett. **74**, 1171 (1995).
- [2] K.-W. Lee and W. E. Pickett, Phys. Rev. B **83**, 180406(R) (2011).
- [3] W. E. Pickett, Phys. Rev. B **57**, 10613 (1998).
- [4] K.-W. Lee and W. E. Pickett, Phys. Rev. B **77**, 115101 (2008).
- [5] H.-S. Jin and K.-W. Lee, Phys. Rev. B **84**, 172405 (2011).
- [6] K.-W. Lee and K.-H. Ahn, Phys. Rev. B **85**, 224404 (2012).
- [7] B. Balke, G. H. Fecher, J. Winterlik, and C. Felser, Appl. Phys. Lett. **90**, 152504 (2007).
- [8] A. K. Nayak, M. Nicklas, S. Chadov, P. Khuntia, C. Shekhar, A. Kalache, M. Baenitz, Y. Skourski, V. K. Guduru, A. Puri, U. Zeitler, J. M. D. Coey, and C. Felser, Nat. Mater. **14**, 679 (2015).
- [9] H. Kurt, K. Rode, P. Stamenov, M. Venkatesan, Y.-C. Lau, E. Fonda, and J. M. D. Coey, Phys. Rev. Lett. **112**, 027201 (2014).
- [10] M. Meinert and M. P. Geisler, J. Magn. Magn. Mater. **341**, 72 (2013).
- [11] M. E. Jamer, L. G. Marshall, G. E. Sterbinsky, L. H. Lewis, and D. Heiman, J. Magn. Magn. Mater. **394**, 32 (2015).
- [12] M. Hakimi, M. Venkatesan, K. Rode, K. Ackland, and J. M. D. Coey, J. Appl. Phys. **113**, 17B101 (2013).
- [13] W. Feng, W. Wang, C. Zhao, N. Van Quang, S. Cho, and D. D. Dung, AIP Adv. **5**, 117223 (2015).
- [14] B. Deka, R. Modak, P. Paul, and A. Srinivasan, J. Magn. Magn. Mater. **418**, 107 (2016).
- [15] M. E. Jamer, G. E. Sterbinsky, G. M. Stephen, M. C. DeCarpua, G. Player, and D. Heiman, Appl. Phys. Lett. **109**, 182402 (2016).
- [16] V. I. Anisimov, I. V. Solovyev, M. A. Korotin, M. T. Czyzyk, and G. A. Sawatzky, Phys. Rev. B **48**, 16929 (1993).
- [17] F. Tran and P. Blaha, Phys. Rev. Lett. **102**, 226401 (2009).
- [18] In the +mBJ calculations, the WIEN2K code use only the local spin density approximation (LSDA), regardless of a type of initial exchange-correlation functionals. Thus, this is the LSDA+mBJ approach.
- [19] P. Novák, J. Kuneš, L. Chaput, and W. E. Pickett, Phys. Status Solidi B **243**, 563 (2006).
- [20] K. Schwarz and P. Mohn, J. Phys. F:Met. Phys. **14**, L129 (1984).
- [21] J. P. Perdew, K. Burke, and M. Ernzerhof, Phys. Rev. Lett. **77**, 3865 (1996).
- [22] K. Schwarz and P. Blaha, Comput. Mater. Sci. **28**, 259 (2003).
- [23] K. Lejaeghere *et al.*, Science **351**, aad3000 (2016).
- [24] K.-W. Lee, J. Kunes, P. Novak, and W. E. Pickett, Phys. Rev. Lett. **94**, 026403 (2005).
- [25] K.-W. Lee and W. E. Pickett, Phys. Rev. B **80**, 125133 (2009).
- [26] H. T. Jeng and G. Y. Guo, Phys. Rev. B **67**, 094438 (2003).
- [27] S. Lv, H. Li, Z. Wang, L. Han, Y. Liu, X. Liu, and J. Meng, Appl. Phys. Lett. **99**, 202110 (2011).
- [28] M. Zhuang, W. Zhang, and N. Ming, Phys. Rev. B **57**, 10705 (1998).
- [29] S. Gangopadhyay and W. E. Pickett, Phys. Rev. B **93**, 155126 (2016).
- [30] H.-S. Jin, Y.-J. Song, W. E. Pickett, and K.-W. Lee, (unpublished).
- [31] Y. Quan V. Pardo, and W. E. Pickett, Phys. Rev. Lett. **109**, 216401 (2012).
- [32] I. Galankis, Ph. Mavropoulos, and P. H. Dederichs, J. Phys. D: Appl. Phys. **39**, 756 (2006).
- [33] A. Mann, J. Walowski, M. Münzenberg, S. Maat, M. J. Carey, J. R. Childress, D. Ebke, V. Drewello, G. Reiss, and A. Thomas, Phys. Rev. X **2**, 041008 (2012).
- [34] G. Chang, S.-Y. Xu, X. Zhou, S.-M. Huang, B. Singh, B. Wang, I. Belopolski, J. Yin, S. Zhang, A. Bansil, H. Lin, and M. Z. Hasan, Phys. Rev. Lett. **119**, 156401 (2017).
- [35] W. Shi, L. Muechler, K. Manna, Y. Zhang, K. Koepernik, R. Car, J. van den Brink, C. Felser, and Y. Sun, Phys. Rev. B **97**, 060406(R) (2018).