

Analytic Expression for Magnetic Activation Energy

Daisuke Miura* and Akimasa Sakuma

Department of Applied Physics, Tohoku University, Sendai 980-8579, Japan

We theoretically investigate the magnetic activation energy of permanent magnets. Practically, it is widely used in a phenomenological form as $\mathcal{F}_B(H_{\text{ext}}) = \mathcal{F}_B^0 (1 - H_{\text{ext}}/H_0)^n$, where \mathcal{F}_B^0 is the activation energy in the absence of an external magnetic field H_{ext} , n is a real parameter, and H_0 is defined by the equation $\mathcal{F}_B(H_0) = 0$. We derive the general and direct expressions for these phenomenological parameters under the restriction of uniform rotation of magnetization and on the basis of the perturbative theory with respect to H_{ext} . Further, we apply our results to $\text{Nd}_2\text{Fe}_{14}\text{B}$ magnets and confirm the validity of the proposed method by comparing with the Monte Carlo calculations.

Elucidating the dominant factors in the coercive force of permanent magnets is a central issue in the fields of magnetism and material science. Magnetocrystalline anisotropy (MA) is one of the dominant factors governing the coercive force in rare-earth (RE) magnets such as a Nd–Fe–B magnet,^{1,2)} whose temperature dependence has been investigated by many authors.^{3–6)} From the theoretical viewpoint, the MA of a ferromagnet is specified by its free energy density as a function of the magnetization angle, and practically, its temperature dependence is expressed in terms of ℓ th-order MA constants (MACs), $K_\ell(T)$, at a temperature T . Especially, in RE magnets, it is often found that those have higher order MACs and strongly depends on temperature. Fortunately, these complex features can be understood within mean field theories (MFTs).^{7–12)} Most recently,¹¹⁾ we described the temperature-dependent MA in local moment systems by using Zener’s phenomenological theory¹³⁾ and derived it in an extended form of the Akulov–Zener–Callen–Callen power law,^{13–15)} which is used to obtain a temperature dependence curve of $K_\ell(T)$ later in this study; there, it is referred to as the “extended power law (EPL).” On the other hand, it was reported that inhomogeneity in magnetic structures seriously affects the coercive forces,¹⁶⁾ and thus numerical analyses have been continued to date.^{17–22)}

As mentioned above, the temperature dependence of MA in RE magnets has been understood well. However, the role of MA in the coercive force mechanism is not clear at this

*dmiura@solid.apph.tohoku.ac.jp

stage even within the MFT. Especially, in the nonzero temperature range, the coercive force depends on the observation time. For this problem, Gaunt gave a direct answer by applying the Arrhenius formula²³⁾ to magnetization reversal dynamics, in which the magnetization reversal time is characterized by a magnetic activation energy density.^{24–26)} Here, the activation energy density was proposed to have a form as²⁷⁾

$$\mathcal{F}_B(H_{\text{ext}}) = \mathcal{F}_B^0(1 - H_{\text{ext}}/H_0)^n, \quad (1)$$

where H_{ext} is the amplitude of the external magnetic field, $\mathcal{F}_B^0 := \mathcal{F}_B(0)$, n is a real parameter, and H_0 is the amplitude of the external magnetic field required to cause magnetic reversal without the thermal activation. $\mathcal{F}_B(H_{\text{ext}})(> 0)$ is defined by subtracting the initial value of the free energy density from the maximum value of one in a magnetization reversal process. Therefore, $\mathcal{F}_B(H_{\text{ext}})$ depends on the path of the magnetization reversal process; in other words, \mathcal{F}_B^0 , H_0 , and n have the information about the magnetization reversal process, and thus, the investigation of these quantities is one of the good methods for understanding the coercive force mechanism from MA.^{27–32)}

In the present study, we aim to reveal the relation between the activation energy and MA by explicitly representing \mathcal{F}_B^0 , H_0 , and n in terms of a given free-energy density, in which we perform a perturbative calculation with respect to H_{ext} . Furthermore, we examine the validity of the perturbative result by comparing it with the non-perturbative one obtained by the Monte Carlo (MC) methods.¹⁹⁾

First, we derive expressions for \mathcal{F}_B^0 , H_0 , and n in terms of the free energy density in a magnet. In this study, we assume that the free energy density in the absence of an external field is given in the form of $F(\theta)$, which limits our discussion to the homogeneous magnetization-reversal process. Taking the initial angle as $\theta = \theta_1$ and the most unstable angle in the process as $\theta = \theta_2$, the angle-dependent free energy density satisfies

$$F'(\theta_1) = F'(\theta_2) = 0, \quad F''(\theta_1) > 0, \quad F''(\theta_2) < 0. \quad (2)$$

Now, applying the external magnetic field $H_{\text{ext}} > 0$ to the magnet, the total free-energy density is given as $F(\theta) - \mu_0 M H_{\text{ext}} \cos \theta$, where θ is measured from the field, μ_0 is the vacuum permeability, and M is the saturation magnetization. Here we notice that the extremal points depend on H_{ext} as $\theta_i \rightarrow \Theta_i(H_{\text{ext}})$, where $\Theta_i(0) \equiv \theta_i$. Then, the magnetic activation energy density in the presence of H_{ext} is defined by $\tilde{\mathcal{F}}_B(H_{\text{ext}}) := F(\Theta_2) - F(\Theta_1) - \mu_0 M H_{\text{ext}} (\cos \Theta_2 - \cos \Theta_1)$,

and perturbatively expanding $\tilde{\mathcal{F}}_B(H_{\text{ext}})$ with respect to H_{ext} , we obtain

$$\begin{aligned} \tilde{\mathcal{F}}_B(H_{\text{ext}}) = \tilde{\mathcal{F}}_B(0) & \left[1 - \frac{\mu_0 M (\cos \theta_2 - \cos \theta_1)}{\tilde{\mathcal{F}}_B(0)} H_{\text{ext}} \right. \\ & \left. - \frac{(\mu_0 M)^2}{2\tilde{\mathcal{F}}_B(0)} \left(\frac{\sin^2 \theta_2}{F''(\theta_2)} - \frac{\sin^2 \theta_1}{F''(\theta_1)} \right) H_{\text{ext}}^2 \right] + O(H_{\text{ext}}^3), \end{aligned} \quad (3)$$

where $\tilde{\mathcal{F}}_B(0) := F(\theta_2) - F(\theta_1)$. On the other hand, the perturbative expansion for Eq. (1) is given by

$$\mathcal{F}_B(H_{\text{ext}}) = \mathcal{F}_B^0 \left(1 - \frac{n}{H_0} H_{\text{ext}} + \frac{n(n-1)}{2H_0^2} H_{\text{ext}}^2 \right) + O(H_{\text{ext}}^3). \quad (4)$$

Therefore, the identity of $\tilde{\mathcal{F}}_B(H_{\text{ext}}) \equiv \mathcal{F}_B(H_{\text{ext}})$ yields the following equations:

$$\mathcal{F}_B^0 = F(\theta_2) - F(\theta_1), \quad (5a)$$

$$n = \left[1 + \frac{\mathcal{F}_B^0}{(\cos \theta_2 - \cos \theta_1)^2} \left(\frac{\sin^2 \theta_2}{F''(\theta_2)} - \frac{\sin^2 \theta_1}{F''(\theta_1)} \right) \right]^{-1}, \quad (5b)$$

$$E_0 := \mu_0 H_0 M = \frac{n \mathcal{F}_B^0}{\cos \theta_2 - \cos \theta_1}. \quad (5c)$$

These are general expressions in the second-order H_{ext} . Here we notice that in the present theory, there is no need to assume that the zero-field angles θ_i is small, although the difference, $\Theta_i(H_{\text{ext}}) - \Theta_i(0)$, must be small. Then, we can consider the usual case of $\theta_1 = \pi$ and $\theta_2 = \pi/2$, and from Eqs. (5) one can obtain

$$\mathcal{F}_B^0 = F(\pi/2) - F(\pi), \quad (6a)$$

$$n = \left(1 + \frac{\mathcal{F}_B^0}{F''(\pi/2)} \right)^{-1}, \quad (6b)$$

$$E_0 = n \mathcal{F}_B^0. \quad (6c)$$

Equations (5) and (6) represent one of the main results in the present study.

Next, let us consider a practically important case of an angle-dependent free energy density given by

$$F(\theta) = K_1 \sin^2 \theta + K_2 \sin^4 \theta. \quad (7)$$

From $F'(\theta) = 0$, it is possible to obtain a solution, except for the trivial angles $\theta = 0, \pi/2$, and π , satisfying

$$\sin^2 \theta_{\text{SRT}} = -\frac{K_1}{2K_2}. \quad (8)$$

When Eq. (8) and $K_1 \leq 0$ are simultaneously satisfied, $\theta = \theta_{\text{SRT}}$ is a minimum angle; hereinafter, this condition is referred to as the “spin reorientation transition (SRT) condition”.

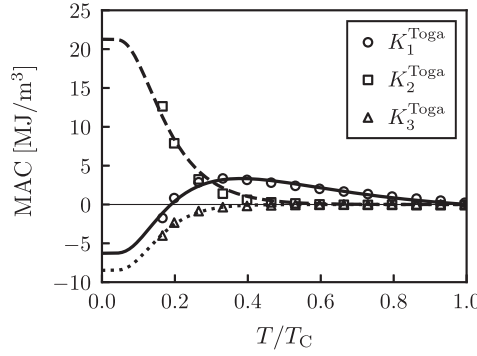


Fig. 1. EPL (lines) calculated by fitting to the ℓ th-order MACs (open symbols) evaluated via the constrained MC method,¹⁹⁾ as a function of temperature. The solid, dashed, and dotted lines denote $K_1^{\text{EPL}}(T)$, $K_2^{\text{EPL}}(T)$, and $K_3^{\text{EPL}}(T)$, respectively.

When the SRT condition is satisfied, the most stable angle is given by $\theta = \theta_{\text{SRT}}$, that is, $\theta_1 = \theta_{\text{SRT}}$ and $\theta_2 = \pi/2$, and accordingly, from Eq. (5) one can obtain

$$\mathcal{F}_B^0 = K_2 \left(1 + \frac{K_1}{2K_2} \right)^2, \quad (9a)$$

$$n = \frac{8}{5}, \quad (9b)$$

$$E_0 = \frac{8K_2}{5} \left(1 + \frac{K_1}{2K_2} \right)^{3/2}. \quad (9c)$$

In the case of $K_1 \geq 0$ and $K_2 \geq 0$, the SRT condition is not satisfied, and thus the result is that $\theta_1 = \pi$ and $\theta_2 = \pi/2$. Then from Eqs. (6), one can get

$$\mathcal{F}_B^0 = K_1 + K_2, \quad (10a)$$

$$n = 2 \frac{K_1 + 2K_2}{K_1 + 3K_2}, \quad (10b)$$

$$E_0 = 2K_1 \frac{(1 + 2K_2/K_1)(1 + K_2/K_1)}{1 + 3K_2/K_1}. \quad (10c)$$

Here we notice that the well-known exact solution in the Stoner–Wohlfarth model³³⁾ is reproduced by putting $K_2 = 0$.

Finally, we examine the validity of our results by comparing with the nonperturbative ones obtained with the MC method. Toga et al.¹⁹⁾ evaluated the temperature-dependent MACs, $K_\ell^{\text{Toga}}(T)$, up to the third order by using the constrained classical MC method³⁴⁾ in $\text{Nd}_2\text{Fe}_{14}\text{B}$ magnets, which is denoted by the open symbols in Fig. 1. To estimate the values of the MACs over the entire temperature range, we can use the EPL as¹¹⁾

$$K_1^{\text{EPL}}(T) = K_1^{\text{EPL}}(0) \mu_{\text{Nd}}(T)^3$$

$$\begin{aligned}
& + \frac{8}{7} K_2^{\text{EPL}}(0) \left[\mu_{\text{Nd}}(T)^3 - \mu_{\text{Nd}}(T)^{10} \right] \\
& + \frac{8}{7} K_3^{\text{EPL}}(0) \left[\mu_{\text{Nd}}(T)^3 - \frac{18}{11} \mu_{\text{Nd}}(T)^{10} + \frac{7}{11} \mu_{\text{Nd}}(T)^{21} \right], \quad (11a)
\end{aligned}$$

$$\begin{aligned}
K_2^{\text{EPL}}(T) &= K_2^{\text{EPL}}(0) \mu_{\text{Nd}}(T)^{10} \\
&+ \frac{18}{11} K_3^{\text{EPL}}(0) \left[\mu_{\text{Nd}}(T)^{10} - \mu_{\text{Nd}}(T)^{21} \right], \quad (11b)
\end{aligned}$$

$$K_3^{\text{EPL}}(T) = K_3^{\text{EPL}}(0) \mu_{\text{Nd}}(T)^{21}, \quad (11c)$$

where $\mu_{\text{Nd}}(T)$ is given by

$$\mu_{\text{Nd}}(T) := B_J \left(\frac{2|g-1|JH_{\text{Nd}}\mu_{\text{Fe}}(T)}{T} \right), \quad (12)$$

$$B_J(x) := \frac{2J+1}{2J} \coth\left(\frac{2J+1}{2J}x\right) - \frac{1}{2J} \coth\left(\frac{x}{2J}\right), \quad (13)$$

$$\mu_{\text{Fe}}(T) := \left[1 - 0.5 \left(\frac{T}{T_C} \right)^{3/2} - 0.5 \left(\frac{T}{T_C} \right)^{5/2} \right]^{1/3}, \quad (14)$$

and $J = 9/2$, $g = 8/11$, $H_{\text{Nd}} = 350\text{K}$,³⁵⁾ $T_C = 586\text{K}$,^{36,37)} for detail, see Ref. 11. Each fitting parameter $K_\ell^{\text{EPL}}(0)$ is determined as $K_1^{\text{EPL}}(0) = -6.28\text{MJ/m}^3$, $K_2^{\text{EPL}}(0) = 21.27\text{MJ/m}^3$, and $K_3^{\text{EPL}}(0) = -8.48\text{MJ/m}^3$ by fitting Eqs. (11) to K_ℓ^{Toga} . As shown in Fig. 1, we can observe that K_ℓ^{Toga} well obeys EPL, reflecting the fact that K_ℓ^{Toga} was obtained in a local moment model. Furthermore, the EPL describes a plateau in the low-temperature range that does not appear within the classical theory, as remarked by Toga et al., and our extrapolated values $K_1^{\text{EPL}}(0)$ and $K_2^{\text{EPL}}(0)$ are consistent with the experimental values -8.86MJ/m^3 and 23.85MJ/m^3 , respectively.³⁸⁾ Now we examine the validity of Eqs. (9) and (10) by using Eqs. (11a) and (11b); Fig. 2 shows the comparison of our perturbative results (lines) with the nonperturbative ones (open symbols), and we can observe that our present results consist with those obtained with the MC method by Toga et al. One of the important conclusions in the presence of both K_1 and K_2 is the point that the value of n considerably deviates from Stoner-Wohlfarth's "2", even in the simplest uniform rotation. In addition, our results demonstrate the presence of clear jumps in n and E_0 at a temperature $T = T_{\text{SRT}} \sim 0.2T_C$, which corresponds to the SRT temperature; $n \rightarrow 8/5$ and $E_0 \rightarrow 8K_2(T_{\text{SRT}})/5$ for $T \nearrow T_{\text{SRT}}$, and $n \rightarrow 4/3$ and $E_0 \rightarrow 4K_2(T_{\text{SRT}})/3$ for $T \searrow T_{\text{SRT}}$. In our macroscopic viewpoints, it is clear that this anomalous behavior originates from the complex temperature dependence of the MA as shown in Fig. 1. Unfortunately, the MC data of n and E_0 did not be given in the temperature range below T_{SRT} , and therefore further investigations are desired to completely reveal the temperature dependence of the

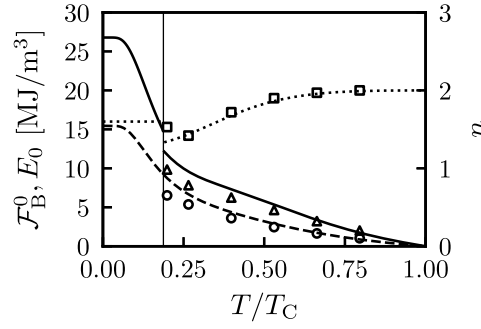


Fig. 2. Calculated phenomenological parameters for the magnetic activation energy density as a function of temperature. The dashed, solid, and dotted lines denote \mathcal{F}_B^0 , E_0 , and n , respectively. The open symbols represent the nonperturbative results evaluated by Toga et al.,¹⁹⁾ in which the circles, triangles, and squares correspond to \mathcal{F}_B^0 , E_0 , and n , respectively.

magnetic activation energy in realistic systems.

In summary, we derived simple analytic expressions for the phenomenological parameters describing the magnetic activation energy within the perturbative theory with respect to the external field, and confirmed that our present results for $\text{Nd}_2\text{Fe}_{14}\text{B}$ magnets consists with the nonperturbative ones obtained with the MC method.

Acknowledgment We would like to thank Dr. Y. Toga for the useful discussions. This work was supported by JSPS KAKENHI Grant No. 16K06702, No. 16H02390, No. 16H04322, and No. 17K14800, in Japan.

References

- 1) M. Sagawa, S. Fujimura, N. Togawa, H. Yamamoto, and Y. Matsuura: J. Appl. Phys. **55** (1984) 2083.
- 2) J. J. Croat, J. F. Herbst, R. W. Lee, and F. E. Pinkerton: J. Appl. Phys. **55** (1984) 2078.
- 3) J. F. Herbst: Rev. Mod. Phys. **63** (1991) 819.
- 4) R. Skomski and J. M. D. Coey: *Permanent Magnetism* (CRC Press, 1999).
- 5) J. M. D. Coey: *Magnetism and Magnetic Materials* (Cambridge University Press, 2010).
- 6) T. Miyake and H. Akai: J. Phys. Soc. Japan **87** (2018) 041009.
- 7) M. D. Kuz'min and A. M. Tishin, Theory of Crystal-Field Effects in 3d-4f Intermetallic Compounds, In K. H. J. Buschow (ed), *Handb. Magn. Mater.*, pp. 149–233. Elsevier, 2007.
- 8) R. Sasaki, D. Miura, and A. Sakuma: Appl. Phys. Express **8** (2015) 043004.
- 9) D. Miura, R. Sasaki, and A. Sakuma: Appl. Phys. Express **8** (2015) 113003.
- 10) M. Ito, M. Yano, N. M. Dempsey, and D. Givord: J. Magn. Magn. Mater. **400** (2016) 379.
- 11) D. Miura and A. Sakuma: AIP Adv. **8** (2018) 075114.
- 12) D. Miura and A. Sakuma: arXiv (2018) 1812.03611.
- 13) C. Zener: Phys. Rev. **96** (1954) 1335.
- 14) N. Akulov: Z. Phys. **100** (1936) 197.
- 15) H. B. Callen and E. Callen: J. Phys. Chem. Solids **27** (1966) 1271.
- 16) C. Mitsumata, H. Tsuchiura, and A. Sakuma: Appl. Phys. Express **4** (2011) 113002.
- 17) M. Nishino and S. Miyashita: Phys. Rev. B **91** (2015) 134411.
- 18) M. Nishino and S. Miyashita: Phys. Rev. B **97** (2018) 019904(E).
- 19) Y. Toga, M. Matsumoto, S. Miyashita, H. Akai, S. Doi, T. Miyake, and A. Sakuma: Phys. Rev. B **94** (2016) 174433.
- 20) M. Matsumoto, H. Akai, Y. Harashima, S. Doi, and T. Miyake: J. Appl. Phys. **119** (2016) 213901.
- 21) M. Nishino, Y. Toga, S. Miyashita, H. Akai, A. Sakuma, and S. Hirosawa: Phys. Rev. B **95** (2017) 094429.
- 22) Y. Toga, M. Nishino, S. Miyashita, T. Miyake, and A. Sakuma: Phys. Rev. B **98** (2018) 054418.
- 23) S. Arrhenius: Z. Phys. Chem. **4** (1889) 226.

- 24) P. Gaunt and G. J. Roy: *Philos. Mag.* **34** (1976) 781.
- 25) P. Gaunt: *Philos. Mag. B* **48** (1983) 261.
- 26) P. Gaunt: *J. Appl. Phys.* **59** (1986) 4129.
- 27) M. El-Hilo, K. O'Grady, and R. W. Chantrell: *J. Magn. Magn. Mater.* **248** (2002) 360.
- 28) D. Givord, A. Lienard, P. Tenaud, and T. Viadieu: *J. Magn. Magn. Mater.* **67** (1987) L281.
- 29) D. Givord, P. Tenaud, and T. Viadieu: *J. M* **72** (1988) 247.
- 30) R. H. Victora: *Phys. Rev. Lett.* **63** (1989) 457.
- 31) S. Bance, J. Fischbacher, A. Kovacs, H. Oezelt, F. Reichel, and T. Schrefl: *JOM* **67** (2015) 1350.
- 32) R. Goto, S. Okamoto, N. Kikuchi, and O. Kitakami: *J. Appl. Phys.* **117** (2015) 17B514.
- 33) E. C. Stoner and F. P. Wohlfarth: *Phil. Trans. Roy. Soc. London* **240** (1948) 599.
- 34) P. Asselin, R. F. L. Evans, J. Barker, R. W. Chantrell, R. Yanes, O. Chubykalo-Fesenko, D. Hinzke, and U. Nowak: *Phys. Rev. B* **82** (2010) 054415.
- 35) M. Yamada, H. Kato, H. Yamamoto, and Y. Nakagawa: *Phys. Rev. B* **38** (1988) 620.
- 36) S. Hirosawa, Y. Matsuura, H. Yamamoto, S. Fujimura, M. Sagawa, and H. Yamauchi: *J. Appl. Phys.* **59** (1986) 873.
- 37) M. Sagawa, S. Hirosawa, H. Yamamoto, S. Fujimura, and Y. Matsuura: *Jpn. J. Appl. Phys.* **26** (1987) 785.
- 38) K. D. Durst and H. Kronmuller: *J. Magn. Magn. Mater.* **59** (1986) 86.