

Templated synthesis of cyclic poly(ionic liquid)s

Qingquan Tang,^a Weiyi Zhang,^b Jiayin Yuan^b and Qiang Zhao^{a*}

a. Key Laboratory of Material Chemistry for Energy Conversion and Storage, Ministry of Education, School of Chemistry and Chemical Engineering, Huazhong University of Science and Technology, Wuhan 430074 China.

b. Department of Materials and Environmental Chemistry, Stockholm University, Stockholm 10691 Sweden.

* Corresponding author, E-mail: zhaoq@hust.edu.cn.

Abstract

Charged cyclic polymers, e.g. cyclic DNAs and polypeptides, play enabling roles in organisms, but their synthesis was challenging due to the well-known “polyelectrolyte effect”. To tackle the challenge, we developed a templated method to synthesize a library of imidazolium and pyridinium based cyclic poly(ionic liquid)s. Cyclic templates, cyclic polyimidazole and poly(2-pyridine), were synthesized first through ring-closure method by light-induced Diels–Alder click reaction. Through quaternization of cyclic templates followed by anion metathesis, the cyclic poly(ionic liquid)s were synthesized, which paired with varied counter anions.

Keywords: Cyclic polymers, Cyclic poly(ionic liquid)s, Ring-closure, Counter-anion exchange.


1. Introduction

Cyclic polymers (CPs) feature unique properties compared to their linear counterparts [1-4], such as lower melt viscosity, smaller hydrodynamic volume and modulated crystallization kinetics, leading to functional materials ranging from gels [5], micelles [6], to nanotubes [7], etc. CPs are normally synthesized through ring-expansion and/or ring-closure methods [8-10]. In contrast to the vast majority of synthetic CPs that are neutral, biology is replete with natural cyclic polymers bearing charge, such as cyclic deoxyribonucleic acid [11-13] and circular polypeptides [14-16], which were discovered in virus and bacterial [17,18], etc. The combination of charge and cyclic topology is crucial for properties such as self-replication [13], biological recognition [11] and activities [14]. As such, charged cyclic polymers, i.e., cyclic polyelectrolytes, are emerging topics attracting growing interest from both the chemistry and materials perspectives. For example, cyclic cationic poly((2-dimethylamino) ethylmethacrylate) exhibited reduced cytotoxicity than its linear counterparts in gene transfer processes [19]. In this context, we are particularly interested in cyclic poly(ionic liquid)s (CPILs), given that PILs is a subclass of ionic polymers highlighting beneficial properties [20-24] including surface activity, adaptive solubility, ionic conductivity, wide electrochemical windows, etc. As an emerging family of functional polymers, PILs have been exploited as membranes [25-28], self-assembly [29-31], ion conductors [32,33], structured carbon [34,35], advanced catalysis [36-38], etc. In this regard, CPILs can exhibit some novel properties than the linear counterparts, such as smaller hydrodynamic volume, unique diffusion dynamic [39], and higher biological activity [19]. As such, CPILs are potentially applicable for self-assembled entities with unique rheological properties, improved bioactivities, and advanced conducting abilities.

Different from neutral CPs synthesized by ring-closure cyclization at extremely diluted polymer solutions [40], synthesis of CPILs suffers from the so-called “polyelectrolyte effect” [41,42]. Under this circumstance, the electrostatic repulsion of charged chains renders collision of chain ends in dilute solution particularly difficult [43,44], thus impeding effective ring-closure. The ring-closure cyclization efficiency could be improved by increasing the polymer solution concentration, at the price of the enhanced intermolecular reaction and polycondensation byproducts. As an alternative approach, the ring-expansion method is more suited for monomers of specific chemical

structures, such as strain olefin [45,46] and lactones [47,48], precluding the majority of ionic liquid monomers such as the most extensively studied the imidazolium ones. Putting together, the synthesis of CPILs is an attractive topic but never reported so far.

Herein, we developed a templated method to synthesize CPILs (**Scheme 1**). Neutral cyclic polymer templates were synthesized first, which were subsequently quaternized and ion exchanged to yield target CPILs. This “template first” strategy skipped the adverse “polyelectrolyte effect” involved in the ring-closure method. In detail, linear poly(2-vinylpyridine) (LP2VP) and poly(1-(4-vinylbenzyl)imidazole) (LPVBIIm) were synthesized by Reversible Addition-Fragmentation Chain Transfer (RAFT) polymerization, followed through cyclization reaction by Diels-Alder click reaction of orthoquinodimethane and dithioester chain ends under UV light (365 nm) [49]. Thereafter, cyclic poly(1-cyanomethyl-2-vinylpyridine bromine) (CP2VP-Br) and cyclic poly(1-cyanomethyl-(4-vinylbenzyl)imidazole bromine) (CPVBIIm-Br), were synthesized by quaternization of the cyclic polymer precursors with bromoacetonitrile (BrCH₂CN). Subsequently, a library of CPILs paired with different counter anions was obtained by counter-ion exchange. They are termed CP2VP-X and CPVBIIm-X, where X is tetrafluoroborate (BF₄), hexafluorophosphate (PF₆), or bis(trifluoromethanesulfonyl)imide) (Tf₂N).

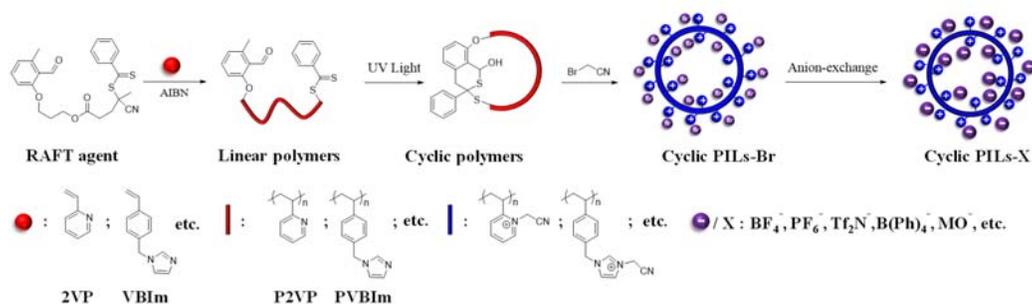

Scheme 1 Templated synthesis of CPILs.

2. Experimental

2.1 Materials

Glyoxaline, 4-(chloromethyl)styrene, bromoacetonitrile, sodium tetrafluoroborate (NaBF₄), potassium hexafluorophosphate (KPF₆), lithium bis(trifluoromethanesulfonyl)imide (LiTf₂N), sodium tetraphenylborate (NaB(Ph)₄) and methyl

orange (MO), sodium hydroxide, imidazole, 4-vinylbenzyl chloride, were purchased as reagent grade from Aldrich, Acros, Alfa Aesar, Aladdin, and used as received. Petroleum ether, methanol, diethyl ether, acetonitrile, dichloromethane (DCM), tetrahydrofuran (THF), hexane, chloroform (CHCl₃), *N,N*-Dimethylformamide (DMF) were purchased as reagent grade from Beijing Chemical Reagent Co. and used as received unless otherwise noted. 2-vinyl pyridine (2VP) were dried over CaH₂ and distilled before use. 2,2'-Azobisisobutyronitrile (AIBN) was recrystallized from ethanol and stored at 4 °C. RAFT agent (3-(2-formyl-3-methylphenoxy)propyl 4-cyano-4-((phenylcarbonothioyl)thio)pentanoate) [49], and *N*-(4-vinylbenzyl)-imidazole (VBI) [50], were synthesized according to the previous literatures. A low-pressure mercury lamp (120 W) (CEL-LPH120-254, Beijing China Education Au-light co. Ltd) was used as the UV light source.

2.2 Characterization

¹H-NMR spectrum were recorded on a Bruker Avance 400 spectrometer at room temperature. Ultraviolet Spectrum were recorded using a TU-1901 Ultraviolet Spectrophotometer. FT-IR spectrum were recorded on a Thermo Nicolet iS5 Spectrometer at room temperature. Gel permeation chromatography (GPC) in DMF was conducted on a system comprised of a Waters 515 HPLC pump, and a Waters 2414 RI detector equipped with four Waters Styragel columns (HT 2, HT 3, HT 4, and HT 5). DMF with 0.01 M LiBr was used as the eluent at a flow rate of 1.0 ml/min. Polystyrene standards were used for the calibration. Matrix-assisted laser desorption and ionization time-of-flight (MALDI-TOF) mass spectrometry was performed on a Bruker Biflex III spectrometer equipped with a 337 nm nitrogen laser. Inductively coupled plasma mass spectrometry (ICP-MS) were recorded on a PerkinElmer NexION 300X. Elemental analysis (C, H, N, S) was performed on a Flash EA1112 from Thermo Quest Italia S.P.A.

2.3 Synthesis of LP2VP

RAFT agent (45.5 mg, 0.1 mmol) and AIBN (3.6 g 0.22 mmol) were dissolved in 2VP (3.15 g, 30 mmol) on stirring under inert atmosphere. The clear solution was degassed via three freeze-thaw-pump cycles. After stirring at 60 °C for 7.5 h, the reaction was terminated by exposure to air. Polymer was precipitated from DCM

solvent into the excess of hexane three times. After drying overnight in a vacuum oven at room temperature, the light red powder was obtained with a monomer conversion of 15.2% from ¹H-NMR with a yield of 83.2%.

2.4 Synthesis of LPVBI_m

RAFT agent (45.5 mg, 0.1 mmol) and AIBN (3.28 g 0.2 mmol) were dissolved in VBI_m (1.84 g, 10 mmol) on stirring under inert atmosphere. The clear solution was degassed via three freeze-thaw-pump cycles. After stirring at 60 °C for 17 h, the reaction was terminated by exposure to air. Polymer was precipitated from DCM solvent into the excess of diethyl ether three times. After drying overnight in a vacuum oven at room temperature, the light red powder was obtained with a monomer conversion of 32.2% from ¹H-NMR with a yield of 90.2%.

2.5 Synthesis of cyclic poly(2-vinylpyridine) (CP2VP)

After dissolving linear precursors (50 mg) in acetonitrile (1000 ml), the solution was stirred under UV light irradiation for 9 h at room temperature. Pure cyclic polymers were conveniently collected by evaporation of solvent. Repeat the procedure 5 times until enough CP2VP were obtained for quaternization.

2.6 Synthesis of cyclic poly(1-(4-vinylbenzyl)imidazole) (CPVBI_m)

Follow similar procedures in “synthesis of CP2VP”, but with less linear precursors (20 mg) in acetonitrile (1000 ml).

2.7 Synthesis of CP2VP-Br

A solution of CP2VP (200 mg) in bromoacetonitrile (5 ml) was stirred at 60 °C for 3 days. After the reaction, the solution was precipitated in diethyl ether (50 ml), and then the precipitations were collected. The precipitations were re-dissolved in water (1 ml), and precipitated in THF (20 ml) again. After 3 dissolving-precipitations circles, the CP2VP-Br was obtained upon vacuum oven at room temperature overnight.

2.8 Synthesis of CPVBI_m-Br

A mixture solution of CPVBI_m (200 mg) with bromoacetonitrile (3 ml) in NMP (2

ml) was stirred at 60 °C for 1 days. After the reaction, the solution was dropped into diethyl ether (50 ml), and then precipitations were collected. The precipitations were re-dissolved in water (1 ml), and precipitated in THF (20 ml) again. After 3 dissolving-precipitations circles, the CPVBI_m-Br was obtained upon vacuum oven at room temperature overnight.

2.9 Synthesis of Various Cyclic PILs

Ten different cyclic PILs were prepared following identical counter-ion exchange procedures, with molar ratios of 2:1 (salts : PILs). The dissolved PILs solution (*e.g.* 50 mg CP2VP-Br/CPVBI_m-Br in 2 ml water) were dropped into salt solution (*e.g.* 36 mg NaBF₄ in 2ml water), and after filtration, the precipitations were washed 3 times with water, and dried in vacuum oven at room temperature overnight for next steps.

2.10 Calculation of counter-ion exchange efficiency

The efficiency of counter-ion exchange (E%) is defined as the ratio between exchanged ionic groups and ionic pyridine or imidazole units (equation 1 below).

$$E\% = \frac{\text{exchanged ionic groups}}{\text{ionic pyridine or imidazole units}} \times 100\% \quad (1)$$

3. Results and discussions

3.1 Synthesis and characterization of cyclic templates

GPC characterization of LP2VP (**Fig. 1A black**) reveal a well-defined, monomodal, and symmetric elution trace, indicative of the successful RAFT polymerization with fine control over molecular weight distribution. The whole GPC trace of CP2VP (**Fig. 1A red**) remains the same to LP2VP but shifts to a lower molecular weight regime. It indicates a smaller hydrodynamic radius of CP2VP and the corresponding apparent molecular weight ($M_n=11490$, PDI=1.15) in comparison to LP2VP precursor ($M_n=14020$, PDI=1.12). MALDI-TOF mass spectrum of LP2VP (**Fig. 2A**) and CP2VP (**Fig. 2B**) indicates that the absolute molecular weights are similar for both cases expanding from 4500 to 7500 and centering at 6000. Combining the much smaller apparent M_n of CP2VP than that of linear precursor from GPC, the successful cyclization is demonstrated [51-53]. Chemical structures of CP2VP were characterized by UV-Vis spectra (**Fig. 3**) and ¹H NMR (**Fig. 4**), whereas the $\pi-\pi^*$ adsorption peak of

the thiocarbonyl moiety at 305 nm disappears after ring closure reaction (Fig. 3A red arrow). Additionally, the NMR signal of orthoquinodimethane end group in LP2VP (at 10.66 ppm, H_a in Fig. 4A) vanishes after Diels-Alder ring-closure reaction (Fig. 4B), in good agreement with the UV-Vis results.

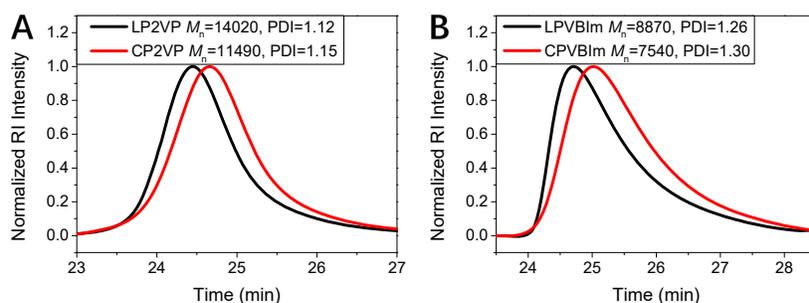


Fig. 1 A) GPC traces of (A) LP2VP and CP2VP, and (B) LPVBIIm and CPVBIIm. Eluent: DMF; calibration standard: polystyrene.

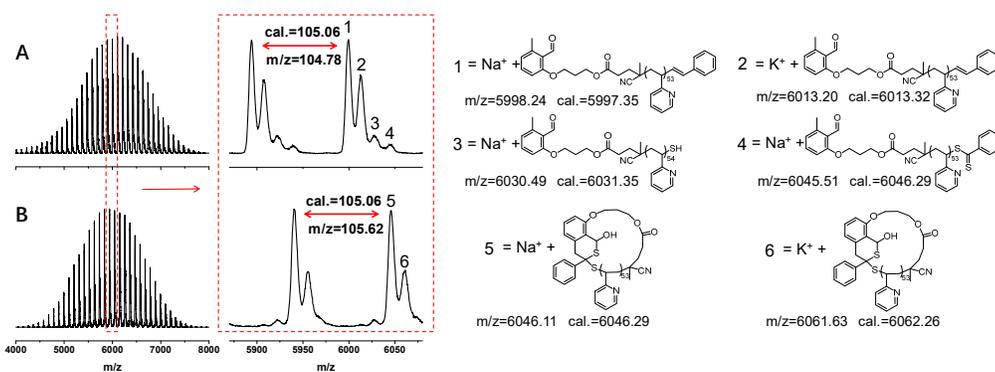


Fig 2. MALDI-TOF mass spectrum for LP2VP precursor and the corresponding CP2VP.

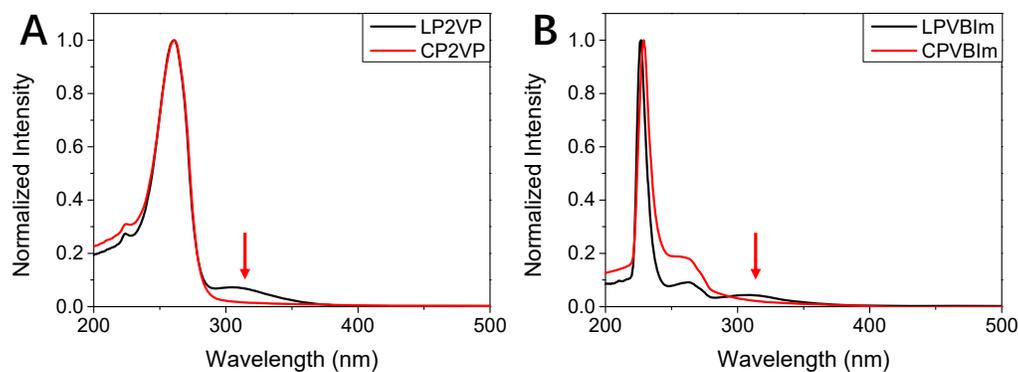


Fig 3. UV-vis spectrum of (A) LP2VP (black) and the resultant CP2VP (red) in DCM, (B) LPVBIIm (black) and the resultant CPVBIIm (red) in DCM.

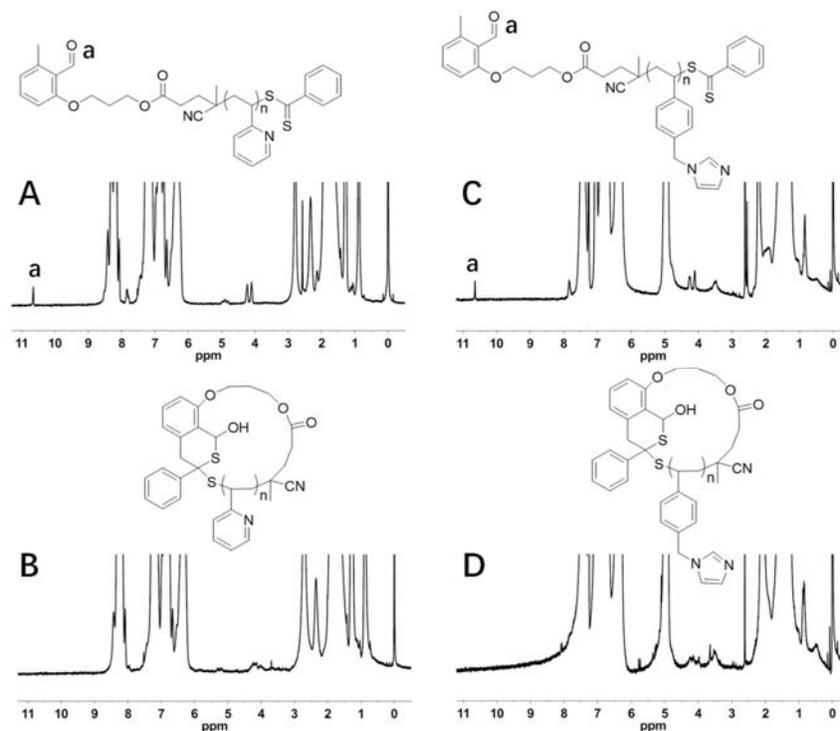


Fig 4. ^1H NMR spectrum of LP2VP (A), CP2VP (B), LPVBIIm (C) and CPVBIIm (D) in CDCl_3 .

Similar results were also found for the synthesis of cyclic PVBIIm (CPVBIIm) from its linear counterpart LPVBIIm. The GPC traces (**Fig. 1B**) in a well-defined, monomodal, and symmetrical shape are observed for LPVBIIm ($M_n=8870$, $\text{PDI}=1.26$) and CPVBIIm ($M_n=7540$, $\text{PDI}=1.30$), respectively. Moreover, the disappearance of orthoquinodimethane and thiocarbonyl group as a result of Diels-Alder ring closure reaction was confirmed by ^1H NMR (**Fig. 4D**) and UV-vis (**Fig. 3B**), respectively. These results all support the successful synthesis of CP2VP and CPVBIIm.

3.2 Synthesis and characterization of cyclic PILs

The two targeted CPILs, *i.e.* CP2VP-Br and CPVBIIm-Br, were synthesized by quaternization of CP2VP and CPVBIIm with BrCH_2CN , which is an active quaternizing agent with beneficial hydrophilicity for improving anion metathesis efficiency. In their ^1H NMR spectrum, new signals of H_b (5.90 ppm, **Fig. 5B**) and H_c (5.50 ppm, **Fig. 5D**) appear for CP2VP-Br and CPVBIIm-Br. Both signals can be assigned to the newly formed $-\text{CH}_2-\text{CN}$ groups, as a result of the quaternization of CP2VP and CPVBIIm by BrCH_2CN . Through the area integration ratio between H_b ($-\text{CH}_2-\text{CN}$) and H_a (pyridine

units), the quaternization degree of CP2VP is calculated to be ca. 60%. In a similar way, the quaternization degree of CPVBI_m-Br is ca. 95%, i.e. being more efficient than CP2VP. From FT-IR spectrum (**Fig. 6**), two new absorption bands (dashed rectangles) are seen at 1200 cm⁻¹ and 2200 cm⁻¹, which are assigned to the vibration mode of newly formed -CH₂-CN, in good agreement with the NMR results (**Fig. 5**).

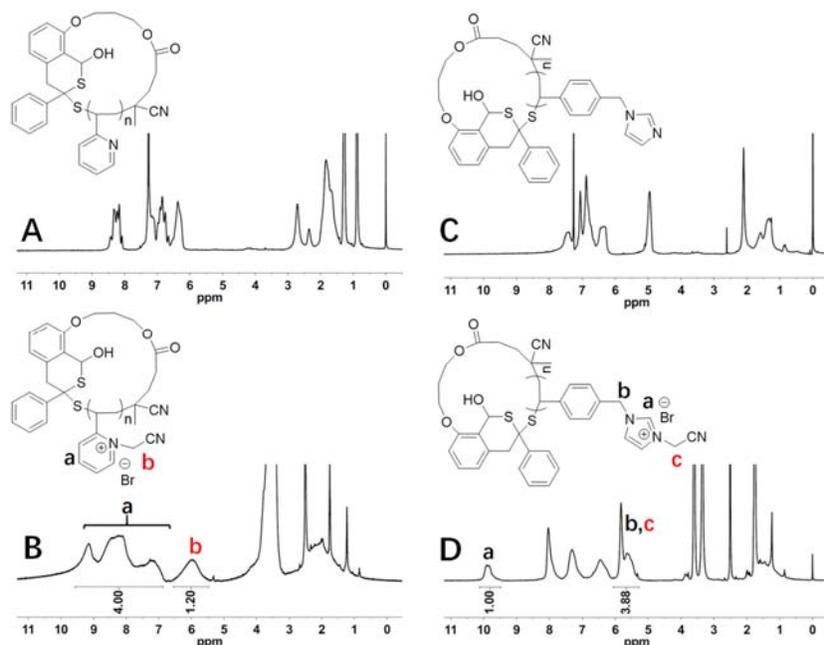


Fig. 5 ¹H NMR spectrum of A) CP2VP and C) CPVBI_m in CDCl₃; B) CP2VP-Br and D) CPVBI_m-Br in DMSO-*d*₆.

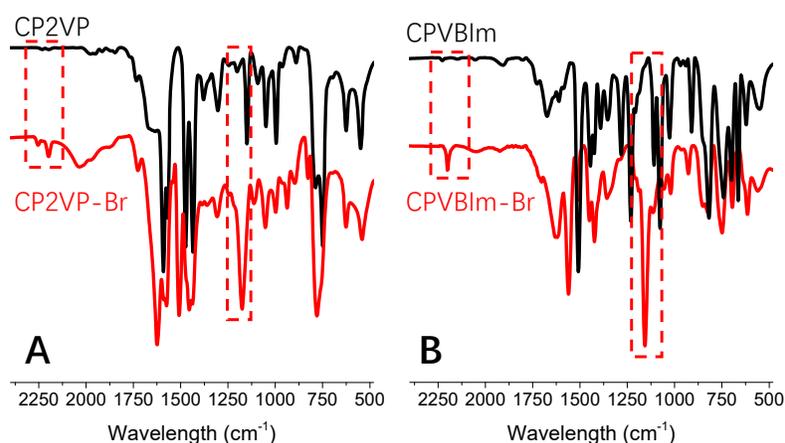


Fig. 6 FT-IR spectrum of CP2VP (A, in black), CP2VP-Br (A, in red), CPVBI_m (B, in black) and CPVBI_m-Br (B, in red).

3.3 Synthesis and characterization of various cyclic PILs

Counter-anion exchange was conducted to expand the structural spectrum of the as-synthesized CPILs. The successful synthesis of CP2VP- B(Ph)₄/MO and CPVBIIm-B(Ph)₄/MO (MO ~ methyl orange) were verified by ¹H NMR spectrum (Fig. 7), whereas the exchange efficiency was also calculated. For both CP2VP-X (Fig. 8A) and CPVBIIm-X (Fig. 8B), characteristic bands of each counter anions (BF₄⁻, PF₆⁻, Tf₂N⁻, B(Ph)₄⁻, MO⁻) are clearly seen from FT-IR curves of the corresponding CPIL-X after counter-ion exchange (dashed rectangles, Fig. 8). The efficiency of counter-ion exchange, defined as the ratio of exchanged repeating ionic units to their overall repeating ionic unit, was further quantified (Fig. 9). The exchange efficiency from Br⁻ to Tf₂N⁻ is 71.3% and 76.2% for CP2VP-X and CPVBIIm-X respectively, and the exchange efficiency of B(Ph)₄⁻ for both polymers is less than 85%. Notably, the anion exchange degree of CP2VP-Br or CPVBIIm-Br with MO anion are 99.1% and 98.1%, respectively, and this quantitative exchange is in agreement with previous works [54,55]. Moreover, the ion exchange degree of CP2VP-Br and CPVBIIm-Br with BF₄⁻ are 81.4% and 93.4%, respectively, as determined by ICP-MS.

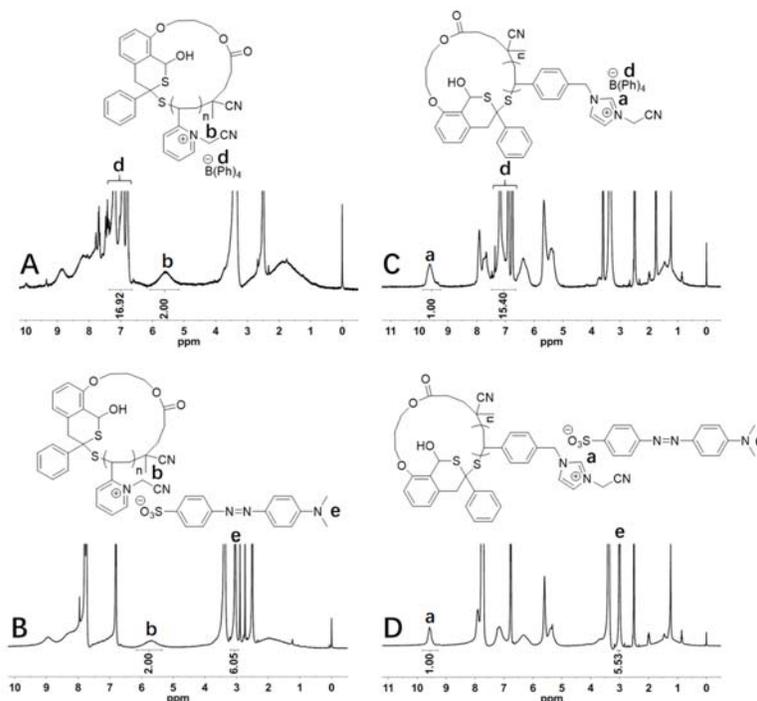


Fig 7. ¹H NMR spectrum of CPILs: A) CP2VP-B(Ph)₄; B) CP2VP-MO; C) CPVBIIm-B(Ph)₄; D) CPVBIIm-MO; in DMSO-*d*₆.

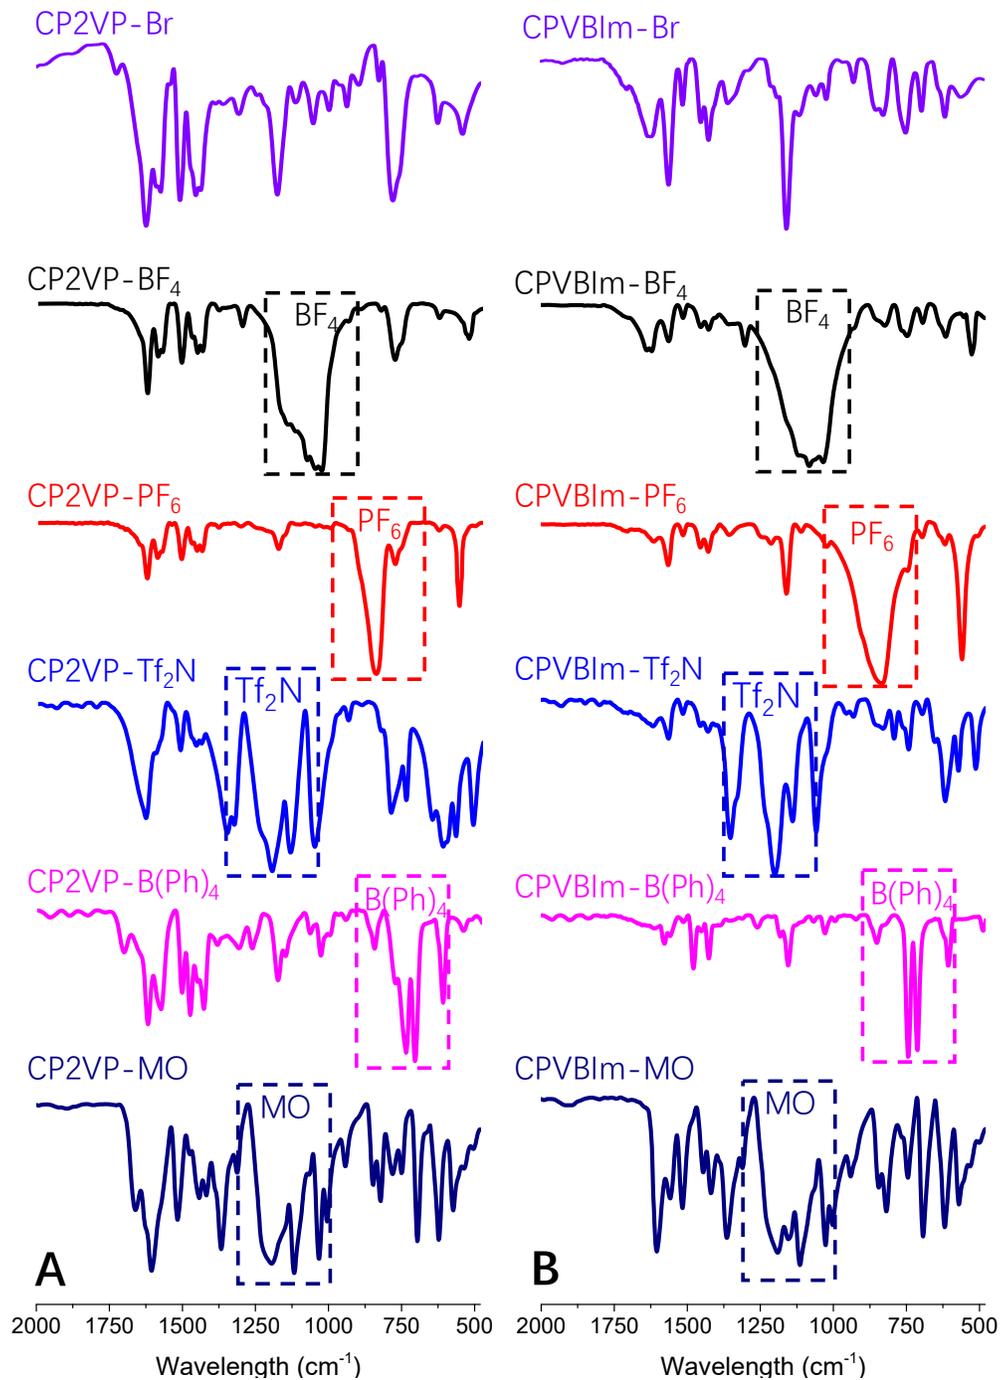


Fig. 8 FT-IR spectrum of CP2VP-Br (A, in purple), CP2VP-BF₄ (A, in black), CP2VP-PF₆ (A, in red), CP2VP-Tf₂N (A, in blue), CP2VP-B(Ph)₄ (A, in red purple), CP2VP-MO (A, in navy), CPVBIIm-Br (B, in purple), CPVBIIm-BF₄ (B, in black), CPVBIIm-PF₆ (B, in red), CPVBIIm-Tf₂N (B, in blue), CPVBIIm-B(Ph)₄ (B, in red purple), CPVBIIm-MO (B, in navy blue).

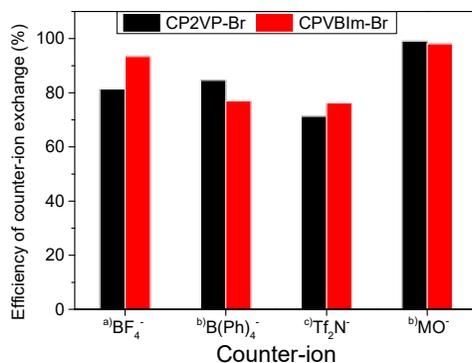


Fig. 9 Efficiency of counter-ion exchange of CP2VP-Br and CPVBIIm-Br with varied anions (BF₄⁻, Tf₂N⁻, B(Ph)₄⁻, MO⁻). a) determined from ICP-MS. b) determined from NMR. c) determined from Element analysis.

4. Conclusions

A templated method was proposed to synthesize pyridinium and imidazolium based cyclic PILs paired with various counter anions. LP2VP and LPVBIIm were synthesized by RAFT polymerization, and the ring-closure was accomplished with quantitation through the UV induced Diels-Alder reaction. Quaternization of CP2VP and CPVBIIm yielded CPILs whose counter anions could be effectively exchanged with other organic anions such as BF₄⁻, PF₆⁻, Tf₂N⁻, B(Ph)₄⁻ and MO⁻. Given that both the cations (pyridinium and imidazolium) and anions are most frequently used for ionic liquids and PILs, this work paves the synthetic path to a broad spectrum of CPILs with enriched topology, self-assembly and implication potentials, which have not been addressed due to the lack of suitable synthetic tools.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

Q. Z. gratefully acknowledges financial support from the Huazhong University of Science and Technology (No. 3004013118). Q. T. acknowledges financial support from the Selected Postdoctoral Technology Foundation in Huibei Province of China. J. Y. acknowledges financial support from the European

Research Council (ERC) Starting Grant (No. 639720-NAPOLI), the Wallenberg Academy Fellow program (No. KAW2017.0166) from the Knut and Alice Wallenbergs Foundation in Sweden, and the Strategic Fund from Stockholm University (Contract number: SU FV-2.1.1-005).

Notes and references

- [1] X. Y. Tu, M.-Z. Liu and H. Wei, Recent progress on cyclic polymers: synthesis, bioproperties, and biomedical applications, *J. Polym. Sci., Part A: Polym. Chem.* 54(2016) 1447-1458.
- [2] E. J. Shin, W. Jeong, H. A. Brown, B. J. Koo, J. L. Hedrick and R. M. Waymouth, Crystallization of cyclic polymers: Synthesis and crystallization behavior of high molecular weight cyclic poly(ϵ -caprolactone)s, *Macromolecules* 44(2011) 2773-2779.
- [3] T. Yamamoto, Synthesis of cyclic polymers and topology effects on their diffusion and thermal properties, *Polym. J.* 45(2012) 711-717.
- [4] T. Yamamoto and Y. Tezuka, Cyclic polymers revealing topology effects upon self-assemblies, dynamics and responses, *Soft Matter* 11(2015) 7458-7468.
- [5] K. Zhang, M. A. Lackey, J. Cui and G. N. Tew, Gels based on cyclic polymers, *J. Am. Chem. Soc.* 133(2011) 4140-4148.
- [6] B. Zhang, H. Zhang, Y. Li, J. N. Hoskins and S. M. Grayson, Exploring the effect of amphiphilic polymer architecture: Synthesis, characterization, and self-assembly of both cyclic and linear poly(ethylene glycol)-b-polycaprolactone, *ACS Macro Lett.* 2(2013) 845-848.
- [7] M. Schappacher and A. Deffieux, Synthesis of macrocyclic copolymer brushes and their self-assembly into supramolecular tubes, *Science* 319(2008) 1512-1515.
- [8] T. Josse, J. De Winter, P. Gerbaux and O. Coulembier, Cyclic polymers by ring-closure strategies, *Angew. Chem. Int. Ed.* 55(2016) 13944-13958.
- [9] B. A. Laurent and S. M. Grayson, Synthetic approaches for the preparation of cyclic polymers, *Chem. Soc. Rev.* 38(2009) 2202-2213.
- [10] Z. Jia and M. J. Monteiro, Cyclic polymers: Methods and strategies, *J. Polym. Sci., Part A: Polym. Chem.* 50(2012) 2085-2097.
- [11] E. T. Kool, Recognition of DNA, RNA, and proteins by circular oligonucleotides, *Acc. Chem. Res.* 31(1998) 502-510.
- [12] A. H. El-Sagheer, R. Kumar, S. Findlow, J. M. Werner, A. N. Lane and T. Brown, A very stable cyclic DNA miniduplex with just two base pairs, *ChemBiochem* 9(2008) 50-52.
- [13] J. Kim, J. Lee, S. Hamada, S. Murata and S. H. Park, Self-replication of DNA rings, *Nat. Nanotech.* 10(2015) 528-534.
- [14] K. W. Plaxco, K. T. Simons, I. Ruczinski and B. David, Topology, stability, sequence, and length: Defining the determinants of two-state protein folding kinetics, *Biochemistry* 39(2000) 11177-11183.
- [15] J. A. Camarero, D. Fushman, S. Sato, I. Girit, D. Cowburn, D. P. Raleigh and T.

- W. Muir, Rescuing a destabilized protein fold through backbone cyclization, *J. Mol. Biol.* 308(2001) 1045-1062.
- [16] J. A. Camarero and T. W. Muir, Biosynthesis of a head-to-tail cyclized protein with improved biological activity, *J. Am. Chem. Soc.* 121(1999) 5597-5598.
- [17] D. R. Helinski and D. B. Clewell, Circular DNA, *Annu. Rev. Biochem.* 40(1971) 899-942.
- [18] R. Borra and J. A. Camarero, Recombinant expression of backbone-cyclized polypeptides, *biopolymers* 100(2013) 502-509.
- [19] H. Wei, D. S. H. Chu, J. Zhao, J. A. Pahang and S. H. Pun, Synthesis and evaluation of cyclic cationic polymers for nucleic acid delivery, *ACS Macro Lett.* 2(2013) 1047-1050.
- [20] J. Yuan, D. Mecerreyes and M. Antonietti, Poly(ionic liquid)s: An update, *Prog. Polym. Sci.* 38(2013) 1009-1036.
- [21] D. Mecerreyes, Polymeric ionic liquids: Broadening the properties and applications of polyelectrolytes, *Prog. Polym. Sci.* 36(2011) 1629-1648.
- [22] J. Lu, F. Yan and J. Texter, Advanced applications of ionic liquids in polymer science, *Chem. Soc. Rev.* 34(2009) 431-448.
- [23] W. Zhang, Q. Zhao and J. Yuan, Porous polyelectrolytes: The interplay of charge and pores for new functionalities, *Angew. Chem. Int. Ed.* 57(2018) 6754-6773.
- [24] N. Patil, D. Cordella, A. Aqil, A. Debuigne, S. Admassie, C. Jérôme and C. Detrembleur, Surface- and redox-active multifunctional polyphenol-derived poly(ionic liquid)s: Controlled synthesis and characterization, *Polymer* 49(2016) 7676-7691.
- [25] Q. Zhao, J. W. C. Dunlop, X. Qiu, F. Huang, Z. Zhang, J. Heyda, J. Dzubiella, M. Antonietti and J. Yuan, An instant multi-responsive porous polymer actuator driven by solvent molecule sorption, *Nat. Commun.* 5(2014) 4293-4301.
- [26] Q. Zhao, J. Heyda, J. Dzubiella, K. Tauer, J. W. C. Dunlop and J. Yuan, Sensing solvents with ultrasensitive porous poly(ionic liquid) actuators, *Adv. Mater.* 27(2015) 2913-2917.
- [27] C. C. Ye, F. Y. Zhao, J. K. Wu, X. D. Weng, P. Y. Zheng, Y. F. Mi, Q. F. An and C. J. Gao, Sulfated polyelectrolyte complex nanoparticles structured nanofiltration membrane for dye desalination, *Desalination* 307(2017) 526-536.
- [28] R. Ma, Y. L. Ji, Y. S. Guo, Y. F. Mi, Q. F. An and C. J. Gao, Fabrication of antifouling reverse osmosis membranes by incorporating zwitterionic colloids nanoparticles for brackish water desalination, *Chem. Eng. J.* 416(2017) 35-44.
- [29] K. Manojkumar, D. Mecerreyes, D. Taton, Y. Gnanou and K. Vijayakrishna, Self-assembly of poly(ionic liquid) (PIL)-based amphiphilic homopolymers into vesicles and supramolecular structures with dyes and silver nanoparticles, *Polym. Chem.* 8(2017) 3497-3503.
- [30] A. J. Erwin, W. Xu, H. He, K. Matyjaszewski and V. V. Tsukruk, Linear and star poly(ionic liquid) assemblies: Surface monolayers and multilayers, *Langmuir* 33(2017) 3187-3199.
- [31] D. Cordella, F. Ouhib, A. Aqil, T. Defize, C. Jerome, A. Serghei, E. Drockenmuller, K. Aissou, D. Taton and C. Detrembleur, Fluorinated poly(ionic liquid) diblock

- copolymers obtained by cobalt-mediated radical polymerization-induced self-assembly, *ACS Macro Lett.* 6(2017) 121-126.
- [32] R. L. Weber, Y. Ye, A. L. Schmitt, S. M. Banik, Y. A. Elabd and M. K. Mahanthappa, Effect of nanoscale morphology on the conductivity of polymerized ionic liquid block copolymers, *Macromolecules* 44(2011) 5727-5735.
- [33] P. Maksym, M. Tarnacka, A. Dzienia, K. Erfurt, A. Chrobok, A. Zięba, K. Wolnica, K. Kaminski and M. Paluch, A facile route to well-defined imidazolium-based poly(ionic liquid)s of enhanced conductivity via RAFT, *Polym. Chem.* 8(2017) 5433-5443.
- [34] T. P. Fellingner, A. Thomas, J. Yuan and M. Antonietti, 25th anniversary article: "Cooking carbon with salt": Carbon materials and carbonaceous frameworks from ionic liquids and poly(ionic liquid)s, *Adv. Mater.* 25(2013) 5838-5854.
- [35] J. Gong, H. Lin, M. Antonietti and J. Yuan, Nitrogen-doped porous carbon nanosheets derived from poly(ionic liquid)s: Hierarchical pore structures for efficient CO₂ capture and dye removal, *J. Mater. Chem. A* 4(2016) 7313-7321.
- [36] Q. Zhao, P. Zhang, M. Antonietti and J. Yuan, Poly(ionic liquid) complex with spontaneous micro-/mesoporosity: Template-free synthesis and application as catalyst support, *J. Am. Chem. Soc.* 134(2012) 11852-11855.
- [37] Y. Lu and M. Ballauff, Spherical polyelectrolyte brushes as nanoreactors for the generation of metallic and oxidic nanoparticles: Synthesis and application in catalysis, *Prog. Polym. Sci.* 59(2016) 86-104.
- [38] J. Y. Yuan, S. Wunder, F. Warmuth and Y. Lu, Spherical polymer brushes with vinylimidazolium-type poly(ionic liquid) chains as support for metallic nanoparticles, *Polymer* 53(2012) 43-49.
- [39] L. Liu, W. Chen and J. Chen, Shape and diffusion of circular polyelectrolytes in salt-free dilute solutions and comparison with linear polyelectrolytes, *Macromolecules*, 50(2017) 6659-6667.
- [40] B. A. Laurent and S. M. Grayson, An efficient route to well-defined macrocyclic polymers via "Click" cyclization, *J. Am. Chem. Soc.* 128(2006) 4238-4239.
- [41] A. R. Khokhlov and K. A. Khachaturian, On the theory of weakly charged polyelectrolytes, *Polymer* 23(1982) 1742-1750.
- [42] B. A. V. Dobrynin, R. H. Colby and M. Rubinstein, Scaling theory of polyelectrolyte solutions, *Macromolecules* 28(1995) 1859-1871.
- [43] M. F. Raymond and P. S. Ulrich, Electrostatic interaction of polyelectrolytes and simple electrolytes, *J. Polym. Sci.* 3(1948) 602-603.
- [44] H. Yang, Q. Zheng and R. Cheng, New insight into "polyelectrolyte effect", *Colloids and Surfaces A: Physicochem. Eng. Aspects.*, 2012, 407, 1-8.
- [45] K. Zhang, M. A. Lackey, Y. Wu and G. N. Tew, Universal cyclic polymer templates, *J. Am. Chem. Soc.* 133(2011) 6906-6909.
- [46] C. W. Bielawski, D. Benitez and R. H. Grubbs, An "endless" route to cyclic polymers, *Science* 297(2002) 2041-2044.
- [47] M. Hong and E. Y. X. Chen, Completely recyclable biopolymers with linear and cyclic topologies via ring-opening polymerization of γ -butyrolactone, *Nat. Chem.* 8(2015) 42-49.

- [48] S. Y. Hu, G. X. Dai, J. P. Zhao and G. Z. Zhang, Ring-opening alternating copolymerization of epoxides and dihydrocoumarin catalyzed by a phosphazene superbase, *Macromolecules* 49(2016) 4462-4472.
- [49] Q. Tang, Y. Wu, P. Sun, Y. Chen and K. Zhang, Powerful ring-closure method for preparing varied cyclic polymers, *Macromolecules* 47(2014) 3775-3781.
- [50] Y. Xie, Q. Sun, Y. Fu, L. Song, J. Liang, X. Xu, H. Wang, J. Li, S. Tu, X. Lu and J. Li, Sponge-like quaternary ammonium-based poly(ionic liquid)s for high CO₂ capture and efficient cycloaddition under mild conditions, *J. Mater. Chem. A* 5(2017) 25594-25600.
- [51] T. Josse, O. Altintas, K. K. Oehlenschlaeger, P. Dubois, P. Gerbault, O. Coulembier and C. Barner-Kowollik, Ambient temperature catalyst-free light-induced preparation of macrocyclic aliphatic polyesters, *Chem. Commun.* 50(2014) 2024-2026.
- [52] P. Sun, Q. Tang, Z. Wang, Y. Zhao and K. Zhang, Cyclic polymers based on UV-induced strain promoted azide-alkyne cycloaddition reaction, *Polym. Chem.* 6(2015) 4096-4101.
- [53] P. Sun, J. a. Liu, Z. Zhang and K. Zhang, Scalable preparation of cyclic polymers by the ring-closure method assisted by the continuous-flow technique, *Polym. Chem.* 7(2016) 2239-2244.
- [54] S. Xiao, X. Lu and Q. Lu, Photosensitive polymer from ionic self-assembly of azobenzene dye and poly(ionic liquid) and its alignment characteristic toward liquid crystal molecules, *Macromolecules* 40(2007) 7944-7950.
- [55] Q. Zhang, C. G. Bazuin and C. J. Barrett, Simple spacer-free dye-polyelectrolyte ionic complex: Side-chain liquid crystal order with high and stable photoinduced birefringence, *Chem. Mater.* 20(2008) 29-31.

Supplementary Information

Experimental

Materials

Glyoxaline, 4-(chloromethyl)styrene, bromoacetonitrile, sodium tetrafluoroborate (NaBF₄), potassium hexafluorophosphate (KPF₆), lithium bis(trifluoromethanesulfonyl)imide (LiTf₂N), sodium tetrphenylborate (NaB(Ph)₄) and methyl orange (MO), sodium hydroxide, imidazole, 4-vinylbenzyl chloride, were purchased as reagent grade from Aldrich, Acros, Alfa Aesar, Aladdin, and used as received. Qetroleum ether, methanol, diethyl ether, acetonitrile, dichloromethane (DCM), tetrahydrofuran (THF), hexane, chloroform (CHCl₃), *N,N*-Dimethylformamide (DMF) were purchased as reagent grade from Beijing Chemical Reagent Co. and used as received unless otherwise noted. 2-vinyl pyridine (2VP) were dried over CaH₂ and distilled before use. 2,2'-Azobisisobutyronitrile (AIBN) was recrystallized from ethanol and stored at 4 °C. *N*-(4-vinylbenzyl)-imidazole¹, RAFT agent² were synthesized according to the previous literatures. A low-pressure mercury lamp (120 W) (CEL-LPH120-254, Beijing China Education Au-light co. Ltd) was used as the UV light source.

Characterization

¹H-NMR spectra were recorded on a Bruker Avance 400 spectrometer at room temperature.

Ultraviolet Spectra were recorded using a TU-1901 Ultraviolet Spectrophotometer.

FT-IR spectra were recorded on a Thermo Nicolet Avatar-330 Spectrometer at room temperature.

Gel permeation chromatography (GPC) in DMF was conducted on a system comprised of a Waters 515 HPLC pump, and a Waters 2414 RI detector equipped with four Waters Styragel columns (HT 2, HT 3, HT 4, and HT 5). DMF with 0.01 M LiBr was used as the eluent at a flow rate of 1.0 mL/min. Polystyrene standards were used for the calibration.

1. Preparation of LP2VP

A mixed solution of 2VP (3.15 g, 30 mmol), RAFT agent **1** (45.5 mg, 0.1 mmol) and AIBN (3.6 g 0.22 mmol) was degassed *via* three freeze-thaw-pump cycles. After stirring at 60 °C for 7.5 h, the reaction was terminated by exposure to air. Polymer was precipitated from an excess of hexane three times. After drying overnight in a vacuum oven at room temperature, the light red product was obtained with a monomer conversion of 15.2% from ¹H-NMR.

2. Preparation of LPVBI_m

A mixed solution of VBI_m (1.84 g, 10 mmol), RAFT agent **1** (45.5 mg, 0.1 mmol) and AIBN (3.28 g 0.2 mmol) was degassed *via* three freeze-thaw-pump cycles. After stirring at 60 °C for 17 h, the reaction was terminated by exposure to air. Polymer was precipitated from an excess of diethyl ether three times. After drying overnight in a vacuum oven at room temperature, the light red product was obtained with a monomer conversion of 32.2% from ¹H-NMR.

3. Preparation of CP2VP

After dissolving linear precursors (50 mg) in acetonitrile (1000 mL), the solution was stirred under UV light irradiation for 9 h at room temperature. Pure cyclic polymers were conveniently collected by evaporation of solvent. Repeat the procedure until enough cyclic P2VP were obtained for quaternization.

4. Preparation of CPVBI_m

Follow similar procedures in “preparation of cyclic P2VP”, but with less linear precursors (20 mg) in acetonitrile (1000 mL).

5. Preparation of CP2VP-Br

A solution of cyclic P2VP (200 mg) in bromoacetonitrile (5 ml) was stirred at 60 °C for 3 days. After the reaction, the solution was precipitated in diethyl ether (50 ml), and then concentrated and the precipitations were collected. The precipitations were re-dissolved in water (1 ml), and precipitate in THF (20 ml) again. After 3 dissolving-precipitation circle, the CP2VP-Br was obtained upon vacuum dry.

6. Preparation of CPVBI_m-Br

A mixture solution of cyclic P2VP (200 mg) with bromoacetonitrile (3 ml) in NMP (2 ml) was stirred at 60 °C for 1 days. After the reaction, the solution was dropped into diethyl ether (50 ml), and then concentrated and the precipitations were collected. The precipitations were re-dissolved in water (1 ml), and precipitate in THF (20 ml) again. After 3 dissolving-precipitation circle, the CPVBI_m-Br was obtained upon vacuum dry.

7. Preparation of Various Cyclic PILs

Ten different cyclic PILs were prepared following identical counter-ion exchange procedures, with molar ratios of 2:1 (salts : PILs). The dissolved PILs solutions (*e.g.* 50 mg CP2VP-Br/CPVBI_m-Br in 2 mL water) were dropped into salt solutions (*e.g.* 36 mg NaBF₄ in 2mL water), and after filtration, the precipitations were washed 3 times with water, and dried in vacuum for next steps.

8. Calculation of counter-ion exchange efficiency

According to the definition of the efficiency of counter-ion exchange, the formula can be shown as (1):

$$E\% = \frac{\text{exchanged ionic groups}}{\text{ionic pyridine or imidazole units}} \times 100\% \quad (1)$$

8.1. The efficiency of counter-ion exchange for CP2VP-Tf₂N and CPVBIIm-Tf₂N by elemental analysis.

Because the efficiency of quaternization of CP2VP-Br was 60%, name is, only 60% pyridine ring unit on the polymer have been ionized. The CP2VP-Tf₂N structure was shown in Figure S1. The formula to calculate the content of sulfur was shown in (2), which 64 is the mass of sulfur, 105 is the mass of pyridine ring, 225 is the mass of unexchanged ionic group, 425 is the mass of exchanged ionic group, and x was 0.4, and y plus z was 0.6, E% was z/0.6. The results of elemental analysis was 10.43%, So the efficiency of counter-ion exchange for CP2VP-Tf₂N is 71.3%.

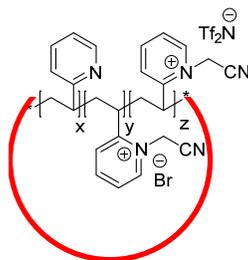


Figure S1. The structure of CP2VP-Tf₂N.

Content of Sulfur

$$\begin{aligned} &= \frac{z * 64}{x * 105 + y * 225 + z * 425} \\ &\times 100\% \quad (2) \\ &= \frac{E * 0.6 * 64}{0.4 * 105 + (0.6 - 0.6 * E) * 225 + E * 0.6 * 425} \times 100\% \end{aligned}$$

Similarly, because the efficiency of quaternization of CPVBIIm-Br was 94%, *i.e.*, only 94% imidazole unit along the polymer backbone have been ionized. The CPVBIIm-Tf₂N structure was shown in Figure S2. The formula to calculate the content of Sulfur was shown in (3), where 64 is the mass of sulfur, 184 is mass of the neutral group, 304 is the mass of unexchanged ionic group, 504 is the mass of the exchanged ionic group, and x was 0.06, and y plus z was 0.94, E% was z/0.94. The result of elemental analysis was 10.51%, so the efficiency of counter-ion exchange for CPVBIIm-Tf₂N is 76.2%.

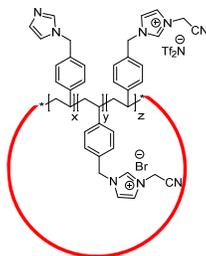


Figure S2 The structure of CPVBIIm-Tf₂N.

Content of Sulfur

$$\begin{aligned}
 &= \frac{z * 64}{x * 184 + y * 304 + z * 504} \times 100\% \quad (3) \\
 &= \frac{E * 0.94 * 64}{0.06 * 184 + (0.94 - 0.94 * E) * 304 + E * 0.94 * 504} \times 100\%
 \end{aligned}$$

8.2. The efficiency of counter-ion exchange for CP2VP-BF₄ and CPVBIIm-BF₄ by the ICP-MS.

Similarly, the efficiency of counter-ion exchange for CP2VP-BF₄ and CPVBIIm-BF₄ could be calculated by the content of boron, which was determined by ICP-MS. The calculation process was the same like E% calculated by content of sulfur for CP2VP-Tf₂N and CPVBIIm-Tf₂N.

For CP2VP-BF₄, formula is (4), and the results of ICP-MS was 2.978%, so the efficiency of counter-ion exchange for CP2VP-BF₄ is 81.4%.

Content of Boron

$$\begin{aligned}
 &= \frac{z * 11}{x * 105 + y * 225 + z * 232} \times 100\% \quad (4) \\
 &= \frac{E * 0.6 * 11}{0.4 * 105 + (0.6 - 0.6 * E) * 225 + E * 0.6 * 232} \times 100\%
 \end{aligned}$$

For CPVBIIm-BF₄, formula is (5), and the results of ICP-MS was 3.187%, so the efficiency of counter-ion exchange for CPVBIIm-BF₄ is 93.4%.

Content of Boron

$$\begin{aligned}
 &= \frac{z * 11}{x * 184 + y * 304 + z * 311} \times 100\% \quad (4) \\
 &= \frac{E * 0.94 * 11}{0.06 * 184 + (0.94 - 0.94 * E) * 304 + E * 0.94 * 311} \times 100\%
 \end{aligned}$$

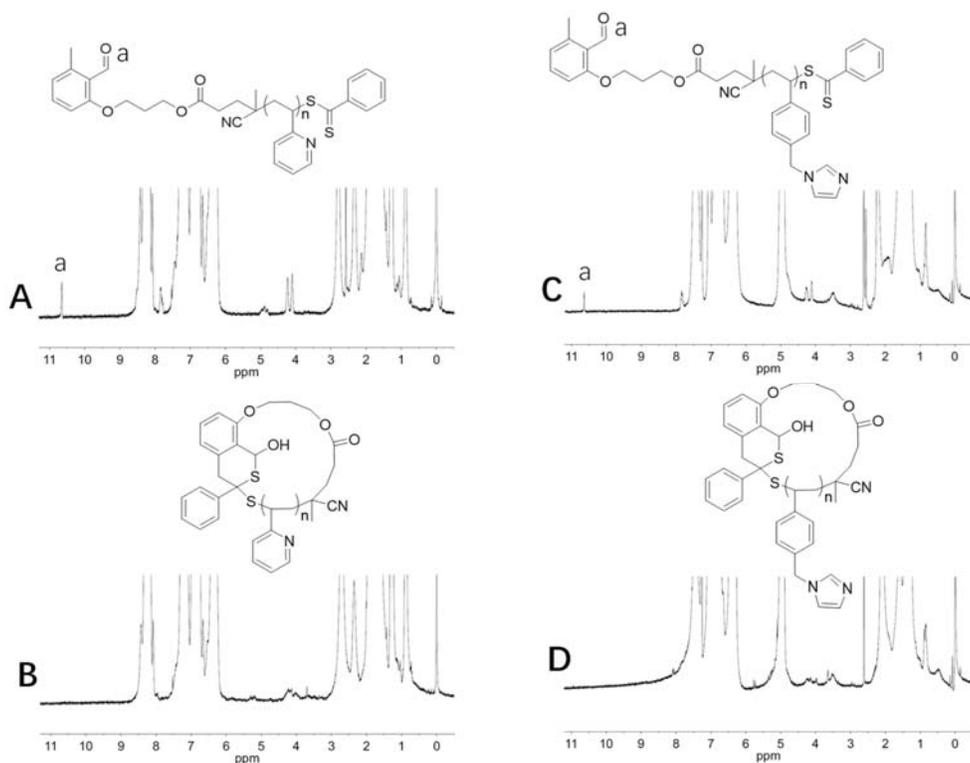


Figure S3 ^1H NMR spectra of linear P2VP (A), cyclic P2VP (B), linear PVBIIm (C) and cyclic PVBIIm (D) in CDCl_3 .

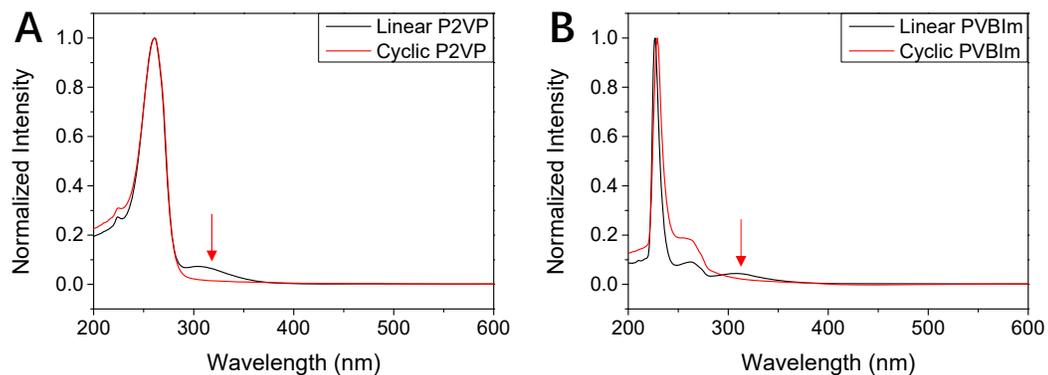


Figure S4 UV-vis spectra of (A) linear P2VP (black) and the resultant cyclic P2VP (red) in DCM, (B) linear PVBIIm (black) and the resultant cyclic PVBIIm (red) in DCM.

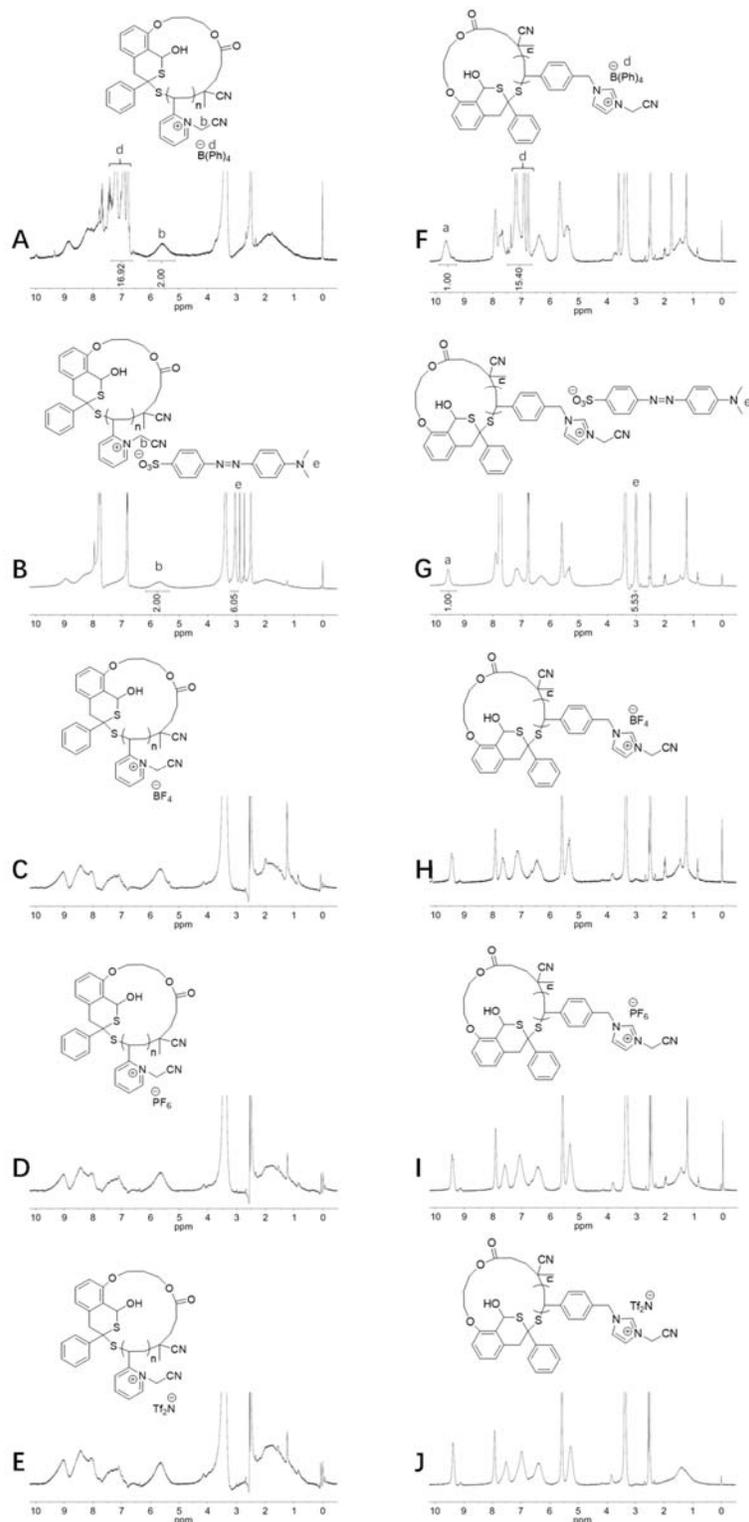


Figure S5 ^1H NMR spectra of CPILs: A) CP2VP-B(Ph) $_4$; B) CP2VP-MO; C) CP2VP-BF $_4$; D) CP2VP-PF $_6$; E) CP2VP-Tf $_2$ N; F) CPVBIIm-B(Ph) $_4$; G) CPVBIIm-MO; H) CPVBIIm-BF $_4$; I) CPVBIIm-PF $_6$; J) CPVBIIm-Tf $_2$ N; in DMSO- d_6 .

Table S1 The content of Nitrogen, Carbon, Hydrogen, Sulfur of CP2VP-Tf₂N and CPVBIIm-Tf₂N.

SAMPLE	DATA			
	N /%	C /%	H /%	S /%
CP2VP-Tf ₂ N	7.80	43.56	3.67	10.99
	7.81	43.66	3.57	10.60
	7.80	43.55	3.48	10.26
CPVBIIm-Tf ₂ N	10.58	37.73	2.35	11.02
	10.57	37.36	2.27	10.42
	10.67	37.35	2.22	10.60

Table S2 The content of Boron of CP2VP-BF₄ and CPVBIIm-BF₄.

Order number	CP2VP-BF ₄	CPVBIIm-BF ₄
Sample(g)	0.0455	0.0099
Volume of solution(mL)	50	50
Concentration of solution (mg/L)	2.710	6.31
Dilution rate	10	1
Concentration of Boron of sample (%)	2.978	3.187

1. Xie, Y.; Sun, Q.; Fu, Y.; Song, L.; Liang, J.; Xu, X.; Wang, H.; Li, J.; Tu, S.; Lu, X.; Li, J., *J. Mater. Chem. A* **2017**, *5*, 25594.
2. Tang, Q.; Wu, Y.; Sun, P.; Chen, Y.; Zhang, K., *Macromolecules* **2014**, *47*, 3775.