Enhanced Carrier Transport by Transition Metal Doping in WS₂ Field Effect Transistors

Maomao Liu,¹ Sichen Wei,² Simran Shahi,¹ Hemendra Nath Jaiswal,¹

Paolo Paletti,³ Sara Fathipour,³ Maja Remskar,⁴ Jun Jiao,⁵

Wansik Hwang, 6† Fei Yao, 2† and Huamin $Li^{1\dagger}$

¹ Department of Electrical Engineering, University at Buffalo, the State University of New York, Buffalo, NY 14260, USA

² Department of Materials Design and Innovation, University at Buffalo, the State University of New York, Buffalo, NY 14260, USA

³ Department of Electrical Engineering, University of Notre Dame, South Bend, IN 46556, USA ⁴ Department of Solid State Physics, Jozef Stefan Institute, Ljubljana, 1000, Slovenia

⁵ Center for Electron Microscopy and Nanofabrication, Portland State University, Portland, OR 97207, USA

⁶ Department of Materials Engineering, Korea Aerospace University, Goyang 10540, Republic of Korea

[†]Corresponding authors: <u>whwang@kau.ac.kr</u>, <u>feiyao@buffalo.edu</u>, <u>huaminli@buffalo.edu</u>

Abstract

High contact resistance is one of the primary concerns for electronic device applications of two-dimensional (2D) layered semiconductors. Here, we explore the enhanced carrier transport through metal-semiconductor interfaces in WS₂ field effect transistors (FETs) by introducing a typical transition metal, Cu, with two different doping strategies: (i) a "generalized" Cu doping by using randomly distributed Cu atoms along the channel and (ii) a "localized" Cu doping by adapting an ultrathin Cu layer at the metal-semiconductor interface. Compared to the pristine WS₂ FETs, both the generalized Cu atomic dopant and localized Cu contact decoration can provide a Schottky-to-Ohmic contact transition owing to the reduced contact resistances by 1 - 3 orders of magnitude, and consequently elevate electron mobilities by 5 - 7 times higher. Our work demonstrates that the introduction of transition metal can be an efficient and reliable technique to enhance the carrier transport and device performance in 2D TMD FETs.

Key words: 2D materials, WS₂, transition metal, transistor, carrier transport

Introduction

Tungsten disulfide (WS₂) with a semiconducting 2H phase is one of two-dimensional (2D) transition metal dichalcogenides (TMDs) exhibiting a series of unique properties, such as strong spin-orbit coupling, band splitting, and high nonlinear susceptibility¹⁻³. Especially for future nanoelectronic applications, WS₂ stands out as a promising channel material compared to other 2D semiconductors. For example, WS₂ has a direct bandgap of $1.4 - 2.0 \text{ eV}^{4-7}$ for the monolayer and an indirect bandgap of $1.2 - 1.3 \text{ eV}^{4-6}$ for the bulk crystals. The carrier mobility of WS₂ has been theoretically predicated up to ~5,300 cm²/Vs at 77 K⁸ and ~700 - 1,100 cm²/Vs at room temperature^{8,9}, which exceeds most of the commonly used semiconducting TMDs such as MoS₂

(340 cm²/Vs), MoSe₂ (240 cm²/Vs), WSe₂ (705 cm²/Vs), owing to the relatively small effective mass $(0.34m_0$ for electrons and $0.46m_0$ for holes, where m_0 is the free electron mass)⁷. Although the experimentally demonstrated electron mobilities, limited by Coulomb impurities, charge traps, surface defects and roughness, are much lower than the theoretical predication, new techniques have been developed to practically improve the mobility, for example, by exploiting h-BN¹⁰ or high- k^{11} dielectrics. For the application of field-effect transistors (FETs), monolayer WS₂ FETs are predicated to outperform other TMD FETs in terms of the on-state current density $(J_{D,on})$ for both p- and n-type transistors (~2,800 μ A/ μ m for the monolayer WS₂ versus 2,200 – 2,400 μ A/ μ m for the monolayer MoS₂, MoSe₂, and MoTe₂ FETs)¹¹. In addition to the carrier mobility, the pristine hysteresis width of WS₂ during reliability tests is the lowest compared to MoS₂, MoSe₂ and MoTe₂ FETs¹². The current on/off ratio at room temperature has been experimentally demonstrated up to ~10⁶ for the monolayer WS₂ FETs^{13,14} and to ~10⁸ for the multilayer WS₂ FETs¹⁵. A nearly ideal subthreshold swing (SS) of 70 mV/decade at room temperature has been demonstrated in a simple back-gated WS₂ FET through a 10-nm-thick SiO₂ layer¹⁶. To further break the thermal limit of the SS, various WS₂-based vertical transistors operated by a band-toband Zener tunneling mechanism have been investigated, including Gr/WS₂/Gr¹⁷ and WS₂/SnS₂¹⁸ van der Waals (vdW) heterostructures where Gr is the monolayer or multilayer graphene.

To fully explore the potential of WS_2 as the semiconducting channel material for the nanoelectronic device applications, the manipulation and improvement of its physical properties especially the carrier transport is highly required. For example, substitutional doping can occur as direct substitution of atoms in the lattice or into interstitial sites between existing atoms in the lattice. Owing to the unique nature of the vdW gaps, the atomic dopants in 2D materials can also intercalate between the layers, resulting in the changes in morphologic, electronic, optical,

magnetic, and catalytic properties etc^{19,20}. Compared to group XI elements such as Ag and Au which are widely used for wire-bonding, interconnects, and electrode materials, Cu as a representative transition metal has been demonstrated to effectively shift the Fermi level (E_F) up to the minima of the conduction band edge (E_C) and induce an n-type doping on black phosphorus (BP, or phosphorene), owing to its low electronegativity which can easily donate its 4s electron to BP^{21,22}. The Cu doping effect on other 2D materials, such as graphene²³, MoS₂^{24,25}, MoSe₂²⁵, Bi₂Se₃²⁶⁻²⁸, ZrSe₂²⁹, SnSe₂³⁰, and SnS³¹ etc. have also been investigated. Especially for WS₂, Cu can serve as an effective dopant to induce a microscopic ferromagnetic development which originates from the *p-d* hybridization between the Cu dopant and its neighboring S atoms and consequently the splitting of the energy levels near E_F^{32} . However, the impact of Cu doping on the electronic carrier transport of WS₂ has not been explored experimentally yet. Furthermore, considering the wide applications of Cu as transistor contacts and interconnects in current semiconductor technology, the metal-semiconductor contact condition at the Cu/WS₂ interface critically limits the carrier injection and collection efficiency during the transistor operation, especially for the extremely-scaled short-channel devices where the contacts play a more important role in the carrier transport and device performance^{33,34}. Therefore, an understanding of Cu/WS₂ contact can be one of the keys to achieve the full performance potential of the emerging WS₂ transistors.

In this work, we experimentally reveal the impact of Cu doping on the carrier transport of WS₂ through the metal-semiconductor interfaces, and statistically evaluate the transistor performance. Specifically, Cu as the representative transition metal is introduced using two different techniques. In the Cu-doping technique, Cu is randomly distributed into the WS₂ crystals during the synthesis and acts as "generalized" n-type atomic dopants within the channel. Whereas

in the Cu-contact technique, Cu is deposited as an ultrathin contact decoration layer on the WS_2 surface and provides a "localized" doping effect only at the metal-semiconductor interface. A schematic illustration of these two doping strategies and the corresponding electron transport through the metal-semiconductor interfaces is shown in Fig. 1. Compared to the pristine WS_2 FETs, both the Cu-doped and Cu-contact WS₂ FETs show a clear Schottky-to-Ohmic contact improvement, due to a significant reduction of the Schottky barrier (about 28% to 60% lower) and thus the contact resistance (over 1 to 3 orders of magnitude lower). The enhanced carrier transport can be attributed to the charge transfer with Cu which changes the Fermi level (by ~0.11 eV) of WS_2 along the channel for the Cu-doped devices, or reduces the workfunction of Cu (by ~0.41 eV) at the metal-semiconductor interface for the Cu-contact devices. In addition, we carry out a statistical study by testing about 30 devices for each type of the WS₂ FETs, and demonstrate the improvement of the transistor performance including field effect mobility (μ_{FE}), on/off ratio, $J_{D,on}$, and SS. Our results suggest that, owing to the doping effect, the transition metal Cu either as the generalized atomic dopant or the localized contact decoration can effectively enhance the carrier transport and device performance for 2D semiconducting WS₂.

Results

Output characteristics. For a comparative study, we fabricate three types of typical global-backgate transistors: pristine, Cu-doped, and Cu-contact WS₂ FETs. Compared to the pristine WS₂ FET which is the control sample in this work, the Cu-doped WS₂ FETs include Cu as the generalized atomic dopants during the WS₂ crystal synthesis. Both the pristine and Cu-doped WS₂ FETs have Ti/Au (10 nm/100 nm) deposited as source and drain electrodes. The Cu-contact WS₂ FETs have Cu/Ti/Au (2 nm/10 nm/100 nm) as the electrodes on the pristine WS₂ flakes where the thin Cu layer serves as a localized contact decoration at the metal-semiconductor interface. A comparison of drain current density versus drain voltage (J_D - V_D) output characteristics at various gate voltages (V_G) for all three types of the devices is performed at room temperature, as shown in **Fig. 2**. The pristine WS₂ FET possesses non-linear current-voltage (IV) characteristics at low V_D , suggesting a large Schottky barrier at the metal-semiconductor contacts. In contrast, the Cu-doped WS₂ FET indicates a linear IV relation and thus an Ohmic contact at low V_D . Meanwhile, current saturation is clearly obtained in the Cu-doped device, for example, at V_D of 2 V for V_G of 30 V. Similar to the Cu-doped WS₂ FET, the Cu-contact WS₂ FET also shows the Ohmic contact and current saturation, but the maximum $J_{D,on}$ is increased significantly up to 42 μ A/ μ m at V_D of 5 V and V_G of 30 V.

To further understand the carrier transport properties, the output characteristics at the on state ($V_G = 30$ V) are replotted in various analytical models, as shown in **Fig. S1** in Supplementary Information. In the log(J_D) versus $V_D^{1/2}$ curves (see **Fig. S1** (a)), a linear dependence is found at $V_D > 2$ V for all three types of the devices, suggesting that the carrier injections subject to the Schottky emission at room temperature³⁵ which is described as

$$J_D \propto exp\left[\frac{-\left(\phi_b - \sqrt{\frac{q^3 V_D}{L\pi \varepsilon_0 \varepsilon_r}}\right)}{k_B T}\right]$$
(1).

Here ϕ_b is the barrier height, *q* is the electronic charge, ε_0 is the permittivity of the vacuum, ε_r is the relative permittivity of WS₂, *L* is the channel length, k_B is the Boltzmann constant, and *T* is the temperature. Due to the identical channel material, both the pristine and Cu-contact devices possess the similar slopes (0.29 and 0.31) compared to that of the Cu-doped device (0.03). The smaller slope of the Cu-doped device also indicates a larger ε_r after the generalized Cu doping in WS₂. Equation 1 can be further modified as

$$J_D \propto \frac{V_D}{L} exp\left[\frac{-\left(\phi_b - \sqrt{\frac{q^3 V_D}{L\pi\varepsilon_0 \varepsilon_r}}\right)}{k_B T}\right]$$
(2),

and a linear dependence of $\ln(J_D/V_D)$ on $V_D^{1/2}$ (see **Fig. S1 (b)**) suggests the dominance of a trapinduced Poole-Frenkel (PF) emission. To better understand the impact of the traps on the carrier transport, the data is replotted in the $\log(J_D)$ versus $\log(V_D)$ curves (see **Fig. S1 (c)**). A current saturation occurs at $V_D > 2$ V for all the devices, implying a transition of the carrier transport from trap-filled limited (TFL) mode to space-charge limited (SCL) mode³⁶, and the current can be described as

$$J_D \propto \frac{1}{q^{m-2}} \left(\frac{2m-1}{m}\right)^m \left[\frac{\varepsilon_0 \varepsilon_r(m-1)}{N_t m}\right]^{m-1} \frac{V_D^m}{L^{2m-1}} \tag{3}$$

where *m* is the power factor determined from the linear slope of the log(J_D) versus log(V_D) curves, and N_i is the trap density. In the TFL region ($V_D < 2$ V), the injected carriers are increased with V_D but not enough to fill the traps which have an exponential distribution^{37,38}. In the SCL region ($V_D > 2$ V), all the traps are filled by the injected carriers, so the subsequently injected carriers are free from the traps and fully controlled by the space charges which limit further injection of the free carriers. The Cu-contact device has a slope (0.66) which is similar with the pristine one (0.62) but different from the Cu-doped one (0.06) in the trap-free SCL region. This result indicates that the SCL current is mainly determined by the channel material rather than the contact condition. Whereas in the TFL region, both the Cu-doped and Cu-contact devices show similar slopes (1.08 and 1.02) which are different from the pristine one (2.16), suggesting the impact of the Cu doping, either along the channel or at the contact interface, on the TFL current. In the $|(J_D/V_D^2)$ versus $1/V_D$ curves (see **Fig. S1 (d)**), the logarithmic dependence implies that the carrier transport is dominated by direct tunneling at the low temperature or thermionic emission (TE) at the high temperature. It can be predicted that by further increasing V_D , a linear decay would occur which corresponds to the Fowler-Nordheim (FN) tunneling through a triangular tunneling barrier and can be described by the following equation

$$J_D \propto \frac{q^3 m_0 V_D^2}{\phi_b L^2 m^*} exp\left[\frac{-8\pi\sqrt{2m^*}\phi_b^{\frac{3}{2}L}}{3hqV_D}\right]$$
(4).

Here m_0 is the free electron mass, m^* is the effective mass of electrons in WS₂, and *h* is the Planck's constant. To prevent the possible damage from the current-induced joule heating, in this work we limit the sweeping range of V_D only up to 5 V so the FN tunneling is excluded. The direct tunneling through a trapezoidal tunneling barrier can be further confirmed by plotting the $\ln(J_D/V_D^2)$ versus $\ln(1/V_D)$ curves (see Fig. S1 (e)), based on the following equation

$$J_D \propto \frac{q^2 V_D \sqrt{m_0 \phi_b}}{h^2 L} exp\left[\frac{-4\pi \sqrt{m_0 \phi_b}L}{h}\right]$$
(5).

The similar linear slopes of both the Cu-doped and Cu-contact devices indicate the comparable trapezoidal barrier heights at low V_D . Based on these analyses, we can conclude that the carrier injection at the low V_D ($V_D < 2$ V) is predominated by the thermionic emission or direct tunneling for all the devices, and the current is mainly attributed to the TFL current (see Fig. S1 (f)). At the high V_D ($V_D > 2$ V), the carrier injection is governed by the Schottky emission and the current is changed to the SCL current. The PF emission occurs at the low V_D for both the pristine and Cu-doped devices, but at the high V_D for the Cu-contact one.

Temperature dependence of the J_D - V_D output characteristics is measured from 218 to 298 K for each type of the devices, and a linear relation in the Arrhenius plot, i.e., $\ln(I_D/T^2)$ versus q/k_BT , is obtained for various V_G , as shown in Fig. 3 (a). Our previous work has demonstrated a gate-dependent Schottky barrier modulation for 2D TMDs³⁹ and the value of ϕ_b for a given V_D is estimated from the slope of each curve, as shown in Fig. 3 (b). At zero V_G or the equilibrium state, the value of ϕ_b is obtained as 166, 59, and 0 meV for the pristine, Cu-doped, and Cu-contact WS₂

devices, respectively. As V_G increases, a transition between the linear and exponential decay is observed, which indicates a flat-band condition across the metal-semiconductor interface. The carrier transport is dominated by the TE when $V_G < V_{FB}$, and by the direct tunneling or FN tunneling when $V_G > V_{FB}$, where V_{FB} is the flat-band gate voltage. The value of ϕ_b at V_{FB} , known as the intrinsic barrier height (ϕ_{b0}), can be used to estimate the band offsets between the metal and semiconductors. To further eliminate the effect from the applied V_D , ϕ_{b0} is plotted as a function of V_D , and the values at zero V_D are estimated based on a linear fit for each type of the devices, as shown in **Fig. 3** (c). Compared to the pristine WS₂ FET ($\phi_{b0} = 123$ meV), the value of ϕ_{b0} is reduced to 89 meV for the Cu-doped WS₂ FET (i.e., ~28% reduction) and to 50 meV for the Cucontact WS₂ FET (i.e., ~60% reduction), suggesting a significant improvement of the metalsemiconductor contact condition. Our results are also compared with the theoretical barrier height calculated by density functional theory (DFT) for the monolayer WS₂ with various metal contacts⁴⁰, as shown in **Fig. 3** (d). The values obtained in this work are about one order of magnitude lower due to the smaller bandgap in the multilayer structure.

Based on the extracted ϕ_{b0} at V_{FB} and ϕ_b at zero V_G , the band diagram of the metalsemiconductor interface can be estimated quantitatively, as shown in **Fig. 4**. Assuming that the work function of Ti (Φ_{Ti}) is 4.33 eV, the electron affinity for the pristine and Cu-doped WS₂ ($\chi_{WS2,pri}$ and $\chi_{WS2,Cu}$) can be calculated through ϕ_{b0} at V_{FB} as 4.21 and 4.24 eV, respectively. These two values are approximately identical as ideally the electron affinity is independent of the doping level. Therefore, we take their average value (4.23 eV) for the following discussion. At the equilibrium condition, the workfunction of the pristine and Cu-doped WS₂ ($\Phi_{WS2,pri}$ and $\Phi_{WS2,Cu}$) can be estimated as 4.4 and 4.29 eV, respectively. Therefore, the Schottky barrier lowering in the Cu-doped WS₂ FET can be interpreted by the electron doping which shifts the position of E_F close to E_C by about 0.11 eV (from 166 meV in the pristine WS₂ to 59 meV in the Cu-doped WS₂). Such n-type doping effect by Cu has also been reported on other 2D semiconducting materials^{22,29}. As a comparison, the Schottky barrier lowering in the Cu-contact WS₂ FET is more complicated, which is mainly attributed to a synergetic interaction of exchange repulsion, covalent bonding, and charge redistribution including electron accumulation in the gap region, depletion near the interface, as well as charge density oscillations within both the metal and semiconductor⁴¹. Specifically, based on the average χ_{WS2} (4.23 eV) and ϕ_{b0} (50 meV) at V_{FB} , the work function of Cu (Φ_{Cu}) is estimated as 4.28 eV which is lower than the known value (4.69 eV, average of Cu (100), (110), and (111)) by about 0.41 eV. This unique decrease of Φ_{Cu} is in a good agreement with the previously theoretical predication, and can be attributed to the generation of a net interfacial dipole induced by the complex charge redistribution at the interface between Cu and group-VI TMDs⁴¹. Meanwhile, although the WS₂ bulk body remains pristine, $\Phi_{WS2,pri}$ at the interface is also reduced by contacting Cu due to the charge redistribution and surface dipole generation⁴¹. Thus, being different from the generalized Cu doping along the channel, the localized Cu contact leads to a strong n-type doping only at the contact surface, and gives rise to the zero ϕ_b at zero V_G . Besides, previous works have experimentally and theoretically demonstrated the great potential of WS₂ and other 2D TMDs acting as the Cu diffusion barrier^{42,43}, which also evidence that the doping effect induced by the Cu contact can be confined only at the contact interface.

Transfer characteristics. The comparison of J_D - V_G transfer characteristics at room temperature is shown in **Fig. 5** (a), from which it can be seen that the transistor performance, such as $J_{D,on}$, μ_{FE} , and SS are improved by introducing Cu as either the atomic dopants or the contact decoration. For

example, the maximum $J_{D,on}$ of the pristine WS₂ FET at V_D of 1 V is 0.94 µA/µm, and this value is increased by about 5 times in the Cu-doped WS₂ FET (4.52 µA/µm) and by about 19 times in the Cu-contact WS₂ FET (17.73 µA/µm). The highest μ_{FE} for the Cu-doped WS₂ FET is 21.9 cm²/Vs and for the Cu-contact WS₂ FET is 26.3 cm²/Vs, which are more than 4 times larger than that of the pristine WS₂ device (4.9 cm²/Vs). The lowest SS of the Cu-contact WS₂ FET is 0.5 V/decade which is about 70% reduced than that of the pristine and Cu-doped WS₂ devices. It is also noted that, even with the Cu atomic dopants in the semiconductor channel or the Cu contact decoration at the metal-semiconductor interface, no extra defects or traps are introduced in the devices. The effective trap density (n_i) can be estimated from the hysteresis of the charge neutral point (ΔV_{CNP}) as $n_t = C_{ox} \Delta V_{CNP}/q$, where C_{ox} is the oxide capacitance (3.84 × 10⁻⁸ F/cm² for a 90nm-thick SiO₂ layer). Because all three types of the devices have the comparable values of ΔV_{CNP} from 13 to 17 V, the calculated n_t ranges from 3 × 10¹² to 4 × 10¹² cm⁻².

Based on the transfer characteristics, transconductance (g_m) is calculated and their temperature dependence indicates a metal-insulator transition (MIT) phenomenon, as shown in **Fig. 5 (b-d)**. The gate voltage required for inducing the MIT ($V_{G,MIT}$) in the pristine WS₂ FET is reduced from about 10 to 5 and 0 V by introducing Cu as the atomic dopant and contact decoration, respectively. The shift of $V_{G,MIT}$ to the negative V_G indicates a Cu-induced n-type doping effect which is consistent with our previous discussion, and can be further interpreted by the frameworks of thermally activated and variable-range hopping (VRH) models¹⁴. For example, activation energy (E_a) which is corresponding to the thermal activation of charge carriers into the conduction band is extracted by fitting the sheet conductivity (G) with the expression $G(T) = G_0 \exp(-E_a/k_BT)$, where G_0 is the constant. A plot of $\ln(G)$ versus 1000/T at the on state for each type of the devices is shown in **Fig. 5** (e). The values of E_a are extracted from the linear fit of the plots, and their

dependence on V_G across the subthreshold and superthreshold regions (-10 to 30 V) are calculated, as shown in Fig. 5 (f). A clear reduction of E_a can be found in the Cu-doped and Cu-contact WS₂ FETs, which is consistent with the behavior of the V_G-dependent ϕ_b (see Fig. 3 (b)). Assuming the dependence of E_a on V_G equals to the dependence of E_F on V_G , the density of the states (DOS) below the conduction band edge can be extracted from the expression $dE_F/dV_G = dE_a/dV_G =$ $C_{ox}/(C_{ox}+C_t)$, where $C_t = e^2 DOS$ is the quantum capacitance. Figure 5 (g) shows the calculated DOS as a function of V_G across the insulating and metallic regimes in a comparison with the theoretically anticipated value of DOS (DOS_{2D,theory}) which equals to $2.85 \times 10^{14} \text{ eV}^{-1} \text{cm}^{-2}$ at the effective mass $m^* = 0.34 m_0^{7,14}$. The average DOS is increased from 10^{12} to $10^{14} \text{ eV}^{-1} \text{ cm}^{-2}$ when V_G increases from the subthreshold region to the superthreshold region. Based on the VRH model⁴⁴⁻⁴⁶, the localization length L_{local} is calculated as $L_{local} = (13.8/k_B T_0 DOS)^{1/2}$, where T_0 is the temperature coefficient to describe the temperature dependence of G as $G(T) \sim \exp(-T_0/T)^{1/3}$. Figure 5 (h) shows that, with the increasing V_G , the electron delocalization occurs and the localization length can reach up to about hundreds of nanometers. Compared to the pristine WS2 FET, both the Cu doping and Cu contact can initiate the delocalization process at lower V_G and potentially benefit the low-power energy-efficient device applications.

Being consistent with the MIT behavior, the electron currents (e.g., at $V_G = 30$ V or the on state) for all three types of the devices decrease with *T* from 218 to 298 K, whereas the hole currents (e.g., at $V_G = -30$ V or the off state) increase with *T*, as shown in **Fig. 6** (a). The *T*-dependent electron current variation can be attributed to the dominance of lattice scattering which decreases μ_{FE} with the increasing *T*. Here μ_{FE} is defined as $(L/W)(1/C_{ox})(1/V_D)g_m$ where *L* and *W* are the channel length and width, respectively. It is found that μ_{FE} follows a power-law relation with *T* as $\mu_{FE} \sim T^{-\gamma}$, where γ is the temperature damping factor and calculated to be 0.7, 0.72, and 1.66 for

the pristine, Cu-doped, and Cu-contact WS₂ FETs, respectively, as shown in **Fig. 6 (b)**. Our results show a good agreement with previous reports on the WS₂ FETs where the value of γ ranges from 0.73 to 1.75¹⁴. On the other hand, the hole currents increase with *T* due to the thermal energy assisted generation of the minority charge carriers which contribute to the leakage current at the off state.

To further confirm the enhancement of the carrier injection through the metalsemiconductor contact interface, we fabricate transmission line measurement (TLM) devices to extract the contact resistance (R_c) as a function of V_G for each type of the devices, as shown in Fig. **6** (c). At the on state, R_c is calculated as 2.2×10^9 , 7.4×10^6 , and $1 \times 10^6 \Omega \mu m$ for the pristine, Cu-doped, and Cu-contact WS₂ FETs, respectively, suggesting a significant improvement (a reduction by about three orders of magnitude) of the carrier injection by introducing Cu. Even at the off state, R_c also shows a reduction by one order of the magnitude with either the Cu atomic doping or Cu contact decoration. Our results are also benchmarked as a function of the channel resistivity, $\rho_{2D,channel} = (R_{total}-R_c)W/L^{34}$, in a comparison with the merit of the monolayer WS₂¹⁴ and few-layer Cl-doped WS₂⁴⁷, as shown in Fig. **6** (d). Here R_{total} is the total resistance measured as V_D/J_D . It is noted that both the Cu atomic doping and Cu contact decoration can provide the lowest R_c/R_{total} ratio which is required to be 20% by the International Technology Roadmap for Semiconductors (ITRS) in 2015.

Discussion

To eliminate the possible deviation among the devices due to the difference in terms of the flake uniformity and contaminations etc., a statistical analysis based on about 30 devices of each type is carried out at room temperature, which proves the reliability and accuracy of our results.

Under the same measurement condition, the J_D - V_G transfer characteristics of all the pristine, Cudoped, and Cu-contact WS₂ FETs are compared, as shown in **Fig. S2** in Supplementary Information. The statistical analysis of the transistor performance, including μ_{FE} , $J_{D,on}$, on/off ratio and SS, are summarized in **Fig. 7**. Both the median and mean values show a clear improvement by introducing the Cu atomic doping and Cu contact decoration. For example, compared to the pristine WS₂ FETs, the mean values of μ_{FE} , $J_{D,on}$, and on/off ratio in the Cu-doped WS₂ FETs are about 5, 4, and 2 times increased, respectively, and the mean value of SS is over 30% reduced. The Cu-contact WS₂ FETs show an even better performance, including about 7 times increases in μ_{FE} and $J_{D,on}$, 6 times increases in on/off ratio, and 26% reduction in SS.

In conclusion, we carry out a comparative study among the pristine, Cu-doped, and Cucontact WS₂ FETs, and demonstrate that both the Cu atomic doping and Cu contact decoration can efficiently enhance the carrier transport in WS₂ FETs. The charge transfer with Cu can effectively change the Fermi level of WS₂ along the channel for the Cu-doped devices, and considerably reduce the workfunction of Cu at the metal-semiconductor interface for the Cu-contact devices. The Schottky-to-Ohmic contact transition with the lowered contact barrier can enhance the carrier injection through the metal-semiconductor interface, and give rise to the drastic reduction of R_c . The statistical analysis shows a significant improvement of the carrier transport as well as the device performance in terms of μ_{FE} , $J_{D,on}$, on/off ratio, and SS.

Methods

Material synthesis and characterization. Both the pristine WS_2 and Cu-doped WS_2 crystals were grown by chemical vapor transport (CVT) reaction using iodine as a transport agent. A slow growth rate from the vapor phase ensures an extremely low density of structural defects in crystals, based on our previous studies⁴⁸⁻⁵¹. Briefly, a silica ampoule containing WS₂ powder and iodine were evacuated and sealed at a pressure of 10^{-3} Pa to synthesis the pristine WS₂. The transport reaction ran at 1060 K with a temperature gradient of 5.6 K/cm in a two-zone furnace. After three weeks of growth, the silica ampoule was slowly cooled to room temperature with a controlled cooling rate of 15 K per hour. Approximately a few percent of the starting material were transported by the reaction to form nanotube structures, and the rest of the transported material grows thin layered crystals. For the Cu-doped WS₂, the growth followed the same procedure but a small amount of Cu foil (0.5% by nominal weight) were added in the ampoule. Then, both the pristine and Cu-doped WS₂ flakes were mechanically exfoliated from the synthesized crystals and transferred onto n-type Si substrates (0.001-0.005 Ω cm) which had a 90-nm-thick SiO₂ layer on the top. An energy-dispersive X-ray spectroscopy (EDX) characterization was carried out to verify the existence of Cu in the synthesized WS_2 flakes, as shown in Fig. S3 (a) and (b) in Supplementary Information. The Cu-doped WS₂ showed a uniform distribution of Cu, and the weight ratio (or atomic ratio) of W/S/Cu was measured as 0.67/0.22/0.03 (or 0.30/0.57/0.04), in addition to O, C, and I in the sample. As a comparison, the pristine WS₂ has the weight ratio (or atomic ratio) of W/S as 0.71/0.28 (or 0.30/0.67). Both the synthesized pristine and Cu-doped WS₂ were also investigated by Raman spectroscopy, as shown in Fig. S3 (c-e) in Supplementary Information. Compared to the monolayer WS₂, both the peak positions and intensity ratios⁵² indicated the few-layer structures of the pristine and Cu-doped WS₂ flakes in this work. Moreover, the E_{2g}^{1} peaks for the pristine and Cu-doped WS₂ were located consistently at around 357 cm⁻¹, suggesting a negligible effort of Cu atomic doping on the in-plane vibrational mode of WS₂. In contrast, the A_g^1 peak was found to be softened (red-shifted) from 422.5 to 421.9 cm⁻¹ due to the Cu-induced electron doping. The insensitivity of the E^{1}_{2g} peak and the pronounced red-shift of the

 A_{g}^{1} peak were consistent with the sign of electron doping on other TMD semiconductors such as MoS_{2}^{53} .

Device fabrication and measurement. For a comparative study, we fabricated three types of typical global-back-gate transistors: the pristine, Cu-doped, and Cu-contact WS₂ FETs. Both the pristine and Cu-doped WS₂ FETs had Ti/Au (10 nm/100 nm) deposited as source and drain electrodes. The Cu-contact WS₂ FETs had Cu/Ti/Au (2 nm/10 nm/100 nm) as the electrodes on the pristine WS₂ flakes where the thin Cu layer serves as a contact decoration at the metal-semiconductor interface. All the pristine and Cu-doped WS₂ flakes had the similar thickness (*t*) ranging from 4 to 8 nm, measured by atomic force microscopy (AFM). The value of *L* was set as 1 µm for all the FETs but the values of *W* were varying for each device. The AFM data of a selected Cu-doped WS₂ FET was shown in Fig. S4 in Supplementary Information, where *t*, *L*, and *W* were measured to be 6 nm, 1 µm, and 4 µm, respectively. The electrical characterization was performed by measuring drain current (*I*_D) at various *V*_D and *V*_G, and the value of *I*_D was further normalized to J_D ($J_D = I_D/W$) for performance comparison. The room-temperature measurement was performed in a dark N₂-filled ambient environment, and the low-temperature measurement was carried out in a vacuum environment (~2 mTorr).

Data availability

The data that support the findings of this study are available from the corresponding author on reasonable request.

References

- Yang, L. et al. Long-lived nanosecond spin relaxation and spin coherence of electrons in monolayer MoS₂ and WS₂. *Nat. Phys.* **11**, 830–834 (2015).
- Zeng, H. *et al.* Optical signature of symmetry variations and spin-valley coupling in atomically thin tungsten dichalcogenides. *Sci. Rep.* 3, 1608 (2013).
- 3. Britnell, L. *et al.* Strong light-matter interactions in heterostructures of atomically thin films. *Sci.* **340**, 1311–1314 (2013).
- Braga, D., Lezama, I. G., Berger, H. & Morpurgo, A. F. Quantitative determination of the band gap of WS₂ with ambipolar ionic liquid-gated transistors. *Nano Lett.* **12**, 5218–5223 (2012).
- 5. Gusakova, J. *et al.* Electronic properties of bulk and monolayer TMDs: Theoretical study within DFT framework (GVJ-2e method). *Phys. Status Solidi (a)* **214**, 1700218 (2017).
- Klein, A., Tiefenbacher, S., Eyert, V., Pettenkofer, C. & Jaegermann, W. Electronic band structure of single-crystal and single-layer WS₂: Influence of interlayer van der Waals interactions. *Phys. Rev. B* 64, 205416 (2001).
- Liu, L., Kumar, S. B., Ouyang, Y. & Guo, J. Performance limits of monolayer transition metal dichalcogenide transistors. *IEEE Trans. Electron Devices* 58, 3042–3047 (2011).
- Chen, K.-T. & Chang, S.-T. How high can the mobility of monolayer tungsten disulfide be? *Vacuum* 140, 172–175 (2017).
- Zhang, W., Huang, Z., Zhang, W. & Li, Y. Two-dimensional semiconductors with possible high room temperature mobility. *Nano Res.* 7, 1731–1737 (2014).
- Iqbal, M. W. *et al.* High-mobility and air-stable single-layer WS₂ field-effect transistors sandwiched between chemical vapor deposition-grown hexagonal BN films. *Sci. Rep.* 5, 10699 (2015).

- Cui, Y. *et al.* High-performance monolayer WS₂ field-effect transistors on high-κ dielectrics, *Adv. Mater.* 27, 5230–5234 (2015).
- Illarionov, Y. Y. *et al.* Reliability of next-generation field-effect transistors with transition metal dichalcogenides. 2018 IEEE Int. Reliab. Phys. Symp. (IRPS) (2018).
- Yue, Y. *et al.* Two-dimensional high-quality monolayered triangular WS₂ flakes for fieldeffect transistors. *ACS Appl. Mater. Interfaces* 10, 22435–22444 (2018).
- Ovchinnikov, D., Allain, A., Huang, Y.-S., Dumcenco, D. & Kis, A. Electrical transport properties of single-layer WS₂. *ACS Nano* 8, 8174–8181 (2014).
- Liu, X. *et al.* High performance field-effect transistor based on multilayer tungsten disulfide. *ACS Nano* 8, 10396–10402 (2014).
- Kumar, J., Kuroda, M. A., Bellus, M. Z., Han, S.-J. & Chiu, H.-Y. Full-range electrical characteristics of WS₂ transistors. *Appl. Phys. Lett.* **106**, 123508 (2015).
- Georgiou, T. *et al.* Vertical field-effect transistor based on graphene–WS₂ heterostructures for flexible and transparent electronics. *Nat. Nanotechnol.* 8, 100–103 (2012).
- Wang, J. *et al.* Vertical WS₂/SnS₂ van der Waals heterostructure for tunneling transistors. *Sci. Rep.* 8, 17755 (2018).
- Tedstone, A. A., Lewis, D. J. & Obrien, P. Synthesis, properties, and applications of transition metal-doped layered transition metal dichalcogenides. *Chem. Mater.* 28, 1965– 1974 (2016).
- Luo, P. *et al.* Doping engineering and functionalization of two-dimensional metal chalcogenides. *Nanoscale Horiz.* 4, 26–51 (2019).

- Sun, H., Shang, Y., Yang, Y. & Guo, M. Realization of n-type semiconducting of phosphorene through surface metal doping and work function Study. *J. Nanomater.* 2018, 6863890 (2018).
- Koenig, S. P. *et al.* Electron doping of ultrathin black phosphorus with Cu adatoms. *Nano Lett.* 16, 2145–2151 (2016).
- 23. Liu, Y. *et al.* Effect of Cu-doped graphene on the flammability and thermal properties of epoxy composites. *Composites, Part B.* **89**, 108–116 (2016).
- Yun, W. S. & Lee, J. D. Unexpected strong magnetism of Cu doped single-layer MoS₂ and its origin. *Phys. Chem. Chem. Phys.* 16, 8990–8996 (2014).
- Hu, A.-M., Wang, L.-L., Xiao, W.-Z. & Meng, B. Electronic structures and magnetic properties in Cu-doped two-dimensional dichalcogenides. *Phys. E* 73, 69–75 (2015).
- Koski, K. J. *et al.* Chemical intercalation of zerovalent metals into 2D layered Bi₂Se₃ nanoribbons. *J. Am. Chem. Soc.* **134**, 13773–13779 (2012).
- Koski, K. J. *et al.* High-density chemical intercalation of zero-valent copper into Bi₂Se₃ nanoribbons. *J. Am. Chem. Soc.* **134**, 7584–7587 (2012).
- Chen, K. P., Chung, F. R., Wang, M. & Koski, K. J. Dual element intercalation into 2D layered Bi₂Se₃ nanoribbons. *J. Am. Chem. Soc.* 137, 5431–5437 (2015).
- Muhammad, Z. *et al.* Electron doping induced semiconductor to metal transitions in ZrSe₂ layers via copper atomic intercalation. *Nano Res.* 11, 4914–4922 (2018).
- 30. Wu, X. *et al.* Half-metals and half-semiconductors in a transition metal doped SnSe₂ monolayer: a first-principles study. *RSC Adv.* **7**, 44499–44504 (2017).
- Wang, F. *et al.* First-principles investigations of magnetic semiconductors: An example of transition metal decorated two-dimensional SnS monolayer. *Nanomater.* 8, 789 (2018).

- 32. Zhao, X., Dai, X. & Xia, C. Magnetic properties of two nearest Cu-doped monolayer WS₂:
 A first-principles study. *Solid State Commun.* 217, 66–69 (2015).
- Franklin, A. D. Nanomaterials in transistors: From high-performance to thin-film applications. *Sci.* 349, 2750 (2015).
- Allain, A., Kang, J., Banerjee, K. & Kis, A. Electrical contacts to two-dimensional semiconductors. *Nat. Mater.* 14, 1195–1205 (2015).
- Kong, Z., Liu, D., He, J. & Wang, X. Electrode buffer layers producing high performance nonvolatile organic write-once-read-many-times memory devices. *RSC Adv.* 7, 13171– 13176 (2017).
- Shin, Y. S. *et al.* Mobility engineering in vertical field effect transistors based on van der Waals heterostructures. *Adv. Mater.* **30**, 1704435 (2018).
- Qu, D., Liu, X., Ahmed, F., Lee, D. & Yoo, W. J. Self-screened high performance multilayer MoS₂ transistor formed by using a bottom graphene electrode. *Nanoscale* 7, 19273– 19281 (2015).
- Ghatak, S. & Ghosh, A. Observation of trap-assisted space charge limited conductivity in short channel MoS₂ transistor. *Appl. Phys. Lett.* 103, 122103 (2013).
- 39. Li, H.-M. *et al.* Metal-semiconductor barrier modulation for high photoresponse in transition metal dichalcogenide field effect transistors. *Sci. Rep.* **4**, 4041 (2014).
- Guo, Y., Liu, D. & Robertson, J. 3D behavior of Schottky barriers of 2D transition-metal dichalcogenides. *ACS Appl. Mater. Interfaces* 7, 25709–25715 (2015).
- Helfrecht, B. A., Guzman, D. M., Onofrio, N. & Strachan, A. H. Interactions between copper and transition metal dichalcogenides: A density functional theory study. *Phys. Rev. Mater.* 1, 034001 (2017).

- 42. Smithe, K. K. H., Zhu, Z., Bailey, C. S., Pop, E. & Yoon, A. Investigation of monolayer MX₂ as sub-nanometer copper diffusion barriers. *2018 IEEE Int. Reliab. Phys. Symp. (IRPS)* (2018).
- Lo, C.-L. *et al.* Studies of two-dimensional h-BN and MoS₂ for potential diffusion barrier application in copper interconnect technology. *npj 2D Mater. Appl.* 1, 42 (2017).
- 44. Jonscher, A. Electronic processes in non-crystalline materials. *Thin Solid Films* 11, 439–440 (1972).
- 45. Keuls, F. W. V., Hu, X. L., Jiang, H. W. & Dahm, A. J. Screening of the Coulomb interaction in two-dimensional variable-range hopping. *Phys. Rev. B* 56, 1161–1169 (1997).
- Ghatak, S., Pal, A. N. & Ghosh, A. Nature of electronic states in atomically thin MoS₂ fieldeffect transistors. *ACS Nano* 5, 7707–7712 (2011).
- 47. Yang, L. *et al.* Chloride molecular doping technique on 2D materials: WS₂ and MoS₂. *Nano Lett.* 14, 6275–6280 (2014).
- 48. Hwang, W. S. *et al.* Transistors with chemically synthesized layered semiconductor WS₂
 exhibiting 10⁵ room temperature modulation and ambipolar behavior. *Appl. Phys. Lett.* 101, 013107 (2012).
- 49. Remskar, M. *et al.* New crystal structures of WS₂: Microtubes, ribbons, and ropes. *Adv. Mater.* 10, 246–249 (1998).
- Virsek, M., Jesih, A., Milosevic, I., Damnjanovic, M. & Remskar, M. Raman scattering of the MoS₂ and WS₂ single nanotubes. *Surf. Sci.* 601, 2868–2872 (2007).
- Krause, M. *et al.* Diameter and morphology dependent Raman signatures of WS₂ nanostructures. *ChemPhysChem* 10, 2221–2225 (2009).

- Berkdemir, A. *et al.* Identification of individual and few layers of WS₂ using Raman spectroscopy. *Sci. Rep.* 3, 1755 (2013).
- Chakraborty, B. *et al.* Symmetry-dependent phonon renormalization in monolayer MoS₂ transistor. *Phys. Rev. B* 85, 161403(R) (2012).

Acknowledgements

This research was partially funded by the National Science Foundation (NSF) under Grant No. ECCS-1745621 and ECCS-1944095.

Author contributions

W.H., F.Y., and H.L. conceived and supervised the project. M.R. synthesized the 2D crystals. P.P. and S.F. prepared the 2D thin flakes. W.H. fabricated the 2D transistor devices. M.L. and P.P. fabricated the 2D TLM devices. M.L., S.S., H.N.J., and H.L. performed the electrical characterizations. M.L., S.W., F.Y., and J.J. performed the material characterizations.

Ethics declarations

The authors declare no competing interests.

Figures

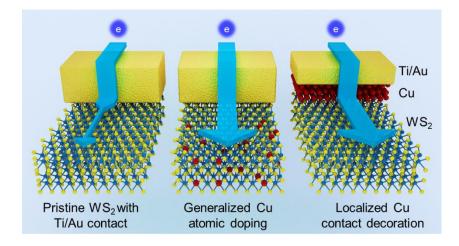


Fig. 1 Schematic illustration of generalized Cu atomic doping and localized Cu contact decoration on WS_2 in a comparison with pristine WS_2 with Ti/Au contact. The blue arrow indicates the electron injection through the metal-semiconductor interface.

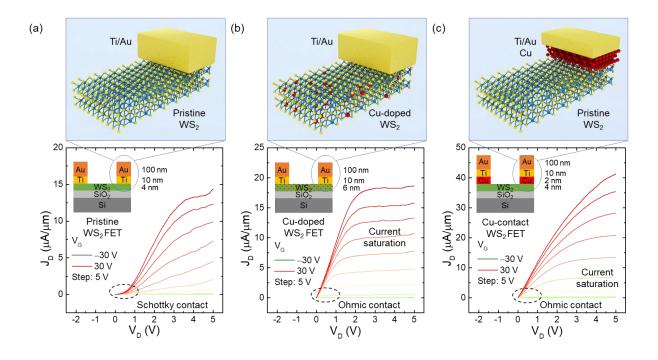


Fig. 2 Comparison of output characteristics of WS₂ FETs. (a, b, c) The output characteristics of pristine, Cu-doped, and Cu-contact WS₂ FETs at various V_G (from –30 to 30 V with a step of 5 V) at room temperature, respectively. Inset: Schematic illustration of the device structures and the corresponding metal-semiconductor interfaces.

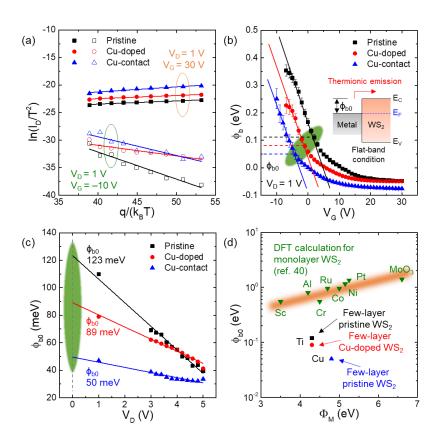


Fig. 3 Schottky barrier heights of WS₂ FETs. (a) The Arrhenius plots for on state ($V_G = 30$ V) and off state ($V_G = -10$ V) at $V_D = 1$ V. (b) The extracted ϕ_b as a function of V_G . The transition between linear and exponential decay highlighted in green indicates the flat-band condition at the metal-semiconductor interface. (c) The extracted ϕ_{b0} as a function of V_D . The values at zero V_D are predicted by a linear fit and highlighted in green. (d) Comparison of the experimentally extracted ϕ_{b0} with the theoretically calculated values for various metals.

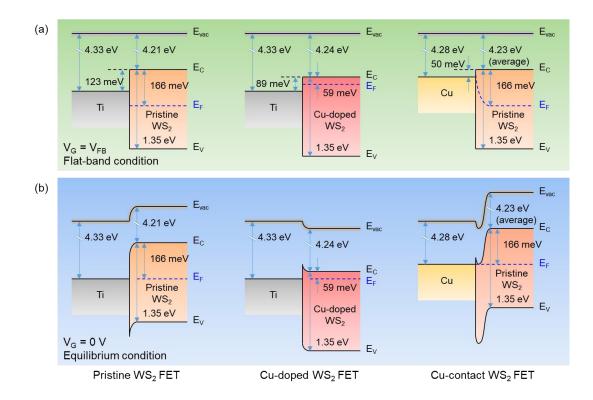


Fig. 4 Energy band diagram of the metal-semiconductor interface at zero V_D . (a) Energy band diagram at flat-band condition ($V_G = V_{FB}$). (b) Energy band diagram at equilibrium condition ($V_G = 0$ V). Here ϕ_{b0} at V_{FB} is measured to be 123, 89, and 50 meV, and ϕ_b at zero V_G is measured to be 166, 59, and 0 meV for the pristine, Cu-doped, and Cu-contact WS₂ FETs, respectively. E_{vac} , E_C , E_V , and E_F denote the vacuum energy level, the minima of the conduction band edge, the maxima of the valance band edge, and the Fermi energy level, respectively.

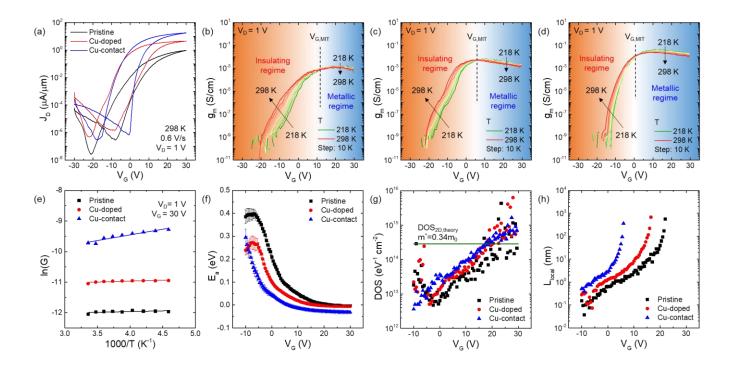


Fig. 5 Comparison of transfer characteristics of WS₂ FETs and *IV* characteristics based on the transfer curves. (a) Comparison of transfer characteristics at room temperature for the pristine, Cu-doped, and Cu-contact WS₂ FETs. (b-d) The extracted g_m as a function of V_G at various *T* illustrates the MIT effect in the pristine, Cu-doped, and Cu-contact WS₂ FETs, respectively. The insulating and metallic regimes are colored in orange and blue. (e, f) A plot of $\ln(G)$ versus 1000/*T* shows the extraction of E_a from a linear fit at $V_D = 1$ V and $V_G = 30$ V, and the extracted E_a as a function of V_G for all three types of the devices. (g, h) The extracted *DOS* and L_{local} as the functions of V_G for all three types of the devices.

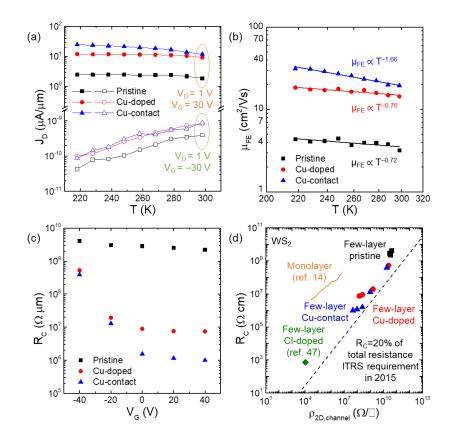


Fig. 6 Carrier mobility and contact resistance of WS₂ FETs. (a, b) J_D as a function of T and μ_{FE} as a function of $\log(T)$ for each type of the devices. (c, d) The extracted R_C as a function of V_G , and its benchmarking as a function of $\rho_{2D,channel}$ in a comparison with monolayer and few-layer Cl-doped WS₂. The dashed line depicts the criterion $R_C = 20\%$ of total resistance in a transistor with a 22-nm-long gate as required by ITRS in 2015.

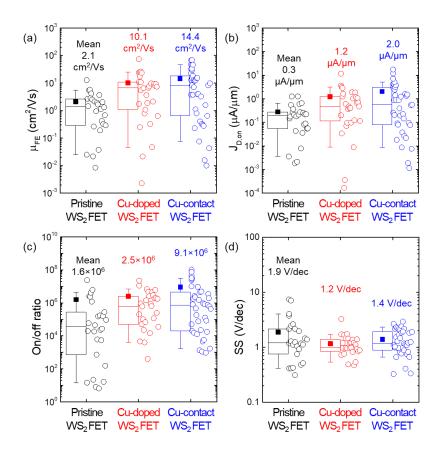


Fig. 7 Statistical analysis of transistor performance for 26 pristine WS₂ FETs, 29 Cu-doped WS₂ FETs, and 39 Cu-contact WS₂ FETs. (a-d) Comparison of transistor performance including μ_{FE} , $J_{D,on}$, on/off ratio, and SS, respectively. Here the box ranges from 25 to 75 percentile and the whisker ranges from 10 to 90 percentile. The bar in the box and the solid square denote the median and mean values, respectively.

Supplementary Information

Enhanced Carrier Transport by Transition Metal Doping in WS₂ Field Effect Transistors

Maomao Liu,¹ Sichen Wei,² Simran Shahi,¹ Hemendra Nath Jaiswal,¹

Paolo Paletti,³ Sara Fathipour,³ Maja Remskar,⁴ Jun Jiao,⁵

Wansik Hwang, 6† Fei Yao, 2† and Huamin $Li^{1\dagger}$

¹ Department of Electrical Engineering, University at Buffalo, the State University of New York, Buffalo, NY 14260, USA

² Department of Materials Design and Innovation, University at Buffalo, the State University of New York, Buffalo, NY 14260, USA

³ Department of Electrical Engineering, University of Notre Dame, South Bend, IN 46556, USA ⁴ Department of Solid State Physics, Jozef Stefan Institute, Ljubljana, 1000, Slovenia

⁵ Center for Electron Microscopy and Nanofabrication, Portland State University, Portland, OR

97207, USA

⁶ Department of Materials Engineering, Korea Aerospace University, Goyang 10540, Republic

of Korea

FIGURES

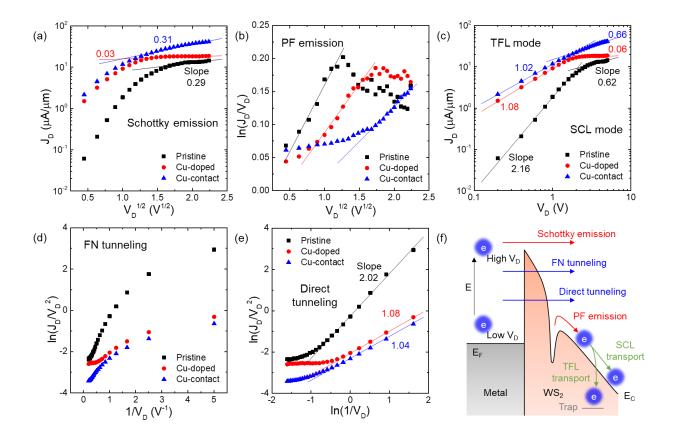


Fig. S1 *IV* characteristics of WS₂ FETs at on state ($V_G = 30$ V) based on the output curves. Various models, including (a) Schottky emission model, (b) PF emission model, (c) TFL/SCL model, (d) FN tunneling model, and (e) direct tunneling model were used for comparative investigation. (f) Energy band diagram at the metal-semiconductor interface illustrates the mechanisms of the carrier injection and transport.

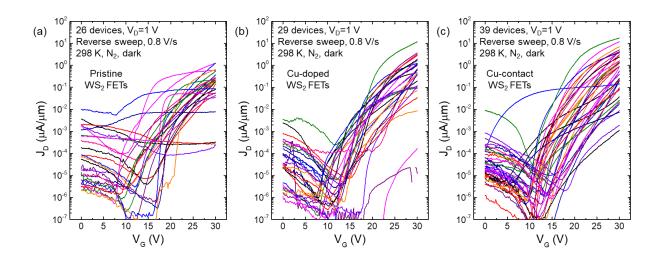


Fig. S2 The transfer characteristics for (a) 26 pristine WS₂ FETs, (b) 29 Cu-doped WS₂ FETs, and (c) 39 Cu-contact WS₂ FETs.

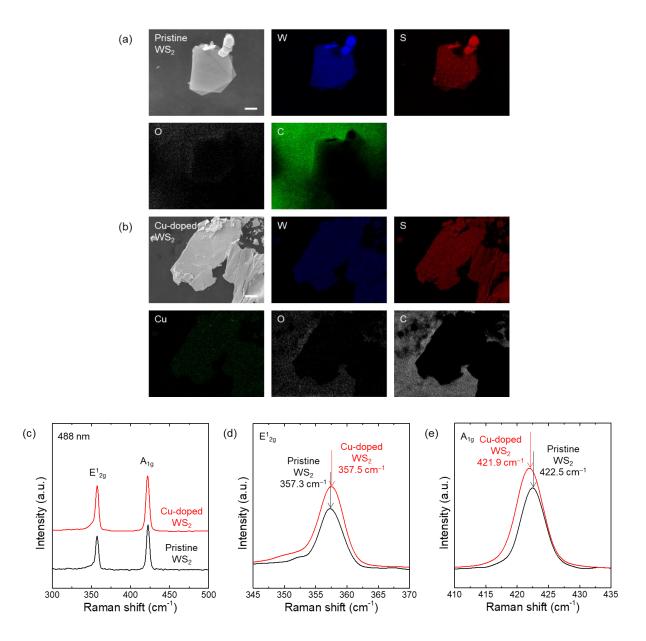


Fig. S3 (a, b) SEM and EDX elemental mapping of a synthesized pristine WS_2 flake and a Cudoped WS_2 flake transferred on the carbon tape surface. Scale bar: 2 μ m. (c-e) Raman spectroscopy of the pristine and Cu-doped WS_2 .




Fig. S4 AFM mapping image of a back-gate FET using the exfoliated Cu-doped WS_2 flake as the channel (inset) and the cross-section profile of the channel.