

Extremely slow non-equilibrium monopole dynamics in classical spin ice

T. Stöter,^{1,2} M. Doerr,³ S. Granovsky,^{3,4} M. Rotter,⁵ S. T. B. Goennenwein,³ S. Zherlitsyn,² O. A. Petrenko,⁶ G. Balakrishnan,⁶ H. D. Zhou,^{7,8} and J. Wosnitzer^{1,2}

¹*Institute for Solid State and Materials Physics and Würzburg-Dresden Cluster of Excellence ct.qmat, TU Dresden, 01062 Dresden, Germany*

²*Hochfeld-Magnetlabor Dresden (HLD-EMFL), Helmholtz-Zentrum Dresden-Rossendorf, 01328 Dresden, Germany*

³*Institute for Solid State and Materials Physics and Würzburg-Dresden Cluster of Excellence ct.qmat, TU Dresden, 01062 Dresden, Germany*

⁴*Faculty of Physics, M. V. Lomonosov Moscow State University, Moscow, 119991, Russia*

⁵*McPhase Project, 01159 Dresden, Germany*

⁶*University of Warwick, Department of Physics, Coventry CV4 7AL, United Kingdom*

⁷*University of Tennessee, Department of Physics and Astronomy, Knoxville, Tennessee 37996-1200, USA*

⁸*National High Magnetic Field Laboratory, Florida State University, Tallahassee 32306-4005, USA*

(Dated: March 12, 2024)

We report on the non-equilibrium monopole dynamics in the classical spin ice $\text{Dy}_2\text{Ti}_2\text{O}_7$ detected by means of high-resolution magnetostriction measurements. Significant lattice changes occur at the transition from the kagome-ice to the saturated-ice phase, visible in the longitudinal and transverse magnetostriction. A hysteresis opening at temperatures below 0.6 K suggests a first-order transition between the kagome and saturated state. Extremely slow lattice relaxations, triggered by changes of the magnetic field, were observed. These lattice-relaxation effects result from non-equilibrium monopole formation or annihilation processes. The relaxation times extracted from our experiment are in good agreement with theoretical predictions with decay constants of the order of 10^4 s at 0.3 K.

Magnetically frustrated materials are the subject of intense research due to inherently competing interactions, large ground-state degeneracy, the appearance of exotic states, such as spin-ice and spin-liquid phases [1, 2], deconfined fractionalized excitations (magnetic monopoles) [3], non-stationary processes [4–6], and unusual spin dynamics [7–13]. However, an analysis of the long-term non-equilibrium processes at low fields is given only in one paper [11].

Prominent examples of frustrated magnetic systems are the pyrochlore oxides $A_2B_2O_7$, with a trivalent rare-earth ion A^{3+} and a tetravalent ion B^{4+} . Especially in the pyrochlores with Dy or Ho on the A site, many different exotic states have been investigated. The single-ion ground state can be treated as an effective spin-half state [14]. The two-ion interaction is very well described by the dipolar spin-ice model [15] which includes dipolar and exchange interaction that result in an effective ferromagnetic nearest-neighbor interaction. These interactions, together with strong magnetic anisotropy due to crystal-electric-field (CEF) effects, favor the highly degenerate spin-ice configuration: two spins point into and two spins point out of each “2-in-2-out” tetrahedron [16]. The excitations of this arrangement to “3-in-1-out” or “1-in-3-out” can be interpreted as the creation of magnetic monopole-antimonopole pairs [3].

The study of thermally activated spin dynamics in $\text{Dy}_2\text{Ti}_2\text{O}_7$ via ac-susceptibility or magnetization is the focus of numerous publications [12, 17–26] because these slow dynamic effects are directly connected to the kinetics and interactions of these monopoles. In detail, a sharp increase of the relaxation times at temperatures

below 1 K was reported and attributed to the Coulomb-gas character of charged particles (monopoles) forming a network of ‘Dirac strings’. This blocks the monopoles in metastable states [27–29]. The temperature-dependent non-equilibrium dynamics was analyzed theoretically in ref. [30]. Field-dependent magnetic investigations which also resolve the monopole dynamics in the “3-in-1-out” or “1-in-3-out” kagome state or in the saturated spin-ice in relation to the crystal lattice are, although of great interest [31], rather rare and, therefore, are the main topic of this report.

Several theoretical [32–41] and experimental studies [5, 6, 42] have investigated the magnetoelastic coupling in pyrochlore systems. As frustration is highly dependent on the symmetry of the lattice, distorting the lattice can relieve the frustration. The spin-ice state was shown to be stable under hydrostatic pressure [42]. Likewise lifting the degeneracy of the frustrated state by a magnetic field could also influence the lattice.

In ultrasound measurements on $\text{Dy}_2\text{Ti}_2\text{O}_7$, dramatic non-equilibrium effects were found: thermal runaway associated with monopole avalanches [5]. In the magnetization, these kinds of avalanches also exist [43]. Apart from these short-time-scale effects, an increase of the time scale of the internal dynamics has been observed in various measurements on spin ice, such as in ac susceptibility [12, 17–24, 26, 44], magnetization [11, 20, 43], the magnetocaloric effect [45], thermal conductivity [46], and heat capacity [47]. Most of these measurements were performed quenching the sample from low fields to zero. From theory, another kind of non-equilibrium effect when quenching the field from the monopole-rich saturated-ice

or kagome-ice phase towards the spin-ice phase with only a few monopoles was suggested. Both, short- and long-time annihilation processes have been proposed in the theory work of Mostame *et al.* [31]. In experiment, a slow relaxation process has been reported to occur [11]. These investigations, however, were performed only at very low magnetic fields. In our studies, on the other hand, we investigate in detail non-equilibrium processes at higher fields, in the kagome-ice state, and, thereby, validate the theoretically proposed behavior [31].

In detail, we observed extremely slow lattice-relaxation processes which can be directly connected to the generation and annihilation of monopole/antimonopole pairs in magnetic field. These macroscopic lattice changes allow us a direct insight into the microscopic spin dynamics. Via magnetoelastic coupling we can indirectly resolve the relevant minute magnetization changes with extraordinary high resolution.

Single crystals of $\text{Dy}_2\text{Ti}_2\text{O}_7$ were grown by the floating-zone technique [48] and oriented along the required crystallographic axes using x-ray Laue diffraction. The crystals used for the experiments were oblate cuboids of dimensions $\sim 3 \times 2 \times 1 \text{ mm}^3$, for which a demagnetization factor of about 0.7 for fields along the shortest dimension was deduced.

For the measurements, we used a capacitive dilatometer [49] that was mounted on a probe placed in a sorb-pumped ^3He -cryostat reaching temperatures down to 0.3 K. For accurate monitoring and control of the dilatometer and sample temperature we used a Cernox and a RuO_2 thermometer (below 1 K). Both thermometers were attached to the dilatometer cell close to the sample.

First, we focus on the (static) low-temperature magnetostriction curves displayed in Fig. 1. Sweeping the field up at lowest temperature of 0.3 K in longitudinal geometry, the crystal contracts at first until it reaches a minimum at around 0.8 T, then expands up to about 1.3 T. Upon further increasing the field, it contracts again reaching a local minimum and turning again to expand linearly with increasing field with a slope of about $1 \times 10^{-5} \text{ T}^{-1}$. Sweeping further up in field, there is no sign of saturation up to 10 T (not shown). This increase of the longitudinal magnetostriction is due to the mixing in of higher CEF terms, as simulations with the program package MCPHASE [50] have shown.

The magnetostriction in transversal geometry is of roughly the opposite character. All magnetostrictive effects are on the order of 10^{-5} , well above the noise level of about 10^{-7} . There is a distinct anomaly at about 1.3 T corresponding to the first-order transition between the kagome and “3-in-1-out” state [51] in good agreement with our own simulations. In the following, we will only discuss the results obtained in longitudinal geometry. The transverse magnetostriction shows similar

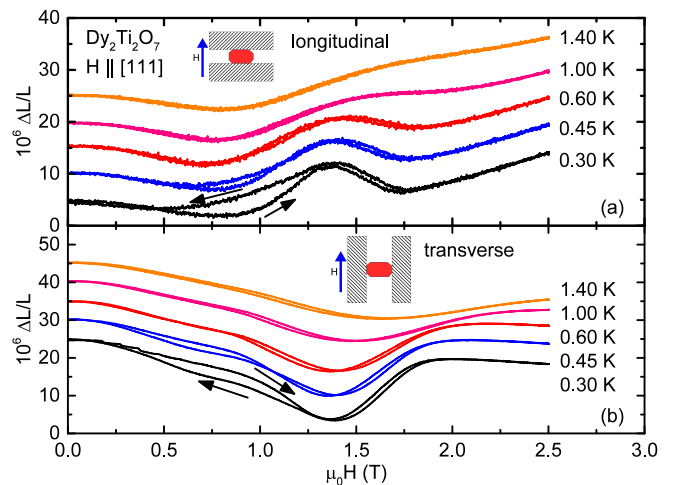


FIG. 1. Field dependence of the relative sample-length change parallel and perpendicular to a magnetic field applied along the [111] direction at various temperatures. The black arrows indicate the field-sweep direction. The sketches show how the sample (red), the magnetic field (blue arrow), and the capacitor plates (grey) are arranged. The curves are offset for clarity.

relaxation phenomena as discussed below.

In the kagome-ice region, we observe a clear hysteresis between about 0.5 and 1.2 T below 0.6 K (Fig. 1). It must be assumed that extensive dynamic effects are present in this area and that the sample is not in an equilibrium state in this range.

We investigated this latter point in more detail by probing the lattice relaxation and non-equilibrium spin dynamics using clearly specified protocols. Before each measurement sequence, we prepared the sample in a well-defined state. After oscillating the field in order to demagnetize the magnet, the sample was cooled down to the measurement temperature and thermally stabilized for 30 min at 0 T. To illustrate, the following sequence gives an example how we performed our measurements. We increased, at constant temperature, the magnetic field at a fast sweep rate of 1 T min^{-1} in steps between 0.1 and 0.5 T up to the final field and decreased step-wise afterwards (with the same sweep rate). After that, we monitored the lattice relaxation using our dilatometer for 1 h or longer at constant field and temperature.

Some typical relaxation data for $\text{Dy}_2\text{Ti}_2\text{O}_7$ in longitudinal geometry are shown in Fig. 2 for various temperatures. These plots display the changes in sample length as a function of time; Figure 2(a) shows the data after rapid (1 T/min) reduction of the magnetic field, Fig. 2(b) those after field increase. While decreasing the field [Fig. 2(a)], the lattice contracts quickly, but even after we stop the field sweep, the lattice still continues to contract very slowly. For 0.3 and 0.45 K, even after 1 h no steady state is reached. At 0.6 K, the lattice changes

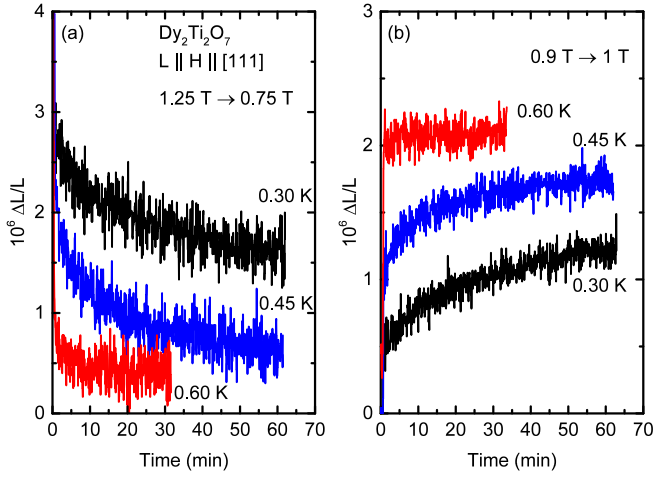


FIG. 2. Typical time dependence of the relative sample length of $\text{Dy}_2\text{Ti}_2\text{O}_7$ in longitudinal geometry $H \parallel \Delta L/L$ at various temperatures (a) sweeping the field quickly from 1.25 down to 0.75 T and (b) sweeping from 0.90 up to 1.00 T.

stop after about 600 s, *i.e.*, the lattice relaxation is slower at lower temperatures. We found corresponding behavior for increasing fields [Fig. 2(b)]. During the sweeps, the lattice expands quickly and continues to do so very slowly even after stopping the sweep. Again, we observe much longer time scales of the lattice relaxation the lower the temperature.

In order to analyze the data quantitatively and to obtain more insight into the non-equilibrium dynamics involved, we need some model to describe the relaxation time. It seems reasonable that some exponential decay law should be adequate to describe the data, but the exact form is not *a priori* known. Therefore, we performed a long-time relaxation measurement (10 h, Fig. 3) to better resolve what kind of decay law describes the data best. The field was swept from 1.25 to 0.75 T at 0.3 K.

Possible models would be a simple exponential decay with one relaxation time

$$(\Delta L/L)(t) = (\Delta L/L)_\infty + Ae^{-(t-t_0)/\tau}, \quad (1)$$

or a stretched-exponential decay

$$(\Delta L/L)(t) = (\Delta L/L)_\infty + Ae^{-((t-t_0)/\tau)^\beta}, \quad (2)$$

where τ is the relaxation time, β an exponent describing the relaxation-time distribution, $(\Delta L/L)_\infty$ the relative sample-length change for $t \rightarrow \infty$, and $(\Delta L/L)_\infty + A$ gives the value of $(\Delta L/L)$ at $t = t_0$, with t_0 usually set to zero. The data were described using the free parameters A , $(\Delta L/L)_\infty$, and τ for both equations and additionally β for the stretched-exponential fit. We found that simple exponential decays using Eq. (1) deviate significantly from the data, either at the beginning or at the end of the relaxation process (dashed and dotted lines in Fig. 3,

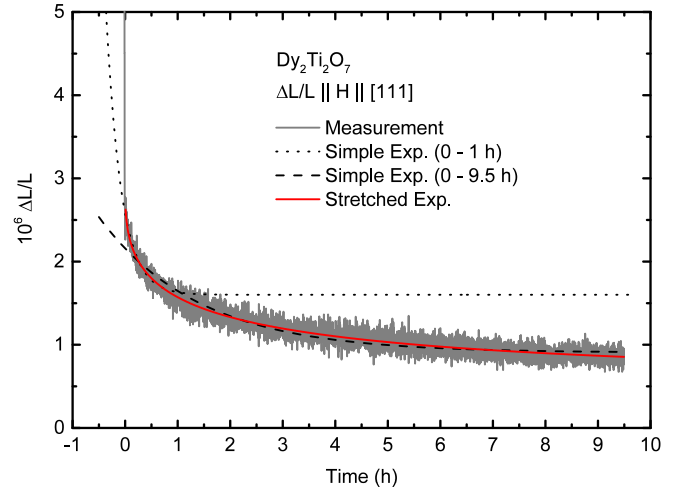


FIG. 3. Long-time change of the sample length after a quick field sweep from 1.25 to 0.75 T and fit lines using different models to describe the data.

respectively). On the other hand, the stretched exponential fit provides a much better match to the data in the whole time range (red line in Fig. 3). The stretched-exponential model describes the data best for $\beta = 0.4$ and $\tau = 5500$ s.

A model with two relaxation times τ_S and τ_L to distinguish between free and bound monopoles, as proposed in [20], describes our data less well, although even more parameters are used. Indeed, the stretched-exponential model is better motivated: Firstly, we observed that any exponential-decay fit saturates too early and should be stretched over longer times. Secondly, applying model (2) is justified by the existence of the mutual interactions of the magnetic monopoles as suggested by theoretical investigations of the spin-ice model [31, 52]. Indeed, this model leads to a distribution of relaxation times. In particular, the formation of incontractable monopole-antimonopole pairs might lead to a slowing down of the dynamics.

In the following, we fixed β to 0.4 and used Eq. (2) to describe our lattice-relaxation data (such as those shown in Fig. 2). The error bars were estimated by varying β by ± 0.2 and checking whether the data could be described with another set of A and τ .

Figure 4 shows the field dependence of the extracted relaxation times of $\text{Dy}_2\text{Ti}_2\text{O}_7$ after rapidly decreasing [Fig. 4(a)] and increasing the field [Fig. 4(b)]. The longest relaxation times were measured in the field region between 0.5 and 1.0 T. Non-equilibrium dynamics could not be observed at fields below 0.2 T or above 1.2 T. The time scales of the relaxation are up to hours at 0.3 K and a few minutes at 0.6 K. Above 0.7 K, no relaxation could be found. This matches approximately the spin-freezing temperature of about 0.6 K [53]. The extremely slow spin dynamics, therefore, is only present

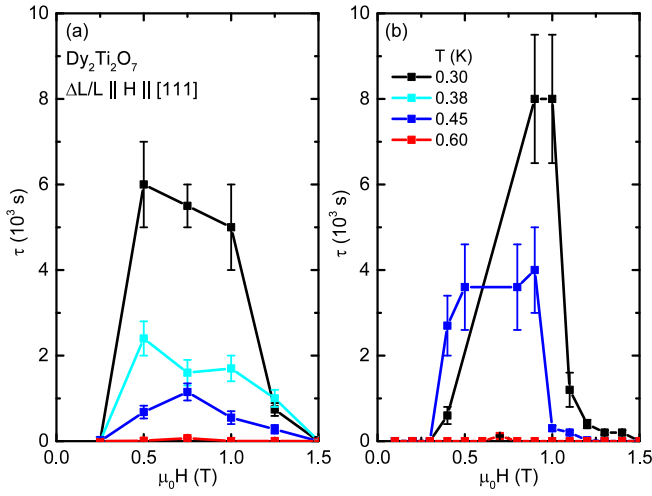


FIG. 4. Field dependence of the relaxation times of $\text{Dy}_2\text{Ti}_2\text{O}_7$ at various magnetic fields in longitudinal geometry $H \parallel \Delta L/L$ after (a) reducing and (b) increasing the magnetic field quickly.

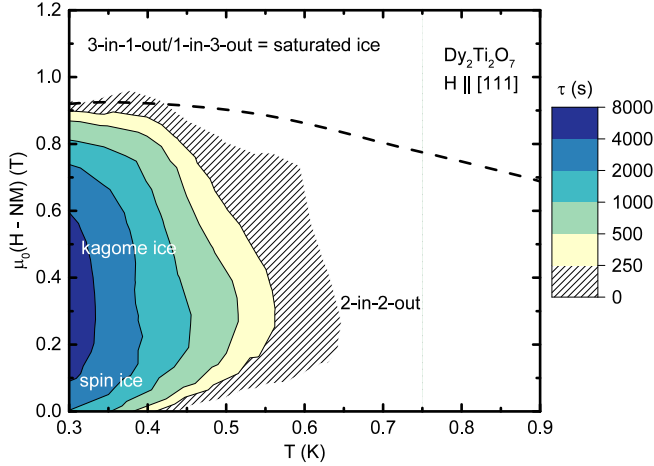


FIG. 5. Contour plot of the relaxation time of $\text{Dy}_2\text{Ti}_2\text{O}_7$ in the phase space of temperature and internal field with long relaxation times in blue and short relaxation fading to lighter colors. The relaxation times are taken from the quench experiments summarized in Fig. 4. Note the exponential scale of the color scale. For comparison, transitions extracted from specific-heat and magnetization data [51] are included as dashed line.

in the kagome-ice region below the saturated-ice phase [51, 54]. Remarkably, within the experimental error, the relaxation times for decreasing and increasing field are of the same order of magnitude.

Finally, we summarize the relaxation times of our field-quench experiments in a phase diagram of temperature and internal field (corrected for demagnetization effects) in Fig. 5. The internal field is calculated using $B_{\text{int}} = \mu_0(H - NM)$, where $\mu_0 H$ is the applied

field, N the demagnetizing factor, and M the known magnetization [55]. In accordance with the known phase diagram of $\text{Dy}_2\text{Ti}_2\text{O}_7$ extracted from specific-heat and magnetization data [51], the lattice relaxation is only observed below the transition from the kagome to saturated-ice phase (dashed line in Fig. 5). The temperature-dependent relaxation time decreases with increasing temperature. The region of our measurable times (minimum 30 s) extends to 0.6 K, the spin-freezing temperature [19]. At higher temperatures no relaxation is observed. The longest relaxation times are found in the kagome-ice phase at low temperatures. The number of monopole-antimonopole pairs is particularly large in this phase and, therefore, in the kagome-ice phase long relaxation times can be expected.

To discuss the experimental facts, the field-quench experiments make the dynamics of thermally activated monopoles in the kagome phase of spin-ice compounds experimentally accessible. The magnetostriction is a highly sensitive probe, especially in the kagome-ice phase where magnetization changes could not be resolved. Our investigations on $\text{Dy}_2\text{Ti}_2\text{O}_7$ evidence the dynamical behavior in spin ice as it has been modeled in theory with monopole “3-in-1-out” or “1-in-3-out” excitations from the ground-state configuration of “2-in-2-out” [30, 31]. Specifically, a significant increase of the time scales of these dynamics at temperatures below 0.6 K has been found. A number of publications deal with the dynamics of pyrochlore compounds, especially with $\text{Dy}_2\text{Ti}_2\text{O}_7$ [5, 12, 17–24, 26, 43–47].

Many earlier investigations show dynamic effects below 1 K on the same order of magnitude as the lattice relaxation and probably having the same origin. Our results confirm that the crystal lattice is active in the magnetic relaxation processes and directly reflects this relaxation. Furthermore, since the relaxation times for increasing and decreasing field are almost identical, we experimentally prove that the formation and decay of monopole pairs follow the same time scales. Our measurements also show an increase of the relaxation times especially in the kagome-ice phase where we could follow the monopole dynamics over long time periods. This is in good agreement with theoretical predictions [31]. The microscopic picture is that monopole-antimonopole pairs (“3-in-1-out” or vice-versa configurations) on neighboring tetrahedra form stable bound pairs, that can neither annihilate nor move away from each other due to their mutual interaction. Therefore, the monopole mobility or spin-flip rate is reduced. Consequently, the probability of the annihilation of monopoles is suppressed and it takes a long time for this process to happen. Additionally, monopole movement (spin flips) might be suppressed at defect sites of the lattice slowing down the intrinsic dynamics [56]; this was suggested to explain the difference between the long-time thermal relaxation in

specific-heat measurements [47] in comparison to other experiments [57, 58].

In summary, we have shown dilatometric results of the lattice relaxation due to monopole dynamics in the classical spin ice compound $\text{Dy}_2\text{Ti}_2\text{O}_7$. The lattice relaxation follows a stretched-exponential law with temperature- and field-dependent relaxation times τ . The analyzed field dependence of the relaxation, presented for the first time, illustrates the different character of the individual states. Extremely long relaxation times were observed in the kagome-ice. Our results fit very well to the behavior expected from theoretical considerations.

ACKNOWLEDGMENTS

We acknowledge support from HLD at HZDR, member of the European Magnetic Field Laboratory (EMFL). This research has been supported by the DFG through SFB 1143 (project-id 247310070) and the excellence cluster *ct.qmat* (EXC 2147, project-id 39085490). The work at the University of Warwick was supported by a grant from the EPSRC, UK (EP/M028771/1). A portion of this work was performed at the NHMFL, which is supported by the NSF Cooperative Agreement No. DMR-1644779 and the State of Florida.

-
- [1] R. Moessner and A. Ramirez, *Phys. Today* **59**(2), 24 (2006).
 - [2] L. Balents, *Nature* **464**, 199 (2010).
 - [3] C. Castelnovo, R. Moessner, and S. L. Sondhi, *Nature* **451**, 42 (2008).
 - [4] D. Slobinsky, C. Castelnovo, R. A. Borzi, A. S. Gibbs, A. P. Mackenzie, R. Moessner, and S. A. Grigera, *Phys. Rev. Lett.* **105**, 267205 (2010).
 - [5] S. Erfanifam, S. Zherlitsyn, J. Wosnitza, R. Moessner, O. A. Petrenko, G. Balakrishnan, and A. A. Zvyagin, *Phys. Rev. B* **84**, 220404(R) (2011).
 - [6] S. Erfanifam, S. Zherlitsyn, S. Yasin, Y. Skourski, J. Wosnitza, A. A. Zvyagin, P. McClarty, R. Moessner, G. Balakrishnan, and O. A. Petrenko, *Phys. Rev. B* **90**, 064409 (2014).
 - [7] R. Borzi, F. Gomez Albarracin, H. Rosales, G. Rossini, A. Steppke, D. Prabhakaran, A. Mackenzie, D. Cabra, and S. Grigera, *Nat. Commun.* **7**, 12592 (2016).
 - [8] V. Kaiser, S. Bramwell, P. Holdsworth, and R. Moessner, *Phys. Rev. Lett.* **115**, 037201 (2015).
 - [9] C. Paulsen, S. Giblin, E. Lhotel, D. Prabhakaran, K. Matsuhira, G. Balakrishnan, and S. Bramwell, *Nat. Commun.* **10**, 1509 (2019).
 - [10] C. Paulsen, S. Giblin, E. Lhotel, B. Canals, D. Prabhakaran, K. Matsuhira, and S. Bramwell, *Nat. Phys.* **12**, 661 (2016).
 - [11] C. Paulsen, M. J. Jackson, E. Lhotel, B. Canals, D. Prabhakaran, K. Matsuhira, S. R. Giblin, and S. T. Bramwell, *Nat. Phys.* **10**, 135 (2014).
 - [12] L. R. Yaraskavitch, H. M. Revell, S. Meng, K. A. Ross, H. M. L. Noad, H. A. Dabkowska, B. D. Gaulin, and J. B. Kycia, *Phys. Rev. B* **85**, 020410(R) (2012).
 - [13] S. Giblin, M. Twengström, L. Bovo, M. Ruminy, M. Bartkowiak, P. Manuel, J. Andresen, D. Prabhakaran, G. Balakrishnan, E. Pomjakushina, C. Paulsen, E. Lhotel, L. Keller, M. Frontzek, S. Capelli, O. Zaharko, P. McClarty, S. Bramwell, P. Henelius, and T. Fennell, *Phys. Rev. Lett.* **121**, 067202 (2018).
 - [14] J. G. Rau and M. J. P. Gingras, *Phys. Rev. B* **92**, 144417 (2015).
 - [15] B. C. den Hertog and M. J. P. Gingras, *Phys. Rev. Lett.* **84**, 3430 (2000).
 - [16] S. T. Bramwell, *Science* **294**, 1495 (2001).
 - [17] K. Matsuhira, Y. Hinatsu, and T. Sakakibara, *J. Phys.: Condens. Mat.* **13**, L737 (2001).
 - [18] J. Snyder, B. G. Ueland, J. S. Slusky, H. Karunadasa, R. J. Cava, A. Mizel, and P. Schiffer, *Phys. Rev. Lett.* **91**, 107201 (2003).
 - [19] J. Snyder, B. G. Ueland, J. S. Slusky, H. Karunadasa, R. J. Cava, and P. Schiffer, *Phys. Rev. B* **69**, 064414 (2004).
 - [20] K. Matsuhira, C. Paulsen, E. Lhotel, C. Sekine, Z. Hiroi, and S. Takagi, *J. Phys. Soc. Jpn.* **80**, 123711 (2011).
 - [21] K. Matsuhira, Y. Hinatsu, K. Tenya, and T. Sakakibara, *J. Phys.: Condens. Mat.* **12**, L649 (2000).
 - [22] J. Snyder, J. S. Slusky, R. J. Cava, and P. Schiffer, *Nature* **413**, 48 (2001).
 - [23] G. Ehlers, A. L. Cornelius, M. Orendá, M. Kajnakov, T. Fennell, S. T. Bramwell, and J. S. Gardner, *J. Phys.: Condens. Mat.* **15**, L9 (2003).
 - [24] G. Ehlers, A. L. Cornelius, T. Fennell, M. Koza, S. T. Bramwell, and J. S. Gardner, *J. Phys.: Condens. Mat.* **16**, S635 (2004).
 - [25] O. A. Petrenko, M. R. Lees, and G. Balakrishnan, *J. Phys.: Condens. Mat.* **23**, 164218 (2011).
 - [26] J. A. Quilliam, L. R. Yaraskavitch, H. A. Dabkowska, B. D. Gaulin, and J. B. Kycia, *Phys. Rev. B* **83**, 094424 (2011).
 - [27] L. C. Jaubert and P. C. W. Holdsworth, *Nat. Phys.* **5**, 258 (2009).
 - [28] L. C. Jaubert and P. C. W. Holdsworth, *J. Phys.: Condens. Mat.* **23**, 164222 (2011).
 - [29] S. R. Giblin, S. T. Bramwell, P. C. W. Holdsworth, D. Prabhakaran, and I. Terry, *Nat. Phys.* **7**, 252 (2011).
 - [30] C. Castelnovo, R. Moessner, and S. L. Sondhi, *Phys. Rev. Lett.* **104**, 107201 (2010).
 - [31] S. Mostame, C. Castelnovo, R. Moessner, and S. L. Sondhi, *Proc. Natl. Acad. Sci. USA* **111**, 640 (2014).
 - [32] Y. Yamashita and K. Ueda, *Phys. Rev. Lett.* **85**, 4960 (2000).
 - [33] O. Tchernyshyov, R. Moessner, and S. L. Sondhi, *Phys. Rev. Lett.* **88**, 067203 (2002).
 - [34] O. Tchernyshyov, R. Moessner, and S. L. Sondhi, *Phys. Rev. B* **66**, 064403 (2002).
 - [35] J. Richter, O. Derzhko, and J. Schulenburg, *Phys. Rev. Lett.* **93**, 107206 (2004).
 - [36] C. Jia, J. H. Nam, J. S. Kim, and J. H. Han, *Phys. Rev. B* **71**, 212406 (2005).
 - [37] K. Penc, N. Shannon, Y. Motome, and H. Shiba, *J. Phys.: Condens. Mat.* **19**, 145267 (2007).
 - [38] K. Terao and I. Honda, *J. Phys.: Condens. Mat.* **19**, 145261 (2007).

- [39] T. E. Saunders and J. T. Chalker, Phys. Rev. B **77**, 214438 (2008).
- [40] S. H. Curnoe, Phys. Rev. B **78**, 094418 (2008).
- [41] K. Aoyama and H. Kawamura, Phys. Rev. Lett. **116**, 257201 (2016).
- [42] I. Mirebeau and I. Goncharenko, J. Phys.: Condens. Mat. **16**, S653 (2004).
- [43] M. J. Jackson, E. Lhotel, S. R. Giblin, S. T. Bramwell, D. Prabhakaran, K. Matsuhira, Z. Hiroi, Q. Yu, and C. Paulsen, Phys. Rev. B **90**, 064427 (2014).
- [44] H. Takatsu, K. Goto, H. Otsuka, R. Higashinaka, K. Matsumabayashi, Y. Uwatoko, and H. Kadowaki, J. Phys. Soc. Jpn. **82**, 104710 (2013).
- [45] M. Orend, J. Hanko, E. imr, A. Orendov, M. Shirai, and S. T. Bramwell, Phys. Rev. B **75**, 104425 (2007).
- [46] S. J. Li, Z. Y. Zhao, C. Fan, B. Tong, F. B. Zhang, J. Shi, J. C. Wu, X. G. Liu, H. D. Zhou, X. Zhao, and X. F. Sun, Phys. Rev. B **92**, 094408 (2015).
- [47] D. Pomaranski, L. R. Yaraskavitch, S. Meng, K. A. Ross, H. M. L. Noad, H. A. Dabkowska, B. D. Gaulin, and J. B. Kycia, Nat. Phys. **9**, 353 (2013).
- [48] G. Balakrishnan, O. A. Petrenko, M. R. Lees, and D. M. Paul, J. Phys.: Condens. Mat. **10**, L723 (1998).
- [49] R. K  chler, T. Bauer, M. Brando, and F. Steglich, Rev. Sci. Instrum. **83**, 095102 (2012).
- [50] M. Rotter, D. M. Le, J. Keller, L. G. Pascut, T. Hoffmann, M. Doerr, R. Schedler, P. Fabi, S. Rotter, and M. Banks, “McPhase Software Suite,” (2000).
- [51] Z. Hiroi, K. Matsuhira, S. Takagi, T. Tayama, and T. Sakakibara, J. Phys. Soc. Jpn. **72**, 411 (2003).
- [52] H. M. Revell, L. R. Yaraskavitch, J. D. Mason, K. A. Ross, H. M. L. Noad, H. A. Dabkowska, B. D. Gaulin, P. Henelius, and J. B. Kycia, Nat. Phys. **9**, 34 (2013).
- [53] H. Fukazawa, R. Melko, R. Higashinaka, Y. Maeno, and M. Gingras, Phys. Rev. B **65**, 054410 (2002).
- [54] R. Higashinaka, H. Fukazawa, K. Deguchi, and Y. Maeno, J. Phys.: Condens. Mat. **16**, S679 (2004).
- [55] T. Sakakibara, T. Tayama, Z. Hiroi, K. Matsuhira, and S. Takagi, Phys. Rev. Lett. **90**, 207205 (2003).
- [56] J. A. Bloxsom, *Thermal and Magnetic Studies of Spin Ice Compounds*, Ph.D. thesis, University College London, London (2016).
- [57] S. R. Giblin, M. Twengstr  m, L. Bovo, M. Ruminy, M. Bartkowiak, P. Manuel, J. C. Andresen, D. Prabhakaran, G. Balakrishnan, E. Pomjakushina, C. Paulsen, E. Lhotel, L. Keller, M. Frontzek, S. C. Capelli, O. Zaharko, P. A. McClarty, S. T. Bramwell, P. Henelius, and T. Fennell, Phys. Rev. Lett. **121**, 067202 (2018).
- [58] P. Henelius, T. Lin, M. Enjalran, Z. Hao, J. G. Rau, J. Altosaar, F. Flicker, T. Yavors’kii, and M. J. P. Gingras, Phys. Rev. B **93**, 024402 (2016).