Solvent Exchange in a Hele-Shaw Cell: Universality of Surface Nanodroplet Nucleation

Binglin Zeng ,^{†,‡} Yuliang Wang ,^{*,†,¶} Xuehua Zhang,^{§,‡} and Detlef Lohse^{*,‡}

†School of Mechanical Engineering and Automation, Beihang University, 37 Xueyuan Rd, Haidian District, Beijing, China

[‡]Physics of Fluids Group, Department of Applied Physics and J. M. Burgers Centre for Fluid Dynamics, University of Twente, P.O. Box 217, 7500 AE Enschede, The Netherlands

¶Beijing Advanced Innovation Center for Biomedical Engineering, Beihang University, 37 Xueyuan Rd, Haidian District, Beijing, China

§Department of Chemical and Materials Engineering, University of Alberta, 12-211 Donadeo Innovation Centre for Engineering, Edmonton, Alberta, Canada

E-mail: wangyuliang@buaa.edu.cn; d.lohse@utwente.nl

Abstract

Solvent exchange (also called solvent shifting or Ouzo effect) is a generally used bottom-up process to mass-produce nanoscale droplets. In this process, a good solvent for some oil is displaced by a poor one, leading to oil nanodroplet nucleation and subsequent growth. Here we perform this process on a hydrophobic substrate so that sessile droplets – so-called surface nanodroplets – develop, following the work of Zhang *et al.* [Zhang, X.; Lu, Z.; Tan, H.; Bao, L.; He, Y.; Sun, C.; Lohse, D. Proc. Natl. Acad. Sci. U. S. A. 2015, 122, 9253-9257]. In contrast to what was done in that paper, we chose a very well controlled Hele-Shaw geometry with negligible gravitational effects, injecting the poor solvent in the center of the Hele-Shaw cell, and characterize the emerging nanodroplets as function of radial distance and flow rates. We find that the mean droplet volume per area $\langle Vol \rangle_{area}$ strongly depends on the local Peclet number Pe and follows an universal scaling law $\langle Vol \rangle_{area} \sim Pe^{3/4}$. Moreover, the probability distribution function of the droplet volume strongly depends on the local Pe as well, regardless of the flow rates and radial distance, giving strong support to the theoretical model of the solvent exchange process developed in Zhang et al's work.

Introduction

The solvent shifting process – also called solvent exchange – is a simple and generic approach for mass-producing droplets or bubbles at solid–liquid interfaces. The droplet or bubble are only several tens to hundreds of nanometers in height, or a few femtoliters in volume.^{1–6} In this process, a good solvent is replaced by a poor solvent, leading to nanodroplets or nanobubble nucleation and subsequent growth on the substrate. The approach has several potential applications, such that it can be used for liquid-liquid microextraction, diagnosis, drug production, extraordinary focusing, micromanufacture and among many others.^{7–19} When applied to oil dissolved in a good solvent, the solvent exchange process has the capability of mass-producing surface nanodroplets of oil on substrates in one step.^{20–25}

In ref.²⁰ the solvent exchange process was performed in a linear channel, with the flow rate Q and the channel height h as control parameters. The nanodroplet generation for seven different flow rates and three different channel heights between h = 0.33 mm and h = 2.21mm was analysed. The main result was that the experimentally found mean droplet volume was consistent with the theoretical results derived in the same paper, namely that the areaaveraged volume of the droplet $\langle Vol \rangle_{area} \sim h^3 P e^{3/4}$, where area-averaged volume $\langle Vol \rangle_{area}$ is defined by the total volume of droplets over a unit surface area, Pe = Q/(wD) is the Peclet number, defined by the flow rate, the width of the channel w = A/h (where A is the rectangular channel cross section), and the mass diffusivity D of the oil, see figure 2G of that paper.

However, for the larger channel heights analyzed in that paper, major convective effects sets in, due to the density difference between the two solvents, leading to considerable inhomogeneities in droplet sizes. Indeed, the role of gravity in the solvent exchange process in such thick channels could later be confirmed in ref.²⁶

The aim of this present paper therefore is to go to a different geometry, namely to a Hele-Shaw cell: a channel formed by two closely spaced parallel glass plates. The employed Hele-Shaw cell possesses a much smaller cell height of $h = 100\mu m$, implying an Archimedes number $Ar = gh^3 \Delta \rho / (\nu^2 \rho)$ (see ref.²⁶) of Ar = 0.61, where $g = 9.81m/s^2$ is the gravitational acceleration, $\nu = 10^{-6}m^2/s$ is the kinematic viscosity, $\rho = 1000kg/m^3$ is the density of the fluid for injection (deionized water, in this case), and $\Delta \rho = 62kg/m^3$ is the density difference between a solution to be repelled from the Hele-Shaw cell (water-ethanol solution with the ethanol concentration of 30 vol%, in this case) and the fluid for injection. For Ar < 1, gravitational effects can be neglected. The Hele-Shaw geometry has the additional advantage that the flow rate now depends on the radial distance r from the point of flow injection, allowing for continuous variation of the local flow velocity, which again leads to the continuous tuning of the Peclet number, which is again the non-dimensionalized flow rate, here given by

$$Pe = \frac{Q}{2\pi r D}.$$
(1)

As a result, the correlation of nanodroplet formation with Peclet number can be easily investigated. The main question which arises is: Does the relationship $\langle Vol \rangle_{area} \sim h^3 P e^{3/4}$ also *locally* hold in the Hele-Shaw geometry and is thus universal?

Figure 1 shows a sketch of the geometry and the employed notations for the nanodroplets. With this setup, we want to test the fluid dynamical theory of solvent exchange (which can straightforwardly be generalized to the present circular geometry) developed in reference.²⁰

The paper is organized as follows: Section 2 gives the details on the employed method

and how the data were collected. Section 3 shows the results, followed by a discussion and the conclusions (section 4).

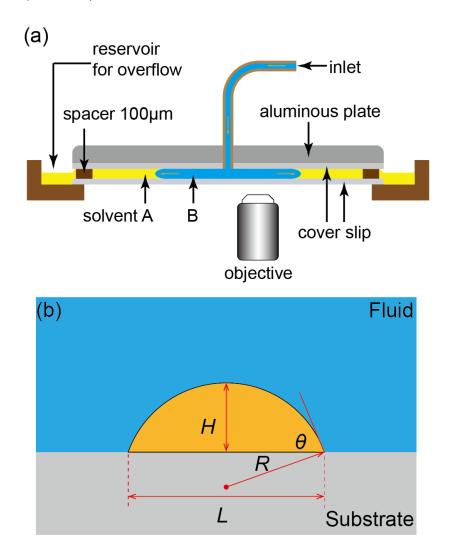


Figure 1: (a) Schematic drawings of the employed Hele-Shaw cell. The cell consists of a bottom cover slip window, a top cover slip attached to an aluminous plate, a spacer of $100\mu m$ in height, an inlet for liquid and a reservoir for overflow. During experiment, the liquid injected through the inlet will flow outwards in radial direction and is observed from the bottom. (b) Schematic diagram of a nanodroplet, where R, θ , H, and L are the radius of curvature, the contact angle, the height, and the footprint diameter of the droplet.

Experimental Section

Sample preparation

A circular glass cover slip (GOLO, China) with a diameter of 50 mm was used as the substrate for droplet nucleation and bottom window for observation in the Hele-Shaw cell. The substrate was hydrophobilized by PVDF-HFP (poly(vinylidene fluoride-co-hexafluoropropylene), Mw = 400000, Sigma-Aldrich, USA). To do so, the cover slip was first cleaned in a sonication bath of piranha solution (70% H₂SO₄- 30% H₂O₂ solution) for 30 min, followed by the sonication bath of acetone and ethanol for 30 min, then in deionized water 3 times for 5 min. After that, the sample was dried by nitrogen gas. The dried cover slip was then immersed in a 3 μL PVDF-HFP in a petri dish. The petri dish remained in an oven at 150°C for 12h. Eventually, a hydrophobic glass substrate coated with PVDF-HFP was obtained. The measured static contact angle of water on the obtained PVDF-HFP hydrophobic surface is 110°.

Formation of nanodroplets through solvent exchange in the Hele-Shaw geometry

Nanodroplets of trans-anethole (4-Propenylanisole, trans-1-Methoxy-4-(1-propenyl)benzene, Solarbio, USA) were produced on the obtained hydrophobic substrate in a Hele-Shaw cell through solvent exchange. As shown in Figure 1a, the top cover slip and the bottom cover slip window form a disk-shaped channel with a height $h = 100\mu m$ and a diameter d = 50mm. Unlike the liquid cell applied in ref.,²⁰ the inlet of the Hele-Shaw cell is in the center of the cell. The size and area density of the droplets are influenced by the solution composition for the solvent exchange.^{24,27} In our experiments, two solutions, solvent A and solvent B, were prepared for solvent exchange. Solvent A is an aqueous ethanol solution with the ethanol (analytically pure,99.8%, Aladdin, China) concentration of 30% vol. The solution was saturated with trans-anethole, which was labeled by a fluorescence dye perylene (Klamar-reagent, China). Solvent A serves as good solvent for trans-anethole with saturation concentration of 0.55 wt%. Solvent B is deionized (DI) water, which serves as poor solvent for the trans-anethole. Before the experiments, solvent B was saturated with trans-anethole as well. Such solution composition produced desirable size and density of droplets, suitable for optical images and data analysis. During the solvent exchange process, $200\mu L$ solution A was displaced by 2 mL solution B. The injection of solution B was performed by a syringe pump at three different flow rates of $Q_1 = 1000$, $Q_2 = 500$, and $Q_3 = 300\mu L/min$.

Characterization of nanodroplets

After the tran-anethole droplets had nucleated on the hydrophobic glass substrate, they were characterized by a reflecting fluorescence microscope (IX71, Olympus, Japan). Two objectives ($4\times$ and $20\times$) were used in the imaging of the nucleated droplets. The images taken with the $20\times$ objective were used for morphological analysis, while the ones taken with the $4\times$ objective were used to determine the radial distance r for each selected area in the the optical images taken with the $20\times$ objective. All the optical images ($20\times$) were analyzed using a home designed image segmentation algorithm for the optimized extraction of the droplet footprint diameters. For details of the algorithm, readers are referred to our previous publications.²⁸⁻³¹

For each of the three flow rates, the nucleated nanodroplets with different radial distance r were captured. The number of the captured nanodroplets are 18332, 14403, and 19990 for flow rates of $1000\mu L/min$, $500\mu L/min$, and $300\mu L/min$, respectively. For each Q, the captured droplets were binned in concentric circular bands with a band width $\Delta r = 100\mu m$.

To extract volumes of the nucleated nanodroplets, a tapping mode atomic force microscopy (TM-AFM) (Resolve, Bruker, USA) was also applied to get high-resolution three dimensional (3D) images of the nucleated droplets, after the growth of the oil droplets was already finished. The nucleated nanodroplets remained in solvent B and were imaged in the liquid mode of TM-AFM. For the duration of the operational time, we did not observed any temporal evolution in the droplet lateral size. The obtained AFM images were analyzed with a home-designed Matlab program to extract the height, width and contact angle of the droplets, as reported in our previous work.³² After that, the volumes of the nanodroplet can be obtained.

Since the number of the captured nanodroplets is huge, it is impractical to measure the volumes of all individual nanodroplets with AFM. Therefore, in this study, only a few nanodroplets with different footprint diameters were imaged with TM-AFM, in order to establish the dependence of the nanodroplet height H and contact angle on its footprint diameter. The height of droplets H was measured for droplets with different footprint diameter L, as shown in figure 3b. From the H(L) relationship, we obtained the $\theta(L)$ dependence, as shown in the dotted blue curve, which provides the basis for estimation of the contact angle for droplets with different L determined from the optical images. This dependence was further used to obtain the volume for each captured nanodroplet in the optical images from the footprint diameter.

Fluid dynamics theory of solvent exchange

The scaling law between the final area-averaged volume of the droplet $\langle Vol \rangle_{area}$ and the Peclet number Pe was established in ref.²⁰ When gravitational effect in solvent exchange process can be ignored (i.e., for small Archimedes number), the final area-averaged droplet volume scales as:

$$\langle Vol \rangle_{area} \sim h^3 \left(\frac{C_{sat}}{\rho_{oil}}\right)^{3/2} \left(\frac{C_{\infty}}{C_{sat}} - 1\right) P e^{3/4}$$
 (2)

where C_{sat} and C_{∞} are the saturation concentrations of oil in the poor solvent and the actual oil concentration, respectively, and ρ_{oil} is the oil density. This fluid dynamics theory of solvent exchange will be further experimentally validated in this paper.

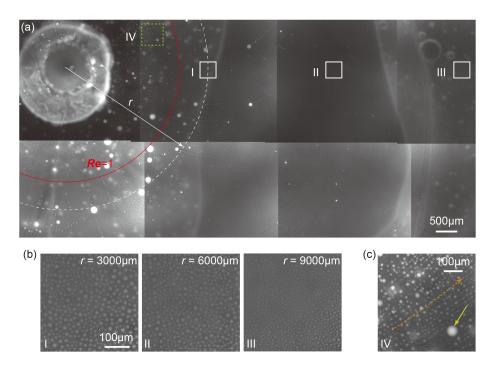


Figure 2: Morphological characterization of the nucleated nanodroplets in the Hele-Shaw geometry: (a) An optical microscope image obtained by aligning different images taken at different radial distance r (4× objective) for $Q = 1000 \mu L/min$. (b) Three example images taken with the 20× objectives at the three selected positions in white boxes of I, II, and III in (a). (c) An enlarged image for an area selected by a dotted green box IV in (a).

Results and Discussion

After solvent exchange, nucleated nanodroplets were attached to the bottom cover slip window. Figure 2a shows an fluorescence image obtained by aligning different images taken with the $4\times$ objective at the flow rate of $Q = 1000 \mu L/min$. Three examples of images taken with a higher magnification objective of $20\times$ are shown in figure 2b for the three selected areas in figure 2a. From the images, one can clearly see that the droplet size decreases with increasing distance r from the center. Figure 2c shows an enlarged image for an area selected by the dotted green box in figure 2a. One can see that the droplets in the area are lined up along the flow direction (as guided by a dotted orange arrow) and exhibits nonuniform size distributions. This will be discussed later in this section.

Figure 3a shows a representative AFM image of the trans-anethole droplets scanned in solvent B on the bottom substrate. From the AFM images, the height and the contact angle

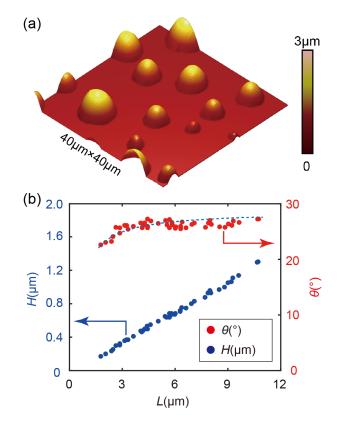


Figure 3: (a) A TM-AFM image of the nucleated droplets, providing their high-resolution 3D morphological characterization. (b) The height H and the contact angle θ as functions of the footprint diameter L of the droplets. The dependence were further used to obtain H and θ for nanodroplets in the optical images.

for the nanodroplets were extracted, as shown in figure 3b. One can see that the droplet height H roughly linearly increases from about $0.2\mu m$ to $1.3\mu m$ as L increases from about $1.5\mu m$ to $11\mu m$. The contact angle θ basically remains constant at 27° after L is larger than $3\mu m$. The aspect ratios of the nucleated droplets are consistent with the results reported in ref.^{20,33} for the same combination of solvents and solutes.

With the developed dependence between H, θ , and L, the droplet volumes Vol for individual captured droplets in the optical microscope images were obtained. After that, the mean droplet volume per area $\langle Vol \rangle_{area}$ was further calculated, as shown in figure 4a. For all the three flow rates, $\langle Vol \rangle_{area}$ decreases with increasing r. Moreover, for the same r, $\langle Vol \rangle_{area}$ increases with increasing flow rates. Most importantly, regardless of the flow rates, all the three curves are well superposed on each other in the plot of $\langle Vol \rangle_{area}$ versus

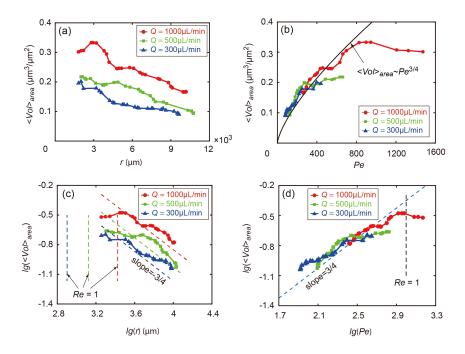


Figure 4: (a, c) Linear and double-logarithmic scale plots of the mean volume per area $\langle Vol \rangle_{area}$ of the nucleated nanodroplets as a function of radial distance r from the flow inlet for the three different flow rates Q of $1000\mu L/min$, $500\mu L/min$, $300\mu L/min$ (top to bottom). (b, d) Linear and double-logarithmic scale plots of $\langle Vol \rangle_{area}$ as a function of the dimensionless form of flow velocity – Peclet number Pe for different Q. All three curves collapse on a curve with a slope of 3/4 (shown as straight line) in the log-log plot, indicating an universal scaling law of $\langle Vol \rangle_{area} \sim Pe^{3/4}$.

Peclet number Pe, as shown in figure 4b, especially for lower Pe value (corresponding to larger distance r from the inlet).

The double logarithmic plots of $\langle Vol \rangle_{area}$ versus the radial distance r and vs the Peclet number Pe are shown in figure 4c,d. It is clear that $\langle Vol \rangle_{area}$ shows a -3/4 and 3/4 power law dependence on r and Pe, respectively. Most importantly, three curves in figure 4d collapse on one universal curve. These results are consistent with the theoretical prediction (eq. (2)) and provide strong support to the model.

In figure 4c, d, for smaller r or larger Pe, the data points for $Q = 1000 \mu L/min$ start to deviate from the -3/4 or 3/4 power law scaling lines. The deviation is likely due to the higher Reynolds number corresponding to smaller r. In the Hele-Shaw cell, the Reynolds number Re at the radial distance r is given by

$$Re = \frac{Q}{2\pi rv}.$$
(3)

where v is the kinematic viscosity of the solution (here $v = 10^{-6}m^2/s$ for water). In figure 4c, the red, green, and blue vertical dashed lines correspond to Re = 1 for the flow rates of $1000\mu L/min$, $500\mu L/min$, and $300\mu L/min$, respectively. In figure 4d, a dashed vertical line was also drown at the position of Re = 1. One can see that the deviations mainly occur in the area where the Reynolds number Re > 1. Indeed, at higher Reynolds numbers, the flow becomes dominated by inertia effects and the laminar theory of ref²⁰ would require extensions. Namely, vortical flow structures may occur, leading to a less organized flow pattern. This may lead to advection of nucleated droplets.

For that case Re > 1, droplets indeed can move outwards along the radial direction of the Hele-Shaw cell. This can be seen from figure 2c. It is an enlarged image for the area highlighted by the dotted green box in the region corresponding to Re > 1, which is defined by a red circle in figure 2a. In the image, one can see that the droplets are mostly lined up along the radial direction, which is clearly different from that shown in figure 2b. The advected droplets can merge with other surface droplets on their paths, leading to an increased size of droplets, as pointed at by the arrow in figure 2c. Meanwhile, the strong outward motion of droplets unavoidably leads to a reduced average volume $\langle Vol \rangle_{area}$ close to the center flow inlet. As a result, in the region with Re > 1, $\langle Vol \rangle_{area}$ is smaller than what is predicted by the model equation(2) of reference²⁰ and the experimental results deviate from the power law line, as shown in figure 4c,d.

Compared to the result reported in ref.²⁰ (Figure 2G, therein), the result shown in figure 2d provide a higher consistency among the experiments with different flow rates. This is attributed to the smaller cell height of $h = 100 \mu m$, which eliminates gravitational effects (i.e., Ar < 1). The results thus give strong support to our previously developed fluid dynam-

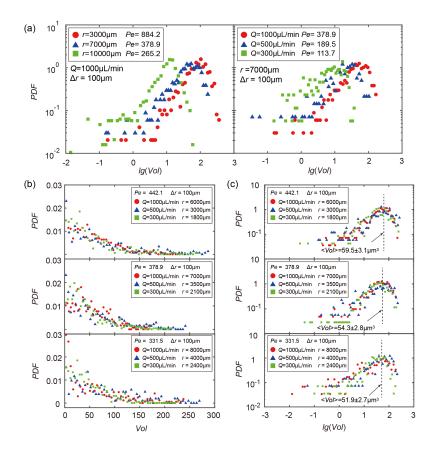


Figure 5: Droplet volume PDFs for various Peclet numbers Pe. (a) Left: PDF of the droplet volume for three different distances r from the point of flow injection at the same flow rate Qof $1000\mu L/min$. Right: PDFs of the droplet volume at the same radial distance r for three different flow rate Q. For both cases, the PDFs shift rightwards with increasing Pe. (b, c) Comparison of the PDFs of droplet volume in linear (b) and double logarithmic (c) plots for droplets nucleated in the areas with the same local Pe but different combinations of Q and r. One can conclude that the PDFs of the droplet volume strongly depend on the local Pe, regardless of Q and r.

ics model of solvent exchange, namely, that the volume of the nucleated droplets strongly depends on the dimensionless flow velocity, perfectly following the relationship $\langle Vol \rangle_{area} \sim h^3 P e^{3/4}$.

After having shown the universality of the 3/4 power law dependence between $\langle Vol \rangle_{area}$ and Pe, one also wonders on the universality of the probability distribution function (PDF) of the droplet volumes, i.e., on the dependence of the PDFs on Pe. To answer this question, the distribution of the droplet volume was calculated. Figure 5a shows the PDF of the droplet volume at different r for the flow rate $Q = 1000 \mu L/min$ (left figure) and at the same radial distance $r = 7000 \mu m$ for different flow rates (right figure). In the left figure, the PDF of droplet volumes shifts rightwards with decreasing r. Similarly, the PDF shifts rightwards with increasing Q in the right figure. Both figures of course reflect that the mean droplet volume increases with Pe.

Since Pe is continuously varying in the Hele-Shaw cell, this gives us the freedom to select a particular Pe value for fixed flow rate. This allows us to compare the distribution of the droplet volume with the same Pe value, but different Q. For the three different flow rates, three different local Pe values of Pe = 442.1, 378.9, and 331.5 were selected. This corresponds to nine areas in total, three for each of flow rate. The linear and doublelogarithmic plots of the PDF of the droplet volumes for the three selected Pe values are shown in figure 5b and c, respectively. Remarkably, it shows that the PDFs of the droplet volume have an *universal* dependence on the Peclet number, regardless of the radial distances r and flow rates Q.

Conclusions

In summary, we experimentally investigated the formation of surface nanodroplets by solvent exchange under a well controlled flow conditions. Compared to the rectangular cross section channels used in one of our previous study,²⁰ a Hele-Shaw cell with a cell height of 100 μm was employed. In the new setup, gravitational effects can be negligible. Moreover, the Hele Shaw setup easily allows the continuous tuning of the dimensionless flow velocity - namely the Peclet number *Pe*. By combining a fluorescence optical microscope and an AFM, the height, contact angle, footprint diameter, and volume of surface nanodroplets were extracted for a huge amount of nanodroplets under three different flow rates. The results reveal the underlying mechanism governing the droplet nucleation through solvent exchange. They show that not only the mean droplet volume, but also the PDF of droplet volumes universally depends on the local *Pe* number. Although the size of the nucleated droplets changes with radial distance r and flow rate Q, the mean droplet volume per area $\langle Vol \rangle_{area}$ shows a universal 3/4 power law dependence on Pe. This is in a good agreement with the model developed in our previous work.²⁰ Moreover, further investigation shows that the PDFs of the droplet volume also follow an universal dependence on the local Pe, regardless of the radial distance r and the employed flow rate Q. The revealed dependences provide an important guideline for the control of the flow conditions in the mass-production of surface nanodroplets, which is very relevant for various applications, such as in diagnostics, liquid-liquid microextraction, drug production, or food-processing.

Acknowledgement

This work is supported by National Natural Science Foundation of China (Grant No. 51775028), Beijing Natural Science Foundation (Grant No. 3182022), and ERC-NSFC joint program (Grant No. 11811530633). The authors thank the Dutch Organization for Research (NWO) and the Netherlands Center for Multiscale Catalytic Energy Conversion (MCEC) for financial support. D.L. also acknowledges financial support by an ERC-Advanced Grant and by NWO-CW.

References

- Lohse, D.; Zhang, X. Surface nanobubble and surface nanodroplets. *Rev. Mod. Phys.* 2015, 87, 981–1035.
- (2) Xiao, Q.; Liu, Y.; Guo, Z.; Liu, Z.; Lohse, D.; Zhang, X. Solvent Exchange Leading to Nanobubble Nucleation: A Molecular Dynamics Study. *Langmuir* 2017, 33, 8090–8096.
- (3) Xu, C.; Peng, S.; Qiao, G. G.; Gutowski, V.; Lohse, D.; Zhang, X. Nanobubble formation on a warmer substrate. Soft Matter 2014, 10, 7857–7864.

- (4) Xu, H.; Zhang, X. Formation, characterization and stability of oil nanodroplets on immersed substrates. Adv. Colloid Interface Sci. 2015, 224, 17–32.
- (5) Zhang, X. H.; Ducker, W. Interfacial oil droplets. Langmuir 2008, 24, 110–115.
- (6) Zhang, H.; Chen, S.; Guo, Z.; Liu, Y.; Bresme, F.; Zhang, X. Contact Line Pinning Effects Influence Determination of the Line Tension of Droplets Adsorbed on Substrates. J. Phys. Chem. C 2018, 122, 17184–17189.
- (7) Strulson, C. A.; Molden, R. C.; Keating, C. D.; Bevilacqua, P. C. RNA catalysis through compartmentalization. *Nat. Chem.* 2012, 4, 941–946.
- (8) Chiu, D. T.; Lorenz, R. M. Chemistry and Biology in Femtoliter and Picoliter Volume Droplets. Acc. Chem. Res. 2009, 42, 649–658.
- (9) Shemesh, J.; Ben Arye, T.; Avesar, J.; Kang, J. H.; Fine, A.; Super, M.; Meller, A.; Ingber, D. E.; Levenberg, S. Stationary nanoliter droplet array with a substrate of choice for single adherent/nonadherent cell incubation and analysis. *Proc. Natl. Acad. Sci. U. S. A.* **2014**, *111*, 11293–11298.
- (10) Chen, Y.; Elshobaki, M.; Gebhardt, R.; Bergeson, S.; Noack, M.; Park, J.-M.; Hillier, A. C.; Ho, K.-M.; Biswas, R.; Chaudhary, S. Reducing optical losses in organic solar cells using microlens arrays: theoretical and experimental investigation of microlens dimensions. *Phys. Chem. Chem. Phys.* **2015**, *17*, 3723–3730.
- Meckenstock, R. U.; Von, N. F.; Stumpp, C.; Lueders, T.; Himmelberg, A. M.; Hertkorn, N.; Schmitt-Kopplin, P.; Harir, M.; Hosein, R.; Haque, S. Oil biodegradation.
 Water droplets in oil are microhabitats for microbial life. *Science* 2014, 345, 673–676.
- (12) Peng, S.; Xu, C.; Hughes, T. C.; Zhang, X. From Nanodroplets by the Ouzo Effect to Interfacial Nanolenses. *Langmuir* 2014, 30, 12270–12277.

- (13) Zhang, X.; Wei, X.; Ducker, W. Formation of Nanodents by Deposition of Nanodroplets at the Polymer-Liquid Interface. *Langmuir* 2010, 26, 4776–4781.
- (14) Darwich, S.; Mougin, K.; Vidal, L.; Gnecco, E.; Haidara, H. Nanobubble and nanodroplet template growth of particle nanorings versus nanoholes in drying nanofluids and polymer films. *Nanoscale* **2011**, *3*, 1211–1217.
- (15) Ma, A.; Xu, J.; Zhang, X.; Zhang, B.; Wang, D.; Xu, H. Interfacial nanodroplets guided construction of hierarchical Au, Au-Pt, and Au-Pd particles as excellent catalysts. *Sci. Rep.* 2014, 4, 4849.
- (16) Duocastella, M.; Florian, C.; Serra, P.; Diaspro, A. Sub-wavelength Laser Nanopatterning using Droplet Lenses. *Sci. Rep.* 2015, *5*, 16199.
- (17) Zhang, R.; Liao, W.; Sun, Y.; Heng, J. Y. Y.; Yang, Z. Investigating the Role of Glass and Quartz Substrates on the Formation of Interfacial Droplets. J. Phys. Chem. C 2019, 123, 1151–1159.
- (18) Hung, S.-W.; Shiomi, J. Dynamic Wetting of Nanodroplets on Smooth and Patterned Graphene-Coated Surface. J. Phys. Chem. C 2018, 122, 8423–8429.
- (19) Gao, S.; Liao, Q.; Liu, W.; Liu, Z. Self-Removal of Multiple and Multisize Coalescing Nanodroplets on Nanostructured Surfaces. J. Phys. Chem. C 2018, 122, 20521–20526.
- (20) Zhang, X.; Lu, Z.; Tan, H.; Bao, L.; He, Y.; Sun, C.; Lohse, D. Formation of surface nanodroplets under controlled flow conditions. *Proc. Natl. Acad. Sci. U. S. A.* 2015, 112, 9253–9257.
- (21) Zhang, X.; Lhuissier, H.; Sun, C.; Lohse, D. Surface nanobubbles nucleate microdroplets. *Phys. Rev. Lett.* **2014**, *112*, 144503.
- (22) Peng, S.; Spandan, V.; Verzicco, R.; Lohse, D.; Zhang, X. H. Growth Dynamics of

Microbubbles on Microcavity Arrays by Solvent Exchange. J. Colloid Interface Sci. **2018**, 532, 103–111.

- (23) Peng, S.; Mega, T. L.; Zhang, X. Collective Effects in Microbubble Growth by Solvent Exchange. Langmuir 2016, 32, 11265–11272.
- (24) Lu, Z.; Peng, S.; Zhang, X. Influence of Solution Composition on the Formation of Surface Nanodroplets by Solvent Exchange. *Langmuir* 2016, *32*, 1700–1706.
- (25) Lu, Z.; Xu, H.; Zeng, H.; Zhang, X. Solvent Effects on the Formation of Surface Nanodroplets by Solvent Exchange. *Langmuir* 2015, *31*, 12120–12125.
- (26) Yu, H.; Lu, Z.; Lohse, D.; Zhang, X. Gravitational Effect on the Formation of Surface Nanodroplets. *Langmuir* 2015, *31*, 12628–12634.
- (27) Li, M.; Bao, L.; Yu, H.; Zhang, X. Formation of Multicomponent Surface Nanodroplets by Solvent Exchange. J. Phys. Chem. C 2018, 122, 8647–8654.
- (28) Wang, Y.; Wang, H.; Bi, S.; Guo, B. Automatic morphological characterization of nanobubbles with a novel image segmentation method and its application in the study of nanobubble coalescence. *Beilstein J. Nanotechnol.* **2015**, *6*, 952–963.
- (29) Wang, Y.; Zhang, Z.; Wang, H.; Bi, S. Segmentation of the Clustered Cells with Optimized Boundary Detection in Negative Phase Contrast Images. *PLoS One* 2015, 10, 1–19.
- (30) Wang, Y.; Lu, T.; Li, X.; Wang, H. Automated image segmentation-assisted flattening of atomic force microscopy images. *Beilstein J. Nanotechnol.* 2018, 9, 975–985.
- (31) Wang, Y.; Zaytsev, M. E.; The, H. L.; Eijkel, J. C. T.; Zandvliet, H. J. W.; Zhang, X.; Lohse, D. Vapor and Gas-Bubble Growth Dynamics around Laser-Irradiated, Water-Immersed Plasmonic Nanoparticles. ACS Nano 2017, 11, 2045–2051.

- (32) Wang, Y.; Li, X.; Ren, S.; Tedros, A. H.; Yang, L.; Lohse, D. Entrapment of interfacial nanobubbles on nano-structured surfaces. *Soft Matter* 2017, 13, 5381–5388.
- (33) Zhang, X.; Wang, J.; Bao, L.; Dietrich, E.; van der Veen, R. C. A.; Peng, S.; Friend, J.; Zandvliet, H. J. W.; Yeo, L.; Lohse, D. Mixed mode of dissolving immersed microdroplets at a solid-water interface. *Soft Matter* **2015**, *11*, 1889–1900.

Graphical TOC Entry

