Dark defect charge dynamics in bulk chemical-vapor-deposition-grown diamonds probed via nitrogen vacancy centers

A. Lozovoi¹, D. Daw^{1,2}, H. Jayakumar¹, C. A. Meriles^{1,2,*}

¹Department of Physics, CUNY - The City College of New York, New York, NY 10031, USA. ²CUNY-Graduate Center, New York, NY 10016, USA.

Abstract

Although chemical vapor deposition (CVD) is one of the preferred routes to synthetic diamond crystals, a full knowledge of the point defects produced during growth is still incomplete. Here we exploit the charge and spin properties of nitrogenvacancy (NV) centers in type-1b CVD diamond to expose an optically and magnetically dark point defect, so far virtually unnoticed despite an abundance comparable to (if not greater than) that of substitutional nitrogen. Indirectly-detected photoluminescence spectroscopy indicates a donor state 1.6 eV above the valence band, although the defect's microscopic structure and composition remain elusive. Our results may prove relevant to the growing set of applications that rely on CVD-grown single crystal diamond.

The development of devices that exploit diamond for applications in emerging areas such as power electronics^{1,2}, quantum information processing³⁻⁷, or nanoscale sensing⁸⁻¹³ hinges on a detailed understanding of the material point defects and their interplay, particularly in the presence of injected or photo-generated charge carriers. This knowledge is especially important in samples created via chemical vapor deposition (CVD), one of the leading growth methods for applications that rely on synthetic single crystals. While various doping techniques have been developed to shape the properties of the host material (e.g., carrier mobility), pure CVD-grown diamond suffers from unwanted contamination during growth (e.g., due to impurities in the gas mixture or from incomplete reaction at the crystal surface), typically leading to the formation of nitrogen- or proton-based complexes 14-17. Despite much progress¹⁸⁻²¹, identifying and cataloguing these CVD-specific defects has proven to be a time-consuming, difficult task, particularly in the case of complexes that do not fluoresce or carry a net electronic spin.

Here we capitalize on the unique properties of the nitrogenvacancy (NV) center²² — a fairly common color center comprising a substitutional nitrogen immediately adjacent to a vacant site — to investigate the dynamics of trapped charge in bulk type 1b CVD-grown diamond. The combined use of fluorescence microscopy, optically detected multi-spin magnetic and photo-luminescence (PL) excitation spectroscopy points to a background defect — here referred to as X — whose concentration is at least comparable to substitutional nitrogen²³ (normally the most abundant in CVD diamond). We find that defect X has no emission in the visible or near-infrared and is (likely) spin-less, probably the reasons why it has remained relatively unnoticed despite its ubiquity. Though we presently cannot derive a concrete atomistic model, our results suggest this point defect may correspond to a proton complex with an acceptor level 1.6 eV above the valence band. Our results are consistent with a prior study²⁴ postulating the presence of defect X to regain balance in the transfer of charge between N⁰ and NVH⁻ in CDV type 1b diamond.

We conduct our experiments in a set of [100] type-1b diamond crystals $(3\times3\times0.1 \text{ mm}^3)$ grown via CVD with a nominal nitrogen concentration of ≤1 ppm and no post treatment. For consistency, we limit our description to the results attained with a CVD-grown sample from Delaware Diamond Knives, though we emphasize virtually identical responses were observed in other type-1b samples with comparable (nominal) nitrogen concentration produced by the same and other manufacturers (e.g., E6). In these samples, there is typically 1 NV every one hundred nitrogen impurities²⁵, i.e., the NV concentration is ≤ 10 ppb. To conduct our experiments, we use a custom-made multi-color optical microscope described before²⁶. Briefly, this system integrates a 532 nm diode laser and a 632 nm He:Ne laser into a 0.43 numerical aperture objective; fluorescence detection is carried out via an avalanche photodetector upon collection into an optical fiber. To separate the emission from neutral and negatively-charged NVs, we use a passband (550-620 nm) and a high-pass (>635 nm) filter, respectively. We conduct optically-detected magnetic resonance experiments (ODMR) with the help of 25-µm-diameter copper wire overlaid on the diamond surface and implement timeresolved measurements using a multi-purpose pulse generator.

To gather initial information on the defect composition of our sample, we first implement a double electron-electron resonance²⁷ (DEER) protocol with the NVs serving as a the optically-detected local spin probe (Fig. 1a). This strategy — already exploited in the past to study both bulk crystals and diamond nanoparticles²⁸⁻³¹ — uses green laser pulses to initialize and readout the NV spin state, as well as synchronous microwave manipulation of the NV spin (MW1) and surrounding paramagnetic defects (MW2). Since the latter are a priori unknown, one can gather valuable information by monitoring the DEER signal — defined as the difference between the NV spin echo response with and without the DEER pulse — as a function of the MW2 frequency.

Fig. 1b shows the results within a frequency window around that expected for spin-1/2 defects at the applied magnetic field

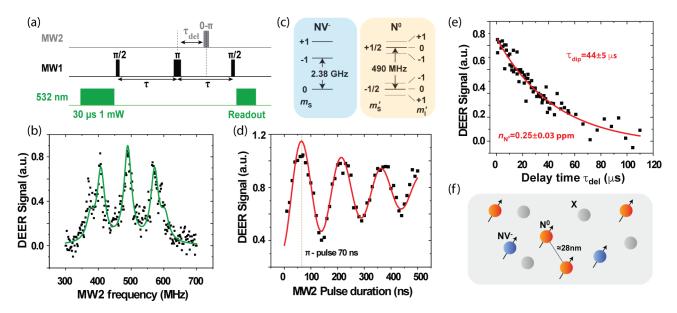


Figure 1. (a) DEER pulse sequence adapted to include a variable delay time $\tau_{\rm del}$ between the MW1 and MW2 inversion pulses. (b) Measured DEER signal as a function of the MW2 frequency for $\tau=57~\mu s$ and $\tau_{\rm del}=0~\mu s$; the solid line is a calculated spectrum using the known ¹⁴N hyperfine coupling constants at the N⁰ site. (c) Ground state energy diagram of the NV⁻ and N⁰ centers (left and right respectively) in a magnetic field of 17 mT aligned with the NV symmetry axis; $m_S~(m_S')$ denotes the NV⁻ (N⁰) electron spin projection number and m_I' is the ¹⁴N spin projection number at the N⁰ site. (d) DEER signal at 490 MHz as a function of the MW2 pulse duration; all other conditions as in (b). The solid trace is a damped sinusoidal and serves as a guide to the eye. (e) DEER signal (at the $m_I'=0$ transition) as a function of $\tau_{\rm del}$ for $\tau=110~\mu s$; the solid line indicates an exponential fit with a time constant $\tau_{\rm dip}=44\pm5~\mu s$ corresponding to an N⁰ concentration $n_{\rm N^0}=0.25\pm0.03~{\rm ppm}$. (f) NV⁻ coexist with N⁰ and a dark defect, referred to as X, at least as abundant as nitrogen, see below.

(17 mT), here oriented parallel with the NV symmetry axis. The observed spectral features — corresponding to ¹⁴N-induced hyperfine shifts — unambiguously point to the presence of N⁰ centers (i.e., spin-1/2 paramagnetic impurities formed by neutral substitutional nitrogen, also known as 'P1', see Fig. 1c). Further, because the amplitude of the central peak relative to the satellites coincides with that expected for N⁰ centers alone (see superimposed solid trace in Fig. 1b), these same observations also allow us to rule out other coexisting spin-1/2 impurities (which would otherwise make the central peak comparatively more prominent²⁹).

To determine the actual nitrogen concentration, we first calibrate the duration of the DEER pulse (Fig. 1d) and subsequently vary the time interval τ_{del} between the π -pulses (Fig. 1e). The observed single-exponential response suggests that each NV center is coupled to multiple P1 centers³². Assuming the measured time constant $\tau_{dip} \approx 73~\mu s$ stems from inter-N⁰ dipolar couplings, we derive^{31,33} an approximate nitrogen concentration of 0.25 ppm, consistent with the manufacturers specifications; this concentration corresponds to an average nitrogen separation of 28 nm (Fig. 1f). For future reference, extensive observations within other frequency windows (corresponding, e.g., to the VH center²¹, not shown) vielded negative results, suggesting that, if at all present, other paramagnetic defects with spin number greater than 1/2 have a concentration lower than nitrogen. We emphasize additional work will be required to validate this notion, as it is nearly impossible to exclude all alternatives (e.g., large crystal fields could shift transitions beyond our experimental range).

A closely related piece of information is presented in Fig. 2. Here we modify the DEER protocol to introduce a variable wait time τ_w after optical charge initialization of the NVs but before application of the MW sequence; we also use a shorter (3 µs) green laser pulse immediately prior to the first MW1 pulse for NV spin repolarization after the wait time (Fig. 2a). Plotting the

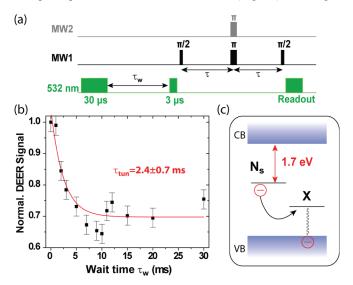


Figure 2. (a) Adapted DEER sequence for monitoring the N charge state. (b) Normalized DEER contrast as a function of the wait time $\tau_{\rm w}$. The amplitudes are recorded at the $m_1'=0$ transition; all other conditions as in Fig. 2. (c) Schematic energy level diagram. The X acceptor level can be populated either by electron tunneling from neighboring N⁰ of by optical injection of a valence electron.

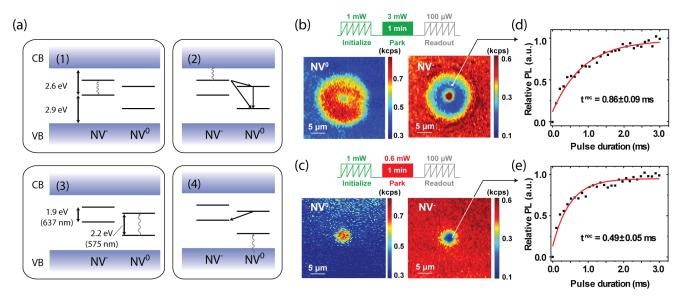


Figure 3. (a) Schematics of NV photochromism under optical (~460-637 nm) excitation. Steps (1) and (2) describe NV⁻ photo-ionization into NV⁰; steps (3) and (4) correspond to recombination of NV⁰ into NV⁻. CB (VB) stands for conduction (valence) band. (b) NV⁰ and NV⁻ selective confocal scans (respectively, left and right) upon application of the upper pulse protocol. Zig-zags (solid rectangles) indicate a beam scan (park); green (red) color indicates laser excitation at 532 nm (632 nm). We use a green (red) laser light for NV⁰ (NV⁻) readout. (c) Same as in (b) but for a red laser park (0.6 mW). In (b) and (c) the park time is 1 min and the scans correspond to 100×100 pixels and a 10 ms dwell time over a 32×32 μm² area. (d) NV⁻ photoluminescence as a function of green laser pulse duration at a point within the NV⁻depleted halo; the laser power is 500 μW. (e) Same as in (d) but at the NV⁻-depleted site created via the protocol in (c).

results as a function of $\tau_{\rm w}$ with all other DEER parameters unchanged, we find a gradual decay with a characteristic time $\tau_{\rm tun}\approx 2.4\,$ ms (Fig. 3b). This result indicates that the $\rm N^0$ concentration decreases after green initialization, a behavior suggestive of electron tunneling to neighboring traps. Note that we can rule out $\rm NV^-$ relaxation as a factor in the observed response, not only because $\rm NV^-$ spins relax slowly (the measured $\rm NV^ T_1$ -time is $\sim 6\,$ ms, longer than $\tau_{\rm tun}$), but, most importantly, because the laser pulse preceding the DEER sequence is sufficiently long to re-pump all NVs into a spin polarized state.

Given the significant fractional change of the observed signal (likely limited by unwanted N^0 reactivation via the 3 μ s laser pulse), we conclude these electron traps are at least as abundant as nitrogen. We tentatively rationalize these results by invoking the presence of a point defect — here named 'X' — presumably a deep acceptor (Fig. 2c, see below). We hypothesize electron capture takes place via tunneling from N^0 (though the non-monotonic decay in Fig. 2b could be indicative of more complex dynamics, a question we defer to future studies).

The model in Fig. 2c also suggest an alternative channel of electron capture via photo-excitation from the valence band, a process necessarily accompanied by the generation of holes. To gather additional information on these traps, we implement the NV photo-conversion experiments in Fig. 3. In the visible range, NV photochromism is generally made possible via two-step, one-photon processes whose exact nature depends on the starting charge state and excitation wavelength³⁴. For example, 'green' laser excitation (532 nm) can ionize negatively charged NVs via the sequential absorption of two photons, successively

promoting the excess electron into the NV excited state, then to the conduction band (Fig. 3a). Conversely, green light excitation of NV⁰ followed by photo-injection of an electron from the valence band can lead to the formation of negatively charged NVs (a process normally referred to as 'recombination'). Continuous 532 nm illumination leads, therefore, to recurring NV charge state interconversion, a process that must be accompanied by a steady stream of diffusing electrons and holes from the NV site into the bulk. Importantly, recombination is largely suppressed under 632 nm illumination, because 'red' photons cannot excite NV⁰ (whose zero-phonon line corresponds to 575 nm, Fig. 3a).

Fig. 3b shows the NV charge pattern emerging from a protocol that starts with a 1 mW green laser scan to (preferentially) initialize NVs into the negatively charged state, followed by a prolonged (1 min) green laser park at the midpoint of the scanned region. Comparison of the left and right panels (respectively selective to NV⁰ and NV⁻), shows that negatively charged NVs in the vicinity of the illumination point gradually transition to the neutral charge state via selective capture of photo-generated holes²⁶. Note that to attain charge neutrality, photo-electrons must be captured by other point defects, arguably positively charged nitrogen²⁶. For future reference, NV⁰ can also form via direct NV⁻ ionization during red illumination³⁴. This is shown in Fig. 3c where we park a 632-nm beam on an NV-initialized plane; we find only local NV charge transformation into the neutral state, consistent with previous work^{26,35}.

A complementary indication of dynamics beyond NV and N charge interconversion is presented in Figs. 3d and 3e (see also

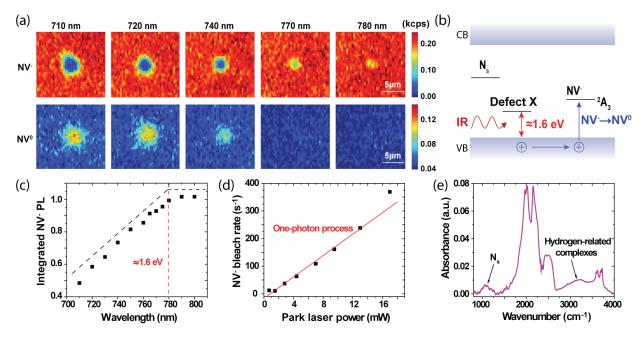


Figure 4. (a) We use a protocol identical to that of Fig. 1c but park an IR beam of variable wavelength. Top (bottom) panels show the NV $^{-}$ (NV 0) fluorescence after a 5 s, 20 mW laser park; all other conditions as in Fig. 1c. (b) Proposed mechanism of the NV $^{-}$ bleaching involving the promotion of the electron from the valence band into defect X and capture of the created hole by NV $^{-}$. (c) Integrated NV $^{-}$ photoluminescence in a 2.8×2.8 μ m around the point of illumination as a function of the illumination wavelength. (d) Decay rate of the NV $^{-}$ fluorescence under 710 nm illumination as a function of the illumination power; the red line is a linear fit. (e) Fourier-transformed infrared absorbance spectrum.

the schematic model in Fig. 2c): Using a 532-nm laser pulse of variable duration, we monitor NV^0 recombination after parking the beam in NV^- -depleted areas produced either via hole capture or red-laser-induced ionization. Remarkably, we find that the observed recombination time is substantially longer for NVs initialized via hole capture, a result we find systematically, irrespective of the exact position within the doughnut-shaped area around the point of illumination (below referred to as the 'halo'). Taking into account the ensemble nature of our measurements (there are $\sim\!500~\text{NV}$ per μm^3 at a concentration of 2.5 ppb) we interpret this finding as an indication of greater hole recapture efficiency, in turn, a consequence of changes in the charge state of defect X, impacted differently depending on the charge initialization protocol.

Although a quantitative description is not presently possible, we gain a crude understanding by considering the rate equation governing the NV^0 density,

$$\frac{dQ_0}{dt} = -k_0 Q_0 + \kappa_p p(Q - Q_0),\tag{1}$$

where k_0 is the recombination rate under green light, κ_p is the NV hole volume capture, p is the hole density, and $Q = Q_0 + Q_-$ is the total NV density. For simplicity, Eq. (1) ignores back-conversion of NV into NV via photo-ionization as well as electron capture by NV (a good approximation in these samples³⁵). The second term in the sum amounts to NV formation via NV ionization from hole capture, a process that effectively slows down the recombination of NV, governed by the first term. The hole concentration, in turn, is largely

dependent on the charge state of X (see Fig. 2c), an interplay that can be cast as

$$\frac{dp}{dt} = -Dp + k_X X_0 - \lambda_p p(X - X_0), \tag{2}$$

and

$$\frac{dX_0}{dt} = -k_X X_0 + \lambda_p p(X - X_0),\tag{3}$$

where D represents an effective hole loss rate due to diffusion outside the point of illumination, X_0 denotes the local density of X defects in the neutral charge state, $X = X_0 + X_-$ is the total density of X defects, k_X is the conversion rate of X^0 into the negatively charged state under green light, and λ_p is the hole volume charge trapping rate by X. In Eq. (2) we ignore hole capture by neutral nitrogen (characterized by a low cross section^{36,37}). Further, since presumably $X \gg Q$, we ignore the generation of holes via NV^0 recombination, as well as hole capture by NV^- , processes we assume dominated by the interconversion between X^0 and X^- .

From Eqs. (2) and (3), we conclude that the concentration of holes reaches a larger value if the starting charge state of X is neutral, as green optical excitation pumps electrons from the valence band in large numbers, i.e., the $k_X X_0$ term becomes dominant and the concentration of holes grows (see also Fig. 2c), effectively reducing the rate of NV⁰ recombination in Eq. (1). This is precisely the starting condition in Fig. 3d, where holes (previously diffusing from the point of illumination under the park beam during preparation, Fig. 3b) arguably neutralize both

NV and X in the halo region. In the converse limit (i.e., when most X defects are initially negatively charged), the number of holes — now limited to those emerging from NV^0 recombination, not considered here — decreases, while hole capture by X^- is maximal (last term on the right-hand side of Eqs. (2) and (3)). This is the starting point in Fig. 3e, where the preceding NV^- ionization is arguably accompanied by the conversion of X into the negatively charged state.

For completeness, we mention that detection of NV⁰ fluorescence during green illumination (not shown for brevity), yields a monotonic exponential decay, indicative of a gradual conversion from neutral to negatively charged NVs. Combined with Figs. 3d and 3e, these observations allow us to rule out the formation of positively charged states³⁸ (potentially produced via the consecutive capture of two diffusing holes), as NV⁺ would arguably reconvert first into neutral and thus lead to a transient growth of NV⁰ during green illumination, in conflict with experiment.

To further these ideas, we implement one more time the laser protocol in Fig. 3c but we replace the 632-nm beam during the park by infra-red excitation in the range 710-800 nm (Fig. 4a). Remarkably, we find that NVs locally transform to neutral even though the photon energy is significantly below the minimum required (637 nm) to activate the two-step ionization process discussed above (Fig. 3a). Local NV→ NV⁰ conversion at the site of illumination points, therefore, to the presence of holes, here generated through trapping of electrons photoexcited from the valence band into the X acceptor level (Fig. 4b). Interestingly, NVs act in this case as charge reporters exposing a process otherwise difficult to observe.

Longer excitation wavelengths gradually lead to less efficient NV ionization, until virtually no NV charge conversion is observed at 780 nm. By plotting the integrated NV fluorescence as a function of wavelength, we conclude the X acceptor level lies ~1.6 eV above the valence band (Fig. 4c). Further, at a given wavelength the NV bleaching rate grows almost linearly with the laser power, hence supporting the notion of a single photon absorption process (Fig. 4d). Note this observation allows one to rule out other, unknown NV

References

- ¹ B. Huang, X. Bai, S.K. Lam, K.K. Tsang, "Diamond FinFET without hydrogen termination", *Sci. Rep.* **8**, 3063 (2018).
- ² Power electronics device applications of diamond semiconductors, S. Koizumi, H. Umezawa, J. Pernot, M. Suzuki, Eds., Elsevier, 2018.
- ³ L. Childress, M.V. Gurudev Dutt, J.M. Taylor, A.S. Zibrov, F. Jelezko, J. Wrachtrup, P.R. Hemmer, M.D. Lukin, "Coherent dynamics of coupled electron and nuclear spin qubits in diamond", *Science* **314**, 281 (2006).
- ⁴ B. Hensen, H. Bernien, A.E. Dréau, A. Reiserer, N. Kalb, M.S. Blok, J. Ruitenberg, R.F.L. Vermeulen, R.N. Schouten, C. Abellán, W. Amaya, V. Pruneri, M.W. Mitchell, M. Markham, D.J. Twitchen, D. Elkouss, S. Wehner, T.H. Taminiau, R. Hanson, "Loophole-free Bell inequality violation using electron spins separated by 1.3 kilometres", *Nature* **526**, 682 (2015).

ionization channels (involving, e.g., excitation into non-ground singlet states or via a phonon-assisted transition into the excited triplet) as they all necessarily fall in the category of two-step, one-photon processes, known to depend quadratically on the excitation laser power.

In summary, by exploiting the singular spin and charge properties of the NV, we reveal the presence of a coexisting point defect featuring a deep acceptor level. Though optically (and magnetically) dark, defect X is found to have an abundance at least comparable to substitutional nitrogen in CVD type 1b diamond. In the absence of site symmetry information, we can only hypothesize about its microscopic structure. N-based complexes seem less likely as they presumably have a concentration considerably lower than substitutional nitrogen. Hydrogen, on the other hand, is known to be a common contaminant in CVD diamond and several H-based point defects have already been identified and characterized. The absorption band in the 2800–3400 cm⁻¹ range — associated to CH stretching modes — in the infra-red spectrum of Fig. 4e supports the presence of hydrogen in our samples. Interestingly, computational studies¹⁸ show that the ground state of the VH (VH⁰) point defect lies 1.67 eV (1.4 eV) above the valence band. However, observations at the expected resonance frequency the VH⁻ has spin number S' = 1 and a crystal field of 2.7 GHz²⁰ — yielded no DEER signal, suggesting defect X is different. The same applies to the NVH defect, forming a paramagnetic, spin-1/2 complex in the negative and positive charge states 17,20,21. Additional work will therefore be mandatory to reveal the microscopic structure of defect X, likely to impact the performance of devices based on CVD diamond.

We thank Vasilios Deligiannakis and Maria Tamargo for assistance with the infra-red measurements. We acknowledge support from the National Science Foundation through grant NSF-1914945, and from Research Corporation for Science Advancement through a FRED Award; we also acknowledge access to the facilities and research infrastructure of the NSF CREST IDEALS, grant number NSF-HRD-1547830.

- ⁵ N. Kalb, A.A. Reiserer, P.C. Humphreys, J.J.W. Bakermans, S.J. Kamerling, N.H. Nickerson, S.C. Benjamin, D.J. Twitchen, M. Markham, R. Hanson, "Entanglement distillation between solid-state quantum network nodes", *Science* **356**, 928 (2017).
- ⁶ M.W. Doherty, C.A. Meriles, A. Alkauskas, H. Fedder, M.J. Sellars, N.B. Manson, "Towards a room-temperature spin quantum bus in diamond via electron photoionization, transport, and capture", *Phys. Rev. X* **6**, 041035 (2016).
- ⁷ M.H. Metsch, K. Senkalla, B. Tratzmiller, J. Scheuer, M. Kern, J. Achard, A. Tallaire, M.B. Plenio, P. Siyushev, F. Jelezko "Initialization and readout of nuclear spins via a negatively charged silicon-vacancy center in diamond", *Phys. Rev. Lett.* **122**, 190503 (2019).
- ⁸ M.S. Grinolds, S. Hong, P. Maletinsky, L. Luan, M.D. Lukin, R.L. Walsworth, A. Yacoby, "Nanoscale magnetic imaging of a

- single electron spin under ambient conditions", *Nat. Phys.* **9**, 215 (2013).
- ⁹ F. Dolde, H. Fedder, M.W. Doherty, T. Nöbauer, F. Rempp, G. Balasubramanian, T. Wolf, F. Reinhard, L.C.L. Hollenberg, F. Jelezko, J. Wrachtrup, "Electric-field sensing using single diamond spins", *Nat. Phys.* **7**, 459 (2011).
- ¹⁰ A. Laraoui, H. Aycock-Rizzo, Y. Gao, X. Lu, E. Riedo, C. A. Meriles, "Imaging thermal conductivity with nanoscale resolution using a scanning spin probe", *Nat. Commun.* **6**, 8954 (2015).
- ¹¹ J.-P. Tetienne, T. Hingant, J.-V. Kim, L. Herrera Diez, J.-P. Adam, K. Garcia, J.-F. Roch, S. Rohart, A. Thiaville, D. Ravelosona, V. Jacques, "Nanoscale imaging and control of domain-wall hopping with a nitrogen-vacancy center microscope", *Science* **344**, 1366 (2014).
- ¹² H.J. Mamin, M. Kim, M.H. Sherwood, C.T. Rettner, K. Ohno, D.D. Awschalom, D. Rugar, "Nanoscale nuclear magnetic resonance with a nitrogen-vacancy spin sensor", *Science* **339**, 557 (2013).
- ¹³ T. Staudacher, F. Shi, S. Pezzagna, J. Meijer, J. Du, C.A. Meriles, F. Reinhard, J. Wrachtrup, "Nuclear magnetic resonance spectroscopy on a (5 nm)³ volume of liquid and solid samples", *Science* **339**, 561 (2013).
- ¹⁴ R. Jones, "Dislocations, vacancies and the brown colour of CVD and natural diamond", *Diam. Rel. Mater.* **18**, 820 (2009).
- ¹⁵ J.E. Butler, Y.A. Mankelevich, A. Cheesman, J. Ma, M.N.R. Ashfold, "Understanding the chemical vapor deposition of diamond: recent progress", *J. Phys. Cond. Matter* **21**, 364201 (2019).
- ¹⁶ R.U.A. Khan, "Colour-causing defects and their related optoelectronic transitions in single crystal CVD diamond", *J. Phys. Cond. Matt.* **25**, 275801 (2013).
- ¹⁷ X. Zhou, G. D. Watkins, K.M. McNamara Rutledge, R.P. Messmer, S. Chawla, "Hydrogen-related defects in polycrystalline CVD diamond", *Phys. Rev. B* 54, 7881 (1996).
- ¹⁸ C.V. Peaker, J.P. Goss, P.R. Briddon, A.B. Horsfall, M.J. Rayson, "The vacancy–hydrogen defect in diamond: A computational study", *Phys. Stat. Solidi A* **212**, 2431 (2015).
- ¹⁹ C. Glover, M.E. Newton, P. Martineau, D.J. Twitchen, J.M. Baker, "Hydrogen incorporation in diamond: the nitrogen-vacancy-hydrogen complex", *Phys. Rev. Lett.* **90**, 185507 (2003).
- ²⁰ C. Glover, M. E. Newton, P. M. Martineau, S. Quinn, D. J. Twitchen, "Hydrogen Incorporation in diamond: The vacancy-hydrogen complex", *Phys. Rev. Lett.* **92**, 135502 (2004).
- ²¹ J.P. Goss, P.R. Briddon, R. Jones, S. Sque, "The vacancy-nitrogen-hydrogen complex in diamond: A potential deep centre in chemical vapour deposited material", *J. Phys. Cond. Matter* **15**, 2903 (2003).
- ²² M.W. Doherty, N.B. Manson, P. Delaney, F. Jelezko, J. Wrachtrup, L.C.L. Hollenberg, "The nitrogen-vacancy colour centre in diamond", *Phys. Rep.* **528**, 1 (2013).
- ²³ R.G. Farrer, "On the substitutional nitrogen donor in diamond", *Sol. State Commun.* 7, 685 (1969).

- ²⁴ R.U.A. Khan, P.M. Martineau, B.L. Cann, M.E. Newton, D.J. Twitchen, "Charge transfer effects, thermo and photochromism in single crystal CVD synthetic diamond", *J. Phys. Cond. Matter* **21**, 364214 (2009).
- ²⁵ A.M. Edmonds, U.F.S. D'Haenens-Johansson, R.J. Cruddace, M.E. Newton, K.-M.C. Fu, C. Santori, R.G. Beausoleil, D.J. Twitchen, M.L. Markham, "Production of oriented nitrogenvacancy color centers in synthetic diamond", *Phys. Rev. B* **86**, 035201 (2012).
- ²⁶ H. Jayakumar, J. Henshaw, S. Dhomkar, D. Pagliero, A. Laraoui, N.B. Manson, R. Albu, M.W. Doherty, C.A. Meriles, "Optical patterning of trapped charge in nitrogen-doped diamond", *Nat. Commun.* 7, 12660 (2016).
- ²⁷ R.G. Larsen, D.J. Singel, "Double electron-electron resonance spin-echo modulation: spectroscopic measurement of electron spin pair separations in orientationally disordered solids", *J. Chem. Phys.* **98**, 5134 (1993).
- ²⁸ R.J. Epstein, F.M. Mendoza, Y.K. Kato, D.D. Awschalom, "Anisotropic interactions of a single spin and dark-spin spectroscopy in diamond", *Nat. Physics* 1, 94 (2005).
- ²⁹ A. Laraoui, J.S. Hodges, C.A. Meriles, "Nitrogen-Vacancy-assisted magnetometry of paramagnetic centers in an individual diamond nanocrystal", *Nano Lett.* **12**, 3477 (2012).
- ³⁰ A. Laraoui, C.A. Meriles, "Approach to dark spin cooling in a diamond nanocrystal", *ACS Nano* 7, 3403 (2013).
- ³¹ V. Stepanov, S. Takahashi, "Determination of nitrogen spin concentration in diamond using double electron-electron resonance", *Phys. Rev. B* **94**, 024421 (2016).
- ³² B. Grotz, J. Beck, P. Neumann, B. Naydenov, R. Reuter, F. Reinhard, F. Jelezko, J. Wrachtrup, D. Schweinfurth, B. Sarkar, P. Hemmer, "Sensing external spins with nitrogen-vacancy diamond", *New J. Phys.* **13**, 055004 (2011).
- ³³ K. Salikhov, S. Dzuba, A. Raitsimring, "The theory of electron spin-echo signal decay resulting from dipole-dipole interactions between paramagnetic centers in solids", *J. Mag. Reson.* **42**, 255 (1981).
- ³⁴ N. Aslam, G. Waldherr, P. Neumann, F. Jelezko, J. Wrachtrup, "Photo-induced ionization dynamics of the nitrogen vacancy defect in diamond investigated by single-shot charge state detection", *New J. Phys.* **15**, 013064 (2013).
- ³⁵ S. Dhomkar, P. Zangara, J. Henshaw, C.A. Meriles, "Ondemand generation of neutral and negatively-charged siliconvacancy centers in diamond", *Phys. Rev. Lett.* **120**, 117401 (2018).
- ³⁶ L.S. Pan, D.R. Kania, P. Pianetta, O.L. Landen, "Carrier density dependent photoconductivity in diamond", *Appl. Phys. Lett.* **57**, 623 (1990).
- ³⁷ S. Han in *Diamond: Electronic Properties and Applications*, ed. L.S. Pan, D.R. Kania (Springer Science, New York, 1995).
- ³⁸ M. Pfender, N. Aslam, P. Simon, D. Antonov, G. Thiering, S. Burk, F. Fávaro de Oliveira, A. Denisenko, H. Fedder, J. Meijer, J.A. Garrido, A. Gali, T. Teraji, J. Isoya, M. William Doherty, A. Alkauskas, A. Gallo, A. Grüneis, P. Neumann, J. Wrachtrup, "Protecting a diamond quantum memory by charge state control", *Nano Lett.* **17**, 5931 (2017).