

Charge disproportionation and nano phase separation in $RSrNiO_4$

H. Guo¹, Z. W. Li^{1,2}, C. F. Chang¹, Z. Hu¹, C.-Y. Kuo^{1,3}, T. G. Perring⁴, W. Schmidt⁵, A. Piovano⁶, K. Schmalzl⁵, H. C. Walker⁴, H. J. Lin³, C. T. Chen³, S. Blanco-Canosa^{7,8}, J. Schlappa⁹, C. Schüßler-Langeheine¹⁰, P. Hansmann¹, D. I. Khomskii¹¹, L. H. Tjeng¹, and A. C. Komarek^{1,*}

¹Max-Planck-Institute for Chemical Physics of Solids, Nöthnitzer Str. 40, D-01187 Dresden, Germany

²Institute of Applied Magnetism, Key Lab for Magnetism and Magnetic Materials of the Ministry of Education, Lanzhou University, Lanzhou 730000, People's Republic of China

³National Synchrotron Radiation Research Center (NSRRC), 101 Hsin-Ann Road, Hsinchu 30076, Taiwan

⁴ISIS Facility, STFC Rutherford Appleton Laboratory, Harwell Oxford, Didcot, OX11 0QX, United Kingdom

⁵Forschungszentrum Jülich GmbH, Jülich Centre for Neutron Science at ILL, 71 avenue des Martyrs, 38000 Grenoble, France

⁶Institut Laue-Langevin, Boite Postale 156X, F-38042 Grenoble Cedex 9, France

⁷IKERBASQUE, Basque Foundation for Science, 48013 Bilbao, Basque Country, Spain

⁸Donostia International Physics Center, DIPC, 20018 Donostia-San Sebastian, Basque Country, Spain

⁹European X-ray Free Electron Laser Facility GmbH, Holzkoppel 4, 22869 Schenefeld, Germany

¹⁰Helmholtz-Zentrum Berlin für Materialien und Energie GmbH, Albert-Einstein-Str. 15, 12489 Berlin, Germany

¹¹Physics Institute II, University of Cologne, Zùlpicher Str. 77, 50937 Cologne, Germany

*Alexander.Komarek@cpfs.mpg.de

ABSTRACT

We have successfully grown centimeter-sized layered $RSrNiO_4$ single crystals under high oxygen pressures of 120 bar by the floating zone technique. This enabled us to perform neutron scattering experiments where we observe close to quarter-integer magnetic peaks below ~ 77 K that are accompanied by steep upwards dispersing spin excitations. Within the high-frequency Ni-O bond stretching phonon dispersion, a softening at the propagation vector for a checkerboard modulation can be observed. Together with our spin wave simulations these observations reveal that this Ni^{3+} system exhibits charge disproportionation with charges segregating into a checkerboard pattern within a nano phase separation scenario rather than showing a Jahn-Teller effect.

Introduction

One of the very interesting classes of transition metal compounds showing quite unusual and rich properties are the rare earth (RE) perovskite nickelates $RNiO_3$, containing Ni ions in a nominal low-spin $3+$ state in octahedral coordination. As was shown starting with the work of Torrance *et al.*,¹ for small RE ions there exist two transitions in these systems, from the high-temperature metallic orthorhombic state $Pbnm$ to a low-temperature insulating monoclinic phase $P2_1/n$, accompanied by magnetic ordering at lower temperatures with a rather unusual magnetic structure with the wave vector $Q=(1/4, 1/4, 1/4)$ (in pseudocubic notation), i.e. with ordering of the type $\uparrow\uparrow\downarrow\downarrow$ in all three directions. For $NdNiO_3$ and $PrNiO_3$ the magnetic transition and the structural transition merge into a common first order phase transition which simultaneously is a metal-insulator transition. And for the largest RE ion La, the rhombohedral $LaNiO_3$ remains metallic down to the lowest temperatures, and was supposed to be paramagnetic until signatures of antiferromagnetic correlations, with about the same magnetic propagation vector $Q=(1/4, 1/4, 1/4)$, have recently also been discovered in $LaNiO_3$ single crystals grown under high oxygen pressure.²

It is remarkable that the Jahn-Teller distortion expected for the nominal low-spin configuration $t_{2g}^6 e_g^1$ does not materialize in this $RNiO_3$ system. This was explained early on^{3,4} by the idea of charge disproportionation of the type $2 \cdot Ni^{3+} \rightarrow Ni^{2+} + Ni^{4+}$ which actually occurs rather on the ligands. The Ni^{3+} and even more so the Ni^{4+} in oxides have very small or negative charge transfer energies $\Delta (= E(d^{(n+1)}2p^5) - E(d^n 2p^6))$,⁵⁻⁷ so that the charge disproportionation should be viewed rather as $2 \cdot (Ni^{2+} \underline{L}) \rightarrow Ni^{2+} + Ni^{2+} \underline{L}^2$, where \underline{L} stands for a ligand hole, which could then be termed as a valence bond disproportionation.⁸ This picture explains the structural transitions in $RNiO_3$, at which inequivalent Ni ions appear.⁹ Moreover, within the charge disproportionation scenario also the low-temperature magnetic structure of the $\uparrow\uparrow\downarrow\downarrow$ type³ is naturally explained. However,

so far, only ‘ad-hoc’ configuration interaction models exist, and the phenomenon remains elusive from the point of view of *ab-initio* theories.^{10,11} Note that the tendency to a charge, or valence bond disproportionation is a local property. However, there exists also an alternative picture,^{12,13} relying mainly on the Fermi-surface properties of metallic nickelates, which is actually a collective, not local physics.

The interesting question now arises whether the charge or valence bond disproportionation still wins over the Jahn-Teller distortion for Ni^{3+} oxides where the local coordination is no longer O_h .^{14,15} For example, the layered system RSrNiO_4 has a K_2NiF_4 crystal structure with NiO_6 octahedra that are elongated along the tetragonal axis. In such a case would the charge disproportionation be absent and instead the Jahn-Teller $t_{2g}^6 e_g^1$ be stabilized? Electronic structure calculations in the LDA+NMTO downfolding scheme predict the $3z^2-r^2$ orbital to be more stable than the x^2-y^2 orbital by about ~ 0.26 eV,^{16–18} which is a large energy difference regarding an optical gap of $\lesssim 0.2$ eV. However, until now one could not prepare large high quality single crystals of these layered Ni^{3+} 2-1-4-nickelates. $\text{R}_{2-x}\text{Sr}_x\text{NiO}_4$ have so far been studied only for doping levels x away from the $x=1$ pure Ni^{3+} situation. It is known, for example, that for $x \ll 1$ that there is $\text{Ni}^{2+}/\text{Ni}^{3+}$ charge order which modulates the spin structure.^{19–21} At half-doping, i.e. for $x = 0.5$, a $\text{Ni}^{2+}/\text{Ni}^{3+}$ checkerboard charge ordering occurs²² similar to the isostructural cobaltates.^{23–28} This checkerboard charge order survives up to $\sim 70\%$ of hole-doping²⁹ and the materials stay insulating.

Some initial studies on single crystals of highly hole-doped $\text{R}_{2-x}\text{Sr}_x\text{NiO}_4$ exist and report an about equal population of four different kind of states around $x \sim 1$: Ni^{2+} , Ni^{3+} with $3z^2-r^2$ orbital occupation, Ni^{3+} with x^2-y^2 orbital occupation and Ni^{4+} .³⁰ Moreover, also ARPES studies on these materials exist.^{16,17}

However, so far, no detailed study of the physical properties of the compounds with the pure Ni^{3+} oxidation state have been carried out and it is unknown whether a Jahn-Teller orbital occupation can be stabilized by the strongly distorted Ni-oxygen environment instead of the $\text{Ni}^{2+}/\text{Ni}^{4+}$ or $\text{Ni}^{2+}/\text{Ni}^{3+}$ charge disproportionation. We note that the mechanism for such a charge disproportionation phenomenon is quite distinct from that for a $\text{Ni}^{2+}/\text{Ni}^{3+}$ charge ordering since a disproportionation in a stoichiometric system involves an energy term related to the on-site Coulomb interaction U (which needs to be compensated by another interaction energy), while for ordering of charge in a non-stoichiometric or doped material the term U is not operative.

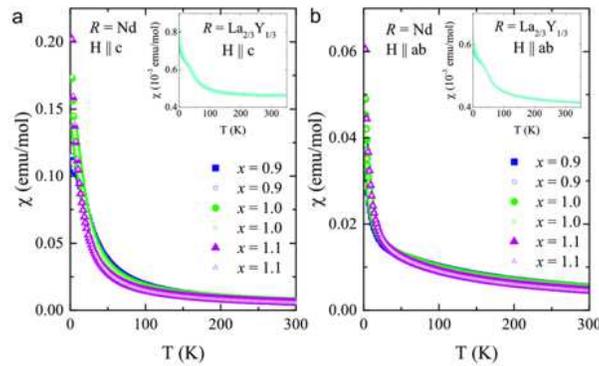


Figure 1. Magnetic susceptibility - Temperature dependence of the magnetic susceptibility χ for $\text{Nd}_{2-x}\text{Sr}_x\text{NiO}_4$ (in the main panel) and $\text{La}_{2/3}\text{Y}_{1/3}\text{SrNiO}_4$ (in the inset). Solid/open symbols denote ZFC /FC measurements. Note, that the magnetic susceptibility of NdSrNiO_4 is governed by the Nd^{3+} ions, which masks the signal from the Ni moments.

Results

Powder X-ray diffraction shows that our NdSrNiO_4 samples are impurity-free. From the refinement of the powder X-ray diffraction data we obtain a c/a ratio that amounts to ~ 3.26 and apical and basal Ni-O distances which amount to $2.058(8)$ Å and $1.895(1)$ Å respectively, thus, indicating a strongly tetragonally distorted oxygen environment with an apical-to-basal distance ratio of 1.09.

The magnetic susceptibility in NdSrNiO_4 is dominated by the Nd^{3+} moments, see Fig. 1. For $\text{La}_{2/3}\text{Y}_{1/3}\text{SrNiO}_4$ with non-magnetic R -ions the effective moment of Ni can be determined and amounts to $\sim 0.23 \mu_B/\text{Ni}$ according to Curie-Weiss fits.

The temperature dependence of the in-plane resistivity is shown in Fig. 2. A bad metallic behavior can be observed at high temperatures followed by a semiconducting temperature dependence at lower temperatures, thus, indicating a (gradual) metal-semiconductor transition around ~ 150 K.

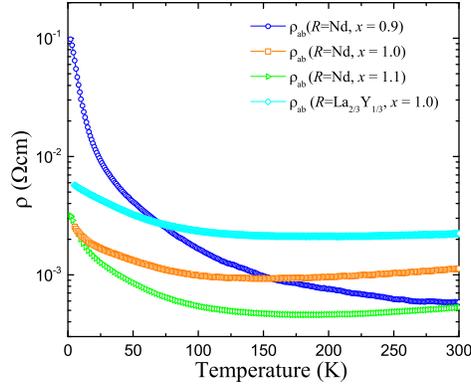


Figure 2. Electrical resistivity - Temperature dependence of the in-plane resistivity $\rho_{ab}(T)$ for $\text{Nd}_{2-x}\text{Sr}_x\text{NiO}_4$ and $\text{La}_{2/3}\text{Y}_{1/3}\text{SrNiO}_4$.

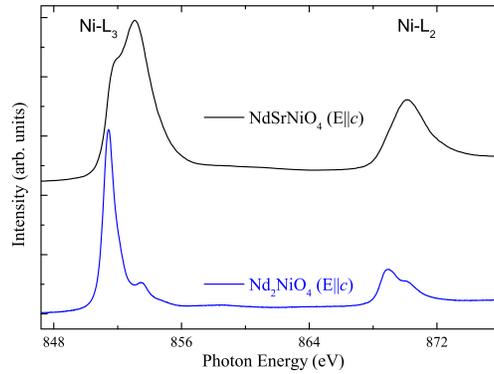


Figure 3. X-ray absorption spectroscopy - Ni- $L_{2,3}$ XAS spectra of the NdSrNiO_4 single crystal and - for comparison - a Nd_2NiO_4 single crystal measured at 300 K.

The Ni- $L_{2,3}$ x-ray absorption spectrum of our NdSrNiO_4 single crystal is shown in Fig. 3 and is compared to that of our Nd_2NiO_4 single crystal serving as a Ni^{2+} reference compound. It is well known that the XAS spectra at the $L_{2,3}$ edge of transition metals are highly sensitive to the valence state³¹⁻³³ - an increase of the valence state of the transition metal ion by one causes a shift of the XAS $L_{2,3}$ spectra by one or more eV towards higher energies. The more than one eV higher energy shift from Nd_2NiO_4 to NdSrNiO_4 indicates the formal Ni^{2+} and Ni^{3+} valence states for the former and the latter compound respectively. Here we would like to note that the NdSrNiO_4 spectrum cannot be interpreted in terms of an ionic Ni $3d^7$ configuration, but, rather by a coherent mixture of $3d^8$ and $3d^8\bar{L}^2$ configurations,^{3,7,34,35} where each \bar{L} denotes a hole in the oxygen ligand. We can exclude any Ni^{2+} impurities in our NdSrNiO_4 single crystal, otherwise the sharp main peak of Ni^{2+} impurity spectrum would have been visible as a sharp shoulder at the leading edge.

Due to the availability of large single crystals we are now able to perform (polarized) neutron scattering experiments on RSrNiO_4 . As shown in Fig. 4, at low temperatures (i.e. below $T_N \sim 80$ K) magnetic peaks could be detected around quarter-integer positions within the $HK0$ plane of reciprocal space. The magnetic origin of these peaks can be confirmed by polarization analysis and the extracted M_y and M_z components are shown in Fig. 4. Gaussian functions are fitted to the data. In NdSrNiO_4 the Ni moments start ordering below ~ 77 K, see Fig. 5. Close to 70 K, the intensities of the M_y and M_z components are comparable, thus, indicating that the magnetic moments are canted out of the ab plane first. But, on further cooling below 60 K the M_y component increases while the M_z component almost vanishes, thus, demonstrating that the magnetic moments become confined to the ab plane. For NdSrNiO_4 the M_z component increases substantially on further cooling below 30 K. This can be attributed to the ordering of the Nd moments in c direction at lowest temperatures. The resulting values for fitted intensities and peak positions are plotted in Fig. 5.

Additionally, we measured also the temperature dependence of the Nd- and Ni- contribution of the antiferromagnetic reflections by means of resonant soft X-ray diffraction,³⁶ see Fig. 6. These element selective measurements corroborate our findings that the Nd-moments start to order at distinctly lower temperatures than the Ni-moments. Note, that resonant X-rays are element specific and not probing the same magnetic intensity as neutrons are doing. Also short range correlations will

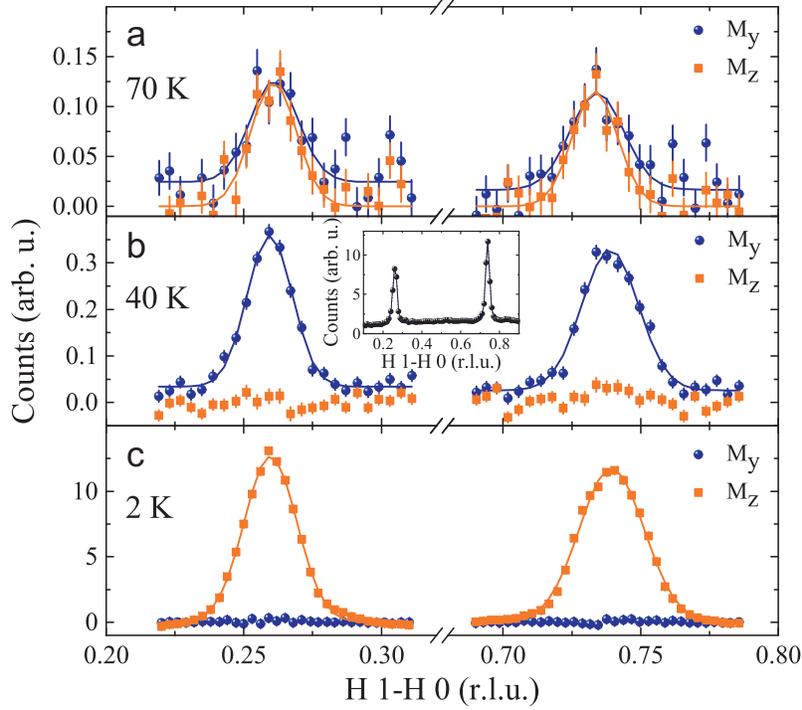


Figure 4. Neutron diffraction - Elastic, polarized neutron scattering measurements of NdSrNiO₄ measured at the IN12 spectrometer showing the extracted M_y and M_z components for $[H, 1-H, 0]$ - scans at different temperatures of (a) 70 K, (b) 40 K and (c) 2 K. The solid curves are Gaussian fits. The inset in (b) shows unpolarized neutron scattering intensities measured at the IN8 spectrometer within a larger range.

be less integrated in this measurement due to the higher resolution which might result in a different temperature dependence compared to the neutron results.

As shown in Fig. 7(a) and (b), the magnetic fields suppress the magnetic reflection intensities drastically at 2 K, while having almost no influence at 40 K, which can be seen more clearly from the extracted magnetic field dependence of the integrated intensities using a Gaussian fit to the data, as shown in Fig. 7(c) and (d). These results reflect the full polarization of the Nd³⁺ moments below the Nd-magnetic ordering temperatures in fields above 6 T whereas the (much smaller) Ni magnetic moments (that are observable at 40 K) are much less affected.

Summarizing, distinctly below T_N (e.g. around 40 K) the Ni magnetic moments are aligned within the ab planes. For NdSrNiO₄ also the Nd moments start ordering below roughly 20 K with the larger Nd moments being aligned in the c -direction. The observation of quarter integer magnetic peaks in $RSrNiO_4$ is compatible with a charge disproportionation of the nominal Ni³⁺ ($3d^7$) ions into a $3d^8/3d^8L^2$ configurations. The ordering of these charges is in a checkerboard pattern.

This kind of charge ordering is also in agreement with our inelastic neutron measurements of the longitudinal Ni-O bond stretching phonon mode, compare also Ref.²³ For high- T_C superconducting cuprates it is known that such phonon softening of the Cu-O bond stretching phonon modes has been observed at the propagation vector of the underlying charge (stripe) order,³⁷ i.e. one would expect a bond-stretching phonon anomaly at the propagation vector of the underlying charge ordering propagation vector. As can be seen in Fig. 8(a), this high-frequency phonon dispersion softens for NdSrNi³⁺O₄ at half-integer propagation vectors similar to that in *half-doped* cobaltates with very robust checkerboard charge order.²³ In contrast to that, the same measurement of the *pure* Co³⁺ reference material LaSrCo³⁺O₄ - see Fig. 8(b) - reveals no such phonon softening at the zone boundary i.e. towards $\mathbf{Q} = (2.5 \ 2.5 \ 0)$.

In NdSrNiO₄ the static distortions implied by this kind of charge distribution could not be detected in analogous elastic neutron measurements. However, these distortions might be too weak to be detectable possibly because of small distortions that are associated with the charge disproportionation since the charges are delocalized towards the oxygen ions. A similar situation might occur in LaNiO₃.² Note that soft X-rays are unable to reach the required points in reciprocal space and that resonant hard x-ray scattering is unfavorable since any gain in intensity at the K-edge is marginal and will be overcompensated by the effects of fluorescence.

Finally, we measured the magnetic excitation spectrum of La_{2/3}Y_{1/3}SrNiO₄ at 6 K (at the MERLIN time-of-flight spec-

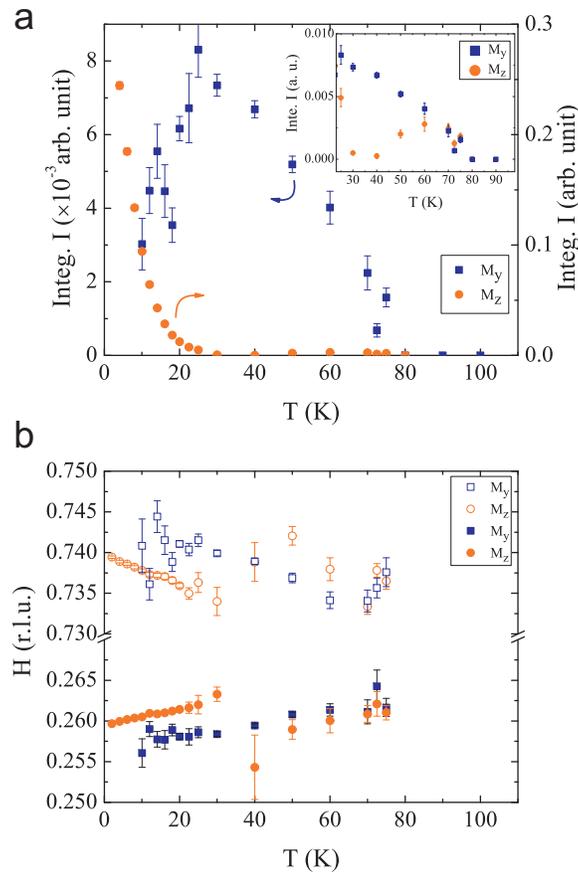


Figure 5. Analysis of polarized neutron data - Fitting results for NdSrNiO_4 . (a) Temperature dependence of the integrated intensities for the M_y and M_z components for the peak near $(0.25, 0.75, 0)$. Note the different scales for the two components. The inset shows an enlargement of the high temperature regime. (b) Temperature dependence of the peak position at $(H \ 1-H \ 0)$.

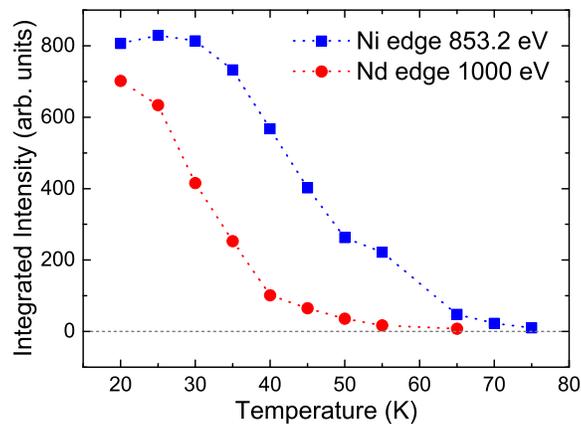


Figure 6. Resonant X-ray diffraction - Temperature dependence of the magnetic intensities at the $\text{Nd-}M_5$ and $\text{Ni-}L_3$ resonances.

trometer with an incident energy of 41 meV), see Fig. 9. These measurements show that these nickelates are different from the usual magnets - an upward dispersion becomes apparent which strongly resembles the one in highly hole-doped cobaltates,²⁶ see Fig. 9(c). In the cobaltates this excitation spectrum could be explained by a nano phase separation model²⁴ with two relevant exchange interactions - one between two Co^{2+} -ions across a hole (J') and a much weaker one across two or

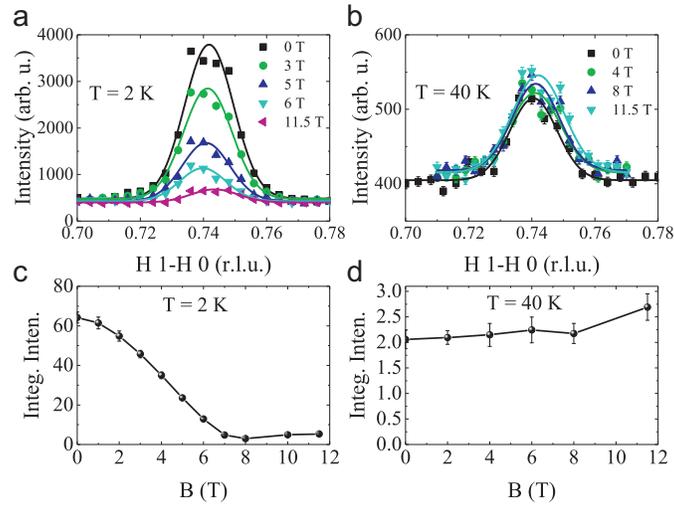


Figure 7. Magnetic field dependence - Magnetic field dependence of the neutron intensities measured along the $[H, 1-H, 0]$ direction at (a) 2 K and (b) 40 K in NdSrNiO₄. (c, d) The magnetic field dependence of the integrated intensities at 2 and 40 K, respectively.

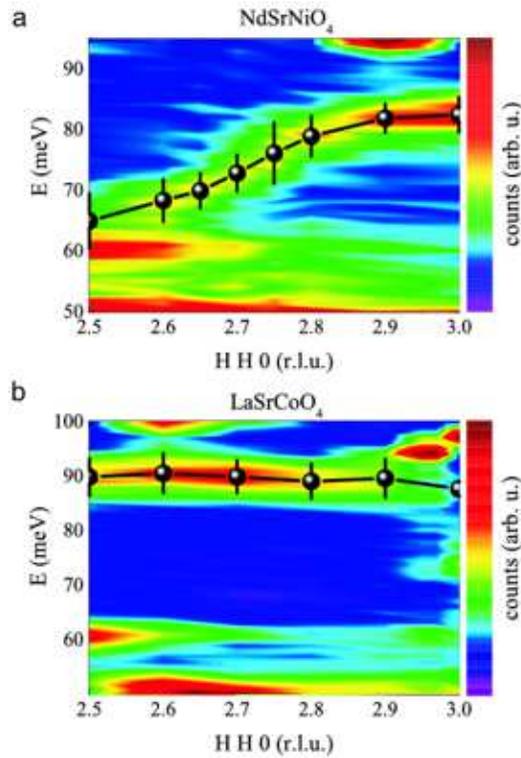


Figure 8. Bond stretching Phonons - Phonon dispersions at 2 K measured at the IN8 spectrometer for (a) NdSrNiO₄ and (b) LaSrCoO₄.

more Co³⁺-ions (J'' etc.). Due to the similarity with the cobaltates, one might think of a similar model for the nickelates, but now with larger values of the exchange interactions that will scale the entire spectrum to higher energies. So we assume a fully charge disproportionated nickelate system with disorder, where we take the nearest neighbor exchange interactions between the magnetic Ni ions to be $J = J^{100} = -30$ meV, and the exchange interaction across a non-magnetic Ni ion to be $J' = J^{200} = -10$ meV, plus also a small (and less important) diagonal exchange interaction $J^{110} = -2$ meV. Using the *McPhase* program code we calculated the magnetic ground state and the corresponding spin wave excitations for four 30×30 meshes -

one of them shown in Fig. 10(a). The corresponding elastic and inelastic neutron scattering intensities of the spin correlations are shown in Fig. 10(b,c). The incommensurate magnetic peaks appear at almost the same positions as observed in the experiment. Furthermore, also the magnetic excitation spectrum strongly resembles the experimental data, compare Figs. 9 and 10(c). Hence, a nano phase separation model for a charge disproportionated sample is able to explain the elastic and inelastic neutron scattering measurements in $RSrNiO_4$. Here, nano phase separation is not driven by carrier doping but by disorder within a completely charge disproportionated sample which inevitably leads to the creation of nanoscopic regions with large exchange interactions J (red areas in Fig. 10(a)) intersected by regions with small exchange interactions J' (blue areas in Fig. 10(a)) and regions with small exchange interactions that can be neglected (black areas in Fig. 10(a)). Such a scenario might be also applicable to other systems with checkerboard charge order with a certain degree of disorder. Indications for nanoscale phase-separation have recently also been reported for the high-temperature superconducting cuprates^{38,39} which points to a possibly significant role of these effects for the physical properties of these systems.

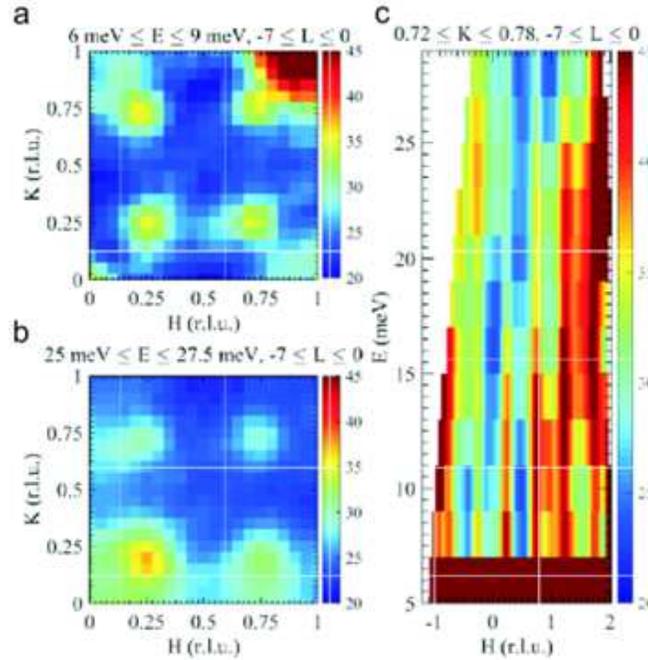


Figure 9. Spin excitations - Magnetic excitation spectra of $La_{2/3}Y_{1/3}SrNiO_4$ measured at the TOF spectrometer MERLIN at 6 K.

Conclusion

We succeeded in synthesizing stoichiometric Ni^{3+} 2-1-4 nickelate single crystals by the high-pressure floating zone technique. We found that this system prefers to undergo a charge disproportionation, although it crystallizes in a tetragonal structure with strongly distorted oxygen environment of the Ni ions that would allow for a Jahn-Teller effect with an occupation of the $3z^2 - r^2$ orbital. Hence, the experimental results suggest that the negative charge transfer character of the Ni^{3+} ion in these oxides provides a very strong drive for charge disproportionation to occur of the type $2 \cdot Ni^{2+\underline{L}} \rightarrow Ni^{2+} + Ni^{2+\underline{L}^2}$, leading to the formation of the observed checkerboard magnetic superstructure. $RSrNiO_4$ can serve as a bench mark system for further theory development to describe properly the role of holes in the oxygen band. Finally, the magnetic correlations and the magnetic excitation spectra in these nickelates can be well explained by a nano phase separation model which is different from usual magnets with long range magnetic order and points to the significance of nano phase separation for an understanding of the physical properties of these materials.

Methods

Single crystals of $NdSrNiO_4$, $La_{2/3}Y_{1/3}SrNiO_4$ and Nd_2NiO_4 were grown by the floating zone technique using a high pressure mirror furnace from Scidre. Here, we studied two Ni^{3+} systems: $NdSrNiO_4$ and $La_{2/3}Y_{1/3}SrNiO_4$. The former one because for $R = Nd$ there is no undesirable mixture of Ni-L₃ and La-M₄ edges in the XAS spectra, the latter one because Nd has an

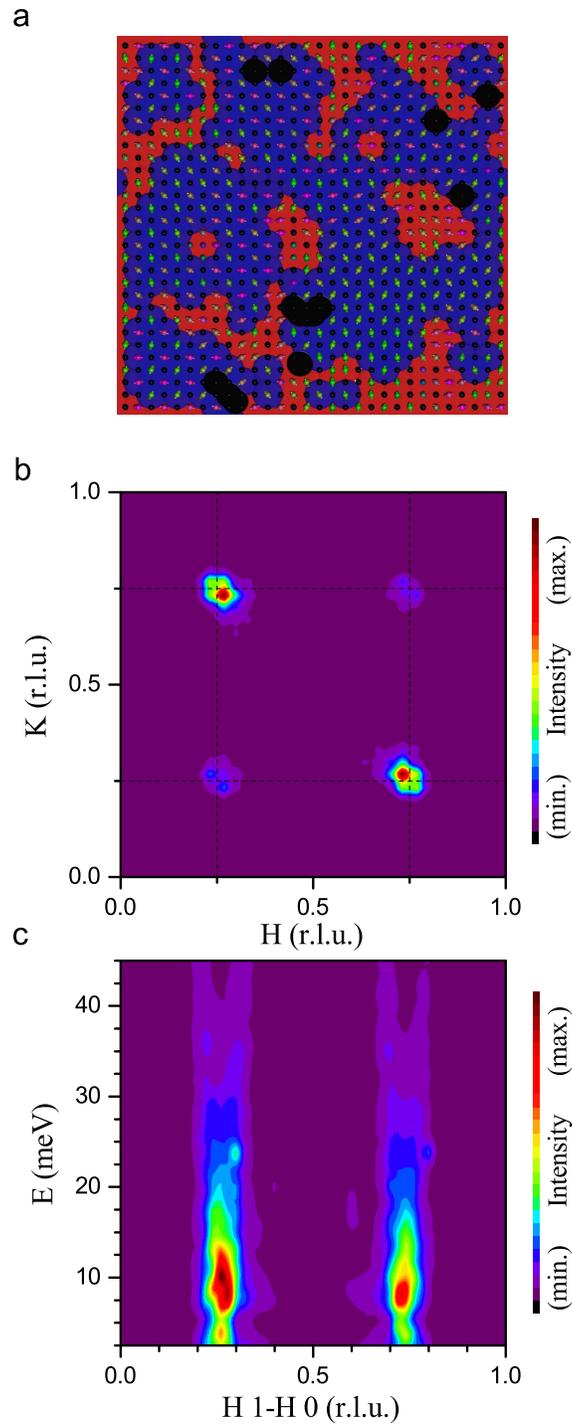


Figure 10. Nano phase separation model - Spin wave simulations of $RSrNiO_4$ within a nano phase separation scenario. (a) One of the four 30×30 meshes obtained from MonteCarlo simulations with a similar algorithm as used for checkerboard charge ordered cobaltates in Ref.²⁴ In (b) and (c) the obtained elastic and inelastic neutron scattering intensities which have been calculated and averaged for four meshes are shown. Black/colored spheres: Ni^{4+} -ions/ Ni^{2+} -ions. In this model only the Ni^{2+} -ions are considered since these are the only ions with sizable nn, nnn, etc. exchange interactions among each other. The red/blue/black areas indicate regions which are hosting large/small/no exchange interactions $J/J'/0$. The incommensurability arises from frustration due to nano phase separation.

undesirable large magnetic moment that might easily overshadow the Ni contribution. We note that the pure La system was more difficult to grow as large single crystals than the Y- substituted compound. The Nd_2NiO_4 was grown to serve as a Ni^{2+} reference system with the same crystal structure as the NdSrNiO_4 and $\text{La}_{2/3}\text{Y}_{1/3}\text{SrNiO}_4$. In order to perform floating zone growth for $\text{Nd}_{2-x}\text{Sr}_x\text{NiO}_4$ ($x=0.9, 1.0$ and 1.1) and $\text{La}_{2/3}\text{Y}_{1/3}\text{SrNiO}_4$ starting materials of R_2O_3 , SrCO_3 and NiO were mixed in appropriate ratios and ground thoroughly in an agate mortar followed by sintering steps at 1000°C - 1200°C in air for several days with intermediate grindings. The obtained composition was then pressed under ~ 100 MPa hydrostatic pressure into a rod of about 6-8 mm in diameter and 120(20) mm in length, which was subsequently sintered at 1000°C in air. The floating zone growth was performed with a growth rate of 2 mm/h in a flowing O_2 atmosphere (~ 0.2 l/min) at a pressure of 100 bar, 120 bar and 150 bar for $x=0.9, 1.0$ and 1.1 , respectively.

Phase purity was confirmed by powder X-ray diffraction (XRD) measurements on ground single crystals with a 2θ step of 0.005° using Cu $K_{\alpha 1}$ radiation of a laboratory X-ray source. It was possible to describe the crystal structure properly with space group $I4/mmm$ for all grown samples. The refined lattice parameters and the resulting unit cell volumes are listed in table 1. The linear change of the lattice parameters as a function of x further confirms the successful substitution of the Nd atom by Sr atom within the $\text{Nd}_{2-x}\text{Sr}_x\text{NiO}_4$ series. This is also corroborated by inductively coupled plasma optical emission spectrometry (ICP-OES) measurements, see the value of $x(\text{ICP})$ in Tab. 1. Moreover, thermogravimetric measurements confirmed that the oxygen content is close to the nominal value, see Tab. 1.

Table 1. Growth condition and physical parameters of $\text{Nd}_{2-x}\text{Sr}_x\text{NiO}_4$ and $\text{La}_{2/3}\text{Y}_{1/3}\text{SrNiO}_4$: v_G is the growth speed, O_2 pressure for the crystal growth, lattice parameters a, b, c and unit cell volume from the Rietveld refinements, $\mu_{eff}^c/\mu_{eff}^{ab}$ and $\theta_{CW}^c/\theta_{CW}^{ab}$ are effective moment per formula unit and Curie-Weiss temperature determined from the Curie-Weiss fit $\chi(T) = \chi_0 + C/(T - \theta_{CW})$ to the magnetic susceptibility. $x(\text{ICP})$ is measured by ICP-OES, $\delta(\text{TG})$ is measured by thermogravimetric (TG) analysis.

sample:	$x = 0.9$	$x = 1.0$	$x = 1.1$	$\text{La}_{2/3}\text{Y}_{1/3}$
v_G (mm/h)	2	2	2	2
O_2 pressure (bar)	100	120	150	150
a, b (\AA)	3.7850(3)	3.7890(3)	3.7956(3)	3.7990(3)
c (\AA)	12.352(1)	12.322(1)	12.278(1)	12.356(1)
volume (\AA^3)	176.96(3)	176.90(2)	176.89(2)	178.318(3)
μ_{eff}^c (μ_B)	3.928(6)	3.777(3)	3.532(6)	0.165(1)
μ_{eff}^{ab} (μ_B)	4.364(4)	3.942(5)	3.701(9)	0.229(1)
θ_{CW}^c (K)	-6.2(3)	-6.2(1)	-10.3(3)	25(1)
θ_{CW}^{ab} (K)	-134.3(3)	-105.8(4)	-92.3(6)	-26(1)
$x(\text{ICP})$	0.90(2)	1.01(2)	1.12(2)	
$\delta(\text{TG})$	0.02(2)	0.00(2)	-0.01(2)	

Magnetic susceptibility (χ) measurements have been performed using a Quantum Design vibrating sample magnetometer (VSM) and the electrical resistivities have been measured with a four-probe method using the Quantum Design PPMS system.

The Ni- $L_{2,3}$ x-ray absorption spectroscopy (XAS) measurements have been performed at the 11A beamline of the National Synchrotron Radiation Research Center (NSRRC), Taiwan. A NiO single crystal was measured simultaneously for energy calibration. The photon energy resolution at the Ni $L_{2,3}$ edges was set at 0.3 eV. The spectra were recorded at 300 K using the total electron yield method.

Unpolarized elastic neutron scattering measurements were performed on the IN8 spectrometer at the Institut Laue Langevin (ILL) using PG monochromator and PG analyzer with fixed $k_f = 2.662\text{\AA}^{-1}$ and two PG filters for the suppression of higher order contaminations. Unpolarized inelastic neutron scattering measurement were performed on the IN8 spectrometer at the ILL and on the MERLIN time-of-flight (TOF) spectrometer at ISIS.^{40,41} For the IN8 measurement, doubly focused Cu monochromator and PG analyzer were used with two PG filters. The MERLIN experiment has been performed in repetition-rate multiplication (RRM) mode. Longitudinal polarized elastic neutron scattering measurements were performed on the IN12 spectrometer at the Institut Laue-Langevin (ILL) equipped with double focusing pyrolythic graphite (PG) monochromator and Heusler analyzer. The beam was polarized by a transmission polarizer in the neutron guide. The monochromator was set for a wave vector of 2.25\AA^{-1} , and, a velocity selector was used for suppression of higher order contamination. The flipping ratio amounts to ~ 22.2 . For the polarization analysis, the x axis is defined along the direction of \mathbf{Q} , the y axis is perpendicular to \mathbf{Q} and within the scattering plane, and the z axis is perpendicular to the scattering plane. Note, that we used the tetragonal setting for all our neutron measurements with lattice constant $a = b \sim 3.79\text{\AA}$ and $c \sim 12.4\text{\AA}$.

Resonant soft X-ray diffraction at the Nd $3d \rightarrow 4f$ (M_5 , 1000 eV) and Ni $2p \rightarrow 3d$ (L_3 , 853.2 eV) resonances have been

measured at the UE56/2-PGM1 beam line at BESSY II. The data were recorded in horizontal scattering geometry with the X-rays linear polarized in the scattering plane (π -polarization). The scattered photons were detected with an in-vacuum CCD camera.

Magnetic field dependence of the antiferromagnetic correlations in NdSrNiO₄ was measured on the D23 diffractometer with magnetic fields applied vertically, i.e., out of the *HK0* scattering plane.

References

1. Torrance, J. B., Lacorre, P., Nazzari, A. I., Ansaldo, E. J. & Niedermayer, C. Systematic study of insulator-metal transitions in perovskites $R\text{NiO}_3$ ($R=\text{Pr, Nd, Sm, Eu}$) due to closing of charge-transfer gap. *Phys. Rev. B* **45**, 8209–8212 (1992). URL <https://link.aps.org/doi/10.1103/PhysRevB.45.8209>.
2. Guo, H. *et al.* Antiferromagnetic correlations in the metallic strongly correlated transition metal oxide LaNiO_3 . *Nat. Commun.* **9**, 43 (2018). URL <https://doi.org/10.1038/s41467-017-02524-x>.
3. Mizokawa, T., Khomskii, D. I. & Sawatzky, G. A. Spin and charge ordering in self-doped mott insulators. *Phys. Rev. B* **61**, 11263–11266 (2000). URL <https://link.aps.org/doi/10.1103/PhysRevB.61.11263>.
4. Johnston, S., Mukherjee, A., Elfimov, I., Berciu, M. & Sawatzky, G. A. Charge disproportionation without charge transfer in the rare-earth-element nickelates as a possible mechanism for the metal-insulator transition. *Phys. Rev. Lett.* **112**, 106404 (2014). URL <https://link.aps.org/doi/10.1103/PhysRevLett.112.106404>.
5. Zaanen, J., Sawatzky, G. A. & Allen, J. W. Band gaps and electronic structure of transition-metal compounds. *Phys. Rev. Lett.* **55**, 418–421 (1985). URL <https://link.aps.org/doi/10.1103/PhysRevLett.55.418>.
6. Khomskii, D. I. Unusual valence, negative charge-transfer gaps and self-doping in transition metal compounds. *Lithuanian Journal of Physics* **37**, 65 (1997).
7. Green, R. J., Haverkort, M. W. & Sawatzky, G. A. Bond disproportionation and dynamical charge fluctuations in the perovskite rare-earth nickelates. *Phys. Rev. B* **94**, 195127 (2016). URL <https://link.aps.org/doi/10.1103/PhysRevB.94.195127>.
8. Bisogni, V. *et al.* Ground-state oxygen holes and the metal-insulator transition in the negative charge-transfer rare-earth nickelates. *Nat. Commun.* **7**, 13017 (2016).
9. Alonso, J. A. *et al.* Charge disproportionation in $R\text{NiO}_3$ perovskites: Simultaneous metal-insulator and structural transition in YNiO_3 . *Phys. Rev. Lett.* **82**, 3871–3874 (1999). URL <https://link.aps.org/doi/10.1103/PhysRevLett.82.3871>.
10. Subedi, A., Peil, O. E. & Georges, A. Low-energy description of the metal-insulator transition in the rare-earth nickelates. *Phys. Rev. B* **91**, 075128 (2015). URL <https://link.aps.org/doi/10.1103/PhysRevB.91.075128>. PRB.
11. Seth, P. *et al.* Renormalization of effective interactions in a negative charge transfer insulator. *Phys. Rev. B* **96**, 205139 (2017). URL <https://link.aps.org/doi/10.1103/PhysRevB.96.205139>. PRB.
12. Lee, S., Chen, R. & Balents, L. Metal-insulator transition in a two-band model for the perovskite nickelates. *Phys. Rev. B* **84**, 165119 (2011). URL <https://link.aps.org/doi/10.1103/PhysRevB.84.165119>.
13. Lee, S., Chen, R. & Balents, L. Landau theory of charge and spin ordering in the nickelates. *Phys. Rev. Lett.* **106**, 016405 (2011). URL <https://link.aps.org/doi/10.1103/PhysRevLett.106.016405>.
14. Khomskii, D. I. *Transition Metal Compounds* (Cambridge Univ. Press, 2014).
15. Wu, H. *et al.* Orbital order in $\text{La}_{0.5}\text{Sr}_{1.5}\text{MnO}_4$: beyond a common local jahn-teller picture. *Phys. Rev. B* **84**, 155126 (2011).
16. Uchida, M. *et al.* Pseudogap of metallic layered nickelate $R_{2-x}\text{Sr}_x\text{NiO}_4$ ($R = \text{Nd, Eu}$) crystals measured using angle-resolved photoemission spectroscopy. *Phys. Rev. Lett.* **106**, 027001 (2011). URL <https://link.aps.org/doi/10.1103/PhysRevLett.106.027001>.
17. Uchida, M. *et al.* Orbital characters of three-dimensional fermi surfaces in $\text{Eu}_{2-x}\text{Sr}_x\text{NiO}_4$ as probed by soft-x-ray angle-resolved photoemission spectroscopy. *Phys. Rev. B* **84**, 241109 (2011). URL <https://link.aps.org/doi/10.1103/PhysRevB.84.241109>.
18. Hansmann, P. *LDA+DMFT: from bulk to heterostructures* (Technische Universität Wien, 2010).
19. Tranquada, J. M., Buttrey, D. J., Sachan, V. & Lorenzo, J. E. Simultaneous ordering of holes and spins in La_2NiO_4 . *Phys. Rev. Lett.* **73**, 1003–1006 (1994). URL <http://link.aps.org/doi/10.1103/PhysRevLett.73.1003>.

20. Tranquada, J. M. *et al.* Oxygen intercalation, stage ordering, and phase separation in $\text{La}_2\text{NiO}_{4+\delta}$ with $0.05 \lesssim \delta \lesssim 0.11$. *Phys. Rev. B* **50**, 6340–6351 (1994). URL <http://link.aps.org/doi/10.1103/PhysRevB.50.6340>.
21. Tranquada, J. M., Buttrey, D. J. & Sachan, V. Incommensurate stripe order in $\text{La}_{2-x}\text{Sr}_x\text{NiO}_4$ with $x=0.225$. *Phys. Rev. B* **54**, 12318–12323 (1996). URL <http://link.aps.org/doi/10.1103/PhysRevB.54.12318>.
22. Yoshizawa, H. *et al.* Stripe order at low temperatures in $\text{La}_{2-x}\text{Sr}_x\text{NiO}_4$ with $0.289 \lesssim x \lesssim 0.5$. *Phys. Rev. B* **61**, R854–R857 (2000). URL <https://link.aps.org/doi/10.1103/PhysRevB.61.R854>.
23. Drees, Y., Lamago, D., Piovano, A. & Komarek, A. C. Hour-glass magnetic spectrum in a stripeless insulating transition metal oxide. *Nat. Commun.* **4**, 2449 (2013). URL <http://dx.doi.org/10.1038/ncomms3449>.
24. Drees, Y. *et al.* Hour-glass magnetic excitations induced by nanoscopic phase separation in cobalt oxides. *Nat. Commun.* **5**, 5731 (2014). URL <http://dx.doi.org/10.1038/ncomms6731>.
25. Guo, H., Schmidt, W., Tjeng, L. H. & Komarek, A. C. Charge correlations in cobaltates $\text{La}_{2-x}\text{Sr}_x\text{CoO}_4$. *Phys. Status Solidi RRL* **9**, 580–582 (2015). URL <http://dx.doi.org/10.1002/pssr.201510290>.
26. Li, Z. W. *et al.* Incommensurate spin correlations in highly oxidized cobaltates $\text{La}_{2-x}\text{Sr}_x\text{CoO}_4$. *Sci. Rep.* **6**, 25117 (2016). URL <http://dx.doi.org/10.1038/srep25117>.
27. Li, Z. W. *et al.* Electronic and magnetic nano phase separation in cobaltates $\text{La}_{2-x}\text{Sr}_x\text{CoO}_4$. *J. Supercond. Nov. Magn.* **29**, 727–731 (2016). URL <https://doi.org/10.1007/s10948-015-3302-4>.
28. Guo, H. *et al.* Suppression of the outwards-dispersing branches in hour-glass magnetic spectra induced by nanoscale phase separation in $\text{La}_{2-x}\text{Sr}_x\text{CoO}_4$. *Phys. Rev. B* **100**, 014411 (2019). URL <https://link.aps.org/doi/10.1103/PhysRevB.100.014411>.
29. Ishizaka, K., Taguchi, Y., Kajimoto, R., Yoshizawa, H. & Tokura, Y. Charge ordering and charge dynamics in $\text{Nd}_{2-x}\text{Sr}_x\text{NiO}_4$ ($0.33 \leq x \leq 0.7$). *Phys. Rev. B* **67**, 184418 (2003). URL <http://link.aps.org/doi/10.1103/PhysRevB.67.184418>.
30. Uchida, M. *et al.* Pseudogap-related charge dynamics in the layered nickelate $R_{2-x}\text{Sr}_x\text{NiO}_4$ ($x \sim 1$). *Phys. Rev. B* **86**, 165126 (2012). URL <http://link.aps.org/doi/10.1103/PhysRevB.86.165126>.
31. Hu, Z. *et al.* Hole distribution between the ni 3d and o 2p orbitals in $\text{Nd}_{2-x}\text{Sr}_x\text{NiO}_{4-\delta}$. *Phys. Rev. B* **61**, 3739–3744 (2000). URL <https://link.aps.org/doi/10.1103/PhysRevB.61.3739>.
32. Burnus, T. *et al.* *Phys. Rev. B* **77**, 125124 (2008).
33. Burnus, T. *et al.* *Phys. Rev. B* **77**, 205111 (2008).
34. Mizokawa, T. & Fujimori, A. Unrestricted hartree-fock study of transition-metal oxides: Spin and orbital ordering in perovskite-type lattice. *Phys. Rev. B* **51**, 12880–12883 (1995). URL <https://link.aps.org/doi/10.1103/PhysRevB.51.12880>.
35. Johnston, S., Mukherjee, A., Elfmov, I., Berciu, M. & Sawatzky, G. A. Charge disproportionation without charge transfer in the rare-earth-element nickelates as a possible mechanism for the metal-insulator transition. *Phys. Rev. Lett.* **112**, 106404 (2014). URL <https://link.aps.org/doi/10.1103/PhysRevLett.112.106404>.
36. Schüßler-Langeheine, C. *et al.* Spectroscopy of stripe order in $\text{La}_{1.8}\text{Sr}_{0.2}\text{NiO}_4$ using resonant soft x-ray diffraction. *Phys. Rev. Lett.* **95**, 156402 (2005).
37. Reznik, D. *et al.* Electron-phonon coupling reflecting dynamic charge inhomogeneity in copper oxide superconductors. *Nature* **440**, 1170–1173 (2006). URL <http://dx.doi.org/10.1038/nature04704>.
38. Campi, G. *et al.* *Nature* **525**, 359 (2015).
39. Fratini, M. *et al.* Scale-free structural organization of oxygen interstitials in $\text{La}_2\text{CuO}_{4+y}$. *Nature* **466**, 841–844 (2010). URL <https://doi.org/10.1038/nature09260>.
40. Bewley, R. I., Guidi, T. & Bennington, S. *Notiziario Neutroni e Luce di Sincrotrone* **14**, 22 (2009).
41. Russina, M. & Mezei, F. First implementation of repetition rate multiplication in cold, thermal and hot neutron spectroscopy. *Nucl. Instrum. Methods in Phys. Res. Sect. A* **604**, 624 (2009).

Acknowledgements (not compulsory)

The research in Dresden is supported by the Deutsche Forschungsgemeinschaft through Grant No. 320571839. D. I. Kh. received support from the Deutsche Forschungsgemeinschaft via the project SFB 1238 and by the German Excellence Initiative. We acknowledge support from the Max Planck-POSTECH-Hsinchu Center for Complex Phase Materials.