Pressure-induced suppression of ferromagnetism in $CePd_2P_2$

T. A. Elmslie,¹ D. VanGennep,¹ W. Bi,^{2, 3, 4} Y. Lai,⁵ S. T. Weir,⁶ Y. K. Vohra,⁴ R. E. Baumbach,⁵ and J. J. Hamlin^{1, *}

¹Department of Physics, University of Florida, Gainesville, FL 32611, USA

²Advanced Photon Source, Argonne National Laboratory, Argonne, IL 60439, USA

³Department of Geology, University of Illinois at Urbana-Champaign, Urbana, IL 61801, USA

⁴Department of Physics, University of Alabama at Birmingham, Birmingham, AL, 35294, USA

⁵National High Magnetic Field Laboratory, Florida State University, Tallahassee, Florida 32310, USA

^oPhysics Division, Lawrence Livermore National Laboratory, Livermore, CA 94550, USA

The correlated electron material $CePd_2P_2$ crystallizes in the ThCr₂Si₂ structure and orders ferromagnetically at 29 K. Lai *et al.* [1] found evidence for a ferromagnetic quantum critical point induced by chemical compression via substitution of Ni for Pd. However, disorder effects due to the chemical substitution interfere with a simple analysis of the possible critical behavior. In the present work, we examine the temperature - pressure - magnetic field phase diagram of single crystalline $CePd_2P_2$ to 25 GPa using a combination of resistivity, magnetic susceptibility, and x-ray diffraction measurements. We find that the ferromagnetism appears to be destroyed near 12 GPa, without any change in the crystal structure.

INTRODUCTION

When a ferromagnetic transition is suppressed by a clean control parameter such as pressure, typically, the second-order phase transition changes to first-order at a critical value of the control parameter [2] and the transition abruptly drops towards 0 K [3–7]. As the system approaches the critical point in a second order phase transition, fluctuations in the order parameter extend to larger and larger length scales, while the order parameter varies smoothly between the ordered and disordered phases. However, in a first order phase transition, this correlation length does not diverge, and the order parameter changes discontinuously [5, 8]. In certain compounds, such as UGe₂ and ZrZn₂, the shift from a secondto first-order transition is accompanied by the appearance of metamagnetic "wings" in the phase diagram, in which the ordered phase reappears when a magnetic field is applied [9–11]. As pressure increases, the metamagnetic transition is smoothly pushed to higher fields and lower temperatures until it can terminate at a quantum wing critical point (QWCP) at 0 K [5, 12, 13]. More complicated scenarios are also possible, where both ferromagnetic and antiferromagnetic or modulated phases are present [12] as observed in LaCrGe₃ [13, 14] and CeTiGe₃ [9]. The complex phase diagrams of such materials represent a critical test of our understanding of quantum phase transitions.

The possibility of these sorts of features make $CePd_2P_2$ an interesting compound for study. The crystal structure of $CePd_2P_2$ was first reported in Ref. [15]. No further characterization was performed until the work of Shang *et al.* [16], which reported resistivity, DC magnetization and DC magnetic susceptibility of polycrystalline $CePd_2As_{2-x}P_x$ for different levels of substitution, and demonstrated a ferromagnetic transition in $CePd_2P_2$ at approximately 29 K. In the same year, Tran and Bukowski [17] reported on DC magnetic susceptibility,

magnetization, specific heat, resistivity, and magnetoresistance measurements on polycrystalline $CePd_2P_2$, and Tran et al. [18] reported AC susceptibility and DC magnetization, also for polycrystalline CePd₂P₂. These papers also confirmed ferromagnetic order in CePd₂P₂ below about 28.4 K. Neutron diffraction and DC magnetization measurements were performed by Ikeda et al. [19] on a polycrystalline sample, including a magnetically aligned polycrystalline sample, which revealed the magnetic anisotropy of $CePd_2P_2$, with the *c*-axis as the magnetic easy axis. This is confirmed by single crystal work [20]. The compound $CeNi_2P_2$ shares the $ThCr_2Si_2$ crystal structure with $CePd_2P_2$, but exhibits a non-magnetic ground state [21], suggesting Pdto-Ni substitution can drive a transition from magnetic to non-magnetic. Lai et al. [1] examined this possibility by substituting Ni to replace Pd, revealing a possible ferromagnetic quantum critical point in the temperatureconcentration phase diagram. Here, according to Belitz-Kirkpatrick-Vojta (BKV) theory [5, 22], the quenched disorder inherent to the chemical substitution allows the transition to be driven continuously to zero.

Because Ni is isoelectronic with Pd and smaller in size, one can think of $Pd \rightarrow Ni$ substitution as inducing chemical pressure. Lai et al. [1] compared this chemical pressure effect to the effects of applied mechanical pressure on CePd₂P₂ up to about 2 GPa. A small suppression of the Curie temperature with applied pressure was observed indicating a critical pressure for full suppression of the transition well beyond the maximum pressure of that experiment. Therefore, we undertook to explore the phase diagram of this material at substantially higher pressures. In particular, we wished to look for the point at which the magnetic transition became first order, as well as any signs of a modulated magnetic phase or metamagnetic wings. We find that magnetic order appears to be destroyed near 12 GPa. We find no evidence of a modulated magnetic phase or metamagnetic wings in resistivity measurements between 12 and 20 GPa in fields up to 9 T.

METHODS

Single crystals of $CePd_2P_2$ were grown in a molten metal flux according to the process outlined in Ref. [1]. The single crystals had a tendency to break into flat platelets perpendicular to the *c*-axis and were therefore easily aligned with the *c*-axis parallel to applied field.

Alternating current (AC) susceptibility measurements were performed in a Quantum Design PPMS using an Almax-EasyLab Chicago Diamond Anvil Cell (Chicago-DAC). The magnetic coil system and measurement electronics have been described elsewhere [23]. In AC susceptibility measurements, diamonds with 0.8 mm culets were used, and Berylco-25 gaskets were pre-indented to 70 µm from a starting thickness of 260 µm. The gasket hole diameter was approximately 260 µm, and these gaskets were sealed in a quartz tube under argon atmosphere and hardened in a furnace at 315 °C. A solution of 50% n-pentane to 50% isoamyl alcohol was used as a pressure transmitting medium [24].

When analyzing the AC susceptibility data, a background subtraction was performed for each run, since the signal from the sample is much smaller than the background. Background subtraction was performed by subtracting one run from another, always choosing runs which had distant values of T_C . The value of T_C was defined as the inflection point of the curve, as determined from second derivative data.

For the resistivity measurements, samples with typical dimensions of $\sim 70 \,\mu\text{m} \times 70 \,\mu\text{m} \times 10 \,\mu\text{m}$ were cut from larger crystals and loaded into either an Almax-EasyLab OmniDAC or the ChicagoDAC mentioned above. While the ChicagoDAC was used in a Quantum Design PPMS, the OmniDAC measurements were carried out in a custom-made continuous flow cryostat built by Oxford Instruments. One of the diamonds used was a so-called designer diamond anvil, which is composed of eight symmetrically arranged tungsten microprobes that are encapsulated in high purity homoepitaxial diamond [25]. The designer diamond anvil had a culet diameter of 180 µm, while the opposing anvil had a culet diameter of 500 µm. Gaskets were made of 316 SS and were preindented to an initial thickness of ~30 µm. Quasihydrostatic, soft, solid steatite was used as a pressure medium. Resistance was measured in the crystalline *ab*-plane using the Van der Pauw geometry with currents of 1 mA. Electrical resistivity measurements performed in the OmniDAC are referred to as "run A," and ChicagoDAC resistivity measurements are designated "run B." In both the ChicagoDAC and OmniDAC, pressure was determined *in-situ* via ruby flourescence [26] so that the reported pressures were measured at the corresponding temperatures.

X-ray diffraction measurements were carried out in beamline 16 ID-B of the Advanced Photon Source at Argonne National Lab using a beam with dimensions of approximately $15 \,\mu\text{m} \times 15 \,\mu\text{m}$ and wavelength $0.4066 \,\text{\AA}$. Samples were powdered in a mortar and pestle before being loaded into a Symmetric Diamond Anvil Cell (Symmetric DAC) alongside a ruby fragment and small piece of Pt foil for pressure determination. The Pt equation of state of Holmes et al. [27] was used for pressure calibration. The diamonds had a culet diameter of 500 µm. The gasket was made from 316 SS and was preindented to an initial thickness of about 60 µm. The gasket hole diameter was approximately 200 µm, and was filled with a pressure medium of 1:1 n-pentane isoamyl alcohol before the sample, ruby and Pt were loaded. The cell was pressurized in situ via a computer-controlled pressure membrane.

EXPERIMENTAL RESULTS

Figure 1 shows a plot of the real part of the AC magnetic susceptibility of $CePd_2P_2$ vs temperature in the vicinity of the transition. Increasing pressure causes the transition to be suppressed to lower temperatures - from 28.3 K at 0.6 GPa, to 15.4 K at 9.5 GPa. As the transition is suppressed, the magnitude of the anomaly at T_C is also reduced. At 9.5 GPa the anomaly is still barely visible, but by 10 GPa it is no longer detectable. The arrows in the figure indicate the criterion used to determine T_C and are based on the inflection point, as determined from second derivative data.

The decreasing size of the susceptibility anomaly is consistent with the Rhodes-Wolfarth picture [28] of itinerant ferromagnetism, which suggests that a decrease in T_C will correspond to a decrease in the ordered moment. There does appear to be a subtle change in the shape of the anomaly in χ vs T. However, the necessity of background subtraction limits the temperature range of the data that can be compared between the high and low pressure data, which makes it difficult to disentangle changes in the background from changes in the shape of the anomaly. While it is possible that the nature of the magnetic order changes with pressure, the resistivity measurements (presented below) also do not allow us to make a definite conclusion regarding the possibility of a change in the nature of the magnetic order.

Figures 2 and 3 present electrical resistivity versus temperature data for two different experimental runs, referred to as run A and run B. In run A, resistivity measurements were performed between 5 K and 40 K, while run B collected data between 5 K and 180 K, demonstrating resistivity behaviour to higher temperature. The left panels show resistivity curves below 12 GPa, where the transition is easily discernible, and decreases in temper-

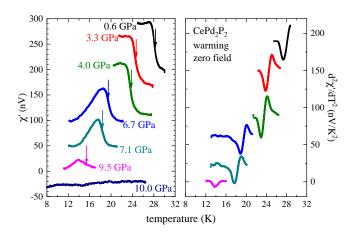


FIG. 1. The left panel shows the PM-FM transition of $CePd_2P_2$ in the real part of the AC magnetic susceptibility at various pressures. Note that as pressure increases, the transition temperature decreases, as does the size of the transition. At 10.0 GPa and above, the transition becomes undetectable in χ . The transition temperature was defined as the inflection point, as determined by the second derivative of the real part of the magnetic susceptibility, and is indicated by arrows on each curve. The right panel shows the second derivative of the real part of the AC magnetic susceptibility for each transition. In both plots, data are offset for clarity.

ature as pressure increases. The plots on the right show data above 12 GPa, where $T_{\rm C}$ can no longer be unambiguously determined. In the right-most plot of Fig. 2, the transition is initially still visible (13.7 GPa), but the broadening prevents accurate and reliable determination of $T_{\rm C}$. As pressure increases further, the transition disappears entirely and the curvature changes from negative to positive. We attempted to fit the low temperature electrical resistivity with a power law of the form $\rho = \rho_0 + AT^n$, but found that the data could not be described in this way over a significant range of temperatures.

The low temperature resistivity versus pressure curve shows a peak near 12.5 GPa, as demonstrated by the data in Fig. 4. Data points in the loading curves are synthesized from resistivity versus temperature sweeps at each pressure, while the unloading curve was taken while continuously sweeping pressure at constant temperature. The location of the peak displays a hysteresis of about 1 GPa between loading and unloading, and shifts to higher pressures at higher temperatures (at 200 K the peak occurs near 15 GPa). The peak appears to coincide roughly with the pressure where the magnetic transition becomes undetectable in χ and ρ .

Figure 5 presents the magnetoresistance behavior of $CePd_2P_2$ as a function of temperature. Below 12 GPa, as temperature decreases, magnetoresistance becomes large and negative near T_C . The temperature at which the magnetoresistance obtains the largest magnitude decreases with increasing pressure, which is consistent with a suppression of the transition to lower temperatures.

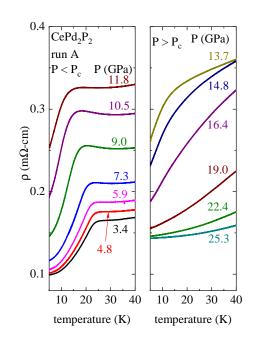


FIG. 2. Resistivity as a function of temperature for $CePd_2P_2$ run A at pressures below 12 GPa (left) and above (right). Above 12 GPa, the transition temperature can not be accurately determined.

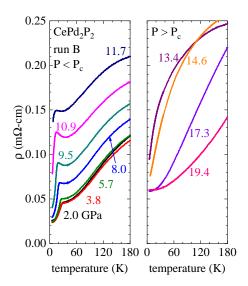


FIG. 3. Resistivity as a function of temperature for $CePd_2P_2$ run B at pressures below 12 GPa (left) and above (right), showing resistivity behaviour up to 180 K.

As pressure increases above 12 GPa, the temperature dependence of the magnetoresistance becomes increasingly flat. The minimum follows similar behavior to $T_{\rm C}$, disappearing near the critical pressure of 12 GPa. This behavior, in which the magnetoresistance extremum follows the transition temperature, is explained by Yamada and Takada [29] as resulting from fluctuations of localized spins. The inset of Figure 5 presents the magnetoresistance as a function of pressure at 9 T for temperatures

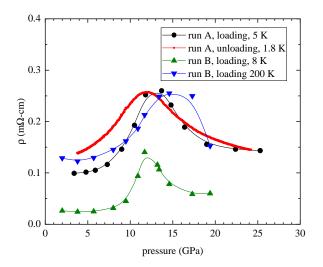


FIG. 4. Resistivity as a function of pressure for CePd₂P₂. Note the resistivity peak near 12 GPa, close to the pressure where the transition disappears in χ and ρ .

of 6 K and 25 K. The 6 K magnetoresistance reaches a minimum at 11.7 GPa, close to the value of critical pressure P_c as determined by zero field resistivity. At higher pressures, the magnetoresistance then rises to be nearly identical to the 25 K curve. The 25 K magnetoresistance starts negative and asymptotically approaches zero as pressure increases. This behavior is consistent with a supression of the magnetic transition near 12 GPa.

An important question is whether the disappearance of the magnetic transition in ρ and χ as well as the peak in resistivity as a function of pressure near 12 GPa occur within the ambient pressure crystal stucture, as a result of the physics predicted by BKV theory [5], or are instead merely related to a pressure-induced structural transition. In order to test this, the crystal structure of CePd₂P₂ was examined via angle-dispersive x-ray diffraction. X-ray data from an area detector were processed into usable XRD patterns using Dioptas [30] and then analyzed via GSAS-II [31]. Figure 6 shows a portion of the results from x-ray diffraction measurements between 1.0 GPa and 30.8 GPa. The data show no evidence for any change in the crystal structure to the highest pressures measured.

Data were fit to the ThCr₂Si₂ structure using LeBail analysis. Figure 7, presents the unit cell volume vs pressure for CePd₂P₂, as determined from these fits. The Vinet equation [32] was fit to the equation of state data to obtain a value for the bulk modulus and its derivative with respect to pressure. Based on the extracted lattice constants a plot of the c/a ratio is shown in the inset. The c/a ratio increases with increasing pressure, demonstrating that CePd₂P₂ exhibits a substantial degree of three dimensional bonding. In a "layered" compound, one would expect c/a to decrease under pressure. The scatter in the c/a ratio increases substantially above

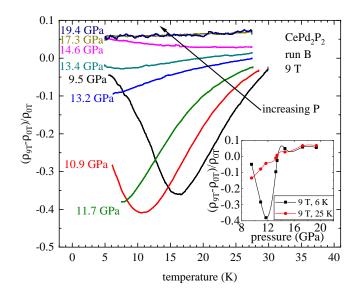


FIG. 5. Magnetoresistance as a function of temperature for $CePd_2P_2$ at varying pressures. At low pressure, magnetoresistance is negative and possesses a clear valley near the transition temperature for a given pressure. Above about 12 GPa, however, this feature vanishes, and as pressure increases further, magnetoresistance shifts from negative to positive above about 13.4 GPa. The inset shows magnetoresistance of $CePd_2P_2$ as a function of pressure at 6 K and 25 K. At 25 K, above T_C , magnetoresistance starts negative and gradually increases, becoming positive at higher pressures. The 6 K data shows a deep minimum at 11.7 GPa, near the critical pressure where the magnetic order appears to vanish.

7.4 GPa, likely due to the freezing of the pressure medium near this pressure. There does appear to be a minimum in the c/a ratio near the critical pressure of 12 GPa, however it is unclear if this is a consequence of the destruction of the magnetic phase or merely a result of the non-hydrostatic pressure.

DISCUSSION

The CePd₂P₂ phase diagram displayed in Fig. 8 contains T_C vs pressure data from Ref. [1] (up to ~ 2 GPa) alongside the data described in this work. The decrease in T_C is observed to be nearly linear with increasing pressure. The scatter in T_C is likely due to the quasihydrostaticity of the pressure media at high pressure and the different media used in different measurements. The dashed orange line is a linear fit to all of our data shown in Fig. 8. The fit gives a slope of -1.31(6) K/GPa, a yintercept of 29.0(3) K, and an x-intercept of 22(1) GPa. The vertical dashed blue line in Fig. 8 indicates the approximate pressure at which the transition disappears in ρ and χ and where a peak in the resistivity versus pressure plot was observed. The general shape of the phase diagram, with a transition that abruptly drops to

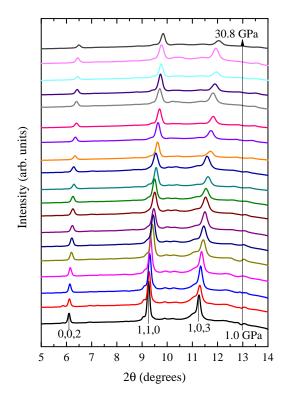


FIG. 6. XRD patterns for CePd₂P₂ at various pressures. Pressure increases with increasing height, beginning at about 1 GPa and increasing to a maximum of about 30 GPa. No structural transition is observed within this pressure range.

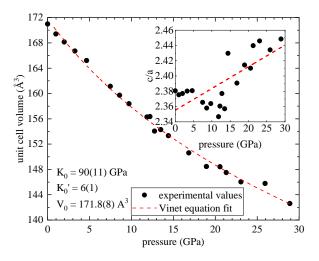


FIG. 7. Unit cell volume vs pressure, obtained by x-ray diffraction. The Vinet equation was fitted to the data to obtain the bulk modulus. The inset shows the ratio of lattice constants c/a as a function of pressure. The c/a ratio increases with pressure, suggesting that CePd₂P₂ exhibits substantially three-dimensional bonding. The increased scatter at around 7.4 GPa may be due to the freezing of the pressure medium. Error bars are approximately the size of the symbols shown.

zero temperature as an order parameter increases (in this case, pressure), is in line with the predictions of BKV theory [5]. However, a central prediction of BKV theory is that this transition is generically of first order, and therefore the second order transition at higher temperature should become first order beyond the tricritical point. Our data is unable to distinguish whether the transition becomes first order before vanishing.

From the X-ray diffraction data, we can also determine the Ce-Ce nearest neighbor distance; at ambient pressure it sits at approximately 4.2 Å, while at the highest measured pressure of 29.8 GPa, it is compressed to 3.9 Å. This is above the cerium Hill limit of 3.6 Å. [33, 34] On its own, this would suggest that CePd₂P₂ is a local moment compound, but this is contradicted by the shape of the phase diagram, which, as noted above, fits the predictions of BKV theory, suggesting that CePd₂P₂ is an itinerant electron compound at high pressure. The reduction of the signal in the AC susceptibility data at high pressure also suggests that CePd₂P₂ may be near to an itinerant-to-local transition [28].

Figure 9 compares the effects on physical pressure on CePd₂P₂ and chemical pressure in Ce(Pd,Ni)₂P₂ by plotting the ordering temperature vs unit cell volume. The change in volume from mechanical compression is derived from LeBail analysis of x-ray diffraction data shown in Fig. 6. This is compared to unit cell volume data for different levels of Ni substitution reported by Y. Lai et al. [1]. In both cases, the critical temperature varies roughly linearly with volume, though chemical compression and mechanical compression suppress the transition at different rates. As the volume decreases, there is a large difference in $T_{\rm C}$ between applied chemical and mechanical pressure. However, remarkably, in both cases, the transition becomes undetectable at roughly the same critical volume. It thus appears that $Ce(Ni,Pd)_2P_2$ and $CePd_2P_2$ may offer an ideal pair of systems to compare ferromagnetic quantum phase transitions driven by compression with or without disorder.

There are a number of compounds to which one can compare $CePd_2P_2$. $CeTiGe_3$ is a ferromagnet at ambient pressure, but, as pressure increases, the ferromagnetic transition is suppressed until 4.1 GPa, at which point it becomes (possibly) antiferromagnetic [9]. LaCrGe₃ provides yet another example of the possible T - p - Hphase diagram that can result from suppressing a ferromagnetic transition. LaCrGe₃ appears to simultaneously exhibit both metamagnetic wings accompanying a shift to a first order transition, as predicted by BKV [5], as well as a modulated magnetic phase [13, 14]. Like these compounds, $CePd_2P_2$ has a ferromagnetic transition suppressed by pressure until it reaches a critical pressure at which the transition abruptly vanishes. However, there are no signs of other features such as metamagnetic wings or other magnetic phases in the $CePd_2P_2$ phase diagram. On the other hand, we can not rule out the possibility of a different type of magnetic order in the region between about 9.5 GPa, where the anomaly in χ disappears, and 12 GPa, where the resistivity peaks and the anomaly disappears in ρ .

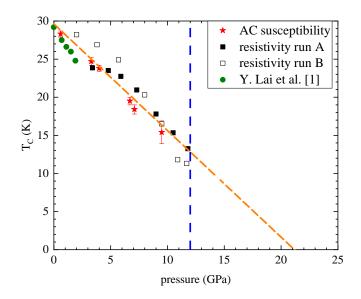


FIG. 8. Phase diagram showing the ferromagnetic transition temperature of $CePd_2P_2$ vs pressure. The orange line represents a linear fit to this data, and the vertical blue line indicates the pressure at which the resistivity peaked as a function of pressure.

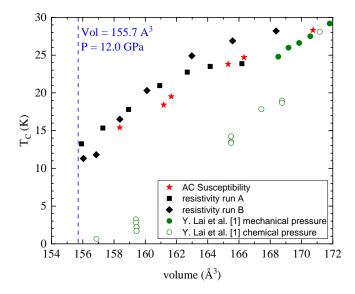


FIG. 9. Critical temperature as a function of volume for $CePd_2P_2$ and $Ce(Ni,Pd)_2P_2$. The filled symbols represent high pressure data on $CePd_2P_2$, while the open symbols correspond to lattice constants for $Ce(Ni,Pd)_2P_2$ from Ref. [1]. The magnetic transition is suppressed by chemical and mechanical compression at different rates, though both decrease roughly linearly. Despite a large difference in T_C , the magnetic transition becomes undetectable at the same critical volume.

CONCLUSION

 $CePd_2P_2$ is a ferromagnet with $T_C \approx 29 \,\mathrm{K}$ at ambient pressure. This transition temperature decreases roughly linearly with pressure at a rate of $1.3 \,\mathrm{K/GPa}$. The second-order transition is expected to shift to first order and then rapidly vanish, as observed in other clean ferromagnets; the vanishing of $T_{\rm C}$ appears to occur in $CePd_2P_2$ near a critical pressure of 12 GPa. This is evidenced by a gradual suppression and then disappearance of the anomaly at T_C in magnetic susceptibility and then a broadening and disappearance of the anomaly in the electrical resistivity. In addition, the apparent disappearance of magnetic order is accompanied by a peak in resistivity and in the magnitude of the magnetoresistance at the critical pressure. However, the shift to a first order transition could not be directly verified through the present measurements. High pressure x-ray diffraction shows that these features are not connected to a structural transition and that the ambient pressure crystal structure is maintained to at least 30 GPa. At pressure above the critical pressure we find no clear evidence for metamagnetic wings (as observed in e.g., UGe₂ [35, 36], $ZrZn_2$ [10, 37], and LaCrGe₃ [13, 14]), or alternative magnetic structures (as observed in *e.q.*, CeRuPO [38, 39], $CeTiGe_3$ [9] and $LaCrGe_3$ [13, 14]). High pressure neutron scattering measurements could help to definitively determine the microscopic nature of the magnetic order in the vicinity of the critical pressure and whether magnetic order persists in the region beyond the critical pressure.

ACKNOWLEDGMENTS

This work was supported by National Science Foundation (NSF) CAREER award DMR-1453752. High pressure technique development was partially supported by a National High Magnetic Field Laboratory User Collaboration Grant. The National High Magnetic Field Laboratory is supported by the NSF via Cooperative agreement No. DMR-1157490, the State of Florida, and the U.S. Department of Energy. Designer diamond anvils were supported by DOE-NNSA Grant No. DE-NA-0002928 and under the auspices of the U.S. Department of Energy by Lawrence Livermore National Laboratory under Contract DE-AC52-07NA27344. Portions of this work were performed at HPCAT (Sector 16), Advanced Photon Source (APS), Argonne National Laboratory. HP-CAT operations are supported by DOE-NNSAs Office of Experimental Sciences. The Advanced Photon Source is a U.S. Department of Energy (DOE) Office of Science User Facility operated for the DOE Office of Science by Argonne National Laboratory under Contract No. DE-AC02-06CH11357. TAE, DV, and JJH thank Yue Meng for her aid in measurements performed at Argonne National Laboratory. Dioptas and GSAS-II programs were used for analysis of x-ray diffraction data. RB and YL acknowledge support from Department of Energy through the Center for Actinide Science and Technology (an EFRC funded under Award DE-SC-0016568). Designer diamond anvils were supported by DOE-NNSA Grant No. DE-NA-0003916.

* Corresponding author: jhamlin@ufl.edu

- Y. Lai, S. E. Bone, S. Minasian, M. G. Ferrier, J. Lezama-Pacheco, V. Mocko, A. S. Ditter, S. A. Kozimor, G. T. Seidler, W. L. Nelson, Y.-C. Chiu, K. Huang, W. Potter, D. Graf, T. E. Albrecht-Schmitt, and R. E. Baumbach, Physical Review B 97 (2018), 10.1103/physrevb.97.224406.
- [2] C. Pfleiderer, G. J. McMullan, S. R. Julian, and G. G. Lonzarich, Physical Review B 55, 8330 (1997).
- [3] M. Brando, D. Belitz, F. Grosche, and T. Kirkpatrick, Reviews of Modern Physics 88, 025006 (2016).
- [4] T. R. Kirkpatrick and D. Belitz, Physical Review B 85, 134451 (2012).
- [5] D. Belitz, T. R. Kirkpatrick, and T. Vojta, Physical Review Letters 82, 4707 (1999).
- [6] D. Belitz, T. R. Kirkpatrick, and J. Rollbhler, Physical Review Letters 94, 247205 (2005).
- [7] T. R. Kirkpatrick and D. Belitz, Physical Review B 91, 214407 (2015).
- [8] M. Janoschek, M. Garst, A. Bauer, P. Krautscheid, R. Georgii, P. Bni, and C. Pfleiderer, Physical Review B 87, 134407 (2013).
- [9] U. S. Kaluarachchi, V. Taufour, S. L. Bud'ko, and P. C. Canfield, Physical Review B 97 (2018), 10.1103/physrevb.97.045139.
- [10] M. Uhlarz, C. Pfleiderer, and S. M. Hayden, Physical Review Letters 93, 256404 (2004).
- [11] N. Kimura, M. Endo, T. Isshiki, S. Minagawa, A. Ochiai, H. Aoki, T. Terashima, S. Uji, T. Matsumoto, and G. G. Lonzarich, Physical Review Letters 92, 197002 (2004).
- [12] D. Belitz and T. Kirkpatrick, Physical Review Letters 119, 267202 (2017).
- [13] U. S. Kaluarachchi, S. L. Bud'ko, P. C. Canfield, and V. Taufour, Nature Communications 8 (2017), 10.1038/s41467-017-00699-x.
- [14] V. Taufour, U. S. Kaluarachchi, S. L. Bud'ko, and P. C. Canfield, Physica B: Condensed Matter 536, 483 (2018).
- [15] W. Jeitschko and W. K. Hofmann, Journal of the Less Common Metals 95, 317 (1983).
- [16] T. Shang, Y. H. Chen, W. B. Jiang, Y. Chen, L. Jiao, J. L. Zhang, Z. F. Weng, X. Lu, and H. Q. Yuan, Journal of Physics: Condensed Matter 26, 045601 (2014).
- [17] V. H. Tran and Z. Bukowski, Journal of Physics: Condensed Matter 26, 255602 (2014).
- [18] V. Tran, Z. Bukowski, L. Tran, and A. Zaleski, Acta Physica Polonica A 126, 334 (2014).
- [19] Y. Ikeda, H. Yoshizawa, S. Konishi, S. Araki, T. C. Kobayashi, T. Yokoo, and S. Ito, Journal of Physics: Conference Series **592**, 012013 (2015).
- [20] G. Drachuck, A. E. Bhmer, S. L. Bud'ko, and P. C. Canfield, Journal of Magnetism and Magnetic Materials

417, 420 (2016).

- [21] N. Nambudripad, E. V. Sampathkumaran, R. Vijayaraghavan, I. Stang, and K. Lders, Solid State Communications 60, 625 (1986).
- [22] D. Belitz, T. R. Kirkpatrick, and T. Vojta, Physical Review B 55, 9452 (1997).
- [23] D. VanGennep, A. Linscheid, D. E. Jackson, S. T. Weir, Y. K. Vohra, H. Berger, G. R. Stewart, R. G. Hennig, P. J. Hirschfeld, and J. J. Hamlin, Journal of Physics: Condensed Matter 29, 09LT02 (2017).
- [24] S. Klotz, J.-C. Chervin, P. Munsch, and G. L. Marchand, Journal of Physics D: Applied Physics 42, 075413 (2009), publisher: IOP Publishing.
- [25] S. T. Weir, J. Akella, C. Aracne-Ruddle, Y. K. Vohra, and S. A. Catledge, Applied Physics Letters 77, 3400 (2000), publisher: American Institute of Physics.
- [26] A. D. Chijioke, W. J. Nellis, A. Soldatov, and I. F. Silvera, Journal of Applied Physics 98, 114905 (2005).
- [27] N. C. Holmes, J. A. Moriarty, G. R. Gathers, and W. J. Nellis, Journal of Applied Physics 66, 2962 (1989).
- [28] P. Rhodes, E. P. Wohlfarth, and H. Jones, Proceedings of the Royal Society of London. Series A. Mathematical and Physical Sciences 273, 247 (1963).
- [29] H. Yamada and S. Takada, Progress of Theoretical Physics 48, 1828 (1972).
- [30] C. Prescher and V. B. Prakapenka, High Pressure Research 35, 223 (2015).
- [31] B. H. Toby and R. B. V. Dreele, Journal of Applied Crystallography 46, 544 (2013).
- [32] P. Vinet, J. R. Smith, J. Ferrante, and J. H. Rose, Physical Review B 35, 1945 (1987).
- [33] K. T. Moore and G. van der Laan, Reviews of Modern Physics 81, 235 (2009).
- [34] W. N. Miner, PLUTONIUM 1970 AND OTHER AC-TINIDES. NUCLEAR METALLURGY, VOLUME 17. Proceedings of the 4th International Conference, Sante Fe, New Mexico, October 5–9, 1970., Tech. Rep. CONF-701001-(Pt.1); EUR-4633 (Los Alamos Scientific Lab., N. Mex., 1971).
- [35] V. Taufour, D. Aoki, G. Knebel, and J. Flouquet, Physical Review Letters 105, 217201 (2010).
- [36] H. Kotegawa, V. Taufour, D. Aoki, G. Knebel, and J. Flouquet, Journal of the Physical Society of Japan 80, 083703 (2011).
- [37] N. Kabeya, H. Maekawa, K. Deguchi, N. Kimura, H. Aoki, and N. K. Sato, Journal of the Physical Society of Japan 81, 073706 (2012).
- [38] H. Kotegawa, T. Toyama, S. Kitagawa, H. Tou, R. Yamauchi, E. Matsuoka, and H. Sugawara, Journal of the Physical Society of Japan 82, 123711 (2013).
- [39] E. Lengyel, M. E. Macovei, A. Jesche, C. Krellner, C. Geibel, and M. Nicklas, Physical Review B 91, 035130 (2015).