

# Mechanical disorder of sticky-sphere glasses. II. Thermo-mechanical inannealability

Karina González-López,<sup>1</sup> Mahajan Shivam,<sup>2</sup> Yuanjian Zheng,<sup>2</sup> Massimo Pica Ciamarra,<sup>2,3</sup> and Edan Lerner<sup>1,\*</sup>

<sup>1</sup>*Institute for Theoretical Physics, University of Amsterdam, Science Park 904, Amsterdam, Netherlands*

<sup>2</sup>*School of Physical and Mathematical Sciences, Nanyang Technological University, Singapore 637371, Singapore*

<sup>3</sup>*CNR-SPIN, Dipartimento di Scienze Fisiche, Università di Napoli Federico II, I-80126 Napoli, Italy*

Many structural glasses feature static and dynamic mechanical properties that can depend strongly on glass formation history. The degree of universality of this history-dependence, and what it is possibly affected by, are largely unexplored. Here we show that the variability of elastic properties of simple computer glasses under thermal annealing depends strongly on the strength of attractive interactions between the glasses' constituent particles – referred to here as glass 'stickiness'. We find that in stickier glasses the stiffening of the shear modulus with thermal annealing is strongly suppressed, while the thermal-annealing-induced softening of the bulk modulus is enhanced. Our key finding is that the characteristic frequency and density per frequency of soft quasilocalized modes becomes effectively invariant to annealing in very sticky glasses, the latter are therefore deemed 'thermo-mechanically inannealable'. The implications of our findings and future research directions are discussed.

## I. INTRODUCTION

One intriguing feature of structural glasses is the strong history dependence of their mechanical properties [1–11]. It has been known since the work of Shi and Falk [12] that plastic strain localization is enhanced, and stress overshoots are more pronounced, in glasses cooled at lower rates from a melt prior to their deformation [3, 5, 8]. Other work has shown that deforming computer glasses under one loading geometry can significantly alter the subsequent responses of the material in the same and other loading geometries [13, 14]. Advances in experimental techniques that allow high control over the precise 'fictive temperature' at which a metallic glass falls out of equilibrium [15] were used to demonstrate that the notch fracture toughness of the same material can change by over a factor of two, depending on its fictive temperature, i.e. on its preparation history.

Methodological advances in computational glass physics have helped to shed considerable light on the aforementioned history dependence of glasses' mechanical properties. In particular, the optimization of polydisperse soft-sphere [16] and other [17] models with respect to their efficiency under Swap Monte Carlo dynamics has allowed the creation of glasses from very deeply supercooled liquids, and the systematic study of those glasses' mechanical properties as a function of their preparation history [8, 18–20]. These studies and others have established that a generic feature of computer [21] and laboratory glasses [15] is that their shear modulus  $G$  typically increases with deeper supercooling prior to glass formation; some observations report a total annealing-induced variation of  $G$  of up to  $\approx 60\%$  in 3D [20] (and  $> 70\%$  in 2D [22]). It has also been shown that the relative, sample-to-sample fluctuations of elastic moduli, shown recently

to control long wavelength wave attenuation rates [23], decrease by over a factor of 3 in well-annealed glasses [19].

Another manifestation of thermal annealing on glasses' elasticity is seen in the energetic, statistical and structural properties of soft, quasilocalized modes [18, 20, 21, 24–28] (QLMs). These low-energy excitations were shown to exist in any structural glass quenched from a melt [29], and presumably play important roles in dynamic glassy phenomena such as wave attenuation [30], elasto-plasticity [31], aging dynamics [32] and structural relaxation in equilibrium supercooled liquids [33]. Evidence that a subset of these excitations may constitute the tunneling two-level systems, responsible for the anomalous thermodynamic and transport properties of glasses at cryogenic temperatures, has also been put forward [34].

Several observations have been made that establish a connection between the degree of thermal annealing of glasses and their featured abundance of QLMs. To the best of our knowledge, the first observation was made by Schober and Oligschleger [24], who argued that the relative absence of soft, quasilocalized vibrational modes in a model glass is attributed to both their stiffening and overall depletion. This assertion was further discussed in [20], where the total number density of QLMs was demonstrated to following a Boltzmann-like law with respect to the parent *equilibrium* temperature  $T_p$  from which the studied glasses were instantaneously quenched. In the same work it was shown that the characteristic frequency of QLMs increases by more than a factor of two due to strong thermal annealing.

What features of model structural glasses' interaction potentials control the degree of susceptibility of statistical-mechanical properties of a glass — in particular its macro- and microscopic elastic properties, and mechanical disorder — to thermal annealing? This is precisely the question we address in the present work, which is the second out of a series of reports aimed at tracing

\* e.lerner@uva.nl

out the effects of strong, attractive interactions between the constituent particles of a glass, on that glass’s mechanical disorder. In the first paper [35], we aimed at avoiding thermal annealing effects on elasticity, in order to cleanly single-out the role of strong attractive interactions in determining glasses’ elastic properties, mechanical disorder and stability. In order to compare between different computer glass models on the same footing, we followed Refs. [19, 29] and exploited the high-temperature plateau of elastic properties featured by most computer glass models, including those considered in this work.

Here we show that in a model computer glass in which the relative strength of pairwise attractive interactions — referred to here as ‘glass stickiness’ — can be readily tuned [36], the degree of thermal-annealing-induced *variations* in glasses’ elastic properties exhibits a strong dependence on glass stickiness. In particular, we find that the relative stiffening of the shear modulus in deeply annealed glasses decreases substantially upon increasing glass stickiness, while the relative softening of the bulk modulus increases. We further find that increasing glass stickiness leads to the indifference of the characteristic frequency scale associated with soft, quasilocalized excitations, of those excitations’ characteristic size, and of their density per frequency, to thermal annealing. We refer to this surprising emergent indifference of mechanical properties to thermal annealing as *thermo-mechanical inannealability* of glasses.

The phenomena of thermo-mechanical inannealability is illustrated within the potential energy landscape picture [37] by the cartoon displayed in Fig. 1. The potential landscape of a generic computer glass model — e.g. the extensively-studied Kob-Andersen Binary Lennard-Jones glass former [38] — is illustrated by Fig. 1a. In those systems, the characteristic frequency of the glass’s soft nonphononic quasilocalized modes — represented by the characteristic *curvature* of the landscape about its local minima, and denoted by  $\omega_g^2$  in Fig. 1a and in what follows — is small at high energies, and grows as lower energies are reached, see related discussions in [21, 39–41].

In contrast with the behavior of generic glass-formers described above, the potential energy landscape of sticky-sphere glasses is substantially different. As illustrated by the bottom panel of Fig. 1, the multidimensional landscape shows almost no change in its characteristic frequencies (curvatures about local minima) as one descends to lower energies. Below we will show that, despite that sticky spheres glass’s potential energy features a *larger* relative variation upon supercooling compared to glasses with weaker attractive interactions, many of these glasses’ mechanical properties, including dimensionless quantifiers of mechanical disorder, are largely indifferent to descending deep down into the energy landscape.

This work is structured as follows; in Sect. II we introduce and motivate the choice of the model system employed in our study, and describe how different ensembles

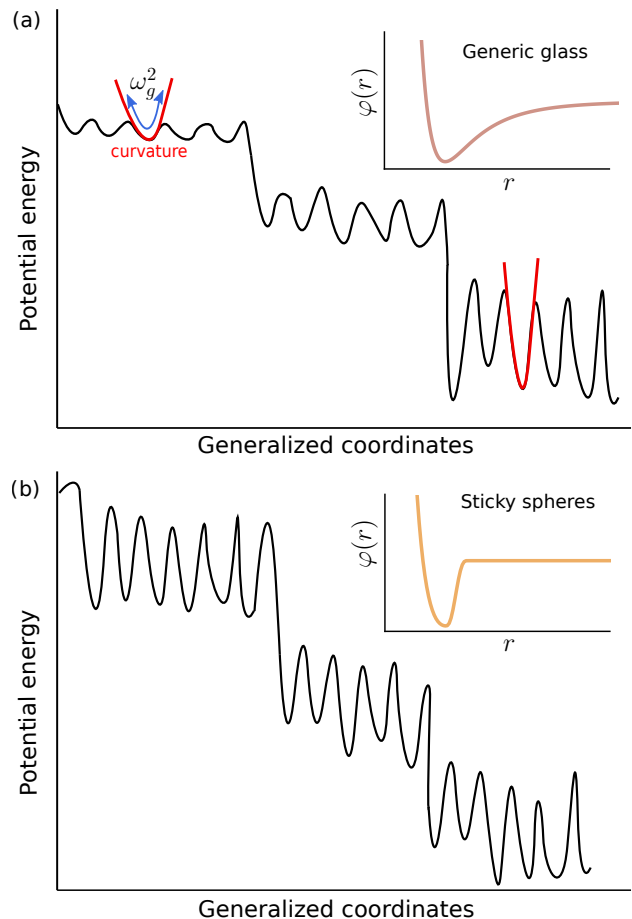


FIG. 1. Illustration of the concept of thermo-mechanical inannealability. The top panel depicts the potential energy landscape (PEL) of a generic glass. In generic glasses the characteristic frequencies associated with local minima *increase* with decreasing energy. As we increase the relative strength of attractive forces and decrease their range (see insets) — namely we make a ‘stickier’ glass —, the PEL is altered (see bottom panel): characteristic frequencies associated with local minima become largely *independent* of the energy.

of glassy samples were created. In Sect. III we put forward a scheme that allows to extract a crossover temperature scale  $T_{co}$  based on the potential energy per particle of our glass ensembles. The scale  $T_{co}$  is then used to organize the rest of our data presentations. Sects. IV and V discuss the effect of particle stickiness on the thermal annealability of macroelastic and microelastic properties, respectively. We summarize our findings and discuss future research questions in Sect. VI. The definitions of, and some explanations about, the physical observables considered in this work can be found in Appendix A.

## II. COMPUTER GLASS MODEL AND GLASS ENSEMBLES

In this work we employ a 50:50 binary mixture of ‘large’ and ‘small’ particles of equal mass  $m$  in three

| $r_c$ | $T_p$  | $N$    | $n$   |
|-------|--|--------|-------|
| 1.1   | 6.00, 4.00, 3.00, 2.00, 1.50, 1.20, 1.00, 0.88, 0.80, 0.76, 0.73 | 3,000  | 9,200 |
| 1.2   | 4.00, 2.60, 1.80, 1.30, 1.00, 0.91, 0.85, 0.80, 0.77             | 3,000  | 9,200 |
| 1.3   | 4.00, 2.60, 1.80, 1.30, 1.15, 1.00, 0.91, 0.85, 0.80, 0.77       | 3,000  | 9,200 |
| 1.5   | 0.76, 0.72, 0.69   | 3,000  | 9,200 |
| 1.5   | 2.60, 1.80, 1.30, 1.00, 0.91, 0.85, 0.80                         | 10,000 | 3,000 |

TABLE I. Equilibrium parent temperatures, for various cutoffs from the SS model. The system and ensemble size shown in the last two columns apply for all parent temperatures listed.

dimensions (3D) at fixed volume  $V$ . Pairs of particles interact via the Piecewise-Sticky-Spheres (PSS) pairwise potential, introduced first in [36], and also studied extensively in the first paper [35] of this series. The equilibrium supercooled liquid dynamics of this model was very recently studied in [42]. The PSS model was chosen for this study since in [35] it featured the strongest variation of elastic properties as a function of its key control parameter, which is described next.

The PSS is a Lennard-Jones-like pairwise potential in which the repulsive part is identical to the canonical Lennard Jones (LJ) potential, but the attractive part is modified such that it and its first two derivatives with respect to interparticle distance  $r_{ij}$  vanish continuously at a (dimensionless) cutoff distance  $x_c$ , the latter serving as a control parameter; the PSS pairwise potential reads

$$\varphi_{\text{PSS}}(r_{ij}) = \begin{cases} 4\epsilon \left[ \left( \frac{\lambda_{ij}}{r_{ij}} \right)^{12} - \left( \frac{\lambda_{ij}}{r_{ij}} \right)^6 \right], & \frac{r_{ij}}{\lambda_{ij}} < x_{\min} \\ \epsilon \left[ a \left( \frac{\lambda_{ij}}{r_{ij}} \right)^{12} - b \left( \frac{\lambda_{ij}}{r_{ij}} \right)^6 + \sum_{\ell=0}^3 c_{2\ell} \left( \frac{r_{ij}}{\lambda_{ij}} \right)^{2\ell} \right], & x_{\min} \leq \frac{r_{ij}}{\lambda_{ij}} < x_c \\ 0, & \frac{r_{ij}}{\lambda_{ij}} \geq x_c \end{cases}, \quad (1)$$

where  $\epsilon$  is a microscopic energy scale,  $x_{\min}, x_c$  are the (dimensionless) locations of the minimum of the LJ potential and modified cutoff, respectively, and the length parameters  $\lambda_{ij}$  are expressed in terms of the ‘small-small’ interaction length  $\lambda_{\text{small}}^{\text{small}}$ , with  $\lambda_{\text{small}}^{\text{large}} = 1.18\lambda_{\text{small}}^{\text{small}}$  and  $\lambda_{\text{large}}^{\text{large}} = 1.4\lambda_{\text{small}}^{\text{small}}$ . The coefficients  $a, b, \{c_{2\ell}\}$  can be found in [35]; they are chosen such that the attractive and repulsive parts of the potential and two derivatives are continuous at  $x_{\min}$  and at  $x_c$ . The pairwise potential  $\varphi_{\text{PSS}}$  is plotted in Fig. 2. In what follows, we express the dimensionless cutoff  $x_c$  of  $\varphi_{\text{PSS}}$  in terms of  $x_{\min} = 2^{1/6}$  by defining  $r_c \equiv x_c/x_{\min}$ , for simplicity.  $r_c$  serves as one of the two key control parameters in our investigation.

We build ensembles of glassy samples at fixed number density  $N/V = 0.60(\lambda_{\text{small}}^{\text{small}})^{-3}$ , using  $r_c = 1.1, 1.2, 1.3$ , and 1.5; glass configurations were initially equilibrated at various parent temperatures  $T_p$  — the second key control parameter in our investigation — for which the liquids’ equilibrium relaxation times (estimated via the stress autocorrelations, see Fig. 17 in Appendix A) vary over approximately 4 orders of magnitude, for each  $r_c$ . Details about the equilibrium parent temperatures, system and ensemble sizes appear in Table I. We have checked and found no signs of crystallization. In what follows, we report all lengths in terms of the characteristic interparticle distance  $a_0 \equiv (V/N)^{1/3}$ , and all frequencies in terms of

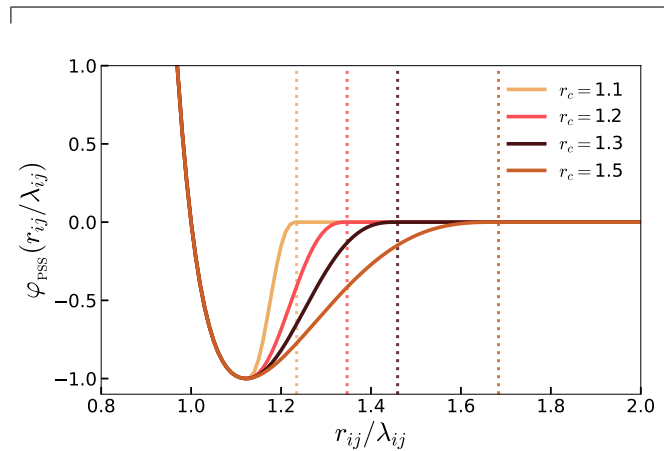


FIG. 2. The Piecewise Sticky Spheres (PSS) pairwise interaction potential employed in this work. The interaction cutoffs  $r_c$  — marked by the color-coded vertical dotted lines — are expressed in terms of the dimensionless distance  $x_{\min} = 2^{1/6}$  at which the canonical Lennard Jones potential attains a minimum.

$\omega_0 \equiv c_s/a_0$ , where the speed of shear waves is defined as  $c_s \equiv \sqrt{G/\rho}$  with  $\rho \equiv mN/V$  denoting the mass density, and notice that  $\omega_0, c_s$  and  $G$  are all  $r_c$ - and  $T_p$ -dependent.

Importantly, we note that the thermal-annealing-induced variation percentages of the observables reported

in what follows depend on the depth of supercooling of glasses' ancestral equilibrium configurations; here, our different glass models (pertaining to different cutoffs  $r_c$ ) were all supercooled roughly evenly, at least in terms of their respective equilibrium liquid dynamics as shown in Fig. 17 of Appendix A. This roughly-even depth of supercooling across models allows us to meaningfully compare thermal-annealing-induced *relative* variations of observables, across the entire parent temperature range of each glass model, and across ensembles of different glass models.

### III. EXTRACTING A CROSSOVER TEMPERATURE SCALE

In the previous paper [35] of this series, we prepared glassy samples by instantaneously quenching high temperature equilibrium liquid states; the equilibrium parent temperatures were chosen to be at least a factor of 4 higher than the computer glass transition temperature  $T_g$ , defined here as the temperature at which the structural relaxation time  $\sim 10^4 \tau_*$ , with  $\tau_*$  representing a characteristic vibrational time scale. As we shall see below, and as previously observed [19, 43–45], elastic properties and various dimensionless quantifiers of mechanical disorder exhibit a plateau above some crossover temperature, denoted in what follows as  $T_{co}$ . An equal-footing comparison of elastic properties is possible by considering parent temperatures  $T_p$  much larger than the crossover temperature  $T_{co}$ .

How should the crossover temperature  $T_{co}$  — with respect to which we compare different glasses made by quenching states equilibrated at various parent temperatures  $T_p$  — be defined? Defining a physically-relevant temperature scale in supercooled liquids is not a trivial task, see e.g. discussions in Refs. [46, 47]. Here we introduce a simple, broadly applicable and evidently useful scheme to define  $T_{co}$ , which is based on the  $T_p$ -dependence of the ensemble average energy per particle  $u(T_p) \equiv U(T_p)/N$  of our computer glasses. The raw data for  $u(T_p)$ , expressed in terms of simulational units, is shown in Fig. 14 of Appendix B.

The scheme is illustrated in Fig. 3; we show  $(u(T_p) - u(T_{co}))/T_{co}$  vs.  $T_p/T_{co}$ , namely the difference between the inherent state energy per particle  $u(T_p)$ , and the linearly interpolated energy per particle  $u(T_{co})$ , rescaled by the crossover temperature  $T_{co}$ , and plotted against the rescaled parent temperature  $T_p/T_{co}$ . This is done by choosing the crossover temperatures  $T_{co}$  for each model, such that the collapse across all models is optimal for  $T_p < T_{co}$ . The quasiuniversal form of the shifted and rescaled  $u(T_p)$  is also shown in Fig. 3 to be followed by 3 additional computer glass models: the canonical Kob-Andersen Binary Lennard-Jones model [38], a Hertzian soft-spheres glass [29], and a polydisperse, inverse power law glass [19, 20], whose respective extracted crossover

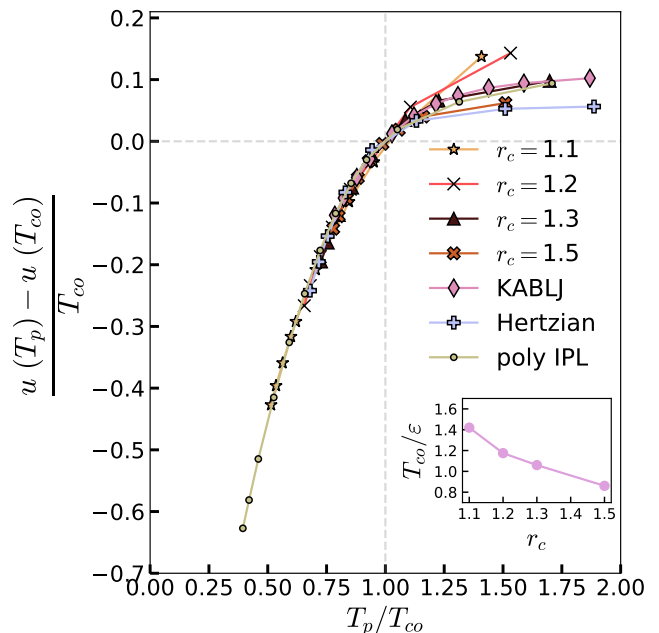


FIG. 3. Glass potential energy per particle  $u(T_p)$ , shifted by the interpolated  $u(T_{co})$ , and rescaled by the crossover temperature  $T_{co}$ , see text for discussion. The inset shows the extracted crossover temperatures  $T_{co}$  for the computer glasses studied in this work.

temperatures  $T_{co}$  can be found in [48].

Interestingly, despite a good collapse of  $u(T_p)$  at  $T_p < T_{co}$  for several different computer glass models, there seems to be no obvious connection between the extracted crossover temperatures  $T_{co}$ , and the supercooled dynamics of the parent equilibrium states from which the glasses were quenched. This is to say that, for example, the dimensionless structural relaxation time of the  $r_c = 1.1$ ,  $T_p/T_{co} \approx 0.52$  liquids is roughly equal to that of the  $r_c = 1.5$ ,  $T_p/T_{co} \approx 0.78$  liquids (see lowest- $T_p$  correlation functions in Fig. 17a,d), implying that the dimensionless relaxation time is *not* a universal function of  $T_p/T_{co}$ . Consequently, the dimensionless glass transition temperature  $T_g/T_{co}$  is not expected to be universal either.

Another interesting observation, discussed further below, is that even though the crossover temperature  $T_{co}$  is a decreasing function of the interaction potential cutoff  $r_c$ , the absolute variation of the rescaled and shifted glass energy  $(u(T_p) - u(T_{co}))/T_{co}$  for  $T_p < T_{co}$  appears to be larger for the stickier glasses, with the smaller cutoffs. This is to say that the largest variation of glass energy per particle — in terms of  $T_{co}$  — is seen for the  $r_c = 1.1$  glasses, in contrast with the  $T_p$ -dependence of many of those glasses' *elastic* properties, as shown in what follows.

An obvious limitation of the scheme described above is that it only allows the extraction of crossover temperatures if  $u(T_p)$  is available for a few computer glass models, that all follow the same quasiuniversal form below  $T_p$ , which is not a-priori known. However, a very close estimate of the extracted  $T_{co}$  — as seen in the inset of

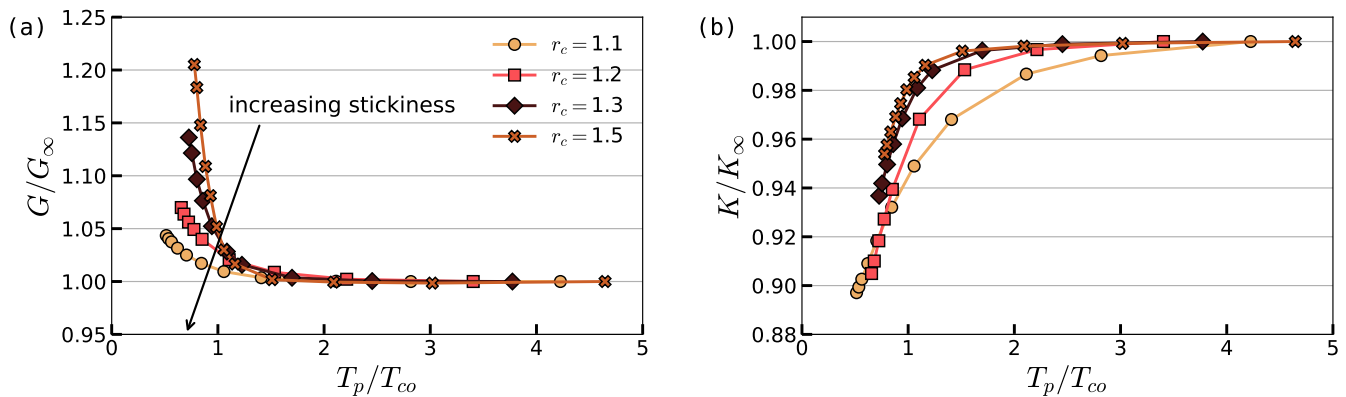


FIG. 4. (a) Sample-to-sample average shear modulus  $G$ , rescaled by its high temperature plateau value  $G_\infty$ , and plotted against  $T_p/T_{co}$ . (b) same as (a) for the sample-to-sample mean bulk modulus  $K$ , see text for discussion.

Fig. 3 — can be obtained by analyzing the  $T_p$ -dependent elastic moduli of a single computer glass model, as explained and demonstrated in Appendix C.

#### IV. EFFECT OF THERMAL ANNEALING ON MACROELASTICITY

Having established how to extract a crossover temperature scale  $T_{co}$  for our different  $r_c$ -ensembles, we next review our measurements of macroelastic observables, namely elastic moduli. Precise definitions of the studied observables can be found in Appendix A.

Elastic moduli of glasses are known to depend on the equilibrium parent temperature  $T_p$  from which those glasses were quenched [7, 19, 21, 22]. Here we assess the degree of this dependence under variations of the relative strength of attractions (glass ‘stickiness’), tuned in turn by varying the interaction cutoff  $r_c$  of our sticky-sphere glasses, as explained in Fig. 2. In Fig. 4a-d we plot the sample-to-sample average athermal shear modulus  $G$ , rescaled by its high- $T_p$  plateau, denoted as  $G_\infty$ . We see that increasing glass stickiness leads to the suppression of the relative thermal-annealing-induced variation in  $G$ : for the  $r_c = 1.5$  glasses  $G$  increases by slightly more than 20%, whereas the  $r_c = 1.1$  glasses feature a much milder variation, of slightly less than 5% — a factor of over 4 smaller relative thermal-annealing-induced variation compared to the  $r_c = 1.5$  glasses. This increasing indifference to thermal annealing by increasing glass stickiness is the first example of thermo-mechanical inannealability presented in this work.

Interestingly, the ensemble-average athermal bulk modulus  $K(T_p)$ , plotted in Fig. 4e-h after rescaling by its high- $T_p$  limit  $K_\infty$ , shows two opposite trends compared to  $G(T_p)$ ; first,  $K(T_p)$  is a decreasing function of the parent temperature  $T_p$ , whereas  $G(T_p)$  is an increasing function of  $T_p$ . The observed decrease of  $K$  with annealing appears to be a common feature of some simple

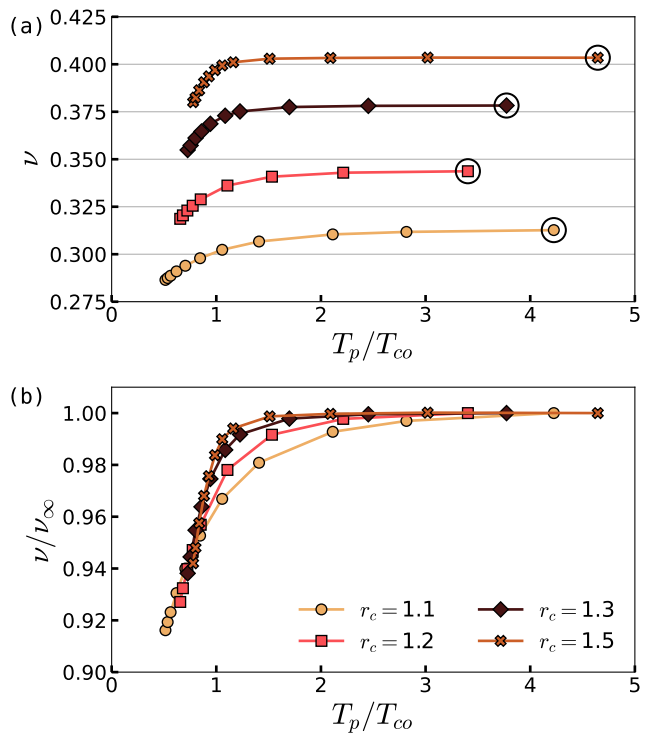


FIG. 5. In panel (a) the Poisson's ratio  $\nu$  is plotted against the parent temperature  $T_p$ , for all  $r_c$ -ensembles. The circled data points represent  $\nu_\infty$ , used for rescaling  $\nu$  as seen in panel (b).

glass models [18, 19], but not of laboratory glasses [26, 49] that are typically annealed at constant pressure. Second, the largest relative decrease in  $K(T_p)$  — of roughly 10% — is featured by the stickiest amongst our glasses: the  $r_c = 1.1$  ensemble, while the largest relative increase in  $G(T_p)$  is featured by the  $r_c = 1.5$  glasses.

Next, we show in Fig. 5a the sample-to-sample average Poisson's ratio  $\nu \equiv (3 - 2G/K)/(6 + 2G/K)$ , plotted against  $T_p$ , for all  $r_c$ -ensembles. We find that while the typical  $\nu$  values depend quite significantly on  $r_c$  (as we

have also shown in [35]), the relative variation of  $\nu$  across the entire sampled  $T_p$  range, as seen in Fig. 5b, does not differ much between the highest and lowest  $r_c$ -ensembles. Clearly, the rescaled curves  $\nu/\nu_\infty$  do not collapse when plotted against  $T_p/T_{co}$ .

## V. EFFECT OF THERMAL ANNEALING ON MICROSCOPIC ELASTICITY

The vibrational density of states (vDOS) associated with nonphononic soft quasilocalized modes in structural glasses has been long ago predicted [50, 51] and recently shown [25] to universally follow a quartic law, namely

$$\mathcal{D}(\omega) = A_g \omega^4, \quad (2)$$

independent of spatial dimension [52], glass formation protocol [18, 20, 21], or form of microscopic interactions [29]. The prefactor  $A_g$  has dimensions of [frequency] $^{-5}$ , and its physical essence has been discussed at length in [20, 21]. In those works it is asserted that  $A_g(T_p) \sim \mathcal{N}(T_p) \omega_g^{-5}(T_p)$ , where  $\mathcal{N}(T_p)$  and  $\omega_g(T_p)$  represent the parent-temperature dependent density per particle and characteristic frequency of soft quasilocalized modes (QLMs), respectively.

Previous investigations have shown that thermal annealing of computer glasses can affect the statistical, energetic and structural properties of their embedded soft QLMs [18–21, 24, 25, 27]. Here we investigate how the susceptibility of those aforementioned properties to thermal annealing – changes by varying glass stickiness.

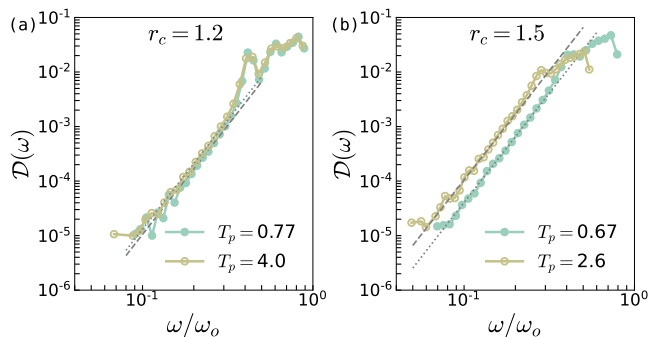


FIG. 6. The vDOS  $\mathcal{D}(\omega)$ , calculated for low and high parent temperatures  $T_p$ , in our  $r_c = 1.2$  systems (left) and for our  $r_c = 1.5$  systems (right). We find that the prefactor  $A_g$  of the  $\omega^4$  scaling depends very weakly on  $T_p$  for moderate particle stickiness ( $r_c = 1.2$ ), and shows a much more pronounced dependence on thermal annealing for weak particle stickiness ( $r_c = 1.5$ ).

### A. Density per frequency of QLMs

We first study the thermal-annealing susceptibility of the prefactor  $A_g(T_p)$ , as measured in our different- $r_c$

glass-ensembles. In Fig. 6 we show examples of the low-frequency vDOS of our computer glasses. In particular, we plot  $\mathcal{D}(\omega)$  against  $\omega/\omega_0$ , for the highest and lowest parent temperatures, and for two cutoffs:  $r_c = 1.2$  (Fig. 6a) and  $r_c = 1.5$  (Fig. 6b). We recall that  $\omega_0 \equiv c_s/a_0$ , where  $c_s$  is the speed of shear waves, and  $a_0$  an interparticle distance. Superimposed dashed and dotted lines are fits to Eq. 2, that demonstrate how  $A_g$  is extracted from the vDOS data.

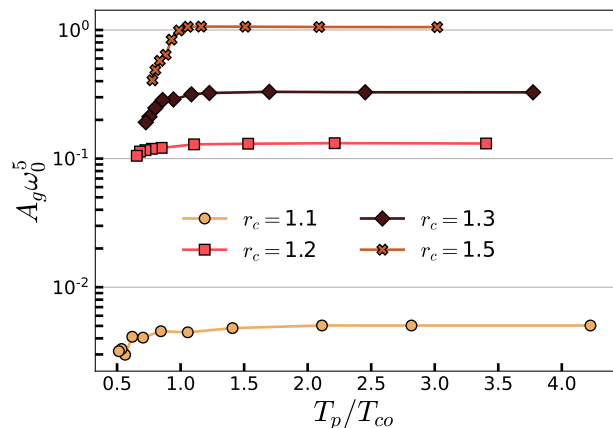


FIG. 7. Prefactors  $A_g$  of the universal nonphononic vDOS  $\mathcal{D}(\omega) = A_g \omega^4$ , made dimensionless by scaling by  $\omega_0^5$ , measured across and plotted against parent temperatures  $T_p$ , for our different  $r_c$ -ensembles.

Comparing the vDOS of the  $r_c = 1.2$  and the  $r_c = 1.5$  glasses, we clearly see that in the former case  $A_g$  is nearly independent of  $T_p$ , while in the latter case a measurable difference is seen between the high and low  $T_p$  data. A more comprehensive presentation of  $A_g$ 's dependence on  $T_p$  is presented in Fig. 7, where we plot  $A_g$  against  $T_p$  for all  $r_c$ 's. In the previous paper of this series [35] we showed that  $A_g$  is very sensitive to increasing glass stickiness; that sensitivity can be seen here too by examining the large  $T_p$  plateaus of  $A_g$  for different  $r_c$ 's.

Consistent with the behavior of other observable shown above,  $A_g$  becomes a weaker function of  $T_p$  as glass stickiness is increased, i.e. the glasses become thermo-mechanically inannealable. We note, importantly, that with conventional molecular dynamics methods we have employed, we are unable to supercool our model systems very deeply. In contrast, using the Swap Monte-Carlo method [16], one is able to achieve very deep supercooling of polydisperse systems, leading in some cases to a thousand-fold decrease in  $A_g$ , as shown in [20, 35]. It is clearly important to establish in the future whether the thermo-mechanical inannealability we observe here in sticky glasses persists under deeper supercooling of their parent equilibrium states, as allowed by Swap Monte-Carlo.

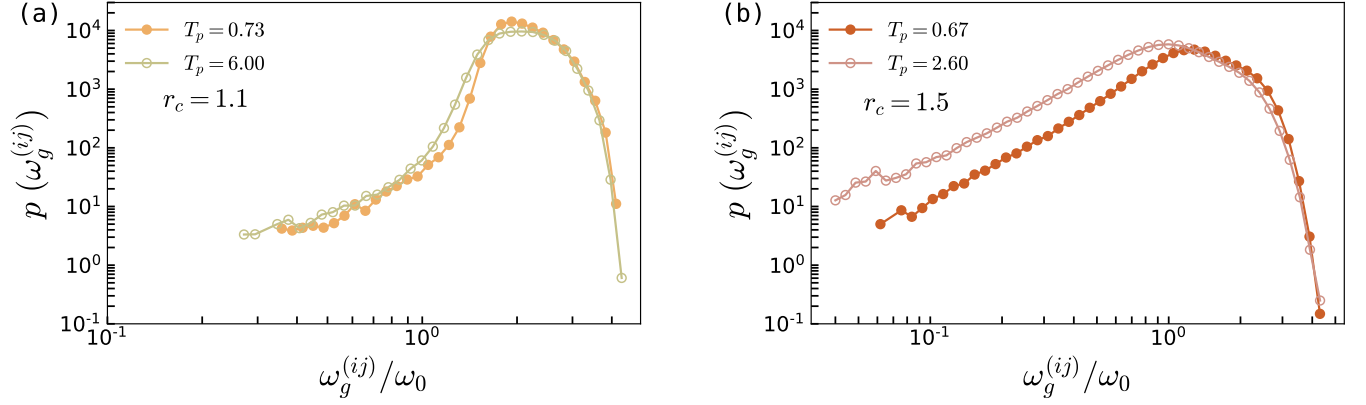


FIG. 8. Distributions  $p(\omega_g^{(ij)})$  of the dipole-response frequencies  $\omega_g^{(ij)}$  (cf. Eq.(3)) vs. the dimensionless  $\omega_g^{(ij)}/\omega_0$ , for (a) our stickiest glasses ( $r_c=1.1$ ) and (b) for the least sticky glasses ( $r_c=1.5$ ), measured for their respective highest and lowest parent temperature  $T_p$  as indicated by the legends.

### B. Characteristic frequency of QLMs

The second microelastic observable we study is the aforementioned characteristic frequency  $\omega_g(T_p)$  of QLMs. It has been suggested in Refs. [20–22] that the characteristic frequency of the displacement-response to locally-imposed force dipoles is a good representation of QLMs' characteristic frequency  $\omega_g$ . Here, we follow those suggestions; we measure

$$\omega_g^{(ij)} \equiv \sqrt{\frac{\mathbf{u}^{(ij)} \cdot \mathcal{M} \cdot \mathbf{u}^{(ij)}}{\mathbf{u}^{(ij)} \cdot \mathbf{u}^{(ij)}}} = \sqrt{\frac{\mathbf{d}^{(ij)} \cdot \mathcal{M}^{-1} \cdot \mathbf{d}^{(ij)}}{\mathbf{d}^{(ij)} \cdot \mathcal{M}^{-2} \cdot \mathbf{d}^{(ij)}}}, \quad (3)$$

for a large, random set of pairs of interacting particles  $i, j$ . Here  $\mathbf{u}^{(ij)} = \mathcal{M}^{-1} \cdot \mathbf{d}^{(ij)}$  is the displacement response to a local force dipole  $\mathbf{d}^{(ij)}$  imposed on the  $i, j$  pair (as illustrated, e.g., in [22]), and  $\mathcal{M} = \frac{\partial^2 U}{\partial \mathbf{x} \partial \mathbf{x}}$  is the Hessian matrix of the potential energy  $U(\mathbf{x})$  that depends on particle coordinates  $\mathbf{x}$ . Finally, in addition to some examples of the distributions  $p(\omega_g^{(ij)})$ , we also report

$$\omega_g \equiv \langle \omega_g^{(ij)} \rangle_{ij}, \quad (4)$$

where  $\langle \bullet \rangle_{ij}$  denotes an average taken over interacting-pairs and glass samples. We note that in the previous paper in this series [35], we followed a different route to extracting  $\omega_g$ ; a short discussion about — and direct comparison between — the two methods is shown in Appendix D.

In Fig. 8 we show the distributions  $p(\omega_g^{(ij)})$  measured for our stickiest ( $r_c = 1.1$ ) and least sticky ( $r_c = 1.5$ ) glasses, for their lowest and highest simulated parent temperatures, as can be seen in the figure legends. Similarly to the low-frequency spectra reported in Fig. 6, here too we find that in the stickier glass the change in  $p(\omega_g^{(ij)})$  between the highest and lowest parent temperatures  $T_p$  is minor, manifesting that system's thermo-mechanical inannealability. In contrast, the distributions

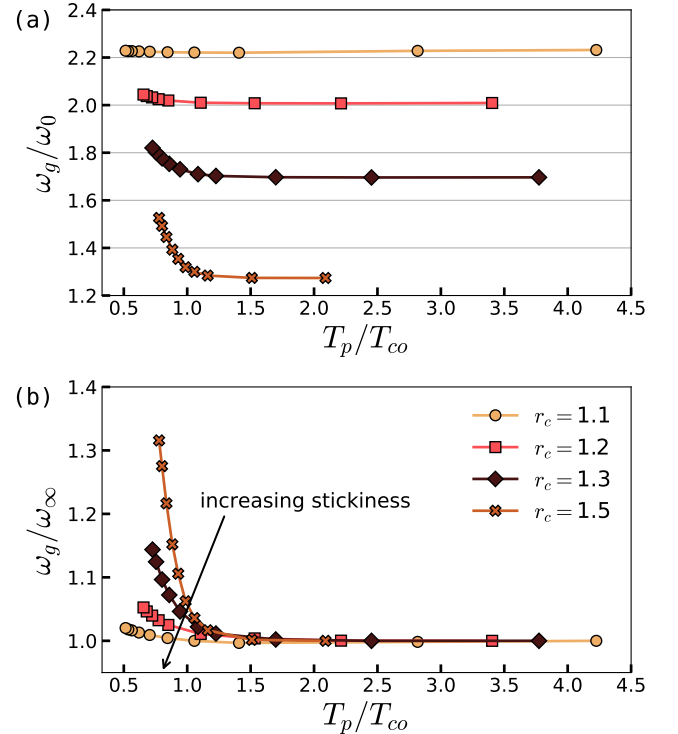


FIG. 9. (a) Characteristic frequency  $\omega_g$  of QLMs, made dimensionless by rescaling by  $\omega_0 \equiv c_s/a_0$ , and plotted against the parent temperature  $T_p$ . (b) same as (a), but rescaled by the high- $T_p$  plateau  $\omega_\infty$ , see text for discussion.

$p(\omega_g^{(ij)})$  for  $r_c = 1.5$  glasses show a measurable difference in the amplitude of their low-frequency tails, supporting further that non-sticky glasses are thermo-mechanically annealable. We can also see that the relative width of  $p(\omega_g^{(ij)})$  changes substantially between the  $r_c = 1.1$  and the  $r_c = 1.5$  glasses, indicating that increasing glass stickiness leads to micromechanical ordering. Similar trends were reported in [22].

We next show our measurements of the means  $\omega_g(T_p)$  in Fig. 9; the reported averages are taken over an immense number of interactions ( $\sim 10^6$ ), thus the data is very smooth. Here we find the same trends as seen above for the  $T_p$ -dependence of  $p(\omega_g^{(ij)})$  and for  $A_g(T_p)$ : the stickier glasses show a pronounced thermo-mechanical inannealability, namely they feature almost no thermal-annealing-induced variation in  $\omega_g/\omega_0$ . In particular, the  $r_c = 1.1$  ensemble shows a total of only 3% change in  $\omega_g/\omega_0$  between its highest and lowest  $T_p$ 's. This should be contrasted with the variation of more than 30% seen for the  $r_c = 1.5$  glasses – a factor of at least 10 larger relative variation, compared to the total variation of  $\omega_g(T_p)$  in the  $r_c = 1.1$  glasses, across the entire simulated  $T_p$  range.

### C. Localization properties of QLMs

It has been previously shown [20, 27, 28] that the core-size of QLMs decreases with strong supercooling of their embedding glasses' ancestral equilibrium states. Here we assess the core size of QLMs via their participation ratio  $e$ , defined given a mode  $\psi$  as

$$e \equiv \frac{(\sum_i \psi_i \cdot \psi_i)^2}{N \sum_i (\psi_i \cdot \psi_i)^2}, \quad (5)$$

where  $\psi_i$  denotes the  $\bar{d}$ -dimensional vector of a mode's Cartesian components associated with the  $i$ th particle. One generally expects  $e \sim 1/N$  for (quasi)localized modes [25], and  $e \sim 1$  for extended modes (such as phonons). It has been shown [27, 28, 34] that the participation ratio of vibrational modes at frequency  $\omega$  plateaus to a value  $e_0$  in the low-frequency,  $\sim \omega^4$  scaling regime of the vDOS. Since the modes populating the scaling regime are quasilocalized, an estimation of QLMs core size — in terms of number of particles — is obtained via the product  $Ne_0$ . The extraction of  $e_0$  from participation ratio data is demonstrated in Figure 13 in Appendix A 2.

Our estimations for  $Ne_0$  are plotted against parent temperature  $T_g$  in Fig. 10, for all  $r_c$ -glass-ensembles. As expected, we see that QLMs core size generally decrease with decreasing parent temperature  $T_p$ , consistent with the aforementioned previous observations. However, the interesting observation here is again the apparent substantial indifference of QLMs' core sizes to thermal annealing in stickier glasses, as shown above to occur for several other observables as well.

### D. How are $A_g$ , $\omega_g$ and $Ne_0$ related?

In the preceding Subsections we have seen that the vDOS prefactor  $A_g$ , the characteristic frequency  $\omega_g$  of QLMs, and QLMs core-size  $Ne_0$ , all show thermo-mechanical inannealability as glass stickiness is increased.

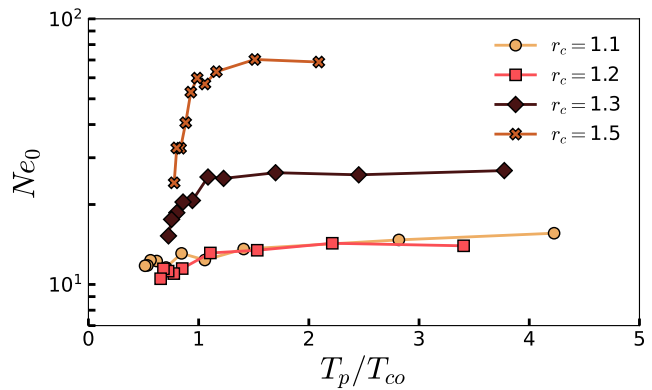


FIG. 10. Scaled mean low-frequency plateau of the participation ratio,  $Ne_0$ , plotted against the parent temperature  $T_p$ ; here again we observe that increasing glass stickiness leads to thermo-mechanical inannealability. For a visual example of how  $Ne_0$  is estimated, see Fig. 13 in Appendix A 2.

The consistency amongst these microelastic observables supports that they are related, as previously suggested and reviewed next.

In Ref. [20] it was established that the core size  $\xi_g$  of QLMs is related to the latter's characteristic frequency  $\omega_g$  via

$$\xi_g = 2\pi c_s / \omega_g, \quad (6)$$

where  $c_s$  denotes the speed of shear waves. Since  $Ne_0$  should approximately represent QLMs' core size, we expect

$$Ne_0 \sim (\xi_g/a_0)^3 \sim (\omega_g/\omega_0)^{-3}, \quad (7)$$

while recalling that  $a_0 \equiv (V/N)^{1/3}$  is an interparticle distance, and that  $\omega_0 \equiv c_s/a_0$  is a characteristic frequency. Eq. (7) is tested in Fig. 11a. The agreement is acceptable; the observed noise may stem from statistical errors in estimations of  $e_0$  (see Appendix A 2 for details), or from a possible intrinsic error in associating the scaled participation ratio  $Ne_0$  with QLMs' core size [53], or both.

We next recall that in [20, 21] it is asserted that

$$A_g \sim \mathcal{N} \omega_g^{-5}, \quad (8)$$

where  $\mathcal{N}$  represents the density per particle of QLMs. With the exception of the stickiest glasses corresponding to  $r_c = 1.1$ , we find that  $A_g$  is entirely determined by  $\omega_g$ , implying that  $\mathcal{N}$  is mostly  $T_p$ -independent and quasiuniversal. The quasiuniversality of  $\mathcal{N}$  was also observed and discussed in the previous paper of this series [35].

Our results are shown in Fig. 11b; had  $\mathcal{N}$  been universal and  $T_p$ -independent, one would simply expect  $A_g \sim \omega_g^{-5}$ . We find that this relation approximately holds for all data points, with the very noticeable exception of the  $r_c = 1.1$  glasses, for which  $A_g \ll \omega_g^{-5}$ , as also seen and discussed in [35]. Thermo-mechanical inannealability is seen here as the dramatically-reduced spread of the data over the  $\omega_g$  axis upon increasing glasses stickiness.



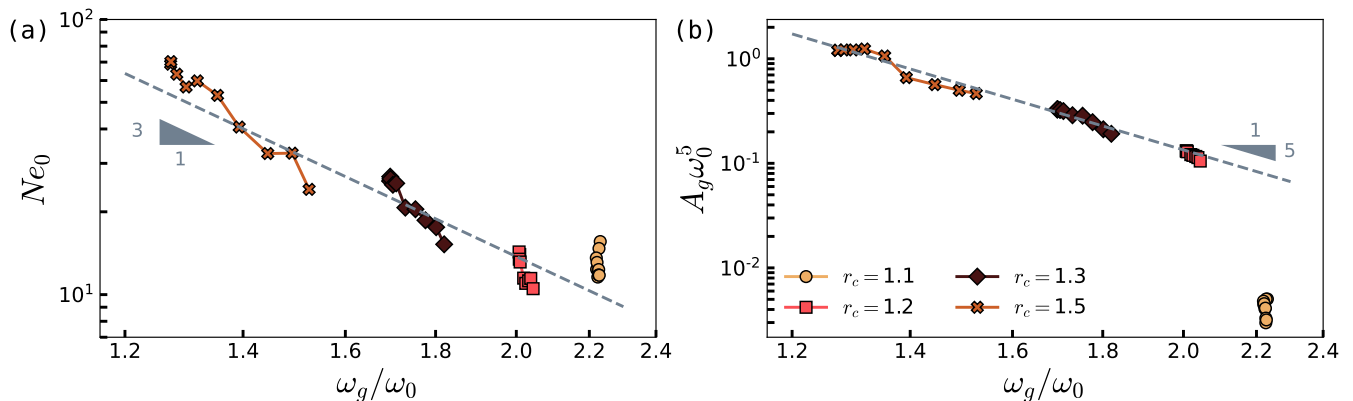


FIG. 11. (a) Scaled participation ratio  $Ne_0$  plotted against the rescaled characteristic frequency  $\omega_g/\omega_0$ . Each point represents a different parent temperature  $T_p$ . The dashed line represents the relation  $Ne_0 \sim (\omega_g/\omega_0)^{-3}$ , see text for discussion. (b) Dimensionless vDOS prefactor  $A_g\omega_0^5$  plotted against the dimensionless characteristic frequency  $\omega_g/\omega_0$  of QLMs, see text for discussion.

## VI. SUMMARY AND OUTLOOK

In this work we present several manifestations of a phenomenon we have coined ‘thermo-mechanical inannealability’. We find that, under some forms of our sticky-sphere glasses’ interaction potential, a large number of micro- and macroelastic properties of glasses are seen to become largely indifferent to deeper supercooling of those glasses’ ancestral equilibrium states. We demonstrated this indifference in the shear modulus  $G$ , as well as in several quantifiers of the statistical-mechanical properties of soft, nonphononic quasilocalized modes, including their size, characteristic frequency, and density per frequency.

What is the degree of thermo-mechanical inannealability of common laboratory glasses? Experimental data (e.g. [15, 26, 49, 54, 55]) clearly indicates that macroelastic properties of metallic glasses can feature large susceptibilities to thermal annealing. In contrast, it was shown e.g. in [26] that the shear modulus of a  $\text{Ce}_{68}\text{Al}_{10}\text{Cu}_{20}\text{Fe}_2$  metallic glass changes only by about 2% after annealing it below  $T_g$  for 150 hours. Interestingly, in [26] that same glass was also shown to be very brittle, as were (thermo-mechanically inannealable) sticky-sphere computer glasses in [56] – using the same model employed here. More work is required in order to understand the extent to which the trends we have identified in simple computer glasses, as employed in this work, are relevant to laboratory glasses.

As mentioned in Sect. V A, here we employed conventional molecular dynamics simulations in order to supercool our parent configurations before casting them into glassy solids. Running-time constraints do not allow to reach very deep supercooling with these methods. It will be very interesting to observe whether the thermo-mechanical inannealability seen here persists in deeply annealed glasses made using the Swap Monte Carlo algorithm [16], and to examine how it may be affected by

polydispersity.

As mentioned above, here and in many other simulation work on different computer glasses (e.g. [18, 19]) it has been shown that  $K(T_p)$  is a decreasing function of  $T_p$ , while it appears to be uncommon to observe a decreasing bulk modulus with thermal annealing in laboratory glasses. We speculate that this is a consequence of considering constant volume annealing, as done here, which usually leads to a decreasing bulk modulus upon thermal annealing, or constant pressure annealing, as typically done in experiments, that leads to the increase of the bulk modulus upon thermal annealing. Future research should resolve whether particular details of interaction potentials can affect the sign of  $dK/dT_p$  under constant pressure annealing.

In this work and in the first paper of this series [35] we find that tuning the interaction potential can lead to effects that resemble those of annealing on elastic properties of glasses, as also pointed out by [56]. Future work should carefully resolve the similarities and differences between stabilization of glasses by thermal annealing, and stabilization of glasses by tailoring the form of interaction potentials.

Finally, our findings suggest the existence of intrinsically-brittle glasses, i.e. whose embedded defects (QLMs) are very stiff and rare, *independent* of those glasses’ formation history. We do not, however, find evidence for the existence of intrinsically-ductile glasses, that are both defect-rich *and* thermo-mechanically inannealable. Our results suggest instead that thermo-mechanical inannealability and intrinsic brittleness share a common origin, related to glass stickiness. We leave revealing that origin to future work.

## ACKNOWLEDGMENTS

We warmly thank Srikanth Sastry, Geert Kapteijns, David Richard, Corrado Rainone, and Eran Bouchbinder for fruitful discussions. We also thank David Richard for the Stillinger-Weber data used in Fig. 15. E. L. acknowledges support from the Netherlands Organisation for Scientific Research (NWO) (Vidi grant no. 680-47-554/3259). K. G. L. thankfully acknowledges the computer resources provided by the Laboratorio Nacional de Supercómputo del Sureste de México, CONACYT member of the national laboratories network. M. P. C. acknowledges support from the Singapore Ministry of Education Research Fund, (MOE2017-T2-1-066(S)). Part of this work was carried out on the Dutch national e-infrastructure with the support of SURF Cooperative.

### Appendix A: Definitions of observables

In this Appendix we provide precise definitions of the physical observables focused on in this study. We divide the observables to macroscopic and microscopic ones, in the next Subsections.

#### 1. Macroscopic observables

We start with athermal ( $T=0$ ) elastic moduli [57]; the shear modulus  $G$  is defined as

$$G \equiv \frac{1}{V} \frac{d^2 U}{d\gamma^2} = \frac{\frac{\partial^2 U}{\partial \gamma^2} - \frac{\partial^2 U}{\partial \gamma \partial \mathbf{x}} \cdot \mathcal{M}^{-1} \cdot \frac{\partial^2 U}{\partial \mathbf{x} \partial \gamma}}{V}, \quad (\text{A1})$$

where  $\mathbf{x}$  denotes particles' coordinates,  $\mathcal{M} \equiv \frac{\partial^2 U}{\partial \mathbf{x} \partial \mathbf{x}}$  is the Hessian matrix of the potential  $U$ , and  $\gamma$  is a shear-strain parameter that parameterizes the imposed affine simple shear (in the  $x$ - $y$  plane) transformation of coordinates  $\mathbf{x} \rightarrow \mathbf{H}(\gamma) \cdot \mathbf{x}$  with

$$\mathbf{H}(\gamma) = \begin{pmatrix} 1 & \gamma & 0 \\ 0 & 1 & 0 \\ 0 & 0 & 1 \end{pmatrix}. \quad (\text{A2})$$

The bulk modulus  $K$  is defined as

$$K \equiv -\frac{1}{\bar{d}} \frac{dp}{d\eta} = \frac{\frac{\partial^2 U}{\partial \eta^2} - \frac{\partial U}{\partial \eta} - \frac{\partial^2 U}{\partial \eta \partial \mathbf{x}} \cdot \mathcal{M}^{-1} \cdot \frac{\partial^2 U}{\partial \mathbf{x} \partial \eta}}{V \bar{d}}, \quad (\text{A3})$$

where  $\bar{d}$  is the dimension of space,  $p \equiv -\frac{1}{V \bar{d}} \frac{dU}{d\eta}$  is the pressure, and  $\eta$  is an expansive-strain parameter that parameterizes the imposed affine expansive transformation of coordinates  $\mathbf{x} \rightarrow \mathbf{H}(\eta) \cdot \mathbf{x}$  as

$$\mathbf{H}(\eta) = \begin{pmatrix} e^\eta & 0 & 0 \\ 0 & e^\eta & 0 \\ 0 & 0 & e^\eta \end{pmatrix}. \quad (\text{A4})$$

The Poisson's ratio  $\nu$  of a glass in 3D is defined as

$$\nu \equiv \frac{3K - 2G}{6K + 2G} = \frac{3 - 2G/K}{6 + 2G/K}. \quad (\text{A5})$$

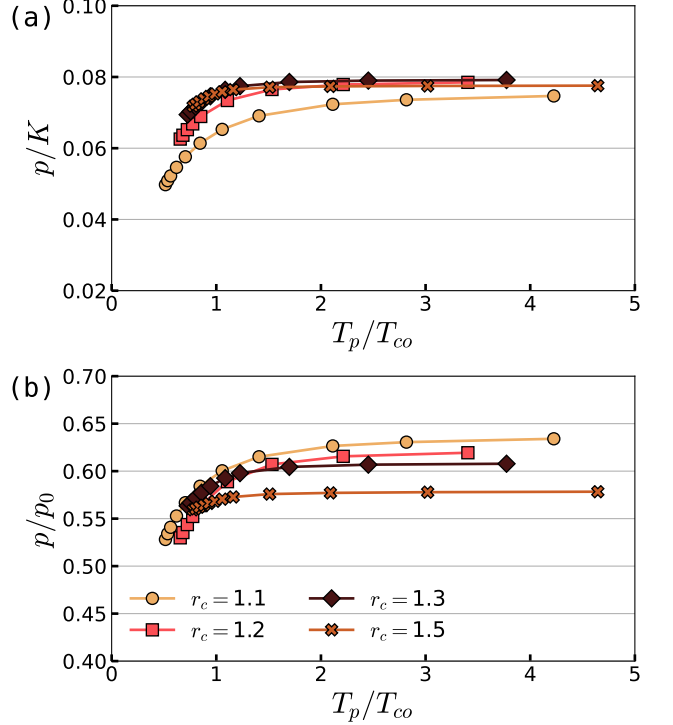


FIG. 12. We consider two dimensionless forms for our glasses' pressure:  $p/K$  and  $p/p_0$  (see text for  $p_0$ 's definition), both indicate only minor variations between our different  $r_c$  ensembles, see further details in Appendix. A 1.

In order to properly compare the pressure between different glasses, we consider here to dimensionless forms of the pressure. For the first one, we write the pressure as

$$p = \frac{1}{V \bar{d}} \sum_{f_{ij} > 0} f_{ij} r_{ij} - \frac{1}{V \bar{d}} \sum_{f_{ij} < 0} (-f_{ij}) r_{ij} \equiv p_+ - p_-. \quad (\text{A6})$$

The above decomposition of the pressure is used to define a characteristic scale  $p_0 \equiv p_+ + p_-$  with respect to which the pressure can be assessed. For the second dimensionless form of the pressure, we consider the ratio  $p/K$ , where  $K$  is the bulk modulus. The two forms of the dimensionless pressure are shown for our sticky sphere glasses in Fig. 12.

#### 2. Microscopic observables

The vibrational density of states (vDOS) is defined as

$$\mathcal{D}(\omega) = \frac{1}{N} \left\langle \sum_{\ell} \delta(\omega - \omega_{\ell}) \right\rangle \quad (\text{A7})$$

where  $\langle \bullet \rangle$  denotes an ensemble average, and  $\omega_\ell$  is the vibrational frequency associated with the vibrational mode  $\psi^{(\ell)}$  that together solve the eigenvalue equation

$$\mathcal{M} \cdot \psi^{(\ell)} = \omega_\ell^2 \psi^{(\ell)}. \quad (\text{A8})$$

The degree of localization of vibrational modes  $\psi$  is conventionally quantified using the participation ratio  $e$ , defined as

$$e \equiv \frac{(\sum_i \psi_i \cdot \psi_i)^2}{N \sum_i (\psi_i \cdot \psi_i)^2}, \quad (\text{A9})$$

where  $\psi_i$  denotes the  $d$ -dimensional vector of a mode's Cartesian components associated with the  $i$ th particle. One generally expects  $e \sim 1/N$  for localized modes, and  $e \sim 1$  for extended modes. We always find that  $e$  plateaus at low frequency, as shown for example in Fig. 13, and also in [27, 28, 34].

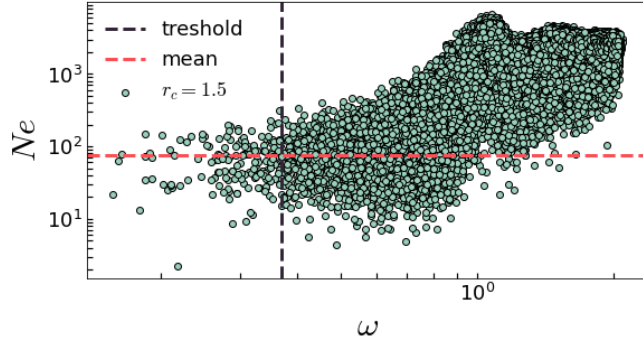


FIG. 13. Scatter plot of the scaled participation ratio  $Ne$  vs. frequency  $\omega$ , for our sticky-sphere glasses with  $r_c = 1.5$  and  $T_p/T_{co} \approx 3.0$ , see text for discussion.

To extract the low-frequency plateau of  $e$ , we set a threshold frequency — marked by the vertical dashed line in Fig. 13, for each glass ensemble, and take the mean over all data points whose frequencies are lower than the chosen threshold, represented in Fig. 13 by the horizontal dashed line. This estimation is in good agreement with the running average of  $Ne_0$  at the plateau.

### Appendix B: Glass potential energy per particle

In Fig. 3 of Sect. III we show the shifted and rescaled potential energy per particle  $u(T_p) \equiv U(T_p)/N$  of sticky sphere glasses, in addition to those of other popular glass models. For readers' reference, in Fig. 14 we present the raw potential energy data, and the interpolated energies  $u(T_{co})$  used in the definition of the onset temperature  $T_{on}$ , see details in Sect. III.

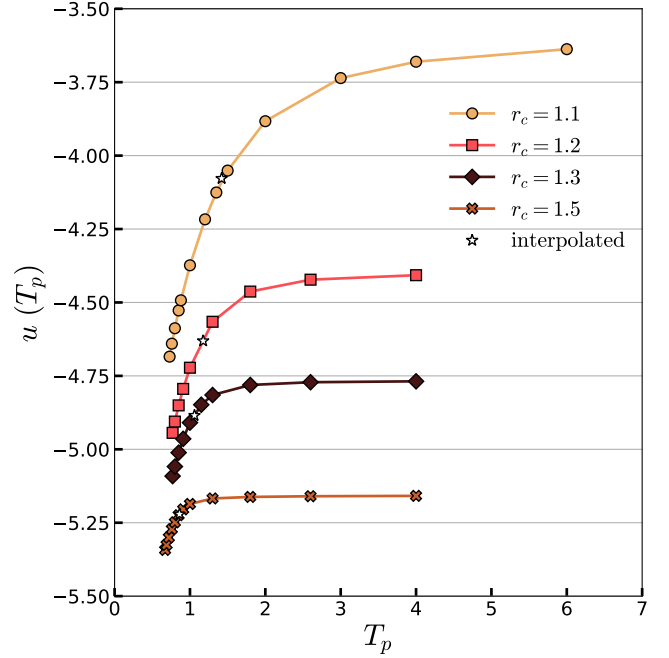


FIG. 14. Potential energy per particle, expressed in terms of *simulational* units, for all studied parent temperatures  $T_p$ , and different glass stickiness as obtained by tuning the interaction cutoff  $r_c$ . The empty stars represent the interpolated energies  $u(T_{co})$ , see discussion in Sect. III.

### Appendix C: Defining the crossover temperature via $T_p$ -dependent elastic moduli

In Sect. III we showed how the potential energy per particle  $u(T_p)$  of different glass models can be collapsed onto a master curve by a proper identification of, and rescaling by, the crossover temperatures  $T_{co}$  for each model system. The disadvantage of this approach is that it is not useful if only one function  $u(T_p)$  (for a single glass model) is available.

Here we offer an alternative definition, demonstrated in Fig. 15. It amounts to constructing a linear extrapolating of the low- $T_p$  quasilinear regime of the shear to bulk moduli ratio  $G/K$ , towards higher  $T_p$ 's. An example of this extrapolation is represented in Fig. 15 by the nearly-vertical dashed line. Our alternative definition of the crossover temperature  $T_{co}$  is given by the intersection of the extrapolated  $G/K$  with the high- $T_p$  limit  $G_\infty/K_\infty$ . In the inset of Fig. 15 we compare the crossover temperatures  $T_{co}$  defined via the two approaches, the one explained here and the one introduced in Sect. III, and find a very good agreement between the two across all models considered. We reiterate that details about the Kob-Andersen Binary Lennard-Jones (KABLJ) model, the Hertzian spheres glass, and the polydisperse inverse-power-law soft sphere glass (poly IPL) can be found in Refs. [38],[29], and [19], respectively.

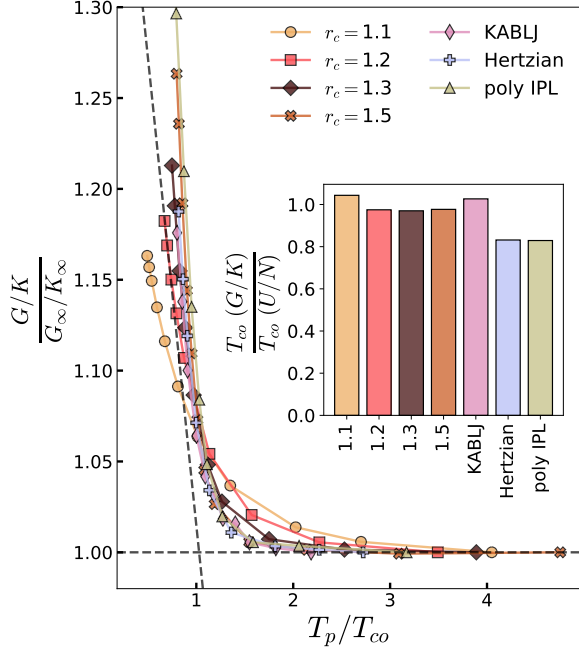


FIG. 15. Shear-to-Bulk moduli ratio  $G/K$ , rescaled by their high- $T_p$  limit  $G_\infty/K_\infty$ , and plotted against the rescaled parent temperature  $T_p/T_{co}$ . Here  $T_{co}$  is defined as the intersection of the linearly extrapolated  $G/K$  — marked for example by the nearly-vertical dashed line — with the high- $T_p$  limit. The inset compares between the crossover temperatures extracted as shown here, and those extracted by the  $u(T_p)$  collapse shown in Fig. 3 of the main text.

#### Appendix D: Extracting QLMs' characteristic frequency scale

In the previous paper [35] in this series, we extracted the characteristic frequency  $\omega_g$  of QLMs by (i) measuring the typical length  $\xi_g$  that characterizes the response of the glass to local force dipoles, and (ii) using the relation

$$\omega_g = 2\pi c_s / \xi_g, \quad (\text{D1})$$

established in [20], where  $c_s$  stands for the speed of shear waves. Since this scheme requires large system sizes (we used  $N \geq 250K$  in [35]), it is impractical once very long simulations are required in order to equilibrate states at very low parent temperatures. In Fig. 16 we show a good agreement between  $\omega_g$  extracted via the scheme employed in this work (cf. Sect. VB), and that extracted as explained in this Appendix.

#### Appendix E: Supercooled-liquid dynamics

In this Appendix we report the supercooled relaxational dynamics of our different glass forming models, defined by the pair interaction cutoff  $r_c$  as explained in Sect. II of the main text. We monitor the stress autocor-

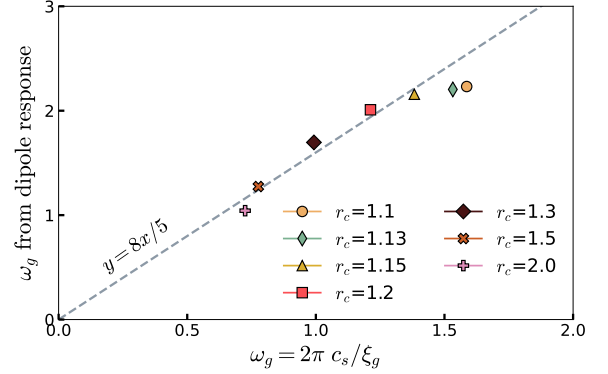


FIG. 16. Comparison of the estimation of  $\omega_g$  obtained as explained in Sect. VB, to that obtained in [35] by following the scheme explained in this Appendix, for all  $r_c$ -glass ensembles (we consider the highest- $T_p$ 's).

relation function  $c(t)$  defined as

$$c(t) = V \overline{\sigma(0)\sigma(t)} / T, \quad (\text{E1})$$

where  $\bar{\cdot}$  denotes a time average, and  $\sigma = V^{-1} \partial U / \partial \gamma$  with  $\gamma$  denoting a shear strain parameter as defined in Appendix A 1. Fig. 17 shows the stress correlations for different cutoffs  $r_c$ . We reiterate that a comprehensive study of the dynamical properties of our sticky sphere glasses was put forward in [42].

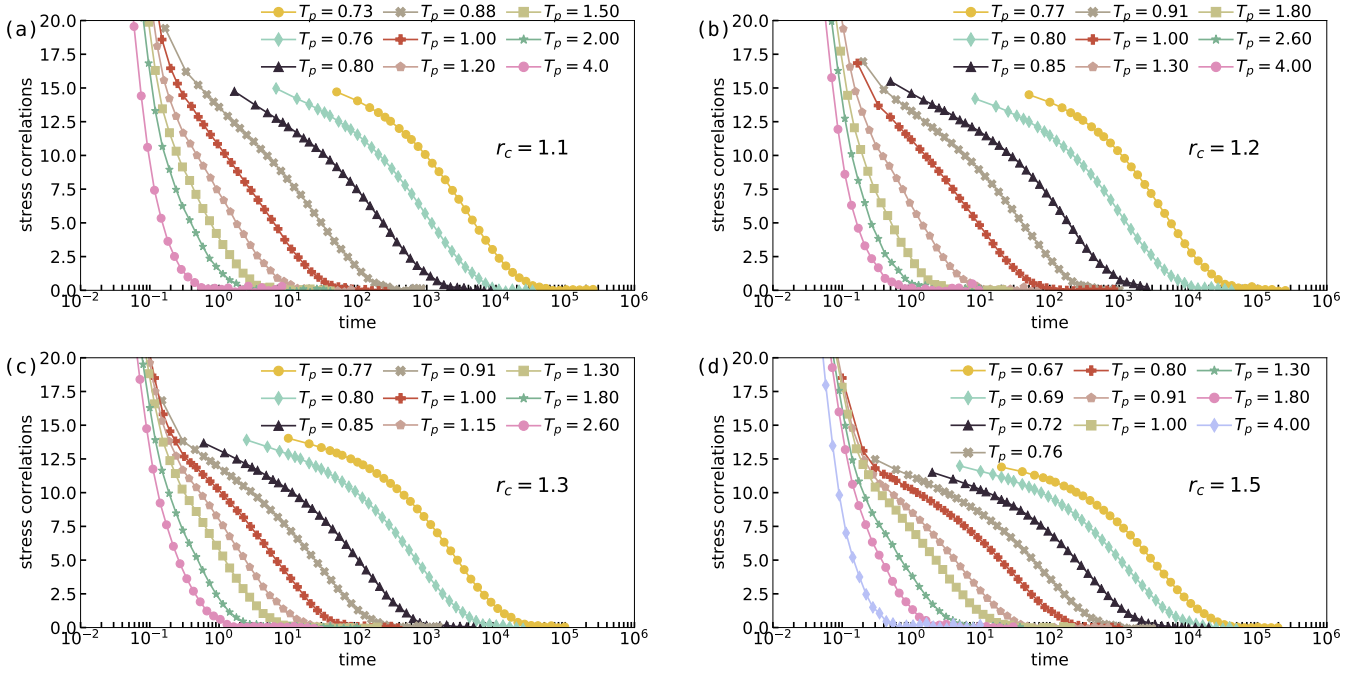


FIG. 17. Stress autocorrelation functions for our model glass formers with different pair interaction cutoffs  $r_c$ .

- [1] E. Bouchbinder and J. S. Langer, Nonequilibrium thermodynamics and glassy rheology, *Soft Matter* **9**, 8786 (2013).
- [2] M. L. Falk and J. S. Langer, Dynamics of viscoplastic deformation in amorphous solids, *Phys. Rev. E* **57**, 7192 (1998).
- [3] F. Varnik, L. Bocquet, and J.-L. Barrat, A study of the static yield stress in a binary lennard-jones glass, *J. Chem. Phys.* **120**, 2788 (2004).
- [4] C. A. Schuh, T. C. Hufnagel, and U. Ramamurty, Mechanical behavior of amorphous alloys, *Acta Materialia* **55**, 4067 (2007).
- [5] J. S. Harmon, M. D. Demetriou, W. L. Johnson, and M. Tao, Deformation of glass forming metallic liquids: Configurational changes and their relation to elastic softening, *Appl. Phys. Lett.* **90**, 131912 (2007).
- [6] W. H. Wang, The elastic properties, elastic models and elastic perspectives of metallic glasses, *Prog. Mater. Sci.* **57**, 487 (2012).
- [7] M. Vasoya, C. H. Rycroft, and E. Bouchbinder, Notch fracture toughness of glasses: Dependence on rate, age, and geometry, *Phys. Rev. Applied* **6**, 024008 (2016).
- [8] M. Ozawa, L. Berthier, G. Biroli, A. Rosso, and G. Tarjus, Random critical point separates brittle and ductile yielding transitions in amorphous materials, *Proc. Natl. Acad. Sci. U.S.A.* **115**, 6656 (2018).
- [9] M. Popović, T. W. J. de Geus, and M. Wyart, Elastoplastic description of sudden failure in athermal amorphous materials during quasistatic loading, *Phys. Rev. E* **98**, 040901 (2018).
- [10] G. Kapteijns, W. Ji, C. Brito, M. Wyart, and E. Lerner, Fast generation of ultrastable computer glasses by minimization of an augmented potential energy, *Phys. Rev. E* **99**, 012106 (2019).
- [11] P. Das, A. D. Parmar, and S. Sastry, Annealing glasses by cyclic shear deformation, *arXiv preprint arXiv:1805.12476* (2018).
- [12] Y. Shi and M. L. Falk, Strain localization and percolation of stable structure in amorphous solids, *Phys. Rev. Lett.* **95**, 095502 (2005).
- [13] S. Karmakar, E. Lerner, and I. Procaccia, Plasticity-induced anisotropy in amorphous solids: The bauschinger effect, *Phys. Rev. E* **82**, 026104 (2010).
- [14] S. Patinet, A. Barbot, M. Lerbinger, D. Vandembroucq, and A. Lemaître, Origin of the bauschinger effect in amorphous solids, *Phys. Rev. Lett.* **124**, 205503 (2020).
- [15] J. Ketkaew, W. Chen, H. Wang, A. Datye, M. Fan, G. Pereira, U. D. Schwarz, Z. Liu, R. Yamada, W. Dmowski, M. D. Shattuck, C. S. O'Hern, T. Egami, E. Bouchbinder, and J. Schroers, Mechanical glass transition revealed by the fracture toughness of metallic glasses, *Nat. Commun.* **9**, 3271 (2018).
- [16] A. Ninarello, L. Berthier, and D. Coslovich, Models and algorithms for the next generation of glass transition studies, *Phys. Rev. X* **7**, 021039 (2017).
- [17] A. D. S. Parmar, M. Ozawa, and L. Berthier, Ultrastable metallic glasses in silico, *Phys. Rev. Lett.* **125**, 085505 (2020).
- [18] L. Wang, A. Ninarello, P. Guan, L. Berthier, G. Szamel, and E. Flenner, Low-frequency vibrational modes of stable glasses, *Nat. Commun.* **10**, 26 (2019).
- [19] E. Lerner, Mechanical properties of simple computer glasses, *J. Non-Cryst. Solids* **522**, 119570 (2019).

- [20] C. Rainone, E. Bouchbinder, and E. Lerner, Pinching a glass reveals key properties of its soft spots, *Proc. Natl. Acad. Sci. U.S.A.* **117**, 5228 (2020).
- [21] E. Lerner and E. Bouchbinder, A characteristic energy scale in glasses, *J. Chem. Phys.* **148**, 214502 (2018).
- [22] C. Rainone, E. Bouchbinder, and E. Lerner, Statistical mechanics of local force dipole responses in computer glasses, *J. Chem. Phys.* **152**, 194503 (2020).
- [23] G. Kapteijns, D. Richard, E. Bouchbinder, and E. Lerner, Elastic moduli fluctuations predict wave attenuation rates in glasses, *arXiv preprint arXiv:2008.08337* (2020).
- [24] H. R. Schober and C. Oligschleger, Low-frequency vibrations in a model glass, *Phys. Rev. B* **53**, 11469 (1996).
- [25] E. Lerner, G. Düring, and E. Bouchbinder, Statistics and properties of low-frequency vibrational modes in structural glasses, *Phys. Rev. Lett.* **117**, 035501 (2016).
- [26] B. Sun, Y. Hu, D. Wang, Z. Zhu, P. Wen, W. Wang, C. Liu, and Y. Yang, Correlation between local elastic heterogeneities and overall elastic properties in metallic glasses, *Acta Mater.* **121**, 266 (2016).
- [27] E. Lerner and E. Bouchbinder, Effect of instantaneous and continuous quenches on the density of vibrational modes in model glasses, *Phys. Rev. E* **96**, 020104 (2017).
- [28] E. Lerner and E. Bouchbinder, Frustration-induced internal stresses are responsible for quasilocalized modes in structural glasses, *Phys. Rev. E* **97**, 032140 (2018).
- [29] D. Richard, K. González-López, G. Kapteijns, R. Pater, T. Vaknin, E. Bouchbinder, and E. Lerner, Universality of the nonphononic vibrational spectrum across different classes of computer glasses, *Phys. Rev. Lett.* **125**, 085502 (2020).
- [30] A. Moriel, G. Kapteijns, C. Rainone, J. Zylberg, E. Lerner, and E. Bouchbinder, Wave attenuation in glasses: Rayleigh and generalized-rayleigh scattering scaling, *J. Chem. Phys.* **151**, 104503 (2019).
- [31] E. Lerner, Micromechanics of nonlinear plastic modes, *Phys. Rev. E* **93**, 053004 (2016).
- [32] C. Oligschleger and H. R. Schober, Collective jumps in a soft-sphere glass, *Phys. Rev. B* **59**, 811 (1999).
- [33] A. Widmer-Cooper, H. Perry, P. Harrowell, and D. R. Reichman, Irreversible reorganization in a supercooled liquid originates from localized soft modes, *Nature Phys.* **4**, 711 (2008).
- [34] L. Gartner and E. Lerner, Nonlinear modes disentangle glassy and Goldstone modes in structural glasses, *SciPost Phys.* **1**, 016 (2016).
- [35] K. González-López, Y. Zheng, M. Shivam, M. Pica Ciamarra, and E. Lerner, Mechanical disorder of sticky-sphere glasses. i. effect of attractive interactions, *arXiv preprint arXiv:2008.12011* (2020).
- [36] S. Karmakar, E. Lerner, I. Procaccia, and J. Zylberg, Effect of the interparticle potential on the yield stress of amorphous solids, *Phys. Rev. E* **83**, 046106 (2011).
- [37] M. Goldstein, Viscous liquids and the glass transition: A potential energy barrier picture, *J. Chem. Phys.* **51**, 3728 (1969).
- [38] W. Kob and H. C. Andersen, Testing mode-coupling theory for a supercooled binary lennard-jones mixture i: The van hove correlation function, *Phys. Rev. E* **51**, 4626 (1995).
- [39] J. C. Dyre, Colloquium, *Rev. Mod. Phys.* **78**, 953 (2006).
- [40] M. Wyart, Correlations between vibrational entropy and dynamics in liquids, *Phys. Rev. Lett.* **104**, 095901 (2010).
- [41] M. Wyart and M. E. Cates, Does a growing static length scale control the glass transition?, *Phys. Rev. Lett.* **119**, 195501 (2017).
- [42] J. Chattoraj and M. P. Ciamarra, Role of attractive forces in the relaxation dynamics of supercooled liquids, *Phys. Rev. Lett.* **124**, 028001 (2020).
- [43] S. Sastry, P. G. Debenedetti, and F. H. Stillinger, Signatures of distinct dynamical regimes in the energy landscape of a glass-forming liquid, *Nature* **393**, 554 (1998).
- [44] S. Sastry, P. G. Debenedetti, F. H. Stillinger, T. B. Schrder, J. C. Dyre, and S. C. Glotzer, Potential energy landscape signatures of slow dynamics in glass forming liquids, *Physica (Amsterdam)* **270A**, 301 (1999).
- [45] S. Sastry, Onset of slow dynamics in supercooled liquid silicon, *Physica A Stat. Mech. Appl.* **315**, 267 (2002), slow Dynamical Processes in Nature.
- [46] Y. Brumer and D. R. Reichman, Mean-field theory, mode-coupling theory, and the onset temperature in supercooled liquids, *Phys. Rev. E* **69**, 041202 (2004).
- [47] A. Banerjee, M. K. Nandi, S. Sastry, and S. Maitra Bhattacharyya, Determination of onset temperature from the entropy for fragile to strong liquids, *J. Chem. Phys.* **147**, 024504 (2017).
- [48] We found  $T_{co} = 0.535, 0.00265$  and  $0.76$  in the respective simulation units of the Kob-Anderson Binary Lennard Jones [38], the Hertzian spheres [29], and the polydisperse inverse-power-law spheres [19].
- [49] W. H. Wang, The elastic properties, elastic models and elastic perspectives of metallic glasses, *Prog. Mater. Sci.* **57**, 487 (2012).
- [50] U. Buchenau, Y. M. Galperin, V. L. Gurevich, and H. R. Schober, Anharmonic potentials and vibrational localization in glasses, *Phys. Rev. B* **43**, 5039 (1991).
- [51] V. L. Gurevich, D. A. Parshin, and H. R. Schober, Anharmonicity, vibrational instability, and the boson peak in glasses, *Phys. Rev. B* **67**, 094203 (2003).
- [52] G. Kapteijns, E. Bouchbinder, and E. Lerner, Universal nonphononic density of states in 2d, 3d, and 4d glasses, *Phys. Rev. Lett.* **121**, 055501 (2018).
- [53] In addition to variations in QLMs' core sizes, changes in the distribution of displacements within QLMs' cores could affect the participation ratio as well.
- [54] W. H. Wang, R. J. Wang, W. T. Yang, B. C. Wei, P. Wen, D. Q. Zhao, and M. X. Pan, Stability of zrticunibe bulk metallic glass upon isothermal annealing near the glass transition temperature, *J. Mater. Res.* **17**, 13851389 (2002).
- [55] L. Huo, J. Zeng, W. Wang, C. Liu, and Y. Yang, The dependence of shear modulus on dynamic relaxation and evolution of local structural heterogeneity in a metallic glass, *Acta Materialia* **61**, 4329 (2013).
- [56] O. Dauchot, S. Karmakar, I. Procaccia, and J. Zylberg, Athermal brittle-to-ductile transition in amorphous solids, *Phys. Rev. E* **84**, 046105 (2011).
- [57] J. F. Lutsko, Generalized expressions for the calculation of elastic constants by computer simulation, *J. Appl. Phys.* **65**, 2991 (1989).