

Limits of Lateral Expansion in Two-Dimensional Materials with Line Defects

Pekka Koskinen*

Nanoscience Center, Department of Physics, University of Jyväskylä.

(Dated: January 7, 2022)

The flexibility of two-dimensional (2D) materials enables static and dynamic ripples that are known to cause lateral contraction, shrinking of the material boundary. However, the limits of 2D materials' *lateral expansion* are unknown. Therefore, here we discuss the limits of intrinsic lateral expansion of 2D materials that are modified by compressive line defects. Using thin sheet elasticity theory and sequential multiscale modeling, we find that the lateral expansion is inevitably limited by the onset of rippling. The maximum lateral expansion $\chi_{\max} \approx 2.1 \cdot t^2 \sigma_d$, governed by the elastic thickness t and the defect density σ_d , remains typically well below one percent. In addition to providing insight to the limits of 2D materials' mechanical limits and applications, the results highlight the potential of line defects in strain engineering, since for graphene they suggest giant pseudomagnetic fields that can exceed 1000 T.

The discoveries of two-dimensional (2D) materials were followed by reports of their subtle mechanical properties [1]. They are never fully flat, since their elastic thinness make them susceptible for stabilizing out-of-plane rippling [2–4]. Rippling also implies in-plane softening and considerable out-of-plane stiffening [5–7]. However, materials' high in-plane stiffness keeps their surface area unchanged, which implies lateral contraction, shrinking of the material boundary [8]. This effect is best known from the negative thermal expansion coefficient of graphene [9–11].

Rippling and lateral contraction are relevant for several reasons. Ripples affect substrate adhesion (and vice versa) as well as in-plane and out-of-plane deformations [12–17]. They can be created by point defects [18], adsorbates [19], grain boundaries [20, 21], or line defects [6], also without excessive hampering of material's mechanical and electronic properties [22]. Contraction influences the functioning of nanoscale devices such as resonators and facilitates strain engineering to control both mechanical and electronic properties [4, 23]. However, despite the prominence of rippling and contraction in practical applications and the abundance of related literature, one fundamental question remains open: *what are the limits of intrinsic lateral expansion for 2D materials?*

An attractive strategy to address this question is to consider 2D materials with compressive line defects. The line defects can act as tiny stitches that can induce local stretched areas that—so the argument goes—cumulate into global lateral expansion [6]. Representing various physical origins such as dislocations [24], adsorbate arrays [19, 25, 26], stacking variations [27], heterostructure interfaces [28], or grain boundaries [29, 30], line defects allow creating local compressive stress at relatively low defect density. While some line defects are created during material synthesis, others can be created afterwards by chemical means or even by direct laser irradiation [31, 32].

In this Letter I use thin sheet elasticity theory and sequential multiscale modeling to investigate the lateral expansion limits of 2D materials with compressive line defects. Theory permits analytical models with simple expressions for ripple properties and lateral expansion. It turns out that lateral expansion and rippling cannot coexist; rippling destroys expansion effectively.

To model the defected 2D materials, I invoke the thin sheet elasticity theory [39], because it has proven effective and reliable even for atomic-scale deformations [1, 33, 40–46]. Theory characterizes membranes by bending modulus k_b , Poisson ratio ν , and 2D Young's modulus k_s . Membrane's intrinsic length scale is given by the elastic thickness

$$t = \sqrt{12k_b/M}, \quad (1)$$

where $M = k_s/(1-\nu^2)$ is the longitudinal modulus. Elastic thickness equals the physical thickness of the 2D material when viewed as a slab of isotropic elastic membrane. Table I shows parameters for selected 2D materials [33–38].

The theory can be augmented to include compressive line defects, modeling them as stripes of width a , length l , and a pre-strain ε_0 that implies the equilibrium length $l(1 + \varepsilon_0)$ (Fig. 1a) [6]. The magnitude of a is around 2–3 Å as it arises from the atomic structure of the defect [6]. The parameter

$$S = a\varepsilon_0 \quad (2)$$

characterizes the *strength* of the line defect. For small deformations (strains $\ll \varepsilon_0$) the line defect corresponds to one-dimensional line stress $\tau = MS$. The strength

TABLE I. Elastic parameters for selected 2D materials.

Material	k_s (eV/Å ²)	k_b (eV)	ν	t (Å)
Graphene [33]	21	1.5	0.15	0.93
Bilayer graphene[34]	42	180	0.15	7.2
MoS ₂ [35, 36]	8	12	0.3	4.2
BN [33]	17	1.3	0.2	0.96
Silicene [37, 38]	3.8	0.4	0.4	1.1

* pekka.j.koskinen@jyu.fi

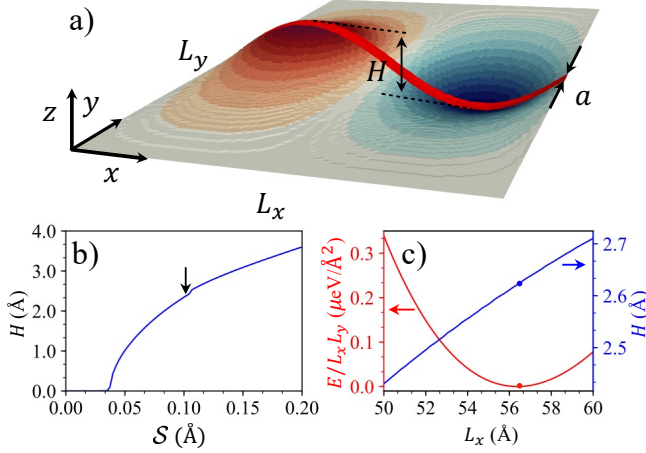


FIG. 1. Rippling of 5 nm \times 10 nm 2D membrane ($t = 1.0$ Å) by an infinitely long compressive line defect. a) One ripple wavelength from a line defect with $S = 0.1$ Å ($a = 2.5$ Å and $\varepsilon_0 = 4$ %). Vertical dimension is scaled by a factor of five and the width of the line defect is exaggerated. b) Ripple height H as a function of the line defect strength S . The membrane buckles at $S = 0.04$ Å; the arrow points the geometry in panel a. c) Surface energy density (left scale) and ripple height (right scale) as a function of ripple wavelength $\lambda = L_x$ for $S = 0.1$ Å.

S is unique for given 2D material and line defect, but here I treat it as a continuous parameter. I ignore tensile pre-strain ($\varepsilon_0 < 0$), because it cannot induce lateral expansion in any situation. Based on earlier atomic simulations, reasonable compressive pre-strains lie in the range $\varepsilon_0 \lesssim 20$ % [6].

The theory was then harnessed for numerical simulations of defected membranes in an $L_x \times L_y$ periodic rectangular cell. Membrane was discretized to an $N_x \times N_y$ grid and the optimum morphology was solved numerically by minimizing the total elastic energy; see Supplemental Material (SM) for details [47]. Materials of different elastic thicknesses $t = 1.0 \dots 10$ Å were simulated by adopting a fixed Poisson ratio ($\nu = 0.15$) and longitudinal modulus ($M = 21.5$ eV/Å²) while varying k_b according to Eq. (1). Line defect strengths S were adjusted by choosing the width equal to a typical lattice constant $a = 2.5$ Å and varying ε_0 . Since the main parameters are t and S , the above choices do not restrict the general validity of the results. In the numerical implementation, because the atomic scale is much smaller than the grid spacing ($a \ll L_x/N_x$), the line defects were introduced via a sequential multiscale model (SM) [47].

To construct a comprehensive understanding of the effect of line defects, I start by discussing isolated infinite and finite line defects before analyzing experimentally relevant random line defect networks.

Consider a 5 nm \times 10 nm membrane with $t = 1.0$ Å and an infinitely long ($l = L_x$) line defect along x -axis (Fig. 1a). The membrane is initially planar, but buckles to a rippled conformation upon increasing line defect

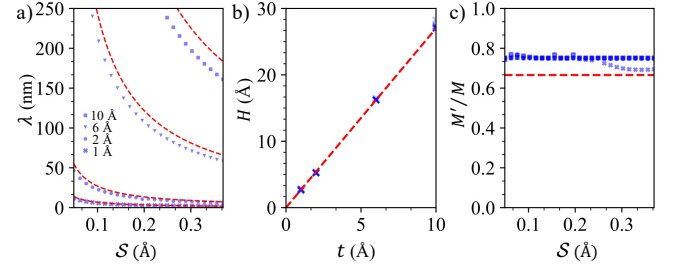


FIG. 2. Ripple trends with infinite line defects. a) Optimum ripple wavelength as a function of line defect strength for different t . b) Ripple height as a function of elastic thickness. c) Longitudinal constant M' of the entire simulation cell as a function of line defect strength. All panels show both numerical simulations (symbols) and analytical estimates [dashed lines from Eq. (4) for λ , Eq. (5) for H and Eq. (S14) for M']. $L_x = \lambda$ and $L_y = 1.5 \cdot \lambda$ in all panels.

strength from zero to $S = 0.04$ Å (Figs 1 a and b). The ripple forms because it releases the compressive stress of the line defect. Further increase in S leads to monotonous increase in ripple height. The ripple height profile can be approximated by the sine wave

$$z(x, y) = \frac{1}{2}H \exp(-y^2/2\sigma^2) \sin(2\pi x/\lambda), \quad (3)$$

where H is the peak-to-peak height, λ is the wavelength, and σ is a measure for the lateral width of the ripple.

The above choice of $L_y = 10$ nm was irrelevant because the ripple decays exponentially in y -direction. However, the choice of L_x must be investigated in detail, as it directly determines the ripple wavelength. Fixing $S = 0.1$ Å and increasing L_x leads to monotonously increasing ripple height and a minimum of the surface energy density $E/(L_x L_y)$ at $L_x = 56.3$ Å with $H = 2.62$ Å (Fig. 1c). This minimum implies that the ripple wavelength in an extended system is $\lambda = 56.3$ Å.

The rippling with line defects can be investigated also analytically. As derived in SM, adopting the ripple profile (3) leads to the estimates for the optimum wavelength as

$$\lambda = 6.8 \cdot t^2/S, \quad (4)$$

for the ripple height as,

$$H = 2.7 \cdot t \quad (5)$$

and for the ripple width as $\sigma \approx \lambda/5$ [47]. The estimates suggest that wavelengths increase for elastically thicker membranes and weaker line defects, which is plausible when viewed in terms of energy; shorter ripples require more energy, which is available in stronger line defects. Unexpectedly, however, the ripple height H depends *only* on elastic thickness and is independent of the properties of the line defect. This implies that ripples would form even with very weak line defects—although with very long wavelengths. In addition, the analytical model provides estimates for maximal slopes $\max(|dz/dx|) = 1.2 \cdot S/t$, curvatures $\max(C_{xx}) = S^2/t^3$,

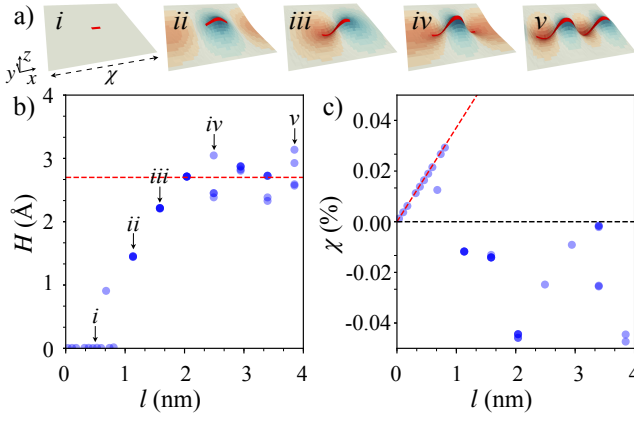


FIG. 3. Lateral uniaxial expansion of $10 \text{ nm} \times 6.6 \text{ nm}$ membrane with $t = 1.0 \text{ Å}$ for line defects with $\mathcal{S} = 0.25 \text{ Å}$ and finite length l . a) Development of ripple morphology with increasing l . The vertical dimension is scaled by a factor of five (see panel b for the color scale). b) Ripple height as a function of l . The arrows point at geometries in panel a. The red dashed line shows the ripple height estimate from Eq. (5) for infinitely long defects. c) Lateral expansion of the membrane in x -direction. The red dashed line is the estimate from Eq. (6). Fluctuations for given l are due to sampling of random initial guesses.

and strains $\max(\varepsilon_{xx}) = 0.4 \cdot (\mathcal{S}/t)^2$ (SM) [47]. For graphene, the strain field implies pseudomagnetic fields equal to $5 \cdot 10^4 \cdot \mathcal{S}^3 \text{ Å}^{-3} \text{ T}$ (SM) [47–50]. For example, graphene with $\mathcal{S} = 0.3 \text{ Å}$ suggests maximal slopes 0.36, curvatures 0.27 nm^{-1} , local strains 3 %, and pseudomagnetic field that exceeds 1000 T.

The analytical results are confirmed by systematic numerical simulations with $t = 1 \dots 10 \text{ Å}$ and $\mathcal{S} = 0 \dots 0.37 \text{ Å}$. As Eqs. (4) and (5) predict, ripple wavelengths are inversely proportional to \mathcal{S} and quadratically proportional to t (Fig. 2a), while ripple amplitude is directly proportional to the elastic thickness, independent of \mathcal{S} (Fig. 2b).

This \mathcal{S} -independence of H brings about a curious effect for lateral elastic properties. The longitudinal modulus M' of the entire simulation cell, which accounts also for rippling, becomes entirely constant—independent of either t or \mathcal{S} (Fig. 2c). Governing the energy curvature upon straining L_x , the longitudinal modulus depends on the width of the simulation cell, which here is $L_y = 1.5 \cdot L_x$. The constancy of M' can be understood as follows: on one hand larger t increases rippling height [Eq. (5)] and thereby tends to decrease M' , but on the other hand larger t increases bending stiffness and thereby tends to increase M' . Combined, these two tendencies cancel and M' becomes approximately constant. An analytical calculation gives the estimate $M'/M = (1 - 0.5 \cdot \lambda/L_y)$ which becomes 0.67 for current parameters (Fig. 2c; SM) [47].

Infinitely long line defects with optimum-wavelength ripples imply that the stress in x -direction vanishes. Any residual stress would lead to strain that changes the wave-

length, creating a contradiction with the presumption of an optimum wavelength. This notion implies an intermediate result: infinitely long ($\text{length} \gg \lambda$) line defects *cannot* induce lateral expansion. But what about finite line defects?

To address this question, consider line defects whose lengths l are around the optimal wavelength, $l \lesssim \lambda$. Let us fix $\mathcal{S} = 0.25 \text{ Å}$ with $t = 1.0 \text{ Å}$ and gradually increase the length l . Initially, at small l the membrane remains flat, until at $l \approx 0.7 \text{ Å}$ it buckles to form a single bump (Fig. 3a). Simulations contain fluctuations due to random initial guesses. Analytical model similar to the one of infinite line defects gives the scaling $l_b = 2.1 \cdot t^2/\mathcal{S} \approx 0.8 \text{ Å}$ for the buckling limit, in fair agreement with numerical simulations (SM) [47]. After buckling, further lengthening leads to increased ripple height and development of alternating up-and-down bumps that gradually resemble the optimum ripple of the $l \gg \lambda$ limit (Fig. 3a).

Yet, unlike infinite line defects, finite line defects *can* induce lateral expansion. The expansion is defined as $\chi = (L_x - L_x^0)/L_x^0$, which is obtained by minimizing energy with respect to cell length L_x for given initial length L_x^0 . As the main observation, the membrane expands steadily upon increasing l until it buckles (Fig. 3c). The expansion is accurately described by the heuristic model

$$\chi = \mathcal{S}l/L_x L_y. \quad (6)$$

The model means that the hidden area of the line defect ($a \cdot l\varepsilon_0 = l\mathcal{S}$) proportionally increases the surface area of the membrane ($L_x L_y$). With $l > l_b$ the membrane ripples and loses its capacity to sustain the compressive stress, rendering the expansion unpredictable.

These results provide sufficient insight to proceed to realistic random line defect networks [51]. I considered a $100 \text{ nm} \times 100 \text{ nm}$ membrane with $n = 25$ and 50 randomly placed and oriented line defects of various lengths (Fig. 4a). The corresponding densities ($0.25 \cdot 10^{12} \text{ cm}^{-2}$ and $0.5 \cdot 10^{12} \text{ cm}^{-2}$) are experimentally relevant and large enough for meaningful statistics but small enough to avoid excessive interaction between the line defects [32]. The length distribution was either even ($l_i = l_{\text{avg}}$) or linear [$l_i = l_{\text{avg}} \cdot 2i/(n+1)$], where $i = 1, 2, \dots, n$ and l_{avg} is the average length (Fig. 4a). Such distributions can be justified by previous models [51].

For a defect network with even length distribution, the membrane expands laterally upon increasing l_{avg} until the buckling threshold $l_{\text{avg}} > l_b$ (Fig. 4b). After buckling the membrane ripples to a height that does not change much upon increasing l_{avg} further. At the full 100 nm scale the ripple height is $\sim 10 \text{ Å}$ but at the local $\sim \lambda$ scale it is $\sim 5 \text{ Å}$, following Eq. (5). For linear distribution the behavior is similar, only the transition to rippled membrane is less sudden. The gradual change occurs because individual line defects buckle at different l_{avg} . However, already the initial buckling of the longest defects ($l_{\text{max}} = 2l_{\text{avg}} > l_b$) effectively eradicates the planar stress and destroys the lateral expansion.

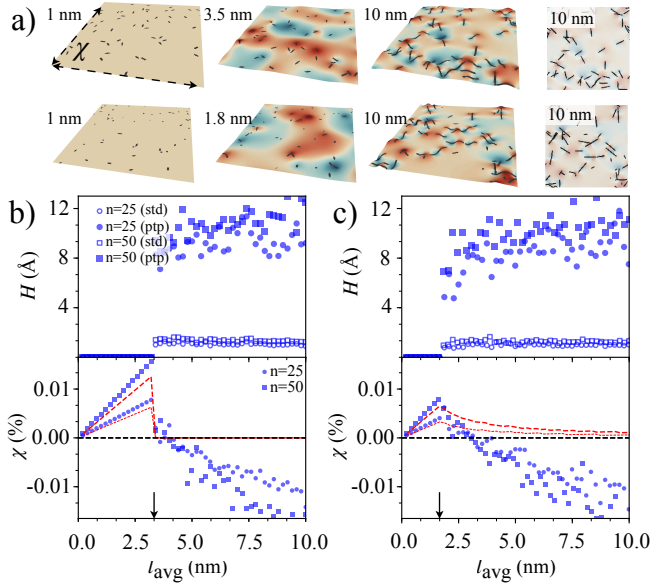


FIG. 4. Lateral biaxial expansion of $100 \text{ nm} \times 100 \text{ nm}$ membranes ($t = 2.0 \text{ Å}$) filled by networks of line defects with $S = 0.25 \text{ Å}$. a) Ripple morphology snapshots with 50 line defects. The networks have even (upper) and linear (lower) length distributions and increasing mean length (shown above). For clarity, the figures on the right show the networks with top views. b) Ripple peak-to-peak (ptp) and standard deviation (std) heights (upper panel) and biaxial strain (lower panel) as a function of mean defect length for $n = 25$ and $n = 50$ line defects with even length distribution. The red dashed line is the strain estimate from Eq. (7). c) Same as panel b for linear length distribution. Arrows point to mean lengths corresponding to the initial buckling of the longest line defects [Eq. (S22)]; for even distribution $l_{\text{max}} = l_{\text{avg}}$ and for linear distribution $l_{\text{max}} = 2l_{\text{avg}}$.

The lateral expansion is described accurately for both distributions by the generalization of Eq. (6),

$$\chi = S l_{\text{tot}}(l < l_b) / L_x L_y, \quad (7)$$

where $l_{\text{tot}}(l < l_b)$ is the cumulative length of all line defects below the buckling length l_b (Figs 4b and 4c). However, the membrane can sustain the lateral stress only as far as all defects remain below the buckling limit. After buckling the expansion becomes unpredictable. Ultimately, far beyond the buckling limit, the rippling strengthens and the membrane predominantly contracts [52].

Thus, 2D materials can expand laterally only when line

defects remain below the buckling limit of Eq. (S22). The maximum expansion is reached when all defects have the maximum length l_b and it equals

$$\chi_{\text{max}} \approx 2.1 \cdot t^2 \sigma_d, \quad (8)$$

where σ_d is the defect density. For instance, for $t = 1 \text{ Å}$ and $\sigma_d = 10^{12} \text{ cm}^{-2}$ the maximum expansion is 0.021 %. A reasonable estimate for a optimal defect density can be obtained by assuming that one line defect occupies a minimum area of $\sim (2l_b)^2$. This assumption yields the theoretical maximum for the strain as $\chi_{\text{max}} \approx S^2/8t^2$. For graphene ($t = 1.0 \text{ Å}$) and $S = 0.3 \text{ Å}$ this implies $\chi_{\text{max}} \approx 1 \%$.

Finally, I discuss briefly the role of substrates, which were excluded from the simulations. The transition from flat to rippled membranes reduces the energy by $0.13 \cdot M S^3/t^2$ per unit length of an infinite line defect (SM) [47]. Assuming that the defects have an effective width of $\lambda/2$, this translates into surface energy density of $0.04 \cdot M(S/t)^4$. For $M \sim 20 \text{ eV/Å}^2$, $t = 1.0 \text{ Å}$ and $S = 0.35 \text{ Å}$ the energy density becomes $\sim 10 \text{ meV/Å}^2$ —and competes with a typical strength of van der Waals adhesion [53–55]. Moreover, substrates themselves can be used for defect and strain engineering [56]. In short, a very strong adhesion can dominate membrane mechanics completely and effectively prevent both rippling and sliding. A very weak adhesion can allow for both rippling (desorption) and sliding, so that the rippling and expansion remains governed by membrane’s intrinsic dynamics. However, an intermediate adhesion can suppress rippling but still allow sliding. For such an adhesion the rippling instability would not limit the maximal intrinsic expansion anymore; the expansion would still be given by Eq. (6), but its upper limit would be given by maximum practical defect density.

To conclude, the onset of rippling dictates the limits of the lateral expansion of 2D materials. The theoretical maximum for the lateral expansion of the thinnest ($t = 1 \text{ Å}$) materials is around 1 %, local strains being far greater. To diminish the effect of substrates, the expansion would be best measured experimentally from suspended 2D material samples or from customized 3D blisters of 2D materials, such as demonstrated for graphene by optical forging [7]. The simulations and analytical models presented here provide a comprehensive picture of the mechanical behavior of 2D materials with line defects and reveal new theoretical limits to open new avenues and further advance the design and strain engineering of 2D materials.

[1] D. Akinwande, C. J. Brennan, J. S. Bunch, P. Egberts, J. R. Felts, H. Gao, R. Huang, J. S. Kim, T. Li, Y. Li, K. M. Liechti, N. Lu, H. S. Park, E. J. Reed, P. Wang, B. I. Yakobson, T. Zhang, Y. W. Zhang, Y. Zhou, and Y. Zhu, A review on mechanics and mechanical prop-

erties of 2D materials, Graphene and beyond, Extreme Mechanics Letters **13**, 42 (2017).
[2] J. C. Meyer, A. K. Geim, M. I. Katsnelson, K. S. Novoselov, T. J. Booth, and S. Roth, The structure of suspended graphene sheets, Nature **446**, 60 (2007).

- [3] C. H. Lui, L. Liu, K. F. Mak, G. W. Flynn, and T. F. Heinz, Ultraflat graphene, *Nature* **462**, 339 (2009).
- [4] S. Deng and V. Berry, Wrinkled, rippled and crumpled graphene: An overview of formation mechanism, electronic properties, and applications, *Materials Today* **19**, 197 (2016).
- [5] M. K. Blees, A. W. Barnard, P. a. Rose, S. P. Roberts, K. L. McGill, P. Y. Huang, A. R. Ruyack, J. W. Kevek, B. Kobrin, D. a. Muller, and P. L. McEuen, Graphene kirigami, *Nature* **524**, 204 (2015).
- [6] T. Kähärä and P. Koskinen, Rippling of two-dimensional materials by line defects, *Phys. Rev. B* **075433**, 075433 (2020).
- [7] V.-M. Hiltunen, P. Koskinen, K. K. Mentel, J. Manninen, P. Myllyperkiö, M. Pettersson, and A. Johansson, Ultrastiff graphene, *2D Materials and Applications* **5**, 49 (2021).
- [8] R. J. Nicholl, N. V. Lavrik, I. Vlassiuk, B. R. Srijanto, and K. I. Bolotin, Hidden Area and Mechanical Nonlinearities in Freestanding Graphene, *Physical Review Letters* **118**, 266101 (2017).
- [9] M. Pozzo, D. Alfe, P. Lacovig, P. Hofmann, S. Lizzit, and A. Baraldi, Thermal expansion of supported and freestanding graphene: lattice constant versus interatomic distance, *Phys. Rev. Lett.* **106**, 135501 (2011).
- [10] A. A. Balandin, Thermal properties of graphene and nanostructured carbon materials, *Nature Mat.* **10**, 569 (2011).
- [11] D. Yoon, Y.-W. Son, and H. Cheong, Negative thermal expansion coefficient of graphene measured by Raman spectroscopy, *Nano Lett.* **11**, 3227 (2011).
- [12] T. Paronyan, E. Pigos, and G. Chen, The Formation of Ripples in Graphene as a Result of Interfacial Instabilities, *ACS nano*, 9619 (2011).
- [13] C. D. Reddy, Y.-W. Zhang, and V. B. Shenoy, Influence of substrate on edge rippling in graphene sheets, *Modelling and Simulation in Materials Science and Engineering* **19**, 054007 (2011).
- [14] L. Tapasztó, T. Dumitrică, S. J. Kim, P. Nemes-Incze, C. Hwang, and L. P. Biró, Breakdown of continuum mechanics for nanometre-wavelength rippling of graphene, *Nature Physics* **8**, 739 (2012).
- [15] P. Koskinen, Graphene cardboard: From ripples to tunable metamaterial, *Appl. Phys. Lett.* **104**, 101902 (2014).
- [16] P. Lambin, Elastic Properties and Stability of Physisorbed Graphene, *Applied Sciences* **4**, 282 (2014).
- [17] P. Koskinen, K. Karppinen, P. Myllyperkiö, V. M. Hiltunen, A. Johansson, and M. Pettersson, Optically Forged Diffraction-Unlimited Ripples in Graphene, *Journal of Physical Chemistry Letters* **9**, 6179 (2018).
- [18] T. Zhang, X. Li, and H. Gao, Defects controlled wrinkling and topological design in graphene, *Journal of the Mechanics and Physics of Solids* **67**, 2 (2014).
- [19] R. C. Thompson-Flagg, M. J. B. Moura, and M. Marder, Rippling of graphene, *EPL* **85**, 46002 (2009).
- [20] S. Malola, H. Häkkinen, and P. Koskinen, Structural, chemical, and dynamical trends in graphene grain boundaries, *Phys. Rev. B* **81**, 165447 (2010).
- [21] J. Lu, Y. Bao, C. L. Su, and K. P. Loh, Properties of strained structures and topological defects in graphene, *ACS Nano* **7**, 8350 (2013).
- [22] A. Zandiatashbar, G. H. Lee, S. J. An, S. Lee, N. Mathew, M. Terrones, T. Hayashi, C. R. Picu, J. Hone, and N. Koratkar, Effect of defects on the intrinsic strength and stiffness of graphene, *Nature Communications* **5**, 3186 (2014).
- [23] P. Koskinen, I. Fampiou, and A. Ramasubramaniam, Density-Functional Tight-Binding Simulations of Curvature-Controlled Layer Decoupling and Band-Gap Tuning in Bilayer MoS₂, *Physical Review Letters* **112**, 186802 (2014).
- [24] J. H. Warner, Y. Fan, A. W. Robertson, K. He, E. Yoon, and G. D. Lee, Rippling Graphene at the Nanoscale through Dislocation Addition., *Nano letters* **13**, 4937 (2013).
- [25] W. H. Brito, R. Kagimura, and R. H. Miwa, Hydrogenated grain boundaries in graphene, *Applied Physics Letters* **98**, 213107 (2011).
- [26] J. Wang, H. Yu, X. Zhou, X. Liu, R. Zhang, Z. Lu, J. Zheng, L. Gu, K. Liu, D. Wang, and L. Jiao, Probing the crystallographic orientation of two-dimensional atomic crystals with supramolecular self-assembly, *Nature Communications* **8**, 1 (2017).
- [27] K. A. N. Duerloo, Y. Li, and E. J. Reed, Structural phase transitions in two-dimensional Mo- and W-dichalcogenide monolayers, *Nature Communications* **5**, 4214 (2014).
- [28] J. Wang, Z. Li, H. Chen, G. Deng, and X. Niu, *Nano-Micro Letters*, Vol. 11 (Springer Singapore, 2019) p. 48.
- [29] C. R. Ryder, J. D. Wood, S. A. Wells, and M. C. Hersam, Chemically Tailoring Semiconducting Two-Dimensional Transition Metal Dichalcogenides and Black Phosphorus, *ACS Nano* **10**, 3900 (2016).
- [30] Y. Liu and B. I. Yakobson, Cones, pringles, and grain boundary landscapes in graphene topology., *Nano letters* **10**, 2178 (2010).
- [31] J. Koivisto, L. Sladkova, J. Aumanen, P. J. Koskinen, K. Roberts, A. Johansson, P. Myllyperkiö, and M. Pettersson, From Seeds to Islands: Growth of Oxidized Graphene by Two-Photon Oxidation, *J. Phys. Chem. C* **120**, 22330 (2016).
- [32] A. Johansson, P. Myllyperkiö, P. Koskinen, J. Aumanen, J. Koivisto, H. C. Tsai, C. H. Chen, L. Y. Chang, V. M. Hiltunen, J. J. Manninen, W. Y. Woon, and M. Pettersson, Optical Forging of Graphene into Three-Dimensional Shapes, *Nano Lett.* **17**, 6469 (2017).
- [33] K. N. Kudin, G. E. Scuseria, and B. I. Yakobson, C₂F, BN, and C nanoshell elasticity from ab initio computations, *Phys. Rev. B* **64**, 235406 (2001).
- [34] P. Koskinen and O. O. Kit, Approximate Modeling of Spherical Membranes, *Phys. Rev. B* **82**, 235420 (2010).
- [35] R. C. Cooper, C. Lee, C. A. Marianetti, X. Wei, J. Hone, and J. W. Kysar, Nonlinear elastic behavior of two-dimensional molybdenum disulfide, *Physical Review B - Condensed Matter and Materials Physics* **87**, 035423 (2013).
- [36] T. Lorenz, D. Teich, J. O. Joswig, and G. Seifert, Theoretical study of the mechanical behavior of individual TiS₂ and MoS₂ nanotubes, *Journal of Physical Chemistry C* **116**, 11714 (2012).
- [37] Q. Peng, X. Wen, and S. De, Mechanical stabilities of silicene, *RSC Adv.* **3**, 13772 (2013).
- [38] H. Zhao, Strain and chirality effects on the mechanical and electronic properties of silicene and silicane under uniaxial tension, *Physics Letters, Section A: General, Atomic and Solid State Physics* **376**, 3546 (2012).
- [39] L. D. Landau and E. M. Lifshitz, *Theory of elasticity*, 3rd ed. (Pergamon, New York, 1986).
- [40] W. Bao, F. Miao, Z. Chen, H. Zhang, W. Jang, C. Dames,

- and C. N. Lau, Controlled ripple texturing of suspended graphene and ultrathin graphite membranes, *Nat. Nanotechnol.* **4**, 562 (2009).
- [41] V. B. Shenoy, C. D. Reddy, and Y.-W. Zhang, Spontaneous curling of graphene sheets with reconstructed edges, *ACS Nano* **4**, 4840 (2010).
- [42] P. Koskinen, Electronic and optical properties of carbon nanotubes under pure bending, *Phys. Rev. B* **82**, 193409 (2010).
- [43] O. O. Kit, T. Tallinen, L. Mahadevan, J. Timonen, and P. Koskinen, Twisting Graphene Nanoribbons into Carbon Nanotubes, *Phys. Rev. B* **85**, 085428 (2012).
- [44] T. Korhonen and P. Koskinen, Electromechanics of graphene spirals, *AIP Advances* **4**, 127125 (2014).
- [45] F. Memarian, A. Fereidoon, and M. Darvish Ganji, Graphene Young's modulus: Molecular mechanics and DFT treatments, *Superlattices and Microstructures* **85**, 348 (2015).
- [46] P. Koskinen, Quantum Simulations of One-Dimensional Nanostructures under Arbitrary Deformations, *Physical Review Applied* **6**, 034014 (2016).
- [47] See supplemental material at [url will be inserted by publisher] for additional results and details in analytical modeling and numerical simulations.
- [48] A. H. Castro Neto, F. Guinea, N. M. R. Peres, K. S. Novoselov, and A. K. Geim, The electronic properties of graphene, *Rev. Mod. Phys.* **81**, 109 (2009).
- [49] E.-A. Kim and A. H. Castro Neto, Graphene as an electronic membrane, *EPL* **84**, 57007 (2008).
- [50] C. C. Hsu, M. L. Teague, J. Q. Wang, and N. C. Yeh, Nanoscale Strain Engineering of Giant Pseudo-Magnetic Fields, Valley Polarization and Topological Channels in Graphene, *Sci. Adv.* **6**, eaat9488 (2020).
- [51] V.-M. Hiltunen, P. J. Koskinen, K. K. Mentel, J. Manninen, P. Myllyperkiö, A. Johansson, and M. Pettersson, Making Graphene Luminescent by Direct Laser Writing, *The Journal of Physical Chemistry C* **124**, 8371 (2020).
- [52] N. Liu, Z. Pan, L. Fu, C. Zhang, and B. Dai, The origin of wrinkles on transferred graphene, *Nano Research* **4**, 996 (2011).
- [53] S. P. Koenig, N. G. Boddeti, M. L. Dunn, and J. S. Bunch, Ultrastrong adhesion of graphene membranes., *Nat. Nanotechnol.* **6**, 543 (2011).
- [54] J. Wang, D. C. Sorescu, S. Jeon, A. Belianinov, S. V. Kalinin, A. P. Baddorf, and P. Maksymovych, Atomic intercalation to measure adhesion of graphene on graphite, *Nature Communications* **7**, 13263 (2016).
- [55] D. L. Duong, S. J. Yun, and Y. H. Lee, van der Waals Layered Materials: Opportunities and Challenges, *ACS Nano* **11**, 11803 (2017).
- [56] P. Nigge, A. C. Qu, E. Lantagne-Hurtubise, E. Marsell, S. Link, G. Tom, M. Zonno, M. Michiardi, M. Schneider, S. Zhdanovich, G. Levy, U. Starke, C. Gutierrez, D. Bonn, S. A. Burke, M. Franz, and A. Damascelli, Room temperature strain-induced Landau levels in graphene on a wafer-scale platform, *Science Advances* **5**, eaaw5593 (2019), 1902.00514.
- [57] C. R. Harris, K. J. Millman, S. J. van der Walt, R. Gommers, P. Virtanen, D. Cournapeau, E. Wieser, J. Taylor, S. Berg, N. J. Smith, R. Kern, M. Picus, S. Hoyer, M. H. van Kerkwijk, M. Brett, A. Haldane, J. F. del Río, M. Wiebe, P. Peterson, P. Gérard-Marchant, K. Sheppard, T. Reddy, W. Weckesser, H. Abbasi, C. Gohlke, and T. E. Oliphant, Array programming with NumPy, *Nature* **585**, 357 (2020).
- [58] P. Virtanen, R. Gommers, T. E. Oliphant, M. Haberland, T. Reddy, D. Cournapeau, E. Burovski, P. Peterson, W. Weckesser, J. Bright, S. J. van der Walt, M. Brett, J. Wilson, K. J. Millman, N. Mayorov, A. R. Nelson, E. Jones, R. Kern, E. Larson, C. J. Carey, f. Polat, Y. Feng, E. W. Moore, J. VanderPlas, D. Laxalde, J. Perktold, R. Cimrman, I. Henriksen, E. A. Quintero, C. R. Harris, A. M. Archibald, A. H. Ribeiro, F. Pedregosa, P. van Mulbregt, A. Vijaykumar, A. P. Bardelli, A. Rothberg, A. Hilboll, A. Kloeckner, A. Scopatz, A. Lee, A. Rokem, C. N. Woods, C. Fulton, C. Masson, C. Häggström, C. Fitzgerald, D. A. Nicholson, D. R. Hagen, D. V. Pasechnik, E. Olivetti, E. Martin, E. Wieser, F. Silva, F. Lenders, F. Wilhelm, G. Young, G. A. Price, G. L. Ingold, G. E. Allen, G. R. Lee, H. Audren, I. Probst, J. P. Dietrich, J. Silterra, J. T. Webber, J. Slavič, J. Nothman, J. Buchner, J. Kulick, J. L. Schönberger, J. V. de Miranda Cardoso, J. Reimer, J. Harrington, J. L. C. Rodríguez, J. Nunez-Iglesias, J. Kuczynski, K. Tritz, M. Thoma, M. Newville, M. Kümmerer, M. Bolingbroke, M. Tartre, M. Pak, N. J. Smith, N. Nowaczyk, N. Shebanov, O. Pavlyk, P. A. Brodtkorb, P. Lee, R. T. McGibbon, R. Feldbauer, S. Lewis, S. Tygier, S. Sievert, S. Vigna, S. Peterson, S. More, T. Pudlik, T. Oshima, T. J. Pingel, T. P. Robitaille, T. Spura, T. R. Jones, T. Cera, T. Leslie, T. Zito, T. Krauss, U. Upadhyay, Y. O. Halchenko, and Y. Vázquez-Baeza, SciPy 1.0: fundamental algorithms for scientific computing in Python, *Nature Methods* **17**, 261 (2020).
- [59] E. Bitzek, P. Koskinen, F. Gähler, M. Moseler, and P. Gumbsch, Structural Relaxation Made Simple, *Phys. Rev. Lett.* **97**, 170201 (2006).