Low Valence Nickelates: Launching the Nickel Age of Superconductivity

Antia S. Botana,¹ Kwan-Woo Lee,² Michael R. Norman,³ Victor Pardo,^{4,5} and Warren E. Pickett⁶

¹Department of Physics, Arizona State University, Tempe, AZ 85287, USA*

²Division of Display and Semiconductor Physics, Korea University, Sejong 30019, Korea

³Materials Science Division, Argonne National Laboratory, Lemont, IL 60439, USA

⁴Departamento de Física Aplicada, Facultade de Física,

Universidade de Santiago de Compostela, E-15782 Spain

⁵Instituto de Materiais iMATUS, Universidade de Santiago de Compostela, E-15782 Spain

⁶Department of Physics and Astronomy, University of California Davis, Davis, CA 95616, USA

(Dated: February 15, 2022)

The discovery of superconductivity in thin films (~10 nm) of infinite-layer hole-doped NdNiO₂ has invigorated the field of high temperature superconductivity research, reviving the debate over contrasting views that nickelates that are isostructural with cuprates are either (1) sisters of the high temperature superconductors, or (2) that differences between nickel and copper at equal band filling should be the focus of attention. Each viewpoint has its merits, and each has its limitations, suggesting that such a simple picture must be superseded by a more holistic comparison of the two classes. Several recent studies have begun this generalization, raising a number of questions without suggesting any consensus. In this paper, we organize the findings of the electronic structures of *n*-layered NiO₂ materials (n=1 to ∞) to outline (ir)regularities and to make comparisons with cuprates, with the hope that important directions of future research will emerge.

I. BACKGROUND

After much synthesis and characterization of lowvalence layered nickelates over three decades¹⁻⁷, superconductivity was finally observed⁸ in hole-doped $\mathcal{R}NiO_2$ (initially for rare earth \mathcal{R} =Nd, later for \mathcal{R} =La^{9,10} and Pr¹¹) with T_c exhibiting a dome-like dependence^{12,13} being maximal (10-15 K) near 20% doping. This series of discoveries in $\mathcal{R}NiO_2$ materials marked the beginning of a new, nickel age of superconductivity^{14,15} launching a plethora of experimental¹⁶⁻²² and theoretical²³⁻⁴³ work.

 \mathcal{R} NiO₂ materials are the $n=\infty$ member of a larger series of layered nickelates with chemical formula $(\mathcal{R}O_2)^{-}[\mathcal{R}(\operatorname{NiO}_2)_n]^+$ (\mathcal{R} =La, Pr, Nd; $n = 2, 3, \ldots, \infty$) that possess n cuprate-like NiO₂ planes in a squareplanar coordination. Except for the $n=\infty$ case, groups of n-NiO₂ layers are separated by \mathcal{R}_2O_2 blocking layers that severely limit coupling between adjacent units. These layered square-planar compounds are obtained via oxygen deintercalation from the corresponding parent perovskite $\mathcal{R}NiO_3$ $(n=\infty)^2$ and Ruddlesden-Popper $\mathcal{R}_{n+1}\mathrm{Ni}_n\mathrm{O}_{3n+1}$ $(n\neq\infty)$ phases¹. As shown in Fig. 1, the $(\mathcal{R}O_2)^{-}[(\mathcal{R}NiO_2)_n]^+$ series can be mapped onto the cuprate phase diagram in terms of the nickel 3d-electron count, with nominal fillings running from d^9 $(n=\infty)$ to d^8 (for n=1). That superconductivity arises in this series suggests that a new family of superconductors has been uncovered, currently with two members, $n=\infty$ and n=5,⁴⁴ the only ones (so far) where an optimal Ni valence near $d^{8.8}$ has been attained.

Some overviews on experimental and theoretical findings in this family of materials have been recently published^{45–48}. In this paper, we focus on the electronic structure of layered nickelates, confining ourselves to materials with the basic infinite-layer structure: n square planar NiO₂ layers each separated by an \mathcal{R}^{3+} ion without the apical oxygen ion(s) that are common in most cuprates and nickelates.

II. FROM ∞ TO ONE

A. 'Infinite-layer' $n = \infty$: $\mathcal{R}NiO_2$

In parent $\mathcal{R}NiO_2$ materials, Ni has the same formal $3d^9$ electronic configuration as in cuprates. As mentioned above, superconductivity in $\mathcal{R}NiO_2$ materials emerges via hole doping, with T_c exhibiting a dome-like dependence^{12,13,49} akin to cuprates, as shown in Fig. 1. However, in parent infinite-layer nickelates the resistivity shows a metallic T-dependence (but with a low temperature upturn)^{7,8} and there is no signature of longrange magnetic order, even though the presence of strong antiferromagnetic (AFM) correlations has recently been reported⁵⁰. This is in contrast to cuprates, where the parent phase is an AFM charge-transfer insulator.

Noteworthy differences from cuprates were already reflected in early electronic structure calculations as well^{51,52}. For the parent material $\mathcal{R}NiO_2$, non-magnetic density functional theory (DFT) calculations show that besides the Ni- $d_{x^2-y^2}$ band, additional bands of \mathcal{R} -5d character cross the Fermi level. The electronic structure of $\mathcal{R}NiO_2$ is three-dimensional-like, with a large *c*-axis dispersion of both (occupied) Ni and (nearly empty) \mathcal{R} - $5d_{z^2}$ bands due to the close spacing of successive NiO₂ planes along the *c*-axis. The \mathcal{R} -5 d_{z^2} dispersion leads to the appearance of electron pockets at the Γ and A points of the Brillouin zone which display mainly \mathcal{R} -5 d_{z^2} and \mathcal{R} -5 d_{xy} character, respectively, that self-dope the large hole-like Ni- $d_{x^2-y^2}$ Fermi surface. This self-doping effect (absent in the cuprates) introduces a substantial difference between nominal and actual filling of the Ni-d

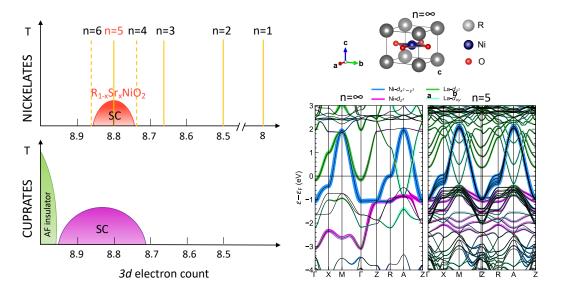


FIG. 1. (Left) Schematic phase diagram as a function of nominal d filling for layered nickelates (top) and cuprates (bottom), highlighting the regions where superconducting domes have been experimentally reported. The possible members of the $\mathcal{R}_{n+1}\operatorname{Ni}_n\operatorname{O}_{2n+2}$ series are marked with lines (dashed lines correspond to materials that have not been synthesized yet). The n = 5 member falls close to the optimal doping value for both cuprates and the infinite-layer nickelate. (Top right) Basic structural unit of the infinite-layer $\mathcal{R}\operatorname{NiO}_2$ with the square planar NiO₂ in the middle. (Bottom right) Band structures for the $n = \infty$ and the n = 5 materials, respectively. The two types of Ni e_g bands are highlighted, as well as the two relevant \mathcal{R} -5d bands.

bands, accounting for conduction and possibly also disrupting AFM order. The presence of the 5*d* electrons is consistent with experimental data, which reveal not only metallic behavior but also evidence for negative charge carriers as reflected in the negative Hall coefficient^{8,12,13}. However, as the material becomes doped with Sr, the \mathcal{R} -5*d* pockets become depopulated, the Hall coefficient changes sign⁸, and the electronic structure becomes more single-band, cuprate-like^{39,53}.

Besides the presence of \mathcal{R} -5d electrons, infinite-layer nickelates have some other relevant differences from the cuprates, particularly their much larger charge-transfer energy between the metal 3d and oxygen 2p states. In cuprates, the charge-transfer energy ε_{3d} - ε_{2p} is as small as 1-2 eV^{54} , indicative of a large *p*-*d* hybridization, and enabling Zhang-Rice singlet formation. In $\mathcal{R}NiO_2$, the charge-transfer energy is much larger, ~ 4.4 eV, as obtained from the on-site energies derived from a Wannier analysis³⁹. This is consistent with the lack of a prepeak in x-ray absorption data at the oxygen K-edge¹⁸. Because of this increase in charge transfer energy, the nickelate is more Mott-like, whereas the cuprate is more charge-transfer-like, in the scheme of Zaanen, Sawatzky and $Allen^{35,38}$. Moreover, the doped holes tend to be on the Ni sites, as opposed to cuprates where they tend to reside on the oxygen sites. This in turn brings up the issue of the nature of the doped holes on the Ni sites. That is, do they behave as effective d^8 dopants, and if so, is d^8 high-spin or low-spin? If the former, then these materials would fall in the category of Hund's metals 40,55-58, and thus would deviate substantially from cuprates. This important matter has yet to be resolved, though *ab initio* calculations point towards a low-spin picture due to the large crystal-field splitting of the e_g states in a square planar environment⁵³.

Because of their lower degree of p - d hybridization, the superexchange in $\mathcal{R}NiO_2$, as determined by resonant inelastic x-ray scattering experiments⁵⁰, is about half that of the cuprates. Still, its value (J=64 meV) confirms the existence of significant AFM correlations 30,50 . Long-range AFM order has however not been reported, with NMR data suggesting the ground state is paramagnetic⁵⁹, and susceptibility data interpreted as spin-glass behavior⁶⁰. Neél type order is consistently obtained in DFT studies^{24,27,29,51}, as in d^9 insulating cuprates. The predicted AFM ground state in DFT+Ucalculations⁶¹ is characterized by the involvement of both $d_{x^2-y^2}$ and d_{z^2} Ni bands⁶². This state is peculiar in that it displays a flat-band one-dimensional-like van Hove singularity of d_{z^2} character pinned at the Fermi level. These flat-band instabilities should inhibit but not eliminate incipient AFM tendencies⁶².

Discussing the origin of superconductivity in $\mathcal{R}NiO_2$, as in the cuprates, is a controversial topic. But certainly the reduced T_c of the nickelate compared to the cuprates is consistent with the reduced value of the superexchange, and the larger charge-transfer energy. t-Jmodel and RPA calculations building from tight-binding parameters derived from DFT calculations show that the dominant pairing instability is in the $d_{x^2-y^2}$ channel, as in cuprates⁶³. Indeed, single-particle tunneling measurements on the superconducting infinite-layer nickelate have revealed a V-shape feature indicative of a d-wave gap⁶⁴. On a broader level, several theoretical papers have speculated that the superconductivity is instead an interfacial effect of the infinite-layer film with the SrTiO₃ substrate^{65–68}, though recently superconductivity has been observed when other substrates are used⁶⁹. In this context, it should be noted that superconductivity has not been observed in bulk samples yet; since the precursor is cubic, there is no set orientation for the *c*-axis, meaning the bulk is far less ordered than the film^{20,21}.

B. The superconducting n = 5 material

Recently, a second superconducting member has been found in the $(\mathcal{R}O_2)^{-}[(\mathcal{R}NiO_2)_n]^+$ family: the n=5 layered nickelate Nd₆Ni₅O₁₂, also synthesized in thin-film form⁴⁴. As schematically shown in Fig. 1, this material has a nominal valence near that of the optimally-doped infinite-layer material (that is, Ni^{1.2+}: $d^{8.8}$ nominal filling) and so, in contrast to its infinite-layer counterpart, it is superconducting without the need for chemical doping. While $\mathcal{R}NiO_2$ displays NiO₂ layers separated by \mathcal{R} ions, this quintuple-layer material (with five NiO_2 layers per formula unit) has an additional fluorite \mathcal{R}_2O_2 slab separating successive five-layer units. Further, each successive five-layer group is displaced by half a lattice constant along the a and b directions (i.e., the body centered translation of the I4/mmm space group). These additional structural features effectively decouple the fivelayer blocks, so the *c*-axis dispersion of this material is much weaker than its infinite-layer counterpart. Despite these significant structural differences, T_c is similar to that of the doped infinite-layer materials (with the onset of the superconducting transition taking place at ~ 15 K), reducing the chances that yet to be synthesized low valence nickelates will have substantially higher transition temperatures.

In terms of its electronic structure⁷⁰, the n=5 material is intermediate between cuprate-like and $n=\infty$ -like behavior. From DFT calculations, the charge-transfer energy of $Nd_6Ni_5O_{12}$ is ~ 4.0 eV. This reduced energy compared to the undoped infinite-layer material means that the Ni-3d states are not as close in energy to the Nd-5d states, consistent with the presence of a pre-peak in the oxygen K-edge (similar to what happens with Sr-doped $NdNiO_2^{53}$). As a consequence, the electron pockets arising from the Nd-5d states are significantly smaller than those in the infinite-layer material (see Fig. 1). This reduced pocket size along with the large hole-like contribution from the Ni-3d states is consistent with experiment in that the Hall coefficient remains positive at all temperatures, with a semiconductor-like temperature dependence reminiscent of under- and optimally-doped layered cuprates. Aside from the appearance of these small Ndderived pockets at the zone corners, the Fermi surface of $Nd_6Ni_5O_{12}$ is analogous to that of multilayer cuprates with one electron-like and four hole-like $d_{x^2-y^2}$ Fermi

surface sheets. Importantly, the Fermi surface of the quintuple-layer nickelate is much more two-dimensional-like compared to the infinite-layer nickelate material, as the presence of the fluorite blocking slab reduces the *c*-axis dispersion, as mentioned above.

C. The n=3 material, the next superconducting member of the series?

The materials discussed above can be put into the context of earlier studies of bulk reduced RP phases with n=2, 3 NiO₂ layers^{5,71–73}, separated by fluorite \mathcal{R}_2O_2 blocking slabs that enforce quasi-2D electronic and magnetic behavior.

The n=3 member of the series, $\mathcal{R}_4 \text{Ni}_3 \text{O}_8$ (with Ni^{1.33+}: $d^{8.67}$ filling), has been studied extensively over the past decade (both single crystal and polycrystralline samples)⁷¹. Since the charge-transfer energy decreases with decreasing n^{70} , the n=3 class is more cuprate-like than its $n=\infty$ and n=5 counterparts. Both La and Pr materials are rather similar regarding their high-energy physics, with a large orbital polarization of the Ni- e_a states, so that the d^8 admixture is low spin^{72,74} (but see Ref. [75]). The primary difference is that $La_4Ni_3O_8$ exhibits long-range diagonal stripe order 73,76 (similar to that seen in 1/3 hole-doped La₂NiO₄), whereas its Pr counterpart appears to have short-range order instead⁷⁷. This results in the La material being insulating⁷⁸ in its low-temperature charge-ordered phase⁷⁹, whereas $Pr_4Ni_3O_8$ remains metallic at all temperatures⁷², with an intriguing linear T behavior in its resistivity for intermediate temperatures (similar to that of cuprates at a comparable hole doping). Nd samples have also been studied⁸⁰, but the degree of insulating/metallicity behavior seems to be sample dependent.

The difference between La and Pr trilayer materials could be due to the reduced volume associated with Pr (one of the motivations for the authors of Ref. [8] to study Sr-doped NdNiO₂ rather than Sr-doped LaNiO₂). The Ni spin state and metal versus insulator character have indeed been calculated to be sensitive to modest pressure⁷⁴. Another factor is possible mixed valency of Pr as observed in cuprates (though Pr-M edge data on $Pr_4Ni_3O_8$ did not indicate mixed valent behavior⁷²). Because of its decreased charge-transfer energy relative to n = 5, the rare-earth derived pockets no longer occur⁸¹. This lack of \mathcal{R} -5d involvement is confirmed by the Hall coefficient that stays positive at all temperatures⁴⁴, (it remains to be understood why the thermopower in the case of $La_4Ni_3O_8$ is always negative⁷⁸, also seen in the metallic phase). In addition, these trilayer nickelates show a reduced charge-transfer energy ($\sim 3.5 \text{ eV}$ as obtained from a Wannier analysis⁷⁰) that, along with the larger effective doping level, is consistent with the strong oxygen K edge pre-peak seen in x-ray absorption data⁷². Oxygen K edge RIXS data indicate a significant contribution of oxygen 2p states to the doped holes⁸². As the effective hole doping level is 1/3, these materials are outside the range where superconductivity would be expected (see Fig. 1). Reaching the desired doping range for superconductivity might be possible via electron doping. This could be achieved by replacing the rare earth with a 4+ ion (such as Ce or Th)⁸³, intercalating with lithium, or gating the material with an ionic liquid.

If superconductivity were to occur, one might hope for a higher T_c as has indeed been predicted via t - J model calculations⁸⁴. Recent RIXS measurements⁷⁷, though, find a superexchange value for n=3 nearly the same as that reported for the infinite-layer material. This suggests the possibility that T_c in the whole nickelate family may be confined to relatively low temperatures compared to the cuprates. The similar value of the superexchange for $n=\infty$ and n=3 is somewhat of a puzzle. Though their t_{pd} hoppings are very similar, the difference in the charge-transfer energy should have resulted in a larger superexchange for n=3. The fact that it is not larger is one of the intriguing questions to be resolved in these low valence layered nickelates.

D. The n=2 material

The n=2 member of the series, La₃Ni₂O₆, has been synthesized and studied as well^{5,85}. In terms of nominal filling, it lies further away from optimal d-filling, being nominally Ni^{1.5+}: $d^{8.5}$. Experimentally, it is a semiconductor with no trace of a transition occurring at any temperature, although NMR data suggest that the AFM correlations are similar to those of the n=3 material. Electronic structure studies⁷⁹ have predicted its ground state to have a charge-ordered pattern with Ni²⁺ cations in a low-spin state and the Ni⁺: d⁹ cations forming a S=1/2 checkerboard pattern. This charge-ordering between S=1/2 Ni⁺: d⁹ and non-magnetic Ni²⁺: d⁸ cations is somewhat similar to the situation in the n=3material⁷⁹. Calculations suggest that it is quite general in these layered nickelates that the Ni^{2+} cations in this square-planar environment are non-magnetic. This has been shown by ab initio calculations to be the case also with the Ni²⁺ dopants in the $\mathcal{R}NiO_2$ materials⁸⁶.

E. The n=1 case

The long-known $\mathcal{R}_2 \text{NiO}_4$ materials, with the n=1 formula as above, contain Ni ions with octahedral coordination. We instead consider Ba₂NiO₂(AgSe)₂ (BNOAS)⁸⁷, as it represents the extreme opposite of the $n=\infty$ member, not only in regards to its d⁸ valence, but also because its square planar coordination with long Ni-O bond is thought to promote 'high-spin' (magnetic) behavior, that is, one hole in $d_{x^2-y^2}$ and one hole in d_{z^2} . Unlike the other n cases, the charge balanced formula is (BaAg₂Se₂)⁰(BaNiO₂)⁰; both blocking and active layers are formally neutral. BNOAS is insulating, distinguished

by a magnetic susceptibiliy that is constant, thus nonmagnetic, above and below a peak at $T^* \sim 130$ K. This increase from and subsequent decrease to its high-T value reflects some kind of magnetic reconstruction at T^* that was initially discussed in terms of canting of high-spin moments. That interpretation does not account for the constant susceptibility above and below the peak.

Valence counting indicates Ni^{2+} : d^8 , so a half-filled e_g manifold. Conventional expectations are either (i) both 3d holes are in the $d_{x^2-y^2}$ orbital – a magnetically dead singlet that cannot account for the behavior around T^* , or (ii) a Hund's rule S=1 triplet, which would show a Curie-Weiss susceptibility above the ordering temperature, but that is not seen in experiment. Correlated DFT calculations⁸⁸ predict an unusual Ni d^8 singlet: a singly occupied d_{z^2} orbital anti-aligned with a $d_{x^2-y^2}$ spin. This 'off-diagonal singlet' consists of two fully spin-polarized 3d orbitals singlet-coupled, giving rise to a 'non-magnetic' ion, however one having an internal orbital texture. Such tendencies were earlier noted⁵¹ in LaNiO₂, and related Ni spin states were observed to be sensitive to modest pressure in the n=2 and n=3classes⁷⁴. Attempts are underway^{89,90} to understand this "magnetic transition in a non-magnetic insulator".

III. OUTLOOK

While this new nickelate family seems to be emerging as its own class of superconductors, its connections to cuprates - crystal and electronic structures, formal dcount in the superconducting region, AFM correlations - retain a focus on similarities between the two classes. Apart from the obvious structural analogy, the cupratemotivated prediction of optimal $d^{8.8}$ filling has been realized in two nickelate materials, one achieved through chemical doping, the other layering dimensionality. In this context, the (so far) little studied n=6 and n=4members of the series⁷⁰ may provide some prospect for superconductivity. Oxygen-reduced samples of these materials are so far lacking (though the n=4 member of the RP series has been epitaxially grown⁹¹), and even if they are synthesized, they might require additional chemical tuning to achieve superconductivity. They share a similar electronic structure to the n = 5 material, but with slightly different nominal filling of the 3d bands⁷⁰. Calculations show that as n decreases from $n=\infty$ to n=3, the cuprate-like character increases, with the charge-transfer energy decreasing along with the self-doping effect from the rare earth 5d states. In contrast, the particular n=1member discussed above seems distinct from other nickelates, and provides a different set of questions in the context of quantum materials^{89,90}.

IV. ACKNOWLEDGMENTS

A.S.B. was supported by the U.S. National Science Foundation, Grant DMR 2045826. K.W.L. was supported by the National Research Foundation of Korea, Grant No. NRF2019R1A2C1009588. M.R.N. was supported by the Materials Sciences and Engineer-

- * Antia.Botana@asu.edu
- ¹ M. Greenblatt, Curr. Opin. Solid State Mater. Sci. **2**, 174 (1997).
- ² M. Hayward, M. Green, M. Rosseinsky, and J. Sloan, J. Am. Chem. Soc. **121**, 8843 (1999).
- ³ M. Crespin, P. Levitz, and L. Gatineau, J. Chem. Soc. Farad. T. 2 **79**, 1181 (1983).
- ⁴ M. Crespin, O. Isnard, F. Dubois, J. Choisnet, and P. Odier, J. Solid State Chem. **178**, 1326 (2005).
- ⁵ V. V. Poltavets, K. A. Lokshin, S. Dikmen, M. Croft, T. Egami, and M. Greenblatt, J. Am. Chem. Soc. **128**, 9050 (2006).
- ⁶ M. Kawai, K. Matsumoto, N. Ichikawa, M. Mizumaki, O. Sakata, N. Kawamura, S. Kimura, and Y. Shimakawa, Cryst. Growth Des. **10**, 2044 (2010).
- ⁷ A. Ikeda, T. Manabe, and M. Naito, Physica C: Superconductivity **495**, 134 (2013).
- ⁸ D. Li, K. Lee, B. Y. Wang, M. Osada, S. Crossley, H. R. Lee, Y. Cui, Y. Hikita, and H. Y. Hwang, Nature (London) 572, 624 (2019).
- ⁹ S. W. Zeng, C. J. Li, L. E. Chow, Y. Cao, Z. T. Zhang, C. S. Tang, X. M. Yin, Z. S. Lim, J. X. Hu, P. Yang, and A. Ariando, arXiv:2105.13492 (2021).
- ¹⁰ M. Osada, B. Y. Wang, B. H. Goodge, S. P. Harvey, K. Lee, D. Li, L. F. Kourkoutis, and H. Y. Hwang, Adv. Mater., 2104083 (2021).
- ¹¹ M. Osada, B. Y. Wang, B. H. Goodge, K. Lee, H. Yoon, K. Sakuma, D. Li, M. Miura, L. F. Kourkoutis, and H. Y. Hwang, Nano Lett. **20**, 5735 (2020).
- ¹² D. Li, B. Y. Wang, K. Lee, S. P. Harvey, M. Osada, B. H. Goodge, L. F. Kourkoutis, and H. Y. Hwang, Phys. Rev. Lett. **125**, 027001 (2020).
- ¹³ S. Zeng, C. S. Tang, X. Yin, C. Li, M. Li, Z. Huang, J. Hu, W. Liu, G. J. Omar, H. Jani, Z. S. Lim, K. Han, D. Wan, P. Yang, S. J. Pennycook, A. T. S. Wee, and A. Ariando, Phys. Rev. Lett. **125**, 147003 (2020).
- ¹⁴ M. R. Norman, Physics **13**, 85 (2020).
- ¹⁵ W. E. Pickett, Nat. Rev. Phys. **3**, 7 (2021).
- ¹⁶ K. Lee, B. H. Goodge, D. Li, M. Osada, B. Y. Wang, Y. Cui, L. F. Kourkoutis, and H. Y. Hwang, APL Mater. 8, 041107 (2020).
- ¹⁷ B. H. Goodge, D. Li, K. Lee, M. Osada, B. Y. Wang, G. A. Sawatzky, H. Y. Hwang, and L. F. Kourkoutis, Proc. Natl. Acad. Sci. USA **118**, e2007683118 (2021).
- ¹⁸ M. Hepting, D. Li, C. J. Jia, H. Lu, E. Paris, Y. Tseng, X. Feng, M. Osada, E. Been, Y. Hikita, Y.-D. Chuang, Z. Hussain, K. J. Zhou, A. Nag, M. Garcia-Fernandez, M. Rossi, H. Y. Huang, D. J. Huang, Z. X. Shen, T. Schmitt, H. Y. Hwang, B. Moritz, J. Zaanen, T. P. Devereaux, and W. S. Lee, Nat. Mater. **19**, 381 (2020).

ing Division, Basic Energy Sciences, Office of Science, U.S. Dept. of Energy. V.P. acknowledges support from the MINECO of Spain through the project PGC2018–101334-BC21. W.E.P. acknowledges support from U.S. National Science Foundation, Grant DMR 1607139.

- ¹⁹ Y. Fu, L. Wang, H. Cheng, S. Pei, X. Zhou, J. Chen, S. Wang, R. Zhao, W. Jiang, C. Liu, M. Huang, X. Wang, Y. Zhao, D. Yu, F. Ye, S. Wang, and J.-W. Mei, arXiv:1911.03177 (2019).
- ²⁰ Q. Li, C. He, J. Si, X. Zhu, Y. Zhang, and H.-H. Wen, Commun. Mater. 1, 16 (2020).
- ²¹ B.-X. Wang, H. Zheng, E. Krivyakina, O. Chmaissem, P. P. Lopes, J. W. Lynn, L. C. Gallington, Y. Ren, S. Rosenkranz, J. F. Mitchell, and D. Phelan, Phys. Rev. Mater. 4, 084409 (2020).
- ²² Q. Gu, Y. Li, S. Wan, H. Li, W. Guo, H. Yang, Q. Li, X. Zhu, X. Pan, Y. Nie, and H.-H. Wen, Nat. Commun. 11, 6027 (2020).
- ²³ P. Jiang, L. Si, Z. Liao, and Z. Zhong, Phys. Rev. B 100, 201106 (2019).
- ²⁴ Z. Liu, Z. Ren, W. Zhu, Z. Wang, and J. Yang, npj Quantum Mater. 5, 31 (2020).
- ²⁵ Y. Nomura, M. Hirayama, T. Tadano, Y. Yoshimoto, K. Nakamura, and R. Arita, Phys. Rev. B **100**, 205138 (2019).
- ²⁶ X. Wu, D. Di Sante, T. Schwemmer, W. Hanke, H. Y. Hwang, S. Raghu, and R. Thomale, Phys. Rev. B 101, 060504 (2020).
- ²⁷ M.-Y. Choi, K.-W. Lee, and W. E. Pickett, Phys. Rev. B 101, 020503 (2020).
- ²⁸ S. Ryee, H. Yoon, T. J. Kim, M. Y. Jeong, and M. J. Han, Phys. Rev. B **101**, 064513 (2020).
- ²⁹ Y. Gu, S. Zhu, X. Wang, J. Hu, and H. Chen, Commun. Phys. **3**, 84 (2020).
- ³⁰ I. Leonov, S. L. Skornyakov, and S. Y. Savrasov, Phys. Rev. B **101**, 241108 (2020).
- ³¹ F. Lechermann, Phys. Rev. B **101**, 081110 (2020).
- ³² F. Lechermann, Phys. Rev. X **10**, 041002 (2020).
- ³³ L.-H. Hu and C. Wu, Phys. Rev. Research 1, 032046 (2019).
- ³⁴ H. Sakakibara, H. Usui, K. Suzuki, T. Kotani, H. Aoki, and K. Kuroki, Phys. Rev. Lett. **125**, 077003 (2020).
- ³⁵ M. Jiang, M. Berciu, and G. A. Sawatzky, Phys. Rev. Lett. 124, 207004 (2020).
- ³⁶ P. Werner and S. Hoshino, Phys. Rev. B **101**, 041104 (2020).
- ³⁷ H. Zhang, L. Jin, S. Wang, B. Xi, X. Shi, F. Ye, and J.-W. Mei, Phys. Rev. Research 2, 013214 (2020).
- ³⁸ J. Karp, A. S. Botana, M. R. Norman, H. Park, M. Zingl, and A. Millis, Phys. Rev. X 10, 021061 (2020).
- ³⁹ A. S. Botana and M. R. Norman, Phys. Rev. X 10, 011024 (2020).
- ⁴⁰ Y. Wang, C.-J. Kang, H. Miao, and G. Kotliar, Phys. Rev. B **102**, 161118 (2020).
- ⁴¹ V. Olevano, F. Bernardini, X. Blase, and A. Cano, Phys. Rev. B **101**, 161102(R) (2020).

- ⁴² Y.-H. Zhang and A. Vishwanath, Phys. Rev. Research 2, 023112 (2020).
- ⁴³ F. Petocchi, V. Christiansson, F. Nilsson, F. Aryasetiawan, and P. Werner, Phys. Rev. X 10, 041047 (2020).
- ⁴⁴ G. A. Pan, D. F. Segedin, H. LaBollita, Q. Song, E. M. Nica, B. H. Goodge, A. T. Pierce, S. Doyle, S. Novakov, D. C. Carrizales, A. T. N'Diaye, P. Shafer, H. Paik, J. T. Heron, J. A. Mason, A. Yacoby, L. F. Kourkoutis, O. Erten, C. M. Brooks, A. S. Botana, and J. A. Mundy, Nat. Mater (accepted), arXiv:2109.09726 (2021).
- ⁴⁵ J. Zhang and X. Tao, CrystEngComm **23**, 3249 (2021).
- ⁴⁶ Y. Nomura and R. Arita, arXiv:2107.12923 (2021).
- ⁴⁷ Q. Gu and H.-H. Wen, arXiv:2109.07654 (2021).
- ⁴⁸ A. S. Botana, F. Bernardini, and A. Cano, J. Exp. Theor. Phys. **132**, 618 (2021).
- ⁴⁹ M. Osada, B. Y. Wang, K. Lee, D. Li, and H. Y. Hwang, Phys. Rev. Mater. 4, 121801 (2020).
- ⁵⁰ H. Lu, M. Rossi, A. Nag, M. Osada, D. F. Li, K. Lee, B. Y. Wang, M. Garcia-Fernandez, S. Agrestini, Z. X. Shen, E. M. Been, B. Moritz, T. P. Devereaux, J. Zaanen, H. Y. Hwang, K.-J. Zhou, and W. S. Lee, Science **373**, 213 (2021).
- ⁵¹ K.-W. Lee and W. E. Pickett, Phys. Rev. B **70**, 165109 (2004).
- ⁵² V. Anisimov, D. Bukhvalov, and T. Rice, Phys. Rev. B 59, 7901 (1999).
- ⁵³ J. Krishna, H. LaBollita, A. O. Fumega, V. Pardo, and A. S. Botana, Phys. Rev. B **102**, 224506 (2020).
- ⁵⁴ C. Weber, C. Yee, K. Haule, and G. Kotliar, EPL (Europhys. Lett.) **100**, 37001 (2012).
- ⁵⁵ B. Kang, C. Melnick, P. Semon, S. Ryee, M. J. Han, G. Kotliar, and S. Choi, arXiv:2007.14610 (2021).
- ⁵⁶ S. Ryee, M. J. Han, and S. Choi, Phys. Rev. Lett. **126**, 206401 (2021).
- ⁵⁷ Z. Liu, C. Xu, C. Cao, W. Zhu, Z. F. Wang, and J. Yang, Phys. Rev. B **103**, 045103 (2021).
- ⁵⁸ C.-J. Kang and G. Kotliar, Phys. Rev. Lett. **126**, 127401 (2021).
- ⁵⁹ D. Zhao, Y. B. Zhou, Y. Fu, L. Wang, X. F. Zhou, H. Cheng, J. Li, D. W. Song, S. J. Li, B. L. Kang, L. X. Zheng, L. P. Nie, Z. M. Wu, M. Shan, F. H. Yu, J. J. Ying, S. M. Wang, J. W. Mei, T. Wu, and X. H. Chen, Phys. Rev. Lett. **126**, 197001 (2021).
- ⁶⁰ H. Lin, D. J. Gawryluk, Y. M. Klein, S. Huangfu, E. Pomjakushina, F. von Rohr, and A. Schilling, arXiv:2104.14324 (2021).
- ⁶¹ R. Zhang, C. Lane, B. Singh, J. Nokelainen, B. Barbiellini, R. S. Markiewicz, A. Bansil, and J. Sun, Commun. Phys. 4, 118 (2021).
- ⁶² M.-Y. Choi, W. E. Pickett, and K.-W. Lee, Phys. Rev. Research 2, 033445 (2020).
- ⁶³ X. Wu, D. Di Sante, T. Schwemmer, W. Hanke, H. Y. Hwang, S. Raghu, and R. Thomale, Phys. Rev. B 101, 060504 (2020).
- ⁶⁴ Q. Gu, Y. Li, S. Wan, H. Li, W. Guo, H. Yang, Q. Li, X. Zhu, X. Pan, Y. Nie, and H.-H. Wen, Nat. Commun. 11, 6027 (2020).
- ⁶⁵ R. He, P. Jiang, Y. Lu, Y. Song, M. Chen, M. Jin, L. Shui, and Z. Zhong, Phys. Rev. B **102**, 035118 (2020).
- ⁶⁶ F. Bernardini and A. Cano, J. Phys. Mater. **3**, 03LT01 (2020).
- ⁶⁷ B. Geisler and R. Pentcheva, Phys. Rev. Research 3, 013261 (2021).

- ⁶⁸ R. A. Ortiz, H. Menke, F. Misják, D. T. Mantadakis, K. Fürsich, E. Schierle, G. Logvenov, U. Kaiser, B. Keimer, P. Hansmann, and E. Benckiser, Phys. Rev. B **104**, 165137 (2021).
- ⁶⁹ X. Ren, Q. Gao, Y. Zhao, X. Z. Hailan Luo, and Z. Zhu, arXiv:2109.05761 (2021).
- ⁷⁰ H. LaBollita and A. S. Botana, Phys. Rev. B **104**, 035148 (2021).
- ⁷¹ V. V. Poltavets, K. A. Lokshin, M. Croft, T. K. Mandal, T. Egami, and M. Greenblatt, Inorg. Chem. 46, 10887 (2007).
- ⁷² J. Zhang, A. Botana, J. Freeland, D. Phelan, H. Zheng, V. Pardo, M. Norman, and J. Mitchell, Nat. Phys. 13, 864 (2017).
- ⁷³ J. Zhang, Y.-S. Chen, D. Phelan, H. Zheng, M. Norman, and J. Mitchell, Proc. Natl. Acad. Sci. USA **113**, 8945 (2016).
- ⁷⁴ V. Pardo and W. E. Pickett, Phys. Rev. B 85, 045111 (2012).
- ⁷⁵ J. Karp, A. Hampel, M. Zingl, A. S. Botana, H. Park, M. R. Norman, and A. J. Millis, Phys. Rev. B **102**, 245130 (2020).
- ⁷⁶ J. Zhang, D. M. Pajerowski, A. S. Botana, H. Zheng, L. Harriger, J. Rodriguez-Rivera, J. P. C. Ruff, N. J. Schreiber, B. Wang, Y.-S. Chen, W. C. Chen, M. R. Norman, S. Rosenkranz, J. F. Mitchell, and D. Phelan, Phys. Rev. Lett. **122**, 247201 (2019).
- ⁷⁷ J. Q. Lin, P. Villar Arribi, G. Fabbris, A. S. Botana, D. Meyers, H. Miao, Y. Shen, D. G. Mazzone, J. Feng, S. G. Chiuzbăian, A. Nag, A. C. Walters, M. García-Fernández, K.-J. Zhou, J. Pelliciari, I. Jarrige, J. W. Freeland, J. Zhang, J. F. Mitchell, V. Bisogni, X. Liu, M. R. Norman, and M. P. M. Dean, Phys. Rev. Lett. **126**, 087001 (2021).
- ⁷⁸ J.-G. Cheng, J.-S. Zhou, J. Goodenough, H. Zhou, K. Matsubayashi, Y. Uwatoko, P. Kong, C. Jin, W. Yang, and G. Shen, Phys. Rev. Lett. **108**, 236403 (2012).
- ⁷⁹ A. S. Botana, V. Pardo, W. E. Pickett, and M. R. Norman, Phys. Rev. B **94**, 081105 (2016).
- ⁸⁰ R. Retoux, J. Rodriguez-Carvajal, and P. Lacorre, J. Solid State Chem. **140**, 307 (1998).
- ⁸¹ V. Pardo and W. E. Pickett, Phys. Rev. Lett. **105**, 266402 (2010).
- ⁸² Y. Shen, J. Sears, G. Fabbris, J. Li, J. Pelliciari, I. Jarrige, X. He, I. Bozovic, M. Mitrano, J. Zhang, J. F. Mitchell, A. S. Botana, V. Bisogni, M. R. Norman, S. Johnston, and M. P. M. Dean, arXiv:2110.08937 (2021).
- ⁸³ A. S. Botana, V. Pardo, and M. R. Norman, Phys. Rev. Mater. 1, 021801 (2017).
- ⁸⁴ E. M. Nica, J. Krishna, R. Yu, Q. Si, A. S. Botana, and O. Erten, Phys. Rev. B **102**, 020504 (2020).
- ⁸⁵ J. Crocker, A. Dioguardi, K. Shirer, V. Poltavets, M. Greenblatt, P. Klavins, and N. Curro, Phys. Rev. B 88, 075124 (2013).
- ⁸⁶ J. Krishna, H. LaBollita, A. O. Fumega, V. Pardo, and A. S. Botana, Phys. Rev. B **102**, 224506 (2020).
- ⁸⁷ Y. Matsumoto, T. Yamamoto, K. Nakano, H. Takatsu, T. Murakami, K. Hongo, R. Maezono, H. Ogino, D. Song, C. M. Brown, C. Tassel, and H. Kageyama, Angew. Chem. Int. Ed. **58**, 756 (2019).
- ⁸⁸ H.-S. Jin, W. E. Pickett, and K.-W. Lee, Phys. Rev. Research 2, 033197 (2020).
- ⁸⁹ W.-L. Tu, E.-G. Moon, K.-W. Lee, W. E. Pickett, and H.-Y. Lee, arXiv:2107.11936 (2021).

⁹⁰ R. R. P. Singh, arXiv:2108.09706 (2021).

⁹¹ Z. Li, W. Guo, T. Zhang, J. Song, T. Gao, Z. Gu, and Y. Nie, APL Mater. 8, 091112 (2020).