

Semiclassical magnetotransport including the effects of the Berry curvature and Lorentz force

Seungchan Woo^{1,2,*}, Brett Min^{3,2,*} and Hongki Min^{1,2†}

¹ *Department of Physics and Astronomy, Seoul National University, Seoul 08826, Korea*

² *Center for Theoretical Physics (CTP), Seoul National University, Seoul 08826, Korea and*

³ *Department of Physics, McGill University, Montréal, Québec H3A 2T8, Canada*

(Dated: May 31, 2022)

In topological semimetals and insulators, negative longitudinal magnetoresistance and angle-dependent planar Hall effect have been reported arising from the Berry curvature. Using the Boltzmann transport theory, we present a closed-form expression for the nonequilibrium distribution function which includes both the effects of the Berry curvature and Lorentz force. Using this formulation, we obtain analytical expressions for conductivity and resistivity tensors in Weyl semimetals demonstrating a characteristic field dependence arising from the competition between the two effects.

I. INTRODUCTION

In topological materials with a nonvanishing Berry curvature, the positive magnetoconductance has been observed experimentally in the presence of parallel electric and magnetic fields [1–15]. This is a unique feature to topological materials that does not occur in conventional magnetotransport which only takes classical Lorentz force effect into account.

The prevailing explanation for the positive longitudinal magnetoconductance is the so-called chiral anomaly. In 1983, Nielsen and Ninomiya suggested the chiral anomaly in Weyl fermions under a strong magnetic field regime where the chiral zeroth Landau level creates a one-dimensional conducting channel that pumps electrons from one Weyl node to another [16]. In 2013, Son and Spivak discussed chiral anomaly in Weyl semimetals under weak external magnetic field using the semi-classical Boltzmann approach [17]. They argued the positive magnetoconductivity that scales quadratically in magnetic field is due to topological charge pumping. One can expect possible detection of chiral anomaly between the valleys, given that the intervalley scattering is negligible compared to the intravalley scattering [18]. However, chiral anomaly cannot be responsible for observed positive magnetoconductivity in topological insulators (TIs) where chiral charges are not well defined [9–15]. In topological materials such as TIs [19] and Weyl semimetals (WSMs) [20], it is suggested that the anomalous velocity induced by the non-trivial Berry curvature alone can generate an additional contribution to the conductivity that grows with the magnetic field.

To understand magnetotransport properties quantitatively, it is important to consider both the effects of the anomalous velocity due to the non-trivial Berry curvature and the classical Lorentz force effect. Most of the previous studies [19–21] have focused on the Berry curvature effect, while only a few took the Lorentz force

into considerations in describing magnetotransport behaviors [22, 23]. In this paper, we revisit semiclassical treatment of magnetotransport in topological materials to shed more light on the origin of the observed positive magnetoconductivity. We present a general semiclassical formula for conductivity which fully incorporates the Berry curvature and the Lorentz force. From the Boltzmann transport equation, we obtain a closed-form expression for the nonequilibrium distribution function by solving the corresponding self-consistent equation. We then apply our formula to WSMs and express the magnetoconductivity in terms of dimensionless parameters characterizing magnetic fields associated with the Lorentz force and the Berry curvature, respectively.

II. SEMICLASSICAL BOLTZMANN MAGNETOTRANSPORT THEORY FOR TOPOLOGICAL MATERIALS

The semiclassical Boltzmann transport equation governs the time evolution of a non-equilibrium distribution function $f = f(\mathbf{r}, \mathbf{k}, t)$ at position \mathbf{r} and momentum \mathbf{k} . It states that the time evolution of f equals the probability rate of electrons being scattered in and out of the distribution, called the collision term $\left(\frac{\partial f}{\partial t}\right)_{\text{coll}}$:

$$\frac{df}{dt} = \left(\frac{\partial f}{\partial t}\right)_{\text{coll}}. \quad (1)$$

In a homogeneous sample with a steady external perturbation, there are no position \mathbf{r} nor time t dependence in the distribution function f . Then, $\frac{df}{dt}$ simplifies to

$$\frac{df}{dt} = \dot{\mathbf{k}} \cdot \frac{\partial f_{\mathbf{k}}}{\partial \mathbf{k}}, \quad (2)$$

where we have included a subscript \mathbf{k} to the non-equilibrium distribution function f to indicate that it is only a function of \mathbf{k} . In a simple relaxation time approximation, the collision integral is replaced by the ratio between the deviation from the equilibrium Fermi-Dirac

* These authors contributed equally to this work.

† hmin@snu.ac.kr

distribution $f_{\mathbf{k}}^{(0)}$ and the average time τ between successive collisions. Hence,

$$\dot{\mathbf{k}} \cdot \frac{\partial f_{\mathbf{k}}}{\partial \mathbf{k}} = -\frac{g_{\mathbf{k}}}{\tau}, \quad (3)$$

where $g_{\mathbf{k}} = f_{\mathbf{k}} - f_{\mathbf{k}}^{(0)}$. Here we assume a constant transport relaxation time τ in momentum \mathbf{k} and magnetic field \mathbf{B} for a given chemical potential. Note that when we fully consider the collision integral in the system with a non-trivial Berry curvature, the transport relaxation time τ may show a field dependent anisotropy induced by the coupling between the Berry curvature and magnetic field [24]. However, in weak magnetic field regime, we can assume τ as a constant. Furthermore, when short-range scattering is dominant or charged impurities are fully screened, we can assume that τ does not depend on \mathbf{k} [25–27].

Here we provide a closed-form expression for magnetoconductivity in the presence of both a non-trivial Berry curvature and the Lorentz force within the semiclassical Boltzmann approach. The semiclassical equations of motion for electrons with a charge $q = -e$ in the presence of the Berry curvature are given by [28]

$$\dot{\mathbf{r}} = \frac{\partial \epsilon_{\mathbf{m}}(\mathbf{k})}{\hbar \partial \mathbf{k}} - \dot{\mathbf{k}} \times \boldsymbol{\Omega}_{\mathbf{k}}, \quad (4a)$$

$$\hbar \dot{\mathbf{k}} = q\mathbf{E} + \frac{q}{c} \dot{\mathbf{r}} \times \mathbf{B}, \quad (4b)$$

where $\epsilon_{\mathbf{m}}(\mathbf{k}) = \epsilon_0(\mathbf{k}) - \mathbf{m}_{\mathbf{k}} \cdot \mathbf{B}$, $\epsilon_0(\mathbf{k})$ is the unperturbed band energy, $\mathbf{m}_{\mathbf{k}}$ is an orbital magnetic moment that couple to the magnetic field and $\boldsymbol{\Omega}_{\mathbf{k}}$ is the Berry curvature. It has been reported that disorder affects not only the carrier distribution but also the semiclassical equations of motion, generating a correction to the velocity proportional to the disorder strength [29]. In this work, we neglect this correction assuming a weak disorder potential for simplicity. In the presence of a magnetic field, $\dot{\mathbf{r}}$ and $\dot{\mathbf{k}}$ in Eq. (4) are coupled through the Lorentz force. Combining these two equations of motion, we have

$$\dot{\mathbf{r}} = D_{\mathbf{k}}^{-1} \left[\mathbf{v}_{\mathbf{k}} - \frac{q}{\hbar} \mathbf{E} \times \boldsymbol{\Omega}_{\mathbf{k}} - \frac{q}{\hbar c} (\boldsymbol{\Omega}_{\mathbf{k}} \cdot \mathbf{v}_{\mathbf{k}}) \mathbf{B} \right], \quad (5a)$$

$$\hbar \dot{\mathbf{k}} = D_{\mathbf{k}}^{-1} \left[q\mathbf{E} + \frac{q}{c} \mathbf{v}_{\mathbf{k}} \times \mathbf{B} - \frac{q^2}{\hbar c} (\mathbf{E} \cdot \mathbf{B}) \boldsymbol{\Omega}_{\mathbf{k}} \right], \quad (5b)$$

where $\mathbf{v}_{\mathbf{k}} = \frac{1}{\hbar} \frac{\partial \epsilon_{\mathbf{m}}(\mathbf{k})}{\partial \mathbf{k}}$ and $D_{\mathbf{k}} = 1 - \frac{q}{\hbar c} (\boldsymbol{\Omega}_{\mathbf{k}} \cdot \mathbf{B})$ represents the modified density of states in the phase space due to the Berry curvature effect [25]. The first term in the square bracket in Eq. (5b) corresponds to electric force due to an electric field \mathbf{E} and the second term represents Lorentz force due to a magnetic field \mathbf{B} . The last term is anomalous electromagnetic force due to the Berry curvature which leads to positive magnetoconductivity in topological materials.

Replacing $f_{\mathbf{k}} = f_{\mathbf{k}}^{(0)} + g_{\mathbf{k}}$ according to the relaxation time approximation in Eq. (3), we have

$$\hbar \dot{\mathbf{k}} \cdot \frac{1}{\hbar} \frac{\partial (f_{\mathbf{k}}^{(0)} + g_{\mathbf{k}})}{\partial \mathbf{k}} = -\frac{g_{\mathbf{k}}}{\tau}. \quad (6)$$

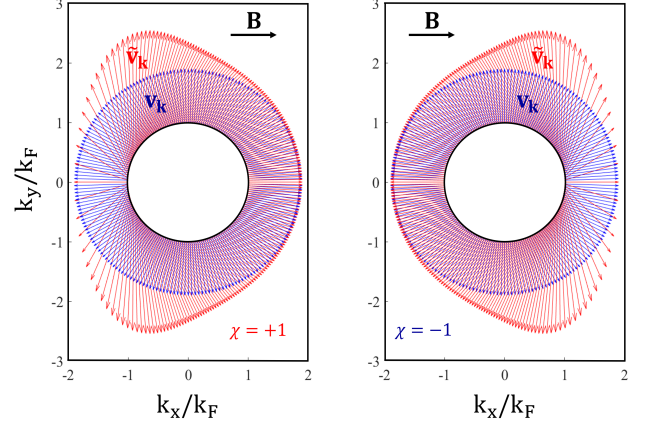


FIG. 1. Schematic picture comparing $\mathbf{v}_{\mathbf{k}}$ (blue) and $\tilde{\mathbf{v}}_{\mathbf{k}}$ (red) near the Weyl nodes described by the Hamiltonian $H = \chi \hbar v_F \mathbf{k} \cdot \boldsymbol{\sigma}$ for $\chi = \pm 1$ in the presence of a constant magnetic field $\mathbf{B} = B_x \hat{x}$. Here the length of an arrow represents the velocity normalized by v_F .

Plugging Eq. (5) into Eq. (6), we get

$$D_{\mathbf{k}}^{-1} \left[q\mathbf{E} \cdot \mathbf{v}_{\mathbf{k}} \frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} + \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \times \mathbf{B}) \cdot \frac{\partial g_{\mathbf{k}}}{\partial \mathbf{k}} - \frac{q^2}{\hbar c} (\mathbf{E} \cdot \mathbf{B}) (\boldsymbol{\Omega}_{\mathbf{k}} \cdot \mathbf{v}_{\mathbf{k}}) \frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right] = -\frac{g_{\mathbf{k}}}{\tau}. \quad (7)$$

In previous studies [19–21] of magnetoconductivity and planar Hall conductivity in topological materials, Lorentz force effect has been often neglected. Therefore, in order to better understand positive longitudinal magnetoconductivity and angle-dependent planar Hall conductivity in topological materials, we take all the terms in Eq. (7) into consideration.

We can rewrite Eq. (7) in the following form:

$$q\mathbf{E} \cdot \tilde{\mathbf{v}}_{\mathbf{k}} \frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} + \frac{q}{\hbar c} (\tilde{\mathbf{v}}_{\mathbf{k}} \times \mathbf{B}) \cdot \frac{\partial g_{\mathbf{k}}}{\partial \mathbf{k}} = -\frac{g_{\mathbf{k}}}{\tau}, \quad (8)$$

where

$$\tilde{\mathbf{v}}_{\mathbf{k}} = D_{\mathbf{k}}^{-1} \left[\mathbf{v}_{\mathbf{k}} - \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \cdot \boldsymbol{\Omega}_{\mathbf{k}}) \mathbf{B} \right]. \quad (9)$$

Figure 1 shows a schematic picture of $\tilde{\mathbf{v}}_{\mathbf{k}}$ in WSMs in the presence of a magnetic field \mathbf{B} . As shown in Fig. 1, $\tilde{\mathbf{v}}_{\mathbf{k}}$ is greater in magnitude than $\mathbf{v}_{\mathbf{k}}$ in all \mathbf{k} except when $\mathbf{v}_{\mathbf{k}}$ is parallel to \mathbf{B} giving $\tilde{\mathbf{v}}_{\mathbf{k}} = \mathbf{v}_{\mathbf{k}}$. In general, it is this effect due to Berry curvature that leads to enhanced magnetoconductivity in topological materials.

Our goal now is to solve for $g_{\mathbf{k}}$ in Eq. (8). We assume that a small deviation from the equilibrium distribution takes the form of $g_{\mathbf{k}} = \tilde{\mathbf{v}}_{\mathbf{k}} \cdot \mathbf{G}$ where \mathbf{G} is some arbitrary vector that is independent of $\tilde{\mathbf{v}}_{\mathbf{k}}$. Upon plugging $g_{\mathbf{k}} = \tilde{\mathbf{v}}_{\mathbf{k}} \cdot \mathbf{G}$ into Eq. (8), we obtain

$$q\tau \frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \mathbf{E} \cdot \tilde{\mathbf{v}}_{\mathbf{k}} + \frac{q\tau}{c} (\tilde{\mathbf{v}}_{\mathbf{k}} \times \mathbf{B}) \cdot \mathbf{M}^{-1} \mathbf{G} + \tilde{\mathbf{v}}_{\mathbf{k}} \cdot \mathbf{G} = 0, \quad (10)$$

where $\mathbf{M}_{ij}^{-1} = \frac{1}{\hbar} \frac{\partial \tilde{v}_{k,i}}{\partial k_j}$ is the inverse mass tensor. Factoring $\tilde{\mathbf{v}}_{\mathbf{k}}$ out,

$$g_{\mathbf{k}} = \tilde{\mathbf{v}}_{\mathbf{k}} \cdot \left[q\tau \left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right) \mathbf{E} - \frac{q\tau}{c} (\mathbf{B} \times \mathbf{M}^{-1} \mathbf{G}) \right]. \quad (11)$$

From $g_{\mathbf{k}} = \tilde{\mathbf{v}}_{\mathbf{k}} \cdot \mathbf{G}$ and Eq. (11), we obtain a self-consistent form of \mathbf{G} as

$$\mathbf{G} = \mathbf{G}_0 - \frac{q\tau}{c} (\mathbf{B} \times \mathbf{M}^{-1} \mathbf{G}), \quad (12)$$

where

$$\mathbf{G}_0 = q\tau \left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right) \mathbf{E}. \quad (13)$$

The solution for Eq. (12) can be obtained as

$$\mathbf{G} = q\tau \left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right) \left(\mathbb{1} + \frac{q\tau}{c} \mathbb{F} \mathbf{M}^{-1} \right)^{-1} \mathbf{E}, \quad (14)$$

where $\mathbb{F}_{ij} = \sum_k \epsilon_{ijk} B_k$ is the magnetic field strength tensor (see Appendix A for a detailed derivation). Thus, we obtain

$$g_{\mathbf{k}} = q\tau \left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right) \tilde{\mathbf{v}}_{\mathbf{k}} \cdot \left[\left(\mathbb{1} + \frac{q\tau}{c} \mathbb{F} \mathbf{M}^{-1} \right)^{-1} \mathbf{E} \right]. \quad (15)$$

The current is therefore computed as

$$J_{\alpha} = q \int \frac{d^d k}{(2\pi)^d} D_{\mathbf{k}} f_{\mathbf{k}} v_{\alpha}, \quad (16)$$

where α is the direction in which we measure the current. Let us denote the current associated with $f_{\mathbf{k}}^{(0)}$ as $J_{\alpha}^{\text{int}} = q \int \frac{d^d k}{(2\pi)^d} D_{\mathbf{k}} f_{\mathbf{k}}^{(0)} v_{\alpha}$ and that associated with $g_{\mathbf{k}}$ as $J_{\alpha}^{\text{ext}} = q \int \frac{d^d k}{(2\pi)^d} D_{\mathbf{k}} g_{\mathbf{k}} v_{\alpha}$. From now on, we will only focus on the extrinsic contribution J_{α}^{ext} arising from scatterings.

Plugging Eq. (15) into J_{α}^{ext} and using $J_{\alpha}^{\text{ext}} = \sum_{\beta} \sigma_{\alpha\beta} E_{\beta}$ relation, we finally arrive at

$$\sigma_{\alpha\beta} = q^2 \int \frac{d^d k}{(2\pi)^d} D_{\mathbf{k}} \tau \left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right) \tilde{v}_{\alpha} \times \left(\tilde{\mathbf{v}}_{\mathbf{k}} \cdot \left\{ \left[\mathbb{1} + \frac{q\tau}{c} \mathbb{F} \mathbf{M}^{-1} \right]^{-1} \hat{\beta} \right\} \right), \quad (17)$$

where β is the direction of an electric field.

Now let us assume that the mobility tensor $e\tau \mathbf{M}^{-1}$ is set to a constant μ for simplicity. Then \mathbf{G} in Eq. (14) becomes (see Appendix A)

$$\mathbf{G} = q\tau \left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right) \frac{\mathbf{E} + \frac{\mu}{c} \mathbf{E} \times \mathbf{B} + \frac{\mu^2}{c^2} (\mathbf{E} \cdot \mathbf{B}) \mathbf{B}}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2}. \quad (18)$$

Note that the obtained \mathbf{G} is consistent with the assumption that \mathbf{G} is independent of $\tilde{\mathbf{v}}_{\mathbf{k}}$. Then $g_{\mathbf{k}}$ is given by

$$g_{\mathbf{k}} = q\tau \left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right) \tilde{\mathbf{v}}_{\mathbf{k}} \cdot \frac{\mathbf{E} + \frac{\mu}{c} \mathbf{E} \times \mathbf{B} + \frac{\mu^2}{c^2} (\mathbf{E} \cdot \mathbf{B}) \mathbf{B}}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2}. \quad (19)$$

Using Eq. (19), we finally obtain the following form for magnetoconductivity

$$\sigma_{\alpha\beta} = q^2 \int \frac{d^d k}{(2\pi)^d} \frac{D_{\mathbf{k}} \tau \left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right)}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2} \times \left[\tilde{v}_{\alpha} \tilde{v}_{\beta} - \frac{\mu}{c} \tilde{v}_{\alpha} (\tilde{\mathbf{v}}_{\mathbf{k}} \times \mathbf{B})_{\beta} + \frac{\mu^2}{c^2} (\tilde{\mathbf{v}}_{\mathbf{k}} \cdot \mathbf{B}) \tilde{v}_{\alpha} B_{\beta} \right]. \quad (20)$$

The above form is a general expression of magnetoconductivity for topological materials including the Berry curvature and Lorentz force within the semiclassical regime under the assumption that \mathbf{G} in $g_{\mathbf{k}} = \tilde{\mathbf{v}}_{\mathbf{k}} \cdot \mathbf{G}$ is independent of $\tilde{\mathbf{v}}_{\mathbf{k}}$ and the mobility tensor is a constant.

III. MAGNETOTRANSPORT IN WEYL SEMIMETALS

In this section, we study the magnetotransport properties of WSMs in three dimensions using a closed-form expression for magnetoconductivity Eq. (20) discussed in the previous section. For simplicity, we consider a single Weyl node described by the Hamiltonian $H = \chi \hbar v_F \mathbf{k} \cdot \boldsymbol{\sigma}$ which has isotropic linear dispersion, where $\chi = \pm 1$ are for the different chiralities of Weyl fermions and $\boldsymbol{\sigma}$ are the Pauli matrices.

A. Longitudinal magnetoconductivity

To investigate longitudinal magnetoconductivity $\sigma_{xx}(\mathbf{B})$ in WSMs, without loss of generality, we set the electric and magnetic field orientations as $\mathbf{E} = E_x \hat{x}$ and $\mathbf{B} = B_x \hat{x} + B_y \hat{y}$, respectively. Organizing terms in Eq. (20) in powers of μ and using Eq. (9),

$$\sigma_{xx} = q^2 \int \frac{d^3 k}{(2\pi)^3} \frac{\tau \left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right) D_{\mathbf{k}}^{-1}}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2} \left[\Sigma_{\mathbf{k}}^{(0)} + \Sigma_{\mathbf{k}}^{(1)} + \Sigma_{\mathbf{k}}^{(2)} \right], \quad (21)$$

where $\Sigma_{\mathbf{k}}^{(i)}$ is a sum of the terms that include i th order of μ . Due to the $D_{\mathbf{k}}^{-1}$ term in Eq. (21), it is difficult to obtain an analytic expression for σ_{xx} incorporating the full density of states correction. Therefore, to obtain a simple closed form result, we first assume $D_{\mathbf{k}}^{-1}$ as 1 in Eq. (21). We will discuss the correction beyond this

approximation later. Here, $\Sigma_{\mathbf{k}}^{(i)}$ are defined as

$$\begin{aligned} \Sigma_{\mathbf{k}}^{(0)} &= v_x^2 - 2 \frac{q}{\hbar c} v_x (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) |\mathbf{B}| \cos \Gamma \\ &\quad + \frac{q^2}{(\hbar c)^2} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}})^2 |\mathbf{B}|^2 \cos^2 \Gamma, \end{aligned} \quad (22a)$$

$$\begin{aligned} \Sigma_{\mathbf{k}}^{(1)} &= \frac{\mu}{c} \left[-v_x (\mathbf{v}_{\mathbf{k}} \times \mathbf{B})_x \right. \\ &\quad \left. + \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \times \mathbf{B})_x (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) |\mathbf{B}| \cos \Gamma \right], \end{aligned} \quad (22b)$$

$$\begin{aligned} \Sigma_{\mathbf{k}}^{(2)} &= \frac{\mu^2}{c^2} \left[(\mathbf{v}_{\mathbf{k}} \cdot \mathbf{B}) v_x |\mathbf{B}| \cos \Gamma \right. \\ &\quad - \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) |\mathbf{B}|^3 v_x \cos \Gamma \\ &\quad - \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{B}) (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) |\mathbf{B}|^2 \cos^2 \Gamma \\ &\quad \left. + \frac{q^2}{(\hbar c)^2} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}})^2 |\mathbf{B}|^4 \cos^2 \Gamma \right], \end{aligned} \quad (22c)$$

where Γ is the angle between \mathbf{E} and \mathbf{B} . The first term v_x^2 in Eq. (22a) gives a well known longitudinal conductivity in the absence of magnetic field: $\sigma_{xx}(\mathbf{B} = 0) = q^2 N_0 D \equiv \sigma_0$ where N_0 is the density of states at the Fermi energy and $D = v_F^2 \tau / d$ is the diffusion constant with $d = 3$.

Collecting terms that would give us non-zero contribution after momentum integral, Eq. (21) can be rewritten as

$$\begin{aligned} \sigma_{xx} &= q^2 \int \frac{d^3 k}{(2\pi)^3} \frac{\tau (-\frac{\partial f^{(0)}}{\partial \epsilon_{\mathbf{k}}})}{(1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2)} \\ &\times \left[v_x^2 + \frac{q^2}{(\hbar c)^2} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}})^2 |\mathbf{B}|^2 \cos^2 \Gamma \right. \\ &\quad \left. + \frac{\mu^2}{c^2} v_x^2 |\mathbf{B}|^2 \cos^2 \Gamma + \frac{\mu^2}{c^2} \frac{q^2}{(\hbar c)^2} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}})^2 |\mathbf{B}|^4 \cos^2 \Gamma \right]. \end{aligned} \quad (23)$$

The Berry curvature in an isotropic WSM is $\mathbf{\Omega}_{\mathbf{k}} = \chi \frac{\mathbf{k}}{2|\mathbf{k}|^3}$. Therefore, $\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}$ becomes $\chi v_F / (2k_F^2)$ where v_F and k_F are the Fermi velocity and Fermi wave vector, respectively. Note that all the surviving terms are even functions of magnetic field $|\mathbf{B}|$ and independent of χ . Here we emphasize that there are two kinds of magnetic field effects: the Lorentz force and anomalous velocity effect due to the Berry curvature. The terms that are related to the Lorentz force comes with a $\frac{\mu}{c} |\mathbf{B}|$ factor. On the other hand, the terms that are related to the Berry curvature comes with a $\frac{q}{\hbar c} |\mathbf{\Omega}_{\mathbf{k}}| |\mathbf{B}| = \frac{q^2}{(\hbar c)^2} \frac{1}{2k_F^2}$ factor.

Since the terms coupled with the magnetic field are proportional to either $\frac{\mu}{c} |\mathbf{B}|$ or $\frac{q}{\hbar c} |\mathbf{\Omega}_{\mathbf{k}}| |\mathbf{B}|$, we introduce the following dimensionless parameters:

$$b_\mu \equiv \frac{\mu}{c} |\mathbf{B}| \equiv \frac{q\tau v_F}{\hbar c k_F} |\mathbf{B}|, \quad (24a)$$

$$b_{BC} \equiv \frac{q}{\hbar c} |\mathbf{\Omega}_{\mathbf{k}}| |\mathbf{B}| \equiv \frac{q}{\hbar c} \frac{1}{2k_F^2} |\mathbf{B}|. \quad (24b)$$

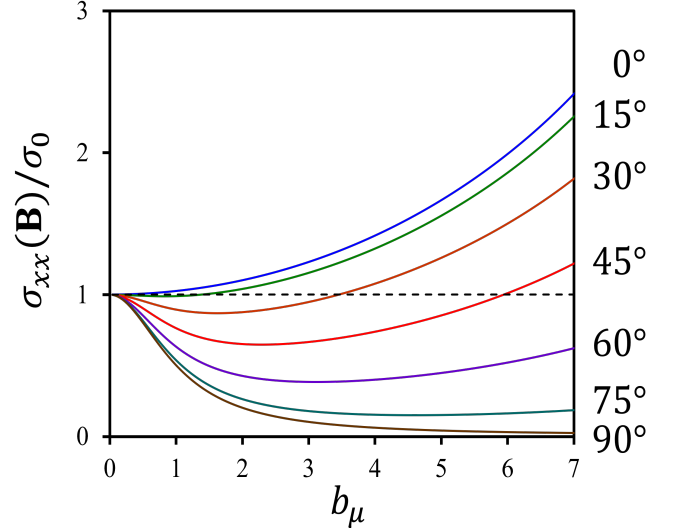


FIG. 2. Longitudinal conductivity as a function of b_μ at selected angles between \mathbf{E} and \mathbf{B} in WSMs for $k_F l = 4$.

Note that these two dimensionless parameters are related with each other as $b_\mu / b_{BC} = 2k_F l$, where $l = v_F \tau$ is the mean-free path. This gives us an important insight that the Lorentz force effect cannot be simply neglected when studying magnetotransport in topological materials within the semiclassical Boltzmann approach which is valid in $k_F l \gg 1$ regime.

Carrying out the momentum integral in Eq. (23), we obtain a longitudinal magnetoconductivity in WSMs for an arbitrary external magnetic field under the assumption that $D_{\mathbf{k}}^{-1} = 1$ (see Appendix B 1):

$$\sigma_{xx}(\mathbf{B}) = \sigma_0 \left[\frac{1}{1 + b_\mu^2} + \left(\frac{b_\mu^2}{1 + b_\mu^2} + 3b_{BC}^2 \right) \cos^2 \Gamma \right]. \quad (25)$$

Note that $\sigma_{xx}(\mathbf{B})$ in Eq. (25) is independent of χ , as b_{BC} comes with a power of two. Thus, the contribution from multiple degenerate Weyl nodes enters as a degeneracy factor when internode scatterings are neglected. Most of previous works for longitudinal magnetoconductivity in WSMs using Boltzmann transport theory reported $\sigma_{xx}(\Gamma) \sim \sigma_0 + \Delta \sigma \cos^2 \Gamma$ where $\Delta \sigma$ is the additional positive magnetoconductivity that scales quadratically in magnetic field [19–22]. Instead, Eq. (25) shows a non-monotonic behavior of magnetoconductivity in magnetic field due to the competition between the Berry curvature and Lorentz force depending on $k_F l$, as shown in Fig. 2. This result is consistent with the previous calculation for WSMs obtained by expanding the non-equilibrium distribution function in Fourier harmonics [22].

We now come back to the approximation we made: $D_{\mathbf{k}}^{-1} = 1$. Note that for weak magnetic fields, we could Taylor expand $D_{\mathbf{k}}^{-1}$ as

$$D_{\mathbf{k}}^{-1} = 1 + \frac{q}{\hbar c} (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}}) + \left(\frac{q}{\hbar c} \right)^2 (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}})^2 + \dots \quad (26)$$

We emphasize that earlier studies of magnetotransport also took the $D_{\mathbf{k}}$ correction into account but incompletely. For instance, Kim *et al.* [20] only took even terms in Taylor expanded $D_{\mathbf{k}}^{-1}$ in Eq. (26) which gave rise to an additional positive correction to magnetoconductivity described in Eq. (25). However, numerical calculations of the full longitudinal magnetoconductivity [Eq. (21)] show a reduced value compared to Eq. (25). The reduced magnetoconductivity is due to terms that are odd orders in $|\mathbf{B}|$ in Eq. (21) coupling with odd orders in $|\mathbf{B}|$ terms in the Taylor expanded $D_{\mathbf{k}}^{-1}$ in Eq. (26). As a result, the pairs of odd terms in $|\mathbf{B}|$ give rise to non-vanishing even terms in $|\mathbf{B}|$ which additionally give negative corrections to the magnetoconductivity.

By incorporating first three terms in Eq. (26), we obtain the longitudinal magnetoconductivity in WSMs up to quadratic order in b_{BC}^2 as

$$\sigma_{xx}(\mathbf{B}) \approx \frac{\sigma_0}{1 + b_{\mu}^2} \times \left\{ 1 + \frac{1}{5} b_{\text{BC}}^2 + \left[\frac{7}{5} b_{\text{BC}}^2 + b_{\mu}^2 \left(1 + \frac{8}{5} b_{\text{BC}}^2 \right) \right] \cos^2 \Gamma \right\}. \quad (27)$$

See Appendix B 1 for detailed derivations. This result is well matched with the previous work which focused on specific angles between applied electric and magnetic fields [22].

B. Planar Hall conductivity

To investigate the planar Hall conductivity in WSMs, we again set the electric and magnetic field orientations as $\mathbf{E} = E_x \hat{x}$ and $\mathbf{B} = B_x \hat{x} + B_y \hat{y}$, respectively. Neglecting terms that would give zero contribution to conductivity, Eq. (20) gives the following form of the planar Hall conductivity $\sigma_{yx}(\mathbf{B})$ assuming $D_{\mathbf{k}}^{-1} = 1$ (see Appendix B 2):

$$\sigma_{yx}(\mathbf{B}) = \sigma_0 \left[\left(\frac{b_{\mu}^2}{1 + b_{\mu}^2} + 3b_{\text{BC}}^2 \right) \sin \Gamma \cos \Gamma \right]. \quad (28)$$

Note that $\sigma_{yx}(\mathbf{B})$ in Eq. (28) is independent of χ . Equation (28) is the analytic form of the planar Hall conductivity in WSMs for an arbitrary angle of the applied magnetic field $|\mathbf{B}|$. The angle dependence of the planar Hall conductivity is well matched with the previous works $\sigma_{yx}(\Gamma) \sim \sin \Gamma \cos \Gamma$ [21, 30–35] but the field dependence shows an additional contribution from the Lorentz force in addition to a quadratic field dependence due to the Berry curvature. As shown in Fig 3, the planar Hall conductivity shows different $|\mathbf{B}|$ dependence at different $k_F l$ regimes. For large $k_F l$, the planar Hall conductivity roughly increases with $|\mathbf{B}|$ quadratically at low $|\mathbf{B}|$ field and saturates at high $|\mathbf{B}|$ field. For low $k_F l$ regime, the planar Hall conductivity shows $|\mathbf{B}|^2$ dependence with no sign of saturation in a broad range of magnetic field as reported in the previous studies [21].

We now come back to the approximation we made: $D_{\mathbf{k}}^{-1} = 1$. Again, including the Taylor expanded $D_{\mathbf{k}}^{-1}$ in

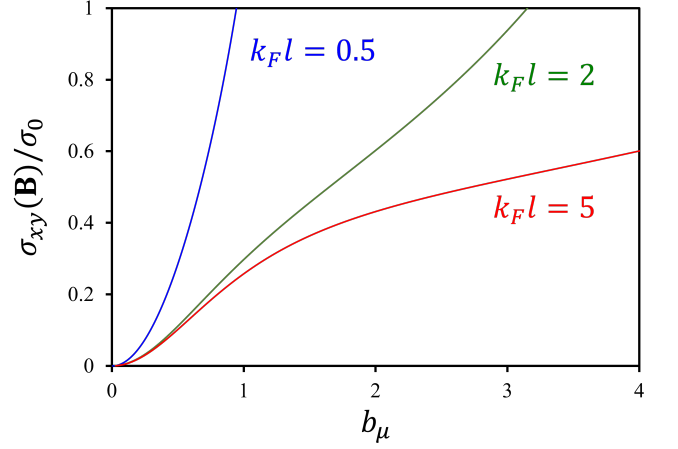


FIG. 3. Planar Hall conductivity as a function of b_{μ} in WSMs at $\Gamma = \frac{\pi}{4}$ for $k_F l = 0.5, 2, 5$.

Eq. (26), we obtain the planar Hall magnetoconductivity in WSMs as

$$\sigma_{yx}(\mathbf{B}) \approx \sigma_0 \left[\frac{b_{\mu}^2}{1 + b_{\mu}^2} \left(1 + \frac{1}{5} b_{\text{BC}}^2 \right) + \frac{7}{5} b_{\text{BC}}^2 \right] \sin \Gamma \cos \Gamma. \quad (29)$$

See Appendix B 2 for detailed derivations.

C. Hall conductivity

To investigate the Hall conductivity in WSMs, we set the electric and magnetic field orientations as $\mathbf{E} = E_x \hat{x}$ and $\mathbf{B} = B_y \hat{y}$, respectively. Then Eq. (20) gives the following form of Hall conductivity $\sigma_{zx}(\mathbf{B})$ assuming $D_{\mathbf{k}}^{-1} = 1$ (see Appendix B 3):

$$\sigma_{zx}(\mathbf{B}) = \sigma_0 \left(\frac{b_{\mu}}{1 + b_{\mu}^2} \right). \quad (30)$$

Note that this result is identical to the conventional magnetotransport result. This implies that there is no anomalous velocity effect in the Hall conductivity.

We now come back to the approximation we made: $D_{\mathbf{k}}^{-1} = 1$. Again, including the Taylor expanded $D_{\mathbf{k}}^{-1}$ in Eq. (26), we can obtain the Hall magnetoconductivity in WSMs as

$$\sigma_{zx}(\mathbf{B}) \approx \sigma_0 \frac{b_{\mu}}{1 + b_{\mu}^2} \left(1 + \frac{1}{5} b_{\text{BC}}^2 \right). \quad (31)$$

See Appendix B 3 for detailed derivations.

D. Conductivity and resistivity tensors

Combining the previous results of magnetoconductivity in WSMs, we obtain the following conductivity tensor

under $\mathbf{B} = B_x \hat{x} + B_y \hat{y}$ with $D_{\mathbf{k}}^{-1} = 1$:

$$\boldsymbol{\sigma}(\mathbf{B}) = \sigma_0 \begin{bmatrix} \frac{1}{1+b_\mu^2} + (\frac{b_\mu^2}{1+b_\mu^2} + 3b_{\text{BC}}^2) \cos^2 \Gamma & (\frac{b_\mu^2}{1+b_\mu^2} + 3b_{\text{BC}}^2) \sin \Gamma \cos \Gamma & -\frac{b_\mu}{1+b_\mu^2} \sin \Gamma \\ (\frac{b_\mu^2}{1+b_\mu^2} + 3b_{\text{BC}}^2) \sin \Gamma \cos \Gamma & \frac{1}{1+b_\mu^2} + (\frac{b_\mu^2}{1+b_\mu^2} + 3b_{\text{BC}}^2) \sin^2 \Gamma & \frac{b_\mu}{1+b_\mu^2} \cos \Gamma \\ \frac{b_\mu}{1+b_\mu^2} \sin \Gamma & -\frac{b_\mu}{1+b_\mu^2} \cos \Gamma & \frac{1}{1+b_\mu^2} \end{bmatrix}, \quad (32)$$

where Γ is the angle between applied electric and magnetic fields. Since the resistivity tensor $\boldsymbol{\rho}(\mathbf{B})$ is the inverse of the conductivity tensor $\boldsymbol{\sigma}(\mathbf{B})$, we obtain $\boldsymbol{\rho}(\mathbf{B})$ in the following form:

$$\boldsymbol{\rho}(\mathbf{B}) = \rho_0 \begin{bmatrix} \frac{1+3b_{\text{BC}}^2 \sin^2 \Gamma}{1+3b_{\text{BC}}^2} & -\frac{3b_{\text{BC}}^2 \sin \Gamma \cos \Gamma}{1+3b_{\text{BC}}^2} & b_\mu \sin \Gamma \\ -\frac{3b_{\text{BC}}^2 \sin \Gamma \cos \Gamma}{1+3b_{\text{BC}}^2} & \frac{1+3b_{\text{BC}}^2 \cos^2 \Gamma}{1+3b_{\text{BC}}^2} & -b_\mu \cos \Gamma \\ -b_\mu \sin \Gamma & b_\mu \cos \Gamma & 1 \end{bmatrix}, \quad (33)$$

where $\rho_0 = \rho_{xx}(\mathbf{B} = 0) = \sigma_0^{-1}$. Note that although both the Lorentz force and the Berry curvature induced terms are present in $\sigma_{ij}(\mathbf{B})$, the Lorentz force induced terms do not appear in the resistivity $\rho_{ij}(\mathbf{B})$ where $i, j = x, y$. This result agrees with the previous one reporting that $\rho_{xx} = \rho_{\parallel} - \Delta\rho \cos^2 \Gamma$, $\rho_{xy} = -\Delta\rho \sin \Gamma \cos \Gamma$ where ρ_{\parallel} (ρ_{\perp}) is the resistivity in longitudinal (transverse) magnetic field and $\Delta\rho = \rho_{\perp} - \rho_{\parallel} = 3b_{\text{BC}}^2/(1 + 3b_{\text{BC}}^2)$ is the resistivity anisotropy [30, 36]. For the conductivity and resistivity tensors including the Taylor expanded $D_{\mathbf{k}}^{-1}$, see Appendix B 5.

IV. CONCLUSION

In this work, we presented a closed-form expression for the magnetoconductivity using the semiclassical magne-

totransport theory that fully incorporates the Berry curvature and the Lorentz force effects. We then applied this formula to WSMs and obtained analytic expressions for the longitudinal, planar Hall and Hall conductivities in terms of dimensionless parameters b_μ and b_{BC} which are normalized magnetic fields associated with the Lorentz force and the Berry curvature, respectively. From these results, we showed a non-monotonic field dependence in the longitudinal and planar Hall conductivities depending on $k_F l$. Furthermore, we clearly demonstrated that although the Lorentz force effect is manifested in the planar Hall conductivity, its contribution vanishes in the planar Hall resistivity.

ACKNOWLEDGMENTS

This work was supported by the National Research Foundation of Korea (NRF) grant funded by the Korea government (MSIT) (Grant No. 2018R1A2B6007837) and Creative-Pioneering Researchers Program through Seoul National University (SNU).

-
- [1] H.-J. Kim, K.-S. Kim, J.-F. Wang, M. Sasaki, N. Satoh, A. Ohnishi, M. Kitaura, M. Yang and L. Li, Dirac versus Weyl Fermions in Topological Insulators: Adler-Bell-Jackiw Anomaly in Transport Phenomena, *Phys. Rev. Lett.* **111**, 246603 (2013).
 - [2] X. Huang, L. Zhao, Y. Long, P. Wang, D. Chen, Z. Yang, H. Liang, M. Xue, H. Weng, Z. Fang, X. Dai and G. Chen, Observation of the Chiral-Anomaly-Induced Negative Magnetoresistance in 3D Weyl Semimetal TaAs, *Phys. Rev. X* **5**, 031023 (2015).
 - [3] J. Xiong, S. Kushwaha, T. Liang, J. Krizan, M. Hirschberger, W. Wang, R. Cava and N. Ong, Evidence for the chiral anomaly in the Dirac semimetal Na₃Bi, *Science* **350**, 413 (2015).
 - [4] C.-Z. Li, L.-X. Wang, H. Liu, J. Wang, Z.-M. Liao and D.-P. Yu, Giant negative magnetoresistance induced by the chiral anomaly in individual Cd₃As₂ nanowires, *Nature Communications* **6**, 10137 (2015).
 - [5] Q. Li, D. E. Kharzeev, C. Zhang, Y. Huang, I. Pletikosić, A. V. Fedorov, R. D. Zhong, J. A. Schneeloch, G. D. Gu and T. Valla, Chiral magnetic effect in ZrTe₅, *Nature Physics* **12**, 550 (2016).
 - [6] C. Zhang, S.-Y. Xu, I. Belopolski, Z. Yuan, Z. Lin, B. Tong, G. Bian, N. Alidoust, C.-C. Lee, S.-M. Huang, T. Chang, G. Chang, C.-H. Hsu, H. Jeng, M. Neupane, D. Sanchez, H. Zheng, J. Wang, H. Lin, C. Zhang, H.-Z. Lu, S. Shen, T. Neupert, M. Z. Hasan and S. Jia, Signatures of the Adler-Bell-Jackiw chiral anomaly in a Weyl fermion semimetal, *Nature Communications* **7**, 10735 (2016).
 - [7] H. Li, H. He, H.-Z. Lu, H. Zhang, H. Liu, R. Ma, Z. Fan, S.-Q. Shen and J. Wang, Negative magnetoresistance in Dirac semimetal Cd₃As₂, *Nature Communications* **7**, 10301 (2016).

- [8] C. Zhang, E. Zhang, W. Wang, Y. Liu, Z.-G. Chen, S. Lu, S. Liang, J. Cao, X. Yuan, L. Tang, Q. Li, C. Zhou, T. Gu, Y. Wu, J. Zou and F. Xiu, Room-temperature chiral charge pumping in Dirac semimetals, *Nature Communications* **8**, 13741 (2017).
- [9] J. Wang, H. Li, C. Chang, K. He, J. S. Lee, H. Lu, Y. Sun, X. Ma, N. Samarth, S. Shen, Q. Xue, M. Xie and M. Chan, Anomalous anisotropic magnetoresistance in topological insulator films, *Nano Research* **5**, 739 (2012).
- [10] H. T. He, H. C. Liu, B. K. Li, X. Guo, Z. J. Xu, M. H. Xie and J. N. Wang, Disorder-induced linear magnetoresistance in (221) topological insulator Bi_2Se_3 films, *Applied Physics Letters* **103**, 031606 (2013).
- [11] L.-X. Wang, Y. Yan, L. Zhang, Z.-M. Liao, H.-C. Wu and D.-P. Yu, Zeeman effect on surface electron transport in topological insulator Bi_2Se_3 nanoribbons, *Nanoscale* **7**, 16687 (2015).
- [12] S. Wiedmann, A. Jost, B. Fauqué, J. van Dijk, M. J. Meijer, T. Khouri, S. Pezzini, S. Grauer, S. Schreyeck, C. Brüne, H. Buhmann, L. W. Molenkamp and N. E. Hussey, Anisotropic and strong negative magnetoresistance in the three-dimensional topological insulator Bi_2Se_3 , *Phys. Rev. B* **94**, 081302(R) (2016).
- [13] F. Arnold, C. Shekhar, S.-C. Wu, Y. Sun, R. D. dos Reis, N. Kumar, M. Naumann, M. O. Ajeesh, M. Schmidt, A. G. Grushin, J. H. Bardarson, M. Baenitz, D. Sokolov, H. Borrmann, M. Nicklas, C. Felser, E. Hassinger and B. Yan, Negative magnetoresistance without well-defined chirality in the Weyl semimetal TaP, *Nature Communications* **7**, 11615 (2016).
- [14] O. Breunig, Z. Wang, A. A. Taskin, J. Lux, A. Rosch and Y. Ando, Gigantic negative magnetoresistance in the bulk of a disordered topological insulator, *Nature Communications* **8**, 15545 (2017).
- [15] B. A. Assaf, T. Phuphachong, E. Kampert, V. V. Volobuev, P. S. Mandal, J. Sánchez-Barriga, O. Rader, G. Bauer, G. Springholz, L. A. de Vaultier and Y. Guldner, Negative Longitudinal Magnetoresistance from the Anomalous $N = 0$ Landau Level in Topological Materials, *Phys. Rev. Lett.* **119**, 106602 (2017).
- [16] H. Nielsen and M. Ninomiya, The Adler-Bell-Jackiw anomaly and Weyl fermions in a crystal, *Physics Letters B* **130**, 389 (1983).
- [17] D. T. Son and B. Z. Spivak, Chiral anomaly and classical negative magnetoresistance of Weyl metals, *Phys. Rev. B* **88**, 104412 (2013).
- [18] A. Sekine, D. Culcer and A. H. MacDonald, Quantum kinetic theory of the chiral anomaly, *Phys. Rev. B* **96**, 235134 (2017).
- [19] X. Dai, Z. Du and H.-Z. Lu, Negative Magnetoresistance without Chiral Anomaly in Topological Insulators, *Phys. Rev. Lett.* **119**, 166601 (2017).
- [20] K.-S. Kim, H.-J. Kim and M. Sasaki, Boltzmann equation approach to anomalous transport in a Weyl metal, *Phys. Rev. B* **89**, 195137 (2014).
- [21] S. Nandy, G. Sharma, A. Taraphder and S. Tewari, Chiral Anomaly as the Origin of the Planar Hall Effect in Weyl Semimetals, *Phys. Rev. Lett.* **119**, 176804 (2017).
- [22] M. Imran and S. Hershfield, Berry curvature force and Lorentz force comparison in the magnetotransport of Weyl semimetals, *Phys. Rev. B* **98**, 205139 (2018).
- [23] A. Johansson, J. Henk and I. Mertig, Chiral anomaly in type-I Weyl semimetals: Comprehensive analysis within a semiclassical Fermi surface harmonics approach, *Phys. Rev. B* **99**, 075114 (2019).
- [24] J. Suh, S. Park and H. Min, Semiclassical Boltzmann magnetotransport theory in anisotropic systems with a nonvanishing Berry curvature, arXiv:2110.08816 (2021).
- [25] D. Xiao, J. Shi and Q. Niu, Berry Phase Correction to Electron Density of States in Solids, *Phys. Rev. Lett.* **95**, 137204 (2005).
- [26] N. W. Ashcroft and N. D. Mermin, *Solid State Physics*, Brooks Cole (1976).
- [27] J. M. Ziman, *Electrons and phonons: the theory of transport phenomena in solids*, International series of monographs on physics, Clarendon Press, Oxford (1960).
- [28] D. Xiao, M.-C. Chang and Q. Niu, Berry phase effects on electronic properties, *Rev. Mod. Phys.* **82**, 1959 (2010).
- [29] R. B. Atencia, Q. Niu and D. Culcer, Semiclassical response of disordered conductors: Extrinsic carrier velocity and spin and field-corrected collision integral, *Phys. Rev. Research* **4**, 013001 (2022).
- [30] A. A. Burkov, Giant planar Hall effect in topological metals, *Phys. Rev. B* **96**, 041110(R) (2017).
- [31] P. Li, C. H. Zhang, J. W. Zhang, Y. Wen and X. X. Zhang, Giant planar Hall effect in the Dirac semimetal $\text{ZrTe}_{5-\delta}$, *Phys. Rev. B* **98**, 121108(R) (2018).
- [32] D. D. Liang, Y. J. Wang, W. L. Zhen, J. Yang, S. R. Weng, X. Yan, Y. Y. Han, W. Tong, W. K. Zhu, L. Pi and C. J. Zhang, Origin of planar Hall effect in type-II Weyl semimetal MoTe_2 , *AIP Advances* **9**, 055015 (2019).
- [33] Q. Liu, F. Fei, B. Chen, X. Bo, B. Wei, S. Zhang, M. Zhang, F. Xie, M. Naveed, X. Wan, F. Song and B. Wang, Nontopological origin of the planar Hall effect in the type-II Dirac semimetal NiTe_2 , *Phys. Rev. B* **99**, 155119 (2019).
- [34] D. Ma, H. Jiang, H. Liu and X. C. Xie, Planar Hall effect in tilted Weyl semimetals, *Phys. Rev. B* **99**, 115121 (2019).
- [35] Z. Li, T. Xiao, R. Zou, J. Li, Y. Zhang, Y. Zeng, M. Zhou, J. Zhang and W. Wu, Planar Hall effect in PtSe_2 , *Journal of Applied Physics* **127**, 054306 (2020).
- [36] J.-P. Jan, Galvanomagnetic and Thermomagnetic Effects in Metals, vol. 5 of *Solid State Physics*, 1–96, Academic Press (1957).

Appendix A: Derivation of the nonequilibrium distribution function

Here we go through a detailed derivation of the nonequilibrium distribution function. Let us start with Eq. (12) in the main text:

$$\mathbf{G} = \mathbf{G}_0 - \frac{q\tau}{c}(\mathbf{B} \times \mathbf{M}^{-1}\mathbf{G}), \quad (\text{A1})$$

where $\mathbf{M}_{ij}^{-1} = \frac{1}{\hbar} \frac{\partial \tilde{v}_{\mathbf{k},i}}{\partial k_i}$ is the inverse mass tensor and

$$\mathbf{G}_0 = q\tau \left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right) \mathbf{E}. \quad (\text{A2})$$

To solve \mathbf{G} in Eq. (A1), note that Eq. (A1) is given by the following self-consistent form for a vector \mathbf{x} :

$$\mathbf{x} = \mathbf{a} + (M\mathbf{x}) \times \mathbf{b}, \quad (\text{A3})$$

where \mathbf{a} and \mathbf{b} are vectors and M is a matrix. Then Eq. (A3) can be rewritten as

$$x_i = a_i + \sum_{jk} \epsilon_{ijk} (M\mathbf{x})_j b_k = a_i + \sum_{jk} F_{ij} M_{jk} x_k, \quad (\text{A4})$$

where $F_{ij} = \sum_k \epsilon_{ijk} b_k$. Thus, we have

$$\mathbf{x} = \mathbf{a} + FM\mathbf{x} = (1 - FM)^{-1} \mathbf{a}. \quad (\text{A5})$$

Using the above result Eq. (A5), we obtain \mathbf{G} as the following form:

$$\mathbf{G} = q\tau \left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right) \left(\mathbb{1} + \frac{q\tau}{c} \mathbf{F} M^{-1} \right)^{-1} \mathbf{E}, \quad (\text{A6})$$

where $\mathbf{F}_{ij} = \sum_k \epsilon_{ijk} B_k$ is the magnetic field strength tensor. Finally, the nonequilibrium distribution function $g_{\mathbf{k}} = \tilde{v}_{\mathbf{k}} \cdot \mathbf{G}$ is given by

$$g_{\mathbf{k}} = q\tau \left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right) \tilde{v}_{\mathbf{k}} \cdot \left[\left(\mathbb{1} + \frac{q\tau}{c} \mathbf{F} M^{-1} \right)^{-1} \mathbf{E} \right]. \quad (\text{A7})$$

The mobility tensor is defined as

$$\tilde{\mu}_{ij} = e\tau \mathbf{M}_{ij}^{-1}, \quad (\text{A8})$$

which is in general a non-diagonal matrix. For a system with an isotropic energy dispersion in the absence of a magnetic field, the mobility tensor is given by a scalar multiple of an identity matrix. For simplicity, we assume that the mobility tensor is set to a constant μ . Then, we can rewrite Eq. (A1) as

$$\mathbf{G} = \mathbf{G}_0 - \frac{\mu}{c} \mathbf{B} \times \mathbf{G}. \quad (\text{A9})$$

Note that Eq. (A9) is given by the following self-consistent form for a vector \mathbf{x} :

$$\mathbf{x} = \mathbf{a} + \mathbf{x} \times \mathbf{b}, \quad (\text{A10})$$

where \mathbf{a} and \mathbf{b} are vectors. Then Eq. (A10) can be rewritten as

$$\begin{aligned} x_i &= a_i + \sum_{jk} \epsilon_{ijk} x_j b_k \\ &= a_i + \sum_{jk} \epsilon_{ijk} \left(a_j + \sum_{lm} \epsilon_{jlm} x_l b_m \right) b_k \\ &= a_i + \sum_{jk} \epsilon_{ijk} a_j b_k + \sum_{jklm} (\delta_{im} \delta_{kl} - \delta_{il} \delta_{km}) x_l b_m b_k \\ &= a_i + (\mathbf{a} \times \mathbf{b})_i + (\mathbf{x} \cdot \mathbf{b}) b_i - b^2 x_i \\ &= \frac{1}{1+b^2} [a_i + (\mathbf{a} \times \mathbf{b})_i + (\mathbf{a} \cdot \mathbf{b}) b_i]. \end{aligned} \quad (\text{A11})$$

Here, we used $\sum_j \epsilon_{ijk} \epsilon_{mjl} = \delta_{im} \delta_{kl} - \delta_{il} \delta_{km}$ and $\mathbf{x} \cdot \mathbf{b} = (\mathbf{a} + \mathbf{x} \times \mathbf{b}) \cdot \mathbf{b} = \mathbf{a} \cdot \mathbf{b}$. Thus, we have

$$\mathbf{x} = \frac{1}{1+b^2} [\mathbf{a} + (\mathbf{a} \times \mathbf{b}) + (\mathbf{a} \cdot \mathbf{b}) \mathbf{b}]. \quad (\text{A12})$$

Using the result of Eq. (A12), we therefore obtain \mathbf{G} as the following form:

$$\mathbf{G} = q\tau \left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right) \frac{\mathbf{E} + \frac{\mu}{c} \mathbf{E} \times \mathbf{B} + \frac{\mu^2}{c^2} (\mathbf{E} \cdot \mathbf{B}) \mathbf{B}}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2}. \quad (\text{A13})$$

Note that Eq. (A6) is reduced to Eq. (A13) when the mobility tensor is given by $\tilde{\mu}_{ij} = \mu \delta_{ij}$.

Finally, the nonequilibrium distribution function $g_{\mathbf{k}} = \tilde{\mathbf{v}}_{\mathbf{k}} \cdot \mathbf{G}$ is given by

$$g = q\tau \left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right) \tilde{\mathbf{v}}_{\mathbf{k}} \cdot \frac{\mathbf{E} + \frac{\mu}{c} \mathbf{E} \times \mathbf{B} + \frac{\mu^2}{c^2} (\mathbf{E} \cdot \mathbf{B}) \mathbf{B}}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2}. \quad (\text{A14})$$

Appendix B: Magnetoconductivity of Weyl semimetals

In this section, we derive the magnetoconductivity of Weyl semimetals including the Taylor expanded $D_{\mathbf{k}}^{-1}$. Here we set the magnetic field orientation as $\mathbf{B} = B_x \hat{x} + B_y \hat{y}$.

1. Longitudinal magnetoconductivity

Here we go through a detailed derivation of the longitudinal magnetoconductivity. Let us start with Eq. (21) in the main text:

$$\sigma_{xx} = q^2 \int \frac{d^3 k}{(2\pi)^3} \frac{\tau \left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right) D_{\mathbf{k}}^{-1}}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2} \left[\Sigma_{\mathbf{k}}^{(0)} + \Sigma_{\mathbf{k}}^{(1)} + \Sigma_{\mathbf{k}}^{(2)} \right] \equiv \sigma_{xx}^{(0)} + \sigma_{xx}^{(1)} + \sigma_{xx}^{(2)}, \quad (\text{B1})$$

where $\Sigma_{\mathbf{k}}^{(i)}$ is a sum of the terms that include i th order of μ described in Eq. (22) in the main text which corresponds to conductivity of $\sigma_{xx}^{(i)}$ respectively. Inserting the Taylor expanded density of states correction

$$D_{\mathbf{k}}^{-1} = 1 + \frac{q}{\hbar c} (\mathbf{B} \cdot \boldsymbol{\Omega}_{\mathbf{k}}) + \left(\frac{q}{\hbar c} \right)^2 (\mathbf{B} \cdot \boldsymbol{\Omega}_{\mathbf{k}})^2 + \dots \quad (\text{B2})$$

to Eq. (B1) and focusing on $\Sigma_{\mathbf{k}}^{(0)}$, $\sigma_{xx}^{(0)}$ yields

$$\sigma_{xx}^{(0)} = q^2 \int \frac{d^3 k}{(2\pi)^3} \frac{\tau \delta(k - k_F)}{\hbar v_F} \frac{1 + \frac{q}{\hbar c} (\mathbf{B} \cdot \boldsymbol{\Omega}_{\mathbf{k}}) + \left(\frac{q}{\hbar c} \right)^2 (\mathbf{B} \cdot \boldsymbol{\Omega}_{\mathbf{k}})^2}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2} \left[v_x^2 - \frac{2q}{\hbar c} v_x (\mathbf{v}_{\mathbf{k}} \cdot \boldsymbol{\Omega}_{\mathbf{k}}) |\mathbf{B}| \cos \Gamma + \frac{q^2}{(\hbar c)^2} (\mathbf{v}_{\mathbf{k}} \cdot \boldsymbol{\Omega}_{\mathbf{k}})^2 |\mathbf{B}|^2 \cos^2 \Gamma \right], \quad (\text{B3})$$

where we replaced $\left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right) = \frac{\delta(k - k_F)}{\hbar v_F}$ for zero temperature. Expanding and throwing away terms that will give zero contribution after the momentum integral due to odd order in k_i ($i = x, y, z$), we are left with the following angular integral after switching to spherical coordinates then integrating k out:

$$\sigma_{xx}^{(0)} = q^2 \int_0^{2\pi} d\phi \int_0^\pi d\theta \frac{k_F^2 \sin \theta}{(2\pi)^3} \frac{\tau I^{(0)}(\theta, \phi)}{\hbar v_F (1 + b_\mu^2)}, \quad (\text{B4})$$

where

$$\begin{aligned} I^{(0)}(\theta, \phi) = v_F^2 & \left[\sin^2 \theta \cos^2 \phi + b_{\text{BC}}^2 \cos^2 \Gamma - 2b_{\text{BC}}^2 \cos^2 \Gamma \sin^2 \theta \cos^2 \phi \right. \\ & + b_{\text{BC}}^2 (\cos^2 \Gamma \sin^4 \theta \cos^4 \phi + \sin^2 \Gamma \sin^4 \theta \cos^2 \phi \sin^2 \phi) \\ & \left. + b_{\text{BC}}^4 (\cos^4 \Gamma \sin^2 \theta \cos^2 \phi + \cos^2 \Gamma \sin^2 \Gamma \sin^2 \theta \sin^2 \phi) \right]. \end{aligned} \quad (\text{B5})$$

Finally, carrying out the angular integral leads to

$$\sigma_{xx}^{(0)} = \frac{\sigma_0}{1 + b_\mu^2} \left[1 + \frac{b_{\text{BC}}^2}{5} (8 \cos^2 \Gamma + \sin^2 \Gamma) + b_{\text{BC}}^4 \cos^2 \Gamma \right], \quad (\text{B6})$$

where $\sigma_0 = q^2 \left(\frac{k_F^2}{2\pi^2 \hbar v_F} \right) \left(\frac{\tau v_F}{3} \right) = q^2 N_0 D$ is the longitudinal magnetoconductivity in the absence of magnetic field.

Focusing now on $\Sigma_{\mathbf{k}}^{(1)}$, $\sigma_{xx}^{(1)}$ yields

$$\sigma_{xx}^{(1)} = q^2 \int \frac{d^3 k}{(2\pi)^3} \frac{\tau \delta(k - k_F)}{\hbar v_F} \frac{1 + \frac{q}{\hbar c} (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}}) + \left(\frac{q}{\hbar c} \right)^2 (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}})^2}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2} \frac{\mu}{c} \left[-v_x (\mathbf{v}_{\mathbf{k}} \times \mathbf{B})_x + \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \times \mathbf{B})_x (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) |\mathbf{B}| \cos \Gamma \right]. \quad (\text{B7})$$

The above whole expression vanishes after the momentum integral, because $(\mathbf{v}_{\mathbf{k}} \times \mathbf{B})_x = v_y B_z - v_z B_y = -v_z B_y$ as $B_z = 0$. This will lead to a single order in v_z in every term in the integrand therefore result in zero after integration.

Finally, focusing on $\Sigma_{\mathbf{k}}^{(2)}$, $\sigma_{xx}^{(2)}$ yields

$$\begin{aligned} \sigma_{xx}^{(2)} = q^2 \int \frac{d^3 k}{(2\pi)^3} \frac{\tau \delta(k - k_F)}{\hbar v_F} \frac{1 + \frac{q}{\hbar c} (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}}) + \left(\frac{q}{\hbar c} \right)^2 (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}})^2}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2} & \left[(\mathbf{v}_{\mathbf{k}} \cdot \mathbf{B}) v_x |\mathbf{B}| \cos \Gamma - \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) |\mathbf{B}|^3 v_x \cos \Gamma \right. \\ & \left. - \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{B}) (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) |\mathbf{B}|^2 \cos^2 \Gamma - \frac{q^2}{(\hbar c)^2} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}})^2 |\mathbf{B}|^4 \cos^2 \Gamma \right]. \end{aligned} \quad (\text{B8})$$

Simplifying the product of the Taylor expanded $D_{\mathbf{k}}^{-1}$ and terms in the square bracket while again, keeping only the non-zero contribution, we are left with the following angular integral after switching to spherical coordinates then integrating k out:

$$\sigma_{xx}^{(2)} = q^2 \int_0^{2\pi} d\phi \int_0^\pi d\theta \frac{k_F^2 \sin \theta}{(2\pi)^3} \frac{\tau I^{(2)}(\theta, \phi)}{\hbar v_F (1 + b_\mu^2)}, \quad (\text{B9})$$

where

$$\begin{aligned} I^{(2)}(\theta, \phi) = v_F^2 b_\mu^2 & \left[\sin^2 \theta \cos^2 \phi \cos^2 \Gamma + b_{\text{BC}}^2 (\cos^2 \Gamma - \cos^2 \Gamma \sin^2 \theta \cos^2 \phi - \sin^2 \theta \cos^2 \phi \cos^4 \Gamma \right. \\ & - \sin^2 \theta \sin^2 \phi \sin^2 \Gamma \cos^2 \Gamma + \sin^4 \theta \cos^4 \phi \cos^4 \Gamma + 3 \sin^4 \theta \cos^2 \phi \sin^2 \phi \cos^2 \Gamma \sin^2 \Gamma) \\ & \left. + b_{\text{BC}}^4 (\sin^2 \theta \cos^2 \phi \cos^4 \Gamma + \sin^2 \theta \sin^2 \phi \sin^2 \Gamma \cos^2 \Gamma) \right]. \end{aligned} \quad (\text{B10})$$

Finally, carrying out the angular integral leads to

$$\sigma_{xx}^{(2)} = \sigma_0 \frac{b_\mu^2}{1 + b_\mu^2} \left(\cos^2 \Gamma + \frac{8}{5} b_{\text{BC}}^2 \cos^2 \Gamma + b_{\text{BC}}^4 \cos^2 \Gamma \right). \quad (\text{B11})$$

Adding up the $\sigma_{xx}^{(i)}$ s, we have

$$\sigma_{xx} = \frac{\sigma_0}{1 + b_\mu^2} \left[1 + \frac{b_{\text{BC}}^2}{5} (8 \cos^2 \Gamma + \sin^2 \Gamma) + b_{\text{BC}}^4 \cos^2 \Gamma + b_\mu^2 \left(\cos^2 \Gamma + \frac{8}{5} b_{\text{BC}}^2 \cos^2 \Gamma + b_{\text{BC}}^4 \cos^2 \Gamma \right) \right]. \quad (\text{B12})$$

2. Planar Hall conductivity

Here we go through a detailed derivation of the planar Hall conductivity. Starting with Eq. (20) in the main text for $d = 3$, we again express it in powers of μ while using the definition for $\tilde{\mathbf{v}}_{\mathbf{k}}$. We then obtain,

$$\sigma_{yx} = q^2 \int \frac{d^3 k}{(2\pi)^3} \frac{\tau \left(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}} \right) D_{\mathbf{k}}^{-1}}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2} \left[\Sigma_{\mathbf{k}}^{(0)} + \Sigma_{\mathbf{k}}^{(1)} + \Sigma_{\mathbf{k}}^{(2)} \right] \equiv \sigma_{yx}^{(0)} + \sigma_{yx}^{(1)} + \sigma_{yx}^{(2)}, \quad (\text{B13})$$

where

$$\Sigma_{\mathbf{k}}^{(0)} = v_y v_x - \frac{q}{\hbar c} v_y (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) |\mathbf{B}| \cos \Gamma - \frac{q}{\hbar c} v_x (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) |\mathbf{B}| \sin \Gamma + \left(\frac{q}{\hbar c} \right)^2 (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}})^2 |\mathbf{B}|^2 \cos \Gamma \sin \Gamma, \quad (\text{B14a})$$

$$\Sigma_{\mathbf{k}}^{(1)} = \frac{\mu}{c} \left[-v_y (\mathbf{v}_{\mathbf{k}} \times \mathbf{B})_x + \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) (\mathbf{v}_{\mathbf{k}} \times \mathbf{B})_x |\mathbf{B}| \sin \Gamma \right], \quad (\text{B14b})$$

$$\begin{aligned} \Sigma_{\mathbf{k}}^{(2)} = \frac{\mu^2}{c^2} & \left[(\mathbf{v}_{\mathbf{k}} \cdot \mathbf{B}) v_y |\mathbf{B}| \cos \Gamma - \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) |\mathbf{B}|^3 v_y \cos \Gamma - \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{B}) (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) |\mathbf{B}|^2 \cos \Gamma \sin \Gamma \right. \\ & \left. + \left(\frac{q}{\hbar c} \right)^2 (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}})^2 |\mathbf{B}|^4 \cos \Gamma \sin \Gamma \right], \end{aligned} \quad (\text{B14c})$$

each corresponds to planar Hall conductivity of $\sigma_{yx}^{(i)}$ respectively. Inserting the Taylor expanded density of states correction

$$D_{\mathbf{k}}^{-1} = 1 + \frac{q}{\hbar c} (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}}) + \left(\frac{q}{\hbar c}\right)^2 (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}})^2 + \dots \quad (\text{B15})$$

to Eq. (B13) and focusing on $\Sigma_{\mathbf{k}}^{(0)}$, $\sigma_{yx}^{(0)}$ yields

$$\sigma_{yx}^{(0)} = q^2 \int \frac{d^3k}{(2\pi)^3} \frac{\tau \delta(k - k_F)}{\hbar v_F} \frac{1 + \frac{q}{\hbar c} (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}}) + \left(\frac{q}{\hbar c}\right)^2 (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}})^2}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2} \left[v_y v_x - \frac{q}{\hbar c} v_y (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) |\mathbf{B}| \cos \Gamma - \frac{q}{\hbar c} v_x (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) |\mathbf{B}| \sin \Gamma + \left(\frac{q}{\hbar c}\right)^2 (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}})^2 |\mathbf{B}|^2 \cos \Gamma \sin \Gamma \right], \quad (\text{B16})$$

where we replaced $(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}}) = \frac{\delta(k - k_F)}{\hbar v_F}$ for zero temperature. Expanding and throwing away terms that will give zero contribution after the momentum integral due to odd order in k_i ($i = x, y, z$), we are left with the following angular integral after switching to spherical coordinates then integrating k out:

$$\sigma_{yx}^{(0)} = q^2 \int_0^{2\pi} d\phi \int_0^\pi d\theta \frac{k_F^2 \sin \theta}{(2\pi)^3} \frac{\tau I^{(0)}(\theta, \phi)}{\hbar v_F (1 + b_\mu^2)}, \quad (\text{B17})$$

where

$$I^{(0)}(\theta, \phi) = v_F^2 \left[b_{\text{BC}}^2 (\cos \Gamma \sin \Gamma - \sin^2 \theta \cos^2 \phi \cos \Gamma \sin \Gamma - \sin^2 \theta \sin^2 \phi \cos \Gamma \sin \Gamma + 2 \sin^4 \theta \cos^2 \phi \sin^2 \phi \cos \Gamma \sin \Gamma) + b_{\text{BC}}^4 (\sin^2 \theta \cos^2 \phi \cos^3 \Gamma \sin \Gamma + \sin^2 \theta \sin^2 \phi \cos \Gamma \sin^3 \Gamma) \right]. \quad (\text{B18})$$

Finally, carrying out the angular integral leads to

$$\sigma_{yx}^{(0)} = \frac{\sigma_0}{1 + b_\mu^2} \left(\frac{7}{5} b_{\text{BC}}^2 + b_{\text{BC}}^4 \right) \cos \Gamma \sin \Gamma. \quad (\text{B19})$$

Focusing now on $\Sigma_{\mathbf{k}}^{(1)}$, $\sigma_{yx}^{(1)}$ yields

$$\sigma_{yx}^{(1)} = q^2 \int \frac{d^3k}{(2\pi)^3} \frac{\tau \delta(k - k_F)}{\hbar v_F} \frac{1 + \frac{q}{\hbar c} (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}}) + \left(\frac{q}{\hbar c}\right)^2 (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}})^2}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2} \frac{\mu}{c} \left[-v_y (\mathbf{v}_{\mathbf{k}} \times \mathbf{B})_x + \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) (\mathbf{v}_{\mathbf{k}} \times \mathbf{B})_x |\mathbf{B}| \sin \Gamma \right]. \quad (\text{B20})$$

The above whole expression vanishes after the momentum integral, because $(\mathbf{v}_{\mathbf{k}} \times \mathbf{B})_x = v_y B_z - v_z B_y = -v_z B_y$ as $B_z = 0$. This will lead to a single order in v_z in every term in the integrand therefore result in zero after integration.

Finally, focusing on $\Sigma_{\mathbf{k}}^{(2)}$, $\sigma_{yx}^{(2)}$ yields

$$\sigma_{yx}^{(2)} = q^2 \int \frac{d^3k}{(2\pi)^3} \frac{\tau \delta(k - k_F)}{\hbar v_F} \frac{1 + \frac{q}{\hbar c} (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}}) + \left(\frac{q}{\hbar c}\right)^2 (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}})^2}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2} \frac{\mu^2}{c^2} \left[(\mathbf{v}_{\mathbf{k}} \cdot \mathbf{B}) v_y |\mathbf{B}| \cos \Gamma - \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) |\mathbf{B}|^3 v_y \cos \Gamma - \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{B}) (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) |\mathbf{B}|^2 \cos \Gamma \sin \Gamma + \left(\frac{q}{\hbar c}\right)^2 (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}})^2 |\mathbf{B}|^4 \cos \Gamma \sin \Gamma \right]. \quad (\text{B21})$$

Simplifying the product of the Taylor expanded $D_{\mathbf{k}}^{-1}$ and terms in the square bracket while again, keeping only the non-zero contribution, we are left with the following angular integral after switching to spherical coordinates then integrating k out:

$$\sigma_{yx}^{(2)} = q^2 \int_0^{2\pi} d\phi \int_0^\pi d\theta \frac{k_F^2 \sin \theta}{(2\pi)^3} \frac{\tau I^{(2)}(\theta, \phi)}{\hbar v_F (1 + b_\mu^2)}, \quad (\text{B22})$$

where

$$I^{(2)}(\theta, \phi) = v_F^2 b_\mu^2 \left[\sin^3 \theta \sin^2 \phi \cos \Gamma \sin \Gamma + b_{\text{BC}}^2 (\sin \theta \cos \Gamma \sin \Gamma - \sin^3 \theta \cos^2 \phi \cos^3 \Gamma \sin \Gamma - \sin^3 \theta \sin^2 \phi \sin \Gamma \cos \Gamma - \sin^3 \theta \sin^2 \phi \cos \Gamma \sin^3 \Gamma + \sin^5 \theta \cos^2 \phi \sin^2 \phi \cos^3 \Gamma \sin \Gamma + 2 \sin^5 \theta \cos^2 \phi \sin^2 \phi \cos^3 \Gamma \sin \Gamma + \sin^5 \theta \sin^4 \phi \cos \Gamma \sin^3 \Gamma) + b_{\text{BC}}^4 (\sin^3 \theta \cos^2 \phi \cos^3 \Gamma \sin \Gamma + \sin^3 \theta \sin^2 \phi \cos \Gamma \sin^3 \Gamma) \right]. \quad (\text{B23})$$

Finally, carrying out the angular integral leads to

$$\sigma_{yx}^{(2)} = \sigma_0 \frac{b_\mu^2}{1 + b_\mu^2} \left(1 + \frac{8}{5} b_{\text{BC}}^2 + b_{\text{BC}}^4 \right) \cos \Gamma \sin \Gamma. \quad (\text{B24})$$

Adding up the $\sigma_{yx}^{(i)}$ s, we have

$$\sigma_{yx} = \frac{\sigma_0}{1 + b_\mu^2} \left[\left(\frac{7}{5} b_{\text{BC}}^2 + b_{\text{BC}}^4 \right) \cos \Gamma \sin \Gamma + b_\mu^2 \left(1 + \frac{8}{5} b_{\text{BC}}^2 + b_{\text{BC}}^4 \right) \cos \Gamma \sin \Gamma \right]. \quad (\text{B25})$$

3. Conductivity σ_{zx}

Here we go through a detailed derivation of σ_{zx} . Starting with Eq. (20) in the main text for $d = 3$, we again express it in powers of μ while using the definition for $\tilde{v}_{\mathbf{k}}$. We then obtain

$$\sigma_{zx} = q^2 \int \frac{d^3 k}{(2\pi)^3} \frac{\tau(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}}) D_{\mathbf{k}}^{-1}}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2} \left[\Sigma_{\mathbf{k}}^{(0)} + \Sigma_{\mathbf{k}}^{(1)} + \Sigma_{\mathbf{k}}^{(2)} \right] \equiv \sigma_{zx}^{(0)} + \sigma_{zx}^{(1)} + \sigma_{zx}^{(2)}, \quad (\text{B26})$$

where

$$\Sigma_{\mathbf{k}}^{(0)} = v_z v_x - \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) v_z |\mathbf{B}| \cos \Gamma, \quad (\text{B27a})$$

$$\Sigma_{\mathbf{k}}^{(1)} = -\frac{\mu}{c} v_z (\mathbf{v}_{\mathbf{k}} \times \mathbf{B})_x, \quad (\text{B27b})$$

$$\Sigma_{\mathbf{k}}^{(2)} = \frac{\mu^2}{c^2} \left[(\mathbf{v}_{\mathbf{k}} \cdot \mathbf{B}) - \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) |\mathbf{B}|^2 \right] v_z |\mathbf{B}| \cos \Gamma, \quad (\text{B27c})$$

each corresponds to Hall conductivity of $\sigma_{zx}^{(i)}$ respectively. Inserting the Taylor expanded density of states correction to Eq. (B26) and focusing on $\Sigma_{\mathbf{k}}^{(0)}$, $\sigma_{zx}^{(0)}$ yields

$$\sigma_{zx}^{(0)} = q^2 \int \frac{d^3 k}{(2\pi)^3} \frac{\tau \delta(k - k_F)}{\hbar v_F} \frac{1 + \frac{q}{\hbar c} (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}}) + (\frac{q}{\hbar c})^2 (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}})^2}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2} \left[v_z v_x - \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \cdot \mathbf{\Omega}_{\mathbf{k}}) v_z |\mathbf{B}| \cos \Gamma \right], \quad (\text{B28})$$

where we replaced $(-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}}) = \frac{\delta(k - k_F)}{\hbar v_F}$ for zero temperature. The above whole expression in Eq. (B28) vanishes after the momentum integral.

Focusing now on $\Sigma_{\mathbf{k}}^{(1)}$, $\sigma_{zx}^{(1)}$ yields

$$\sigma_{zx}^{(1)} = q^2 \int \frac{d^3 k}{(2\pi)^3} \frac{\tau \delta(k - k_F)}{\hbar v_F} \frac{1 + \frac{q}{\hbar c} (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}}) + (\frac{q}{\hbar c})^2 (\mathbf{B} \cdot \mathbf{\Omega}_{\mathbf{k}})^2}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2} \left[-\frac{\mu}{c} v_z (\mathbf{v}_{\mathbf{k}} \times \mathbf{B})_x \right]. \quad (\text{B29})$$

Expanding and throwing away terms that will give zero contribution after the momentum integral due to odd order in k_i ($i = x, y, z$), we are left with the following angular integral after switching to spherical coordinates then integrating k out:

$$\sigma_{zx}^{(2)} = q^2 \int_0^{2\pi} d\phi \int_0^\pi d\theta \frac{k_F^2 \sin \theta}{(2\pi)^3} \frac{\tau b_\mu I^{(1)}(\theta, \phi)}{\hbar v_F (1 + b_\mu^2)}, \quad (\text{B30})$$

where

$$I^{(1)}(\theta, \phi) = v_F^2 \left[\cos^2 \theta \sin \theta \sin \Gamma + b_{\text{BC}}^2 (\cos^2 \theta \sin^3 \theta \cos^2 \phi \cos^2 \Gamma \sin \Gamma + \cos^2 \theta \sin^3 \theta \sin^2 \phi \sin^3 \Gamma) \right]. \quad (\text{B31})$$

Finally, carrying out the angular integral leads to

$$\sigma_{zx}^{(1)} = \sigma_0 \frac{b_\mu}{1 + b_\mu^2} \left(1 + \frac{1}{5} b_{\text{BC}}^2 \right) \sin \Gamma. \quad (\text{B32})$$

Finally, focusing on $\Sigma_{\mathbf{k}}^{(2)}$, $\sigma_{zx}^{(2)}$ yields

$$\sigma_{zx}^{(0)} = q^2 \int \frac{d^3k}{(2\pi)^3} \frac{\tau \delta(k - k_F)}{\hbar v_F} \frac{1 + \frac{q}{\hbar c} (\mathbf{B} \cdot \boldsymbol{\Omega}_{\mathbf{k}}) + (\frac{q}{\hbar c})^2 (\mathbf{B} \cdot \boldsymbol{\Omega}_{\mathbf{k}})^2}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2} \frac{\mu^2}{c^2} \left[(\mathbf{v}_{\mathbf{k}} \cdot \mathbf{B}) - \frac{q}{\hbar c} (\mathbf{v}_{\mathbf{k}} \cdot \boldsymbol{\Omega}_{\mathbf{k}}) |\mathbf{B}|^2 \right] v_z |\mathbf{B}| \cos \Gamma. \quad (\text{B33})$$

The above expression vanishes after the momentum integral.

Adding up the $\sigma_{zx}^{(i)}$ s, we have

$$\sigma_{zx} = \sigma_0 \frac{b_\mu}{1 + b_\mu^2} \left(1 + \frac{1}{5} b_{\text{BC}}^2 \right) \sin \Gamma. \quad (\text{B34})$$

Note that σ_{zx} at $\Gamma = \frac{\pi}{2}$ in Eq. (B34) corresponds to the Hall conductivity.

4. Conductivity σ_{zz}

Here we go through a detailed derivation of the σ_{zz} . Starting with Eq. (20) in the main text for $d = 3$, we again express it in powers of μ while using the definition for $\hat{\mathbf{v}}_{\mathbf{k}}$. We then obtain

$$\sigma_{zz} = q^2 \int \frac{d^3k}{(2\pi)^3} \frac{\tau (-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}}) D_{\mathbf{k}}^{-1}}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2} \left[\Sigma_{\mathbf{k}}^{(0)} + \Sigma_{\mathbf{k}}^{(1)} + \Sigma_{\mathbf{k}}^{(2)} \right] \equiv \sigma_{zz}^{(0)} + \sigma_{zz}^{(1)} + \sigma_{zz}^{(2)}, \quad (\text{B35})$$

where

$$\Sigma_{\mathbf{k}}^{(0)} = v_z^2, \quad (\text{B36a})$$

$$\Sigma_{\mathbf{k}}^{(1)} = -\frac{\mu}{c} v_z (\mathbf{v}_{\mathbf{k}} \times \mathbf{B})_z, \quad (\text{B36b})$$

$$\Sigma_{\mathbf{k}}^{(2)} = 0, \quad (\text{B36c})$$

as $B_z = 0$. Note that after the momentum integral, $\Sigma_{\mathbf{k}}^{(1)}$ will vanish due to odd order in v_z . The only remaining contribution is from $\Sigma_{\mathbf{k}}^{(0)}$ which gives

$$\begin{aligned} \sigma_{zz}^{(0)} &= q^2 \int \frac{d^3k}{(2\pi)^3} \frac{D_{\mathbf{k}}^{-1} \tau (-\frac{\partial f_{\mathbf{k}}^{(0)}}{\partial \epsilon_{\mathbf{k}}})}{1 + \frac{\mu^2}{c^2} |\mathbf{B}|^2} v_z^2 \\ &= q^2 \int \frac{d\Omega}{\hbar v_F (2\pi)^3} \frac{\tau v_F^2 k_F^2}{1 + b_\mu^2} \left(\cos^2 \theta + b_{\text{BC}}^2 \cos^2 \theta \sin^2 \theta \cos^2 \phi \cos^2 \Gamma + b_{\text{BC}}^2 \cos^2 \theta \sin^2 \theta \sin^2 \phi \sin^2 \Gamma \right) \sin \theta \\ &= \frac{\sigma_0}{1 + b_\mu^2} \left(1 + \frac{1}{5} b_{\text{BC}}^2 \right). \end{aligned} \quad (\text{B37})$$

5. Conductivity and resistivity tensors

Finally, we have the following conductivity tensor including the Taylor expanded $D_{\mathbf{k}}^{-1}$:

$$\begin{aligned} \boldsymbol{\sigma}(\mathbf{B}) &= \frac{\sigma_0}{1 + b_\mu^2} \\ &\times \begin{bmatrix} 1 + \frac{1}{5} b_{\text{BC}}^2 + \left[\frac{7}{5} b_{\text{BC}}^2 + b_\mu^2 \left(1 + \frac{8}{5} b_{\text{BC}}^2 \right) \right] \cos^2 \Gamma & \left[b_\mu^2 \left(1 + \frac{1}{5} b_{\text{BC}}^2 \right) + \frac{7}{5} (1 + b_\mu^2) b_{\text{BC}}^2 \right] \sin \Gamma \cos \Gamma & -b_\mu \left(1 + \frac{1}{5} b_{\text{BC}}^2 \right) \sin \Gamma \\ \left[b_\mu^2 \left(1 + \frac{1}{5} b_{\text{BC}}^2 \right) + \frac{7}{5} (1 + b_\mu^2) b_{\text{BC}}^2 \right] \sin \Gamma \cos \Gamma & 1 + \frac{1}{5} b_{\text{BC}}^2 + \left[\frac{7}{5} b_{\text{BC}}^2 + b_\mu^2 \left(1 + \frac{8}{5} b_{\text{BC}}^2 \right) \right] \sin^2 \Gamma & b_\mu \left(1 + \frac{1}{5} b_{\text{BC}}^2 \right) \cos \Gamma \\ b_\mu \left(1 + \frac{1}{5} b_{\text{BC}}^2 \right) \sin \Gamma & -b_\mu \left(1 + \frac{1}{5} b_{\text{BC}}^2 \right) \cos \Gamma & 1 + \frac{1}{5} b_{\text{BC}}^2 \end{bmatrix}. \end{aligned} \quad (\text{B38})$$

The resistivity tensor $\boldsymbol{\rho}(\mathbf{B})$ is then obtained by the inverse of the conductivity tensor $\boldsymbol{\sigma}(\mathbf{B})$ as

$$\boldsymbol{\rho}(\mathbf{B}) = \rho_0 \begin{bmatrix} \frac{50+10b_{\text{BC}}^2+70b_{\text{BC}}^2 \sin^2 \Gamma}{50+90b_{\text{BC}}^2+16b_{\text{BC}}^4} & -\frac{35b_{\text{BC}}^2 \cos \Gamma \sin \Gamma}{25+45b_{\text{BC}}^2+8b_{\text{BC}}^4} & \frac{5b_{\mu} \sin \Gamma}{5+b_{\text{BC}}^2} \\ -\frac{35b_{\text{BC}}^2 \cos \Gamma \sin \Gamma}{25+45b_{\text{BC}}^2+8b_{\text{BC}}^4} & \frac{50+10b_{\text{BC}}^2+70b_{\text{BC}}^2 \cos^2 \Gamma}{50+90b_{\text{BC}}^2+16b_{\text{BC}}^4} & -\frac{5b_{\mu} \cos \Gamma}{5+b_{\text{BC}}^2} \\ -\frac{5b_{\mu} \sin \Gamma}{5+b_{\text{BC}}^2} & \frac{5b_{\mu} \cos \Gamma}{5+b_{\text{BC}}^2} & \frac{5}{5+b_{\text{BC}}^2} \end{bmatrix}. \quad (\text{B39})$$

Note that although both the Lorentz force and the Berry curvature induced terms are present in $\sigma_{ij}(\mathbf{B})$, the Lorentz force induced terms do not appear in the resistivity $\rho_{ij}(\mathbf{B})$ where $i, j = x, y$ even if we include the Taylor expanded $D_{\mathbf{k}}^{-1}$.