

High- T_c superconductivity of clathrate $\text{Y}_3\text{EuH}_{24}$

Abdul Ghaffar

School of Information Science, JAIST

Peng Song

School of Information Science, JAIST

Kenta Hongo

Research Center for Advanced Computing Infrastructure, JAIST

Ryo Maezono

School of Information Science, JAIST

Abstract

Recent progress on theoretical predictions of ternary superhydrides and their subsequent experimental confirmations have introduced us with a new generation of superconductors, having the potential to realize the synthesis of the most anticipated room temperature superconductors. Motivated by the recent high pressure experiment on YH_6 and EuH_6 , we have theoretically examined the stability as well as superconductivity by mixing the two compounds. Here we identified four phases capable of maintaining thermodynamic stability in the pressure range of 150-300 GPa, namely $Fm\bar{3}m\text{-Y}_3\text{EuH}_{24}$, $Cmmm\text{-YEuH}_{12}$, $Cmmm\text{-YEu}_3\text{H}_{24}$, $Immm\text{-YEu}_3\text{H}_{24}$. Among them, only $Fm\bar{3}m\text{-Y}_3\text{EuH}_{24}$ can maintain dynamically stability in the searched pressure range. The Allen-Dynes modified McMillan formula was used to further check the superconductivity of this phase, and the results reveal that the predicted superconducting transition temperature T_c of $\text{Y}_3\text{EuH}_{24}$ is approaching 220 K at 200 GPa. $Fm\bar{3}m\text{-Y}_3\text{EuH}_{24}$ has a nearly identical logarithmic average phonon frequency ω_{log} to YH_6 , but its electron-phonon coupling (EPC) constant λ is somewhat smaller than YH_6 's 2.56, resulting in a lower ultimate T_c value.

Keywords: High- T_c Superconductivity, USPEX, Room-temperature T_c , Ternary hydrides, *ab initio*

1. Introduction

Search for high temperature superconducting compounds has been a long sought after research endeavor among the scientific community. Metallic hydrogen was hypothesized theoretically to meet the requirement of high- T_c superconductivity at a T_c of 242 K at a pressure of 450 GPa [1]. However, it has been demonstrated that metallization of molecular hydrogen requires even higher pressure of 495 GPa [2], and achieving such extreme pressure condition is highly challenging [3, 4, 5, 6], which renders its application quite difficult to be realized. To mitigate this problem, an ingenious concept was later on introduced by Ashcroft [4] to utilize superconducting properties of metallic hydrogen by incorporating heavier metals in to the lattice which reduces the required metallization pressure by providing metal assisted pre-compression to the system. Along this line of finding an alternative, hydrogen-rich compounds have been the promising candidate for high- T_c superconductivity at a significantly lower pressure [7].

Soon after the synthesis of high- T_c phase of H_3S via compression of H_2S [8, 9], there has been a surge of theoretical and experimental studies on hydrogen rich compounds. These compounds, often termed as superhydrides, specifically binary hydrides, have dominated the research in recent years due to their excellent metallic and superconducting properties resulting from their extremely high electron-phonon interaction [4, 7]. Superhydride lattices consist of H-based, metal-encapsulated clathrate structures, where H-atoms are weakly bonded together to form sodalite-like structural configuration around the metal atom. In this typical atomic arrangement, H-atoms draw electrons from the metal, increasing the density of state (DOS) contributin at the Fermi level which in turn actively contributes to the electron-phonon coupling, resulting from the phonon vibration of H-H bonds, which gives rise to a remarkably high superconducting temperature.

After the first theoretical prediction of exceptional superconducting properties with a T_c of 235 K at 150 GPa, in clathrate Calcium-hexahydride CaH_6 [10], a spike

Email address: mwkspg2002@icloud.com (Peng Song)

in the search for similar other potential superhydrides can be witnessed [11, 12, 13, 14, 15, 16, 17, 18, 19]. Interestingly, among the binary superhydrides proposed theoretically, some of them were subsequently synthesized [20, 21, 22, 23, 24, 25, 26, 27, 28, 27, 29] and found to confirm the predicted results, which evidently provides motivation towards further theoretical exploration in this field.

Inspired from the predictions of CaH_6 [10] and YH_6 [30], Liang et al. [31], theoretically examined the properties of ternary hydride CaYH_{12} and reported the T_c of 258 K at 200 GPa which is surprisingly similar to those of parent binary phases. A more recent report [32] has suggested stable high- T_c ternary hydrides YCeH_{20} and LaCeH_{20} motivated by the properties of parent binaries CeH_9 , YH_9 and LaH_{10} , CeH_{10} respectively. Meanwhile, La-Ce-H based ternary hydride $(\text{La}, \text{Ce})\text{H}_9$ has just been experimentally realized to show excellent stability against their binary phases, it was also found to exhibit a dramatic increase in superconducting temperature by 50-80 K compared to the binary CeH_9 [33]. Furthermore, a successful synthesis of ternary hydrides $(\text{La}, \text{Y})\text{H}_6$ and $(\text{La}, \text{Y})\text{H}_{10}$ with a maximum T_c of ~ 253 K at 183 GPa [34] has been established recently inspired by the theoretical work of Song et al. [35] on La-Y-H ternary hydrides. In addition, Mg-Ca-H [36], Li-Mg-H [37], La-B-H [38], La-Nd-H [39] high- T_c ternary phases have been studied lately. These studies clearly substantiate the belief that ternary hydrides have the potential to pave the way for achieving room-temperature superconductivity at comparatively lower pressure than their binary counterparts.

A very simple widely accepted method [33] to hypothesize new ternary hydride $(\text{A}_x\text{B}_y\text{H}_z)$ using binary compound $(\text{A}_{x+y}\text{H}_z)$ is the random substitution of one of the metal atom in the binary with another atom having comparable chemical properties. The resulting stability and the superconducting properties of the new ternary hydride obtained from the mixture of two binaries can be associated to the similar structural and chemical properties of the metals involved in the formation of parent binaries.

Although record high T_c values has been reported for CHS_x [40] of 288 K at ~ 275 GPa, for LaH_{10} of 288 K at 200 GPa [16], for YH_{10} of 326 K at 250 GPa [15], and for $\text{Li}_2\text{MgH}_{16}$ of ~ 473 K at 250 GPa [37], pressure requirement for phase stability still seems unsuitable for practical applications, and achieving such high- T_c at more feasible synthesis condition remains a challenge. To address this issue, and motivated by the theoretical predictions and their subsequent experimental confirmations, we have systematically explored the possibility of potentially high- T_c stable ternary phases in Y-Eu-H system. Interestingly, according to the recent published data, the binary phases of yttrium hexahydride $\text{Im}\bar{3}m\text{-YH}_6$ [23] has been reported experimentally to display a T_c of 224 K at 166 GPa, similar T_c of ~ 220 K was also reported [24] recently for YH_6 at a slightly higher pressure of 183 GPa, and around the same

time europium hexahydride $\text{Im}\bar{3}m\text{-EuH}_6$ [41] was synthesized to indicate towards a possibility for a high T_c of 258 K at as low pressure as 152 GPa. Moreover, it is worth mentioning here that, using first-principles based theoretical approach, above two binary hydrides were also predicted to show almost the same high T_c superconducting characteristics at the same pressure condition [15, 42, 30, 43, 41], once again, solidifying the importance of theoretical work as a guiding framework for the further experimental research.

We introduce here a theoretical investigation on Yttrium and Europium based new ternary hydrides having ability to demonstrate as high- T_c as 221 K at 200 GPa, contributing towards the search for potential high- T_c hydrides. In this work we have exploited the similar synthesis condition of YH_6 and EuH_6 binary hydrides to speculate the possibility of novel ternary superhydrides (Y-Eu-H) over a range of pressure 150-300 GPa. Additionally, Y and Eu have quite close atomic radius 212 pm, 231 pm and electronegativity of 1.22, 1.20 on the Pauling scale, respectively, which ensures the stability of ternary lattice [44, 45, 33].

2. Computational details

Theoretical prediction of thermodynamically stable structures was carried out using the variable-composition evolutionary algorithm USPEX (Universal Structure Predictor: Evolutionary Xtallography) [46] which was interfaced with the Vienna Ab initio Simulation Package (VASP) [47, 48, 49, 50] to calculate the Density Functional Theory (DFT) enthalpy for the stability comparison. The USPEX input parameters were set to generate 400 random initial structures based on the YEuH_{12} stoichiometry. Out of which 100 structures were allowed to evolve with 40% heredity, 40% randomness, 10% soft mutation, and 10% transmutation in every subsequent generations. Stopping criteria was set to 10 generations in case no new structure was detected. Eventually, the most stable structures were subjected to rigorous geometry optimization on VASP using the PBE-GGA [51] exchange correlation functional followed by the more accurate enthalpy calculation for the convex-hull generation.

We employed ab initio phonon DOS calculations to predict the dynamical stability of the most stable candidate structures ($Cmmm\text{-YEu}_3\text{H}_{24}$ at 150-165 GPa, $Cmmm\text{-YEuH}_{12}$ at 150-200 GPa, $Immm\text{-YEu}_3\text{H}_{24}$ at 165-300 GPa, and $Fm\bar{3}m\text{-Y}_3\text{EuH}_{24}$ at 150-250 GPa), and Allendynes modified MacMillan formalism [52, 53, 54] was applied for T_c calculations as implemented in the Quantum Espresso package [52]. Convergence test was carried out to determine the appropriate cutoff energy for the plane-wave basis, and the size of the mesh-grid for the brillouin-zone integration. A $8\times 8\times 5$ k-mesh was used for the self-consistent field convergence in Marzai-Vanderbilt smearing scheme [55]. Smearing parameter was extrapolated to-

wards zero for most accurate energy calculations. For the phonon calculations, $16 \times 16 \times 10$ and $4 \times 4 \times 2$ meshes were chosen for k- and q-mesh integration, respectively.

3. Results

Several possibly stable structures were generated based on the stoichiometric composition $(YH_6)_x(EuH_6)_y$ as displayed in the convex-hull diagram in Figure 1, among which $Cmmm$ - YEu_3H_{24} , $Cmmm$ - $YEuH_{12}$, $Immm$ - YEu_3H_{24} , and $Fm\bar{3}m$ - Y_3EuH_{24} seemed to be thermodynamically stable. The existence of promising high- T_c ternary hydride candidates based on binary hexahydrides have already been investigated for La-Ce-H [34], Ca-Y-H [31, 56], La-Y-H [35], Y/La-K-H [57]. Nevertheless, all the other compositions lying above the convex-hull are meta-stable structures which could potentially decompose into their parent binaries $Im\bar{3}m$ - YH_6 and $Im\bar{3}m$ - EuH_6 . In the convex-hull diagram, at pressure 150 GPa, three stable structures (YEu_3H_{24} , $YEuH_{12}$, and Y_3EuH_{24}) can be detected along with some metal-stable phases with different compositions. Once pressure is increased to 200 GPa, $YEuH_{12}$ phase moves above the hull while YEu_3H_{24} and Y_3EuH_{24} structures manifest a very slight change keeping the stability of the two structures intact. At 300 GPa, only YEu_3H_{24} continues to be stable with even a more deeper hull making it the most stable ternary hydride structure throughout the study.

Furthermore, As demonstrated in Figure 2, all the stable structures have the same kind of sodalite-like clathrate structure with $Y@H_{24}$ and $Eu@H_{24}$ unit clathrate cages arranged differently depending upon the symmetry of the structures. Similar clathrate cages were also observed in the high- T_c binaries of CaH_6 [10], YH_6 [30], EuH_6 [41]. As a matter of fact, prior research generally confirms that the high- T_c superconductivity found in these binaries could be attributed to this peculiar arrangement having hydrogen rich environment. Therefore, after convex-hull assesment of all the structures, it is quite reasonable to presume that the two ternary hydrides namely $Fm\bar{3}m$ - Y_3EuH_{24} and $Immm$ - YEu_3H_{24} , observed at 200 GPa and above, could have phonon-stability and therefore, might show high- T_c superconducting properties.

Phonon dispersion in Figure 3(a) shows that $Fm\bar{3}m$ - Y_3EuH_{24} is stable at 200 GPa and above, A very small contribution of stable phonon vibrations at negative frequency can be seen at several locations (between Γ -L and at L), similarly, as shown in (b), for $Cmmm$ - $YEuH_{12}$, phonon-vibrations at significantly high negative frequencies has raised question on their dynamical stability at 150 GPa. As depicted in Figure 3(c), a vanishingly small negative phonon contribution can also be observed for $Cmmm$ - YEu_3H_{24} , which undergoes a phase transition ($Cmmm$ to $Immm$) upon increasing pressure (to 200 GPa, 250 GPa, and 300 GPa) as demonstrated in (d). No appreciable change was spotted at increasing pressure towards

higher negative frequencies, which makes YEu_3H_{24} interesting for further analysis for its superconducting properties. However, due to the negative contribution of its phonon frequency, it could lead to a wrong calculation of the Electron-Phonon coupling constant (EPC) and therefore a non-reliable prediction of transition temperature is expected. As a result, we have focussed our attention to $Fm\bar{3}m$ - Y_3EuH_{24} phase for its EPC calculations and used it further for the T_c estimation.

The EPC (λ), logarithmic frequency (w_{log}), phonon-DOS (N_{EF}), and T_c calculated using Allen-Dynes (AD) and AD-modified McMillan (McM) formula with coulumb pseudopotential (μ) of 0.1 - 0.13 for $Fm\bar{3}m$ - Y_3EuH_{24} are listed in the Table 1. Highest T_c detected employing AD formalism at 200 GPa, agrees within a reasonable accuracy to its parent binary phase $Im\bar{3}m$ - YH_6 ($T_c \sim 220$ K at 183 GPa [24]). On the other hand, the other parent binary $Im\bar{3}m$ - EuH_6 was synthesized to show a slightly higher T_c of ~ 250 K under a pressure of 152 GPa [41]. The observed properties of Y_3EuH_{24} akin to YH_6 could be linked to a higher contribution of 75% YH_6 compared to a 25% contribution of EuH_6 , in the formation of Y_3EuH_{24} with a stichiometry of $(YH_6)_3(EuH_6)$.

4. Discussion

The calculated electronic band structure and DOS for $Fm\bar{3}m$ - Y_3EuH_{24} are shown in Figure 4. The presence of the several bands corssing over the fermi-level highlights its metallic nature. Some flatter bands in the vicinity of of fermi-level can also be observed, which is apparently reported to enhance the electron-phonon coupling [58] and thereby increasing the observed T_c . Besides, from the atomic contribution of electronic density of states (DOS), an appreciable amount of DOS associated to hydrogen can be seen at the fermi-level emerged from hydrogen-generated phonon-modes, further strengthening the electron-phonon interaction.

Prior studies [35, 57] employing machine learning technique indicate towards the stability dependence on the relative admixture of the two binaries taking part in the formation of the ternary phase. In Figure 1, our predicted ternary phases $(EuH_6)_x(YH_6)_y$ show the instability along x-axis as pressure gets higher and higher consistent with the preceding works. The phase YEu_3H_{24} was detected with the highest stability, over the pressure range of 150-300 GPa having two different symmetry structures ($Cmmm$: 150-165 GPa, $Immm$: 165-300 GPa). However, any prospect for high- T_c prediction seems to be in vain because of the appearance of a very minute negative phonon-modes as visible in Figure 3. In additional, our calculation uses harmonic approximation for EPC estimation, which according to some earlier studies may yield some discrepancy with that of obtained from the anharmonic calculations [59, 60]. Please note that, we restrict

ourselves to the harmonic approximation based calculation as anharmonic calculations are computationally demanding, which is out of scope for this study. Moreover, anharmonic interaction increases with temperature, which causes imaginary modes become weaker and weaker, and at a certain temperature phonon-phonon interaction becomes strong enough to stabilize the lattice. As a consequence, pertaining to the studies [61, 62, 63], we speculate that imaginary phonon modes in $\text{YEu}_3\text{H}_{24}$ might disappear at higher temperature synthesis condition, thereby making it a relevant high- T_c candidate.

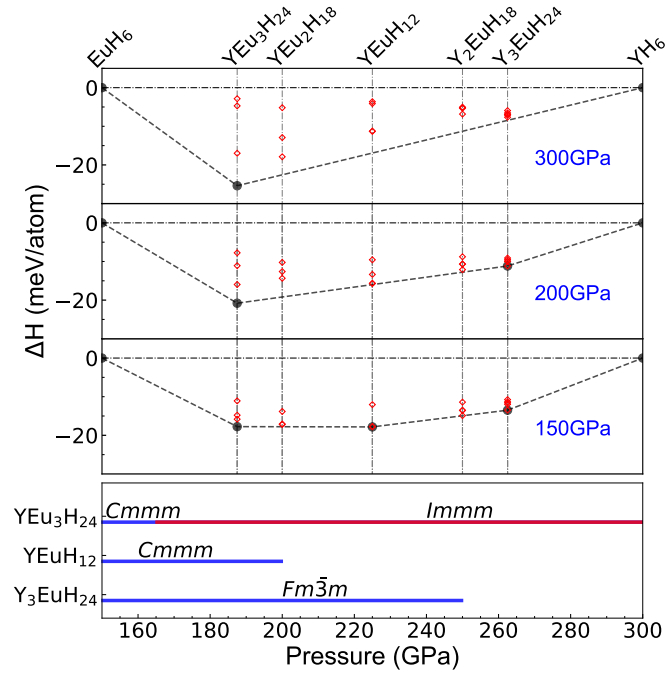


Figure 1: convex hull, phase diagram

5. Conclusion

The purpose of this research was to explore the potential high- T_c ternary hydride compounds emerging from the admixture of the two recently synthesized binaries, namely YH_6 and EuH_6 with transition temperature of over 200 K at pressures under 200 GPa. We have successfully, introduced $Fm\bar{3}m\text{-Y}_3\text{EuH}_{24}$ as a prospective high- T_c (~ 220 K at 200 GPa) candidate along with a few other thermodynamically stable phases such as $Cmmm\text{-YEuH}_{12}$, $Cmmm\text{-YEu}_3\text{H}_{24}$, and $Immm\text{-YEu}_3\text{H}_{24}$. In particular, we have argued that $\text{YEu}_3\text{H}_{24}$ may also exhibit superconductivity at a finite temperature condition. Eventually, our prediction of excellent superconducting properties of $\text{Y}_3\text{EuH}_{24}$ strengthens the position that ternary hydrides possess the ability to demonstrate high- T_c and possibly room-temperature T_c at a similar synthesis condition to their parent binaries.

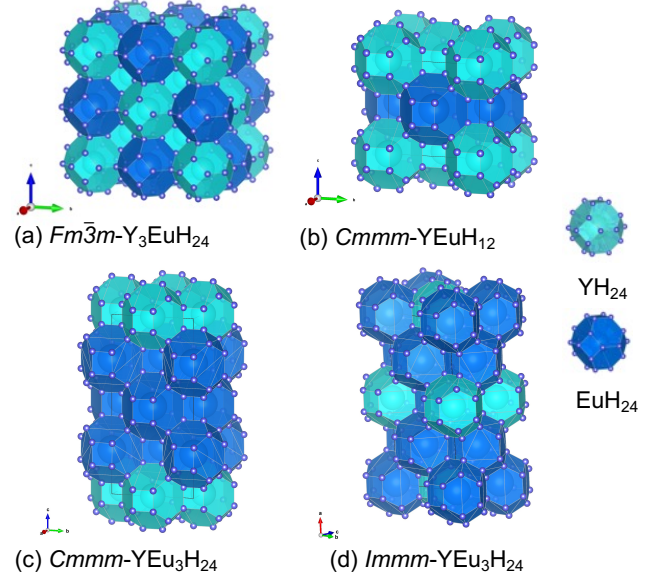


Figure 2: crystal structure

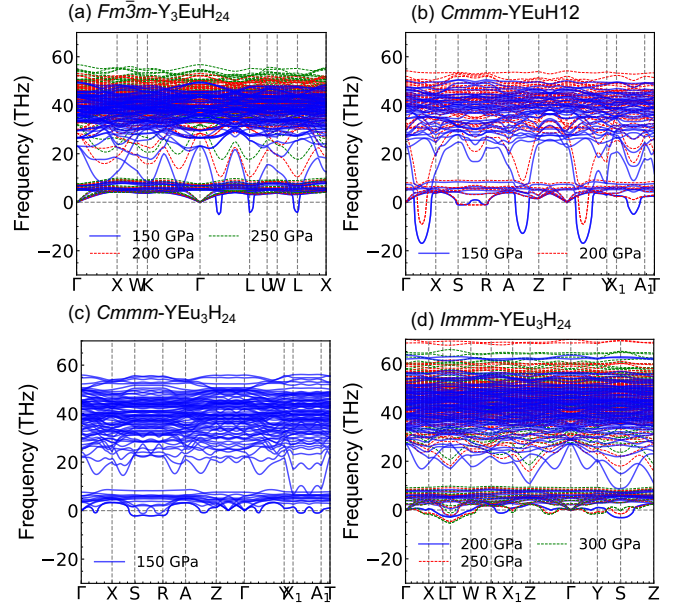


Figure 3: Phonon dispersion with increase of the pressures.

Table 1: T_c estimated by Allen-Dynes modified McMillan formula using first-principles phonon calculations for Y-Eu-H at each pressure. λ and ω_{\log} are the parameters appearing in the formula.

| Phase | Space group | P (GPa) | Volume ($\text{\AA}^3/\text{f.u.}$) | λ | ω_{\log} | N_{E_F} (states/eV/ \AA^3) | $T_c(\text{McM})$ (K) at $\mu = 0.1 - 0.13$ | $T_c(\text{AD})$ (K) at $\mu = 0.1 - 0.13$ |
|----------------------------------|--------------|--------------|--|-----------|-----------------|---|--|---|
| Y ₃ EuH ₂₄ | $Fm\bar{3}m$ | 200 | 87.60 | 2.254 | 1140.3 | 0.0282 | 177.1 – 166.4 | 221.3 – 202.8 |
| | | 250 | 81.96 | 2.0396 | 1222.1 | 0.0299 | 178.1 – 166.4 | 217.4 – 198.4 |

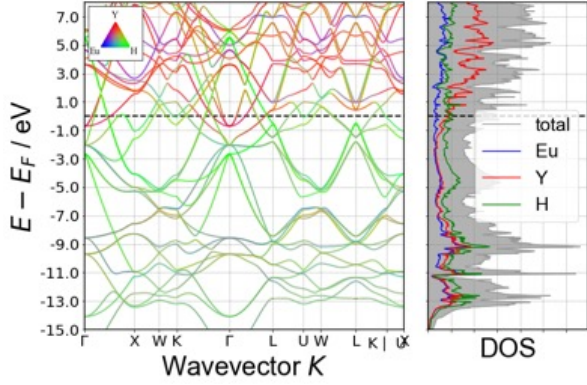


Figure 4: The electronic structure of $Fm\bar{3}m$ -Y₃EuH₂₄ at the pressure of 200 GPa.

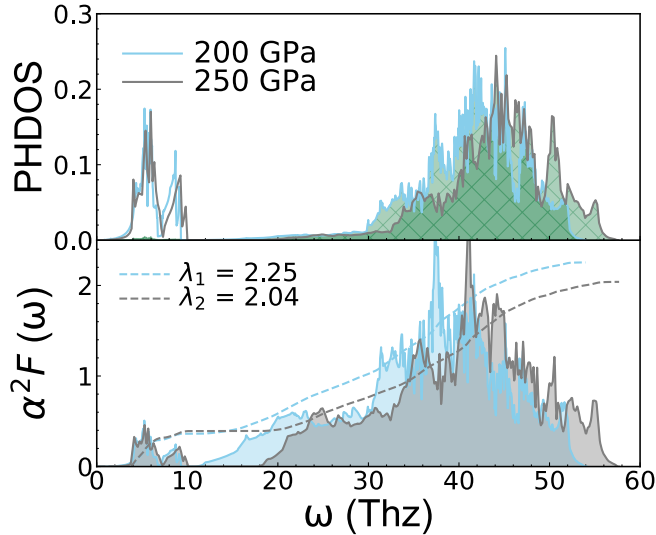


Figure 5: Calculated phonon DOS and Eliashberg spectral functions and electron-phonon coupling parameter (λ) for $Fm\bar{3}m$ -Y₃EuH₂₄ with increase of pressure.

Acknowledgments

The computations in the present study were partially performed using the facilities of the Research Center for Advanced Computing Infrastructure (RCACI) at JAIST.

References

- [1] L. Zhang, Y. Niu, Q. Li, T. Cui, Y. Wang, Y. Ma, Z. He, G. Zou, Ab initio prediction of superconductivity in molecular metallic hydrogen under high pressure, *Solid state communications* 141 (11) (2007) 610–614.
- [2] R. P. Dias, I. F. Silvera, Observation of the wigner-huntington transition to metallic hydrogen, *Science* 355 (6326) (2017) 715–718.
- [3] P. Loubeyre, F. Occelli, P. Dumas, Synchrotron infrared spectroscopic evidence of the probable transition to metal hydrogen, *Nature* 577 (7792) (2020) 631–635.
- [4] N. W. Ashcroft, Metallic hydrogen: A high-temperature superconductor?, *Physical Review Letters* 21 (26) (1968) 1748.
- [5] P. Dalladay-Simpson, R. T. Howie, E. Gregoryanz, Evidence for a new phase of dense hydrogen above 325 gigapascals, *Nature* 529 (7584) (2016) 63–67.
- [6] M. I. Eremets, A. P. Drozdov, P. Kong, H. Wang, Semimetallic molecular hydrogen at pressure above 350 gpa, *Nature Physics* 15 (12) (2019) 1246–1249.
- [7] N. Ashcroft, Hydrogen dominant metallic alloys: high temperature superconductors?, *Physical Review Letters* 92 (18) (2004) 187002.
- [8] D. Duan, Y. Liu, F. Tian, D. Li, X. Huang, Z. Zhao, H. Yu, B. Liu, W. Tian, T. Cui, Pressure-induced metallization of dense (h2s) 2h2 with high- t_c superconductivity, *Scientific reports* 4 (1) (2014) 1–6.
- [9] D. Duan, X. Huang, F. Tian, D. Li, H. Yu, Y. Liu, Y. Ma, B. Liu, T. Cui, Pressure-induced decomposition of solid hydrogen sulfide, *Physical Review B* 91 (18) (2015) 180502.
- [10] H. Wang, S. T. John, K. Tanaka, T. Iitaka, Y. Ma, Superconductive sodalite-like clathrate calcium hydride at high pressures, *Proceedings of the National Academy of Sciences* 109 (17) (2012) 6463–6466.
- [11] Y. Xie, Q. Li, A. R. Oganov, H. Wang, Superconductivity of lithium-doped hydrogen under high pressure, *Acta Crystallographica Section C: Structural Chemistry* 70 (2) (2014) 104–111.
- [12] X. Feng, J. Zhang, G. Gao, H. Liu, H. Wang, Compressed sodalite-like mgh 6 as a potential high-temperature superconductor, *RSC advances* 5 (73) (2015) 59292–59296.
- [13] S. Zhang, Y. Wang, J. Zhang, H. Liu, X. Zhong, H.-F. Song, G. Yang, L. Zhang, Y. Ma, Phase diagram and high-temperature superconductivity of compressed selenium hydrides, *Scientific reports* 5 (1) (2015) 1–8.
- [14] X. Zhong, H. Wang, J. Zhang, H. Liu, S. Zhang, H.-F. Song, G. Yang, L. Zhang, Y. Ma, Tellurium hydrides at high pressures: High-temperature superconductors, *Physical review letters* 116 (5) (2016) 057002.

- [15] H. Liu, I. I. Naumov, R. Hoffmann, N. Ashcroft, R. J. Hemley, Potential high-*tc* superconducting lanthanum and yttrium hydrides at high pressure, *Proceedings of the National Academy of Sciences* 114 (27) (2017) 6990–6995.
- [16] F. Peng, Y. Sun, C. J. Pickard, R. J. Needs, Q. Wu, Y. Ma, Hydrogen clathrate structures in rare earth hydrides at high pressures: Possible route to room-temperature superconductivity, *Physical review letters* 119 (10) (2017) 107001.
- [17] D. Duan, Y. Liu, Y. Ma, Z. Shao, B. Liu, T. Cui, Structure and superconductivity of hydrides at high pressures, *National Science Review* 4 (1) (2017) 121–135.
- [18] K. Abe, Hydrogen-rich scandium compounds at high pressures, *Physical Review B* 96 (14) (2017) 144108.
- [19] A. G. Kvashnin, D. V. Semenov, I. A. Kruglov, I. A. Wrona, A. R. Oganov, High-temperature superconductivity in a th-h system under pressure conditions, *ACS applied materials & interfaces* 10 (50) (2018) 43809–43816.
- [20] M. Somayazulu, M. Ahart, A. K. Mishra, Z. M. Geballe, M. Baldini, Y. Meng, V. V. Struzhkin, R. J. Hemley, Evidence for superconductivity above 260 k in lanthanum superhydride at megabar pressures, *Physical review letters* 122 (2) (2019) 027001.
- [21] A. Drozdov, P. Kong, V. Minkov, S. Besedin, M. Kuzovnikov, S. Mozaffari, L. Balicas, F. Balakirev, D. Graf, V. Prakapenka, et al., Superconductivity at 250 k in lanthanum hydride under high pressures, *Nature* 569 (7757) (2019) 528–531.
- [22] L. Ma, K. Wang, Y. Xie, X. Yang, Y. Wang, M. Zhou, H. Liu, G. Liu, H. Wang, Y. Ma, Experimental observation of superconductivity at 215 k in calcium superhydride under high pressures, *arXiv preprint arXiv:2103.16282* (2021).
- [23] I. A. Troyan, D. V. Semenov, A. G. Kvashnin, A. V. Sadakov, O. A. Sobolevskiy, V. M. Pudalov, A. G. Ivanova, V. B. Prakapenka, E. Greenberg, A. G. Gavriluk, et al., Anomalous high-temperature superconductivity in yh6, *Advanced Materials* 33 (15) (2021) 2006832.
- [24] P. Kong, V. S. Minkov, M. A. Kuzovnikov, A. P. Drozdov, S. P. Besedin, S. Mozaffari, L. Balicas, F. F. Balakirev, V. B. Prakapenka, S. Chariton, et al., Superconductivity up to 243 k in the yttrium-hydrogen system under high pressure, *Nature communications* 12 (1) (2021) 1–9.
- [25] N. P. Salke, M. M. Davari Esfahani, Y. Zhang, I. A. Kruglov, J. Zhou, Y. Wang, E. Greenberg, V. B. Prakapenka, J. Liu, A. R. Oganov, et al., Synthesis of clathrate cerium superhydride ceh9 at 80–100 gpa with atomic hydrogen sublattice, *Nature communications* 10 (1) (2019) 1–10.
- [26] X. Li, X. Huang, D. Duan, C. J. Pickard, D. Zhou, H. Xie, Q. Zhuang, Y. Huang, Q. Zhou, B. Liu, et al., Polyhydride ceh9 with an atomic-like hydrogen clathrate structure, *Nature communications* 10 (1) (2019) 1–7.
- [27] E. Snider, N. Dasenbrock-Gammon, R. McBride, X. Wang, N. Meyers, K. V. Lawler, E. Zurek, A. Salamat, R. P. Dias, Synthesis of yttrium superhydride superconductor with a transition temperature up to 262 k by catalytic hydrogenation at high pressures, *Physical Review Letters* 126 (11) (2021) 117003.
- [28] D. Zhou, D. V. Semenov, D. Duan, H. Xie, W. Chen, X. Huang, X. Li, B. Liu, A. R. Oganov, T. Cui, Superconducting praseodymium superhydrides, *Science advances* 6 (9) (2020) eaax6849.
- [29] W. Chen, D. V. Semenov, A. G. Kvashnin, X. Huang, I. A. Kruglov, M. Galasso, H. Song, D. Duan, A. F. Goncharov, V. B. Prakapenka, et al., Synthesis of molecular metallic barium superhydride: pseudocubic bah12, *Nature communications* 12 (1) (2021) 1–9.
- [30] Y. Li, J. Hao, H. Liu, J. S. Tse, Y. Wang, Y. Ma, Pressure-stabilized superconductive yttrium hydrides, *Scientific Reports* 5 (1) (2015) 1–8.
- [31] X. Liang, A. Bergara, L. Wang, B. Wen, Z. Zhao, X.-F. Zhou, J. He, G. Gao, Y. Tian, Potential high-*t c* superconductivity in cayh 12 under pressure, *Physical Review B* 99 (10) (2019) 100505.
- [32] P. Song, Z. Hou, K. Nakano, K. Hongo, R. Maezono, Potential high-*tc* superconductivity in yceh20 and laceh20 under pressure, *arXiv preprint arXiv:2204.01921* (2022).
- [33] J. Bi, Y. Nakamoto, K. Shimizu, M. Zhou, H. Wang, G. Liu, Y. Ma, Efficient route to achieve superconductivity improvement via substitutional la-ce alloy superhydride at high pressure, *arXiv preprint arXiv:2204.04623* (2022).
- [34] D. V. Semenov, I. A. Troyan, A. G. Ivanova, A. G. Kvashnin, I. A. Kruglov, M. Hanfland, A. V. Sadakov, O. A. Sobolevskiy, K. S. Pervakov, I. S. Lyubutin, et al., Superconductivity at 253 k in lanthanum–yttrium ternary hydrides, *Materials Today* 48 (2021) 18–28.
- [35] P. Song, Z. Hou, P. B. d. Castro, K. Nakano, K. Hongo, Y. Takano, R. Maezono, High-*t c* superconducting hydrides formed by lah24 and yh24 cage structures as basic blocks, *Chemistry of Materials* 33 (24) (2021) 9501–9507.
- [36] W. Sukmas, P. Tsuppayakorn-aek, U. Pinsook, T. Bovornratanaraks, Near-room-temperature superconductivity of mg/ca substituted metal hexahydride under pressure, *Journal of Alloys and Compounds* 849 (2020) 156434.
- [37] Y. Sun, J. Lv, Y. Xie, H. Liu, Y. Ma, Route to a superconducting phase above room temperature in electron-doped hydride compounds under high pressure, *Physical review letters* 123 (9) (2019) 097001.
- [38] S. Di Cataldo, C. Heil, W. von der Linden, L. Boeri, La bh 8: Towards high-*t c* low-pressure superconductivity in ternary superhydrides, *Physical Review B* 104 (2) (2021) L020511.
- [39] D. V. Semenov, I. A. Troyan, A. V. Sadakov, D. Zhou, M. Galasso, A. G. Kvashnin, I. A. Kruglov, A. A. Bykov, K. Y. Terent'ev, A. V. Cherepahin, et al., Effect of paramagnetic impurities on superconductivity in polyhydrides: s-wave order parameter in nd-doped lah10 (2022).
- [40] E. Snider, N. Dasenbrock-Gammon, R. McBride, M. Debessai, H. Vindana, K. Vencatasamy, K. V. Lawler, A. Salamat, R. P. Dias, Room-temperature superconductivity in a carbonaceous sulfur hydride, *Nature* 586 (7829) (2020) 373–377.
- [41] L. Ma, M. Zhou, Y. Wang, S. Kawaguchi, Y. Ohishi, F. Peng, H. Liu, G. Liu, H. Wang, Y. Ma, Experimental clathrate superhydrides euh 6 and euh 9 at extreme pressure conditions, *Physical Review Research* 3 (4) (2021) 043107.
- [42] K. Grishakov, N. Degtyarenko, E. Mazur, Electron, phonon, and superconducting properties of yttrium and sulfur hydrides under high pressures, *Journal of Experimental and Theoretical Physics* 128 (1) (2019) 105–114.
- [43] D. V. Semenov, D. Zhou, A. G. Kvashnin, X. Huang, M. Galasso, I. A. Kruglov, A. G. Ivanova, A. G. Gavriluk, W. Chen, N. V. Tkachenko, et al., Novel strongly correlated europium superhydrides, *The Journal of Physical Chemistry Letters* 12 (1) (2020) 32–40.
- [44] E. P. George, D. Raabe, R. O. Ritchie, High-entropy alloys, *Nature reviews materials* 4 (8) (2019) 515–534.
- [45] M. Rahm, R. Cammi, N. Ashcroft, R. Hoffmann, Squeezing all elements in the periodic table: electron configuration and electronegativity of the atoms under compression, *Journal of the American Chemical Society* 141 (26) (2019) 10253–10271.
- [46] C. W. Glass, A. R. Oganov, N. Hansen, Uspekh—evolutionary crystal structure prediction, *Computer physics communications* 175 (11–12) (2006) 713–720.
- [47] G. Kresse, J. Hafner, Ab initio molecular dynamics for liquid metals, *Physical review B* 47 (1) (1993) 558.
- [48] G. Kresse, J. Furthmüller, J. Hafner, Theory of the crystal structures of selenium and tellurium: the effect of generalized-gradient corrections to the local-density approximation, *Physical Review B* 50 (18) (1994) 13181.
- [49] G. Kresse, J. Furthmüller, Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set, *Computational materials science* 6 (1) (1996) 15–50.
- [50] G. Kresse, J. Furthmüller, Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set, *Physical review B* 54 (16) (1996) 11169.
- [51] J. P. Perdew, K. Burke, M. Ernzerhof, Generalized gradient approximation made simple, *Physical review letters* 77 (18) (1996)

3865.

- [52] P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, et al., Quantum espresso: a modular and open-source software project for quantum simulations of materials, *Journal of physics: Condensed matter* 21 (39) (2009) 395502.
- [53] K. Nakano, K. Hongo, R. Maezono, Phonon dispersions and fermi surfaces nesting explaining the variety of charge ordering in titanium-oxypnictides superconductors, *Scientific reports* 6 (1) (2016) 1–10.
- [54] K. Nakano, K. Hongo, R. Maezono, Investigation into structural phase transitions in layered titanium-oxypnictides by a computational phonon analysis, *Inorganic chemistry* 56 (22) (2017) 13732–13740.
- [55] N. Marzari, D. Vanderbilt, A. De Vita, M. Payne, Thermal contraction and disordering of the al (110) surface, *Physical review letters* 82 (16) (1999) 3296.
- [56] H. Xie, D. Duan, Z. Shao, H. Song, Y. Wang, X. Xiao, D. Li, F. Tian, B. Liu, T. Cui, High-temperature superconductivity in ternary clathrate ycah12 under high pressures, *Journal of Physics: Condensed Matter* 31 (24) (2019) 245404.
- [57] P. Song, Z. Hou, P. B. de Castro, K. Nakano, K. Hongo, Y. Takano, R. Maezono, High-tc ternary metal hydrides, ykh12 and lakh12, discovered by machine learning, *arXiv preprint arXiv:2103.00193* (2021).
- [58] A. Simon, Superconductivity and chemistry, *Angewandte Chemie International Edition in English* 36 (17) (1997) 1788–1806.
- [59] W. Sano, T. Koretsune, T. Tadano, R. Akashi, R. Arita, Effect of van hove singularities on high-t c superconductivity in h 3 s, *Physical Review B* 93 (9) (2016) 094525.
- [60] I. Errea, M. Calandra, C. J. Pickard, J. Nelson, R. J. Needs, Y. Li, H. Liu, Y. Zhang, Y. Ma, F. Mauri, High-pressure hydrogen sulfide from first principles: A strongly anharmonic phonon-mediated superconductor, *Physical review letters* 114 (15) (2015) 157004.
- [61] O. Hellman, I. Abrikosov, S. Simak, Lattice dynamics of anharmonic solids from first principles, *Physical Review B* 84 (18) (2011) 180301.
- [62] J. C. Thomas, A. Van der Ven, Finite-temperature properties of strongly anharmonic and mechanically unstable crystal phases from first principles, *Physical Review B* 88 (21) (2013) 214111.
- [63] T. Chen, D. Shao, P. Lu, X. Wang, J. Wu, J. Sun, D. Xing, Anharmonic effect driven topological phase transition in pb o 2 predicted by first-principles calculations, *Physical Review B* 98 (14) (2018) 144105.