

# Role of hidden spin polarization in non-reciprocal transport of antiferromagnets

Weizhao Chen,<sup>1</sup> Mingqiang Gu,<sup>1</sup> Jiayu Li,<sup>1</sup> Panshuo Wang,<sup>1</sup> and Qihang Liu<sup>1,2,3,\*</sup>

<sup>1</sup>Shenzhen Institute for Quantum Science and Engineering and Department of Physics, Southern University of Science and Technology, Shenzhen 518055, China

<sup>2</sup>Guangdong Provincial Key Laboratory of Computational Science and Material Design, Southern University of Science and Technology, Shenzhen 518055, China

<sup>3</sup>Shenzhen Key Laboratory of for Advanced Quantum Functional Materials and Devices, Southern University of Science and Technology, Shenzhen 518055, China

(Dated: May 20, 2022)

The discovery of hidden spin polarization (HSP) in centrosymmetric nonmagnetic crystals, i.e., spatially distributed spin polarization originated from local symmetry breaking, has promised an expanded material pool for future spintronics. However, the measurements of such exotic effects have been limited to subtle space- and momentum-resolved techniques, unfortunately hindering their applications. Here, we theoretically predict macroscopic non-reciprocal transports induced by HSP when coupling another spatially distributed quantity, such as staggered local moments in a  $PT$ -symmetric antiferromagnet. By using a four-band model Hamiltonian, we demonstrate that HSP plays a crucial role in determining the asymmetric bands with respect to opposite momenta. Such band asymmetry leads to non-reciprocal nonlinear conductivity, exemplified by tetragonal CuMnAs via our first-principles calculations. We further provide the material design principles for large nonlinear conductivity, including two-dimensional nature, multiple band crossings near the Fermi level, and symmetry protected HSP. Our work not only reveals direct spintronic applications of HSP (such as Néel order detection), but also sheds light on finding observables of other hidden effects, such as hidden optical polarization and hidden Berry curvature.

*Introduction.*—According to the seminal works of Dresselhaus and Rashba, spin polarization in nonmagnetic crystals that lack inversion symmetry  $P$  is possible due to the relativistic spin-orbit coupling (SOC) [1, 2]. Recent studies revealed that a related form of hidden spin polarization (HSP) should exist even in centrosymmetric crystals, as long as atomic sites individually break inversion symmetry locally [3, 4]. Such an HSP effect could significantly expand the pool of potential materials for spintronics [5, 6], and provide new physical insights into the relevant hidden physics such as optical polarization, valley polarization, orbital polarization, Berry curvature, etc [7–17]. Owing to the coexistence of  $P$  and time-reversal symmetry  $T$ , the HSP in nonmagnetic materials localized at a sector  $\mathbf{P}_k(r)$  is odd distributed in both real and momentum spaces, i.e.,  $\mathbf{P}_k(r) = -\mathbf{P}_k(-r)$ , and  $\mathbf{P}_k(r) = -\mathbf{P}_{-k}(r)$ . Therefore, while HSP has been successfully measured by techniques with both  $\mathbf{r}$ - and  $\mathbf{k}$ -resolution, such as spin- and angle-resolved photoemission spectroscopy (spin-ARPES) [18–26], its application in spintronics is still hindered by the compensation of polarization originated from the high global symmetry.

To utilize the HSP effect for a macroscopic observation requires breaking both sector and momentum compensation conditions described above, rendering a challenging issue as long as the global symmetry is still maintained. Here we propose a way to manipulate HSP by introducing another odd-distributed quantity  $\mathbf{M}(r)$  to couple  $\mathbf{P}_k(r)$ . The resultant observable  $O(r) = \mathbf{P}(r) \cdot \mathbf{M}(r)$  yields a superposition effect between the two sectors rather than compensation. Specifically, when  $\mathbf{M}(r)$  represents the staggered Néel order in antiferromagnetic (AFM) ma-

terials, the absence of  $T$  also removes the momentum compensation, leading to possible spin-orbitronic applications. Recently, the coupling between the AFM order and SOC-induced spin texture is predicted to induce a spin-orbit torque that can in turn switch the Néel order electrically in antiferromagnets CuMnAs and Mn<sub>2</sub>Au [27, 28]. However, a following experimental study suggested that the thermal effect may reduce the reliability of such electrical switching [29].

In this work, we investigate the non-reciprocal transport in  $PT$ -symmetric antiferromagnets, in which every band is spin degenerate with double degeneracy, yet exhibiting HSP effects due to the local symmetry breaking. Starting from a four-band model and Boltzmann transport theory, we elucidate that by coupling the staggered AFM magnetization, HSP is not only the trigger of non-reciprocal transport but also determines the magnitude of the non-reciprocal nonlinear current (NLC) via the pivot of band asymmetry between opposite momenta  $\pm k$ . Compared with the conventional non-reciprocal transport in nonmagnetic materials lacking inversion symmetry [30, 31], the present proposal takes advantage of the staggered local moments of the material rather than external magnetic fields. To demonstrate our theory, we apply first-principles calculations to simulate the NLC of tetragonal CuMnAs, yielding consistent results with the recent experiment [32], and identify the crucial role of HSP. We then provide the design principle of antiferromagnets with large NLC, including large HSP that could be protected by nonsymmorphic symmetry, band crossings/anticrossings around the Fermi surface, and the nature of low dimension. Our finding reveals a nonzero

macroscopic observable of HSP whose identification is previously limited to space and momentum resolved measurements, paving an avenue for HSP materials in the applications of future AFM spintronics.

*Coupling between hidden SOC and Néel order.*—To elucidate the coupling between the HSP effect and Néel order, we consider  $PT$ -symmetric antiferromagnets. While the global  $PT$  symmetry ensures spin degeneracy throughout the whole Brillouin zone, in real space there could be “sectors” breaking  $PT$  locally and thus manifesting spin polarization owing to the relativistic SOC effect anchored on the nuclear sites. Such a concept of HSP is originally proposed and classified via crystallographic group in nonmagnetic materials with inversion symmetry [3], but can be easily extended to  $PT$ -symmetric antiferromagnets. Taking the tetragonal structure of CuMnAs

as an example [Fig. 1(a)], the two Mn atoms (site symmetry 4mm) in a unit cell with opposite in-plane magnetizations (parallel to the  $x$ -direction) are symmetric with respect to the  $PT$  center, thus belonging to two sectors  $\alpha$  and  $\beta$ , respectively. Therefore, the HSP is defined by projecting the Bloch wavefunctions  $\psi_{nk}$  of the doubly degenerate bands onto a specific sector, say  $\alpha$ ,  $\mathbf{P}_k^\alpha = \sum_{i \in \alpha} \sum_{n \in \mathbb{N}} \langle \psi_{nk} | \boldsymbol{\sigma} \otimes |i\rangle \langle i| \psi_{nk} \rangle$ , where  $k$ ,  $\boldsymbol{\sigma}$ , and  $|i\rangle$  denote the wavevector, Pauli operator, and the localized orbitals belonging to sector  $\alpha$ , respectively.  $\mathbb{N}$  denotes the summation over the two degenerate bands, implying that  $\mathbf{P}_k^\alpha$  is independent of the choice of the wavefunction basis.

We then construct a four-band model Hamiltonian containing both HSP and Néel order as follows:

$$H = \begin{pmatrix} \epsilon_k^\alpha & ((\boldsymbol{\lambda}_k + \mathbf{M}) \cdot \boldsymbol{\sigma})_{12} & t_k & 0 \\ ((\boldsymbol{\lambda}_k + \mathbf{M}) \cdot \boldsymbol{\sigma})_{12}^* & \epsilon_k^\alpha & 0 & t_k \\ t_k^* & 0 & \epsilon_k^\beta & -((\boldsymbol{\lambda}_k + \mathbf{M}) \cdot \boldsymbol{\sigma})_{12} \\ 0 & t_k^* & -((\boldsymbol{\lambda}_k + \mathbf{M}) \cdot \boldsymbol{\sigma})_{12}^* & \epsilon_k^\beta \end{pmatrix}, \quad (1)$$

where  $\epsilon_k^\alpha = \epsilon_k^\beta = \epsilon_k$  is the on-site energy and  $t_k$  is the wavefunction hybridization between the two sectors.  $\boldsymbol{\lambda}_k$  and  $\mathbf{M}$  denote the effective magnetic field caused by SOC and the local moment, respectively. For example, classic Rashba and Dresselhaus effects correspond to  $\boldsymbol{\lambda}_k = \alpha_R(k_y, -k_x, 0)$  and  $\boldsymbol{\lambda}_k = \alpha_D(k_x, -k_y, 0)$ , respectively. Since  $PT$ -symmetry is conserved, there are the two sets of doubly degenerate bands with the eigenvalues  $E_k(\pm) = \epsilon_k \pm \sqrt{|\boldsymbol{\lambda}_k + \mathbf{M}|^2 + |t_k|^2}$ , as shown in Fig. 1(b). The corresponding HSP are  $\mathbf{P}_k(\pm) = \pm(\boldsymbol{\lambda}_k + \mathbf{M})/\sqrt{|\boldsymbol{\lambda}_k + \mathbf{M}|^2 + |t_k|^2}$ , indicating that the hybridization between sectors  $t_k$  is detrimental to the magnitude of HSP.

A key condition to have non-zero macroscopic observable such as non-reciprocal carrier transport is the band asymmetry with respect to opposite vectors, i.e.,  $E_k \neq E_{-k}$  [31, 33]. While such condition is fulfilled when both time-reversal and inversion symmetry are broken, its magnitude, namely,  $\Delta E = E_k - E_{-k}$ , is not determined by symmetry arguments and remains unclear. According to Eq. (1), we analytically obtain:

$$\Delta E(\pm) = \frac{\pm 4P_k^{ave} \boldsymbol{\lambda}_k \cdot \mathbf{M}}{|\boldsymbol{\lambda}_k + \mathbf{M}| + |\boldsymbol{\lambda}_k - \mathbf{M}|}, \quad (2)$$

where  $P_k^{ave} = \{w|P_{+k}^\alpha| + (1-w)|P_{-k}^\alpha|\}$  is the weighted average of HSP with the weight  $w = \sqrt{|\boldsymbol{\lambda}_k + \mathbf{M}|^2 + |t_k|^2} / \{\sqrt{|\boldsymbol{\lambda}_k + \mathbf{M}|^2 + |t_k|^2} + \sqrt{|\boldsymbol{\lambda}_k - \mathbf{M}|^2 + |t_k|^2}\}$ . From Eq. (2) we find that when  $\boldsymbol{\lambda}_k$  is parallel to  $\mathbf{M}$  (e.g., when the polar field is along  $z$ , the local Rashba spin polarization at the

momentum in the  $k_y$  axis is along  $x$ , aligned with the magnetization in CuMnAs), the band asymmetry  $\Delta E = 2\min\{|\boldsymbol{\lambda}_k|, |\mathbf{M}|\}P_k^{ave}$  is proportional to the HSP. On the other hand,  $\Delta E$  vanishes when  $\boldsymbol{\lambda}_k$  is perpendicular to  $\mathbf{M}$ . Eq. (2) clearly shows that in  $PT$ -symmetric antiferromagnets, the cooperation of magnetic order, SOC and local symmetry breaking gives rise to band asymmetry, which further leads to a global non-reciprocal transport behavior, as discussed in the following.

*Non-reciprocal nonlinear conductivity.*—The essence of band asymmetry for the non-reciprocal nonlinear transport is illustrated in Figs. 1(c) and 1(d). Unlike the first-order current caused by the drifting move, the second-order effect of the electrical field  $\mathbf{E}$  originates from the expansion or shrinking of the Fermi surface due to carrier acceleration. In this way, an asymmetric Fermi surface caused by band asymmetry leads to a net nonlinear current [Fig. 1(c)]. Expanding the Boltzmann equation to the second-order with respect to  $\mathbf{E}$  (see Supplementary Section A for details), we obtain a nonlinear current  $j_{2,\gamma} = \sum_{\alpha\beta} \sigma_{\gamma\alpha\beta} E_\alpha E_\beta$  with the coefficient NLC for an energy band as follows:

$$\sigma_{\gamma\alpha\beta} = \frac{e^3 \tau^2}{VN_k} \sum_{k \in BZ} m_{\gamma\alpha}^{-1} v_\beta \frac{\partial f_0}{\partial \epsilon}, \quad (3)$$

where  $\tau$  is the relaxation time and  $m_{\gamma\alpha}^{-1} = \frac{1}{\hbar} \frac{\partial v_\gamma}{\partial k_\alpha}$  is the inverse effective mass with the group velocity  $v$ . We note that Eq. (3) describes the extrinsic NLC, which is equiv-

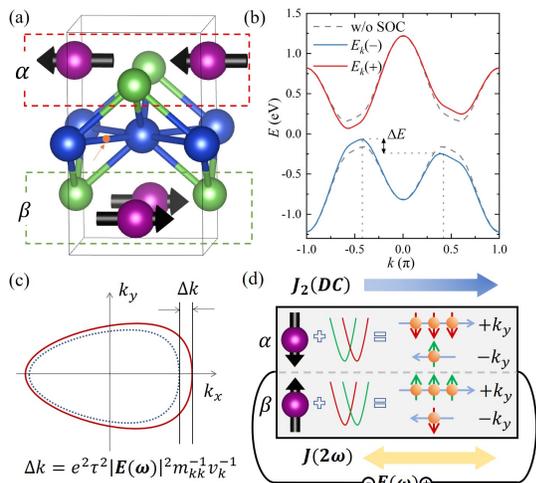


FIG. 1. (a) Crystal structure of CuMnAs as an example of  $PT$ -symmetric antiferromagnets with two sectors  $\alpha$  and  $\beta$  connected by  $PT$  center. (b) The band structure of the four-band Hamiltonian with band asymmetry. The parameters used for calculation are  $t_k = \cos^2 k$ ,  $\epsilon_k = 0.2 \cos k$ ,  $M = 0.2$ , and  $\lambda_k = 0.1 \sin k$  for SOC. (c) Schematic plot of the Fermi surface expansion/shrinking due to the second-order effect of the electrical field. (d) Schematic plot of the formation of longitudinal nonlinear current, which is originated from the coupling between HSP and staggered magnetization.

alent to the other forms of the Drude term used in recent studies by linear response theory and Kubo formula [34–36]. Nevertheless, Eq. (3) explicitly highlights the effective mass as another key ingredient of the nonlinear current.

As shown in Fig. 1(d), given a nonzero  $\sigma_{\gamma\alpha\beta}$ , an electric field  $\mathbf{E}(\omega)$  would drive a nonlinear current  $j_{2,\gamma}$  composed of an alternating current  $J(2\omega)$  with the frequency of  $2\omega$  and a direct current  $J_2$ , leading to the unidirectional magnetoresistance effect [37–39]. Specifically, for an HSP system with local sectors breaking  $PT$ , such as CuMnAs, the forward and backward currents in the  $y$ -direction carry opposite spin polarization ( $\pm x$ ) due to the Rashba-type spin texture and then are scattered by the atomic magnetic moments (along  $x$ ), resulting in a unidirectional current in a single sector. For the other sector, the cooperation of both reversed HSP and magnetic moment leads to a coherent effect. As a result, a longitudinal nonlinear current driven by  $E_y(\omega)$  emerges with a nonzero  $\sigma_{yyy}$ . The nonlinear current has been proposed to be a rectifier [33], while in antiferromagnets it can also be used as the reading head of the Néel order [32, 34, 40].

To further investigate the relationship between band asymmetry and nonlinear current, we simplify Eq. (3) and consider the  $\sigma_{yyy}$  by assuming uniform dispersions along  $k_x$  and  $k_z$ ,

$$\begin{aligned} \sigma_{yyy} &= \frac{e^3 \tau^2}{2\pi V} \{m_{yy}^{-1}(k_F^-) - m_{yy}^{-1}(k_F^+)\} \\ &\approx \frac{e^3 \tau^2}{2\pi V} \left\{ \frac{\partial m_{yy}^{-1}}{\partial \epsilon}(k_F^-) \Delta E + \frac{\partial^2 \Delta E}{\partial k^2} \right\}, \end{aligned} \quad (4)$$

where  $k_F^+(k_F^-)$  is the Fermi vector with the positive (negative) group velocity. Eq. (4) directly explains the relationship between NLC and the band asymmetry  $\Delta E = E(k_F^-) - E(k_F^+)$ , which is characterized by HSP as discussed above. In addition, the first term indicates that large changes in effective mass, such as the tipping point caused by band crossing or anticrossing, could also enhance the conductivity. We next perform the calculation of NLC for CuMnAs based on atomistic Hamiltonians obtained from density-functional theory (DFT) to further show the role of HSP in non-reciprocal transports (based on Eq. (3), see Supplementary Section B for computational methods).

*Nonlinear conductivity in CuMnAs.*—We choose the CuMnAs to identify the characteristics of nonreciprocal NLC and the role of HSP because it is a room-temperature,  $PT$ -symmetric, antiferromagnetic metal with intriguing Dirac fermions in various structures [41–43], rendering a nice platform for novel transport properties. While recent works study its intrinsic nonlinear Hall effect, which is related to the Berry curvature of the material [44, 45], we focus on the extrinsic current related to impurities scattering that can be either longitudinal or transverse. According to Eq. (2), the coupling between the Mn local moment  $M_x$  and the in-plane Rashba field generates a nonzero longitudinal NLC along  $y$ , i.e.,  $\sigma_{yyy}$ , as discussed in the following, while the transverse NLC component  $\sigma_{yxx}$  has similar behavior (see Supplementary Section C).

To demonstrate the role of HSP in non-reciprocal transports, we first calculate the NLC in a CuMnAs thin film with the thickness of two primitive cells and discuss the results of the bulk later. The calculated  $\sigma_{yyy}$  as a function of the chemical potential  $\mu$  is shown in Fig. 2(a), where a large and sharp peak appears at  $\mu = 0.22$  eV accompanied by some oscillations. To reveal the origin of this peak, we decompose  $\sigma_{yyy}$  onto the contributions from different bands around the Fermi energy. Three pairs of doubly degenerate bands, i.e., the highest valence bands VB-1,2, and the lowest conduction bands CB-1,2 and CB-3,4 are thus involved. As shown in Fig. 2(b), around  $\mu = 0.22$  eV the NLC from CB-1,2 shows a negative peak followed by a positive one, while that of CB-3,4 shows positive and negative peaks sequentially. The two positive peaks happen to overlap each other and contribute to the peak of total NLC as denoted by the black arrow in Fig. 2(b).

From the band structure shown in Fig. 2(c), we find that the band asymmetry between the M-Y and M'-Y ensures the existence of the NLC. Specifically, the Dirac

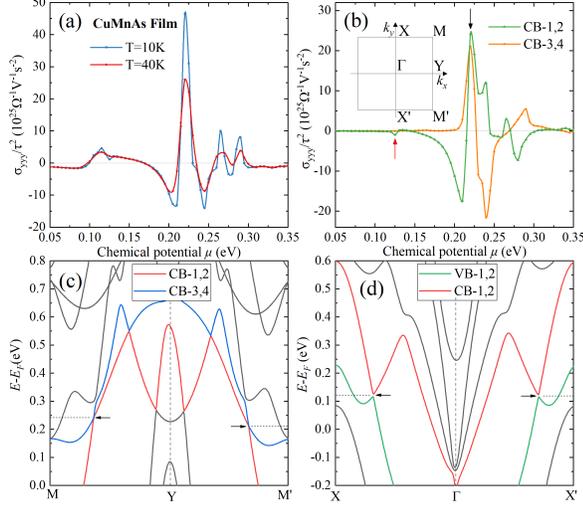


FIG. 2. (a) Nonlinear conductivity  $\sigma_{yyy}$  of CuMnAs film with a thickness of two primitive cells as a function of the chemical potential  $\mu$  with different temperatures. (b) The band-decomposed  $\sigma_{yyy}$  of CuMnAs film, where a small peak and a large peak for CB-1,2 are marked by the red and black arrows, respectively. The inset shows the two-dimensional Brillouin zone. (c) Band structure for the  $k$ -path along M-M', where the type-II Dirac points are marked by the black arrows. (d) Band structure for the  $k$ -path along X-X', where the band anticrossings are marked by the black arrows.

cone along M-Y is 0.29 eV higher than that along M'-Y, as denoted by the black arrows in Fig. 2(c). Further analysis reveals that these type-II Dirac points formed by CB-1,2 and CB-3,4 around  $\mu = 0.22$  eV, lead to the large NLC peak and oscillations in Fig. 2(b). Furthermore, these Dirac points induce discontinuous effective mass and thus significantly enhance the NLC effect according to Eq. (4). We also notice that there is another small peak at  $\mu \sim 0.12$  eV for the decomposed NLC from CB-1,2, as denoted by the red arrow in Fig. 2(b). This peak is caused by the band anticrossing between VB-1,2 and CB-1,2 along the  $k$ -path X-X' as shown in Fig. 2(d). The comparison between this small peak to the large peak at 0.22 eV reveals the important role of HSP to the non-reciprocal NLC.

We next project the Bloch wavefunctions onto the magnetic Mn atoms and calculate the HSP  $P_k^\alpha(\text{Mn})$ . Fig. 3(a) shows  $P_k^\alpha(\text{Mn})$  of CB-1,2 and CB-3,4 along M-Y-M', where two Dirac points are clearly presented with a momentum offset, indicating the band asymmetry. We find that both bands manifest large HSP, with one of them approaching almost 100% polarization. In sharp contrast,  $P_k^\alpha(\text{Mn})$  of VB-1,2 and CB-1,2 along X- $\Gamma$ -X' is much smaller, as shown in Fig. 3(b). Such significant difference in HSP is caused by the nonsymmorphic structure of CuMnAs. The glide mirror reflection minimizes the spin

compensation between different sectors at the boundary of the Brillouin zone M-Y-M', thus retaining the HSP in each sector [6, 26]. When multiple-orbital characters and sector hybridization are involved, the HSP is suppressed accordingly.

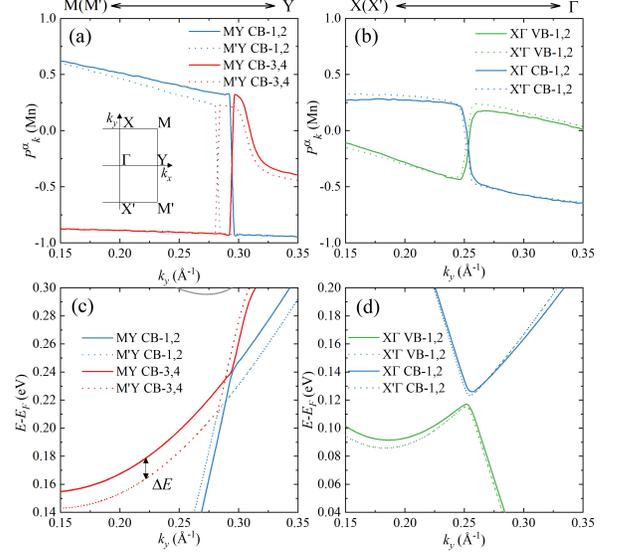


FIG. 3. The magnitude of HSP  $P_k^\alpha(\text{Mn})$  for the corresponding bands in the  $k$ -path along (a) M-M' with the type-II Dirac points and (b) X-X' with the band anticrossings. The band structures of CuMnAs film for the  $k$ -path along (a) M-M' with the type-II Dirac points and (b) X-X' with the band anticrossings. The bands are folded with respect to Y and  $\Gamma$  to show the band asymmetry  $\Delta E$  clearly. The solid and dashed lines represent the  $k$ -path M-Y (X- $\Gamma$ ) and M'-Y (X'- $\Gamma$ ), respectively.

As shown in Eq. (2), the HSP closely correlates the band asymmetry  $\Delta E$ . This is further illustrated in Figs. 3(c) and 3(d), where we fold the band structures along M-Y-M and X- $\Gamma$ -X with respect to Y and  $\Gamma$ , respectively, with the bands with  $\pm k_y$  plotted on top of each other. As shown in Fig. 3(c), the large band asymmetry  $\Delta E$  (about 17 meV) is attributed to the nearly 100%  $P_k^\alpha(\text{Mn})$  around the Dirac cone, while  $\Delta E$  around the band anticrossing in Fig. 3(d) is rather small with only 4 meV. As a result, the comparison between  $\Delta E$  gives rise to the sharp contrast of the two peaks of NLC in Fig. 2(b), fully consistent with Eq. (4). The above analysis clearly highlights the significant role of HSP in the generation of nonlinear current: The required local symmetry breaking determines the existence of the nonlinear current in the AFM system with  $PT$  symmetry; more importantly, it is also a key factor to the magnitude of NLC. Moreover, it is worth mentioning that HSP also has an effect on the critical temperature of NLC (see Supplementary Section D).

*Design principles.*—Before uncovering the design principles of large non-reciprocal NLC, we calculate the NLC

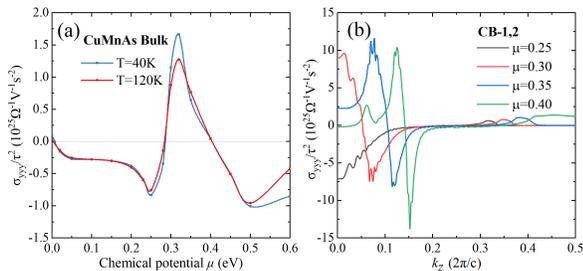


FIG. 4. (a) Nonlinear conductivity  $\sigma_{yyy}$  of Bulk CuMnAs as a function of chemical potential  $\mu$  with different temperatures. (b) The  $k_z$ -resolved conductivity  $\sigma_{yyy}$  with different chemical potential  $\mu$ .

of 3D bulk CuMnAs for comparison. Fig. 4(a) shows the  $\sigma_{yyy}$  as a function of the chemical potential  $\mu$ . It is found that similar with the 2D case, at around  $\mu = 0.3$  eV the type-II Dirac points induce a peak accompanied by oscillation, but the peak of bulk CuMnAs is one order of magnitude smaller than that of the thin film. To understand this, we resort to the  $k_z$ -resolved NLC, integrating over the  $k_x$ - $k_y$  plane. As shown in Fig. 4(b), the resolved  $\sigma_{yyy}$  as the function of  $k_z$  is composed of a positive peak followed by a negative peak, resulting in significant compensation over the integration. This feature essentially originates from the shift of Dirac cones in the energy scale with increasing  $k_z$  (see Supplementary Section E), implying that a small energy dispersion along  $k_z$  or reducing the size from the bulk to thin film would suppress the compensation and thus enhance the magnitude of NLC. In this sense, a (quasi-) 2D system with quantum confinement along the  $z$ -direction is highly favorable for designing an NLC device.

Except for reducing the dimension, more design principles for  $PT$ -symmetric antiferromagnets with advanced non-reciprocal transport properties are also revealed by the case of CuMnAs. First of all, a collinear Néel order that couples HSP induced by local symmetry breaking is the precondition for the existence of nonzero NLC. Secondly, nonsymmorphic symmetry could retain large HSP, which also determines the magnitude of band asymmetry and NLC. Moreover, the band crossing and anticrossing from specific band inversion around the Fermi level serve as another amplifier of extrinsic NLC because of the large effective mass change. Interestingly, the intrinsic non-reciprocal transport, e.g., nonlinear Hall conductivity, is also associated with band anticrossings due to the large Berry curvature [44, 45], while here we take advantage of the band crossing and anticrossing for their abrupt change of the effective mass.

*Discussion.*—By coupling HSP with another spatially distributed quantity such as the Néel order of  $PT$ -symmetric antiferromagnets, we show that a macroscopic measurable quantity, such as high-order non-reciprocal

transport, could emerge. Such finding expands the conventional detection of HSP that requires both space and momentum resolution, and proposes specific applications in antiferromagnetic spintronics, such as the identification and manipulation of Néel order [32]. To manifest a large NLC, the design principle of material candidates is favorable to include two-dimensional nature, multiple band crossings/anticrossings near the Fermi level, and symmetry protected HSP.

More importantly, the basic idea of cooperating two spatially odd-distributed quantities opens a new avenue for exotic phenomena in the systems with various hidden effects. For example, coupling between the electron velocity (odd in position space) and the local spin polarization leads to a second-order spin photogalvanic effect [46, 47], which can be understood as an optical response in the HSP system. A recent proposal of inverse Faraday effect in Weyl semimetals adopts a similar strategy [48], which could be migrated to  $PT$ -symmetric HSP system. A more generic picture can be grasped by considering the orbital Hall effect in centrosymmetric materials, which originates from the coupling of hidden Berry curvature and hidden orbital polarization [49, 50]. Very recently, the nontrivial transport response originated from the coupling between the hidden Berry curvature and the Néel order is reported, dubbed as layer Hall effect [51]. Overall, the non-reciprocal transport proposed by our work is a comprehensive demonstration of such effects, hopefully triggering future studies to unveil practical applications of hidden physical quantities.

This work was supported by National Key R&D Program of China under Grant No. 2020YFA0308900, the National Natural Science Foundation of China under Grant No. 11874195, Guangdong Provincial Key Laboratory for Computational Science and Material Design under Grant No. 2019B030301001, the Science, Technology and Innovation Commission of Shenzhen Municipality (No. ZDSYS20190902092905285) and Center for Computational Science and Engineering of Southern University of Science and Technology.

\* Corresponding Author: liuqh@sustech.edu.cn

- [1] G. Dresselhaus, Spin-Orbit Coupling Effects in Zinc Blende Structures, *Phys. Rev.* **100**, 580 (1955).
- [2] Y. A. Bychkov, E.I. Rashba, Properties of a 2D electron gas with lifted spectral degeneracy, *Soviet Journal of Experimental and Theoretical Physics Letters* **39(2)**, 78 (1984).
- [3] X. Zhang, Q. Liu, J.-W. Luo, A.J. Freeman, A. Zunger, Hidden spin polarization in inversion-symmetric bulk crystals, *Nat. Phys.* **10**, 387-393 (2014).
- [4] Q. Liu, Y. Guo, A.J. Freeman, Tunable Rashba effect in two-dimensional LaOBiS<sub>2</sub> films: ultrathin candidates for spin field effect transistors, *Nano Lett.* **13** 5264-5270 (2013).

- [5] Q. Liu, X. Zhang, H. Jin, K. Lam, J. Im, A.J. Freeman, A. Zunger, Search and design of nonmagnetic centrosymmetric layered crystals with large local spin polarization, *Phys. Rev. B* **91**, 235204 (2015).
- [6] Y. Zhang, P. Liu, H. Sun, S. Zhao, H. Xu, Q. Liu, Symmetry-Assisted Protection and Compensation of Hidden Spin Polarization in Centrosymmetric Systems, *Chin. Phys. Lett.* **37**, 087105 (2020).
- [7] R. Suzuki, M. Sakano, Y.J. Zhang, R. Akashi, D. Morikawa, A. Harasawa, K. Yaji, K. Kuroda, K. Miyamoto, T. Okuda, K. Ishizaka, R. Arita, Y. Iwasa, Valley-dependent spin polarization in bulk MoS<sub>2</sub> with broken inversion symmetry, *Nat. Nanotech.* **9**, 611-617 (2014).
- [8] Q. Liu, X. Zhang, A. Zunger, Intrinsic circular polarization in centrosymmetric stacks of transition-metal dichalcogenide compounds, *Phys. Rev. Lett.* **114**, 087402 (2015).
- [9] R. Gautier, J.M. Klingsporn, R.P. Van Duyne, K.R. Poeppelmeier, Optical activity from racemates, *Nat. Mater.* **15**, 591-592 (2016).
- [10] J.H. Ryoo, C.-H. Park, Hidden orbital polarization in diamond, silicon, germanium, gallium arsenide and layered materials, *NPG Asia Materials* **9**, e382-e382 (2017).
- [11] S. Beaulieu, J. Schusser, S. Dong, M. Schuler, T. Pincelli, M. Dendzik, J. Maklar, A. Neef, H. Ebert, K. Hricovini, M. Wolf, J. Braun, L. Rettig, J. Minar, R. Ernstorfer, Revealing Hidden Orbital Pseudospin Texture with Time-Reversal Dichroism in Photoelectron Angular Distributions, *Phys. Rev. Lett.* **125**, 216404 (2020).
- [12] S. Cho, J.H. Park, J. Hong, J. Jung, B.S. Kim, G. Han, W. Kyung, Y. Kim, S.K. Mo, J.D. Denlinger, J.H. Shim, J.H. Han, C. Kim, S.R. Park, Experimental Observation of Hidden Berry Curvature in Inversion-Symmetric Bulk 2H-WSe<sub>2</sub>, *Phys. Rev. Lett.* **121**, 186401 (2018).
- [13] Michael Schüler, Umberto De Giovannini, Hannes Hübener, Angel Rubio, Michael A. Sentef, P. Werner, Local Berry curvature signatures in dichroic angle-resolved photoelectron spectroscopy from two-dimensional materials, *Sci. Adv.* **6**, eaay2730 (2020).
- [14] C. Wang, B. Lian, X. Guo, J. Mao, Z. Zhang, D. Zhang, B.L. Gu, Y. Xu, W. Duan, Type-II Ising Superconductivity in Two-Dimensional Materials with Spin-Orbit Coupling, *Phys. Rev. Lett.* **123**, 126402 (2019).
- [15] Joseph Falson, Yong Xu, Menghan Liao, Yunyi Zang, Kejing Zhu, Chong Wang, Zetao Zhang, Hongchao Liu, Wenhui Duan, Ke He, Haiwen Liu, Jurgen H. Smet, Ding Zhang, Q.-K. Xue, Type-II Ising pairing in few-layer stanene, *Science* **367**, 1454C1457 (2020).
- [16] L. Yuan, Q. Liu, X. Zhang, J.W. Luo, S.S. Li, A. Zunger, Uncovering and tailoring hidden Rashba spin-orbit splitting in centrosymmetric crystals, *Nat. Commun.* **10**, 906 (2019).
- [17] S. Guan, J.-X. Xiong, Z. Wang, J.-W. Luo, Progress of hidden spin polarization in inversion-symmetric crystals, *Science China Physics, Mechanics & Astronomy* **65**, No. 3: 237301 (2022).
- [18] J.M. Riley, F. Mazzola, M. Dendzik, M. Michiardi, T. Takayama, L. Bawden, C. Granerød, M. Leandersson, T. Balasubramanian, M. Hoesch, T.K. Kim, H. Takagi, W. Meevasana, P. Hofmann, M.S. Bahramy, J.W. Wells, P.D.C. King, Direct observation of spin-polarized bulk bands in an inversion-symmetric semiconductor, *Nat. Phys.* **10**, 835-839 (2014).
- [19] E. Razzoli, T. Jaouen, M.L. Mottas, B. Hildebrand, G. Monney, A. Pisoni, S. Muff, M. Fanciulli, N.C. Plumb, V.A. Rogalev, V.N. Strocov, J. Mesot, M. Shi, J.H. Dil, H. Beck, P. Aebi, Selective Probing of Hidden Spin-Polarized States in Inversion-Symmetric Bulk MoS<sub>2</sub>, *Phys. Rev. Lett.* **118**, 086402 (2017).
- [20] S.L. Wu, K. Sumida, K. Miyamoto, K. Taguchi, T. Yoshikawa, A. Kimura, Y. Ueda, M. Arita, M. Nagao, S. Watauchi, I. Tanaka, T. Okuda, Direct evidence of hidden local spin polarization in a centrosymmetric superconductor LaO<sub>0.55</sub>F<sub>0.45</sub>BiS<sub>2</sub>, *Nat. Commun.* **8**, 1919 (2017).
- [21] W. Yao, E. Wang, H. Huang, K. Deng, M. Yan, K. Zhang, K. Miyamoto, T. Okuda, L. Li, Y. Wang, H. Gao, C. Liu, W. Duan, S. Zhou, Direct observation of spin-layer locking by local Rashba effect in monolayer semiconducting PtSe<sub>2</sub> film, *Nat. Commun.* **8**, 14216 (2017).
- [22] M. Gehlmann, I. Aguilera, G. Bihlmayer, E. Mlynczak, M. Eschbach, S. Doring, P. Gospodaric, S. Cramm, B. Kardynal, L. Plucinski, S. Blugel, C.M. Schneider, Quasi 2D electronic states with high spin-polarization in centrosymmetric MoS<sub>2</sub> bulk crystals, *Sci. Rep.* **6**, 26197 (2016).
- [23] Kenneth Gotlieb, Chiu-Yun Lin, Maksym Serbyn, Wentao Zhang, Christopher L. Smallwood, Christopher Jozwiak, Hiroshi Eisaki, Zahid Hussain, Ashvin Vishwanath, A. Lanzara, Revealing hidden spin-momentum locking in a high-temperature cuprate superconductor, *Science* **362**, 1271-1275 (2018).
- [24] G. Gatti, D. Gosálbez-Martnez, S. Roth, M. Fanciulli, M. Zacchigna, M. Kalläne, K. Rossnagel, C. Jozwiak, A. Bostwick, E. Rotenberg, A. Magrez, H. Berger, I. Vobornik, J. Fujii, O.V. Yazyev, M. Grioni, A. Crepaldi, Hidden bulk and surface effects in the spin polarization of the nodal-line semimetal ZrSiTe, *Communications Physics* **4**(1), 1-9 (2021).
- [25] H.J. Qian, X. Zhang, C.M. Liu, Q. Jiang, W.J. Liu, H.M. Zha, D.Y. Wang, X.P. Shen, M. Ye, Y.F. Guo, S. Qiao, Layer-locked spin states revealed in the centrosymmetric nodal-line semimetal HfSiS, *Phys. Rev. B*, **104**, 035145 (2021).
- [26] K. Zhang, S. Zhao, Z. Hao, S. Kumar, E.F. Schwier, Y. Zhang, H. Sun, Y. Wang, Y. Hao, X. Ma, C. Liu, L. Wang, X. Wang, K. Miyamoto, T. Okuda, C. Liu, J. Mei, K. Shimada, C. Chen, Q. Liu, Observation of Spin-Momentum-Layer Locking in a Centrosymmetric Crystal, *Phys. Rev. Lett.* **127**, 126402 (2021).
- [27] J. Zelezny, H. Gao, K. Vyborny, J. Zemen, J. Masek, A. Manchon, J. Wunderlich, J. Sinova, T. Jungwirth, Relativistic Neel-order fields induced by electrical current in antiferromagnets, *Phys. Rev. Lett.* **113**, 157201 (2014).
- [28] P. Wadley, B. Howells, J. Železný, C. Andrews, V. Hills, R. P. Campion, V. Novák, K. Olejník, F. Maccherozzi, S. S. Dhesi, S. Y. Martin, T. Wagner, J. Wunderlich, F. Freimuth, Y. Mokrousov, J. Kuneš, J. S. Chauhan, M. J. Grzybowski, A. W. Rushforth, K.W. Edmonds, B. L. Gallagher, T. Jungwirth, Electrical switching of an antiferromagnet, *Science* **351**, 587 (2016).
- [29] C.C. Chiang, S.Y. Huang, D. Qu, P.H. Wu, C.L. Chien, Absence of Evidence of Electrical Switching of the Antiferromagnetic Néel Vector, *Phys. Rev. Lett.* **123**, 227203 (2019).
- [30] T. Ideue, K. Hamamoto, S. Koshikawa, M. Ezawa, S. Shimizu, Y. Kaneko, Y. Tokura, N. Nagaosa, Y. Iwasa,

- Bulk rectification effect in a polar semiconductor, *Nat. Phys.* **13**, 578-583 (2017).
- [31] Y. Tokura, N. Nagaosa, Nonreciprocal responses from non-centrosymmetric quantum materials, *Nat. Commun.* **9**, 3740 (2018).
- [32] J. Godinho, H. Reichlova, D. Kriegner, V. Novak, K. Olejnik, Z. Kaspar, Z. Soban, P. Wadley, R.P. Campion, R.M. Otxoa, P.E. Roy, J. Zelezny, T. Jungwirth, J. Wunderlich, Electrically induced and detected Neel vector reversal in a collinear antiferromagnet, *Nat. Commun.* **9**, 4686 (2018).
- [33] Hiroki Isobe, Su-Yang Xu, L. Fu, High-frequency rectification via chiral Bloch electrons, *Sci. Adv.* **6** eaay2497 (2020).
- [34] H. Watanabe, Y. Yanase, Nonlinear electric transport in odd-parity magnetic multipole systems: Application to Mn-based compounds, *Phys. Rev. Research* **2**, 043081 (2020).
- [35] J. Železný, Z. Fang, K. Olejník, J. Patchett, F. Gerhard, C. Gould, L.W. Molenkamp, C. Gomez-Olivella, J. Zemen, T. Tichý, T. Jungwirth, C. Ciccarelli, Unidirectional magnetoresistance and spin-orbit torque in NiMnSb, *Phys. Rev. B* **104**, 054429 (2021).
- [36] M. Razeghi, J.-E. Wegrowe, H.-J. Drouhin, H. Jaffrès, G. Vignale, S. Zhang, Theory of bilinear magneto-electric resistance from topological-insulator surface states, *Spintronics XI* (Vol. 10732, p. 1073215) (2018).
- [37] T. Guillet, C. Zucchetti, Q. Barbedienne, A. Marty, G. Isella, L. Cagnon, C. Vergnaud, H. Jaffres, N. Reyren, J.M. George, A. Fert, M. Jamet, Observation of Large Unidirectional Rashba Magnetoresistance in Ge(111), *Phys. Rev. Lett.* **124**, 027201 (2020).
- [38] K. Olejník, V. Novák, J. Wunderlich, T. Jungwirth, Electrical detection of magnetization reversal without auxiliary magnets, *Phys. Rev. B*, **91** 180402(R) (2015).
- [39] C.O. Avci, K. Garello, A. Ghosh, M. Gabureac, S.F. Alvarado, P. Gambardella, Unidirectional spin Hall magnetoresistance in ferromagnet/normal metal bilayers, *Nat. Phys.* **11**, 570-575 (2015).
- [40] D.F. Shao, S.H. Zhang, G. Gurung, W. Yang, E.Y. Tsymbal, Nonlinear Anomalous Hall Effect for Néel Vector Detection, *Phys. Rev. Lett.* **124**, 067203 (2020).
- [41] Peizhe Tang, Quan Zhou, Gang Xu, S.-C. Zhang, Dirac fermions in an antiferromagnetic semimetal, *Nat. Phys.* **12**, 1100 (2016).
- [42] L. Smejkal, J. Zelezny, J. Sinova, T. Jungwirth, Electric Control of Dirac Quasiparticles by Spin-Orbit Torque in an Antiferromagnet, *Phys. Rev. Lett.* **118** 106402 (2017).
- [43] S.-G. Xu, Z.-J. Chen, X.-B. Chen, Y.-J. Zhao, H. Xu, X. Zhang, Dirac fermions in the antiferromagnetic spintronics material CuMnAs, *Phys. Rev. B* **102**, 125123 (2020).
- [44] C. Wang, Y. Gao, D. Xiao, Intrinsic Nonlinear Hall Effect in Antiferromagnetic Tetragonal CuMnAs, *Phys. Rev. Lett.* **127**, 277201 (2021).
- [45] H. Liu, J. Zhao, Y.X. Huang, W. Wu, X.L. Sheng, C. Xiao, S.A. Yang, Intrinsic Second-Order Anomalous Hall Effect and Its Application in Compensated Antiferromagnets, *Phys. Rev. Lett.* **127**, 277202 (2021).
- [46] R. Fei, W. Song, L. Pusey-Nazzaro, L. Yang, *PT*-Symmetry-Enabled Spin Circular Photogalvanic Effect in Antiferromagnetic Insulators, *Phys. Rev. Lett.* **127**, 207402 (2021).
- [47] H. Xu, H. Wang, J. Zhou, J. Li, Pure spin photocurrent in non-centrosymmetric crystals: bulk spin photovoltaic effect, *Nat. Commun.* **12**(1), 1-9 (2021).
- [48] Yang Gao, Chong Wang, D. Xiao, Topological Inverse Faraday Effect in Weyl Semimetals, arXiv:2009.04140 (2020).
- [49] L. Du, Comment on “Disentangling Orbital and Valley Hall Effects in Bilayers of Transition Metal Dichalcogenides”, *Phys. Rev. Lett.* **127**, 149701 (2021).
- [50] T.P. Cysne, M. Costa, L.M. Canonico, M.B. Nardelli, R.B. Muniz, T.G. Rappoport, Disentangling Orbital and Valley Hall Effects in Bilayers of Transition Metal Dichalcogenides, *Phys. Rev. Lett.* **126**, 056601 (2021).
- [51] A. Gao, Y.F. Liu, C. Hu, J.X. Qiu, C. Tzschaschel, B. Ghosh, S.C. Ho, D. Berube, R. Chen, H. Sun, Z. Zhang, X.Y. Zhang, Y.X. Wang, N. Wang, Z. Huang, C. Felser, A. Agarwal, T. Ding, H.J. Tien, A. Akey, J. Gardener, B. Singh, K. Watanabe, T. Taniguchi, K.S. Burch, D.C. Bell, B.B. Zhou, W. Gao, H.Z. Lu, A. Bansil, H. Lin, T.R. Chang, L. Fu, Q. Ma, N. Ni, S.Y. Xu, Layer Hall effect in a 2D topological axion antiferromagnet, *Nature* **595**, 521-525 (2021).