

Enhanced thermally-activated skyrmion diffusion in synthetic antiferromagnetic systems with tunable effective topological charge

Takaaki Dohi^{1*}, Markus Weißenhofer^{2*}, Nico Kerber^{1,3}, Fabian Kammerbauer¹, Yuqing Ge¹, Klaus Raab¹,
Jakub Zázvorka⁴, Maria-Andromachi Syskaki^{1,5}, Aga Shahee¹, Moritz Ruhwedel⁶, Tobias Böttcher^{3,6},
Philipp Pirro⁶, Gerhard Jakob^{1,3}, Ulrich Nowak², and Mathias Kläui^{1,3*}

¹ Institut für Physik, Johannes Gutenberg-Universität Mainz, Staudingerweg 7, 55128 Mainz, Germany

² Fachbereich Physik, Universität Konstanz, DE-78457 Konstanz, Germany

³ Graduate School of Excellence Materials Science in Mainz, Staudingerweg 9, 55128 Mainz, Germany

⁴ Institute of Physics, Faculty of Mathematics and Physics, Charles University, Ke Karlovu 5, Prague 12116,
Czech Republic

⁵ Singulus Technologies AG, 63796 Kahl am Main, Germany

⁶ Fachbereich Physik and Landesforschungszentrum OPTIMAS, Technische Universität Kaiserslautern,
Gottlieb-Daimler-Straße 46, 67663 Kaiserslautern, Germany

E-mail addresses

Dr. Takaaki Dohi: tdohi@uni-mainz.de

Dr. Markus Weißenhofer: markus.weissenhofer@uni-konstanz.de

Prof. Dr. Mathias Kläui: klaeui@uni-mainz.de

Abstract

Magnetic skyrmions, topologically-stabilized spin textures that emerge in particular magnetic systems, have attracted attention due to a variety of electromagnetic responses that are governed by the topology. A well-studied effect of topology on the deterministic and drift motion under a nonequilibrium excitation is the so-called skyrmion Hall effect. For stochastic diffusive motion, the effect of topology is expected to have a drastically stronger impact, but the predicted even qualitative impact has not been demonstrated. The required tuning of the topology to achieve zero effective topological charge can be achieved using antiferromagnetic skyrmions. However, the diffusive motion has previously not been observed due to strong pinning in ferrimagnets and intrinsic antiferromagnets. Here we demonstrate enhanced thermally-activated diffusive motion of skyrmions in a specifically designed synthetic antiferromagnet where the topology can be tuned. Suppressing the effective topological charge for synthetic antiferromagnetic skyrmions leads to a more than 10 times enhanced diffusion coefficient as compared to ferromagnetic skyrmions. By varying the topology, we can not only demonstrate the topology-dependence of the diffusion coefficient but also enable ultimately energy-efficient unconventional computing that is actively making use of the stochasticity.

Magnetic skyrmions are topologically-stabilized spin textures¹⁻⁸ that exhibit an intriguing dynamics governed by their topology⁹⁻¹³. In particular, in thin film systems it has been well known that magnetic skyrmions can be stabilized above room temperature with fixed chirality determined by the Dzyaloshinskii-Moriya interaction (DMI) induced at the heavy metal (HM)/ferromagnet (FM) interface^{4,14-18}. Simultaneously, the adjacent HM produces a spin-orbit torque (SOT)¹⁹ allowing for manipulation of the magnetic skyrmions by electrical means, which is an essential function for skyrmion electronics often termed skyrmionics^{4,5,8,20,21}.

Recent material development of ultralow pinning systems hosting magnetic skyrmion has led to the successful observation of thermally-activated diffusive skyrmion dynamics²²⁻²⁵. The magnetic skyrmions exhibit Brownian-like motion generated by the thermal fluctuation leading to a linear time dependence of the mean-squared displacement (MSD)^{22,26-29}. Such stochastic dynamics of the magnetic skyrmions has been suggested for ultimately energy-efficient unconventional computing^{22,30,31}.

So far most studies of the impact of skyrmion topology on the dynamics have focused on deterministic current-driven skyrmion dynamics. For such drift motion the skyrmion Hall effect^{11,12,32-34}, which is a perpendicular motion component to the current flow direction, has been observed. This is an archetypal example of the strong topology-dependence of magnetic skyrmion dynamics. While the effect of topology on the deterministic current-induced drift motion of magnetic skyrmions has been well studied, for the diffusive motion regime so far only the intriguing theoretical predictions have been made. In particular, it was calculated that the gyrotropic force originating from the finite topology gives rise to a drastic decrease of the diffusion coefficient via a different dependence on the damping as compared to topologically trivial structures²⁶⁻²⁸. So to

maximize diffusive dynamics, one needs to be able to tailor the skyrmion topology and reduce the effective topological charge.

A possible approach is antiferromagnetically-coupled skyrmions having opposite topological charge in the two sub-lattices that allow for the control of the effective topological charge through the compensation of angular momentum in the two sub-lattices³⁵⁻⁴¹. However, typical intrinsic crystalline antiferromagnets or ferrimagnets have been found to exhibit strong pinning^{40,41} making these systems not suitable for the observation of diffusive motion.

Here we demonstrate that an amorphous-like synthetic antiferromagnetic (SyAFM) system with low pinning enables us to observe a thermally-activated diffusive motion of antiferromagnetically-coupled skyrmions. The systematic investigation varying the compensation ratio of magnetic moments in the magnetic layers allows us to flexibly tune the topology. By accounting for pinning effects, we can directly demonstrate the influence of the topology of the diffusive motion. Our analysis reveals a more than 10 times larger diffusion coefficient for highly compensated antiferromagnetically-coupled skyrmions that is a direct consequence of the reduction of the effective topological charge, which provides crucial insights into the thermally-activated dynamics of the topological objects in antiferromagnetic systems.

Experimental setup and magnetic properties

A schematic of the experimental setup is shown in Fig. 1a, where magnetic thin films are placed on Peltier modules to investigate diffusive motion of magnetic skyrmions imaged by a magneto-optical Kerr effect (MOKE) microscope in a polar configuration. While ferrimagnets or crystalline intrinsic antiferromagnets have been

shown to exhibit strong skyrmion pinning^{40,41}, the advantage of SyAFM systems is to use low pinning magnetic materials such as CoFeB⁴². Our SyAFM systems consist of Ta(5.0)/ Pt(1.03)/ Co_{0.60}Fe_{0.20}B_{0.20}(*t*_{CFB1})/ Co_{0.20}Fe_{0.60}B_{0.20}(*t*_{FCB1})/ Ir(1.20)/ Co_{0.60}Fe_{0.20}B_{0.20}(*t*_{CFB2})/ Co_{0.20}Fe_{0.60}B_{0.20}(*t*_{FCB2})/ Ru(1.0) (in nm) where *t*_{CFB} and *t*_{FCB} are tuned to control magnetic properties such as the compensation ratio of magnetic moments (see Methods for more details). As a reference, a FM bi-layer stack consisting of Ta(5.0)/ Pt(1.03)/ Co_{0.60}Fe_{0.20}B_{0.20}(0.5)/ Co_{0.20}Fe_{0.60}B_{0.20}(0.35)/ Ir(1.60)/ Co_{0.60}Fe_{0.20}B_{0.20}(0.5)/ Co_{0.20}Fe_{0.60}B_{0.20}(0.35)/ Ru(1.0) is prepared. The Ir thickness is controlled to tailor the sign and the strength of interlayer exchange coupling (see Supplementary Note 1).

Figure 1b shows magnetization curves (*m*-*H* curves) for the FM bi-layer and SyAFM systems. Note that measurements are conducted near the temperature at which the diffusive motion of skyrmions can be measured in the SyAFM systems for accurate determination of the compensation ratio $m_{\text{Com}} = 1 - |M_1 + M_2| / (|M_1| + |M_2|)$, $M_1 = m_{\text{CFB1}} + m_{\text{FCB1}}$ (the bottom FM's magnetic moment), $M_2 = m_{\text{CFB2}} + m_{\text{FCB2}}$ (the top FM's magnetic moment). We intentionally tailor the maximum compensation ratio to be ~90% to still allow for the observation using MOKE while keeping $M_2 > M_1$ to make use of the surface sensitivity⁴³ (see Methods and Supplementary Note 2). As shown in Fig. 1b, all used SyAFM systems exhibit a spin-flop transition indicating that the effective magnetic anisotropy energy density is smaller than the interlayer exchange coupling $K_{\text{eff}} < -J_{\text{int}}/(t_{\text{CFB}} + t_{\text{FCB}})$, facilitating the emergence of antiferromagnetically-coupled magnetic domain states^{37,38,44} at zero magnetic field, which however stay always coupled in our experiments (see Supplementary Note 3).

Thermally-activated skyrmion diffusion and its temperature dependence

Magnetic skyrmions are nucleated using magnetic in-plane field pulses, where the strength of the pulses is tuned to control the density of magnetic skyrmions. Fig. 2a shows the observed SyAFM skyrmions for $m_{\text{Com}} = 75\%$ at $T = 320.7$ K. We find that the SyAFM skyrmions clearly exhibit thermally-activated diffusive motion as shown in Fig. 2b (also, see Supplementary video 1). The SyAFM skyrmions are tracked in a similar manner as established for FM skyrmions²² (see Methods). Fig. 2c shows that the exemplary mean-squared displacement (MSD) of individual skyrmions representing the linear behavior as a function of time t , indicating pure diffusive Brownian motion. The diffusion coefficient, D_{dif} for the Brownian motion in two dimensional (xy) coordinate systems reads the MSD $= \langle x^2(t) + y^2(t) \rangle = 4 D_{\text{dif}} t$. Hence, we determine the diffusion coefficient from the slope of the MSD at a specific temperature. Fig. 2d shows the temperature dependence of the diffusion coefficients for each stack. Note that the measurable temperature range is limited due to constraints regarding the skyrmion nucleation, stability and the time resolution of our imaging setup. We find that the diffusion coefficient for all the stacks exhibits a linear dependence on a semi-logarithmic scale, which is analogous to the ferromagnetic counterpart in a single layer²²⁻²⁴. Moreover, we reveal that the slope becomes steeper with increasing m_{Com} as seen in Fig. 2d, and e. The highest compensation ($m_{\text{Com}} = 90\%$) clearly exhibits the steepest slope in the temperature dependence. Intriguingly, a different material system with a compensation ratio of 65%, consisting of Ta(5)/ Ir(1.2)/ Co_{0.40}Fe_{0.40}B_{0.20}(1.0)/ Ir(1.2)/ Co_{0.20}Fe_{0.60}B_{0.20} (0.8)/Ta (0.09)/MgO(2)/Ta(5), shown in light green in Fig. 2d, exhibits a similar behavior to that of m_{Com} (60 or 75%). This implies that the steeper slope with the compensation is not a material-specific behavior but rather a more general feature resulting from the

compensation. To clarify the intrinsic effect of the compensation on the diffusive motion and to understand the intriguing temperature dependence, we next perform atomistic spin simulations and establish an analytical description of both the compensation dependence as well as the pinning effects.

Theoretical calculations

Atomistic spin simulations⁴⁵ within a toy model system (for details, see Methods) in the absence of pinning are performed first. We consider two ferromagnetic monolayers that are either coupled ferro-, or antiferromagnetically. The compensation of the synthetic antiferromagnet is varied by keeping M_2 fixed and varying M_1 between $-M_2$ and 0. The ferromagnetic bilayer is described by $M_1=M_2$. Note, that the skyrmions described by the toy model are small compared to the ones in the experiment. This, however, is not a problem because the atomistic spin simulations are merely used to demonstrate the validity of an analytic theory that holds irrespective of the skyrmion size as discussed next.

Fig. 3a displays the diffusion coefficient of the SyAFM skyrmions with $M_2 = -M_1$ ($m_{\text{Com}} = 100\%$), $M_2 = -0.75M_1$ ($m_{\text{Com}} = 85.7\%$), $M_2 = -0.5M_1$ ($m_{\text{Com}} = 66.6\%$), $M_2 = -0.25M_1$ ($m_{\text{Com}} = 40\%$) and the FM skyrmions versus temperature in a semi-logarithmic plot. This data can be well described by the following formula which is derived from an effective Thiele equation (see Supplementary Note 4),

$$D_{\text{dif}} = k_{\text{B}}T \frac{\alpha\Gamma}{\alpha^2\Gamma^2 + G^2(1 - m_{\text{Com}})^2}, \quad (1)$$

where k_B , α , Γ , and G represent the Boltzmann constant, the Gilbert damping constant, the dissipative constant for the spatial derivatives of the magnetization, and the absolute value of the gyrotropic term, respectively. Eq. (1) differs from the expression for the diffusion coefficient derived earlier²⁶ by a scaling with the effective topological charge (the compensation-weighted gyrotropic term). Based on Ref. 28, we expect a change in this term to heavily impact the diffusion coefficient: decreasing the effective topological charge by increasing the compensation can suppress the microscopic thermal gyrotropic motion that arises from the finite effective topological charge. As a consequence, the SyAFM skyrmion shows a higher diffusion coefficient compared to its FM counterpart as shown in Fig. 3a. Hence, the behavior crucially depends on the magnetic parameters.

The most remarkable feature is the distinctly and qualitatively different role of the Gilbert damping constant for different topologies. Fig. 3b shows the damping dependence of the diffusion coefficient at fixed temperature. It has been known that FM skyrmions show a counterintuitive friction dependence of the diffusive motion²⁶, i.e., decreasing the damping constant (friction) leads to decreasing diffusion, which is opposite to the behavior of condensed matter particles such as colloids. The fully-compensated SyAFM skyrmion, however, can retrieve the conventional behavior owing to the effective topological charge being zero. Hence, if the system possesses a low damping constant, it is expected that the effective topological charge significantly and qualitatively affects the diffusive motion of magnetic skyrmions via the modulation of the compensation.

On the other hand, coming back to the compensation dependence of the diffusion coefficient, the steeper slope with increasing compensation in the semi-logarithmic plot in Figure 2d cannot be described within this simple model. Here we need to take pinning effects into account, described via an Arrhenius law, which is a critical factor for a typical

sputtered magnetic film, based on the observed linear temperature behavior of the D_{dif} on a semi-logarithmic scale as previously shown for FM skyrmions in the single FM layer^{22–24}.

Considering pinning effects, the temperature dependence of the skyrmion diffusion can be estimated as

$$D_{\text{dif}} = D_0 k_B T \exp(-\Delta E / k_B T) \quad (2)$$

with ΔE being the depinning energy of the magnetic skyrmion. If the thermal energy is much lower than this depinning energy, the skyrmion diffusion corresponds to Kramer's escape problem where the exponential factor accounts for the (low) probability that the skyrmion can overcome ΔE and escape to the next pinning site. As long as the thermal energy is much larger than the depinning energy, the free diffusive motion is recovered. From comparison with Eq. (1) it follows that $D_0 = \alpha \Gamma / [\alpha^2 \Gamma^2 + G^2 (1 - m_{\text{com}})^2]$. D_0 , as given in the Arrhenius law in Eq. (2), can also be interpreted as the attempt frequency for overcoming the energy barrier. As such, a higher D_0 for AFM skyrmions as compared to those in FM systems can be understood on the same grounds as the increased attempt frequency found for the superparamagnetic behavior of AFM nanoparticles⁴⁶.

Taylor expanding the Arrhenius law around the skyrmion's activation temperature T_0 , above which the magnetic skyrmion exhibits the diffusive motion, provides

$$\ln[D_0 k_B T \exp(-\Delta E / k_B T)] \approx \ln(D_0 k_B T) - 2 \frac{\Delta E}{k_B T_0} + \frac{\Delta E}{(k_B T_0)^2} k_B T. \quad (3)$$

Therefore, the linear slope of D_{dif} in the semi-logarithmic plot underlines that the skyrmions are still in the pinning-dominated diffusion regime. Also, importantly the slope has implications on the depinning energy for the magnetic skyrmion, which reveals that ΔE increases monotonically with the compensation ratio. We note that the averaged-

depinning energy of the magnetic skyrmions is connected to the pinning of the domain wall surrounding the core domain rather than the core itself⁴⁷, that would scale with the cross-sectional area⁴⁸. Thus, it is expected that the depinning energy roughly scales with the size (radius) of the skyrmion (not the area), which reads

$$\Delta E = \Delta E(R_{\text{sk.ave}}(T)) \approx \varepsilon R_{\text{sk.ave}}(T), \quad (4)$$

where $R_{\text{sk.ave}}$, and ε represent the averaged radius, and the depinning energy density, respectively. The size dependence of the depinning energy leads to a stronger pinning for bigger skyrmions resulting in a lower diffusion constant as already observed experimentally²². Equation (4) demonstrates that the skyrmion size needs to be considered in order to clarify the origin of the steeper slope with varying the compensation ratio.

Temperature dependence of the skyrmion size

So based on our theoretical analysis, in order to investigate the systematic increase of the slope, we need to next explore the temperature dependence of the SyAFM skyrmion size (see Methods and Supplementary Note 5). Figure 4a shows the temperature dependence of the skyrmion size in the temperature range where diffusive motion is observed. Intriguingly, the skyrmion size changes drastically as a function of temperature (see Supplementary Video 2 and 3, and Supplementary Note 5). The trend is significant for the highly compensated state in line with existing theory³⁶, which predicts a strong temperature dependence. However, the observed size decrease is opposite to the previously predicted increase in size with temperature³⁶, probably due to a temperature dependence of DMI, which was previously not taken into account. As shown in Fig. 4b, we find that the skyrmion size increases with the compensation, which in turn leads to an increased pinning energy based on equation (4). Therefore, we can conclude that the

increasing slope of the diffusion coefficient is mostly attributed to the size-related pinning effect. Whereas the effect explains well the systematic increase of the slope of the diffusion coefficient, the drastic size modification and larger size at highly compensated states are different from the previous experimental observation in a Pt/Co/Ru/Pt/Co/Ru/Pt system³⁸. One of the possible reasons is the large difference of magnitude of the interfacial DMI. In our system, the value is too small to stabilize the skyrmion at ultra-small size e.g. less than 10 nm via the DMI-dominated mechanism⁴⁹ ($\sim 0.01\text{-}0.06$ mJ/m² is found from Brillouin light scattering) owing to the amorphous nature of the system or possibly opposite sign of the DMI between top and bottom FMs (note that the chirality of the Néel-type skyrmions is fixed and left-handed due to the interfacial DMI, see Methods and Supplementary Video 4 and 5), which is also supported by Fig. 4 implying that the dipolar coupling effects could play a key role in the stabilization.

Size dependence of the diffusion coefficient

Finally, we disentangle the size-related pinning influence to identify the pure influence of the effective topological charge on the diffusion. This is realized in Fig. 5a by plotting the size dependence of the diffusion coefficient in a semi-logarithmic scale at a specific fixed T , where reference data²² was also included previously taken in Ta/CoFeB/MgO system for FM skyrmions for which their diffusive motion data is available around 300 K. On the basis of equation (3) with ΔE as in equation (4), the slope and the intercept in Fig. 5a can be related to the depinning energy density and the intrinsic diffusion coefficient, respectively.

Fig. 5b indicates that the compensation dependence of D_0 normalized to that of FM skyrmions (the intercept divided by T to compensate for the temperature difference),

represents the intrinsic diffusion coefficient reflecting the effect of topology on the thermal dynamics of the skyrmion, where D_0^{FM} denotes the averaged D_0 for FM skyrmions in Fig. 5a. We clearly observe an increase of the diffusion coefficients with increasing the compensation and an approximately 10-30 times larger diffusion coefficient for the 90% compensated SyAFM skyrmions compared to the FM skyrmions. To verify the qualitative consistency, we calculate the compensation ratio dependence of D_0 based on equation (1) which is shown by solid lines in Fig. 5b. We note that skyrmion radius $R_{\text{sk.ave}}$ and domain wall width δ would affect the intrinsic diffusion coefficient via the dissipative term Γ that is proportional to $R_{\text{sk.ave}}/\delta^{11}$. Hence, we could access only the averaged D_0 experimentally for varying $R_{\text{sk.ave}}$ owing to the fact that Γ is put to be constant to obtain the intrinsic D_0 . Thus, various $R_{\text{sk.ave}}$ and δ are accounted for in the calculation, which are experimentally obtained for each stack (see Methods for more details). We find that our calculation reproduces the monotonic increasing of experimental compensation dependence, where we emphasize that only changing Γ with assuming zero compensation cannot describe the 10-30 times larger diffusion coefficients. Therefore, the enhanced diffusion coefficient is mainly ascribed to the suppressed effective topological charge for the highly compensated SyAFM system.

Discussion

We have realized skyrmion diffusion in low pinning synthetic antiferromagnets, which in contrast to amorphous ferrimagnets or crystalline antiferromagnets with strong pinning allow us to experimentally probe predictions of the drastic impact of the topology on the diffusion.

Previously it has been found to be very challenging to observe the stochastic dynamics of topological spin textures in antiferromagnetic systems, and thus the application for antiferromagnetic skyrmions with reduced topological charge has been limited to deterministic devices. However, antiferromagnets have been predicted to be intrinsically preferable for probabilistic spintronic devices including Brownian computing rather than for conventional drift motion which requires deterministic operation owing to enhanced stochasticity and thus rapid diffusion^{28,36,46}. By designing multilayer systems of amorphous CoFeB with low pinning, we have successfully demonstrated thermally-activated antiferromagnetically coupled skyrmion diffusion with a more than 10 times larger diffusion coefficient compared to the conventional ferromagnetic counterparts, which using our developed analytical formula, we can qualitatively describe to result from the suppression of the effective topological charge. Even though we have judiciously used relatively large skyrmions that allow for the observation using optical Kerr-microscopy, our results of the enhancement of the diffusion coefficient will be key also for smaller skyrmions because of a smaller dissipative term $\alpha\Gamma$ indicating that the skyrmion is close to the low damping regime shown Fig. 3b, which means being promising in terms of device scalability as well.

In summary, our findings that provide crucial insights into the thermally-activated dynamics of the topological objects in antiferromagnet systems would enable scalable effective unconventional computing using antiferromagnetic systems for which a probabilistic operation based on fast diffusion is key.

References

1. Rößler, U. K., Bogdanov, A. N. & Pfleiderer, C. Spontaneous skyrmion ground states in magnetic metals. *Nature* **442**, 797–801 (2006).
2. Mühlbauer, S. *et al.* Skyrmion Lattice in a Chiral Magnet. *Science* **323**, 915–919 (2009).
3. Yu, X. Z. *et al.* Real-space observation of a two-dimensional skyrmion crystal. *Nature* **465**, 901–904 (2010).
4. Dohi, T., Reeve, Robert. M. & Kläui, M. Thin Film Skyrmionics. *Annu. Rev. Condens. Matter Phys.* **13**, 73 (2022).
5. Finocchio, G., Büttner, F., Tomasello, R., Carpentieri, M. & Kläui, M. Magnetic skyrmions: from fundamental to applications. *J. Phys. D: Appl. Phys.* **49**, 423001 (2016).
6. Wiesendanger, R. Nanoscale magnetic skyrmions in metallic films and multilayers: a new twist for spintronics. *Nat. Rev. Mater.* **1**, 16044 (2016).
7. Jiang, W. *et al.* Skyrmions in magnetic multilayers. *Phys. Rep.* **704**, 1–49 (2017).
8. Everschor-Sitte, K., Masell, J., Reeve, R. M. & Kläui, M. Perspective: Magnetic skyrmions—Overview of recent progress in an active research field. *J. Appl. Phys.* **124**, 240901 (2018).
9. Jonietz, F. *et al.* Spin Transfer Torques in MnSi at Ultralow Current Densities. *Science* **330**, 1648–1651 (2010).
10. Schulz, T. *et al.* Emergent electrodynamics of skyrmions in a chiral magnet. *Nat. Phys.* **8**, 301–304 (2012).
11. Jiang, W. *et al.* Direct observation of the skyrmion Hall effect. *Nat. Phys.* **13**, 162–169 (2017).
12. Litzius, K. *et al.* Skyrmion Hall effect revealed by direct time-resolved X-ray microscopy. *Nat. Phys.* **13**, 170–175 (2017).
13. Nagaosa, N. & Tokura, Y. Topological properties and dynamics of magnetic skyrmions. *Nat. Nanotechnol.* **8**, 899–911 (2013).
14. Jiang, W. *et al.* Blowing magnetic skyrmion bubbles. *Science* **349**, 283–286 (2015).
15. Boule, O. *et al.* Room-temperature chiral magnetic skyrmions in ultrathin magnetic nanostructures. *Nat. Nanotechnol.* **11**, 449–454 (2016).

16. Moreau-Luchaire, C. *et al.* Additive interfacial chiral interaction in multilayers for stabilization of small individual skyrmions at room temperature. *Nat. Nanotechnol.* **11**, 444–448 (2016).
17. Woo, S. *et al.* Observation of room-temperature magnetic skyrmions and their current-driven dynamics in ultrathin metallic ferromagnets. *Nat. Mater.* **15**, 501–506 (2016).
18. Soumyanarayanan, A. *et al.* Tunable room-temperature magnetic skyrmions in Ir/Fe/Co/Pt multilayers. *Nat. Mater.* **16**, 898–904 (2017).
19. Manchon, A. *et al.* Current-induced spin-orbit torques in ferromagnetic and antiferromagnetic systems. *Rev. Mod. Phys.* **91**, 035004 (2019).
20. Fert, A., Cros, V. & Sampaio, J. Skyrmions on the track. *Nat. Nanotechnol.* **8**, 152–156 (2013).
21. Zhang, X. *et al.* Skyrmion-electronics: writing, deleting, reading and processing magnetic skyrmions toward spintronic applications. *J. Phys.: Condens. Matter* **32**, 143001 (2020).
22. Zázvorka, J. *et al.* Thermal skyrmion diffusion used in a reshuffler device. *Nat. Nanotechnol.* **14**, 658–661 (2019).
23. Nozaki, T. *et al.* Brownian motion of skyrmion bubbles and its control by voltage applications. *Appl. Phys. Lett.* **114**, 012402 (2019).
24. Zhao, L. *et al.* Topology-Dependent Brownian Gyromotion of a Single Skyrmion. *Phys. Rev. Lett.* **125**, 027206 (2020).
25. Miki, S. *et al.* Brownian Motion of Magnetic Skyrmions in One- and Two-Dimensional Systems. *J. Phys. Soc. Jpn.* **90**, 083601 (2021).
26. Schütte, C., Iwasaki, J., Rosch, A. & Nagaosa, N. Inertia, diffusion, and dynamics of a driven skyrmion. *Phys. Rev. B* **90**, 174434 (2014).
27. Miltat, J., Rohart, S. & Thiaville, A. Brownian motion of magnetic domain walls and skyrmions, and their diffusion constants. *Phys. Rev. B* **97**, 214426 (2018).
28. Weißenhofer, M. & Nowak, U. Diffusion of skyrmions: the role of topology and anisotropy. *New J. Phys.* **22**, 103059 (2020).
29. Weißenhofer, M., Rózsa, L. & Nowak, U. Skyrmion Dynamics at Finite Temperatures: Beyond Thiele’s Equation. *Phys. Rev. Lett.* **127**, 047203 (2021).

30. Pinna, D. *et al.* Skyrmion Gas Manipulation for Probabilistic Computing. *Phys. Rev. Appl.* **9**, 064018 (2018).
31. Jibiki, Y. *et al.* Skyrmion Brownian circuit implemented in continuous ferromagnetic thin film. *Appl. Phys. Lett.* **117**, 082402 (2020).
32. Litzius, K. *et al.* The role of temperature and drive current in skyrmion dynamics. *Nat. Electron.* **3**, 30–36 (2020).
33. Zeissler, K. *et al.* Diameter-independent skyrmion Hall angle observed in chiral magnetic multilayers. *Nat. Commun.* **11**, 428 (2020).
34. Tan, A. K. C. *et al.* Visualizing the strongly reshaped skyrmion Hall effect in multilayer wire devices. *Nat. Commun.* **12**, 4252 (2021).
35. Zhang, X., Zhou, Y. & Ezawa, M. Magnetic bilayer-skyrmions without skyrmion Hall effect. *Nat. Commun.* **7**, 10293 (2016).
36. Barker, J. & Tretiakov, O. A. Static and Dynamical Properties of Antiferromagnetic Skyrmions in the Presence of Applied Current and Temperature. *Phys. Rev. Lett.* **116**, 147203 (2016).
37. Dohi, T., DuttaGupta, S., Fukami, S. & Ohno, H. Formation and current-induced motion of synthetic antiferromagnetic skyrmion bubbles. *Nat. Commun.* **10**, 5153 (2019).
38. Legrand, W. *et al.* Room-temperature stabilization of antiferromagnetic skyrmions in synthetic antiferromagnets. *Nat. Mater.* **19**, 34–42 (2020).
39. Woo, S. *et al.* Current-driven dynamics and inhibition of the skyrmion Hall effect of ferrimagnetic skyrmions in GdFeCo films. *Nat. Commun.* **9**, 959 (2018).
40. Caretta, L. *et al.* Fast current-driven domain walls and small skyrmions in a compensated ferrimagnet. *Nat. Nanotechnol.* **13**, 1154–1160 (2018).
41. Hirata, Y. *et al.* Vanishing skyrmion Hall effect at the angular momentum compensation temperature of a ferrimagnet. *Nat. Nanotechnol.* **14**, 232–236 (2019).
42. Burrowes, C. *et al.* Low depinning fields in Ta-CoFeB-MgO ultrathin films with perpendicular magnetic anisotropy. *Appl. Phys. Lett.* **103**, 182401 (2013).

43. Duine, R. A., Lee, K.-J., Parkin, S. S. P. & Stiles, M. D. Synthetic antiferromagnetic spintronics. *Nat. Phys.* **14**, 217–219 (2018).
44. Pirro, P. *et al.* Perpendicularly magnetized CoFeB multilayers with tunable interlayer exchange for synthetic ferrimagnets. *Journal of Magnetism and Magnetic Materials* **432**, 260–265 (2017).
45. Nowak, U. *Classical Spin Models, Handbook of Magnetism and Advanced Magnetic Materials*. vol. 2 (John Wiley, 2007).
46. Rózsa, L., Selzer, S., Birk, T., Atxitia, U. & Nowak, U. Reduced thermal stability of antiferromagnetic nanostructures. *Phys. Rev. B* **100**, 064422 (2019).
47. Gruber, R. *et al.* Skyrmion pinning energetics in thin film systems. *arXiv:2201.01618*.
48. Tetienne, J.-P. *et al.* Nanoscale imaging and control of domain-wall hopping with a nitrogen-vacancy center microscope. *Science* **344**, 1366–1369 (2014).
49. Büttner, F., Lemesh, I. & Beach, G. S. D. Theory of isolated magnetic skyrmions: From fundamentals to room temperature applications. *Sci. Rep.* **8**, 4464 (2018).

Methods

Film preparation.

The samples were prepared by sputtering using a Singulus Rotaris sputtering machine with a base pressure better than 3×10^{-8} mbar. Using the Singulus Rotaris deposition system, we can tune the thickness of the layers with a high accuracy (reproducibility better than 0.01 nm). Table 1 summarizes the FM thickness (extracted from the deposition rate calibrated from X-ray reflectivity measurements) used for each compensation ratio. We used the different composition of CoFeB, with Co-rich CoFeB ($\text{Co}_{0.6}\text{Fe}_{0.2}\text{B}_{0.2}$) and Fe-rich CoFeB ($\text{Co}_{0.2}\text{Fe}_{0.6}\text{B}_{0.2}$) playing different roles in the system. Whereas Co-rich CoFeB acts as a source of the interfacial magnetic anisotropy and DMI, Fe-rich CoFeB is deposited for making the systems close to amorphous to reduce pinning and evoke diffusive motion. In our SyAFM system, the material layers deposited on top of the FMs are different for the bottom and top FMs to break the spatial inversion symmetry (Ir, or Ru), causing a difference in the magnetic dead layer⁵⁰, which provides a not fully-compensated state under the condition $t_{\text{CFB1}} + t_{\text{FCB1}} = t_{\text{CFB2}} + t_{\text{FCB2}}$. Due to Ir being a heavy metal, the bottom FMs typically have lower magnetic moment for which we easily get the preferable condition that is $M_2 > M_1$, since the Kerr imaging is a surface sensitive technique. This is supported by the fact that even when using the completely same thickness for the bottom and top FMs, we obtained a different compensation by using different capping layers (see <25% and 60%). For the 25% compensation SyAFM the top FM is covered by HfO_x , exhibiting a lower compensation compared to the SyAFM covered by Ru owing to a thinner dead layer for the top FM. Note that even though the magnetic proximity effect^{51,52} could also cause such deviation of magnetic moments, the relationship becomes reversed ($M_1 > M_2$) as the bottom seed Pt layer⁵³ has larger proximity-induced moments when the effect is significant. This is not the case though for our system.

Table 1 Summary of FM thickness for each compensation ratio

	t_{CFB1} (nm)	t_{FCB1} (nm)	t_{CFB2} (nm)	t_{FCB2} (nm)
FM bi-layer (covered by Ru, 1.6 nm Ir)	0.50	0.35	0.50	0.35
$m_{\text{Com}} < 25$ % (covered by HfO _x , 1.2 nm Ir)	0.45	0.40	0.45	0.40
$m_{\text{Com}} = 60$ % (covered by Ru, 1.2 nm Ir)	0.45	0.40	0.45	0.40
$m_{\text{Com}} = 75$ % (covered by Ru, 1.2 nm Ir)	0.43	0.48	0.43	0.48
$m_{\text{Com}} = 90$ % (covered by Ru, 1.2 nm Ir)	0.43	0.50	0.43	0.45

Magnetic parameters.

Saturation magnetization M_s and compensation ratio of magnetic moments are determined from the M - H curve obtained from a superconducting quantum interference device and a vibrating sample magnetometer. The effective magnetic anisotropy field, the exchange stiffness A_s , and the magnitude of DMI are determined using the spin-wave dispersion relation obtained using the Brillouin light scattering method⁵⁴, where we also determined the damping constant α to be 0.022 assuming a gyromagnetic ratio of 28 GHz T⁻¹, which is consistent with previous work^{50,55}. For the Gilbert damping constant, the line width of a spin-wave mode close to the ferromagnetic resonance is measured as a function of the magnetic field to be able to separate it from the inhomogeneous broadening. Following an analytical approximation formula of the dissipative tensor¹¹, we roughly estimated the dissipative term $\alpha\Gamma$ as well as the gyrotropic term G for the SyAFM system with $m_{\text{Com}} = 90, 60,$ and 0 % (FM bi-layer system), reproducing consistent results based on equation (1) in Fig. 5b. For the calculation, we assume domain wall width δ to be constant whereas $R_{\text{sk,ave}}$ changes at the fixed T as skyrmion size was controlled by changing magnetic fields. Table 2 summarize the parameter used for the calculation in Fig. 5b, in which δ is also calculated using those parameters⁵⁶. The interlayer exchange coupling J_{int} is estimated by using the relation⁵⁷, $J_{\text{int}} = M_s t_{\text{CFB}+\text{FCB}} (-H_s + H_K^{\text{eff}})/2$, where H_s and H_K^{eff} are the saturation

field and effective anisotropy field, respectively. For 90% compensation, J_{int} is determined to be ~ 0.05 mJ/m² (the used parameters are $M_S = 1$ T, $\mu_0 H_S = 100$ mT, and $\mu_0 H_K^{\text{eff}} = 45$ mT).

Table 2 Summary of magnetic parameters used for the calculation in Fig. 5b

	Thickness (nm)	M_S (T)	$\mu_0 H_K^{\text{eff}}$ (mT)	A_S (pJ/m)	δ (nm)	α
FM bi-layer	1.70	1.0	147	12.1	12.8	0.022
$m_{\text{Com}} = 60\%$	1.70	0.4	44	5.6	26.1	0.022
$m_{\text{Com}} = 90\%$	1.82	0.1	45	6.2	58.2	0.022

Experimental setup.

A commercial Evico GmbH MOKE microscope combined with 3 light-emitting diodes (LEDs) giving white light with a continuous wavelength spectrum was used in polar configuration for detecting the magnetic domain state. The differential image between uniform and non-uniform states was recorded to obtain better contrast. The frame rate used for recording a video was 16 frames per second (fps) corresponding to a time resolution of 62.5 ms. To be able to apply both out-of-plane and in-plane magnetic fields simultaneously for controlling skyrmion density⁵⁸, the electromagnetic coil was custom made at Johannes Gutenberg-Universität Mainz. It was calibrated by a magnetometer with a Hall probe. For the Peltier module, it was confirmed that the temperature ranging from 290 to 360 K was stable during the measurement. The temperature was monitored by a Pt100 resistive temperature sensor which was placed on top of the Peltier element next to the sample.

Skyrmion tracking and size evaluation.

The python module TrackPy was used to track skyrmions^{59,60}. For full statistics, multiple magnetic skyrmion videos were recorded for approximately 2 to 3 minutes, of which 2000 frames were used for tracking. Note that since we use a continuous film, magnetic skyrmions bounce in and out of the view; also the trackable time for the diffusive motion is limited. The positions of skyrmions were detected using proper conditions⁶¹, then the linking function was used to obtain

the skyrmion trajectories during diffusive motion as can be seen in Supplementary Video 1. Using a few skyrmions, it was confirmed manually that the used algorithm is functioning properly by checking if the tracking is successful. In order to focus on extracting the intrinsic diffusion coefficient, individual skyrmions were measured without any confinement which leads to the anomalous diffusive motion^{62,63}. The error bar of the diffusion coefficient was calculated as the standard deviation (s.d.) of the MSDs. For the size evaluation, the radius of gyration of the Gaussian-like profile was employed to take into account the deformation of skyrmion in time³⁶ (see Supplementary Note 5). The error bar was also calculated as the s.d. of the size of skyrmions.

Current-induced domain motion.

The continuous magnetic film (SyAFM system with 90% compensation) was first cleaved into small pieces with width of 3 mm. After that, a contact pad consisting of Cr(5)/Au(30) was constructed through liftoff process to obtain uniform current distribution in the film. Any baking/annealing processes were avoided to preserve the properties of the film. The resistance was 82 Ω and 8 V with 10 ms pulse width and a pulse repetition rate of 1 s, resulted in a current density of $\sim 3.2 \times 10^9$ A/m², which were applied in Supplementary Video 4 and 5. Positive and negative pulses (regarding the bottom side being the ground) were used for Supplementary Video 2 and 3, respectively. To avoid mixing diffusive motion during drift motion, we investigated the collective domain motion to check whether the chirality is fixed throughout the film. As can be seen in Supplementary Video 4 and 5 (note that the magnification is different from the other videos), it is unambiguously shown that the domain is collectively displaced along the current flow direction (opposed to electron flow direction), indicating that the stable left-handed Néel-type domain walls in the film were moved by a SOT generated from the Pt heavy metal layer with the positive spin Hall angle of Pt⁶⁴.

Atomistic simulations of thermal skyrmion motion.

We perform atomistic spin simulations to compare our results for the Brownian motion of skyrmions with the analytical theory we establish in Supplementary Note 4. To be able to realize these simulations with reasonable computational effort, we use toy model parameters instead of the magnetic parameters for the experimentally investigated SyAFM and FM bi-layer stacks. In such a toy model the skyrmions are of the order of a few nanometers and their thermal motion can be observed using finite temperature spin model simulations, while this is challenging for the large skyrmions in the experimentally used stacks. Besides, the experimental timescales of seconds can be computed neither using atomistic spin models nor micromagnetics.

For the simulations, we use an atomistic spin Hamiltonian of the form

$$H = -\frac{1}{2} \sum_{i,j} J_{ij} \mathbf{S}_i \cdot \mathbf{S}_j - \frac{1}{2} \sum_{i,j} \mathbf{D}_{ij} \cdot (\mathbf{S}_i \times \mathbf{S}_j) - \kappa \sum_i S_{i,z}^2 \quad (5)$$

where the first term is the Heisenberg exchange, the second term is the Dzyaloshinskii–Moriya interaction (DMI) and the third is the uniaxial anisotropy. Note that it is assumed that the z-axis corresponds to the out-of-plane direction. The \mathbf{S}_i denote the normalized magnetic moments which are located at each lattice site. The lattice structure is assumed to be a simple cubic system with dimensions $2 \times N \times N$ in order to describe a bi-layer structure. The isotropic Heisenberg coupling within each monolayer has a value of $J_{\text{intra}} = 10$ meV and the Heisenberg coupling between the layers is $J_{\text{inter}} = \pm J_{\text{intra}}$, depending on whether a FM bi-layer or a SyAFM is simulated. Note that for the sign convention used in Eq. (5) a positive or negative Heisenberg coupling corresponds to FM or AFM coupling, respectively. The DMI within each layer is assumed to be of an interfacial type and hence the DMI vectors \mathbf{D}_{ij} are within the x-y plane. They are orthogonal to the vector connecting the lattice site i and j and their absolute value is $D = 3$ meV. The DMI between the two monolayers is assumed to be zero. The uniaxial anisotropy constant is set to $\kappa = 1.5$ meV.

To investigate the dynamics, we solve the stochastic Landau-Lifshitz-Gilbert equation of motion⁴⁵

$$\frac{\partial \mathbf{S}_i}{\partial t} = \frac{-\gamma}{(1 + \alpha^2)\mu_i} \mathbf{S}_i \times (\mathbf{H}_i + \alpha \mathbf{S}_i \times \mathbf{H}_i) \quad (6)$$

with the Gilbert damping constant α , the gyromagnetic ratio $\gamma = 1.76 \times 10^{11} T^{-1} s^{-1}$ and the effective field $\mathbf{H}_i = -\partial H / \partial \mathbf{S}_i + \boldsymbol{\zeta}_i$, where $\boldsymbol{\zeta}_i$ are thermal fluctuations in the form of Gaussian white noise. The saturation magnetic moments in the two monolayers are given by $\mu_1 = M_1 a^2$ and $\mu_2 = M_2 a^2$.

The simulations are performed via a GPU-accelerated implementation of Heun's method⁴⁵ with a fixed time step of 0.1 fs and a system consisting of $2 \times 64 \times 64$ spins and periodic boundary conditions are assumed. Initially, a SyAFM or FM skyrmion is placed in the center of the system and thermalized at finite temperature. Subsequently, its position is tracked every 5ps over 500ps by using an adaption of the algorithm in Appendix A of Ref. 26. For each set of parameters (temperature, damping and compensation) 100 simulations are performed, in order to provide sufficient statistics.

References

50. Belmeguenai, M. *et al.* Magnetic Anisotropy and Damping Constant in CoFeB/Ir and CoFeB/Ru Systems. *IEEE Trans. Magn.* **54**, 1–5 (2018).
51. Wilhelm, F. *et al.* Layer-Resolved Magnetic Moments in Ni / Pt Multilayers. *Phys. Rev. Lett.* **85**, 413–416 (2000).
52. Huang, S. Y. *et al.* Transport Magnetic Proximity Effects in Platinum. *Phys. Rev. Lett.* **109**, 107204 (2012).
53. Inyang, O. *et al.* Threshold interface magnetization required to induce magnetic proximity effect. *Phys. Rev. B* **100**, 174418 (2019).
54. Böttcher, T. *et al.* Heisenberg Exchange and Dzyaloshinskii–Moriya Interaction in Ultrathin Pt(W)/CoFeB Single and Multilayers. *IEEE Trans. Magn.* **57**, 1–7 (2021).

55. Huang, L., He, S., Yap, Q. J. & Lim, S. T. Engineering magnetic heterostructures to obtain large spin Hall efficiency for spin-orbit torque devices. *Appl. Phys. Lett.* **113**, 022402 (2018).
56. Lemesh, I., Büttner, F. & Beach, G. S. D. Accurate model of the stripe domain phase of perpendicularly magnetized multilayers. *Phys. Rev. B* **95**, 174423 (2017).
57. Bloemen, P. J. H., van Kesteren, H. W., Swagten, H. J. M. & de Jonge, W. J. M. Oscillatory interlayer exchange coupling in Co/Ru multilayers and bilayers. *Phys. Rev. B* **50**, 13505–13514 (1994).
58. Zázvorka, J. *et al.* Skyrmion Lattice Phases in Thin Film Multilayer. *Adv. Funct. Mater.* **30**, 2004037 (2020).
59. Allan, D. B., Caswell, T., Keim, N. C. & van der Wel, C. M. Trackpy: Fast, Flexible Particle-Tracking Toolkit — trackpy 0.4.2 documentation. <https://doi.org/10.5281/zenodo.3492186> (2019).
60. Crocker, J. C. & Grier, D. G. Methods of Digital Video Microscopy for Colloidal Studies. *Journal of Colloid and Interface Science* **179**, 298–310 (1996).
61. Ge, Y. *et al.* Constructing coarse-grained skyrmion potentials from experimental data with Iterative Boltzmann Inversion. *arXiv:2110.14333*.
62. Palyulin, V. V. *et al.* First passage and first hitting times of Lévy flights and Lévy walks. *New J. Phys.* **21**, 103028 (2019).
63. Song, C. *et al.* Commensurability between Element Symmetry and the Number of Skyrmions Governing Skyrmion Diffusion in Confined Geometries. *Adv. Funct. Mater.* **31**, 2010739 (2021).
64. Emori, S., Bauer, U., Ahn, S.-M., Martinez, E. & Beach, G. S. D. Current-driven dynamics of chiral ferromagnetic domain walls. *Nat. Mater.* **12**, 611–616 (2013).

Acknowledgements

The group in Mainz acknowledge funding from TopDyn, SFB TRR 146, SFB TRR 173 Spin+X (project A01 #268565370), SFB 1432, the Deutsche Forschungsgemeinschaft (DFG, German Research Foundation) Project No. 403502522 (SPP 2137 Skyrmionics). We

acknowledge financial support from the Horizon 2020 Framework Programme of the European Commission under FET-Open Grant No. 863155 (s-Nebula) and Grant No. 856538 (ERC-SyG 3D MAGiC). M.W. and U.N. in Konstanz acknowledge funding from the Deutsche Forschungsgemeinschaft (DFG, German Research Foundation) through the Project No. 403502522 (SPP 2137 Skyrmionics) and the SFB 1432. The group in Kaiserslautern acknowledges funding from TopDyn, SFB TRR 173 Spin+X (project B01 #268565370), and the Deutsche Forschungsgemeinschaft (DFG, German Research Foundation) Project No. 403512431 (SPP 2137 Skyrmionics). This project has received funding from the European Union's Horizon 2020 research and innovation program under the Marie Skłodowska-Curie Grant Agreement No. 860060 "Magnetism and the effect of Electric Field" (MagnEFi). This work was supported by the Max Planck Graduate Center with the Johannes Gutenberg-Universität Mainz (MPGC). T.D. gratefully acknowledges the help and advice of many members including the technicians of the Kläui group, and financial support by the Canon Foundation in Europe. N.K. and M.K. gratefully acknowledge financial support by the Graduate School of Excellence Materials Science in Mainz (Mainz, GSC266). J.Z. acknowledges support from Charles University (Grant No. PRIMUS/20/SCI/018).

Competing Interests

The authors declare no conflict of interest.

Author Contributions

T.D., M.W., U.N., and M.K. initiated, designed, and supervised the project. T.D., F.K., and M.A.S. designed and prepared the stack structure. T.D. prepared the experimental setup together with K.R., F.K., and N.K.; T.D. and M.A.S. conducted magnetization measurements with

technical support from G.J.; T.D. measured the diffusive and current-induced dynamics of magnetic skyrmions. T.D. and Y.G. analysed the experimental data for the diffusive dynamics. A.S. conducted the Hall measurement. T.B., M.R., and P.P. measured and evaluated the Brillouin light scattering spectra. M.W. derived the analytical formula and performed the atomistic simulation. T.D., N.K., and M.W. drafted the manuscript with help of U.N. and M.K. All authors discussed the results and commented on the manuscript.

Code availability

The computer codes used for data analysis are available upon reasonable request from the corresponding author.

Data availability

The data supporting the findings of this work are available from the corresponding authors upon reasonable request.

Figures

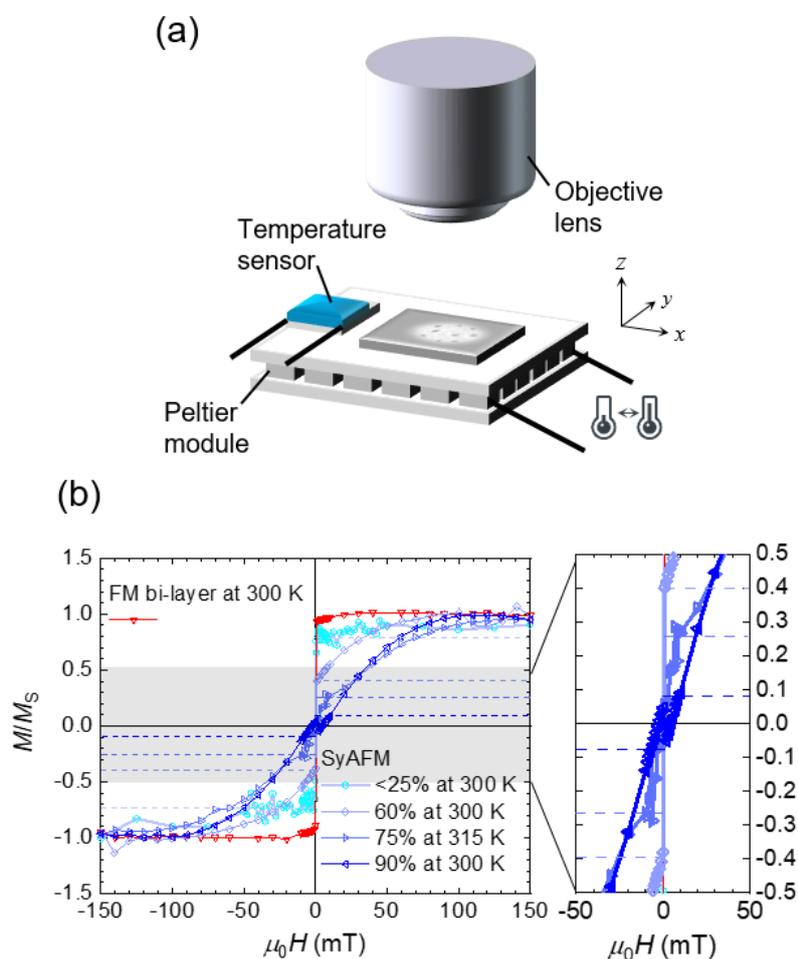


Figure 1

Experimental setup and measurements. (a) Schematic of the experimental setup. Magnetic thin films are placed on a Peltier module. The magnetic domain configuration is observed using a magneto-optical Kerr-effect microscope in polar configuration. (b) Exemplary $m-H$ curves for ferromagnetic bi-layer and synthetic antiferromagnetic systems with various compensation ratio. Red color corresponds to FM bi-layer and the blue colors to the SyAFM systems with <25 (very light blue), 60 (light blue), 75 (intermediate blue), and 90 % (dark blue) compensation ratios, respectively.

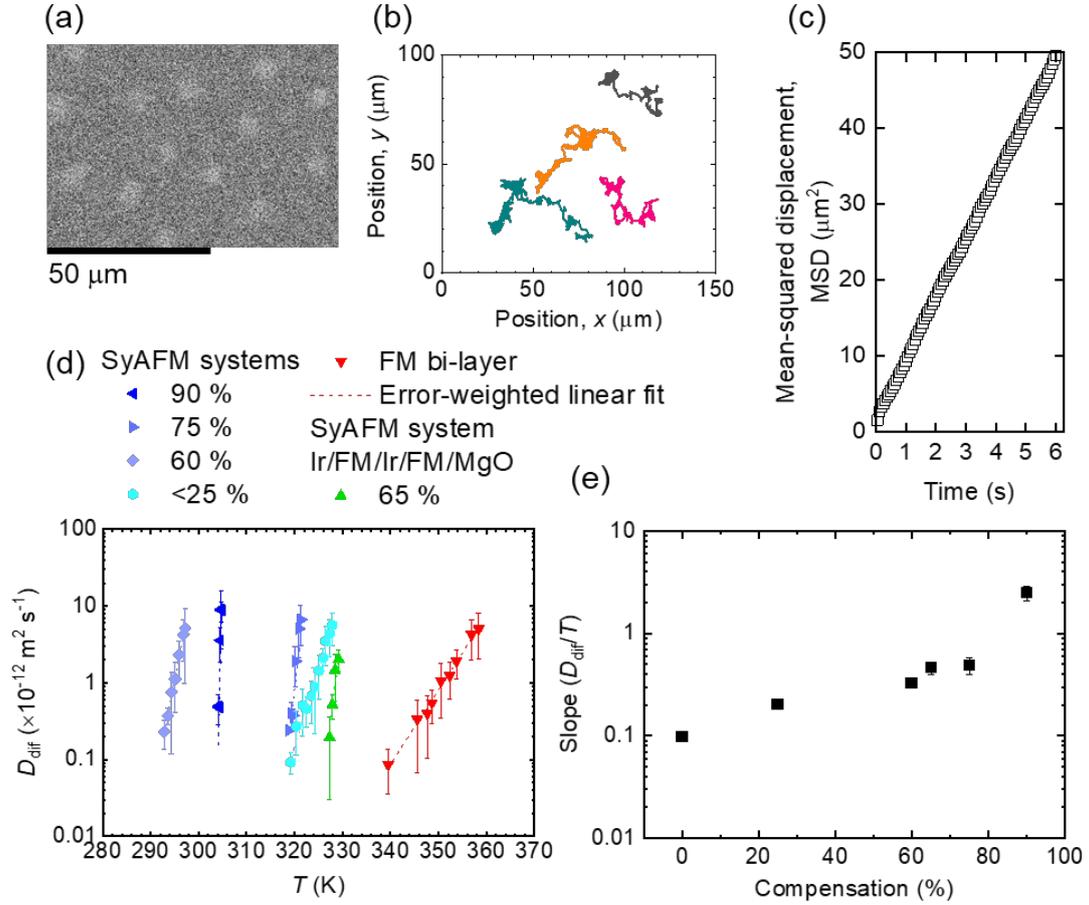


Figure 2

Thermally-activated diffusive motion of SyAFM skyrmions. (a) SyAFM skyrmions ($m_{\text{Com}} = 75\%$) at 320.7 K under $\mu_0 H_z = 0.35$ mT. (b) Trajectories of selected SyAFM skyrmions ($m_{\text{Com}} = 75\%$) at 320.2 K under $\mu_0 H_z = 0.12$ mT. (c) Exemplary mean-squared displacement as a function of time in Fig. 2b. (d) Temperature dependence of the diffusion coefficient for the FM bi-layer and the SyAFM systems with various compensation ratios. Red and the other colors denote the FM bi-layer and the SyAFM systems, respectively. Green plots indicate a different type of material system, Ir/Co_{0.40}Fe_{0.40}B_{0.20}/Ir/Co_{0.20}Fe_{0.60}B_{0.20}/MgO/Ta. The dashed line denotes error-weighted linear fit. (e) Compensation ratio dependence of the slope (D_{diff}/T) for Fig. 2d.

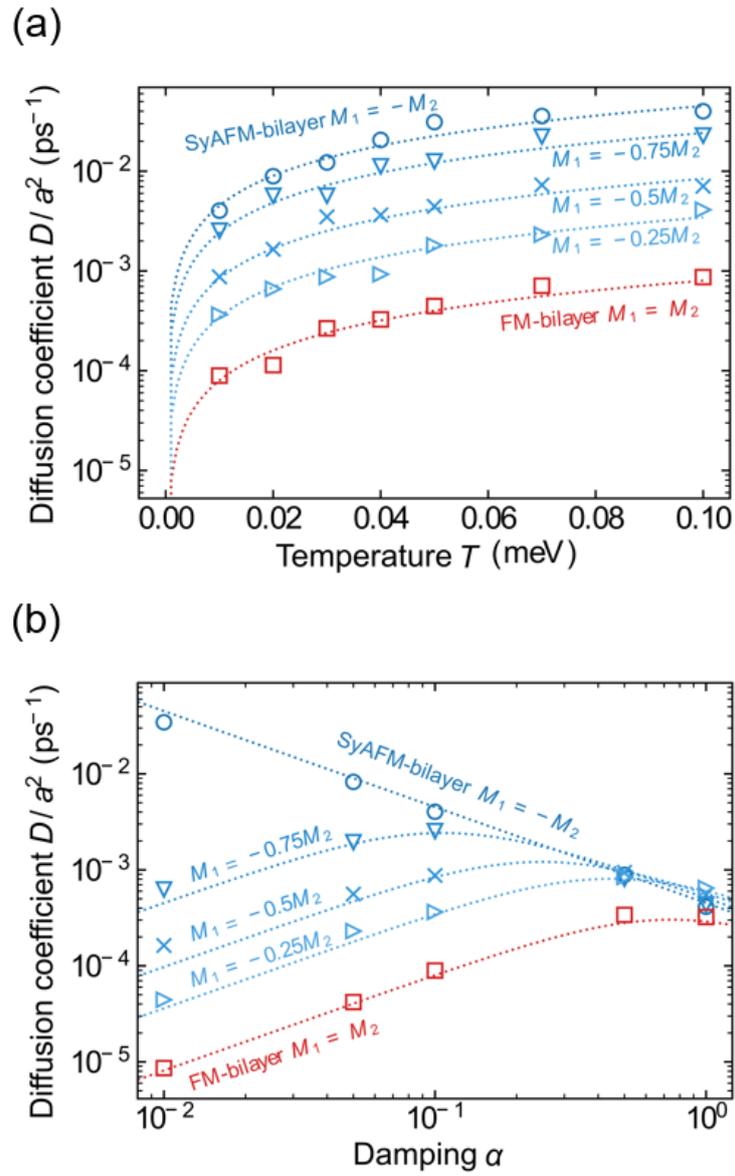


Figure 3

Atomistic simulations within a model using computationally feasible small skyrmions. (a) Temperature dependence of the diffusion coefficient. The same color code as in Fig. 2d is used. (b) The Gilbert damping constant dependence of the diffusion coefficient. The atomistic simulation data is compared with the analytical description established in Equation (1), which describes the numerical results well.

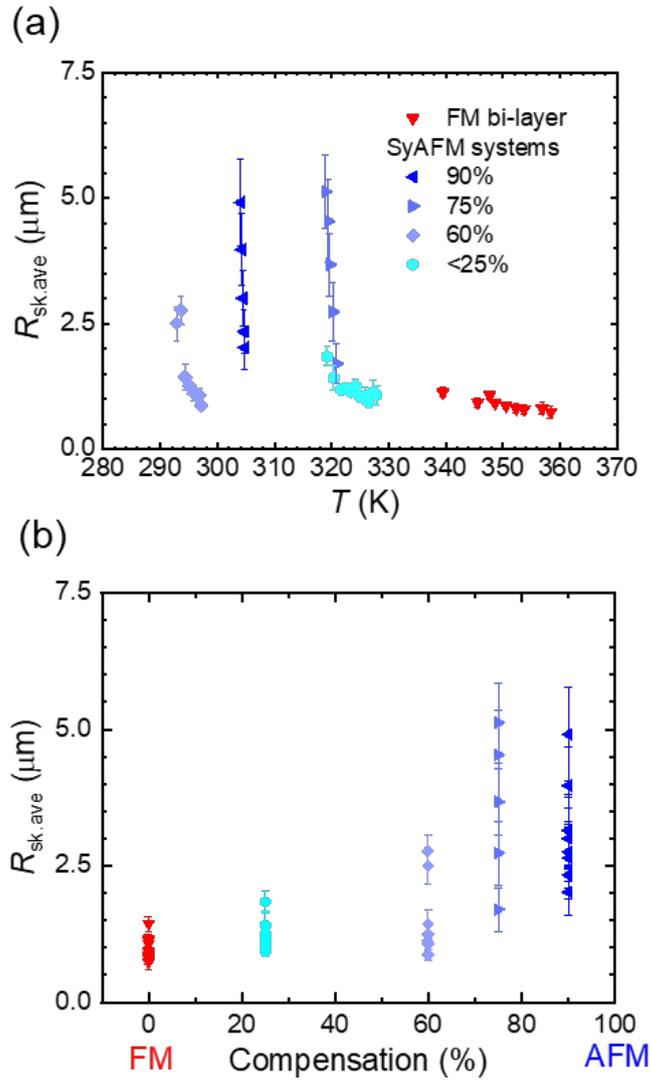


Figure 4

Characterization of skyrmion size as a function of temperature. (a) Temperature dependence of the averaged-radius of the skyrmion. The same color code as in Fig. 2d is used. (b) The compensation ratio of magnetic moments dependence of the averaged-size of the skyrmion where diffusive motion is observed.

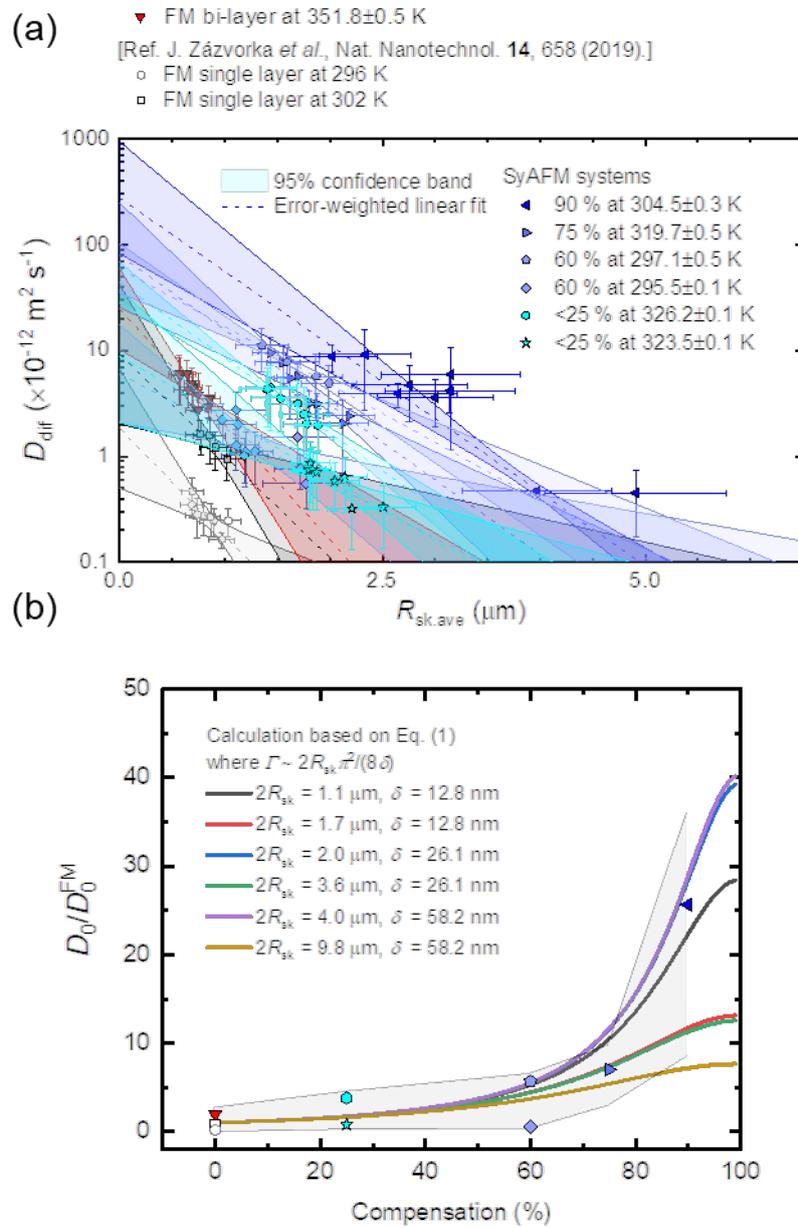


Figure 5

The influence of effective topological charge on the diffusion coefficient and the depinning energy of the systems. (a) The averaged-size dependence of the diffusion coefficient at a fixed temperature. The same color code as in Fig. 2d is used. The size of skyrmions was controlled by out-of-plane magnetic field. The dashed line, and shaded-

area represent error-weighted linear fit, and 95% confidence band calculated from the fit, respectively. (b) The compensation ratio dependence of the ratio of D_0/D_0^{FM} , where D_0^{FM} denotes the averaged D_0 for FM skyrmions in Fig. 5a. The value of D_0 is obtained by dividing the intercept by T to compensate for the temperature difference. The same symbols and color coding as in Fig. 5a are used. The shadow area corresponding to error bar calculated by the standard deviation. The solid line shows theoretical calculation based on equation (1) using the experimentally obtained parameters for the SyAFM system with 90, 60, and 0 % (FM bi-layer) compensation, where $\Gamma \sim 2R_{\text{sk,ave}} \pi^2 (8\delta)^{-1}$ based on Ref. 11.