

Anomalous quasiparticles in the zone center electron pocket of the kagomé ferromagnet Fe_3Sn_2

Sandy Adhithia Ekahana¹, Y. Soh^{1*}, Anna Tamai², Daniel Gosálbez-Martínez^{4,5}, Mengyu Yao³, Andrew Hunter², Wenhui Fan^{6,7}, Yihao Wang⁸, Junbo Li⁸, Armin Kleibert¹, C. A. F. Vaz¹, Junzhang Ma^{9,1}, Yimin Xiong⁸, Oleg V. Yazyev^{4,5}, Felix Baumberger^{2,1}, Ming Shi¹, Gabriel Aeppli^{1,4,10,11}

1 Paul Scherrer Institute, Forschungstrasse 111, CH-5232, Villigen, Switzerland

2 Department of Quantum Matter Physics, University of Geneva, 24 Quai Ernest-Ansermet, CH-1211, Geneva, Switzerland

3 Max Planck Institute for Chemical Physics of Solids, D-01187 Dresden, Germany

4 Institut de Physique, Ecole Polytechnique Fédérale de Lausanne (EPFL), CH-1015 Lausanne, Switzerland

5 National Centre for Computational Design and Discovery of Novel Materials MARVEL, Ecole Polytechnique Fédérale de Lausanne (EPFL), CH-1015 Lausanne, Switzerland

6 Beijing National Laboratory for Condensed Matter Physics and Institute of Physics, Chinese Academy of Sciences, P. O. Box 603, Beijing, 100190, China.

7 University of Chinese Academy of Sciences, Beijing 101408, China.

8 Anhui Province Key Laboratory of Condensed Matter Physics at Extreme Conditions, High Magnetic Field Laboratory of the Chinese Academy of Sciences, Hefei 230031, China

9 Department of Physics, City University of Hong Kong, Kowloon, Hong Kong, China

10 Department of Physics, Eidgenössische Technische Hochschule Zurich (ETHZ), CH-8093, Switzerland

11 Quantum Center, Eidgenössische Technische Hochschule Zurich (ETHZ), CH-8093 Zurich, Switzerland

*To whom correspondence should be addressed. Email: yona.soh@psi.ch

Abstract:

The kagomé lattice is a triangular lattice with all corner sites removed on a 2×2 superlattice. The enlarged unit cell enhances the possibility of topological effects on the properties of materials constructed from such lattices. One material containing kagome bilayers and featuring both exceptional magnetism and electron transport is the ferromagnetic metal Fe_3Sn_2 ¹⁻⁶. Notwithstanding the widespread interest in Fe_3Sn_2 , crystal twinning, difficulties of distinguishing surface from bulk states, and a large unit cell have until now prevented the synchrotron-based spectroscopic observation of sharply resolved quasiparticles near the Fermi surface which could be responsible for the anomalous properties appearing at low temperatures for the material. Here we report microfocused laser-based angle-resolved photoemission spectroscopy (μ -ARPES), which offers the first look at such quasiparticles. The high spatial resolution allows individual crystal twin domains to be examined in isolation, resulting in the discovery of three-fold symmetric electron pockets at the Brillouin zone (BZ) center, not predicted by early tight-binding descriptions but in agreement with density functional theory (DFT) calculations, which also feature Weyl nodes ⁴. The quasiparticles in these pockets have a remarkably long mean free paths, and their Fermi surface area is consistent with reported quantum oscillations ⁷. At the same time, though, the best-defined Fermi surface is reduced at low temperature, and the quasiparticles generally are marginal in the sense that their wavelength uncertainty is of order the deviation of the quasiparticle wavelength from the Fermi vector. We attribute these manifestations of strong electron-electron interactions to a flat band predicted by our DFT to lie just above the dispersive bands seen in this experiment. Thus, beyond demonstrating the impact of twin averaging for ARPES measurements of band structures, our experiments reveal many-body physics unaccounted for by current theories of metallic kagomé ferromagnets.

The kagomé lattice was first introduced in 1951 ⁸ as a natural expansion of square ⁹, honeycomb, and triangular lattices ^{10,11} for the study of Ising magnets. An important observation of the original publication was that for antiferromagnetic interactions, no conventional classical order is expected at finite temperatures. Long after its introduction, it remained the province of theory ^{12,13} until its first experimental discoveries in jarosites ¹⁴ and magnetoplumbites ^{15,16}. A second strand of research concerns the band structure for electrons hosted by such lattices which, in the simplest tight-binding limit, not only share the Dirac crossings of honeycomb lattices such as graphene, but also display flat bands. Particularly

noteworthy is the prediction from 2011 based on a tight binding model that a kagomé material which is both ferromagnetic and metallic could display interesting collective phenomena such as the fractional quantum Hall effect in the absence of an external magnetic field³. Rhombohedral (space group R-3m, SG-166) Fe₃Sn₂ is precisely such a substance¹⁷. Its building blocks are bilayers of distorted, three-fold (not six-fold) symmetric kagomé layers of Fe atoms alternating with single layers of stanene, as shown in Fig. 1a. Of long-standing interest have been the ferromagnetic properties, including a high Curie temperature of 640 K¹ and a spin reorientation transition near 120 K, which was recently confirmed to be of first order^{5,6}. The latter follows from a crossing of different free energies associated with subtly different band structures and resulting Fermi surfaces for the different moment directions^{4,6} (see figure SI8 in supplementary information (SI)). The electronic band structure itself has been directly investigated by photoemission^{4,18-20}, scanning tunneling microscopy²¹, and bulk transport measurements^{2,5,22-24}. The simplest tight-binding calculations (single orbital per site of kagomé lattice) for idealized two-dimensional slabs reveal flat bands and Dirac points, and there are claims of their observation in angle-resolved photoemission (ARPES), bulk Hall effect, and de Haas-van Alphen measurements^{7,18}. In contrast, density functional theory (DFT) for the bulk material yields neither obvious flat bands nor Dirac nodes (see figure SI10) but does reveal Weyl points near the Fermi surface⁴. Nonetheless, it accounts for the seeming appearance of Dirac nodes in ARPES in terms of superposed bulk and surface bands^{4,20}. The ARPES data collected so far do not display sharply resolved Weyl nodes. However, there is another feature that unambiguously distinguishes the tight-binding calculations from DFT predictions, namely, only DFT predicts electron pockets surrounding the zone centers (see figure 1c and figure SI7 – SI9⁴). Furthermore, as shown in figure 1c, the pockets are highly sensitive to electron correlation effects as parametrized by the effective Coulomb interaction U in DFT + U calculations, and so could be exploited for measurement of U . We have therefore set out to search for and characterize these pockets experimentally.

Here, we report the first detailed experimental study of the distinct electron pockets, present in lower resolution and more surface-sensitive measurements at the Brillouin zone (BZ) center of Fe₃Sn₂⁴, by employing state-of-the-art micro-focused laser ARPES (μ -ARPES) to overcome the presence of crystallographic twinning. Our results are consistent with the same density functional calculations which suggest that the Dirac-like cones reported in conventional synchrotron-based ARPES^{4,18} derive from a coincidence between minima and maxima of surface and bulk bands^{4,20}, respectively. At the lowest temperature (6 K), there are very sharp

quasiparticles which define small Fermi surfaces around the Brillouin zone centre, and their inverse lifetimes show the rapid linear increase with binding energy characteristic of strongly interacting fermions. On warming, the most sharply resolved band crossing the Fermi surface effectively dissolves, possibly due to hybridization and subsequent localization involving a flat band placed by DFT just above the chemical potential.

Motivation for spatially resolved ARPES experiments

ARPES is the natural technique for determining the electronic band structure and has been applied on numerous occasions to Fe_3Sn_2 ^{4,18-20}. However, there are four potential difficulties in assessing ARPES data, beyond the usual challenge of distinguishing surface from bulk contributions. A first challenge relates to the large number of atoms per unit cell (18 Fe and 12 Sn), leading to closely spaced bands which, due to magnetic order, will also be spin-split. A second difficulty is the possibility of crystal twinning originating during the crystal growth and which corresponds to rotation by $\delta = m \times 60^\circ, m = \pm(1,3,5)$ (figure 1a). A third problem is the possibility of different surface terminations, which would yield different ARPES results. A fourth aspect is the presence of ferromagnetism where, due to spin-orbit coupling, different magnetic domains are associated with different electronic structures⁴.

The first problem can only be remedied by ultra-high-resolution spectroscopy, while the remaining three are all linked to different types of multidomain structures over which ordinary ARPES measurements perform averages. For instance, in the case of crystal twinning, the complication is caused by the “breathing” kagomé motif of Fe_3Sn_2 consisting of two different corner-triangle sizes denoted by triangles with different colors in figure 1a, resulting in a three-fold rotation symmetry, rather than six-fold, in the absence of magnetic order⁴. The twinning will be clearly observed when the isoenergy surfaces are away from the high symmetry $k_z = \left(0, \frac{\pi}{c}\right)$ planes as shown by the results of the DFT calculations in figure 1b ($U = 1.3$ eV); $U = 1.3$ eV is chosen (figure 1c) as it can reproduce the electron pockets found by ARPES near the Γ point, which will be discussed in detail later. However, the ARPES results reported thus far are predominantly six-fold symmetric^{4,18-20}, which can only be attained at exactly the high symmetry $k_z = \left(0, \frac{\pi}{c}\right)$ planes for a single domain phase. Tanaka et al.²⁰ interpreted their

ARPES results as being three-fold symmetric for $k_z \neq \left(0, \frac{\pi}{c}\right)$, but the data quality is not sufficient to reach that conclusion unambiguously.

Here, we address the question of discriminating domains with different crystallographic twins, surface termination, and magnetic orientation, by using three forms of photoemission microscopy to characterize Fe_3Sn_2 , namely, spatially-resolved X-ray photoelectron spectroscopy (XPS), X-ray absorption spectroscopy (XAS), and X-ray magnetic circular dichroism (XMCD), which are used to distinguish physical domains related to surface termination and magnetism, respectively, and show that in fact they are uncorrelated. Separately, by using μ -focused laser ARPES, we probe at very high energy and momentum resolution the band structure close to the Brillouin zone center Γ . In addition to discovering electron pockets, we also observe directly that there are different electronic domains in Fe_3Sn_2 rotated around the c-axis by $\delta = m \times 60^\circ, m = \pm(1,3,5)$. By varying the temperature and by comparing the evolving magnetic domain pattern, we conclude that the observed differences in band structure are solely due to twinning and not due to different magnetic states. Direct comparison of the laser μ -ARPES data with synchrotron ARPES data that averages over much larger areas (presented in the SI) shows that the data from synchrotron ARPES corresponds to the average over crystallographic twins and therefore cannot be interpreted without help from either calculations or a spatially resolved technique like μ -ARPES.

Spatially-resolved XMCD, XAS, and XPS

We first consider the magnetic domain configuration and different surface terminations, which typical ARPES averages over, by using x-ray photoemission electron microscopy (XPEEM) to obtain spatially resolved XAS and XPS maps of the sample. In our case, the XAS is monitored using photoelectrons with kinetic energy below $\sim 1 - 2$ eV (low energy secondary electron, ‘bulk’ sensitive to a depth of a few nm from the surface) while the XPS photoelectrons have a kinetic energy of 96 eV (surface sensitive); the sample was cleaved in vacuum and investigated at 80 K, the base temperature of the cryostat. Figure 2a shows the XMCD map, which is obtained from the differences of XAS collected for left circular (CL) and right circular (CR) polarized photons at the Fe L_3 -edge, while figure 2b shows the map of the photoelectron yield summed over both polarizations (CL+CR). Figure 2a displays the magnetic domains of the system while figure b confirms that the iron in the bulk of the sample is homogeneous.

Moving to the topic of surface termination, figure 2c shows the XPS map for the same region as in figure 2a and b, obtained for the Sn 3d levels and indicating variations in the Sn intensity. Similar results are observed for a different cleaved surface, shown in figure SI2. Figure 2d displays the intensity histogram from the red square in figure 2c: it is bimodal (in this case well characterized as the sum of two Gaussians), which indicates that there are two possible Sn populations for the surfaces formed upon cleaving Fe_3Sn_2 . The ratio between the mean intensities for the two Gaussians is $I_1/I_2 = 1.8 \pm 0.6$, where I_1 is the brighter intensity and I_2 is the darker intensity mean value (follow the derivation in SI). The quantization of the Sn intensity suggested by the bimodal histogram is also apparent from the line scan, also shown in figure 2d, revealing a sharp step in intensity. These phenomena follow because the material consists of (kagomé) Fe bilayers alternating with stanene monolayers. In the first two top-most layers one expects either one or two Fe layers (no stanene layer). Thus, the clear contrast in Sn distribution (figure 2c) arises from stanene-termination for the brighter areas and kagomé-termination for the smaller lower intensity islands. Furthermore, given the much bigger area associated with the larger Sn photoemission intensity, we conclude that the majority of the sample is stanene-terminated, agreeing with the suggestion made in reference ⁴. Comparison of figures 2c and 2a also demonstrates that the magnetic domain pattern is uncorrelated with the surface termination. More discussions about the XPEEM and its interpretation can be found in the SI.

The XMCD map reveals a magnetic domain pattern with a hierarchy of characteristic features ranging from 50 to $< 1 \mu\text{m}$, indicating the need for μ -ARPES to avoid averaging of momentum and energy-resolved states associated with different magnetization directions at 80 K. At the same time, the different surface terminations as established by XPS are characterized by length scales in the same range, implying that μ -ARPES could also detect differences in surface states should they matter for the photon energy chosen.

Laser μ -ARPES

We performed laser μ -ARPES (detailed setup described in SI) to probe the electronic structure at high energy and spatial resolution to determine inhomogeneities in the electronic structure linked to magnetic, chemical, and crystallographic domains. The 6.01 eV photon energy limits

the Brillouin zone probed to near the Γ point, which nonetheless is of great interest because it enables detailed imaging of the electron pocket seen previously at low resolution with a large beam⁴, and predicted by DFT^{4,19,20} but not by other band theories¹⁸. Figure 3a shows our experimental data at 6 K, which reveal this electron pocket with unprecedented clarity for two laser beam positions on the sample.

The Fermi surfaces are located on three rings in (k_x, k_y) , with the inner ring clearly three-fold modulated, and the second and third less obviously so, but nonetheless with their most intense feature 60 degrees out-of-phase with the inner ring. The data presented in figure 3a are superpositions of data from both linear laser polarizations. Comparison of the data in figure 3a(i) and (ii) immediately indicates a relative rotation of 180° , which is equivalent to 60° for this rhombohedral material. We thus come to the important finding that the electronic structure of Fe_3Sn_2 at 6 K shows two distinct yet equivalent areas (rotated from each other). The positions of these rings are located at the center of the BZ as shown in figure 3b(i). The dispersion curves in figure 3a(iii) and (iv) show the intercepts of three bands with the three Fermi surfaces, and confirms the same 180° rotation in (k_x, k_y) which relates to their respective Fermi surfaces measured in figure 3a(i) and (ii). Two of the bands cross the inner and outermost Fermi surfaces and are labeled as α and γ in figure 3a(iii) and (iv), respectively, and merge to form a parabola centered at $\bar{\Gamma}$ with 0.1 eV minimum binding energy. There is also a very sharp feature between α and γ labelled β , which abruptly loses intensity through α around $E_B = 0.025$ eV, as can be seen from the energy-momentum cut image (figure 3a(iii) and (iv)). We also notice a very weak broad band lying at higher binding energy labeled as δ , which has asymmetric intensity similar to that of the γ and β bands, indicating that it is three-fold symmetric as well.

The two distinct areas rotated by 180° with respect to each other, *i.e.*, twinned domains, can be mapped in real-space by tracing the intensity differences between the left versus right side of the α band in the ARPES cut [figure 3a(iii) and (iv), where data for LH and LV polarizations are summed]. Figure 3c is the resulting domain image, where for α band intensity larger on the left side, we label the sample position in red, otherwise we color it green. In the gradation from green to red, white indicates no intensity difference. In the upper panel of figure 3c, we see that there is a relatively abrupt transition from the “red” to “green” regions, indicating that the twinned domain is rotated discontinuously. A rough measurement of the domain wall angle gives a value of 60° , in agreement with the twin rotation for the crystal structure.

The bulk electronic properties of Fe_3Sn_2 undergo pronounced evolution on cooling below 80 K, where the spin reorientation to the low temperature phase is complete⁵. Particularly dramatic are the modulation of the carrier density depending on the magnetization direction below 80 K²⁴ and the temperature dependence of the anisotropic magnetoresistance and planar Hall effect²³, which features a threefold (not sixfold) antisymmetric term as a function of in-plane field direction. To determine whether any of the ARPES features which we see at low temperature could be related to these transport phenomena, we have collected μ -ARPES data at 80 K, which is at the boundary of these characteristic temperatures but still in the regime where the magnetism is dominated by domains with moments along the kagomé planes⁶, although with smaller domains compared to 6 K. The lower panel of Figure 3c shows the intensity asymmetry image for 80 K, which is not appreciably different from the 6 K image above it. This is not surprising since based on magnetometry⁶, magnetoresistance⁵, and magnetic domain imaging⁶, the magnetization is in the kagome plane for temperatures below 80 K. The major effect of warming in this case is a broadening of the spectra, and in particular the loss of the very sharp β bands as seen in figure 4a, which we discuss in greater detail below. In the SI, we show that the earlier synchrotron ARPES data are consistent with an average over the twin domain data obtained from laser μ -ARPES. We attribute the three-fold pattern itself to originate from probing off high-symmetry k_z plane, yet still close to $k_z = 0$ plane (see SI for further explanation), confirming the bulk nature of the spectral data; high symmetry probing at $k_z = 0$ plane or $k_z = \pi$ plane will generate a six-fold pattern regardless of the “breathing” pattern of the kagomé.

Comparison to DFT calculations

We now take advantage of the high real and reciprocal space resolution of our single domain ARPES to investigate the effect of correlations on the electronic band structure of Fe_3Sn_2 . The first question concerns the effective on-site Coulomb potential U , which should be included in the DFT + U band structure calculations. Electron pockets centered on Γ and close to the Fermi level exist for a large range of U values ($U = 0.0 - 3.0$ eV) (see figure SI7). However, the distance ΔE to the Fermi energy from the bottom of the bands for the pocket varies strongly with U , as do the Fermi vectors k_F , which can be seen in figure 1c and SI7. The best description

of the α and γ bands, taking into account both the band bottom and k_F , occurs for $U = 1.3$ eV, differing from the values $U = 0.5$ eV⁴ or $U > 2$ eV²⁵ selected for previous DFT calculations.

We display the DFT cut along $\bar{M}\bar{\Gamma}\bar{M}'$, for $k_z = 0 - 0.05\pi$, $U = 1.3$ eV in figure 3b(ii). The cut is dominated by parabolic bands coexisting with a relatively flat band located around 15 meV above E_F , and supports the assertion that α and γ originate from bulk states smeared due to k_z broadening²⁶, and are asymmetric (3-fold instead of 6-fold) due to slight off $k_z = 0$ probing. We have labelled the features in the cut accordingly: the k_z broadening yields **two** visible branches cutting the Fermi level along the $\bar{M}\bar{\Gamma}$ trajectory, while there is a broader, merged α – like dispersion along $\bar{\Gamma}\bar{M}'$. The Fermi velocities do not precisely match those obtained by ARPES but can be tuned via small adjustments to the chemical potential on account of the apparent hybridization with the flat band very close to the Fermi level. We note that irrespective of the choice of U significant differences remain between ARPES and DFT. None of the existing DFT calculations reproduces the very small gap between the bottom of the α and γ bands and the top of δ ; additionally, the sharp β band found by ARPES near the Fermi level is not seen in calculations.

Sharp but marginal quasiparticles at low temperatures

Key parameters of quasiparticles which include their Fermi surface areas, mass, and scattering rates, are calculated from our experimental data. We display the representative dispersion cuts for the individual linear photon polarizations in figure 4a(i) and (iii) for horizontal (LH) polarization at 6 and 70 K, respectively, and in figure 4a(ii) and (iv) for vertical (LV) polarization at 6 and 70 K, respectively. LH displays mostly the α band, indicating it is an even orbital with respect to the incident plane of the experiment, while the β , γ , and δ bands are odd parity orbitals. In Table I we summarize for the three pockets the effective mass at the Fermi level calculated as $m^* = \hbar k_F (v_F)^{-1}$, where the Fermi velocity is $v_F = \left. \frac{1}{\hbar} \frac{\partial E}{\partial k} \right|_F$, the area of the electron pocket converted into the de Haas-van Alphen (dHvA) frequency as $f(T) = \frac{\hbar}{2\pi e} \times area$, and the scattering lengths of the quasiparticle defined as $\lambda = \frac{1}{\Delta k}$, where Δk is the half width of the momentum distribution curve (MDC) peaks (at 6 K and at the Fermi level). The area of the electron pockets is calculated by tracing the visible peaks of the corresponding

band at the Fermi level and assuming a circular extrapolation to make closed contours. More details on the EDC of the bands from k_F to band minimum can be found in figure SI5.

For the β band, $\lambda = 155 \pm 5 \text{ \AA}$ at 6 K, a remarkably long mean free path for a topological (bulk) metal and comparable to that for the much simpler surface Dirac quasiparticles for the n -type Bi_2Te_3 topological insulator ($\sim 190 \text{ \AA}$)²⁷; for α , λ is reduced by a factor of two to $\sim 85 \text{ \AA}$ but is still long by the same standards. These values are consistent with the residual ($T = 2 \text{ K}$) resistivity $\rho_{xx}(0) = 4.35 \mu\Omega \cdot \text{cm}$ and a carrier density of $1.8 \times 10^{28} \text{ m}^{-3}$ from transport data^{5,24} for samples similar to ours, grown by the same method by the same group. In particular, applying the Drude formula $\sigma_0 = \frac{ne^2\tau}{m}$ for conductivity, we obtain a scattering time $\tau \sim 4.5 \times 10^{-14} \text{ s}$ by assuming that the carriers have an effective mass $m = m_e$. For an averaged Fermi velocity of $\sim 1.2 \text{ eV- \AA}$, τ converts to a mean free path $l = v_F\tau \sim 82 \text{ \AA}$, which is of the order of the ARPES results for the α and β bands.

It is also interesting to ask whether there is bulk evidence for small Fermi surfaces similar to those which we have discovered. The answer is yes: the calculated de Haas van Alphen (dHvA) frequency 254 T of the β band, whose Fermi surface is centered on Γ , is in reasonable agreement with that measured for reference⁷ ($\sim 200 \text{ T}$) and attributed to the ‘‘Dirac ring’’ emanating from the putative Dirac point at the \bar{K} point and 0.1 eV below the Fermi surface. Given that DFT accounts for electron pockets centered on Γ while explaining the Dirac-like features in terms of an overlap of surface and bulk bands²⁰, a re-interpretation of the observed dHvA frequency is needed.

Moving below E_F , the β band is significantly broadened and effectively disappears for binding energies in excess of approximately 20 meV. Below this energy, the half-width at half-maxima $\Delta k(E)$ of the peaks in the MDC increases linearly with $|k(E) - k_F|$, with slope $b_\beta = 0.361 \pm 0.062$, as shown in figure 4. For the much steeper α band, there is a similar finding: $\Delta k(E)$ rises linearly with $|k(E) - k_F|$. The fitted slope $b_\alpha = 0.353 \pm 0.071$ is indistinguishable from both that for the β band, and is also not far from $b_\pi = \frac{1}{\pi}$, for which the relative quasiparticle wavelength $2\pi/|k(E) - k_F|$ is precisely twice the quasiparticle scattering length $1/\Delta k(E)$. Because of the linearity of the quasiparticle dispersions (upper frame of Fig. 4b) over the same momentum ranges, the low temperature (6 K) results are all

consistent with a marginal Fermi liquid hypothesis^{28,29}, for which the imaginary part of the self-energy is $\text{Im}(\Sigma) = \Delta E = \max(|E_B|, k_B T) = \max(b\hbar v_F |k(E) - k_F|, b'k_B T)$, which translates to $\Delta k(E) = \max(b|k(E) - k_F|, b'k_B T/\hbar v_F)$ (1), where b and b' are coupling constants of order unity, where the initial theoretical Ansatz was $\frac{b'}{b} = 1$. Experiments have yielded a variety of values for b in strongly correlated systems. For example, for the cuprate superconductor $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ (BSCCO), $b_{\text{BSCCO}} = 0.75^{29}$, while for BaCr_2As_2 , $b_{\text{BaCr}_2\text{As}_2}$ depends strongly on the band chosen, with resulting values from 0.35 to 0.63³⁰, and for the ferropnictides b varies throughout the range between 0 and 1.7^{31,32}.

Eq.(1) implies that a temperature increase from $T_{base} = 6$ to 70 K, as in figure 4a should cause, for small E and $\frac{b'}{b} = 1$, $\Delta k(E)$ to increase by $b'k_B(T - T_{base})/\hbar v_F = 1.3 \times 10^{-3} \text{ \AA}^{-1}$ and $2.7 \times 10^{-3} \text{ \AA}^{-1}$ for the α and β bands respectively. This is much more modest than what we actually observe for Fe_3Sn_2 , where at E_F , Δk for α grows by $(8 \pm 1) \times 10^{-3} \text{ \AA}^{-1}$, which is $b'/b = 6$ times larger than the theoretically expected ratio of unity and 2.4 times bigger than b'/b observed for BSCCO^{31,32}, while corresponding to a very large scattering rate, $\Delta E = \hbar \Delta k * v_F \approx 20 \text{ meV} \approx 3.3 k_B T$. At the same time, any distinction between the β and γ bands, which near the Fermi level are simply displaced by 20 meV with respect to each other, vanishes, which is consistent with the ΔE measured for the α band at 70 K, and also the fact that at 6 K, the β band becomes invisible for binding energies above a similar energy.

The conclusion is that E/T scaling is roughly obeyed in the sense that marginal quasiparticles for both the α and the β bands are distinguishable or not near the Fermi surface to an extent consistent with Eq(1). However, the value for b'/b is unusually large, and the energy-momentum diagram is very peculiar in that the much broader γ band seems much more associated with the minimum near Γ than the short, 20 meV stretch of β band visible near the Fermi surface, which simply looks like a sharp copy of the γ band displaced upwards by the same ~ 20 meV towards E_F . These observations, not easily accounted for by DFT, together suggest a many-body origin for the β band. A possible scenario is that there is strong hybridization between flat and γ band states near the bare Fermi surface which results in interaction-induced (Mott-like) localization that reduces the free carrier density; k_F for the electron pockets seen here would then be correspondingly reduced by δk_F , and the resulting (β) band will be raised towards E_F by $\Delta = \hbar v_F \delta k_F$. There will of course still be broad spectral

weight from the unrenormalized (γ) bands at the original k_F , and for binding energies in excess of Δ , the localized electrons rejoin the Fermi sea and the spectral weight will reside primarily near the γ band as might be calculated using DFT. Warming would similarly act to delocalize the carriers, and thus cause the loss of the β “band”.

Band	Fermi surface area (\AA^{-2})	dHvA frequency (T)	Fermi velocity v_F ($\text{\AA} \cdot \text{s}^{-1}/\hbar$)	Effective mass (m^*/m_e)	Scatt. length λ (\AA)
α	0.015 ± 0.005	157 ± 20	1.62 ± 0.05	0.36 ± 0.06	85 ± 5
β	0.024 ± 0.005	254 ± 20	0.78 ± 0.01	1.01 ± 0.08	155 ± 20
γ	0.041 ± 0.002	433 ± 20	0.79 ± 0.04	1.10 ± 0.10	38 ± 5

Table I Summary of the calculated quantities (at 6 K): Fermi surface area, dHvA frequency, Fermi velocity, effective mass, and scattering length, calculated at the Fermi surface of the corresponding α , β , and γ bands.

Conclusions

We have discovered electron pockets labeled as α , β , and γ centered at the Γ point in Fe_3Sn_2 by employing state-of-the-art μ -focused laser ARPES to overcome the averaging effects of crystallographic twinning in Fe_3Sn_2 crystals. These electron pockets are not found in the simple tight-binding models proposed for Fe_3Sn_2 , which also posit doubled Dirac cones near the K point, while they can be reproduced by DFT calculations, where no Dirac cones are predicted (see SI for detailed discussion). The α and γ electron pockets are very sensitive to the Coulomb interaction parameter U in DFT+U calculations, and are well reproduced by $U = 1.3$ eV. The same calculations also yield a flat band about 20 meV above the Fermi level for the pockets.

Our combination of high-resolution spectroscopy with single domain selection provides an unprecedented opportunity to examine the quasiparticles in a strongly correlated kagome metal. This means that we are able to measure scattering lengths as well as Fermi surface areas. The former is in semiquantitative agreement with the mean free path obtainable from residual resistance data, while the Fermi surface areas are near de Haas van Alphen results previously interpreted to derive from the Dirac cones not found by DFT.

At low temperature, once the quasiparticle Green's functions are examined away from the regime where their widths are dominated by elastic scattering, it appears that their widths in momentum space scale with their momenta, implying marginal rather than ordinary Fermi liquid behaviour, and associated strong correlation physics. However, the abrupt disappearance of the sharpest band at the very modest binding energy of 20 meV, and quasiparticle broadening greatly in excess of $k_B T$ on warming to 70 K indicate that the kagome ferromagnet Fe_3Sn_2 is hosting more than "conventional" strong correlations. The flat band seen in DFT just above the Fermi energy is a distinguishing feature: virtual and thermal occupancy of this band could greatly enhance electron-electron scattering that we see directly in our data, and also account for formation of the peculiarly sharp and displaced β band which appears below 70 K together with numerous anomalous magnetotransport properties. We close by noting that there is an enormous literature dealing with the Anderson and Kondo lattices where dispersive bands coexist with bands which are flat on account of small underlying atomic orbitals³³. Our β band results, which we can only explain at a qualitative level, suggest further theoretical and experimental studies to examine interaction effects where dispersive bands cross bands which are flat for reasons of lattice geometry, as exhibited for example by kagome systems, rather than small orbital extent³⁴.

Acknowledgement

S.A.E, D.G.-M., O.V.Y., M.S. acknowledge the support from NCCR-MARVEL funded by Swiss National Science Foundation, S.A.E. acknowledges the European Union's Horizon 2020 research and innovation programme under the Marie Skłodowska-Curie grant agreement No 701647, G.A. acknowledges the European Research Council HERO Synergy grant SYG-18 810451. The laser-ARPES work at the University of Geneva was supported by the SNSF grants 2000020_165791, 200020_184998. Part of this work was performed at the Surface/Interface: Microscopy (SIM) beam line of the Swiss Light Source, Paul Scherrer Institut, Villigen, Switzerland. All first-principles calculations were performed at the Swiss National Supercomputing Centre (CSCS) under the projects s1008 and mr27. We acknowledge Neeraj Kumar for taking the XMCD-PEEM images, and Markus Müller for helpful discussions.

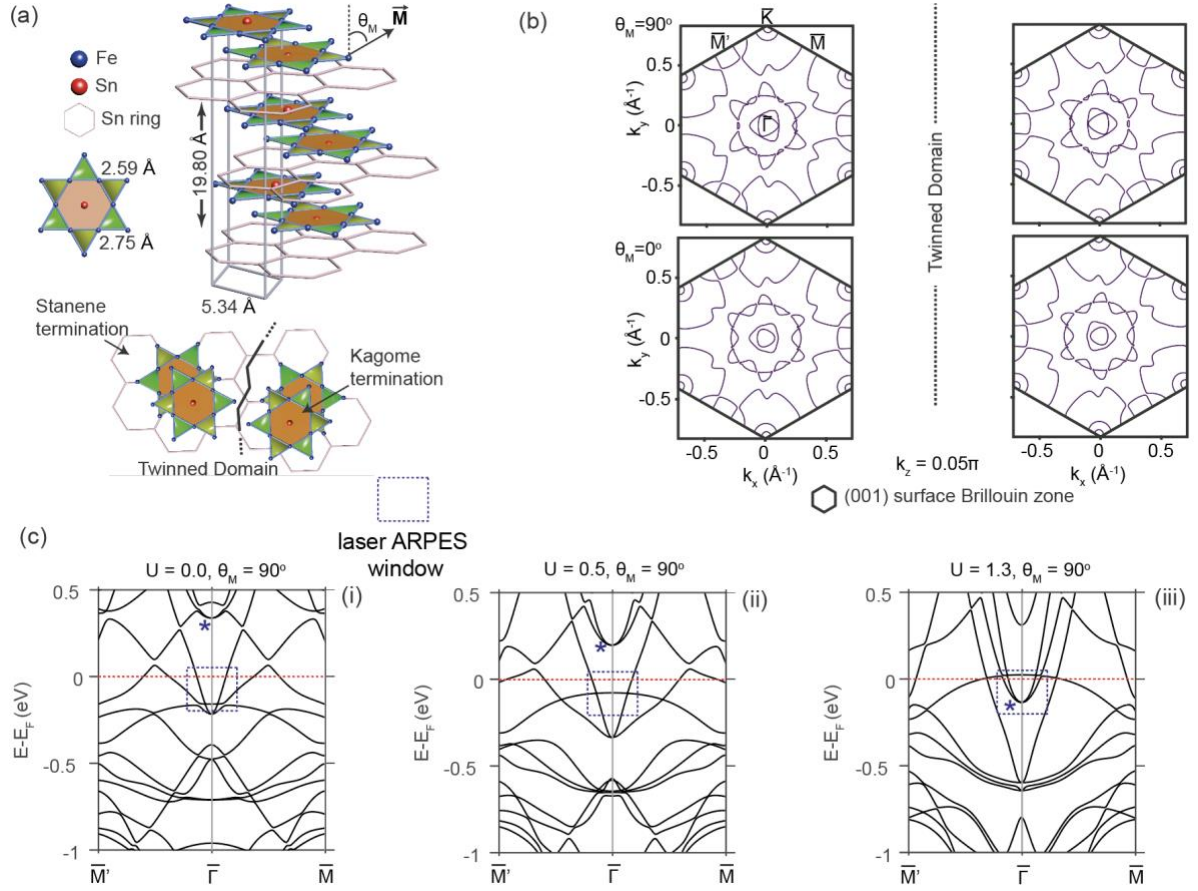


Figure 1. a. Crystal structure of Fe_3Sn_2 displaying a stanene layer sandwiched between kagomé bilayers. θ_M denotes the angle between the magnetic moment \vec{M} and the c -axis. Twin domains may occur when the system is rotated around the c -axis. b. Calculated Fermi surface at $k_z = 0.05\pi/c$ for $U = 1.3$ eV showing a three-fold pattern (left) and its twinned image (right) when the magnetic moment is pointing off the c -axis ($\theta_M = 90^\circ$) and along the c -axis ($\theta_M = 0^\circ$). c. Results of DFT calculations for $k_z = 0$ with representative $U = 0, 0.5,$ and 1.3 eV values showing the presence of an electron pocket (denoted by asterisks), which is investigated by μ -ARPES (marked by the area within the dashed-line).

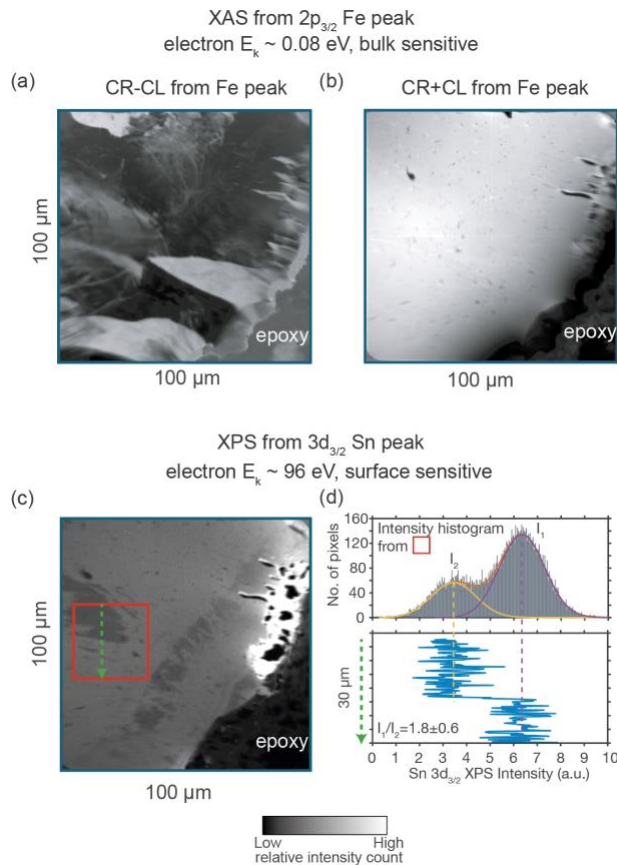


Figure 2. a. XPEEM magnetic contrast (CR-CL intensity) map taken at the Fe L_3 peak, whose signal is ‘bulk’-sensitive, showing a complex magnetic domain configuration in an area where b. panel (CR+CL intensity) shows a homogeneous contrast, indicating a homogeneous phase of the sample. c. XPEEM XPS map of the sample at the Sn $3d_{3/2}$ peak, whose signal is surface sensitive, showing a domain structure distinct from the magnetic domain shown in panel a., which is attributed to different cleaving terminations, *i.e.*, two different surface terminations. This shows that the magnetic domain has no correlation to the surface termination. Panel d. shows that the intensity difference found in panel c. is step-like with intensity ratio of 1.8 ± 0.6 .

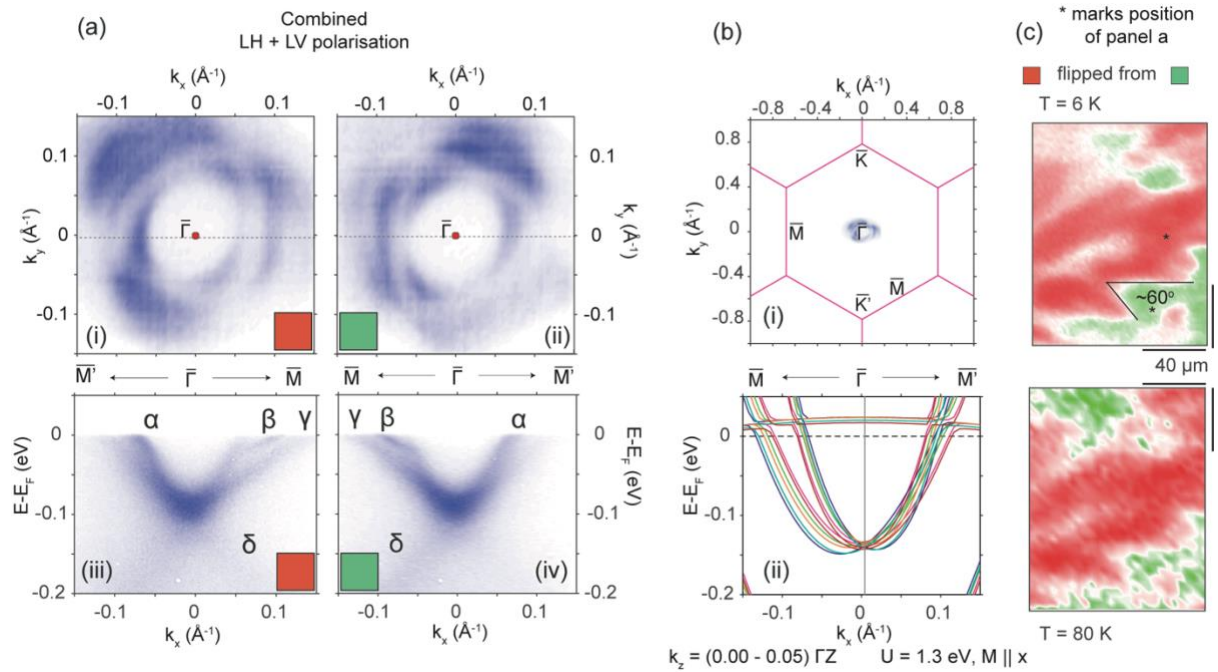


Figure 3. a. Laser ARPES data for Sn-terminated Fe₃Sn₂. (i)-(ii) Fermi surfaces showing a three-fold pattern with an electron pocket at the $\bar{\Gamma}$ point and three petals, which are rotated relative to each other distinguishing the crystal twin domains. (iii)-(iv) Energy versus momentum cut of one of the petals (dashed line at (i) and (ii), $\bar{M}\bar{\Gamma}\bar{M}'$ direction) showing the electron pocket band labeled α , a band labeled β , which abruptly disappears through α , a petal labeled γ sharing a bottom with the α band, and lastly a broad and weak band referred to as δ . b (i) Illustration of the reciprocal space probed with laser ARPES, which spans a small portion of the total BZ. b (ii) DFT calculation along $\bar{M}\bar{\Gamma}\bar{M}'$ direction for $k_z = 0 - 0.05 \pi$ as illustration of k_z broadening and asymmetrization, agreeing tentatively on the formation of α and γ bands. c. Twin domains showing a relatively unchanged shape at 6 K as compared to 80 K. The magnetisation points along the ab -plane at both temperatures but the magnetic domain size is known to be different at these two temperatures, with large domains at temperatures below 64 K and with relatively smaller domains at 80 K ⁶.

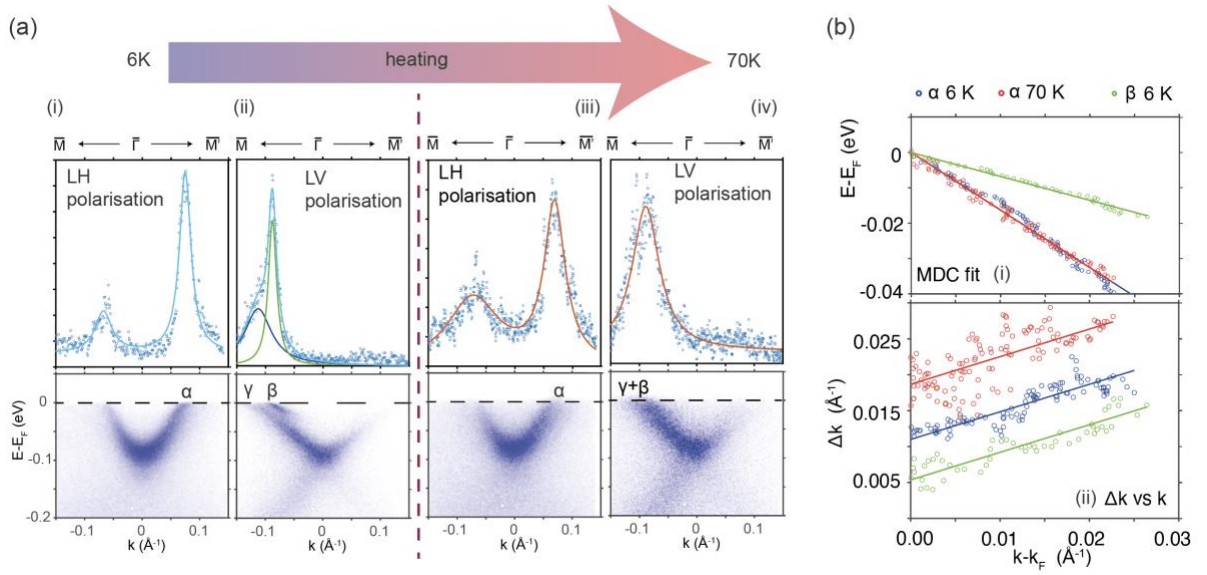


Figure 4. (a) $\bar{M}\bar{\Gamma}\bar{M}'$ cut from LH polarization displays mostly band labeled α at 6 K (i) and 70 K (iii), with MDC at the Fermi energy and the fitting result. $\bar{M}\bar{\Gamma}\bar{M}'$ cut from LV polarization reveals mostly the band labeled β and γ at 6 K (ii) and 70 K (iv), with MDC at the Fermi energy and the fitting result. (b) (i) Plot of the fitted peak position from MDC for α (blue 6 K and red 70 K) and β (green 6 K) with resulting linear fit super-imposed. (ii) Plot of peak width Δk vs $k - k_F$ showing a same-gradient linear behaviour close to the Fermi level for α (blue 6 K and red 70 K) and β (green 6 K) indicating a marginal Fermi liquid. Upon heating to 70 K we can see that the line is shifted as described by Eq. (1) in text.

- 1 Lecaer, G., Malaman, B. & Roques, B. MOSSBAUER-EFFECT STUDY OF Fe_3Sn_2 . *Journal of Physics F-Metal Physics* **8**, 323-336 (1978).
- 2 Kida, T. *et al.* The giant anomalous Hall effect in the ferromagnet Fe_3Sn_2 —a frustrated kagome metal. *Journal of Physics: Condensed Matter* **23**, 112205, doi:10.1088/0953-8984/23/11/112205 (2011).
- 3 Tang, E., Mei, J.-W. & Wen, X.-G. High-Temperature Fractional Quantum Hall States. *Physical Review Letters* **106**, 236802, doi:10.1103/PhysRevLett.106.236802 (2011).
- 4 Yao, M. *et al.* Switchable Weyl nodes in topological Kagome ferromagnet Fe_3Sn_2 . *arXiv* **1810.01514** (2018).
- 5 Kumar, N., Soh, Y., Wang, Y. & Xiong, Y. Magnetotransport as a diagnostic of spin reorientation: Kagome ferromagnet as a case study. *Physical Review B* **100**, 214420, doi:10.1103/PhysRevB.100.214420 (2019).
- 6 Heritage, K. *et al.* Images of a First-Order Spin-Reorientation Phase Transition in a Metallic Kagome Ferromagnet. *Advanced Functional Materials* **30**, 1909163, doi:10.1002/adfm.201909163 (2020).
- 7 Ye, L. D. *et al.* de Haas-van Alphen effect of correlated Dirac states in kagome metal Fe_3Sn_2 . *Nature Communications* **10**, doi:10.1038/s41467-019-12822-1 (2019).

- 8 Syozi, I. STATISTICS OF KAGOME LATTICE. *Progress of Theoretical Physics* **6**, 306-308, doi:10.1143/ptp.6.306 (1951).
- 9 Onsager, L. Crystal statistics I A two-dimensional model with an order-disorder transition. *Physical Review* **65**, 117-149, doi:10.1103/PhysRev.65.117 (1944).
- 10 Husimi, K. & Syozi, I. THE STATISTICS OF HONEYCOMB AND TRIANGULAR LATTICE .1. *Progress of Theoretical Physics* **5**, 177-186, doi:10.1143/ptp/5.2.177 (1950).
- 11 Syozi, I. THE STATISTICS OF HONEYCOMB AND TRIANGULAR LATTICE .2. *Progress of Theoretical Physics* **5**, 341-351, doi:10.1143/ptp/5.3.341 (1950).
- 12 Kano, K. & Naya, S. ANTIFERROMAGNETISM - THE KAGOME ISING NET. *Progress of Theoretical Physics* **10**, 158-172, doi:10.1143/ptp.10.158 (1953).
- 13 Miyazima, S. & Syozi, I. MODIFIED SLATER MODEL IN KAGOME LATTICE. *Progress of Theoretical Physics* **40**, 425-&, doi:10.1143/ptp.40.425 (1968).
- 14 Takano, M., Shinjo, T., Kiyama, M. & Takada, T. MAGNETIC PROPERTIES OF JAROSITES RFE₃(OH)₆(SO₄)₂(R=NH₄,NA OR K). *Journal of the Physical Society of Japan* **25**, 902-&, doi:10.1143/jpsj.25.902 (1968).
- 15 Obradors, X. *et al.* Magnetic frustration and lattice dimensionality in SrCr₈Ga₄O₁₉. *Solid State Communications* **65**, 189-192, doi:[https://doi.org/10.1016/0038-1098\(88\)90885-X](https://doi.org/10.1016/0038-1098(88)90885-X) (1988).
- 16 Broholm, C., Aeppli, G., Espinosa, G. P. & Cooper, A. S. ANTIFERROMAGNETIC FLUCTUATIONS AND SHORT-RANGE ORDER IN A KAGOME LATTICE. *Physical Review Letters* **65**, 3173-3176, doi:10.1103/PhysRevLett.65.3173 (1990).
- 17 Malaman, B., Roques, B., Courtois, A. & Protas, J. CRYSTAL-STRUCTURE OF IRON STANNIDE FE₃SN₂. *Acta Crystallographica Section B-Structural Science* **32**, 1348-1351, doi:10.1107/s0567740876005323 (1976).
- 18 Ye, L. D. *et al.* Massive Dirac fermions in a ferromagnetic kagome metal. *Nature* **555**, 638-+, doi:10.1038/nature25987 (2018).
- 19 Lin, Z. Y. *et al.* Flatbands and Emergent Ferromagnetic Ordering in Fe₃Sn₂ Kagome Lattices. *Physical Review Letters* **121**, doi:10.1103/PhysRevLett.121.096401 (2018).
- 20 Tanaka, H. *et al.* Three-dimensional electronic structure in ferromagnetic Fe₃Sn₂ with breathing kagome bilayers. *Physical Review B* **101**, doi:10.1103/PhysRevB.101.161114 (2020).
- 21 Yin, J. X. *et al.* Giant and anisotropic many-body spin-orbit tunability in a strongly correlated kagome magnet. *Nature* **562**, 91-+, doi:10.1038/s41586-018-0502-7 (2018).
- 22 Wang, Q., Sun, S., Zhang, X., Pang, F. & Lei, H. Anomalous Hall effect in a ferromagnetic Fe₃Sn₂ single crystal with a geometrically frustrated Fe bilayer kagome lattice. *Physical Review B* **94**, doi:10.1103/PhysRevB.94.075135 (2016).
- 23 Kumar, N., Soh, Y., Wang, Y., Li, J. & Xiong, Y. Anomalous planar Hall effect in a kagome ferromagnet. *arXiv* (2020).
- 24 Kumar, N., Soh, Y., Wang, Y., Li, J. & Xiong, Y. Tuning the electronic band structure in a kagome ferromagnetic metal via magnetization. *arXiv* **2111.03826** (2021).
- 25 Lin, Z. Z. & Chen, X. Tunable Massive Dirac Fermions in Ferromagnetic Fe₃Sn₂ Kagome Lattice. *Physica Status Solidi-Rapid Research Letters* **14**, doi:10.1002/pssr.201900705 (2020).
- 26 Strocov, V. N. Intrinsic accuracy in 3-dimensional photoemission band mapping. *Journal of Electron Spectroscopy and Related Phenomena* **130**, 65-78, doi:10.1016/s0368-2048(03)00054-9 (2003).

- 27 Chen, C. Y. *et al.* Tunable Dirac Fermion Dynamics in Topological Insulators. *Scientific Reports* **3**, doi:10.1038/srep02411 (2013).
- 28 Varma, C. M., Littlewood, P. B., Schmittrink, S., Abrahams, E. & Ruckenstein, A. E. PHENOMENOLOGY OF THE NORMAL STATE OF CU-O HIGH-TEMPERATURE SUPERCONDUCTORS. *Physical Review Letters* **63**, 1996-1999, doi:10.1103/PhysRevLett.63.1996 (1989).
- 29 Valla, T. *et al.* Evidence for quantum critical behavior in the optimally doped cuprate Bi₂Sr₂CaCu₂O_{8+δ}. *Science* **285**, 2110-2113, doi:10.1126/science.285.5436.2110 (1999).
- 30 Nayak, J. *et al.* Observation of a remarkable reduction of correlation effects in BaCr₂As₂ by ARPES. *Proc. Natl. Acad. Sci. U. S. A.* **114**, 12425-12429, doi:10.1073/pnas.1702234114 (2017).
- 31 Fink, J. *et al.* Experimental evidence for importance of Hund's exchange interaction for incoherence of charge carriers in iron-based superconductors. *Physical Review B* **95**, doi:10.1103/PhysRevB.95.144513 (2017).
- 32 Fink, J. *et al.* Non-Fermi-liquid scattering rates and anomalous band dispersion in ferropnictides. *Physical Review B* **92**, doi:10.1103/PhysRevB.92.201106 (2015).
- 33 Paschen, S. & Si, Q. Quantum phases driven by strong correlations. *Nature Reviews Physics* **3**, 9-26, doi:10.1038/s42254-020-00262-6 (2021).
- 34 Ye, L. *et al.* A flat band-induced correlated kagome metal. arXiv:2106.10824 (2021). <<https://ui.adsabs.harvard.edu/abs/2021arXiv210610824Y>>.