

Absence of a pressure gap and atomistic mechanism of the oxidation of pure Co nanoparticles

Jaianth Vijayakumar,[†] Tatiana M. Savchenko,[†] David M. Bracher,[†] Gunnar Lumbeeck,[‡] Armand Béch  ,[‡] Jo Verbeeck,[‡] Štefan Vajda,[¶] Frithjof Nolting,[†] C.A.F. Vaz,^{*,†} and Armin Kleibert^{*,†}

[†]*Swiss Light Source, Paul Scherrer Institut, 5232 Villigen PSI, Switzerland*

[‡]*EMAT, University of Antwerp, 2020 Antwerpen, Belgium*

[¶]*Department of Nanocatalysis, J. Heyrovský Institute of Physical Chemistry v.v.i., Czech Academy of Sciences, Dolejš  kova 2155/3, 18223 Prague, Czech Republic*

E-mail: carlos.vaz@psi.ch; armin.kleibert@psi.ch

Abstract

We present a detailed atomistic picture of the oxidation mechanism of Co nanoparticles and its impact on magnetism by experimentally following the evolution of the structure, chemical composition, and magnetism of individual, gas-phase grown Co nanoparticles during controlled oxidation. The early stage oxidation occurs in a two-step process characterized by (i) the initial formation of small CoO crystallites randomly distributed across the nanoparticle surface, until their coalescence leads to structural completion of the oxide shell and passivation of the metallic core; (ii) progressive conversion of the CoO shell to Co₃O₄, accompanied by void formation due to the nanoscale Kirkendall effect. The Co nanoparticles remain highly reactive toward oxygen during

phase (i), demonstrating the absence of a pressure gap whereby a low reactivity at low pressures is postulated. Our results provide an important benchmark for an improved understanding of the magnetism of oxidized cobalt nanoparticles, with potential implications on their performance in catalytic reactions.

Keywords

Nanoparticles, oxidation, pressure gap, reactivity, magnetism, cobalt, cobalt oxide, rock-salt CoO, spinel Co₃O₄, scanning transmission electron microscopy, x-ray absorption spectroscopy, x-ray magnetic circular dichroism, x-ray magnetic linear dichroism, soft x-ray spectro-microscopy, x-ray photoemission electron microscopy

Introduction

The chemistry and magnetism of nanoparticles of 3*d* transition metals and metal-oxides are of fundamental interest for applications in fields ranging from spintronics, as elemental building blocks or as components in novel high performance magnets;^{1,2} to catalysis, including for water hydrolysis, Fischer–Tropsch reactions, or for controlling reaction kinetics using local magnetic heating protocols;^{3–7} and in biomedicine, for example, as environmental assays, for applications in tissue imaging, or in hyperthermia for cancer treatment.^{8,9} Such interest is a direct consequence of their reduced size and of the modified properties that emerge at the nanoscale induced by quantum confinement and dominant surface effects that lead to enhanced electronic and magnetic properties and to high chemical reactivity. The reduction in size to the nanoscale also permits the stabilisation of crystal structures not stable in bulk, while the presence of varying oxidation states of metal cations leads to a wide range of nanoparticle systems, each with its unique properties. Among these systems, cobalt and cobalt oxide nanoparticles in particular have led to important discoveries, such as the nanoscale Kirkendall effect, which underpins the synthesis process of hollow nanos-

structures for nano-reactors or for complex nanocomposite systems,^{10–12} and the magnetic exchange-bias effect,¹³ which has been fundamental for the development of today’s spintronics devices.^{2,14–17} However, and despite the immense body of work, basic questions about the actual oxide shell formation in cobalt nanoparticles and its impact on the magnetism of oxide-shell-metallic-core nanoparticles remain open. For instance, most investigations on the oxidation of cobalt nanoparticles report the presence of rocksalt cobalt oxide (CoO) shells surrounding a remaining metallic cobalt core or CoO hollow spheres, while the formation of the anticipated, thermodynamically more stable spinel Co_3O_4 is less frequently found.^{9,10,18–26} Moreover, in most experiments, high or even ambient pressures and elevated temperatures were required to achieve a substantial oxidation of the Co nanoparticles. These findings are in stark contrast to the high reactivity of molecular oxygen with thin Co films, which occurs at minute oxygen exposures under the initial formation of CoO and subsequent formation of Co_3O_4 , even at cryogenic temperatures and under vacuum conditions.^{27–29}

Such differences in chemical reactivity are often assigned to the so-called pressure gap, which refers to the long-standing problem of reconciling low and high pressure reactivity in heterogeneous catalysis^{30–32} and attributed to mass transfer limitations, surface coverage with adsorbed species, the onset of chemical reactions that are absent at low pressure, or the formation of different products under low and high pressure, including the variances in the oxidation of the catalytic metal and the reactivity of particles dependent of their oxidation state under different working conditions of pressure.³³ Of particular impact to the atomic-level understanding of the pressure gap could be the presence of contaminants at higher pressures which are absent under ultrahigh vacuum conditions.³⁰ Concerning the magnetic properties, the reported structural and chemical properties hardly explain the magnitude of the experimentally determined exchange bias effects as well as other magnetic phenomena such as superparamagnetic inclusions or disordered spins in the oxide shell.² Finally, an experimental confirmation for the uniform oxidation process that is assumed in the oxidation theory by Cabrera and Mott frequently discussed in the context of $3d$

transition metal nanoparticles oxidation is still missing.^{2,25,34–39}

These ambiguities are compounded by the experimental difficulty of investigating the structure, composition, and magnetic properties of $3d$ transition metal nanoparticles during oxidation under well-defined conditions. For instance, it is well known that both the reactivity with oxygen and the magnetic properties of nanoparticles depend on a large variety of factors including particle size, shape, structure, separation, mobility, nature of the substrate or embedding medium, and reaction conditions, which makes it difficult to disentangle these different aspects. Also, the detailed structural characterisation of nanoparticles during the different stages of oxidation is challenging, since typical investigations require air exposure of the samples for the transfer to suitable high resolution electron microscopes, while the vacuum conditions in most of these instruments are not suitable for well-controlled *in situ* oxidation studies. Moreover, it is known that Co nanoparticles with very distinct magnetic properties in the pristine metallic state can coexist, irrespective of particle size, which makes the interpretation of their magnetic properties upon oxidation complicated, in particular when averages over large ensembles are considered.⁴⁰

In this work, we take advantage of the capabilities of *in situ* photoemission electron microscopy (XPEEM)⁴¹ for probing the electronic, chemical, and magnetic state of individual nanoparticles in combination with *ex situ* high-angle annular dark-field scanning transmission electron microscopy (HAADF-STEM) measurements to yield the atomically resolved structure of nanoparticles conserved in different oxidation states by means of passivating carbon capping layers.^{40,42–48} This approach enables us to exclude effects of particle size, shape, mobility, and interparticle magnetic and chemical interactions to determine the intrinsic oxidation process of metallic Co nanoparticles and its impact on the magnetic properties. Our results unambiguously demonstrate that pure Co nanoparticles supported on chemically inert substrates exhibit a high reactivity with molecular oxygen, comparable to that of thin Co films under ultrahigh vacuum conditions. We argue that the very different oxidability of the metal reported in the literature is related rather to the purity of the Co nanoparti-

cles than due to the presence of a pressure gap between low and high pressure experiments. Our structural characterisation shows that the oxide shell does not grow continuously, as frequently assumed in the literature and premised in the metal oxidation theory by Cabrera and Mott,⁴⁹ but instead, develops through the simultaneous nucleation and growth of independent CoO crystallites randomly distributed over the nanoparticle surface. In fact, we find that the oxidation reaction in Co nanoparticles occurs in a two step process with an initial rapid formation of CoO and a subsequent progressive conversion of CoO to Co₃O₄ upon coalescence of the CoO crystallites, closing the oxide shell. At this stage, the nanoscale Kirkendall effect sets in, which leads to a physical and magnetic decoupling of the oxide shell and the remaining metallic core, possibly explaining the reduced exchange bias effect observed in this system as compared to the theoretical value.

Experimental

Pure metallic fcc Co nanoparticles with sizes ranging between 10–20 nm are grown from the gas phase in an arc cluster ion source and deposited in ultrahigh vacuum (UHV) on chemically inert substrates containing marker structures for sample navigation. After deposition, the nanoparticles are characterised *in situ* by means of XPEEM, Fig. 1(a). The chemical state of the nanoparticles directly after deposition as well as after step-wise oxidation is characterized by means of local x-ray absorption (XA) spectroscopy using linearly polarized x-rays. The magnetic properties are probed using circularly polarized x-rays by taking advantage of the x-ray magnetic circular dichroism (XMCD) effect at the Co L_3 edge.^{50,51} For *in situ* oxidation and temperature-dependent investigations, Si-wafers with native oxide layer (SiO_x) are used as substrates, Fig. 1(b). Samples suitable for *ex situ* HAADF-STEM studies are prepared under similar conditions on electron transparent Si₃N₄-membranes with a thickness of 10 nm covered with an amorphous carbon layer to improve the electric conductivity required in XPEEM, as illustrated in Fig. 1(c). As determined by the XA spectra,

we found that we required approximately ten times higher oxygen exposure for the carbon-coated samples to achieve similar oxidation states as for the samples on the Si-wafers. Upon controlled oxidation and XPEEM characterisation of the resulting magnetic and chemical state, the nanoparticles are covered with an additional amorphous carbon layer in UHV before exposing the sample to air for the transfer to the HAADF-STEM instrument, Fig. 1(d). Further details about the sample preparation and the XPEEM data acquisition and analysis are provided in the Methods section.

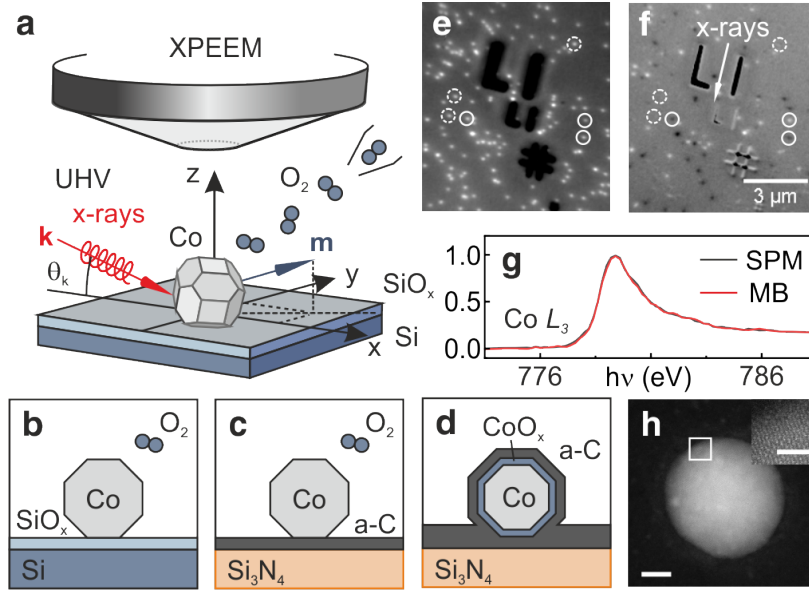


Figure 1: *In situ* XPEEM nanospectroscopy. (a) Schematic of the XPEEM setup for the *in situ* oxidation of Co nanoparticles by means of molecular oxygen dosing under UHV-conditions. (b–d) Illustration of the samples under investigation: (b) Co nanoparticles on Si/SiO_x-wafers, (c) on electron transparent Si₃N₄-membranes covered with an amorphous carbon (a-C) layer, and (d) upon capping with an additional a-C-layer for transfer to the HAADF-STEM instrument. (e) XPEEM elemental and (f) respective magnetic contrast map of Co nanoparticles in the pristine metallic state on Si/SiO_x acquired with the photon energy $h\nu$ set to the Co L_3 peak energy (the XMCD contrast ranges from ± 0.025). The white arrow indicates the projected x-ray propagation direction. White circles indicate MB, dashed circles denote SPM nanoparticles. The dark features are due to the saturated signal of lithographic gold marker structures used for sample navigation. (g) Corresponding XA spectra at the Co L_3 edge. (h) HAADF-STEM micrograph of a Co nanoparticle preserved in the pristine metallic state by means of the a-C-layers (scale bar is 5 nm). The inset displays an enlarged image of the highlighted region (scale bar is 1 nm).

Results

Figure 1(e) shows an XPEEM elemental contrast map of a pristine, metallic Co nanoparticle sample on a Si/SiO_x-wafer. Bright spots originate from the resonant Co L_3 edge excitation of nanoparticles, which are randomly distributed across the substrate. The corresponding magnetic contrast map, shown in Fig. 1(f), reveals that about half of the nanoparticles are in a magnetically blocked (MB) state (see for instance the solid circles in the figure) and exhibit stable magnetic contrast ranging from black to white similar to earlier findings.⁴⁰ The magnetic contrast distribution in Fig. 1(f) reflects a random orientation of the magnetisation (\mathbf{m}) of the nanoparticles due to the stochastic deposition process.⁴⁰ The other portion of nanoparticles is in a superparamagnetic (SPM) state (dashed circles), which is characterized by thermally induced fluctuations of \mathbf{m} at a rate τ_r faster than the experimental data acquisition time, $\tau = 400$ s in the present experiments. For $\tau \leq \tau_r$ ($\tau > \tau_r$) the nanoparticles are in a SPM (MB) state. We have earlier shown that the pristine Co nanoparticles in the MB state indicate a significantly enhanced MAE when compared to the known properties of bulk fcc Co, in contrast to the SPM nanoparticles.⁴⁰ Fig. 1(g) shows that the *in situ* XA spectra extracted from both types of particles correspond to metallic Co and are practically identical, demonstrating that their different magnetic behaviour cannot be assigned to different chemical states (reference XA spectra are shown in Fig. S1). The metallic purity of the nanoparticles in their pristine state irrespective of their magnetic state, SPM or MB, is further confirmed by *ex situ* HAADF-STEM investigations upon passivation (without oxygen dosing) using a-C-layers on the Si₃N₄-membranes illustrated in Fig. 1(d). An example HAADF-STEM micrograph is shown in Fig. 1(h) displaying a pure metallic Co nanoparticle showing no magnetic contrast in XPEEM at room temperature, indicating an SPM state. The absence of an oxide shell confirms the effective passivation of the nanoparticles against air exposure by the a-C-layers.

The effect of oxygen exposure on the chemical state and the magnetism of the nanoparticles at room temperature is shown in Fig. 2. Panels (a-g) display the evolution of the XA

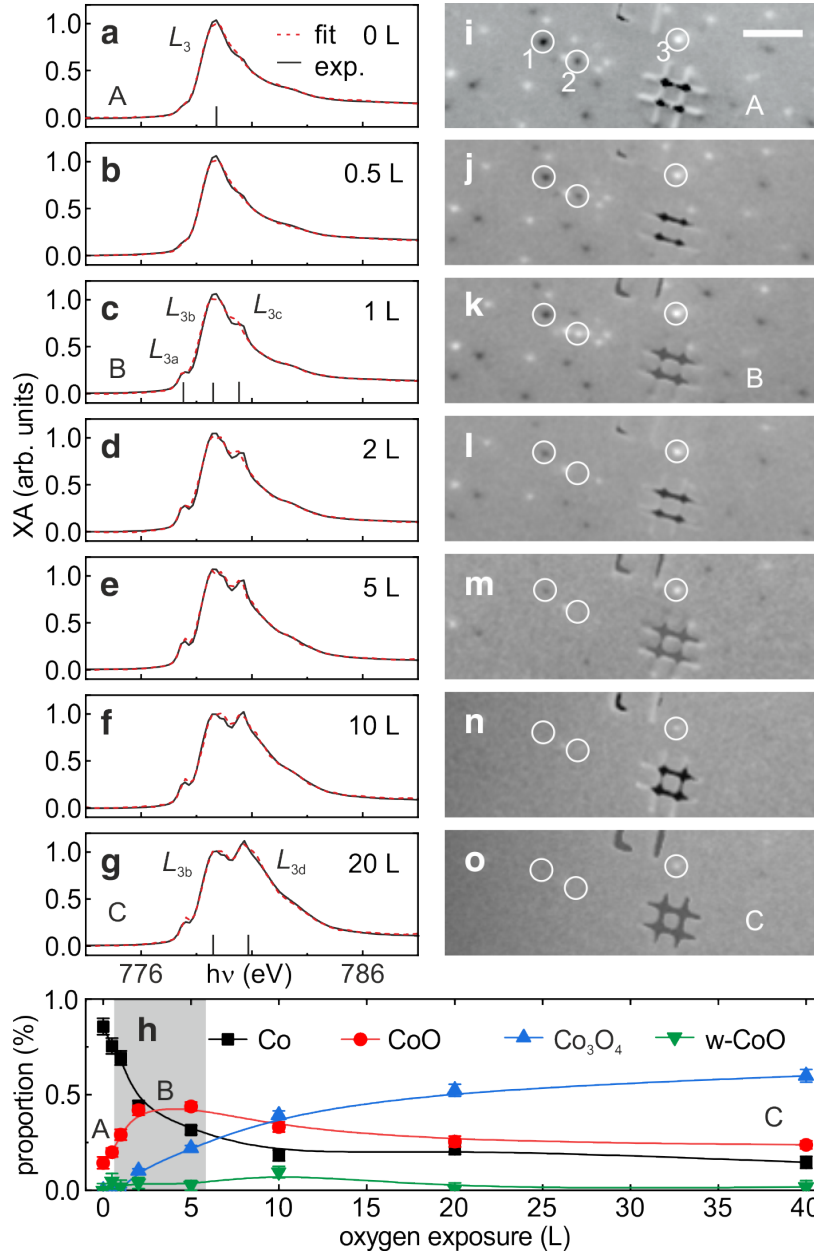


Figure 2: Evolution of the chemical and magnetic states of Co nanoparticles deposited on Si/SiO_x during *in situ* oxidation. (a-g) XA spectra as a function of molecular oxygen dosage (black lines). Specific features at the Co L_3 edge of metallic Co and of the different cobalt oxides discussed in the text are indicated in (a), (c), and (g). (h) Relative proportion of Co, CoO, wustite-CoO, and Co₃O₄ as a function of oxygen dosage obtained from a chemical composition analysis (statistical error bars are smaller than the symbol size). The lines are guides to the eye. The corresponding fits to the XA spectra are shown as red dashed lines in panels (a-g). (i-o) Magnetic contrast maps for the different oxygen dosages. The scale bar is 500 nm. The onset of three specific chemical states, A – pristine, metallic state, B – CoO-dominated state, and C – Co₃O₄-dominated state are denoted in the respective panels.

spectra (black lines) up to an exposure of 20 L ($1 \text{ L} = 1.33 \times 10^{-6} \text{ mbar} \cdot \text{s}$, see Methods). Fig. 2(a) displays again the XA spectra (average over SPM and MB) of the pristine state of the nanoparticles for better comparison. Exposure to about 1 L oxygen leads to the appearance of two noticeable shoulders on both sides of the metallic Co L_3 peak, Fig. 2(c). These shoulders, here referred to as Co L_{3a} and L_{3c} , correspond to XA features of CoO, see Fig. S1(b). A third CoO peak, denoted as Co L_{3b} , coincides with the Co L_3 peak of metallic cobalt. Up to this oxidation stage, we find only minor changes in the magnetic contrast maps, see Figs. 2(i-k). For instance, a few nanoparticles, such as particle "2", reverse their magnetic contrast due to thermally induced reversals of \mathbf{m} .^{40,52} Upon further oxygen exposure, the XA spectra evolve through another peak that appears at higher photon energy, as shown in Figs. 2(d-g), which is referred to as Co L_{3d} and indicates the formation of Co_3O_4 , see Fig. S1(c). These chemical changes are accompanied by a loss of magnetic contrast in most of the nanoparticles, see for instance particles "1" and "2" in Figs. 2(l-o). Only a few nanoparticles retain magnetic contrast at all exposures, see for instance particle "3" in Figs. 2(i-o). Quantitative composition analysis of the XA spectra reveals the proportion of Co, CoO, and Co_3O_4 as a function of oxygen exposure in the surface-near volume of the nanoparticles that is detected in XPEEM with the probing depth being 3–5 nm, see Methods. The data reveal an initial rapid increase of CoO peaking at about 5 L before its relative proportion starts to decrease, see Fig. 2(h). A small amount of wustite-CoO, which can be stabilised in cobalt oxide nanoparticles,²¹ appears only at 10 L, possibly as a transition phase between CoO and Co_3O_4 . The formation of Co_3O_4 occurs at a much lower rate when compared to CoO and increases monotonously, saturating at about 40 L. The contribution of metallic Co in the surface near region drops rapidly till 5 L and approaches zero at highest dosages. Based on this evolution and the respective signature in the magnetic contrast maps, we refer to three different chemical states as follows: (A) pristine metallic state, (B) CoO-dominated state, and (C) saturated, Co_3O_4 -dominated state, whose onsets are labeled in Fig. 2.

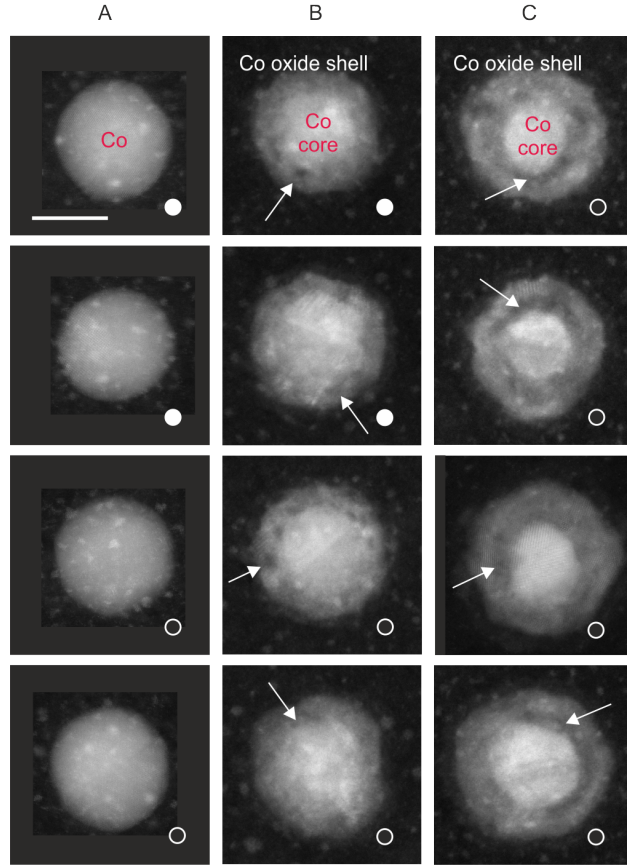


Figure 3: HAADF-STEM micrographs of carbon-capped Co nanoparticles in states A – C on Si_3N_4 -membranes (corresponding to 0 L, 1 L, and 20 L on Si/ SiO_x of Fig. 2). The micrographs in each column correspond to the same oxidation state as indicated by the labels. The white arrows highlight specific defects. Solid (open) white circles indicate that the respective nanoparticle exhibits (no) magnetic contrast in XPEEM in the indicated chemical state. The scale bar is 10 nm.

An overview with representative HAADF-STEM micrographs of Co nanoparticles in states A – C embedded in a-C on Si₃N₄-membranes are shown in Fig. 3, while the chemical and magnetic characterization of these samples by means of XPEEM is shown in Fig. S2. The left column displays Co nanoparticles in the pristine metallic state A. The solid and open white circles represent particles with and without XPEEM magnetic contrast, respectively. The middle column of Fig. 3 displays Co nanoparticles in oxidation state B that exhibited magnetic contrast (MB state) before oxidation. As indicated, the bottom two nanoparticles lost their magnetic contrast upon oxidation. The HAADF-STEM data yield no obvious morphological or structural characteristics that would explain the different magnetic behaviour. Instead, in all cases we find a defect-rich oxide shell with a thickness of about 4 nm around the remaining metallic core. Some larger defects in the oxide shell are highlighted with white arrows. The right column of Fig. 3 shows the Co nanoparticles in state C, where magnetic contrast is lost in nearly all nanoparticles (see Fig. 2). Most obvious in this state are the extended voids between the metallic core and the oxide shell, indicating the onset of the nanoscale Kirkendall effect.¹⁰ Furthermore, the metallic core size is reduced, while the oxide shell thickness is approximately the same as in state B. Like in state B, we do not find a correlation between structural features and the magnetic state before and after oxidation.

A closer inspection of the HAADF-STEM data reveals further structural details in the nanoparticles and their oxide shells. Specifically, we find that most of the metallic nanoparticles in state A possess face-centered-cubic (fcc) structure and not the hexagonally-closed-packed lattice known from bulk Co at room temperature. Moreover, most of the nanoparticles are not single crystalline, but consist of several grains or possess structural defects, as frequently reported for fcc Co nanoparticles.⁴⁰ One example is given in Fig. 4(a), where regions "i" and "ii" correspond to fcc Co grains with different crystallographic orientations. Similar to Fig. 4(b), we find that all nanoparticles in state B possess oxide shells that consist of many small crystallites. The typical size of the oxide crystals is 3–5 nm. The atomic resolution HAADF-STEM data allow us to probe possible crystallographic relations between

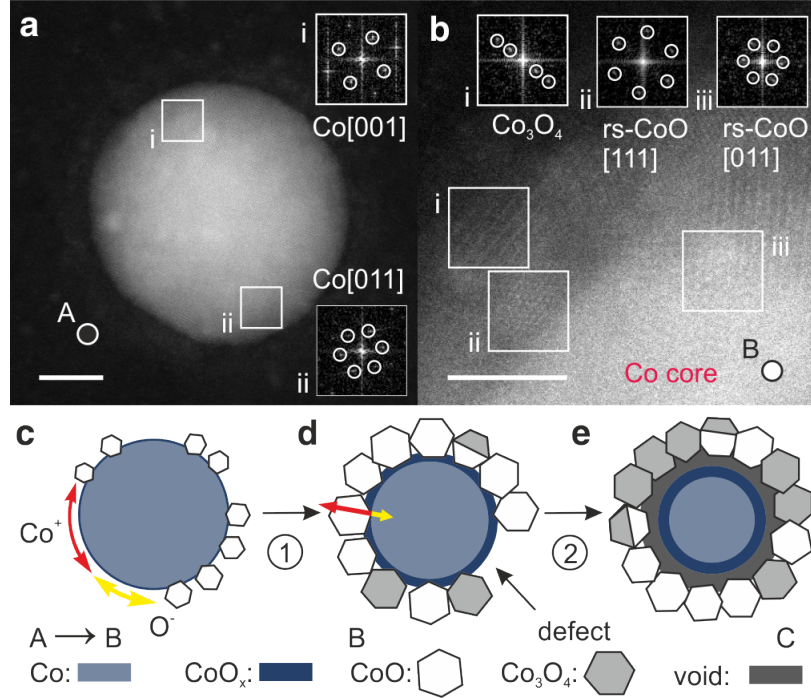


Figure 4: Atomic structure and atomistic oxidation model. (a) HAADF-STEM micrograph of a pure metallic nanoparticle (state A); insets (i) and (ii) show fast Fourier transforms (FFTs) and the deduced zone axes of the areas with the same labels marked by white squares (scale bar is 5 nm). (b) Enlarged image with atomic level resolution of a nanoparticle in state B; the insets (i-iii) show FFTs of the areas with the same labels marked by white squares revealing one Co_3O_4 , (i), and two CoO crystallites, (ii) and (iii), with different orientations (scale bar is 2 nm). Notice the preferred orientation between CoO and Co_3O_4 crystallites in region "i" and "ii", where the $\{110\}$ -planes of CoO and $\{110\}$ -planes of Co_3O_4 are parallel, but without a specific in-plane orientation of the crystal axes. (c-e) Model of the oxidation process showing the onset of the different oxidation states, A, B, and C.

the metallic Co cores, the CoO, and the Co₃O₄ oxide crystallites. In particular, we find no specific orientation of the CoO crystallites relative to the lattice of the metallic Co core grains, suggesting the nucleation of oxide crystallites with a random orientation relative to the metallic Co core.

To further study the correlation between the magnetic properties and composition of the oxide shell, we perform temperature-dependent *in situ* XPEEM experiments on nanoparticles in different oxidation states. Fig. 5(a) shows the XA spectra (black line) of the pure nanoparticles in the initial state A. The corresponding XPEEM image and the magnetic contrast map are shown in Figs. 5(d,g), respectively. As already shown above (Fig. 2), oxidation to state B, Fig. 5(b), results in a reduction of magnetic contrast in a large number of nanoparticles, Fig. 5(e). Cooling the sample to 114 K leads to a recovery of magnetic contrast in most of the nanoparticles. The vast majority of the nanoparticles exhibits the same magnetic contrast (black or white) upon oxidation and cooling as in the pristine, metallic state, e.g., particles "3" and "4" in Fig. 5(h) and (g). Increasing the amount of Co₃O₄ by further oxidation to state C results in a further loss of magnetic contrast at room temperature, Fig. 5(f), and almost no recovery of contrast at 114 K, Fig. 5(i), and down to 58 K (not shown).

Discussion

Oxidation and impact of the substrate

The present investigation demonstrates that pure Co nanoparticles oxidize in a two-step process with an immediate CoO formation and subsequent conversion to Co₃O₄, very similar to what is found for Co thin films or in bulk.²⁷ Our data show that these oxidation steps occur at room temperature, at very low O₂ partial pressure, and at very low oxygen doses, comparable to the oxidation of ultrathin Co films under ultrahigh vacuum conditions and as expected given the reactivity of 3d transition metals and the high number of low-coordinated

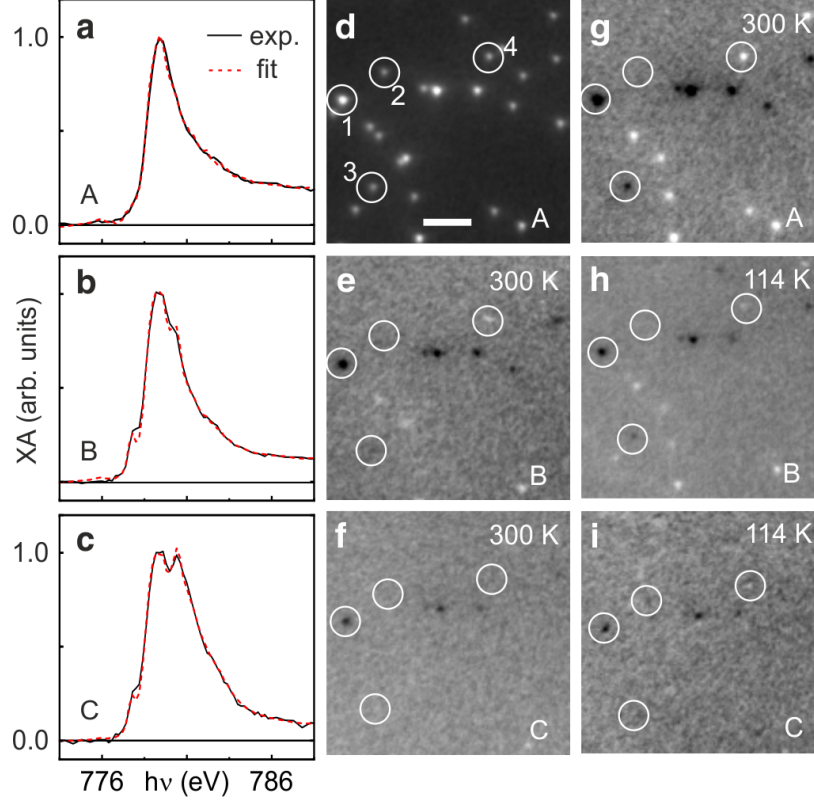


Figure 5: Temperature dependent magnetic state of pure and oxidised nanoparticles. (a-c) XA spectra of Co nanoparticles at states A, B, and C (black lines). (d,g) Co XPEEM elemental map and magnetic contrast of the nanoparticles at 300 K in state A. (e,h) Magnetic contrast maps of the nanoparticles upon oxidation to state B at 300 K and at 114 K and (f,i) in state C at 300 K and at 114 K. The scale bar in (d) is $1\ \mu\text{m}$.

surface atoms. Based on this finding, we attribute the much lower reactivity of Co nanoparticles towards oxidation found in earlier reports,^{2,18,21,24,26,35–37} requiring often considerably elevated temperatures and (near) atmospheric oxygen pressure for the transformation of metallic cobalt into an oxide phase, to the partial or full passivation of the nanoparticle surface with uncontrolled pre-oxidation or chemical agents such as oleic acid used as capping ligands which block the access of molecular oxygen to the surface of the nanoparticle. Hence, to exploit the full chemical reactivity of pure metallic Co nanoparticles, the preparation of bare, unpassivated and/or ligand-free surfaces is critical. For example, thermal decomposition is employed often to remove undesired oxide shells from the particle surface, motivated by the thermal instability of the 3d metal oxides. However, earlier *in situ* experiments revealed that such an approach for Co nanoparticles, even under additional reductive exposure to near ambient pressure of molecular hydrogen, does not fully remove the oxide shell, which was ascribed to the possible formation of a stable nanophase of wurtzite CoO.²¹ A more promising approach was demonstrated based on exposure to a hydrogen plasma, which can be preceded by an oxygen plasma exposure if organic shells need to be removed.^{24,25} In order to avoid here any ambiguities in the chemical nature of the particles entering interrogations with oxygen, metallic ligand-free cobalt nanoparticles were deposited under UHV-conditions, free of contaminants, and directly entered into the oxidation experiments.

We may further compare the thickness of the observed oxide shells with the thickness of comparable oxide layers in thin films.²⁷ Upon exposure to a few Langmuir of molecular oxygen, thin films form typically oxide layers with a thickness in the order of 1–2 nm.⁵³ In contrast, the present Co nanoparticles form a 4 nm thick CoO shell upon exposure to 1 L molecular oxygen on Si/SiO_x, see Figs. 2 and 3. Such thick oxide shell in a comparable chemical state may indicate a higher reactivity when compared to thin films due to the larger surface-to-volume ratio. However, assuming that each oxygen molecule hitting the nanoparticle surface is chemisorbed and contributes to the formation of the oxide shell, one finds that a nominal exposure of 6 L molecular oxygen to form a 4 nm CoO dominated shell

is required, see Supplementary Information. This strongly indicates that the substrate plays a major role in the oxidation of supported nanoparticles via surface diffusion of adsorbed oxygen, similar to spillover effects known from other chemical surface reactions.⁵⁴ For SiO_x , we estimate an oxygen diffusion length of $1\text{ }\mu\text{m}$, such that diffusion of oxygen physisorbed on the substrate will provide nearly 4000 times more oxygen than that directly adsorbed on the surface of the Co nanoparticles, see Supplementary Information. Further evidence for the role of the substrate comes from the observation that we need approximately ten times higher oxygen exposures to achieve oxidation states B or C on the carbon-coated Si_3N_4 -membranes when compared to the Si-wafers. Additional evidence for the role of the substrate can be adduced from previous *in situ* oxidation studies under ultrahigh vacuum conditions. For instance, in well separated Co nanoparticles deposited onto a clean, but chemically reactive Ni film, an oxygen dose approximately two orders of magnitude higher than in the present work was required to reach an oxidation of the Co nanoparticles similar to the present state C.³⁸ In another example, *in situ* oxidation of a dense array of nanoparticles on a chemically inert Si-substrates²⁴ required a dosage of molecular oxygen for oxidation three orders of magnitude higher compared to the present work, while *ex situ* experiments showed that a much higher amount of oxygen is required for the oxidation of dense nanoparticle arrays than for isolated nanoparticles.¹⁹ The latter findings can be explained by the fact that most of the substrate surface is covered with nanoparticles, such that oxygen diffusion through the substrate is strongly hindered.

Growth kinetics and structure of the oxide shell

In most previous investigations, a uniform, closed oxide shell with a thickness that grows with oxygen exposure is assumed and discussed in terms of the metal oxidation theory of Cabrera and Mott.⁴⁹ However, our data show that in the early stages of oxidation (state B) the oxide shell is not uniform. Instead, the oxide shell consists of randomly oriented CoO grains with sizes matching well the thickness of the oxide shell. In addition, as seen in the middle column

of Fig. 3, the shells can exhibit large defects. Moreover, the oxide shell thickness is practically the same in states B and C, although significant oxygen uptake and chemical reactions take place. These findings strongly suggest that the initial oxide shell formation occurs through independent nucleation and growth of CoO crystallites, rather through a uniform and closed oxide shell with a thickness that increases with the oxygen dosage. The extended defects also indicate that the probability for the formation/nucleation of oxide crystallites is not uniform at the nanoparticle surface, as expected from the varying surface atomic coordination and additional possible surface modifications induced by structural defects in the pristine metallic nanoparticles. Also the sizeable lattice mismatch between fcc Co and CoO is expected to prevent a uniform and/or epitaxial oxide shell growth and might promote the growth of small crystallites. Such a growth mode explains also the immediate formation of CoO in the first oxidation phase, Fig. 2(h), since oxygen and metal ions can freely diffuse over the surface of both the metallic nanoparticle and the growing oxide crystallites, as illustrated in Fig. 4(c). This efficient material transport stops when the growing CoO crystals merge to form a closed CoO shell as in state B. At this stage, the metallic core is largely passivated, and subsequent chemical reactions occur mostly as conversion of CoO to Co_3O_4 via ion diffusion through the oxide shell, which is much slower, Fig. 4(d). The onset of the nanoscale Kirkendall effect in state C confirms that the conversion to Co_3O_4 is dominated by Co ion diffusion through the oxide layer, which might be driven by the electric field-induced ion diffusion mechanism through the oxide shell as proposed for the low temperature oxidation of thin films by Cabrera and Mott.^{10,18,49} The random orientation of oxide crystals observed in this work is not compatible with the formation of a uniform fcc oxygen lattice, in which the local Co ion concentration determines the nature of the oxide, CoO or Co_3O_4 , respectively, as speculated earlier.²¹ Our data show that the conversion is a process linked to the individual oxide grains, perhaps dependent on their orientation and the resulting surface facets exposed, see Fig. 4(b), rather than a gradual, uniform process across the entire oxide shell surface. As a result, the oxide shell possesses a complex structure with phase pure CoO or Co_3O_4 and mixed phase

oxide crystallites as shown in Fig. 4(e). Finally, we note that exposure to a higher oxygen pressure is expected to lead to an increased number of nucleation sites and therefore, to a larger number of growing CoO crystallites which will coalesce at a smaller size, resulting in a somewhat thinner oxide shell. Indeed, previous work shows that similar Co nanoparticles exhibit a thinner oxide shell upon ambient air exposure.⁴⁰ The evolution of the oxidation state of cobalt, as well as of the morphology of the particles can have pronounced effects in catalytic reactions, up to defining both catalyst activity and selectivity in reactions that are structure sensitive and/or where the oxidation state of cobalt dictates performance, like in Fischer-Tropsch synthesis,⁵⁵ or dehydrogenation reactions⁵⁶ or combustion of hydrocarbons.⁵⁷

Impact of oxidation on the magnetism of Co nanoparticles

As shown in Fig. 5, oxidation to state B leads to a loss of magnetic contrast in a large portion of the nanoparticles at room temperature. Since the oxide shells of the individual nanoparticles develop with similar structure and thickness and a number of nanoparticles in this chemical state still exhibit magnetic contrast, we conclude that the loss of magnetic contrast is not due to screening of the signal of the ferromagnetic metal core by the growing oxide shell and the limited XPEEM probing depth, see Methods. Further evidence for this can be concluded from the XA spectra, which reveal that in state B, about 30 % of the signal originates from the metallic core, see Fig. 2(h). Hence, the loss of magnetic contrast could be either due to the onset superparamagnetic fluctuations or due to the occurrence of disordered spins in the probed volume of the nanoparticles. The experiments show that the magnetic contrast nearly recovers when cooling the samples to 114 K with the sign (i.e. dark or bright) being the same at low temperature as in the initial (metallic) state. Hence, the data exclude the onset of superparamagnetic fluctuations due to oxidation, which would lead to a random magnetic contrast at low temperature, and indicate instead a magnetically blocked ferromagnetic core. Support for this interpretation comes from earlier ensemble measurements, which suggested that oxidation leads even to the enhancement of magnetic

energy barriers in the ferromagnetic cores of Co nanoparticles.^{2,25,35} This scenario would further imply that the main contribution to the magnetic energy barrier of the metallic Co nanoparticles resides in the inner core of the particle and that the surface does not dominate the magnetism of nanoparticles, as frequently assumed in the literature.⁴⁰

The loss of magnetic contrast at room temperature could be assigned to the onset of oxygen-induced magnetic disorder at the oxide-shell-metal-core interface as postulated in earlier works.^{2,35} Such disorder could be related with oxygen ion diffusion into the metallic Co and a related perturbation of the local exchange interaction. The recovery of magnetic contrast in our data shows that such disorder can be partially overcome at lower temperatures. Taking advantage of the x-ray magnetic linear dichroism (XMLD) effect at the Co L_3 edge we have further addressed possible antiferromagnetic order in the oxide shell (see Methods and Fig. S3). The data reveal no sign of antiferromagnetic order in the oxide shell at 114 K although the small CoO crystallites in the oxide shell of oxidized Co nanoparticles have been found to order below $T = 235$ K, which is slightly below the corresponding Néel temperature of CoO bulk.³⁶ We assign the absence of an XMLD effect at 114 K either to a lack of uniform alignment of the antiferromagnetic spin systems as suggested by the randomly oriented CoO grains across the shell or to a possible SPM state of the CoO oxide crystals due to their small size. Further oxidation to state C eventually results in a loss of magnetic contrast in nearly all nanoparticles at room temperature. At 114 K a few nanoparticles still exhibit weak magnetic contrast with the same sign as before oxidation, see circles in Fig. 5. No further changes are observed down to 58 K. The weaker magnetic contrast when compared to state B at low temperature can be assigned to the reduced volume of the ferromagnetic core and the respectively smaller metallic Co signal when compared to state B, see Fig. 3. Also the physical separation of the metallic core and the oxide shell due to the Kirkendall effect might play a role in the attenuation of the metallic core signal.

Finally, we argue that the complex evolution of the structure of the oxide shell needs to be fully taken into account when discussing the magnetic properties of oxidized Co nanoparti-

cles. In particular, we propose that in state B the random orientation of the CoO crystals and the absence of a uniform antiferromagnetic spin order in the oxide shell, in addition to the possible spin disorder underneath the CoO crystals due to oxygen diffusion into the metallic Co, is responsible for the reported reduced exchange bias of about 1 T in comparison to the theoretically expected 5–6 T. In state C, the physical and magnetic decoupling between the ferromagnetic core and the oxide shell due to the Kirkendall effect may explain the reduction of the exchange bias fields at higher oxidation states.² Further, a superparamagnetic contribution to the magnetisation curves of oxidized Co nanoparticles was found which had been assigned to small metallic Co clusters in the interface region between the metallic core and the oxide shell.² Such clusters could be related either with metallic Co filaments that connect the metallic core with the oxide shell upon the onset of the Kirkendall-effect and/or with CoO crystals that are converted partially to Co₃O₄.¹⁰ Several reports have predicted a ferromagnetic layer at the interface between CoO and Co₃O₄.^{58,59} Our data show that, in state C, mixed phase CoO-Co₃O₄-crystals exist and therefore, such ferromagnetic interface layers could be present. Due to their small size they are likely in a superparamagnetic state.

Conclusions

In conclusion, we have demonstrated that pure Co nanoparticles have a chemical reactivity with molecular oxygen which is comparable to that of clean *in situ* prepared films and bulk surfaces at room temperature under ultrahigh vacuum conditions. Hence, their actual reactivity is orders of magnitude higher when compared to previous studies on Co nanoparticles, possibly further enhanced via oxygen diffusion over the substrate surface. We identify a two-step oxidation mechanism whereby a rapid CoO shell formation is followed by a slower conversion to Co₃O₄, i.e., longer oxygen exposures results in only small increases in the oxide shell thickness. The lattice mismatch between metallic Co and CoO prevents the formation of a homogeneous oxide shell. Instead, CoO crystals nucleate and grow independently until

they merge and form a closed layer. The large surface area emerging in the first growth mode promotes oxygen adsorption and Co ion diffusion and results in the very rapid formation of the CoO shell. In the second phase, outwards Co ion diffusion dominates the oxidation kinetics, while inward oxygen diffusion might lead to the formation of a layer with disordered spins in the metallic core. This layer and the random orientation of the CoO crystals relative to each other and to the metal core is likely responsible for the limited exchange bias observed in other reports. Further oxidation results in the nanoscale Kirkendall effect, which effectively decouples the oxide shell from the metallic core, explaining the reported reduction of the exchange bias effect upon advanced oxidation. Partial oxidation of the CoO crystals may lead to small ferromagnetic inclusions that could give rise to superparamagnetic inclusions reported in the literature. Finally, our data demonstrate the absence of a pressure gap in the oxidation of Co nanoparticles and provide a benchmark for the development of theoretical models for the chemical reactivity in catalysis and magnetism in metal oxidation at the nanoscale.

Methods

Sample preparation

Mass-filtered Co nanoparticles with sizes ranging from 8 to 20 nm are obtained from the gas phase by means of an UHV-compatible arc cluster ion source (ACIS) attached to a sample preparation chamber with a base pressure $< 2 \times 10^{-10}$ mbar.⁴³ A gold mesh in the particle beam is used to control the particle density on the substrate. The particle density is set to about one nanoparticle per μm^2 in order to achieve well isolated nanoparticles resolvable with the spatial resolution of about 50 nm of the XPEEM instrument. The low particle density on the surface is chosen to prevent chemical and magnetic inter-particle interactions and to enable the detection of the signal of individual nanoparticles in XPEEM. The nanoparticles are deposited under soft landing conditions to avoid particle fragmentation

or damage to the substrate.⁶⁰ Prior to the particle deposition, the substrates are annealed at 200 °C for 1–2 hours in UHV to remove ambient air adsorbates from the surface. For the HAADF-STEM measurements, the Co particles are deposited onto transmission electron microscopy compatible Si₃N₄-membranes with a thickness of 10 nm, which are additionally covered with conductive amorphous carbon films with a thickness of 2–3 nm to facilitate XPEEM measurements on these substrates. Gold (platinum) markers are fabricated on the Si-substrates (Si₃N₄-membranes) prior to the experiments using electron beam lithography (electron-beam induced deposition in a focussed ion beam instrument) in order to identify the same particles for comparison between different measurement techniques.

In situ XPEEM characterisation and data processing

After the particle deposition, the samples are transferred under UHV from the deposition system to the XPEEM characterisation chamber with a base pressure of 2×10^{-10} mbar. To oxidize the nanoparticles we introduce molecular oxygen (99.999% pure) into the XPEEM chamber through a leak valve at partial pressures ranging from 2×10^{-8} mbar to 2×10^{-6} mbar. The nominal dosages, $1 \text{ L} = 1.33 \times 10^{-6} \text{ Torr} \cdot \text{s}$, are estimated from the pressure reading in the XPEEM chamber. XA spectra and magnetic contrast images are acquired before and after each dosage to determine the change in chemical and magnetic states. XPEEM characterisation is carried out at the Surface/Interface: Microscopy (SIM) beamline at the Swiss Light Source (SLS).⁶¹ XPEEM is a spectromicroscopy technique capable of providing spatially resolved spectroscopic data. In XPEEM, the local intensity of secondary electrons emitted from a surface near region (3–5 nm) of the sample excited by tunable, monochromatic x-ray light (proportional to the x-ray absorption) is measured to provide local maps of the XA of the sample with a lateral spatial resolution on the order of 50 nm.⁴⁶ The high voltage applied between the sample and the microscope objective lens used to accelerate the excited photo-electrons towards the imaging lenses is set to 15 kV for the samples using Si-substrates and to 10 kV for the Si₃N₄-samples in order to minimise eventual discharges that would lead

to damage to the membrane. To obtain XA spectra, a sequence of images is taken at increasing photon energy, in the present case limited to the Co L_3 edge (770–790 eV); for better signal to noise ratio, the individual spectra of more than fifteen particles are averaged in our analysis. To identify the Co nanoparticles on the sample, we acquire separate images at the photon energy tuned to the L_3 edge of the metallic Co (779 eV) and a pre-edge energy (770 eV); pixelwise division of the two images give an elemental contrast image of the sample, where the Co nanoparticles appear as small dots with bright contrast in a grey background where no Co is present, see Fig. 1(e). To obtain magnetic information, we use the XMCD effect corresponding to the difference in absorption for left and right circularly polarised light.^{50,51} The magnetic contrast of an individual nanoparticle is given by the orientation of its magnetisation (\mathbf{m}) relative to the x-ray propagation vector (\mathbf{k}) according to $\mathbf{m} \cdot \mathbf{k}$, see schematic in Fig. 1(a). Magnetic contrast maps are obtained by pixelwise division of images acquired with right and left circularly polarised light (I^-/I^+) with the photon energy set to the metallic Co L_3 edge (779 eV) to give a direct measurement of the direction of the net magnetic moment on the sample; they are converted to XMCD maps by using the relation $\text{XMCD} = (1 - I^-/I^+)/(1 + I^-/I^+)$. The magnetic contrast maps are acquired using integration times of 10 s for each light polarisation; for better signal-to-noise ratio, 20 such images are acquired and averaged, resulting in a total experimental data acquisition time of $\tau = 400$ s. The magnetic relaxation time of the nanoparticles is given by an Arrhenius-type law $\tau_r = \tau_0 \exp(E_m/k_B T)$ with $\tau_0 = f_0^{-1}$ with f_0 being the attempt frequency $f_0 = 1.9 \times 10^9 \text{ s}^{-1}$, T the temperature, k_B the Boltzmann constant, and E_m is the magnetic energy barrier. The latter is determined by the magnetic anisotropy energy (MAE) of the nanoparticles, which describes the preferred magnetisation axis and the energy required to reorient or reverse \mathbf{m} within the nanoparticle. Possible antiferromagnetic order in the oxide shell is investigated by employing the XMLD effect at the Co L_3 edge.

XA spectra analysis

XA spectra were analyzed using spectral composition analysis⁶² based on fitting a linear combination of reference spectra for metallic Co,⁶³ CoO,⁶⁴ wustite-CoO,²¹ and Co₃O₄ to the experimental data,⁶⁵ see Fig. S1.

Structural characterisation

Atomic resolution HAADF-STEM characterisation was carried out using FEI Titan³ microscopes, equipped with Cs probe correctors and operated at 300 kV, at EMAT at the University of Antwerp, Belgium. The beam current was set to 50 pA with a STEM pixel dwell time of 1–5 μ s. Additional electron energy loss spectra (EELS) acquired in STEM revealed an oxide shell composition similar to the XA spectra analysis. The spectra were acquired at a dispersion of 0.25 eV per channel on a Gatan 977 spectrometer, with the monochromator of the microscope excited at 0.70. In addition, EELS maps were acquired using a beam current of 90–130 pA with an exposure time of 110 ms per pixel; to check for possible sample damage, two consecutive measurements on a number of particles were performed (with a smaller scanning step size for the second scan). These measurements revealed a sizeable reduction under the extended electron beam exposure in the EELS mode, see Fig. S4. No such effects were observed in HAADF-STEM imaging due to the much lower electron beam intensities and exposure times. These observations suggest that combining HAADF-STEM imaging with chemical analysis through *in situ* XA spectroscopy provides a least destructive tool for investigating oxide shells of the present Co nanoparticles. We note that besides spherical nanoparticles, we find also a small proportion of elongated nanoparticles typically composed of two or more merged spherical nanoparticles. While the shape plays an important role for the magnetic properties due to the shape anisotropy, we find no indication for a different chemical reactivity with oxygen (we also observe no size-dependent chemical behaviour in the investigated particle size range). Scanning electron microscopy was used to determine nanoparticle shapes and to distinguish individual nanoparticles from clusters of nanoparticles

for the magnetic study on the Si/SiO_x-wafers.

Acknowledgement

This work is funded by Swiss National Foundation (SNF) (Grants. No 200021_160186 and 2002_153540), and the Swiss Nanoscience Institut (SNI) (Grant No. SNI P1502). S.V. acknowledges support from the European Union’s Horizon 2020 research and innovation program under grant agreement no. 810310, which corresponds to the J. Heyrovsky Chair project (“ERA Chair at J. Heyrovský Institute of Physical Chemistry AS CR – The institutional approach towards ERA”). The funders had no role in the preparation of the article. Part of this work was performed at the Surface/Interface: Microscopy (SIM) beamline of the Swiss Light Source (SLS), Paul Scherrer Institut, Villigen, Switzerland. We kindly acknowledge Anja Weber and Elisabeth Müller from PSI for their help in fabricating the sample markers. A.B. and J.Ve. received funding from the European Union’s Horizon 2020 Research Infrastructure - Integrating Activities for Advanced Communities under grant agreement No 823717 – ESTEEM3.

Author contributions

A.K. and C.A.F.V. conceived the project. J.Vi., T.M.S., D.M.B, A.K., and C.A.F.V. performed the XPEEM experiments. J.Vi. and T.M.S. analysed and interpreted the XPEEM data with support from A.K., C.A.F.V., and F.N. The HAADF-STEM measurements were performed by A.B., G.L., and J.Ve. The HAADF-STEM data were analysed by A.K., J.Vi., G.L., and A.B. The manuscript was written by A.K., C.A.F.V., S.V., J.Vi., and T.M.S. with input from all authors.

Supporting Information Available

The following files are available free of charge:

- A Supplementary Information file containing Figs. S1 – S4 and a section describing the estimate of the oxide shell thickness due to oxygen adsorption and diffusion across the sample.
- A movie sequence of Fig. 2(i-o) showing the evolution of the magnetic contrast as a function of oxygen dosage, over a larger sample area of 20 μm .

References

1. Fu, L.; Liu, Z.; Liu, Y.; Han, B.; Hu, P.; Cao, L.; Zhu, D. Beaded Cobalt Oxide Nanoparticles along Carbon Nanotubes: Towards More Highly Integrated Electronic Devices. *Adv. Mater.* **2005**, *17*, 217.
2. Tracy, J. B.; Weiss, D. N.; Dinega, D. P.; Bawendi, M. G. Exchange biasing and magnetic properties of partially and fully oxidized colloidal cobalt nanoparticles. *Phys. Rev. B* **2005**, *72*, 064404.
3. Lewis, L. N. Chemical catalysis by colloids and clusters. *Chem. Rev.* **1993**, *93*, 2693.
4. Yi, D. K.; Lee, S. S.; Ying, J. Y. Synthesis and Applications of Magnetic Nanocomposite Catalysts. *Chemistry of Materials* **2006**, *18*, 2459.
5. Michalek, F.; Lagunas, A.; Jimenoa, C.; Pericàs, M. A. Synthesis of functional cobalt nanoparticles for catalytic applications. Use in asymmetric transfer hydrogenation of ketones. *J. Mater. Chem.* **2008**, *18*, 4692.
6. Wang, J.; Gao, D.; Wang, G.; Miao, S.; Wu, H.; Liab, J.; Bao, X. Cobalt nanoparticles encapsulated in nitrogen-doped carbon as a bifunctional catalyst for water electrolysis. *J. Mater. Chem. A* **2014**, *2*, 20067.

7. Rivas-Murias, B.; Asensio, J. M.; Mille, N.; Rodríguez-González, B.; Fazzini, P.-F.; Carrey, J.; Chaudret, B.; Salgueiriño, V. Magnetically Induced CO₂ Methanation Using Exchange-Coupled Spinel Ferrites in Cuboctahedron-Shaped Nanocrystals. *Angew. Chem. Int. Ed.* **2020**, *59*, 15537.
8. Farkas, B.; Santos-Carballal, D.; Cadi-Essadek, A.; de Leeuw, N. H. A DFT + U study of the oxidation of cobalt nanoparticles: Implications for biomedical applications. *Materials* **2019**, *7*, 100381.
9. Qiu, C.; Odarchenko, Y.; Meng, Q.; Cong, P.; Schoen, M. A. W.; Kleibert, A.; Forrester, T.; Beale, A. M. Direct observation of the evolving metal–support interaction of individual cobalt nanoparticles at the titania and silica interface. *Chem. Sci.* **2020**, *11*, 13060.
10. Yin, Y.; Rioux, R. M.; Erdonmez, C. K.; Hughes, S.; Somorjai, G. A.; Alivisatos, A. P. Formation of Hollow Nanocrystals Through the Nanoscale Kirkendall Effect. *Science* **2004**, *304*, 711.
11. Ibáñez, M.; Fan, J.; Li, W.; Cadavid, D.; Nafria, R.; Carrete, A.; Cabot, A. Means and Limits of Control of the Shell Parameters in Hollow Nanoparticles Obtained by the Kirkendall Effect. *Chem. Mater.* **2011**, *23*, 3095.
12. Lee, Y.; Jo, M. R.; Song, K.; Nam, K. M.; Park, J. T.; Kang, Y.-M. Hollow Sn-SnO₂ Nanocrystal/Graphite Composites and Their Lithium Storage Properties. *ACS Appl. Mater. Interfaces* **2012**, *4*, 3459.
13. Meiklejohn, W. H.; Bean, C. P. New Magnetic Anisotropy. *Phys. Rev.* **1957**, *105*, 904.
14. Skumryev, V.; Stoyanov, S.; Zhang, Y.; Hadjipanayis, G.; Givord, D.; Nogués, J. Beating the superparamagnetic limit with exchange bias. *Nature* **2003**, *423*, 850.

15. Nogués, J.; Skumryev, V.; Sort, J.; Stoyanov, S.; Givord, D. Shell-Driven Magnetic Stability in Core-Shell Nanoparticles. *Phys. Rev. Lett.* **2006**, *97*, 157203.
16. Gruyters, M.; Riegel, D. Optimized exchange biasing by controlled in situ oxidation. *J. Appl. Phys.* **2000**, *88*, 6610.
17. Stamps, R. L. Mechanisms for exchange bias. *J. Phys. D: Appl. Phys.* **2000**, *33*, R247.
18. Ha, D.-H.; Moreau, L. M.; Honrao, S.; Hennig, R. G.; Robinson, R. D. The Oxidation of Cobalt Nanoparticles into Kirkendall-Hollowed CoO and Co₃O₄: The Diffusion Mechanisms and Atomic Structural Transformations. *J. Phys. Chem. C* **2013**, *117*, 14303.
19. Yang, Z.; Lisiecki, I.; Walls, M.; ; Pileni, M.-P. Nanocrystallinity and the Ordering of Nanoparticles in Two-Dimensional Superlattices: Controlled Formation of Either Core/Shell (Co/CoO) or Hollow CoO Nanocrystals. *ACS Nano* **2013**, *7*, 1342.
20. Yang, Z.; Yang, N.; Yang, J.; Bergström, J.; Pileni, M.-P. Control of the Oxygen and Cobalt Atoms Diffusion through Co Nanoparticles Differing by Their Crystalline Structure and Size. *Adv. Funct. Mater.* **2015**, *25*, 891.
21. Papaefthimiou, V.; Dintzer, T.; Dupuis, V.; Tamion, A.; Tournus, F.; Hillion, A.; Teschner, D.; Hävecker, M.; Knop-Gericke, A.; Schlögl, R.; Zafeirotas, S. Nontrivial Redox Behavior of Nanosized Cobalt: New Insights from Ambient Pressure X-ray Photoelectron and Absorption Spectroscopies. *ACS Nano* **2011**, *5*, 2182.
22. S, B.; Pohl, M.-M.; Meiwes-Broer, K.-H.; Barke, I. Morphological impact on the reaction kinetics of size-selected cobalt oxide nanoparticles. *J. Chem. Phys.* **2015**, *143*, 114301.
23. Bartling, S.; Yin, C.; Barke, I.; Oldenburg, K.; Hartmann, H.; von Oeynhausen, V.; Pohl, M.-M.; Houben, K.; Tyo, E. C.; Seifert, S.; Lievens, P.; Meiwes-Broer, K.-H.; S.Vajda, Pronounced Size Dependence in Structure and Morphology of Gas-Phase Pro-

- duced, Partially Oxidized Cobalt Nanoparticles under Catalytic Reaction Conditions. *ACS Nano* **2015**, *9*, 5984.
24. Boyen, H.-G.; Kästle, G.; Zürn, K.; Herzog, T.; Weigl, F.; Ziemann, P.; Mayer, O.; Jerome, C.; Möller, M.; Spatz, J.; Garnier, M.; Oelhafen, P. A Micellar Route to Ordered Arrays of Magnetic Nanoparticles: From Size-Selected Pure Cobalt Dots to Cobalt–Cobalt Oxide Core–Shell Systems. *Adv. Funct. Mater.* **2003**, *13*, 359.
25. Wiedwald, U.; Fauth, K.; Hessler, M.; Boyen, H.-G.; Weigl, F.; Hilgendorff, M.; Giersig, M.; Schütz, G.; Ziemann, P.; Farle, M. From Colloidal Co/CoO Core/Shell Nanoparticles to Arrays of Metallic Nanomagnets: Surface Modification and Magnetic Properties. *ChemPhysChem* **2005**, *6*, 2522.
26. Zhang, D.; Jin, C.; Li, Z. Y.; Zhang, Z.; Li, J. Oxidation behavior of cobalt nanoparticles studied by in situ environment transmission electron microscopy. *Sci. Bull.* **2017**, *62*, 775.
27. Clemens, W.; Vescovo, E.; Kachel, T.; Carbone, C.; Eberhardt, W. Spin-resolved photoemission study of the reaction of O₂ with fcc Co(100). *Phys. Rev. B* **1992**, *46*, 4198.
28. Picone, A.; Riva, M.; Brambilla, A.; Giannotti, D.; Ivashko, O.; Bussetti, G.; Finazzi, M.; Ciccacci, F.; Duo, L. Atomic Scale Insights into the Early Stages of Metal Oxidation: A Scanning Tunneling Microscopy and Spectroscopy Study of Cobalt Oxidation. *J. Phys. Chem. C* **2016**, *120*, 5233.
29. Franchy, R. Growth of thin, crystalline oxide, nitride, and oxynitride films on metal and metal alloy surfaces. *Surf. Sci. Rep.* **2000**, *38*, 195.
30. Robinson, A. L. Heterogeneous Catalysis: Can Surface Science Contribute? *Science* **1974**, *185*, 4153.

31. Freund, H.-J.; Kuhlenbeck, H.; Libuda, J.; Rupprechter, G.; Bäumer, M.; Hamann, H. Bridging the pressure and materials gaps between catalysis and surface science: clean and modified oxide surfaces. *Topics in Catalysis* **2001**, *15*, 201.
32. Imbihl, R.; Behm, R. J.; Schlögl, R. Bridging the pressure and material gap in heterogeneous catalysis. *Phys. Chem. Chem. Phys.* **2007**, *9*, 3459.
33. Bron, M.; Teschner, D.; Knop-Gericke, A.; Steinhauer, B.; Scheybal, A.; Hävecker, M.; Wang, D.; Födisch, R.; Hönicke, D.; Wootsch, A.; Schlögl, R.; Claus, P. Bridging the pressure and materials gap: in-depth characterisation and reaction studies of silver-catalysed acrolein hydrogenation. *Journal of Catalysis* **2005**, *234*, 37.
34. Gangopadhyay, S.; Hadjipanayis, G. C.; Sorensen, C. M.; Klabunde, K. J. Exchange anisotropy in oxide passivated Co fine particles. *J. Appl. Phys.* **1993**, *73*, 6964.
35. Peng, D. L.; Sumiyama, K.; Hihara, T.; Yamamuro, S.; Konno, T. J. Magnetic properties of monodispersed Co/CoO clusters. *Phys. Rev. B* **2000**, *61*, 3103.
36. Inderhees, S. E.; Borchers, J. A.; Green, K. S.; Kim, M. S.; Sun, K.; Strycker, G. L.; Aronson, M. C. Manipulating the Magnetic Structure of Co Core/CoO Shell Nanoparticles: Implications for Controlling the Exchange Bias. *Phys. Rev. Lett.* **2008**, *101*, 117202.
37. Rinaldi-Montes, N.; Gorria, P.; Martínez-Blanco, D.; Amghouz, Z.; Fuertes, A. B.; Fernández, J. R.; Barquín, L. F.; Olivi, L.; Aquilanti, G.; Blanco, J. A. Disentangling magnetic core/shell morphologies in Co-based nanoparticles. *J. Mater. Chem. C* **2016**, *4*, 2302.
38. Bansmann, J.; Getzlaff, M.; Kleibert, A.; Bulut, F.; Gebhardt, R.; Meiwes-Broer, K.-H. Mass-filtered cobalt clusters in contact with epitaxially ordered metal surfaces. *Appl. Phys. A* **2006**, *82*, 73.

39. Jia, S.; Hsia, C.-H.; Son, D. H. In Situ Study of Room-Temperature Oxidation Kinetics of Colloidal Co Nanocrystals Investigated by Faraday Rotation Measurement. *J. Phys. Chem. C* **2011**, *115*, 92.
40. Kleibert, A.; Balan, A.; Yanes, R.; Derlet, P. M.; Vaz, C. A. F.; Timm, M.; Rodríguez, A. F.; Béché, A.; Verbeeck, J.; Dhaka, R. S.; Radovic, M.; Nowak, U.; Nolting, F. Direct observation of enhanced magnetism in individual size- and shape-selected transition metal nanoparticles. *Phys. Rev. B* **2017**, *95*, 195404.
41. Vaz, C. A. F.; Kleibert, A.; Kazzi, M. E. In *21st CENTURY NANOSCIENCE – A HANDBOOK*; Sattler, K. D., Ed.; Taylor & Francis (CRC Press), 2020; Chapter 17.
42. Getzlaff, M.; Kleibert, A.; Methling, R.; Bansmann, J.; Meiwes-Broer, K.-H. Mass-filtered ferromagnetic alloy clusters on surfaces. *Surface Science* **2004**, *566–568*, 332.
43. Kleibert, A.; Passig, J.; Meiwes-Broer, K.-H.; Getzlaff, M.; Bansmann, J. Structure and magnetic moments of mass-filtered deposited nanoparticles. *J. Appl. Phys.* **2007**, *101*, 114318.
44. Rodríguez, A. F.; Nolting, F.; J. Bansmann, A. K.; Heyderman, L. J. X-ray imaging and spectroscopy of individual cobalt nanoparticles using photoemission electron microscopy. *Journal of Magnetism and Magnetic Materials* **2007**, *316*, 426.
45. Rodríguez, A. F.; Kleibert, A.; Bansmann, J.; Voitkans, A.; Heyderman, L. J.; Nolting, F. Size-dependent spin structures in iron nanoparticles. *Phys. Rev. Lett.* **2010**, *104*, 127201.
46. Guyader, L. L.; Kleibert, A.; Rodríguez, A. F.; Moussaoui, S. E.; Balan, A.; Buzzi, M.; Raabe, J.; Nolting, F. Studying nanomagnets and magnetic heterostructures with X-ray PEEM at the Swiss Light Source. *J. Electron Spectrosc. Relat. Phenom.* **2012**, *185*, 371.
47. Fauth, K.; Ballentine, G. E.; Praetorius, C.; Kleibert, A.; Wilken, N.; Voitkans, A.;

- Meiwes-Broer, K.-H. Magnetic properties of Fe nanoclusters on Cu (111) studied with X-ray magnetic circular dichroism. *Phys. Status Solidi B* **2010**, *247*, 1170.
48. Vaz, C. A. F.; Balan, A.; Nolting, F.; Kleibert, A. In situ magnetic and electronic investigation of the early stage oxidation of Fe nanoparticles using X-ray photo-emission electron microscopy. *Phys. Chem. Chem. Phys.* **2014**, *16*, 26624.
49. Cabrera, N.; Mott, N. F. Theory of the oxidation of metals. *Rep. Prog. Phys.* **1949**, *12*, 163.
50. Stöhr, J. Exploring the microscopic origin of magnetic anisotropies with X-ray magnetic circular dichroism (XMCD) spectroscopy. *J. Magn. Magn. Mater.* **1999**, *200*, 470.
51. Stöhr, J.; Anders, S. X-ray spectro-microscopy of complex materials and surfaces. *IBM J. Res. Develop.* **2000**, *44*, 535.
52. Balan, A.; Derlet, P. M.; Rodríguez, A. F.; Bansmann, J.; Yanes, R.; Nowak, U.; Kleibert, A.; Nolting, F. Direct Observation of Magnetic Metastability in Individual Iron Nanoparticles. *Phys. Rev. Lett.* **2014**, *112*, 107201.
53. Klingenberg, B.; Grellner, F.; Borgmann, D.; Wedler, G. Low-energy electron diffraction and X-ray photoelectron spectroscopy on the oxidation of cobalt (1120). *Surf. Sci.* **1997**, *383*, 13.
54. Karim, W.; Spreafico, C.; Kleibert, A.; Gobrecht, J.; VandeVondele, J.; Ekinici, Y.; van Bokhoven, J. A. Catalyst support effects on hydrogen spillover. *Nature* **2017**, *541*, 68.
55. Fischer, N.; van Steen, E.; Claeys, M. Structure sensitivity of the Fischer–Tropsch activity and selectivity on alumina supported cobalt catalysts. *Journal of Catalysis* **2013**, *299*, 67.

56. Koirala, R.; Safonova, O. V.; Pratsinis, S. E.; Baiker, A. Effect of cobalt loading on structure and catalytic behavior of $\text{CoO}_x/\text{SiO}_2$ in CO_2 -assisted dehydrogenation of ethane. *Applied Catalysis A, General* **2018**, *552*, 77.
57. Wang, H.; Chen, C.; Zhang, Y.; Peng, L.; Ma, S.; Yang, T.; Guo, H.; Zhang, Z.; Su, D. S.; Zhang, J. *In situ* oxidation of carbon-encapsulated cobalt nanocapsules creates highly active cobalt oxide catalysts for hydrocarbon combustion. *Nature Communications* **2015**, *6*, 7181.
58. Fontaina-Troitano, N.; Liebana-Vinas, S.; Rodriguez-Gonzalez, B.; Li, Z.-A.; Spasova, M.; Farle, M.; Salgueirino, V. Room-Temperature Ferromagnetism in Antiferromagnetic Cobalt Oxide Nanooctahedra. *Nano Lett.* **2014**, *14*, 640.
59. Chen, X.; van Gog, H.; van Huis, M. A. Transformation of Co_3O_4 nanoparticles to CoO monitored by in situ TEM and predicted ferromagnetism at the $\text{Co}_3\text{O}_4/\text{CoO}$ interface from first principles. *J. Mater. Chem. C* **2021**, *9*, 5662.
60. Popok, V. N.; Barke, I.; Campbell, E. E. B.; Meiwes-Broer, K.-H. Cluster–surface interaction: From soft landing to implantation. *Surface Science Reports* **2011**, *66*, 347.
61. Flechsig, U.; Nolting, F.; Rodríguez, A. F.; Krempaský, J.; Quitmann, C.; Schmidt, T.; Spielmann, S.; Zimoch, D. Performance measurements at the SLS SIM beamline. *AIP Conf. Proc.* **2010**, *1234*, 319.
62. Karim, W.; Kleibert, A.; Hartfelder, U.; Balan, A.; Gobrecht, J.; van Bokhoven, J. A.; Ekinici, Y. Size-dependent redox behavior of iron observed by in-situ single nanoparticle spectro-microscopy on well-defined model systems. *Sci. Rep.* **2016**, *6*, 18818.
63. Kleibert, A.; Meiwes-Broer, K.-H.; Bansmann, J. Size-dependent magnetic spin and orbital moments of Fe nanoparticles deposited onto Co/W (110). *Phys. Rev. B* **2009**, *79*, 125423.

64. Regan, T. J.; Ohldag, H.; Stamm, C.; Nolting, F.; Lüning, J.; Stöhr, J.; White, R. L. Chemical effects at metal/oxide interfaces studied by x-ray-absorption spectroscopy. *Phys. Rev. B* **2001**, *64*, 214422.
65. Bergmann, A.; Martinez-Moreno, E.; Teschner, D.; Chernev, P.; Gliech, M.; de Araújo, J. F.; Reier, T.; Dau, H.; Strasser, P. Reversible amorphization and the catalytically active state of crystalline Co_3O_4 during oxygen evolution. *Nat. Commun.* **2015**, *6*, 8625.