Linear Modeling of the Glass Transition Temperature of the system SiO₂-CaO-Na₂O

Patrick dos Anjos¹*
Lucas de Almeira Quaresma*
Marcelo Lucas Pereira Machado*

*Federal Institute of Espírito Santo (IFES), Vitória, ES, Brazil

Abstract

This work aimed to mathematically model the glass transition temperature (T_g), one of the most important parameters regarding the behavior of slag, being responsible for the sudden change in thermomechanical properties of non-crystalline materials, by the chemical composition of the SiO_2 -CaO-Na₂O system, widely applicable in the production of glasses and constituent of iron, magnesium and aluminum metallurgy slags. The SciGlass database was used to provide data for mathematical modeling through the Python programming language, using the method of least squares. A new equation was established, called *P Model*, and it presented a lower mean absolute error and lower standard deviation of absolute errors in relation to 3 equations in the literature. The raised equation provides significant results in the mathematical modeling of T_g by the chemical system SiO_2 -CaO-Na₂O, being valid for the limits of the data used in the mathematical modeling.

Keywords: Glass Transition Temperature, Database, Mathematical Modeling, Statistical Evaluation.

DOI: https://arxiv.org/abs/2211.11533 arXiv®

1 Introduction

The glass transition temperature known as T_g is one of the most important parameters in relation to the crystalline behavior of slag, and can be directly obtained through the analysis of the differential exploratory calorimetry (DSC) technique [1]. T_g denotes an abrupt change in the thermomechanical properties of non-crystalline materials, marking the temperature, or its range, where below it the atoms of a supercooled liquid are temporarily frozen, without crystallizing, after cooling [2]. Viscosity is directly related to T_g [3] (Equation 1).

$$\log_{10}(\eta(T, \eta_{\infty}, T_{g}, m)) = \log_{10}(\eta_{\infty}) + T_{g}/T (12 - \log_{10}(\eta_{\infty})) \exp((T_{g}/T - 1) (m/(12 - \log_{10}(\eta_{\infty})) - 1)$$
 (1)

The parameter m known as the fragility index is a relationship between viscosity (η) and T_g , as shown in Equation 2.

¹ E-mail: patrick.dosanjos@outlook.com

$$m = \partial \log_{10}(\eta(T))/\partial(T_g/T) \mid T = T_g$$
 (2)

The SiO₂-CaO-Na₂O system is one of the chemical systems used for application in glasses and containers [4], being components in blast furnace slag [5], in the slag of the Pidgeon process [6] and in the red mud resulting from the leaching of aluminum ores [7]. Slag applied in continuous casting may have glass phases [8], and the study of the glass transition temperature can be valuable.

Mathematical modeling of T_g can be done through chemical composition [9-10]. Mills et al. (2016) described a linear equation that correlates T_g in the SiO₂-CaO-Al₂O₃-Na₂O-K₂O-MgO-CaF₂-MnO-FeO system, modeled through T_g data from 23 different mould slags, resulting in Equation 3, which has uncertainty of approximately 20K (X = mole fraction).

$$T_{g}(K) = 906 - 330.5XSiO_{2} + 190XCaO + 440XAl_{2}O_{3} - 440X(Na_{2}O + K_{2}O) - 11XMgO + 154XCaF_{2} - 309XMnO - 1391XFeO$$
(3)

Andersson (1992) established the glass transition temperature in a SiO_2 -Na₂O-CaO-P₂O₅-Al₂O₃-B₂O₃ system, which can be calculated by Equation 4 or Equation 5. These equations were modeled through 16 different glasses, providing mean absolute error of 6.7°C for Equation 4 and 8.2°C for Equation 5 (% = mass percentage).

$$T_g(^{\circ}C) = 44.3136 + 6.27159\%SiO_2 + 6.90715\%CaO + 6.32101\%P_2O_5 + 6.75157\%Al_2O_3$$
 (4)

$$T_g(^{\circ}C) = 674.483 - 6.26843\% Na_2O$$
 (5)

This work aimed to perform a linear modeling of the glass transition temperature correlating the chemical composition of the SiO₂-CaO-Na₂O system to provide an equation with low error and low variability.

2 Materials and Methods

For the mathematical modeling of the SiO_2 -CaO-Na₂O system relating to T_g , the SciGlass database was used [3]. For data modeling, the treatments of missing values (NaN) were performed, the removal of a sub-database where the sum of the elements SiO_2 , CaO and Na₂O completed 100%, with subsequent conversion of the chemical species to molar fraction and the conversion of T_g values to Kelvin. The resulting sub-database had the SiO_2 -CaO-Na₂O system relating each chemical system to its T_g . The sub-database parameters are seen in Table 1.

Table 1. Parameters of the sub-database used for linear modeling.

| Parameters | SiO ₂ (%mol) | CaO (%mol) | Na ₂ O (%mol) | T _g (K) |
|--------------------|-------------------------|---------------|-----------------------------|--------------------|
| Data | 512 | 512 | 512 | 512 |
| Mean | 68.13 | 12.23 | 19.64 | 835.40 |
| Standard Deviation | 14.34 | 17.64 | 13.90 | 160.78 |
| Minimum | 31.25 | 0.00 | 0.00 | 579.15 |
| Maximum | 100.00 | 61.00 | 68.75 | 1495.15 |

Isolated chemical species do not have a linear mathematical relationship with T_g, as can be seen in Figure 1. Hence a simple linear regression does not have statistical representation.

Mathematical modeling was performed using the Python programming language by applying the least squares method, by minimizing and generalizing Equation 6 (*a*=linear coefficient, *b*=angular coefficients vector, *y*=dependent variable, *x*=independent variables vector).

$$f(a, b) = \Sigma(y - a - bx)^2$$
(6)

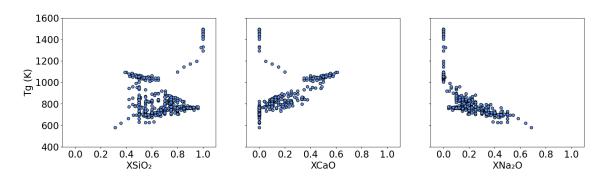


Figure 1. Relationship between SiO_2 , CaO and Na_2O separately with T_g (X = molar fraction).

The evaluations of the new model were performed by statistical methods of mean absolute error (MAE) (Equation 7) and the standard deviation of the absolute error between the results of the new model in relation to the sub-database (STD) (Equation 8).

MAE (K) =
$$1/N \Sigma \mid ypredicted - ytrue \mid$$
 (7)

$$STD(K) = \sqrt{Var(|ypredicted - ytrue|)}$$
(8)

For mathematical consistency, the evaluation was also performed in the model described by Mills et al. (2016) and by both models developed by Andersson (1992).

3 Results and discussion

The result of the multiple regression resulted in the values of a=776.62, b=180.77, c=332.45 and d=513.22 and the linear equation resulting from the mathematical modeling is denoted by Equation 9, named $P \mod (X = \text{molar fraction})$.

$$T_g(K) = 776.62 + 180.77XSiO_2 + 332.45XCaO - 513.22XNa_2O$$
(9)

The statistical parameters of mean absolute error (MAE) and standard deviation of absolute error (STD) are seen in Table 2.

Table 2. MAE and STD statistical parameters of Equations 3, 4, 5 and 9.

| Models | Mills et al. (2016) (Equation 3) | Andersson (1992) (Equation 4) | Andersson (1992) (Equation 5) | P Model (Equation 9) |
|---------|-------------------------------------|----------------------------------|----------------------------------|-------------------------|
| MAE (K) | 219.49 | 62.72 | 67.68 | 58.40 |
| STD (K) | 126.59 | 88.09 | 88.67 | 86.35 |

P Model exhibited MAE of 58.40K and STD of 86.35K and the best model among those mentioned was Equation 4 of Andersson (1992) with MAE of 62.72K and STD of 88.09K.

Among the 4 models, the P Model was considered the model with the lowest error and lowest variability. The Andersson (1992) model with the lowest error and lowest variability was Equation 4, being modeled with 16 different glasses, whereas the P Model was built from 520 different chemical composition data of the SiO₂-CaO-Na₂O system relating the T_g. Therefore, the P Model has a greater statistical representation, since it used a greater amount of data.

With the results predicted in the 2 best models, the P model and Equation 4 described by Andersson (1992), a scatter plot of errors was generated in relation to the sub-database (Figure 2).

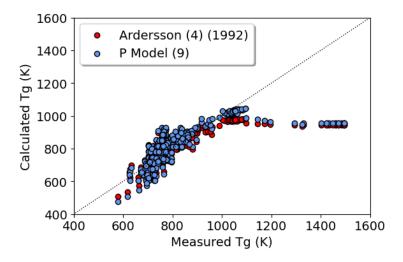


Figure 2. Scatter plot of errors between Equations 4 and 9 in relation to the sub-database.

The sensitivity of the system regarding the constants related to the chemical species remained the same, with the molar fraction of SiO₂ and CaO increasing T_g and Na₂O decreasing in the SiO₂-Na₂O-CaO-P₂O₅-Al₂O₃-B₂O₃ and SiO₂-CaO-Na₂O systems. The deviation values of the P Model are shown in Figure 3.

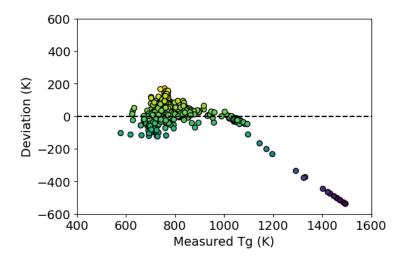


Figure 3. P Model deviation values.

By analysis, it can be seen that there is an increase in the deviation values when the $T_{\rm g}$ is greater than 1000K, which denotes that the $T_{\rm g}$ has more predictors than just the chemical composition.

4 Conclusion

Glass transition temperature (T_g) values were modeled using the SciGlass database, the predictor variables being the chemical composition of the SiO₂-CaO-Na₂O system. Using a linear modeling, the equation $T_g(K) = 776.62 + 180.77XSiO_2 + 332.45XCaO - 513.22XNa_2O$ called *P Model* was obtained relating the chemical composition of the system in molar fraction. The P Model was statistically evaluated and resulted in a mean absolute error (MAE) of 58.40K and standard deviation of absolute error (STD) of 86.35K and the best model in literature, the model of Andersson (1992) represented by Equation 4, resulted in a MAE of 62.72K and STD of 88.09K, demonstrating that the P Model has less error and less variability in the 4 equations described. With a sub-database composed of 520 different data P Model

was modeled, in contrast to the best model in the literature, Andersson (1992) represented by Equation 4, which was modeled with 16 different data, denoting that the P Model has a greater statistical representation analyzing the results, the values of $T_{\rm g} > 1000 {\rm K}$ have deviation values greater than the $T_{\rm g} < 1000 {\rm K}$, demonstrating a threshold of divergence in the P Model, indicating that above this threshold the $T_{\rm g}$ has more predictive elements than just the chemical composition.

References

- [1] Ding B, Wang H, Zhu X, He X, Tan Y, Liao Q. Prediction on crystallization behaviors of blast furnace slag in a phase change cooling process with corrected optical basicity. Fuel. 2018;223;360-365.
- [2] Cassar DR, Carvalho ACPLF, Zanotto ED. Predicting glass transition temperatures using neural networks. Acta Materialia. 2018;159;249-256.
- [3] Cassar DR. ViscNet: Neural network for predicting the fragility index and the temperature-dependency of viscosity. Acta Materialia. 2021;206;116602.
- [4] Bourhis, E. Glass: Mechanics and Technology. 2. ed. Wiley-VCH. 2014.
- [5] Sajid M, Bai C, Aamir M, You Z, Yan Z, Lv X. Understanding the Structure and Structural Effects on the Properties of Blast Furnace Slag (BFS). ISIJ International. 2019;59(7);1153-1166.
- [6] Wu L, Han F, Liu G. Comprehensive Utilization of Magnesium Slag by Pidgeon Process. SpringerBriefs in Materials, 2021.
- [7] Friedrich B, Kalisch M, Friedmann D, Degel R, Kauben F, Bohlke J. The Submerged Arc Furnace (SAF): State-of-the-Art Metal Recovery from Nonferrous Slags. Journal of Sustainable Metallurgy. 2018;4;77-94.
- [8] Alves LM, Voltz H, Carvalho CS, Nascimento AD, Vieira EA. Use of ornamental rock residues for mould flux development. REM. 2018;71(3);403-410.
- [9] Andersson O. H. Glass transition temperature of glasses in the SiO₂-Na₂O-CaO-P₂O₅-Al₂O₃-B₂O₃ system. Journal of Materials Science: Materials in Medicine. 1992;3;326-328.
- [10] Mills KC, Karagadde S, Lee PD, Yuan L, Shahbazian F. Calculation of Physical Properties for Use in Models of Continuous Casting Process-Part 1: Mould Slags. ISIJ International. 2016;56(2);264-273.