

Spin superfluidity

E. B. Sonin

*Racah Institute of Physics,
Hebrew University of Jerusalem,
Givat Ram, Jerusalem 9190401,
Israel*

(Dated: November 30, 2022)

The phenomenon of superfluidity (superconductivity) is a possibility of transport of mass (charge) on macroscopical distances without essential dissipation. In magnetically ordered media with easy-plane topology of the order parameter space the superfluid transport of spin is also possible despite the absence of the strict conservation law for spin. The article addresses three key issues in the theory of spin superfluidity: topology of the order parameter space, Landau criterion for superfluidity, and decay of superfluid currents via phase slip events, in which magnetic vortices cross current streamlines. Experiments on detection of spin superfluidity are also surveyed.

Keywords: coherent spin precession, Landau criterion, magnetic vortex, order parameter, phase slip, skyrmion, spin supercurrent, spin superfluidity, spin wave, topology

Key Points/Objective

- Spin superfluidity is the possibility to transport spin with essentially suppressed dissipation on long distances.
- Spin superfluidity is possible if the magnetic order parameter space has the topology of a circumference.
- The necessary topology is provided by easy-plane anisotropy in ferromagnets or by magnetic field in antiferromagnets.
- Metastability of spin superfluid current states is restricted by the Landau criterion.
- Decay of spin superfluid currents is realized via phase slips, in which magnetic vortices cross current streamlines.

CONTENTS

1. Introduction	1
2. Concept of superfluidity	2
3. Spin superfluidity in ferromagnets	5
4. Spin superfluidity in antiferromagnets	8
5. Superfluid spin transport without spin conservation law	10
6. Long-distance superfluid spin transport	11
7. Experiments on detection of spin superfluidity	12
8. Discussion and conclusions	13
References	14

1. INTRODUCTION

The phenomenon of superfluidity (superconductivity in the case of charged fluids) is known more than a hundred years. Its analog for spin (spin superfluidity) occupies minds of condensed matter physicists from 70s of the

last century. The term *superfluidity* is used in the literature to cover a broad range of phenomena in superfluid ^4He and ^3He , Bose-Einstein condensates of cold atoms, and solids. In this article superfluidity means only the possibility to transport a physical quantity (mass, charge, spin, ...) without dissipation (more accurately, with essentially suppressed dissipation). This corresponds to the original hundred-years old meaning of the term from the times of Kamerlingh Onnes and Kapitza.

The superfluidity is conditioned by the special topology of the order parameter space (vacuum manifold). Namely, this topology is that of a circumference in a plane. The angle of rotation around this circumference is the order parameter phase describing all degenerate ground states. In superfluids the phase is the phase of the macroscopic wave function. In magnetically ordered systems (ferro- and antiferromagnets) the necessary topology is provided by easy-plane magnetic anisotropy, and the phase is the angle of rotation around the axis (further the axis z) normal to the easy plane. Currents of mass (charge) or spin are proportional to phase gradients and are called supercurrents.

In early discussions of the spin supercurrent it was con-

sidered as a counterflow of superfluid currents of particles with different spins in superfluid ^3He (Vuorio, 1974), i.e., spin was transported by itinerant spin carriers. Later it was demonstrated that spin superfluidity is a universal phenomenon, which does not require mobile spin carriers and is possible in magnetic insulators (Sonin, 1978a, 1982). It can be described within the framework of the standard Landau–Lifshitz–Gilbert (LLG) theory. However, the publications conditioning spin superfluid transport by the presence of mobile carriers of spin continued to appear in the literature (Bunkov, 1995; Shi *et al.*, 2006). According to Shi *et al.* (2006), it is a critical flaw of spin-current definition if it predicts spin currents in insulators.

Strictly speaking the analogy of spin superfluidity with superfluids is complete only if there is invariance with respect to any rotation in the spin space around the axis z . Then according to Noether’s theorem the spin component along the axis z is conserved. But there is always some magnetic anisotropy, which breaks the rotational invariance. Correspondingly, there is no strict conservation law for spin, while in superfluids the gauge invariance is exact, and the conservation law of mass (charge) is also exact.

In the past there were arguments about whether superfluidity is possible in the absence of the conservation law. This dispute started at discussion of superfluidity of electron-hole pairs or excitons. The number of electron-hole pairs can vary due to interband transitions, and the degeneracy with respect to the phase of the pair condensate is lifted. Guseinov and Keldysh (1972) called this effect “fixation of phase”. They demonstrated that spatially *homogeneous* stationary current states are impossible, and concluded that there is no analogy with superfluidity. However, later it was demonstrated that phase fixation does not rule out the existence of weakly *inhomogeneous* stationary current states analogous to superfluid current states (Kulik and Shevchenko, 1976; Lozovik and Yudson, 1977; Sonin, 1977). This analysis was extended on spin superfluidity (Sonin, 1978a,b, 1982). In magnetism violation of the spin conservation law usually is rather weak because it is related with relativistically small (inversely proportional to the speed of light) processes of spin-orbit interaction. In fact, the LLG theory itself is based on the assumption of weak spin-orbit interaction (Landau and Lifshitz, 1980).

Above we discussed supercurrents generated in the equilibrium (ground state) of the magnetically ordered medium with easy plane topology. But in magnetically ordered system this topology is possible also in non-equilibrium coherent precession states, when spin pumping supports spin precession with fixed spin component along the magnetic field. Such non-equilibrium coherent precession states, which are called nowadays magnon BEC, were experimentally investigated in the B phase of superfluid ^3He and in yttrium-iron-garnet (YIG) films

(Bunkov, 1995; Demokritov *et al.*, 2006).

Spin superfluid transport is possible as long as the spin phase gradient does not exceeds the critical value determined by the Landau criterion. The Landau criterion checks stability of supercurrent states with respect to elementary excitations of all collective modes. The Landau criterion determines a threshold for the current state instability, but it tells nothing about how the instability develops. The decay of the supercurrent is possible only via phase slips. In a phase slip event a magnetic vortex crosses current streamlines decreasing the phase difference along streamlines. Below the critical value of supercurrent phase slips are suppressed by energetic barriers. The critical value of the supercurrent at which barriers vanish is of the same order as that estimated from the Landau criterion. This leads to a conclusion that the instability predicted by the Landau criterion is a precursor of the avalanche of phase slips not suppressed by any activation barrier.

The superfluid spin transport on macroscopical distances is possible only if the spin phase performs a large number of full 2π rotations along current streamlines (large winding number), and phase slips are suppressed by energetic barriers. On the other hand, small phase variations less than 2π are ubiquitous in magnetism. They emerge in any spin wave, any domain wall, or due to disorder. Their existence is confirmed by numerous experiments in the past. Spin currents generated by these small phase differences transport spin only on small distances and oscillate in space or time, or both. Their existence is not a manifestation of spin superfluidity.

In last decades the interest to spin superfluidity was revived (Bunkov and Volovik, 2013; Chen and MacDonald, 2017; Evers and Nowak, 2020; Iacocca *et al.*, 2017; Qaiumzadeh *et al.*, 2017; Sonin, 2010, 2017, 2019b; Sun *et al.*, 2016; Takei *et al.*, 2014; Takei and Tserkovnyak, 2014; Tserkovnyak and Kläui, 2017) in connection with the emergence of spintronics. The present article reviews the three essentials of the spin superfluidity concept: topology, Landau criterion, and phase slips. The article focuses on the qualitative analysis avoiding details of calculations, which can be found in original papers. After the theoretical analysis the experiments searching for spin superfluidity are shortly discussed.

2. CONCEPT OF SUPERFLUIDITY

Let us remind the concept of superfluidity for the transport of mass (charge). In superfluid hydrodynamics there are the Hamilton equations for the pair of the canonically conjugate variables “phase - particle density”:

$$\hbar \frac{d\varphi}{dt} = -\frac{\delta \mathcal{H}}{\delta n}, \quad \frac{dn}{dt} = \frac{\delta \mathcal{H}}{\hbar \delta \varphi}. \quad (1)$$

Here

$$\frac{\delta \mathcal{H}}{\delta n} = \frac{\partial \mathcal{H}}{\partial n} - \nabla \cdot \frac{\partial \mathcal{H}}{\partial \nabla n}, \quad \frac{\delta \mathcal{H}}{\delta \varphi} = \frac{\partial \mathcal{H}}{\partial \varphi} - \nabla \cdot \frac{\partial \mathcal{H}}{\partial \nabla \varphi} \quad (2)$$

are functional derivatives of the Hamiltonian

$$\mathcal{H} = \frac{\hbar^2 n}{2m} \nabla \varphi^2 + E_0(n), \quad (3)$$

φ is the phase of the wave function describing the Bose-Einstein condensate (BEC) in Bose liquids or the Cooper pair condensate in Fermi liquids, and $E_0(n)$ is the energy of the superfluid at rest, which depends only on the particle density n . Taking into account the gauge invariance [$U(1)$ symmetry] $\partial \mathcal{H} / \partial \varphi = 0$, the Hamilton equations are reduced to the equations of hydrodynamics for an ideal liquid:

$$m \frac{d\mathbf{v}}{dt} = -\nabla \mu, \quad (4)$$

$$\frac{dn}{dt} = -\nabla \cdot \mathbf{j}. \quad (5)$$

In these expressions

$$\mu = \frac{\partial E_0}{\partial n} + \frac{\hbar^2}{2m} \nabla \varphi^2 \quad (6)$$

is the chemical potential, and

$$\mathbf{j} = n\mathbf{v} = \frac{\partial \mathcal{H}}{\hbar \partial \nabla \varphi} \quad (7)$$

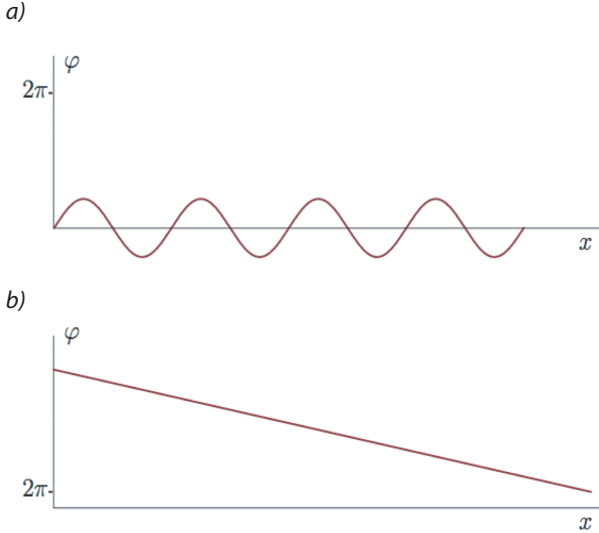


FIG. 1 Phase (in-plane rotation angle) variation in space at the presence of mass (spin) currents [From Sonin (2010)]. (a) Oscillating currents in a sound (spin) wave. (b) Stationary mass (spin) supercurrent.

is the particle current. We consider the zero-temperature limit, when the superfluid velocity coincides with the center-of-mass velocity of the whole liquid:

$$\mathbf{v} = \frac{\hbar}{m} \nabla \varphi. \quad (8)$$

The continuity equation Eq. (5) satisfies the conservation law of mass (charge), which follows from the gauge invariance.

A collective mode of the ideal liquid is a plane sound wave $\propto e^{i\mathbf{k}\cdot\mathbf{r} - i\omega t}$ with the wave vector \mathbf{k} , the frequency ω , and the linear spectrum $\omega = u_s k$. The sound velocity is

$$u_s = \sqrt{\frac{n}{m} \frac{\partial^2 E_0}{\partial n^2}}. \quad (9)$$

In the sound wave the phase varies in space, i.e., the wave is accompanied by mass currents [Fig. 1(a)]. An amplitude of the phase variation is small, and currents transport mass on distances of the order of the wavelength. A real superfluid transport on macroscopic distances is possible in current states, which are stationary solutions of the hydrodynamic equations with finite constant currents, i.e., with constant nonzero phase gradients. In the current state the phase rotates through a large number of full 2π -rotations along streamlines of the current [Fig. 1(b)]. These are supercurrents or persistent currents.

The crucial point of the superfluidity theory is why the supercurrent in Fig. 1(b) is a metastable state and does not decay a long time. The first explanation of the supercurrent metastability was the well known Landau criterion (Landau, 1941). According to this criterion, the current state is stable as far as *any quasiparticle* in a moving liquid has a positive energy in the laboratory frame and therefore its creation requires an energy input. Let us suppose that elementary quasiparticles of the liquid at rest have an energy $\varepsilon(\mathbf{p}) = \hbar\omega(\mathbf{k})$, where $\mathbf{p} = \hbar\mathbf{k}$ is the quasiparticle momentum. If the liquid moves with the velocity \mathbf{v} the quasiparticle energy in the laboratory frame becomes $\tilde{\varepsilon}(\mathbf{p}) = \varepsilon(\mathbf{p}) + \mathbf{p} \cdot \mathbf{v}$. This is the Doppler effect in the Galilean invariant fluid. The current state is stable if the energy $\tilde{\varepsilon}$ is never negative. This condition is the Landau criterion:

$$v < v_L = \min \frac{\varepsilon(\mathbf{p})}{p} = \min \frac{\omega(\mathbf{k})}{k}. \quad (10)$$

If quasiparticles are phonons (quanta of sound waves) the Landau critical velocity v_L is the sound velocity u_s . In superfluid ^4He the Landau critical velocity v_L is determined by the roton part of the spectrum. It is a few times less than the sound velocity.

The Landau criterion checks the stability with respect to elementary microscopic perturbations of the current

state, but does not provide an information how the instability would develop. The whole process of the supercurrent decay is connected with generation of macroscopic perturbations. These perturbations are quantum vortices. If the vortex axis (vortex line) coincides with the z axis, the phase gradient around the vortex line is given by

$$\mathbf{v}_v = \frac{\hbar}{m} \nabla \varphi_v = \frac{\kappa [\hat{z} \times \mathbf{r}]}{2\pi r^2}, \quad (11)$$

where \mathbf{r} is the position vector in the xy plane and $\kappa = h/m$ is the velocity circulation quantum.

Creation of the vortex requires some energy. The vortex energy per unit length (line tension) is determined mostly by the kinetic (gradient) energy in the area not very close to the vortex axis where the particle density does not differ essentially from its equilibrium value n_0 (the London region):

$$\varepsilon_v = n_0 \int d^2\mathbf{r} \frac{\hbar^2 (\nabla \varphi_v)^2}{2m} = \frac{\pi \hbar^2 n_0}{m} \ln \frac{r_m}{r_c}. \quad (12)$$

The upper cut-off r_m of the logarithm is determined by geometry. For the vortex shown in Fig. 2(a) it is the distance of the vortex line from a sample border. The lower cut-off r_c is the vortex-core radius. It determines the distance r at which the phase gradient is so high that the density n starts to decrease compared to the equilibrium density n_0 at large r . The energy $E_0(n)$ of the resting superfluid at small $n - n_0$ is determined by the fluid compressibility:

$$E_0(n) = E_0(n_0) + \frac{m(n_0 - n)^2 u_s^2}{2n_0}. \quad (13)$$

At the distance r_c from the vortex axis the energy $mn\nabla\varphi_v^2/2$ becomes of the order of the compressibility energy at $n_0 - n \sim n_0$. This happens when the velocity $v_v(r)$ induced by the vortex becomes of the order of the sound velocity u_s . This yields $r_c \sim \kappa/u_s$. Inside the core the density vanishes at the vortex axis eliminating the singularity in the kinetic energy. For the weakly non-ideal Bose-gas r_c is on the order of the coherence length.

Phase slips are impeded by energy barriers determined by topology of the order parameter space (vacuum manifold). The order parameter of a superfluid is a complex wave function $\psi = \psi_0 e^{i\varphi}$, where the modulus ψ_0 of the wave function is a positive constant determined by minimization of the energy and the phase φ is a degeneracy parameter. Any degenerate ground state in a closed annular channel (torus) with some constant phase φ maps on some point at the circumference $|\psi| = \psi_0$ in the complex plane ψ , while a current state with the phase change $2\pi N$ around the torus maps onto a path [Fig. 3(a)] winding around the circumference N times. The integer winding number N is a topological charge. The current can relax if it is possible to change the topological charge.

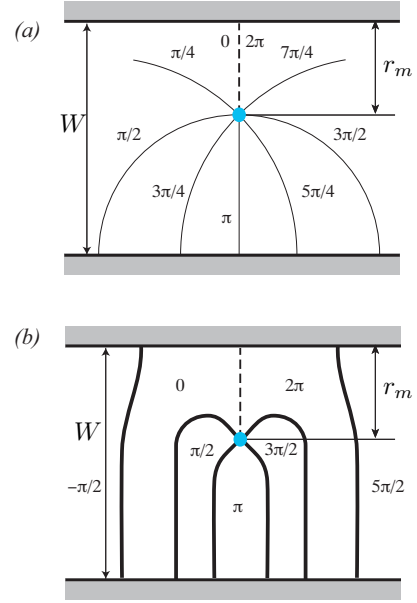


FIG. 2 Mass and magnetic vortices [From Sonin (2010)]. (a) Vortex in a superfluid or magnetic vortex in an easy-plane ferromagnet without in-plane anisotropy. (b) magnetic vortex at small average spin currents ($\langle \nabla \varphi \rangle \ll 1/l$) for four-fold in-plane symmetry. The vortex line is a confluence of four 90° domain walls (solid lines).

A change of the topological charge from N to $N - 1$ is possible, if a vortex generated at one border of a channel with a moving superfluid moves across current streamlines “cutting” the channel cross-section, and annihilates at another border as shown in Fig. 2(a). This is a phase slip. In the phase slip event the distance r_m of the vortex from a border varies from zero to the width W of the channel. The energy of the vortex in a moving superfluid is determined by a sum of the constant gradient $\nabla\varphi_0$, which determines the supercurrent, and the phase gradient $\nabla\varphi_v$ induced by the vortex. The vortex energy consists of the energy of the vortex in a resting fluid given by Eq. (12) and of the energy from the cross terms of the two gradient fields $\nabla\varphi_0$ and $\nabla\varphi_v$:

$$\tilde{\varepsilon}_v = \frac{\pi \hbar^2 n_0}{m} L \ln \frac{r_m}{r_c} - \frac{2\pi \hbar^2 n_0}{m} S \nabla \varphi_0, \quad (14)$$

where L is the length of the vortex line and S is the area of the cut, at which the phase jumps by 2π . For the 2D case shown in Fig. 2(a) (a straight vortex in a slab of thickness L normal to the picture plane) $S = Lr_m$. The vortex motion across the channel (growth of r_m) is impeded by the barrier determined by the maximum of the energy $\tilde{\varepsilon}_v$ as a function r_m . The height of the barrier is the vortex energy at $r_m = 1/2\nabla\varphi_0$:

$$\varepsilon_b \approx \frac{\pi \hbar^2 n}{m} L \ln \frac{2}{r_c \nabla \varphi_0}. \quad (15)$$

The barrier disappears at gradients $\nabla\varphi_0 \sim 1/r_c$, which

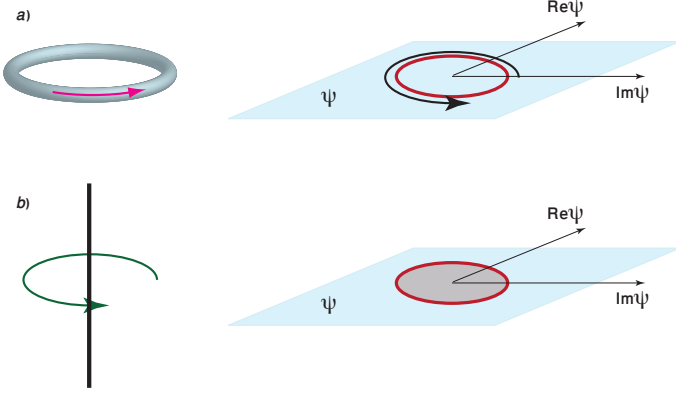


FIG. 3 Topology of the uniform mass current and the vortex states [From Sonin (2010)]. (a) The current state in a torus maps onto the circumference $|\psi| = \psi_0$ in the complex ψ -plane, where ψ_0 is the modulus of the equilibrium order parameter wave function in the uniform state. (b) The current state with a vortex maps onto the circle $|\psi| \leq \psi_0$.

are of the same order as the critical gradient determined from the Landau criterion. On the other hand, in the limit of small velocity $v \propto \nabla\varphi_0$ the barrier height grows and at very small velocity $v \sim \hbar/mW$ reaches the value

$$\varepsilon_m \approx \frac{\pi \hbar^2 n}{m} L \ln \frac{W}{r_c \nabla \varphi_0}. \quad (16)$$

Thus, in the thermodynamic (macroscopic) limit $W \rightarrow \infty$ the barrier height becomes infinite. Since the phase slip probability exponentially decreases on the barrier height (whether the barrier is overcome due to thermal fluctuations or via quantum tunneling) the life time of the current state in conventional superfluidity diverges when the velocity (phase gradient) decreases. This justifies calling superfluidity macroscopic quantum phenomenon.

In the 3D geometry the phase slip is realized with expansion of vortex rings. For the ring of radius R the vortex-length and the area of the cut are $L = 2\pi R$ and $S = \pi R^2$ respectively, and the barrier disappears at the same critical gradient $\sim 1/r_c$ as in the 2D case.

The state with the vortex in a moving superfluid maps on the full circle $|\psi| \leq \psi_0$ [Fig. 3(b)]. The area outside the vortex core maps on the circumference $|\psi| = \psi_0$, while the core maps on the interior of the circle. In a weakly interacting Bose-gas the structure of the core is determined by solution of the Gross—Pitaevskii equation (Pitaevskii and Stringari, 2003; Sonin, 2016). The details of the core structure are not important for the content of the present article.

For better understanding of the superfluidity phenomenon it is useful to consider a mechanical analogue of superfluid current (Sonin, 1982). Let us twist a long elastic rod so that a twisting angle at one end of the rod with respect to an opposite end reaches values many times 2π . Bending the rod into a ring and connecting the

ends rigidly, one obtains a ring with a circulating persistent angular-momentum flux (Fig. 4). The flux is proportional to the gradient of twisting angle, which plays the role of the phase gradient in the supercurrent. The deformed state of the ring is not the ground state of the ring, but it cannot relax to the ground state via any elastic process, because it is topologically stable. The only way to relieve the strain inside the rod is *plastic displacements*. This means that dislocations start to move across rod cross-sections. The role of dislocations in the twisted rod is similar to the role of vortices in the superfluid.

3. SPIN SUPERFLUIDITY IN FERROMAGNETS

For a ferromagnet with magnetization density \mathbf{M} the LLG equation is (Landau and Lifshitz, 1980)

$$\frac{\partial \mathbf{M}}{\partial t} = \gamma [\mathbf{H}_{eff} \times \mathbf{M}], \quad (17)$$

where γ is the gyromagnetic ratio between the magnetic and mechanical moment. The effective magnetic field is determined by the functional derivative of the Hamiltonian \mathcal{H} :

$$\mathbf{H}_{eff} = -\frac{\delta \mathcal{H}}{\delta \mathbf{M}} = -\frac{\partial \mathcal{H}}{\partial \mathbf{M}} + \nabla_i \frac{\partial \mathcal{H}}{\partial \nabla_i \mathbf{M}}. \quad (18)$$

According to the LLG equation, the absolute value M of the magnetization does not vary. The evolution of \mathbf{M} is a precession around the effective magnetic field \mathbf{H}_{eff} .

If spin-rotational invariance is broken and there is uniaxial crystal magnetic anisotropy the phenomenological Hamiltonian is

$$\mathcal{H} = \frac{A}{2} \nabla_i \mathbf{M} \cdot \nabla_i \mathbf{M} + \frac{GM_z^2}{2M^2} - \mathbf{H} \cdot \mathbf{M}. \quad (19)$$

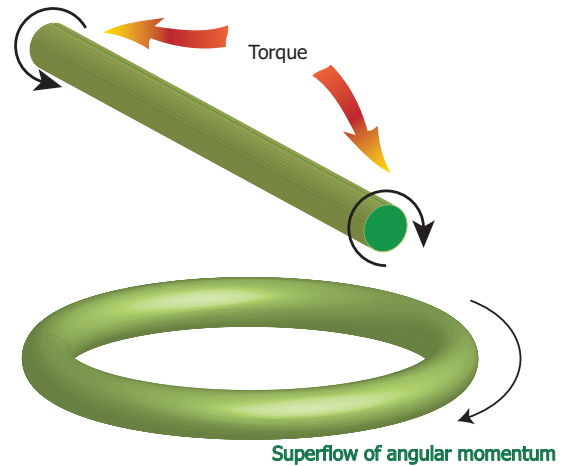


FIG. 4 Mechanical analogue of a persistent current: A twisted elastic rod bent into a closed ring. There is a persistent angular-momentum flux around the ring [From Sonin (2010)].

The parameter A is stiffness of the spin system determined by exchange interaction. If the anisotropy parameter G is positive, it is the “easy plane” anisotropy, which keeps the magnetization in the xy plane. If the external magnetic field \mathbf{H} is directed along the z axis, the z component of spin is conserved because of invariance with respect to rotations around the z axis. For the sake of simplicity we ignore the magnetostatic energy, which depends on sample shape.

Since the absolute value M of magnetization is fixed, the magnetization vector \mathbf{M} is fully determined by the z magnetization component M_z and the angle φ showing the direction of \mathbf{M} in the easy plane xy :

$$M_x = M_\perp \cos \varphi, \quad M_y = M_\perp \sin \varphi, \quad M_\perp = \sqrt{M^2 - M_z^2}. \quad (20)$$

In the new variables the Hamiltonian is

$$\mathcal{H} = \frac{AM_\perp^2(\nabla\varphi)^2}{2} + \frac{M_z^2}{2\chi} - HM_z. \quad (21)$$

Here we neglected gradients of M_z . The magnetic susceptibility $\chi = M^2/G$ along the z axis is determined by the easy-plane anisotropy parameter G . The LLG equation reduces to the Hamilton equations for a pair of canonically conjugate continuous variables “angle–moment”:

$$\frac{1}{\gamma} \frac{d\varphi}{dt} = -\frac{\delta\mathcal{H}}{\delta M_z} = -\frac{\partial\mathcal{H}}{\partial M_z}, \quad (22)$$

$$\frac{1}{\gamma} \frac{dM_z}{dt} = \frac{\delta\mathcal{H}}{\delta\varphi} = -\nabla \cdot \frac{\partial\mathcal{H}}{\partial\nabla\varphi}, \quad (23)$$

where functional derivatives are taken from the Hamiltonian Eq. (21). Using the expressions for functional derivatives the Hamilton equations are

$$\frac{1}{\gamma} \frac{d\varphi}{dt} = AM_z(\nabla\varphi)^2 - \frac{M_z - \chi H}{\chi}, \quad (24)$$

$$\frac{1}{\gamma} \frac{dM_z}{dt} + \nabla \cdot \mathbf{J}_s = 0, \quad (25)$$

where

$$\mathbf{J}_s = -\frac{\partial\mathcal{H}}{\partial\nabla\varphi} = -AM_\perp^2 \nabla\varphi \quad (26)$$

is the spin current. Although our equations are written for magnetization, but not for the spin density, \mathbf{J}_s is defined as a current of spin with the spin density M_z/γ .

There is an evident analogy of Eqs. (24) and (25) with the hydrodynamic equations (4) and (5) for the superfluid. This analogy of magnetodynamics with hydrodynamics was pointed out by Halperin and Hohenberg (1969) for spin waves in antiferromagnets. The analogy is also important for spin superfluidity.

There are linear solutions of Eqs. (24) and (25) describing the plane spin-wave mode $\propto e^{i\mathbf{k}\cdot\mathbf{r} - i\omega t}$ with the sound-like spectrum:

$$\omega = c_{sw}k, \quad (27)$$

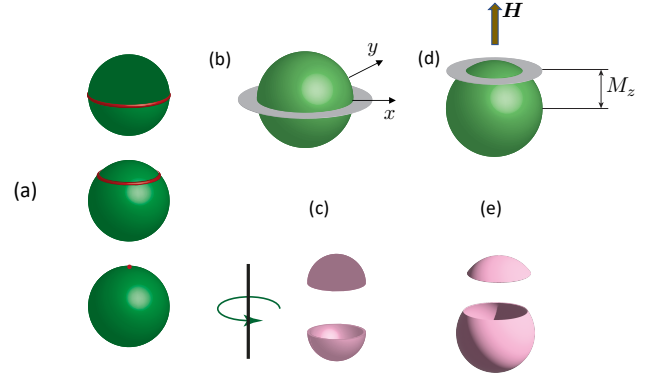


FIG. 5 Mapping of spin current states on the order parameter space of the ferromagnet [From Sonin (2020)]. (a) Spin current in an isotropic ferromagnet. The current state in torus maps on an equatorial circumference on the sphere of radius M (top). Continuous shift of mapping on the surface of the sphere (middle) reduces it to a point at the northern pole (bottom), which corresponds to the ground state without currents. (b) Spin current in an easy-plane ferromagnet at $M_z = 0$. The easy-plane anisotropy reduces the order parameter space to an equatorial circumference in the xy plane topologically equivalent to the order parameter space in superfluids. (c) Spin current state with a magnetic vortex in an easy-plane ferromagnet at $M_z = 0$. The states map on the surface of the upper or the lower hemisphere. (d) Spin current in an easy-plane ferromagnet at $M_z \neq 0$. Spin is confined in the plane parallel to the xy plane but shifted closer to the northern pole. A nonzero M_z appears either in the equilibrium due to a magnetic field parallel to the axis z , or due to spin pumping. (e) Spin current state with a magnetic vortex in an easy-plane ferromagnet at $M_z \neq 0$. The state maps on the surface of the upper or the lower parts of the sphere. Two options of mapping are not degenerate, and the phase slip with the magnetic vortex of a smaller energy (a smaller area of mapping) is more probable.

where

$$c_{sw} = \gamma M_\perp \sqrt{\frac{A}{\chi}} \quad (28)$$

is the spin-wave velocity in the ground state. The variation of the phase in the space is the same as in the sound mode propagating in the superfluid and shown in Fig. 1(a).

However, as well as the mass current in a sound wave, the small oscillating spin current in the spin wave does not lead to long-distance superfluid spin transport, which this article addresses. Spin superfluid transport on long distances is realized in current states with spin performing a large number of full 2π -rotations in the easy plane as shown in Fig. 1(b). In the current state with a constant gradient of the spin phase $\mathbf{K} = \nabla\varphi$, there is a constant magnetization component along the magnetic field (the axis z):

$$M_z = \frac{\chi H}{1 - \chi A K^2}. \quad (29)$$

Like in superfluids, the stability of current states is connected with topology of the order parameter space. In isotropic ferromagnets ($G = 0$) the order parameter space is a spherical surface of radius equal to the absolute value of the magnetization vector \mathbf{M} [Fig. 5(a)]. All points on this surface correspond to the same energy of the ground state. Suppose we created the spin current state with monotonously varying phase φ in a torus. This state maps on the equatorial circumference in the order parameter space. The topology allows to continuously shift the circumference and to reduce it to a point (the northern or the southern pole). During this process shown in Fig. 5(a) the path remains in the order parameter space all the time, and therefore, no energetic barrier resists to the transformation. Thus, in isotropic ferromagnets the metastable current state are not expected.

In a ferromagnet with easy-plane anisotropy ($G > 0$) the order parameter space reduces from the spherical surface to a circumference parallel to the xy plane. It is shown in Fig. 5(b) for zero magnetic field when the circumference is the equator. This order parameter space is topologically equivalent to that in superfluids. Now the transformation of the circumference to the point costs the anisotropy energy. This allows to expect metastable spin currents (supercurrents). The magnetic field along the anisotropy axis z shifts the easy plane either up [Fig. 5(d)] or down away from the equator.

In order to check the Landau criterion, one should know the spectrum of spin waves in the current state with the constant value of the spin phase gradient $\mathbf{K} = \nabla\varphi$ and with the longitudinal (along the magnetic field) magnetization given by Eq. (29). The spectrum is determined by solving the Hamilton equations Eqs. (24) and (25) linearized with respect to weak perturbations of the current state. We skip the standard algebra given elsewhere (Sonin, 2019b). Finally one obtains (Iacocca *et al.*, 2017; Sonin, 2019b) the spectrum of plane spin waves:

$$\omega + \mathbf{w} \cdot \mathbf{k} = \tilde{c}_{sw} k. \quad (30)$$

Here

$$\tilde{c}_{sw} = \sqrt{1 - \chi A K^2} c_{sw} \quad (31)$$

is the spin-wave velocity in the current state, and the spin wave velocity c_{sw} in the ground state is given by Eq. (28). The velocity

$$\mathbf{w} = 2\gamma M_z A \mathbf{K} \quad (32)$$

can be called Doppler velocity because its effect on the frequency is similar to the Doppler effect in a Galilean invariant fluid [see the text before Eq. (10)]. However, our system is not Galilean invariant (Iacocca *et al.*, 2017), and this is the pseudo Doppler effect. Because of it, the gradient K proportional to w is present also on the right-hand side of the dispersion relation Eq. (30).

We obtained the gapless Goldstone mode with the sound-like linear in \mathbf{k} spectrum. The current state becomes unstable when at \mathbf{k} antiparallel to \mathbf{w} the frequency ω becomes negative. This happens at the gradient K equal to the Landau critical gradient

$$K_L = \frac{M_\perp}{\sqrt{4M^2 - 3M_\perp^2}} \frac{1}{\sqrt{\chi A}}. \quad (33)$$

In the limit of weak magnetic fields when $M_z \ll M$ the Landau critical gradient is

$$K_L = \frac{1}{\sqrt{\chi A}} = \frac{\gamma M}{\chi c_{sw}}. \quad (34)$$

In this limit the pseudo-Doppler effect is not important, and at the Landau critical gradient K_L the spin-wave velocity \tilde{c}_{sw} in the current state vanishes.

In the opposite limit $M_z \rightarrow M$ ($M_\perp \rightarrow 0$) the Landau critical gradient,

$$K_L = \frac{M_\perp}{2M} \frac{1}{\sqrt{\chi A}}, \quad (35)$$

decreases, and the spin superfluidity becomes impossible at the phase transition to the easy-axis anisotropy ($M_\perp = 0$).

Deriving the sound-like spectrum of the spin wave we neglected in the Hamiltonian terms dependent on gradients ∇M_z . One should take into account these terms at the wavelength on the order of the coherence length

$$\xi_0 = \frac{M}{M_\perp} \sqrt{\chi A} = \frac{M^2}{M_\perp} \sqrt{\frac{A}{G}}. \quad (36)$$

The Landau critical gradient K_L is on the order of the inverse coherence length $1/\xi_0$.

The current states relax to the ground state via phase slips events, in which magnetic vortices cross spin current streamlines. At $M_z = 0$ the current state with a magnetic vortex maps on a surface of a hemisphere of radius M either above or below the equator (Nikiforov and Sonin, 1983) as shown in Fig. 5(c). The vortex core has a structure of a skyrmion. The skyrmion mapping on a hemisphere is called meron. At $M_z = 0$ two magnetic vortices with opposite spin polarizations have the same energy, and both can participate in phase slips. But at $M_z \neq 0$ the magnetic vortex with a smaller mapping area [Fig. 5(e)] has a smaller energy, and phase slips with its participation are more frequent. Since inside the core the gradients ∇M_z cannot be ignored, the core radius is on the order of the coherence length ξ_0 . Variation of the magnetization direction in space inside the skyrmion core is schematically shown in Fig. 6(a). One can find more details and numerical calculations of the structure of skyrmion cores of magnetic vortices in ferromagnets elsewhere (Sonin, 2018).

The estimation of barriers for phase slips in spin-superfluid ferromagnets is similar to that in the case of

mass superfluidity. The spin phase gradient in the current state with a straight magnetic vortex parallel to the axis z is

$$\nabla\varphi = \frac{[\hat{z} \times \mathbf{r}]}{r^2} + \mathbf{K}. \quad (37)$$

We consider a 2D problem of the straight magnetic vortex at the distance r_m from the plane border. The gradient \mathbf{K} is parallel to the border. Substituting the phase gradient field Eq. (37) into the kinetic energy and integrating the energy over the London region, where M_\perp is close to its value in the ground state, one obtains the energy of the magnetic vortex per unit length:

$$\tilde{\varepsilon}_v = \pi A M_\perp^2 \left(\ln \frac{r_m}{r_c} - 2K r_m \right). \quad (38)$$

The magnetic vortex energy has a maximum at $r_m = 1/2K$. The energy at the maximum is a barrier preventing phase slips:

$$\varepsilon_b = \pi A M_\perp^2 \ln \frac{1}{2K r_c}. \quad (39)$$

The barrier vanishes if the gradient K becomes of the order of the inverse vortex core radius r_c . This gradient is on the order of the Landau critical gradient K_L .

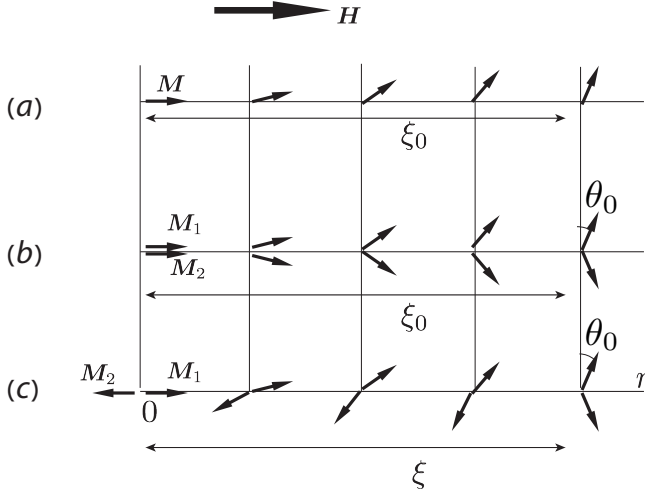


FIG. 6 Skyrmion cores of magnetic vortices. Variation of magnetization vectors (\mathbf{M} in a ferromagnet, \mathbf{M}_1 and \mathbf{M}_2 in an antiferromagnet) in the vortex core as a function of the distance r from the vortex axis is shown schematically. Horizontal directions of magnetizations correspond to the direction of the z axis in the spin space [From Sonin (2019a)]. (a) The magnetic vortex in the ferromagnet corresponding to the gapless Goldstone spin wave mode with the coherence length ξ_0 given by Eq. (36). (b) The magnetic vortex in the antiferromagnet corresponding to the Goldstone spin wave mode with the coherence length ξ_0 given by Eq. (59). (c) The magnetic vortex in the antiferromagnet corresponding to the gapped spin wave mode with the coherence length ξ given by Eq. (61).

Considering mapping of current states with nonzero magnetization M_z [Figs. 5(d) and (e)], we had in mind the equilibrium magnetization $M_z = \chi H$ produced by an external magnetic field \mathbf{H} . In the equilibrium there is no precession of the magnetization \mathbf{M} around the axis z . However, non-equilibrium states with non-equilibrium magnetization M_z , which makes the magnetization (spin) to coherently precess, are also possible. One can create them by pumping of magnons, which bring spin and energy into the system. Spin pumping compensates inevitable losses of spin due to spin relaxation. However, usually the process of spin relaxation is weak, and one may treat the coherent precession state as a quasi-equilibrium state at fixed M_z . The coherent precession state does not require the crystal easy-plane anisotropy for its existence. The easy-plane topology of Fig. 5(d) is provided dynamically, and, as a result, metastable spin current states are also possible.

Spin superfluidity in the quasi-equilibrium coherent precession state was investigated theoretically and experimentally in the B phase of superfluid ^3He (Bunkov, 1995). Later the coherent precession state in ^3He was rebranded as magnon BEC (Bunkov and Volovik, 2013). Coherent spin precession state (also under the name of magnon BEC) was revealed also in YIG magnetic films (Demokritov *et al.*, 2006). Spin superfluidity in YIG was discussed by Sun *et al.* (2016, 2017) and Sonin (2017). In the quasi-equilibrium coherent precession state demonstration of the long-distance superfluid spin transport is problematic (see Sec. 7). Semantic dilemma “coherent precession state, or magnon BEC” was discussed by Sonin (2010).

4. SPIN SUPERFLUIDITY IN ANTIFERROMAGNETS

The dynamics of a bipartite antiferromagnet can be described by the LLG equations for two spin sublattices coupled via exchange interaction (Keffer and Kittel, 1951):

$$\frac{d\mathbf{M}_i}{dt} = \gamma [\mathbf{H}_i \times \mathbf{M}_i]. \quad (40)$$

Here the subscript $i = 1, 2$ indicates to which sublattice the magnetization \mathbf{M}_i belongs, and

$$\mathbf{H}_i = -\frac{\delta\mathcal{H}}{\delta\mathbf{M}_i} = -\frac{\partial\mathcal{H}}{\partial\mathbf{M}_i} + \nabla_j \frac{\partial\mathcal{H}}{\partial\nabla_j\mathbf{M}_i} \quad (41)$$

is the effective field for the i th sublattice determined by the functional derivative of the Hamiltonian \mathcal{H} . For an isotropic antiferromagnet the Hamiltonian is

$$\mathcal{H} = \frac{\mathbf{M}_1 \cdot \mathbf{M}_2}{\chi} + \frac{A(\nabla_i\mathbf{M}_1 \cdot \nabla_i\mathbf{M}_1 + \nabla_i\mathbf{M}_2 \cdot \nabla_i\mathbf{M}_2)}{2} + A_{12}\nabla_j\mathbf{M}_1 \cdot \nabla_j\mathbf{M}_2 - \mathbf{H} \cdot \mathbf{m} \quad (42)$$

The total magnetization is

$$\mathbf{m} = \mathbf{M}_1 + \mathbf{M}_2, \quad (43)$$

and the staggered magnetization

$$\mathbf{L} = \mathbf{M}_1 - \mathbf{M}_2 \quad (44)$$

is normal to \mathbf{m} .

In the LLG theory absolute values of sublattice magnetizations \mathbf{M}_1 and \mathbf{M}_2 are equal to constant M , and in the uniform state without gradients the Hamiltonian is

$$\mathcal{H} = -\frac{M^2}{\chi} + \frac{m^2}{2\chi} - Hm_z. \quad (45)$$

Here and later on we assume that the magnetic field is applied along the z axis. The constant term M^2/χ can be ignored. In the ground state the total magnetization \mathbf{m} is directed along the magnetic field (the z axis), and the staggered magnetization \mathbf{L} is confined to the xy plane.

The order parameter for an antiferromagnet is the unit Néel vector $\mathbf{l} = \mathbf{L}/L$. The order parameter space for the isotropic antiferromagnet in the absence of the external magnetic field is a surface of a sphere, as for isotropic ferromagnets. But in ferromagnets the magnetic field produces an easy axis for the magnetization, while in the antiferromagnet the magnetic field produces the easy plane for the order parameter vector \mathbf{l} . Thus, the easy-plane topology necessary for the spin superfluidity in antiferromagnets does not require the crystal easy-plane anisotropy.

In the analogy to the ferromagnetic case, one can describe the vectors of sublattice magnetizations \mathbf{M}_i with the constant absolute value M by the two pairs of the conjugate variables (M_{iz}, φ_i) , which are determined by the two pairs of the Hamilton equations:

$$\frac{1}{\gamma} \frac{d\varphi_i}{dt} = -\frac{\delta\mathcal{H}}{\delta M_{iz}} = -\frac{\partial\mathcal{H}}{\partial M_{iz}}, \quad (46)$$

$$\frac{1}{\gamma} \frac{dM_{iz}}{dt} = \frac{\delta\mathcal{H}}{\delta\varphi_i} = \frac{\partial\mathcal{H}}{\partial\varphi_i} - \nabla \cdot \frac{\partial\mathcal{H}}{\partial\nabla\varphi_i}. \quad (47)$$

Let us consider the magnetization distribution with axial symmetry around the axis z :

$$\begin{aligned} M_{1z} = M_{2z} = \frac{m_z}{2} = M \sin \theta_0, \quad m_y = m_z = 0, \\ M_{1x} = -M_{2x} = \frac{L}{2} \cos \varphi, \\ M_{1y} = -M_{2y} = \frac{L}{2} \sin \varphi, \quad L_z = 0. \end{aligned} \quad (48)$$

Here $\varphi = \varphi_1 = \pi - \varphi_2$ is the angle of rotation of \mathbf{L} around the z axis, $L = \sqrt{4M^2 - m_z^2} = 2M \cos \theta_0$, and θ_0 is the canting angle. The Hamiltonian Eq. (42) for the axisymmetric case becomes the Hamiltonian

$$\mathcal{H} = \frac{m_z^2}{2\chi} - Hm_z + \frac{A_- L^2 (\nabla\varphi)^2}{4} \quad (49)$$

for the pair of the canonically conjugate variables (m_z, φ) . The Hamilton equations for this pair are

$$\frac{1}{\gamma} \frac{d\varphi}{dt} = \frac{A_- m_z (\nabla\varphi)^2}{2} - \frac{m_z - \chi H}{\chi}, \quad (50)$$

$$\frac{1}{\gamma} \frac{dm_z}{dt} + \nabla \cdot \mathbf{J}_s = 0. \quad (51)$$

Here $A_- = A - A_{12}$, and

$$\mathbf{J}_s = -\frac{A_- L^2}{2} \nabla\varphi \quad (52)$$

is the superfluid spin current. These equations are identical to Eqs. (24)-(26) for the ferromagnet after replacing the spontaneous magnetization component M_z by the total magnetization component m_z , A by $A_-/2$, and M_\perp by L .

In the stationary spin current state there is a constant gradient $\mathbf{K} = \nabla\varphi$ of the spin phase and a constant total magnetization

$$m_z = \frac{\chi H}{1 - \chi A_- K^2/2}. \quad (53)$$

For checking the Landau criterion we must know the spectrum of all collective modes. Solution of Eqs. (50) and (51) linearized with respect to plane wave perturbations $m' \propto e^{i\mathbf{k}\cdot\mathbf{r} - i\omega t}$ and $\varphi' \propto e^{i\mathbf{k}\cdot\mathbf{r} - i\omega t}$ of the stationary spin current state yield the spectrum of the Goldstone gapless mode:

$$\omega + \mathbf{w} \cdot \mathbf{k} = \tilde{c}_{sw} k. \quad (54)$$

Here the spin-wave velocity \tilde{c}_{sw} in the current state and the Doppler velocity \mathbf{w} are

$$\tilde{c}_{sw} = c_{sw} \sqrt{1 - \frac{\chi A_- K^2}{2}}, \quad \mathbf{w} = \gamma m_z A_- \mathbf{K}, \quad (55)$$

while

$$c_{sw} = \gamma L \sqrt{\frac{A_-}{2\chi}} = 2\gamma M \cos \theta_0 \sqrt{\frac{A_-}{2\chi}} \quad (56)$$

is the spin-wave velocity in the ground state without spin currents. The difference between gapless modes in a ferromagnet and an antiferromagnet is that in the former the total magnetization precesses around the z axis, while in the latter there is the precession of the staggered magnetization. Oscillations of sublattice magnetizations \mathbf{M}_1 and \mathbf{M}_2 in the gapless mode are illustrated in Fig. 7(a).

In antiferromagnets there is another mode in which the total magnetization \mathbf{m} and the staggered magnetization \mathbf{L} perform rotational oscillations around the axis normal to the axis z . Without spin supercurrents this axis does not vary in space, and one can choose it to be the axis y . The oscillations of the sublattice magnetizations are illustrated in Fig. 7(b). In the spin current state \mathbf{L} rotates

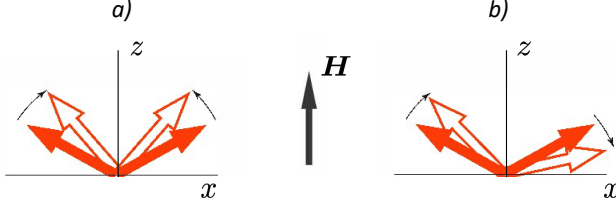


FIG. 7 The schematic picture of the two spin wave modes in the bipartite antiferromagnet in the plane xz [From Sonin (2020)]. (a) The gapless Goldstone mode. There are oscillations of the canting angle determining the magnetization component m_z and rotational oscillations around the axis z . (b) The gapped mode. There are rotational oscillations of the two magnetizations around the axis y .

around the axis, which itself rotates in the easy-plane xy along the current streamlines. The magnetic field breaks invariance with respect to rotations around axes normal to the field, and the mode spectrum is

$$\omega + \mathbf{w} \cdot \mathbf{k} = \sqrt{\omega_0^2 + c_{sw}^2 k^2}, \quad (57)$$

where the gap is given by

$$\omega_0 = \sqrt{\frac{\gamma^2 m_z^2}{\chi^2} - c_{sw}^2 K^2}. \quad (58)$$

More details of the derivation are given by Sonin (2019b).

Applying the Landau criterion to the gapless mode at small canting angles θ_0 (weak magnetic fields), one obtains the critical gradient K_L and the correlation length ξ_0 ,

$$K_L = \frac{1}{\xi_0}, \quad \xi_0 = \sqrt{\frac{\chi A_-}{2}}, \quad (59)$$

similar to those obtained for a ferromagnet [Eqs. (35) and (36)]. However, in contrast to a ferromagnet where the susceptibility χ is connected with weak anisotropy energy, in an antiferromagnet the susceptibility χ is determined by a much larger exchange energy and is rather small. As a result, in the antiferromagnet the gapped mode loses its stability at much lower values of K than the gapless mode. This happens at the Landau critical gradient

$$K_L = \frac{1}{\xi} \quad (60)$$

when the gap given by Eq. (58) vanishes and the mode frequency becomes complex. Here we introduced a new correlation length

$$\xi = \frac{c_s}{\gamma H} = \frac{\chi c_s}{\gamma m_z}. \quad (61)$$

As usual, the instability with respect to phase slips with magnetic vortices starts at the gradients of the same

order as the Landau critical gradient. Two modes in antiferromagnets have different correlation lengths, and, correspondingly, there are two types of magnetic vortices with different structure and size of the skyrmion core. Figure 6(b) shows schematically spatial variation of the sublattice magnetizations in the skyrmion core of a magnetic vortex connected with the Goldstone gapless mode. The core radius is of the order of the correlation length ξ_0 given by Eq. (59). Inside the core the canting angle θ_0 grows and reaches $\pi/2$ at the vortex axis. This transforms an antiferromagnet to a ferromagnet with the magnetization $2M$. The transformation increases the exchange energy, and at weak magnetic fields creation of magnetic vortices connected with the gapped mode starts earlier. Its core size is determined by the larger correlation length ξ determined by the Zeeman energy and given by Eq. (61). The skyrmion core connected with the gapped mode is illustrated in Fig. 6(c).

5. SUPERFLUID SPIN TRANSPORT WITHOUT SPIN CONSERVATION LAW

Though processes violating the spin conservation law are relativistically weak, their effect is of principal importance and cannot be ignored in general. Here we consider the effect of broken rotational symmetry in the easy plane in ferromagnets. Its extension on antiferromagnets requires insignificant modifications. One should add the s -fold in-plane anisotropy energy $\propto G_{in}$ to the Hamiltonian (21), which becomes

$$\mathcal{H} = \frac{M_z^2}{2\chi} - \gamma M_z H + \frac{AM_{\perp}^2 (\nabla\varphi)^2}{2} + G_{in} [1 - \cos(s\varphi)]. \quad (62)$$

Then the spin continuity equation (25) becomes

$$\frac{dM_z}{dt} = -\nabla \cdot \mathbf{J}_s + s G_{in} \sin(s\varphi) = AM_{\perp}^2 \left[\nabla^2 \varphi - \frac{\sin(s\varphi)}{l^2} \right], \quad (63)$$

where

$$l = \sqrt{\frac{AM_{\perp}^2}{s G_{in}}} \quad (64)$$

is the thickness of the wall separating domains with s equivalent easiest directions in the easy plane. In the stationary spin current states $dM_z/dt = 0$, and the phase φ is a periodical solution of the sine-Gordon equation parametrized by the average phase gradients $\langle \nabla\varphi \rangle$. At small $\langle \nabla\varphi \rangle \ll 1/l$ the spin structure constitutes the chain of domains with the period $2\pi/s\langle \nabla\varphi \rangle$. Spin currents (gradients) inside domains are negligible but there are spin currents inside domain walls. The spin current has a maximum in the center of the domain wall equal to

$$J_l = \sqrt{\frac{2}{s}} \frac{A}{l}. \quad (65)$$

The spin transport in the case $\langle \nabla \varphi \rangle \ll 1/l$ hardly reminds the superfluid transport on macroscopic scales: spin is transported over distances on the order of the domain-wall thickness l . With increasing $\langle \nabla \varphi \rangle$ the density of domain walls grows, and at $\langle \nabla \varphi \rangle \gg 1/l$ the domains coalesce. Deviations of the gradient $\nabla \varphi$ from the constant average gradient $\langle \nabla \varphi \rangle$ become negligible. This restores the analogy with the superfluid transport in superfluids (Sonin, 1978a,b, 1982), and spin non-conservation can be ignored. The transformation of the domain wall chain into a weakly inhomogeneous current state at growing $\langle \nabla \varphi \rangle$ is illustrated in Fig. 8. According to the Landau criterion, spin current states become unstable at $\nabla \varphi \sim 1/\xi_0$, where the correlation length ξ_0 is given by Eq. (36). Thus, one can expect metastable nearly uniform current states at $1/l \ll \langle \nabla \varphi \rangle \ll 1/\xi_0$. This is possible if the easy plane anisotropy energy G essentially exceeds the in-plane anisotropy energy G_{in} .

In the limit $\nabla \varphi \ll 1/l$ of strongly nonuniform current states the decay of the current is also possible only via phase slips, but the structure of magnetic vortices is essentially different from that in the opposite limit $\nabla \varphi \gg 1/l$. The magnetic vortex is a line defect at which s domain walls end. The phase slip with the magnetic vortex crossing the streamlines in the channel leads to annihilation of s domain walls. This process is illustrated in Fig. 2(b) for the four-fold in-plane symmetry ($s = 4$).

An important difference with conventional mass superfluidity is that while the existence of conventional superfluidity is restricted only from above by the Landau critical gradients, the spin superfluidity is restricted also from below: gradients should not be less than the value

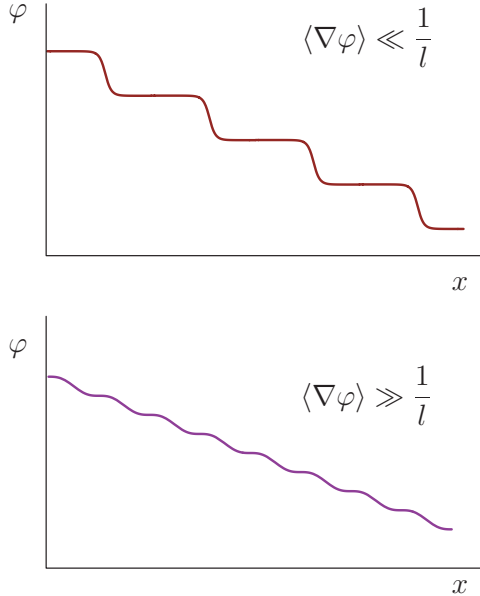


FIG. 8 The nonuniform spin-current states with $\langle \nabla \varphi \rangle \ll 1/l$ and $\langle \nabla \varphi \rangle \gg 1/l$ [From Sonin (2010)].

$1/l$. Thus, the gradient $K = \langle \nabla \varphi \rangle$ in the expression Eq. (39) barrier height cannot be less than $1/l$, and the height of the barrier cannot exceed

$$\varepsilon_m = \pi A M_{\perp}^2 \ln \frac{l}{r_c}. \quad (66)$$

In contrast to the maximal phase slip barrier Eq. (16) in mass superfluidity, in spin superfluidity the maximal phase slip barrier does not become infinite in the macroscopic limit $W \rightarrow \infty$ (König *et al.*, 2001; Sonin, 1978a,b, 1982).

6. LONG-DISTANCE SUPERFLUID SPIN TRANSPORT

The absence of the strict spin conservation law also leads to the dissipative process, which is impossible in the mass superfluidity and very important for long-distance superfluid spin transport (Sonin, 1978a, 2010; Takei *et al.*, 2014; Takei and Tserkovnyak, 2014): longitudinal spin relaxation characterized in the magnetism theory by the Bloch time T_1 . Taking the Bloch relaxation into account, the equation for the non-equilibrium magnetization $M'_z = M_z - \chi H$ becomes

$$\frac{1}{\gamma} \frac{dM'_z}{dt} = -\nabla \cdot \mathbf{J} - \frac{M'_z}{\gamma T_1}. \quad (67)$$

Here the total current $\mathbf{J} = \mathbf{J}_s + \mathbf{J}_d$ includes not only the spin supercurrent \mathbf{J}_s given by Eq. (26), but also the spin

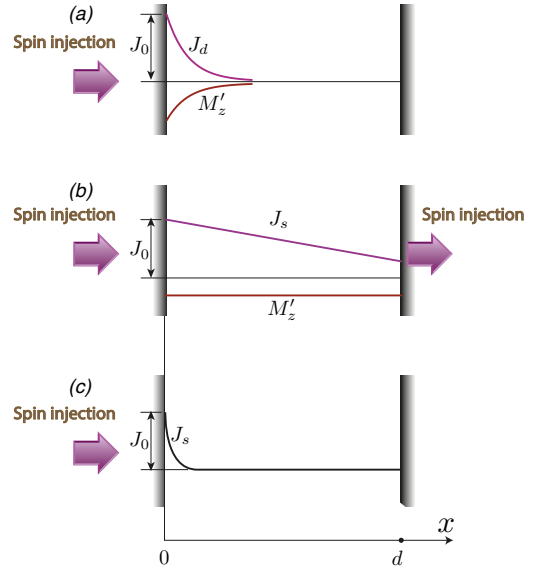


FIG. 9 Long distance spin transport [From Sonin (2010)]. (a) Injection of the spin current J_0 into a spin-non-superfluid medium. (b) Injection of the strong spin current $J_0 \gg J_l$ into a spin-superfluid medium. (c) Injection of the weak spin current $J_0 < J_l$ into a spin-superfluid medium.

diffusion current

$$\mathbf{J}_d = -\frac{D}{\gamma} \nabla M_z. \quad (68)$$

In the absence of spin superfluidity ($\mathbf{J}_s = 0$) Eq. (67) describes pure spin diffusion [Fig. 9(a)]. Its solution, with the boundary condition that the spin current J_0 is injected at the interface $x = 0$, is

$$J_d = J_0 e^{-x/L_d}, \quad M'_z = \gamma J_0 \sqrt{\frac{T_1}{D}} e^{-x/L_d}, \quad (69)$$

where

$$L_d = \sqrt{DT_1} \quad (70)$$

is the spin-diffusion length. Thus, the effect of spin injection exponentially decays at the scale of the spin-diffusion length, and the density of spin accumulated at the other border of the medium decreases exponentially with growing distance d .

However, if spin superfluidity is possible, the spin precession equation Eq. (24) becomes relevant. According to this equation, in a stationary state the magnetization M'_z cannot vary in space [Fig. 9(b)] since the gradient $\nabla M'_z$ leads to the linear in time growth of the gradient $\nabla \varphi$. The right-hand side of Eq. (24) is an analog of the chemical potential, and the requirement of constant in space magnetization M_z is similar to the requirement of constant in space chemical potential in superfluids, or the electrochemical potential in superconductors. As a consequence of this requirement, spin diffusion current is impossible in the bulk since it is simply “short-circuited” by the superfluid spin current. The bulk spin diffusion current can appear only in AC processes.

If the spin superfluidity is possible, the spin current can reach the spin detector at the plane $x = d$ opposite to the border where spin is injected. As a boundary condition at $x = d$, one can use a phenomenological relation $J_s(d) = M'_z(d)v_d$ connecting the spin current with the non-equilibrium magnetization at the border with a non-magnetic medium. Here v_d is a phenomenological constant. This boundary condition (Sonin, 1978a) was confirmed by the microscopic theory of Takei and Tserkovnyak (2014). Together with the boundary condition $J_s(0) = J_0$ at $x = 0$ this yields the solution of Eqs. (24) and (67):

$$M'_z = \frac{T_1}{d + v_d T_1} \gamma J_0, \quad J_s(x) = J_0 \left(1 - \frac{x}{d + v_d T_1} \right). \quad (71)$$

Thus, the spin accumulated at large distance d from the spin injector slowly decreases with d as $1/(d + C)$ [Fig. 9(b)], in contrast to the exponential decay $\propto e^{-d/L_d}$ in the spin diffusion transport [Fig. 9(a)]. The constant C is determined by the boundary condition at $x = d$.

The long-distance superfluid spin transport is possible only if the injected spin current is not too small. If

the injection spin current J_0 is less than the current J_l determined by Eq. (65) the superfluid spin current penetrates into the medium only at distances not longer than the width l of a domain wall in a non-uniform spin current state at a very small average gradient $\langle \nabla \varphi \rangle \ll 1/l$ [Fig. 9(c)]. This threshold for the long-distance spin superfluid transport is connected with the absence of the strict conservation law for spin (Sec. 5).

7. EXPERIMENTS ON DETECTION OF SPIN SUPERFLUIDITY

Experimental detection of spin superfluidity does not reduce to experimental evidence of the existence of spin supercurrents proportional to gradients of spin phase. As pointed out in Introduction (Sec. 1), such supercurrents produced by spin phase difference smaller than 2π emerge in any non-uniform spin structure. Numerous observations of spin waves and domain structures during the more than half-a-century history of modern magnetism cannot be explained without these microscopic spin currents. Only detection of macroscopical spin supercurrents produced by the phase difference many times larger than 2π is evidence of spin superfluidity.

The experimental evidence of macroscopical spin supercurrents was obtained in the past in the B phase of superfluid ^3He (Borovik-Romanov *et al.*, 1987). A spin current was generated in a long channel connecting two cells filled by ^3He - B . The quasi-equilibrium state of the coherent spin precession was supported by spin pumping. The magnetic fields applied to the two cells were slightly different, and therefore, the spins in the two cells precessed with different frequencies. A small difference in the frequencies leads to a linear growth of difference of the precession phases in the cells and a phase gradient in the channel. When the gradient reached the critical value, 2π phase slips were detected. This was evidence of non-trivial spin supercurrents.

This experiment was done in the dynamical state of coherent spin precession (non-equilibrium magnon BEC). The states require pumping of spin in the whole bulk for their existence. In the geometry of the experiment on long-distance spin transport (Sec. 6) this would mean that spin is permanently pumped not only by a distant injector but also all the way up to the place where its accumulation is probed. Thus, the spin detector measures not only spin coming from the distant injector but also spin pumped close to the detector. Therefore, the experiment cannot demonstrate the existence of long-distance superfluid spin transport, but can provide, nevertheless, indirect evidence that long-distance superfluid spin transport is possible in principle.

The experiment on detection of long-distance superfluid spin transport (Sec. 6) was recently done by Yuan *et al.* (2018) in antiferromagnetic Cr_2O_3 . The spin was

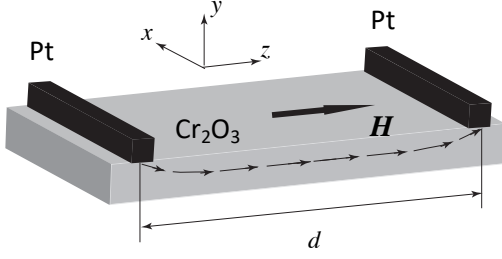


FIG. 10 Long distance spin transport in the experiment by Yuan *et al.* (2018). Spin is injected from the left Pt wire and flows along the Cr_2O_3 film to the right Pt wire, which serves as a detector. The arrowed dashed line shows a spin-current streamline [From Sonin (2020)].

injected from a Pt injector by heating [the Seebeck effect (Seki *et al.*, 2015)] on one side of the Cr_2O_3 film and spin accumulation was probed on another side of the film by the Pt detector via the inverse spin Hall effect (Fig. 10). In agreement with the theoretical prediction, they observed spin accumulation inversely proportional to the distance from the interface where spin was injected.

In the experiment of Yuan *et al.* (2018) spin injection required heating of the Pt injector, and the spin current to the detector is inevitably accompanied by a heat flow. Lebrun *et al.* (2018) argued that Yuan *et al.* (2018) detected a signal not from spin coming from the distant injector but from spin generated by the Seebeck effect at the interface between the heated antiferromagnet and the Pt detector. If true, Yuan *et al.* (2018) observed not long-distance spin transport but long-distance heat transport. A resolution of this controversy requires further experimental and theoretical investigations. In particular, one could check long-distance heat transport scenario by replacing the Pt spin injector in the experiment of Yuan *et al.* (2018) by a heater, which produces heat but no spin.

Observation of the long-distance superfluid spin transport was also reported by Stepanov *et al.* (2018) in a graphene quantum Hall antiferromagnet. However, the discussion of this report requires an extensive theoretical analysis of the $\nu = 0$ quantum Hall state of graphene, which goes beyond the scope of the present article. A reader can find this analysis in Takei *et al.* (2016).

8. DISCUSSION AND CONCLUSIONS

The article addressed the basics of the spin superfluidity concept: topology, Landau criterion, and phase slips. Metastable (persistent) superfluid current states are possible if the order parameter space (vacuum manifold) has the topology of a circumference like in conventional superfluids. In ferromagnets it is the circumference on the spherical surface of the spontaneous magnetizations \mathbf{M} ,

and in antiferromagnets it is the spherical surface of the unit Néel vector \mathbf{L}/L , where \mathbf{L} is the staggered magnetization. The topology necessary for spin superfluidity requires the magnetic easy-plane anisotropy in ferromagnets, while in antiferromagnets this anisotropy is provided by the Zeeman energy, which confines the Néel vector in the plane normal to the magnetic field.

The Landau criterion was checked for the spectrum of elementary excitations, which are spin waves in our case. In ferromagnets there is only one gapless Goldstone spin wave mode. In bipartite antiferromagnets there are two modes: the Goldstone mode in which spins perform rotational oscillations around the symmetry axis and the gapped mode with rotational oscillations around the axis normal to the symmetry axis. At weak magnetic fields the Landau instability starts not in the Goldstone mode, but in the gapped mode. In contrast to superfluid mass currents in conventional superfluids, metastable spin superfluid currents are restricted not only by the Landau criterion from above but also from below. The restriction from below is related to the absence of the strict conservation law for spin.

The Landau instability with respect to elementary excitations is a precursor for the instability with respect to phase slips. The latter instability starts when the spin phase gradient reaches the value of the inverse vortex core radius. This value is on the same order of magnitude as the Landau critical gradient. Magnetic vortices participating in phase slips have skyrmion cores, which map on the upper or lower part of the spherical surface in the space of spontaneous magnetizations in ferromagnets, or in the space of the unit Néel vectors in antiferromagnets.

It is worthwhile to note that in reality it is not easy to reach the critical gradients discussed in the present article experimentally. The decay of superfluid spin currents is possible also at subcritical spin phase gradients since the barriers for phase slips can be overcome by thermal activation or macroscopic quantum tunneling. This makes the very definition of the real critical gradient rather ambiguous and dependent on duration of observation of persistent currents. Calculation of real critical gradients requires a detailed dynamical analysis of processes of thermal activation or macroscopic quantum tunneling through phase slip barriers, which is beyond the scope of the present article. One can find examples of such analysis for conventional superfluids with mass supercurrents in Sonin (2016).

Experimental evidence of the existence of metastable superfluid spin currents in the B phase of superfluid ^3He was reported long ago (Borovik-Romanov *et al.*, 1987). The experiment was done in the non-equilibrium state of coherent spin precession, which requires permanent spin pumping in whole bulk for its existence. This does not allow to check true long-distance superfluid spin transport without any additional spin injection on the way from an injector to a detector of spin. The experiment

demonstrating the long-distance transport of spin in the solid antiferromagnet was reported recently (Yuan *et al.*, 2018). But the interpretation of this experiment in the terms of spin superfluidity was challenged (Lebrun *et al.*, 2018), and experimental verification of the long-distance superfluid spin transport in magnetically ordered solids convincing many (if not all) in the community is still wanted.

Mechanical analogy of the mass superfluidity discussed in the end of Sec. 2 is valid also for spin superfluidity. The “superfluid” flux of the angular momentum in a twisted elastic rod is similar to the superfluid spin current in magnetically ordered solids. Of course, it is not obligatory to discuss the twisted rod in terms of angular-momentum flux. More usual is to discuss it in the terms of the elasticity theory: deformations, stresses, and elastic stiffness. On the same grounds, one can avoid to use the terms “spin current” and “spin superfluidity” and consider the spin current states as metastable helicoidal spin structures determined by “phase stiffness”. This stance was quite popular in early disputes about spin superfluidity. Nowadays in the era spintronics the terms “spin supercurrents” and “spin superfluidity” are widely accepted.

In this article the essentials of spin superfluidity were discussed for simpler cases of a ferromagnet and of a bipartite antiferromagnet at zero temperature. Spin superfluidity was also investigated in antiferromagnets with a more complicated magnetic structure (Li and Kovalev, 2021). At finite temperatures the presence of the gas of incoherent magnons was taken into account in the two-fluid theory (Flebus *et al.*, 2016) similar to the two-fluid theory in the theory of mass superfluidity.

The present article focused on spin superfluidity in magnetically ordered solids. In superfluid ^3He spin superfluidity coexists with mass superfluidity. Recently investigations of spin superfluidity were extended to spin-1 BEC, where spin and mass superfluidity also coexist and interplay (Armaitis and Duine, 2017; Lamacraft, 2017; Sonin, 2018, 2019a). This interplay leads to a number of new nontrivial features of the phenomenon of superfluidity. The both types of superfluidity are restricted by the Landau criterion for the softer collective modes, which usually are the spin wave modes. As a result, the presence of spin superfluidity diminishes the possibility of the conventional mass superfluidity. Another consequence of the coexistence of spin and mass superfluidity is phase slips with bicirculation vortices characterized by two topological charges (winding numbers) (Sonin, 2019a).

REFERENCES

- Armaitis, J, and R. A. Duine (2017), “Superfluidity and spin superfluidity in spinor Bose gases,” *Phys. Rev. A* **95**, 053607.
- Borovik-Romanov, A S, Yu. M. Bunkov, V. V. Dmitriev, and Yu. M. Mukharskii (1987), “Observation of phase slippage during the flow of a superfluid spin current in $^3\text{He-B}$,” *Pis'ma Zh. Eksp. Teor. Fiz.* **45**, 98–101, [*JETP Lett.* **45**, 124–128 (1987)].
- Bunkov, Yu M (1995), “Spin supercurrent and novel properties of nmr in ^3He ,” in *Progress of Low Temperature Physics*, Vol. 14, edited by W. P. Halperin (Elsevier) p. 68.
- Bunkov, Yu M, and G. E. Volovik (2013), “Spin superfluidity and magnon Bose-Einstein condensation,” in *Novel Superfluids*, International Series of Monographs on Physics, Vol. 1, edited by K. H. Bennemann and J. B. Ketterson, Chap. IV (Oxford University Press) pp. 253–311.
- Chen, Hua, and Allan H. MacDonald (2017), “Spin-superfluidity and spin-current mediated nonlocal transport,” in *Universal themes of Bose-Einstein condensation*, edited by N.P. Proukakis, D.W. Snoke, and P.B. Littlewood, Chap. 27 (Cambridge University Press) pp. 525–548, arXiv:1604.02429.
- Demokritov, S O, V. E. Demidov, O. Dzyapko, G. A. Melkov, A. A. Serga, B. Hillebrands, and A. N. Slavin (2006), “Bose-Einstein condensation of quasi-equilibrium magnons at room temperature under pumping,” *Nature* **443**, 430–433.
- Evers, Martin, and Ulrich Nowak (2020), “Transport properties of spin superfluids: Comparing easy-plane ferromagnets and antiferromagnets,” *Phys. Rev. B* **101**, 184415.
- Flebus, B, S. A. Bender, Y. Tserkovnyak, and R. A. Duine (2016), “Two-fluid theory for spin superfluidity in magnetic insulators,” *Phys. Rev. Lett.* **116**, 117201.
- Guseinov, R R, and L. V. Keldysh (1972), “Nature of the phase transition under the conditions of an “exitonic” instability in the electronic spectrum of a crystal,” *Zh. Eksp. Teor. Fiz.* **63**, 2255, [*Sov. Phys.-JETP* **36**, 1193 (1972)].
- Halperin, B I, and P. C. Hohenberg (1969), “Hydrodynamic theory of spin waves,” *Phys. Rev.* **188**, 898–918.
- Iacocca, Ezio, T. J. Silva, and Mark A. Hoefer (2017), “Breaking of Galilean invariance in the hydrodynamic formulation of ferromagnetic thin films,” *Phys. Rev. Lett.* **118**, 017203.
- Keffer, F, and C. Kittel (1951), “Theory of antiferromagnetic resonance,” *Phys. Rev.* **85**, 329–337.
- König, J, M. C. Bønsager, and A. H. MacDonald (2001), “Dissipationless spin transport in thin film ferromagnets,” *Phys. Rev. Lett.* **87**, 187202.
- Kulik, I O, and S. I. Shevchenko (1976), “Exciton pairing and superconductivity in layered systems,” *Fiz. Nizk. Temp.* **2**, 1405–1426, [*Sov. J. Low Temp. Phys.* **2**, 687 (1976)].
- Lamacraft, Austen (2017), “Persistent currents in ferromagnetic condensates,” *Phys. Rev. B* **95**, 224512.
- Landau, L D (1941), “Theory of superfluidity of helium II,” *J. Phys. (USSR)* **5**, 71.
- Landau, L D, and E. M. Lifshitz (1980), *Statistical physics. Part II* (Pergamon Press).
- Lebrun, R, A. Ross, S. A. Bender, A. Qaiumzadeh, L. Baldrati, J. Cramer, A. Brataas, R. A. Duine, and M. Kläui (2018), “Tunable long-distance spin transport in a crystalline antiferromagnetic iron oxide,” *Nature* **561**, 222–225.
- Li, Bo, and Alexey A. Kovalev (2021), “Spin superfluidity in noncollinear antiferromagnets,” *Phys. Rev. B* **103**, L060406.
- Lozovik, Yu E, and V. I. Yudson (1977), “Interband transitions and the possibility of current states in systems with electron-hole pairing,” *Pis'ma Zh. Eksp. Teor. Fiz.* **25**, 18–21, [*JETP Lett.* **25**, 14–17 (1977)].

- Nikiforov, A V, and E. B. Sonin (1983), “Dynamics of magnetic vortices in a planar ferromagnet,” *Zh. Eksp. Teor. Fiz.* **85**, 642–651, [*Sov. Phys.–JETP* **58**, 373 (1983)].
- Pitaevskii, L, and S. Stringari (2003), *Bose–Einstein condensation* (Oxford University Press).
- Qaiumzadeh, Alireza, Hans Skarsvåg, Cecilia Holmqvist, and Arne Brataas (2017), “Spin superfluidity in biaxial antiferromagnetic insulators,” *Phys. Rev. Lett.* **118**, 137201.
- Seki, S, T. Ideue, M. Kubota, Y. Kozuka, R. Takagi, M. Nakamura, Y. Kaneko, M. Kawasaki, and Y. Tokura (2015), “Thermal generation of spin current in an antiferromagnet,” *Phys. Rev. Lett.* **115**, 266601.
- Shi, Junren, Ping Zhang, Di Xiao, and Qian Niu (2006), “Proper definition of spin current in spin-orbit coupled systems,” *Phys. Rev. Lett.* **96**, 076604.
- Sonin, E B (1977), “On superfluidity of Bose condensate of electron-hole pairs,” *Pis'ma Zh. Eksp. Teor. Fiz.* **25**, 95–98, [*JETP Lett.* **25**, 84–87 (1977)].
- Sonin, E B (1978a), “Analogues of superfluid currents for spins and electron-hole pairs,” *Zh. Eksp. Teor. Fiz.* **74**, 2097–2111, [*Sov. Phys.–JETP*, **47**, 1091–1099 (1978)].
- Sonin, E B (1978b), “Phase fixation, excitonic and spin superfluidity of electron-hole pairs and antiferromagnetic chromium,” *Solid State Commun.* **25**, 253–255.
- Sonin, E B (1982), “Superflows and superfluidity,” *Usp. Fiz. Nauk* **137**, 267, [*Sov. Phys.–Usp.*, **25**, 409 (1982)].
- Sonin, E B (2010), “Spin currents and spin superfluidity,” *Adv. Phys.* **59**, 181–255.
- Sonin, E B (2016), *Dynamics of quantised vortices in superfluids* (Cambridge University Press).
- Sonin, E B (2017), “Spin superfluidity and spin waves in YIG films,” *Phys. Rev. B* **95**, 144432.
- Sonin, E B (2018), “Spin and mass superfluidity in ferromagnetic spin-1 BEC,” *Phys. Rev. B* **97**, 224517, Although the subject of the paper is the BEC of cold atoms with spin 1, Sec. VII of the paper investigates vortices in a solid ferromagnet in order to compare them with vortices in the spin-1 BEC.
- Sonin, E B (2019a), “Interplay of spin and mass superfluidity in antiferromagnetic spin-1 Bose–Einstein condensates and bicirculation vortices,” *Phys. Rev. Research* **1**, 033103.
- Sonin, E B (2019b), “Superfluid spin transport in ferro- and antiferromagnets,” *Phys. Rev. B* **99**, 104423.
- Sonin, E B (2020), “Superfluid spin transport in magnetically ordered solids (review article),” *Fiz. Nizk. Temp.* **46**, 523–535, [*Low Temp. Phys.* **46**, 436 (2020)].
- Stepanov, Petr, Shi Che, Dmitry Shcherbakov, Jiawei Yang, Ruoyu Chen, Kevin Thilagar, Greyson Voigt, Marc W. Bockrath, Dmitry Smirnov, Kenji Watanabe, Takashi Taniguchi, Roger K. Lake, Yafis Barlas, Allan H. MacDonald, and Chun Ning Lau (2018), “Long-distance spin transport through a graphene quantum Hall antiferromagnet,” *Nat. Phys.* **14** (9), 907–911.
- Sun, Chen, Thomas Nattermann, and Valery L. Pokrovsky (2016), “Unconventional superfluidity in yttrium iron garnet films,” *Phys. Rev. Lett.* **116**, 257205.
- Sun, Chen, Thomas Nattermann, and Valery L. Pokrovsky (2017), “Bose–Einstein condensation and superfluidity of magnons in yttrium iron garnet films,” *J. Phys. D: Appl. Phys.* **50** (14), 143002.
- Takei, So, Bertrand I. Halperin, Amir Yacoby, and Yaroslav Tserkovnyak (2014), “Superfluid spin transport through antiferromagnetic insulators,” *Phys. Rev. B* **90**, 094408.
- Takei, So, and Yaroslav Tserkovnyak (2014), “Superfluid spin transport through easy-plane ferromagnetic insulators,” *Phys. Rev. Lett.* **112**, 227201.
- Takei, So, Amir Yacoby, Bertrand I. Halperin, and Yaroslav Tserkovnyak (2016), “Spin superfluidity in the $\nu = 0$ quantum Hall state of graphene,” *Phys. Rev. Lett.* **116**, 216801.
- Tserkovnyak, Yaroslav, and Mathias Kläui (2017), “Exploiting coherence in nonlinear spin-superfluid transport,” *Phys. Rev. Lett.* **119**, 187705.
- Vuorio, M (1974), “Condensate spin currents in helium-3,” *J. Phys. C: Solid State Phys.* **7** (1), L5–L8.
- Yuan, Wei, Qiong Zhu, Tang Su, Yunyan Yao, Wenyu Xing, Yangyang Chen, Yang Ma, Xi Lin, Jing Shi, Ryuichi Shindou, X. C. Xie, and We Han (2018), “Experimental signatures of spin superfluid ground state in canted antiferromagnet Cr_2O_3 via nonlocal spin transport,” *Sci. Adv.* **4** (4), eaat1098.