A note on the constant characteristic time of failure incubation processes under various highrate loads

Ivan Smirnov

Saint Petersburg State University, Universitetskaya nab. 7/9, St. Petersburg, 199034, Russia Corresponding author: ivansmirnov.sci@gmail.com

Abstract. The research reveals the existence of a constant characteristic time of preparatory microstructural processes before the onset of macro-failure at various high loading rates of brittle and quasi-brittle materials. The presence of this characteristic is analysed based on available data in the literature from dynamic tests for uniaxial compression and splitting. It is shown that the characteristic time can be determined experimentally and used to calculate the strain rate dependencies of either critical failure stresses or time to failure, at least in the case of linearly growing loads. In addition, it is discussed that the presence of this constant parameter opens up a prospective opportunity for research and development of new methods for assessing the structuraltemporal and scale characteristics of the strength and failure of materials under dynamic loads.

Keywords: quasi-brittle material, high strain rate, dynamic strength, time to fracture, characteristic time, failure criteria.

1. Introduction

The problems of deformation and failure of materials at high-rate intensive loads have been relevant for a significant period of time. Today, these studies continue to both certify the behaviour of materials at a given range of strain rates [1-3], and solve fundamental issues in order to develop approaches for qualitative forecasting the behaviour of materials, regardless of loading history [1,4,5]. However, there are still no universally accepted test methods or parameters that could allow us to evaluate and model the dynamic strength of materials based on simple engineering principles.

At sufficiently slow loads, the tensile strength and yield strength can, in fact, be assumed to be constant and considered as characteristic strength parameters of a material. This forms the basis of systems for state and industry standards to determine the strength characteristics of brittle and plastic materials. When the strain or loading rates exceed the standardized quasi-static range, these strength characteristics can become unstable and often strongly depend on the load history [5,6]. Therefore, under dynamic loads, they can no longer be considered as material parameters. To date, there is no agreement on which characteristics can serve as the primary indicators of the properties of materials under high-rate and shock loads. There is an urgent need to identify the characteristics, which do not depend on the history and method (set-up) of load application.

This short communication presents an important, previously unknown effect of the connection between failure incubation processes in the material structure and a constant time characteristic, which are independent of strain/loading rate. It is shown that this characteristic time can be determined experimentally and applied to criteria for evaluating the strength of a material within a wide range of loading rates.

2. The characteristic time of failure incubation processes

Let us consider the case of uniaxial loading for which failure begins at the stage of load growth without the pronounced and irreversible deformation of a specimen. This situation is typical when testing brittle and quasi-brittle materials, using the scheme of uniaxial compression or splitting tensile tests, for example. Let the beginning of a decrease in stresses in the stress-time or stress-strain diagram be the factor indicating the beginning of failure. The strength of a material then corresponds to the maximum value of stress. This is a common procedure for determining the strength of such materials with quasi-static tests. However, with an increase in the load or strain rate above the quasi-static range, the maximum failure stresses increase. Further in this paper, the maximum failure stresses are assumed as critical stresses.

Fig. 1 demonstrates the case described above. Since the loading area up until the moment of failure can be considered linear, the next expression is valid for the critical stress σ_{cr} :

$$\sigma_{cr} = E\dot{\varepsilon}t_{cr}, \quad t_{cr} > 0, \tag{1}$$

where *E* is the modulus of elasticity, $\dot{\varepsilon}$ is the strain rate and t_{cr} is the time before the start of failure. When the critical stress σ_{cr} is greater than the quasi-static strength σ_{st} , the time to failure and expression (1) can be written as the sum of two terms:

$$t_{cr} = t_{st} + t_d = \frac{\sigma_{st}}{E\dot{\varepsilon}} + t_d,$$
(2)

$$\sigma_{cr} = \sigma_{st} + E\dot{\varepsilon}t_d, \qquad t_{st} + t_d > 0, \tag{3}$$

where t_d is the time from time t_{st} when the quasi-static strength of a material is reached to the time of the actual critical stress t_{cr} . As a rule, experimental equipment allows for recording time diagrams of load and strain. The strain or loading rate is specified by the input test conditions. For the case under consideration, the stress rate is $\dot{\sigma} = E\dot{\epsilon}$. Thus, all components of expression (3) can be determined from the experiment.

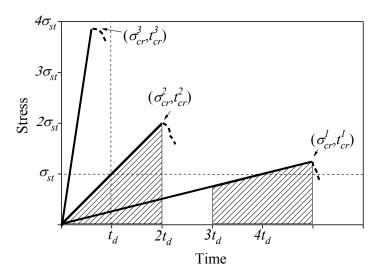


Fig. 1. Schematic representation of loading at different rates. Designations are disclosed in the text.

Then we can estimate the time t_d that characterises the dynamics of micro-processes in the structure of the material after reaching the quasi-static strength of the material σ_{st} until the onset of 'macro' failure t_{cr} :

$$t_d = \frac{\sigma_{cr} - \sigma_{st}}{E\dot{\varepsilon}}.$$
(4)

Let us consider such an estimate regarding various experimental data. Dynamic strength is typically evaluated by the dependence of critical stress on the strain or stress rate. An example of such dependence for the case of dynamic uniaxial compression of concrete is presented in Fig. 2. Substituting the experimental points in expression (4), we derive the dependence of time t_d on the strain rate. Fig. 3 presents such calculations for the uniaxial compression and splitting test of various materials. Usually experimental points have a spread, so it is convenient to use the equation of the slope of a regression line to determine the time t_d . The results show that, regardless of the material and loading scheme, the time t_d for each experiment can be considered constant.

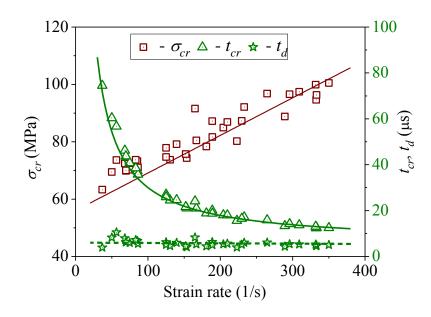


Fig. 2. Strain rate dependencies of critical stresses and time to failure for dynamic uniaxial compression testing of concrete. Experimental data were obtained by [7]. The solid curves ware calculated using expressions (2) and (3). The dashed line is a linear approximation.

Note that we use the same notation for the case of compression and splitting. This is not only to avoid unnecessary notation, but also to show the commonality of the effect for various tests. A caveat, however, is that when considering a specific test method, these load and material parameters only apply to this method of testing.

Up to this point, it has been assumed that the time to failure t_{cr} is greater than the time t_d . However, the question arises: up to what value does the time to failure decrease, and would it be less than time t_d ? In order to answer this question, it is necessary to consider the stress impulse before the start of failure.

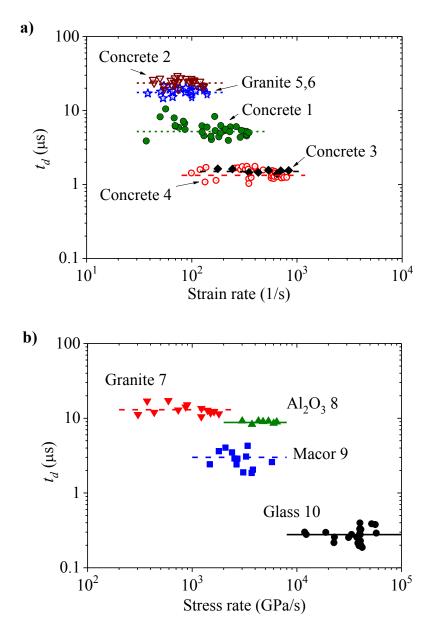


Fig. 3. The characteristic times of incubation micro-processes from the moment of reaching quasistatic strength to the moment of the onset of macro-failure of various materials under high-rate loading. The calculations were carried out by Eq. (4) for the experimental data: a) compression tests of concrete 1 [7], 2 [8], 3 [9], 4 [10], and granite 5 [11] and 6 [12]; b) splitting test of granite 7 [13], ceramics 8 [14] and 9 [15] and glass 10 [16].

A stress analysis shows that for critical stress $\sigma_{st} < \sigma_{cr} < 2\sigma_{st}$, the stress impulse applied to a specimen is constant over a time from $t_{cr} - 2t_d$ to t_{cr} (at the condition that t_d is constant). These segments of the stress pulses J_{cr} are indicated by the shaded areas in Fig. 1. It is evident that the stress impulse J_{cr} is equal to

$$J_{cr} = 2\sigma_{st}t_d.$$
 (5)

Suppose this impulse is the minimum value of the stress impulse that must be applied to the specimen in order to initiate and prepare its macro failure. Then, if the time to failure is $t_{cr} \leq 2t_d$, the failure stress impulse must also be at least $2\sigma_{st}t_d$. Since for $t_{cr} \leq 2t_d$ $2\sigma_{st}t_d = 0.5\sigma_{cr}t_{cr}$, then the expressions for the strain rate dependence of the critical stress and time to failure, taking (1) into account, can be written in the following form:

$$\sigma_{cr} = \sqrt{4E\sigma_{st}t_d\dot{\varepsilon}}, \quad t_{cr} \le 2t_d, \tag{6}$$

$$t_{cr} = \sqrt{\frac{4\sigma_{st}t_d}{E\dot{\varepsilon}}}, \quad t_{cr} \le 2t_d.$$
⁽⁷⁾

In addition, the condition for time to failure in expression (3) should now be specified as $t_{cr} \ge 2t_d$.

The characteristic time t_d can be easily obtained from expression (6). Fig. 4 and 5 present these calculations for the uniaxial compression and splitting test of various materials. Thereby, the time t_d was determined by formula (4) for the case $\sigma_{cr} < 2\sigma_{st}$ and from formula (6) for $\sigma_{cr} \ge 2\sigma_{st}$. This example also demonstrates that the time t_d can be considered constant for various strain and loading rates.

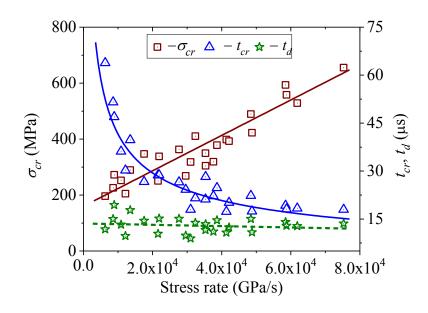


Fig. 4. Strain rate dependencies of critical stresses and time to failure for dynamic uniaxial compression tests of concrete in the cases of $t_{cr} \ge 2t_d$ and $t_{cr} \le 2t_d$. Experimental data was obtained by [17]. The solid curves were calculated using conditions (2), (3), (6) and (7). The dashed line is a linear approximation.

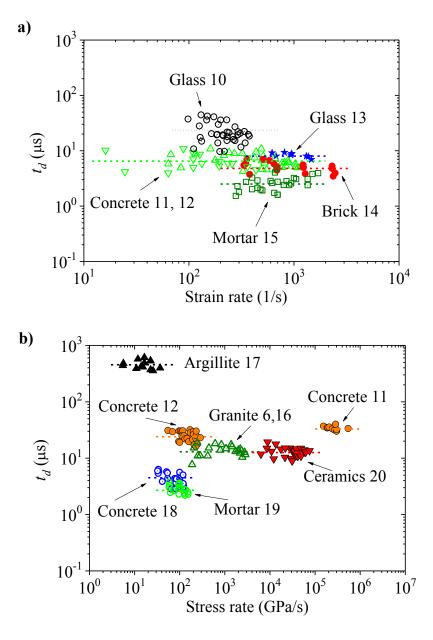


Fig. 5. The characteristic times calculated for different conditions of $\sigma_{cr} < 2\sigma_{st}$ and $\sigma_{cr} \ge 2\sigma_{st}$. The calculations were carried out according to Eq. (4) and (6) for the experimental data: a) compression tests of concrete 11 [18] and 12 [19], glass 10 [16] and 13 [20], brick 14 [21], and mortar 15 [22]; b) splitting test of rocks 6 [12], 16 [23], and 17 [24], concrete 11 [18] and 12 [19], and 18 [25], mortar 19 [25], and ceramics 20 [26].

3. Discussion and future work

Thus, the experimental data provides reason to introduce the characteristic time of incubation processes of failure t_d , which can be considered a constant value independent of a strain rate above the quasi-static range, at least for cases of continuous linear increase in load during the

uniaxial compression or splitting tests. This time parameter characterises the individual response of a material to dynamic loads. Therefore, this characteristic time can be used in criteria conditions of structural-temporal approaches to failure analysis and strength prediction. For example, similar expressions for (3) and (6) were obtained theoretically using the incubation time criterion [5,27,28]. The criterion assumes that the following condition must be implemented for failure to occur:

$$\int_{t-\tau}^{t} \sigma(t)dt \ge \sigma_{st}\tau,$$
(8)

where $\sigma(t)$ is the stress profile at the failure place, σ_{st} is the quasi-static strength, and τ is the incubation time of failure. The parameters σ_{st} and τ are strength parameters of a material for a particular test scheme, for example, compression or tension. The incubation time was introduced as a hypothetical characteristic period of time responsible for the incubation period of macro-failure. This was necessary to ensure the possibility of a smooth transition from pulsed loads to quasi-static loads using the Nikiforovsky-Shemyakin integral criterion for spall fracture (full integral of the stress over time at the spall section should reach a critical value) [5,29]. Therefore, according to (8), failure will occur in the case that the stress impulse in the region of failure is not less than $\sigma_{st}\tau$ for the time $t \leq \tau$ (for t < 0, $\sigma(t) = 0$). A similar assumption is made in the discussion of (5).

Substituting (1) for $\sigma(t)$ in (8), we can obtain simple relationships for calculating the strain rate dependencies of critical stresses σ_{cr} and the time to failure t_{cr} :

$$\begin{cases} \sigma_{cr} = \sigma_{st} + 0.5E\dot{\epsilon}\tau, & t_{cr} = \frac{\tau}{2} + \frac{\sigma_{st}}{E\dot{\epsilon}}, & t_{ct} > \tau, \\ \sigma_{cr} = \sqrt{2E\sigma_{st}\tau\dot{\epsilon}}, & t_{cr} = \sqrt{\frac{4\sigma_{st}t_d}{E\dot{\epsilon}}}, & t_{cr} \le \tau. \end{cases}$$
(9)

Substituting $\tau = 2t_d$, we derive the expressions in (9), which correspond exactly to expressions (2), (3), (6) and (7).

The incubation time approach allows us to successfully solve a number of dynamic problems related to fracture mechanics [5,27–30]. However, the question of experimental determination of the incubation time of failure still remains open-ended. The obtained result shows

that the incubation time of failure, at least for the case of a controlled linear increase in fast loading, can be determined experimentally by estimating t_d .

The demonstrated effect opens up new possibilities for solving important problems related to the mechanics of dynamic deformation and fracture of materials. One of these tasks relates to the possibility of determining the parameters of the dynamic strength of materials using basic tests that are both publicly available and generally accepted. Furthermore, it is necessary to study appropriate methods and basic rules to determine the characteristic time t_d . Experimental conditions affecting time t_d should also be established.

Another problem relates to the determination of the strain rate dependence of the yield strength. The presented reasoning can be applied to consider similar characteristic time of incubation processes involved in the plastic deformation [30].

The found characteristic time of failure incubation processes can provide a new approach to the determination of scale levels of failure. Since we have a constant time characteristic for the implementation of preparatory failure processes, we can assume that there is also a constant characteristic structural scale at which these processes are realised. For example, according to the structural-temporal approach [29], this characteristic scale can relate to the propagation distance of the elastic wave during time τ ($d = \tau C$, in which *C* is the speed of sound); as well, the scale can be introduced as $d = (2KI_C^2)/(\pi \sigma_{st}^2)$ (KI_C as the stress intensity factor). However, the accuracy of these expressions for the elementary scale of failure is still being studied. Thus, the relationship of time t_d , scale factors and the dynamics of the preparatory microstructural processes of macrofracture should be studied.

4. Conclusions

The presented study shows the existence of a characteristic time for preparatory microprocesses of macro-failure of brittle and quasi-brittle materials. This time does not depend on the strain or loading rate, at least in terms of the compression and splitting test methods under consideration. The value of the characteristic time can be determined directly from the experiment. The presented results show that this integral time characteristic of the dynamic failure process can be used for the development of experimental and theoretical foundations to determine and predict the strength characteristics of constructional materials across a wide range of loading rates.

Acknowledgements

This work was supported by the Russian Science Foundation, grant № 18-79-00193.

References

- Zhang QB, Zhao J. A Review of Dynamic Experimental Techniques and Mechanical Behaviour of Rock Materials. Rock Mech Rock Eng 2014;47:1411–78. https://doi.org/10.1007/s00603-013-0463-y.
- [2] Shukla A, Ravichandran G, Rajapakse YDS, editors. Dynamic Failure of Materials and Structures. Boston, MA: Springer US; 2010. https://doi.org/10.1007/978-1-4419-0446-1.
- Brara A, Klepaczko JR. Experimental characterization of concrete in dynamic tension. Mech Mater 2006;38:253–67. https://doi.org/10.1016/j.mechmat.2005.06.004.
- [4] Forquin P, Hild F. A Probabilistic Damage Model of the Dynamic Fragmentation Process in Brittle Materials, 2010, p. 1–72. https://doi.org/10.1016/S0065-2156(10)44001-6.
- [5] Morozov N, Petrov Y. Dynamics of Fracture. Berlin, Heidelberg: Springer Berlin Heidelberg; 2000. https://doi.org/10.1007/978-3-540-69712-1.
- [6] Curran DR, Seaman L, Shockey DA. Dynamic failure of solids. Phys Rep 1987;147:253– 388. https://doi.org/10.1016/0370-1573(87)90049-4.
- [7] Zhang M, Wu HJ, Li QM, Huang FL. Further investigation on the dynamic compressive strength enhancement of concrete-like materials based on split Hopkinson pressure bar tests.
 Part I: Experiments. Int J Impact Eng 2009;36:1327–34. https://doi.org/10.1016/j.ijimpeng.2009.04.009.
- [8] Chen X, Wu S, Zhou J. Experimental and modeling study of dynamic mechanical properties of cement paste, mortar and concrete. Constr Build Mater 2013;47:419–30.

https://doi.org/10.1016/j.conbuildmat.2013.05.063.

- [9] Malvern LE, Ross CA. Dynamic response of concrete and concrete structures, Second Annual Technical Report, AFOSR Contract No. F49620-83-K007. 1985.
- [10] Klepaczko JR. Behavior of rock-like materials at high strain rates in compression. Int J Plast 1990;6:415–32. https://doi.org/10.1016/0749-6419(90)90011-3.
- [11] Xia K, Nasseri MHB, Mohanty B, Lu F, Chen R, Luo SN. Effects of microstructures on dynamic compression of Barre granite. Int J Rock Mech Min Sci 2008;45:879–87. https://doi.org/10.1016/j.ijrmms.2007.09.013.
- [12] Dai F, Huang S, Xia K, Tan Z. Some Fundamental Issues in Dynamic Compression and Tension Tests of Rocks Using Split Hopkinson Pressure Bar. Rock Mech Rock Eng 2010;43:657–66. https://doi.org/10.1007/s00603-010-0091-8.
- [13] Dai F, Xia K. Loading Rate Dependence of Tensile Strength Anisotropy of Barre Granite.
 Pure Appl Geophys 2010;167:1419–32. https://doi.org/10.1007/s00024-010-0103-3.
- [14] Chen P, Guo B, Chen J. Dynamic Brazilian Test Using the Kolsky-Hopkinson Bar Machine.
 Kolsk. Bar Mach., Cham: Springer International Publishing; 2018, p. 121–41.
 https://doi.org/10.1007/978-3-319-71919-1_4.
- [15] Dong S, Xia K, Huang S, Yin T. Rate dependence of the tensile and flexural strengths of glass-ceramic Macor. J Mater Sci 2011;46:394–9.
 https://doi.org/10.1007/s10853-010-4852-2.
- [16] Zhang X, Zou Y, Hao H, Li X, Ma G, Liu K. Laboratory Test on Dynamic Material Properties of Annealed Float Glass. Int J Prot Struct 2012;3:407–30. https://doi.org/10.1260/2041-4196.3.4.407.
- [17] Liu P, Zhou X, Qian Q, Berto F, Zhou L. Dynamic splitting tensile properties of concrete and cement mortar. Fatigue Fract Eng Mater Struct 2020;43:757–70. https://doi.org/10.1111/ffe.13162.
- Tedesco JW, Ross CA. Strain-Rate-Dependent Constitutive Equations for Concrete. J Press
 Vessel Technol 1998;120:398–405. https://doi.org/10.1115/1.2842350.

- Bragov AM, Lomunov AK, Lamzin DA, Konstantinov AY. Change of Strength of Brittle Building Materials under High Strain and Stress Rates. Lobachevskii J Math 2019;40:284– 91. https://doi.org/10.1134/S1995080219030077.
- [20] Zhang X, Hao H, Ma G. Dynamic material model of annealed soda-lime glass. Int J Impact Eng 2015;77:108–19. https://doi.org/10.1016/j.ijimpeng.2014.11.016.
- [21] Lamzin DA, Bragov AM, Lomunov AK, Konstantinov AY, Dell'Isola F. Analysis of the dynamic behavior of sand-lime and ceramic bricks. Mater Phys Mech 2019;42:691–698. https://doi.org/10.18720/MPM.4262019_1.
- [22] Grote DL, Park SW, Zhou M. Dynamic behavior of concrete at high strain rates and pressures: I. experimental characterization. Int J Impact Eng 2001;25:869–86. https://doi.org/10.1016/S0734-743X(01)00020-3.
- [23] Dai F, Xia K, Tang L. Rate dependence of the flexural tensile strength of Laurentian granite.
 Int J Rock Mech Min Sci 2010;47:469–75. https://doi.org/10.1016/j.ijrmms.2009.05.001.
- [24] Cai M, Kaiser PK, Suorineni F, Su K. A study on the dynamic behavior of the Meuse/Haute-Marne argillite. Phys Chem Earth, Parts A/B/C 2007;32:907–16. https://doi.org/10.1016/j.pce.2006.03.007.
- [25] Jin X, Hou C, Fan X, Lu C, Yang H, Shu X, et al. Quasi-static and dynamic experimental studies on the tensile strength and failure pattern of concrete and mortar discs. Sci Rep 2017;7:15305. https://doi.org/10.1038/s41598-017-15700-2.
- [26] Liu J, Hu Z, Zhang Y. Dynamic tensile mechanical properties and failure mode of zirconium diboride-silicon carbide ceramic composites. Int J Appl Ceram Technol 2020;17:886–92. https://doi.org/10.1111/ijac.13462.
- [27] Morozov NF, Petrov Y V. Incubation time based testing of materials. Eur J Mech A/Solids 2006;25:670–6. https://doi.org/10.1016/j.euromechsol.2006.05.005.
- [28] Petrov YV, Smirnov IV, Volkov GA, Abramian AK, Bragov AM, Verichev SN. Dynamic failure of dry and fully saturated limestone samples based on incubation time concept. J Rock Mech Geotech Eng 2017;9. https://doi.org/10.1016/j.jrmge.2016.09.004.

- [29] Petrov Y V., Gruzdkov AA, Bratov VA. Structural-temporal theory of fracture as a multiscale process. Phys Mesomech 2012;15:232–7. https://doi.org/10.1134/S1029959912020117.
- [30] Borodin EN, Mayer AE, Petrov Y V., Gruzdkov AA. Maximum yield strength under quasistatic and high-rate plastic deformation of metals. Phys Solid State 2014;56:2470–9. https://doi.org/10.1134/S1063783414120051.