

Glassy materials for Silicon-based solar panels: present and future

Marcos Paulo Belançon^a, Marcelo Sandrini^a, Vitor Santaella Zanuto^b,
Robson Ferrari Muniz^c

^a*Universidade Tecnológica Federal do Paraná, Campus Pato Branco, Pato Branco, 85503-040, Paraná, Brazil*

^b*Universidade Estadual de Maringá, Campus Maringá, Departamento de Física, Maringá, Paraná, Brazil*

^c*Universidade Estadual de Maringá, Campus Goioerê, Departamento de Ciências, Goioerê, Paraná, Brazil*

Abstract

Glass provides mechanical, chemical, and UV protection to solar panels, enabling these devices to withstand weathering for decades. The increasing demand for solar electricity and the need to reduce anthropogenic carbon emissions demands new materials and processes to make solar even more sustainable. Here, we review the current research to create environmentally friendly glasses and to add new features to the cover glass used in silicon solar panels, such as anti-reflection, self-cleaning, and spectral conversion properties. While several studies have proposed spectral converters and reported information regarding their light-conversion efficiency, there is still a need for a standardized protocol to investigate and compare the impact of these modified materials on the electrical output of photovoltaic systems. In light of these issues, we propose a framework for quantifying parameters that can serve as benchmarks for comparing different cover glasses, which is especially important in the search for a viable spectral converter.

Keywords: Glasses, Cover glass, Spectral converter, Energy

PACS: 0000, 1111

2000 MSC: 0000, 1111

Contents

1 Introduction

2

2	Reducing energy inputs	4
2.1	Alternative glass matrix	5
2.1.1	Aluminosilicates	6
2.1.2	YAG Glass Ceramics	6
2.1.3	SLS variations	7
2.1.4	Silicates containing fluorine	7
2.1.5	Other alternatives	8
3	Increasing energy outputs	8
3.1	Anti-reflective glass surfaces	9
3.2	Self-cleaning and multifunctional glass surfaces	9
3.3	Spectral converters (SC)	10
3.3.1	Main rare-earth dopants for spectral conversion	11
3.3.2	Non-rare-earth ions for spectral conversion	15
3.3.3	A benchmark framework for spectral converters	16
3.3.4	The ideal SC	19
4	Emerging trends	22
4.1	Lowering carbon emission with Hydrogen	22
4.2	Alternative materials and methods	22
5	Discussion	23
6	Conclusion	24
7	Acknowledgement	25

1. Introduction

The annual glass consumption worldwide surpassed 21 kg per person in 2014 [1]. Besides traditional applications such as packaging or flat glass for cars and buildings, the glass demand for cover glasses (CG) in solar panels is significant. Silicon-based photovoltaic panels (PV) are already responsible for about 3% of electricity produced annually worldwide, and this share is expected to grow significantly in the following decades [2, 3]. A standard PV produce an electrical output of $\sim 210 W_p/m^2$ from $1000 W/m^2$ of sunlight, which corresponds to efficiencies of about 21% at the industry level [4]. As the world transitions to more sustainable energy sources, new PVs are installed as fast as $183 GW_p$ per year, corresponding to an additional area of about

1 billion square meters. CG demand is high, and the share of bifacial PVs (which may have glass on both the front and back sides [5]) is growing and pushing the consumption of float glass by this sector even further.

However, several aspects of the PV technology need further improvements to guarantee its sustainability in the future [3, 6, 7, 8, 9, 10], and some of them are related to the glass ecological footprint [11, 12], as well as its features, such as UV-filtering, anti-reflective and self-cleaning properties [13]. Glass makes 67%-76% of the total solar panel weight. There is a growing concern about the industrial impact of glass production, which includes significant energy inputs and emissions of about 60 million tons of CO₂ equivalent per year [12]. From another hand, silicon’s characteristic spectral sensitivity limits the efficiency of sunlight to power conversion, and the industry is already reaching the practical limits imposed by the Shockley-Queisser theory [14, 15].

In this context, glass science may address these problems and help expand and develop more sustainable technologies, materials, and processes. Here, we review some of the glass research related to this subject, highlighting advances and the most critical challenges associated with PV expansion. We critically discuss these new glassy materials and technologies in light of the terawatt scale of photovoltaic systems worldwide, highlighting aspects that may constrain their adoption, such as inadequate mechanical or chemical properties, abundance of minerals, and cost.

To effectively synthesize and evaluate the vast array of information available, we implemented a systematic approach in our literature review by categorizing the relevant topics into distinct sections. Our objective was to address specific issues of interest to the glass science community, and to establish a cohesive framework for analysing these topics. These topics are organized in terms of the “energy return on investment” (EROI) concept [16, 17, 18, 19, 20]. The EROI for a solar panel is the sum of energy invested in all materials and processes needed to build the devices, divided by all the energy produced during the panel lifespan. In other words, there are advances that researchers may pursue that will contribute to one or other part of this equation, and some of the most interesting ones are presented and discussed in this work.

In the 1950s, the Pilkington process, or float process, revolutionized the glass-making industry [21, 22]. Glass production could grow while enabling glass to be produced faster, with much higher quality and a reduced cost, and these features were necessary to make possible such massive production of PV in the world today. However, even though the knowledge of several

families of glasses is abundant, only soda-lime silicate (SLS) glass is adequate to Pilkington’s process, and cheap enough to meet the industry needs.

It is important to remember that SLS glass making is an energy-intensive process due to this material high melting temperature ($\sim 1500^{\circ}C$), which requires about 7-8 GJ/t to be produced [1]. This value is significantly higher for other materials, such as aluminum (90-100 GJ/t). However, explicitly speaking of the CG, the challenge remains not precisely in how much energy is consumed per ton of glass, but in the amount of material needed in each panel, the growing demand [4, 11], and the difficult task of recycling CG. As this material should have a specific composition, which includes a low iron concentration, it is challenging to perform the recycling process without introducing impurities, namely, iron. In this way, while SLS glass can be indefinitely recycled, the amount of glass mixed with the melt in the float glass production is limited to about $\sim 11\%$ [1], to avoid negative impacts to the final glass sheet.

Considering the vast number of different glasses and treatments applied to their surfaces under investigation by researchers worldwide, here we review some trends that may potentially enhance the EROI of PVs. Several possibilities exist that could either reduce the energy input or increase the energy output of the panel. We will now focus our discussion on those that pertain to the former alternative.

2. Reducing energy inputs

At the industry level, glass has become a synonym for SLS glass. However, other glasses, such as borosilicates, are fundamental for some applications due to their improved chemical and thermal resistance. It presents a reduced expansion coefficient, vital for several applications [23], but also preventing it from being thermally toughened [13]. This fact clearly illustrates that, when developing a new glass system, an improved property often has a downside.

Anyhow, one can see that basic research plays a critical role in creating an environment that enables breakthroughs to occur. In the case of borosilicate, there is still much research going on about its structure [24, 25, 26], corrosion [27], effects of dopants [28] and other basic science studies. In such a context, we are not looking to present a glass ready to replace the SLS in solar panels but to highlight some of the most recent and exciting results in the literature concerning the search for alternatives.

2.1. Alternative glass matrix

Glasses and glass ceramics have been a constant subject of research world-wide. Besides several applications that include lasers [29], amplifiers [30], glass fibers [31, 32], sensors [33, 34, 35] and white-light applications [36, 37, 38, 39, 40, 41, 42, 43], several studies have been developed aiming to apply a glassy material to enhance photovoltaic energy production. In Table 1, we have listed some of these materials recently investigated for this application, as well as their primary raw materials and the respective melting temperature (T_{Melt}).

Glass	Main Components	T_{Melt} ($^{\circ}C$)
Aluminosilicates [44, 45]	SiO_2 -CaO- Al_2O_3	1400-1600
YAG Glass-Ceramic [46]	SiO_2 - Al_2O_3 - Y_2O_3 - B_2O_3	1500
Fluorosilicate [47]	SiO_2 - Al_2O_3 -CaF ₂	1500
SLS-Lithium [13]	SiO_2 -Na ₂ O-CaO-MgO- Al_2O_3 -Li ₂ O	1450-1480
SLS-Titanium [48]	SiO_2 -Na ₂ O-CaO-TiO ₂	-
Alkali alumina-borate GC [49]	Al_2O_3 - B_2O_3 -K ₂ O-Li ₂ O	1400
SCS [50, 51]	SiO_2 -Na ₂ O-CaO- Al_2O_3 -CaF ₂	1150-1250
Recycled SLS [52, 53]	SiO_2 -Na ₂ O-CaO-MgO- Al_2O_3	1100
Borates [54]	B_2O_3 -ZnO- Al_2O_3 -BaO	1100
Phosphates [55, 56, 57]	NaH ₂ PO ₄ -H ₂ O	1000
Lead-Bismuthate [58]	Li ₂ O-Bi ₂ O ₃ -PbO	800-1000
Lithium-Tellurite [59]	TeO ₂ -Li ₂ O	850
Fluorochlorozirconate [60]	ZrF ₄ -BaCl ₂ -NaF-AlF ₃	825
Fluorozirconate [61]	ZrF ₄ -BaF ₂ -NaF-AlF ₃	745
Tellurite-Tungstate [30, 62]	TeO ₂ -WO ₃ -Nb ₂ O ₅ -Na ₂ O	700-800
Zinc-Tellurite [63, 64, 65, 66, 67]	TeO ₂ -ZnO-Na ₂ O	600-800

Table 1: Some glassy materials recently investigated for photovoltaic applications and its T_{Melt} value, or range value.

This list includes materials with chemistry very similar to the commercial SLS glass and some based on entirely different systems. From the point of view of reducing the energy inputs, it would be interesting to develop low-melting temperature materials. However, it seems impossible for large-scale applications to be based on some of those materials in table 1. For example, even though Tellurium is used to produce commercial thin-film technologies such as CdTe solar cells [68], this mineral is a secondary product

in mining [69, 70], and its availability would never allow the production of tellurite glass to be even a fraction of that demanded from PVs.

On the other hand, the upper part of table 1 contains a few glass matrices that rely on quite common and abundant minerals. Yttrium is not as abundant as silicon or aluminum, although it is the second most abundant rare-earth [71]. Some of these glasses are presented and discussed hereafter, following descending order of melting temperature.

2.1.1. Aluminosilicates

The incorporation of aluminum brings substantial modification to silicates in general. Properties such as the elastic module and hardness increase monotonically with alumina content from 30 mol% to 60 mol% [72]. Related to this phenomenon, pure silica fibers may have their Brillouin coefficient reduced by two orders of magnitude due to Aluminum [31]. Aluminosilicate compositions with up to 39% Al_2O_3 content [44] have already been used as active media for lasers [29, 73], which demonstrates high optical quality as well as efficient luminescent properties that are both required to develop spectral converters (SCs) for photovoltaics. However, the viscosity of the silica melt is significantly reduced by the aluminum [74], and conventional production methods of flat glass are not compatible with these melts [31]. One exciting possibility is the development of thin films, recently demonstrated by Savi [45] et al. Though a sophisticated UV-pulsed laser deposition technique was used, it is remarkable that films as thin as 17 nm were obtained, and most properties of the bulk glass samples were preserved. Several complementary works to this study could be exciting, such as investigating the mechanical properties and strength of the film, as well as its production by more straightforward techniques.

2.1.2. YAG Glass Ceramics

Yttrium-Aluminum-Garnet (YAG) has been used as active media and phosphor for lighting applications for several decades. Tai et al. [46] have prepared glass samples containing Yttrium, which were heat-treated at $\sim 750^\circ\text{C}$ to grow YAG nanocrystals inside bulk samples. The resulting Nd^{3+} - Yb^{3+} co-doped glass-ceramic demonstrated NIR DC of photons with quantum efficiencies as high as 185%. One exciting aspect of these materials is the production of nanocrystals at moderately low temperatures, which may favor their production for practical applications. Besides, analyzing this remarkable material on a photovoltaic panel prototype would be essential since the

material refractive index and its optical quality may introduce significant reflection losses. As recently demonstrated, such evaluation can be performed under natural sunlight irradiation using an affordable apparatus [67].

2.1.3. SLS variations

Modified SLS glass has also been under investigation aiming at photovoltaic applications. Allsopp et al. [13] have demonstrated an extensive study of Bi^{3+} - Gd^{3+} co-doped SLS glass, which was also slightly modified with the incorporation of Li_2O to facilitate the production of flat samples. Miniaturized solar module prototypes fabricated using the most optimal glass samples demonstrated enhanced electricity production, which was explained in terms of the fluorescent dopants incorporated into the glass, even though the authors also pointed out that further measurements are advisable. Remarkably, such samples are similar to the commercial CG, indicating that mass production could be feasible.

Another possibility of improvement of the SLS glass is the mechanical strengthening due to TiO_2 incorporation. Bengtsson et al. [48] reported a decrease in the alkali diffusion coefficient of SLS glass when Titanium is incorporated by ion exchange. This may be essential to expand the PV lifespan, as Na^+ diffusion is one of the leading causes of potential-induced degradation (PID) in these devices. It has been demonstrated that Ti films in SLS glass reduce the PID [75], and the potential to combine this feature with others, such as self-cleaning [76, 77] and anti-reflective [78] properties is quite exciting.

2.1.4. Silicates containing fluorine

The incorporation of fluorine in silicate glasses has been extensively investigated [79, 80, 81], and it is well-known that this modification reduces both glass transition and peak crystallization temperatures while also improving glass transparency. All these effects can help develop an environmentally friendly CG, as they may reduce energy inputs in glass manufacturing and enhance the sunlight power reaching the solar cells. Muniz, one of the authors of this work, has investigated silicates containing up to $\sim 20\%$ of CaF_2 [50], and rare-earth doped samples [51, 82] based on the system 50SiO_2 - $29\text{Na}_2\text{O}$ - 12.5CaO - 7.5CaF_2 - $1\text{Al}_2\text{O}_3$. Such a high Na concentration, coupled with the fluorine effect, resulted in a significant decrease in the melting temperature to only 1200°C . Down-conversion with up to $\sim 87\%$ efficiency was achieved in co-doped samples [51], and the next steps are underway to evaluate the

performance of solar panel prototypes based on this Sodium-Calcium-Silicate (SCS) glass.

Besides the results already demonstrated, this material should have its chemical and mechanical properties evaluated carefully to check if it can reach the standards needed for applications in solar panels [13]. Some critical aspects requiring investigation are the chemical stability of the glass. The dissolution of silicates in water [83, 84, 85, 86, 87, 88] is a complex phenomenon, which is likely to be altered due to the high sodium concentration [89], and the presence of fluorine, which can make it more challenging to process the material at an industrial scale.

2.1.5. Other alternatives

The number of glass systems is limitless and constantly growing and expanding. Many recent works have demonstrated interesting spectroscopic properties [90, 91, 92, 93, 94, 95, 96, 97, 98, 99], though, in many of these cases the glass composition depends on a scarce mineral (such as Te), a toxic one (such as Bi, Cd or Pb) or even result in chemically unstable materials. In this regard, though the search for innovative materials for several applications should always be pursued, for PV, more common chemistry, such as those mentioned above, seems to have the best chances. One possibility that does not seem to have been fully explored is the modification of SLS glass, such as proposed by Allsopp et al. [13], but also those including surface modification, doping by ion-exchange and others, and we believe researchers worldwide should be encouraged to do so.

3. Increasing energy outputs

The conversion of sunlight into electricity is subjected to the Carnot heat engine limit [100, 101]. As the sun is a black body at 5500°C and a Si-cell has a working temperature of about 80°C , the Carnot efficiency limit is 94% for the energy transfer from the sun to the cell [102]. However, a Si-cell is not an ideal black body. Due to its spectral sensitivity and internal losses such as electron recombination, the practical efficiency limit for PVs is about 30% [14, 15, 102, 103]. Considering these constraints, and the relatively complex and expensive processes needed to produce solar cells, it has been fundamental to expand electricity production by maximizing the sunlight reaching the cells.

3.1. Anti-reflective glass surfaces

The CG and the encapsulant material in PVs should be very transparent and exhibit proper refractive indices to reduce reflection losses. Even though sunlight is scattered when reaching the Earth, most of the power produced in PVs is related to the plane-polarized light component. The Fresnel theory states that this component will be reflected in an interface between two mediums, which can be calculated by Equation 1,

$$R_s = \left(\frac{n_1 \cos \theta_i - n_2 \sqrt{1 - \left(\frac{n_1}{n_2} \sin \theta_i \right)^2}}{n_1 \cos \theta_i + n_2 \sqrt{1 - \left(\frac{n_1}{n_2} \sin \theta_i \right)^2}} \right)^2, \quad (1)$$

where R_s is the reflection coefficient, n_1 and n_2 are the refractive indexes of the two mediums, and θ_i is the incidence angle.

Before reaching the Silicon, sunlight is subjected to air-glass, glass-encapsulant, and encapsulant-silicon interfaces. As the refractive index of Silicon is very high, to avoid $\sim 20\%$ loss in its interface, an anti-reflective coating on the Silicon surface is mandatory. On the other hand, SLS glass has a refractive index of 1.52, which results in over 4% loss by reflection for perpendicular incidence of light. Surface texturing of the CG has been explored to produce a refractive index gradient, which further reduces air-glass interface reflection. These structures may enhance the PV's efficiencies by up to 8.7% [104]. Some theoretical work has even proposed surface texturing to increase the panel's emissivity [105] as a pathway to reduce its temperature.

AR coatings based on "Moth-eye" and multiple interference films have been investigated, and several techniques to produce them have already been demonstrated [106, 107]. These and other results are fascinating; however, as PVs should withstand weathering for at least a few decades, it is fundamental to investigate the durability of these coatings under the most distinct climatic and meteorological conditions and specific conditions caused by regionally located situations. [108, 109].

3.2. Self-cleaning and multifunctional glass surfaces

PVs are supposed to produce as much electricity as possible during their lifetimes. These devices are installed literally in all continents of the Earth and, in this sense, are subject to a wide range of environments, wind, storms, etc. Soiling is an important issue [110] as it may significantly reduce the

amount of light reaching the solar cells inside the panel. This has fuelled the development of self-cleaning surfaces.

In some cases, rain is well distributed throughout the year, which can be enough to keep PVs satisfactorily clean. However, in some environments, such as dry or icy ones, even though one may have an excellent potential for solar power production, keeping the CG surfaces clean can be challenging as water may not be available [111, 112]. In the context discussed in this work, some exciting results have proposed multifunctional coatings exhibiting self-cleaning, anti-reflective, and even luminescent properties [113, 114]. We will come back to this subject on section 4.2, but next we review some research on spectral converters.

3.3. Spectral converters (SC)

In a commercial PV, most of the sunlight is converted into heat [115], and the spectral mismatch between the sunlight and silicon sensitivity plays a central role in this inefficiency [14, 15, 102, 103]. The standard 1.5G solar spectrum has an intensity of 1000 W/m^2 . Photons below the silicon bandgap ($\sim 1100\text{-}2200 \text{ nm}$) account for 164 W/m^2 [116]. Theoretically, these photons can be up-converted to higher energy ones, enabling additional sunlight to produce electricity. However, up-conversion efficiency is inherently low [117], and after extensive research on the subject in the last decades [118], there is no clear evidence of a feasible up-converter for PVs. Most experiments claiming to measure an increment in electricity output due to up-converter materials were performed in impractical conditions, often based on laser illumination and/or highly concentrated light [119]. In this way, the stokes shift is far more likely to occur than the anti-stokes shift, hence we will focus here on the spectral conversion of the above bandgap photons only.

Each incoming photon may produce a maximum of one free electron in the Si-cell by creating an electron-hole pair. Above bandgap photons, however, have excess energy that will be wasted. About 149 W/m^2 of the incoming sunlight consists of UV-blue photons ($\sim 300\text{-}450 \text{ nm}$) with at least twice the silicon bandgap energy [116]. Besides this significant loss due to energy excess, these high-energy photons are also linked to solar panel degradation [120, 121, 122, 123, 124, 125]. The electricity output could be increased if these photons were converted or split into two half-energy photons. This could modify the spectrum to enrich the NIR part, where PV is more sensitive, reducing the heat associated with the electron-hole pair creation or even

increasing the number of photons reaching the solar cell (if the SC exhibits quantum efficiency higher than one).

Most of the proposed SCs are based on rare-earth active ions, though there is plenty of research on other dopants, such as transition metals or metallic nanoparticles [126, 127]. Two main approaches concerning SC exist: developing CGs containing optically active ions and producing optically active films on top of a standard CG. Although the list of dopants being investigated is long and has been reviewed recently [126, 127], here we provide a short description of the most common ones, highlighting some key aspects of the complex task of developing a viable SC.

3.3.1. Main rare-earth dopants for spectral conversion

Ce^{3+}

Cerium is one of the most abundant rare-earths and is widely used in industrial applications such as catalysis, UV-blocking agent in glasses, etc. When incorporated into glass, it can exist in two different valence states, either Ce^{3+} or Ce^{4+} [66]. As Ce has the atomic number 58, it will have 54 electrons in its oxidized state and present full electron shells and no optical transitions.

The additional electron in the Ce^{3+} ion, though, has a 4f-5d parity allowed transition [128], which is very sensitive to the host crystal field. Absorption bands of Ce^{3+} are often observed in the UV-blue range [129], while emission bands have been reported ranging from UV-blue [130, 131] to the yellow-red parts of the visible spectrum [132]. In this way, to develop SCs for PVs, Cerium is often used to absorb UV-blue light. In most cases, it is designed to work coupled with some other ion such as Nd^{3+} [133, 134] or Yb^{3+} [135, 136, 137] which are well-known for their emission lines near the silicon sensitivity peak [115].

One of the drawbacks reported with Cerium-doped glasses is the difficulty of controlling its valence states. In most cases, the final material will have a mix of both states [138, 139, 140]. For PV applications, Ce^{4+} may be an excellent UV-blocking agent, though it may prevent spectral conversion [66].

Pr^{3+}

The Pr^{3+} energy diagram is broadly investigated as it has several absorption and emission bands between the blue and the near-infrared, including an emission line near the silicon sensitivity peak around $1\mu m$ [30]. In practice, most of the blue light absorbed by this ion will suffer a slight Stokes shift

and result in visible emission, which will barely benefit the PV efficiency. Similar to the case of Cerium, Praseodymium has been proposed to be used alongside a NIR emitter, such as Yb^{3+} [141]. Such mechanism of spectral conversion has been demonstrated experimentally [142]. The energy diagram of this ion results in a relatively narrow absorption band in the blue region due to ground state absorption to the ^3P levels. Because of that, besides co-doping schemes with a NIR emitter, Pr^{3+} has also been used as co-dopant with Ce^{3+} [143].

However, as we have pointed in a recent work [67], one should not neglect the negative impact of any ion absorption bands on a solar cell performance. Even if the spectral conversion can be observed, it has no straightforward relation to the overall efficiency of a solar cell prototype. In the case of Praseodymium doped and co-doped samples, electrons excited to the ^3P levels may result in quantum-cutting or down-conversion. However, the lower energetic $^1\text{D}_2$ level is expected to reduce the yellow-red (~ 590 nm) transmission through the sample. Even though resonant emission from this level is expected (~ 612 nm), it will also result in the emission of low-energy photons, including some with energy below the silicon bandgap [30] (for example at ~ 1480 nm).

Eu^{2+}

Europium-doped glasses will more often result in Eu^{3+} rich materials, and this valence state provides a mechanism to obtain intense red emission [36, 65, 82, 144]. This ion can sometimes be found or reduced to Eu^{2+} [51, 145], which has spectroscopical properties similar to Ce^{3+} . Indeed, Dorenbos [146, 147] have demonstrated a strong correlation between the spectroscopic properties of these two ions. Also similar to the case of Cerium, Europium has been incorporated into several different materials where often a NIR emitter co-dopant is used, such as Pr^{3+} [148], Dy^{3+} [149], Nd^{3+} [51, 150, 151] and Yb^{3+} [133].

Nd^{3+}

As previously mentioned, Nd^{3+} has been used as a NIR emitter in materials proposed as SCs for PVs [51, 133, 144, 150, 151, 152]. However, this ion has also been a donor to Yb^{3+} ions [45, 46]. Though it could be theoretically possible to perform some spectral conversion using Nd^{3+} single-doped samples, in practice, the ion has several absorption lines in the visible and NIR that are likely to have some negative impact in the spectrum reaching

the Si-cell. We will be back to this question hereafter.

Yb^{3+}

Yb^{3+} is probably the most investigated NIR emitter for PVs [45, 46, 142, 153, 154, 155, 156, 157]. The main reason for that relies on the simple energy levels diagram of this ion, which has absorption bands (between 850-1000 nm) and intense emission (between 970-1050 nm) in the NIR range. Though absorption in this region may not be beneficial for PVs [13, 158], Yb^{3+} can be excited by energy transfer from several rare-earths and transition metals [157, 159]. In the next section, we discuss the challenges related to choosing dopants.

Selecting rare earth elements for spectral converters.

As we have pointed out, several rare-earth doped materials have been investigated as a mechanism to achieve spectral conversion. In figure 1, we show a simplified representation of the main energy levels in Yb^{3+} and Nd^{3+} , which play an important role in the development of SCs.

Absorption of photons with wavelengths higher than 1100 nm is unharmed to the electrical output of PVs, as these photons have significantly low energy. As we have mentioned, the up-conversion from these photons seems unlikely and is not within the scope of this work. On the other hand, absorption in the range of 300-1100 nm is desirable only if we can increase the electrical output of the PV after the spectral modification. As the optimum sensitivity of PVs is found near the Si bandgap, there is no point in having an SC absorbing energy in this region.

Yb^{3+} is transparent in almost all silicon sensitivity range and exhibits a resonant absorption/emission matching the PV sensitivity peak. On the other hand, Nd^{3+} exhibits many absorption peaks along the UV-visible range, presenting a solid emission in the NIR region. However, the same excited level related to the emission at ~ 1064 nm is also the origin of the emission at ~ 1350 nm, below the bandgap. Nd^{3+} is also a strong absorber between 730-830 nm, a region where the down-conversion of a photon is not favorable for PV.

To the best of our knowledge, the research on both Yb^{3+} and Nd^{3+} based SCs has yet to consider the negative impacts of this ion on the overall efficiency of PVs. Most of the research has focused on optimizing the dopant concentrations to obtain higher quantum efficiencies in the conversion of

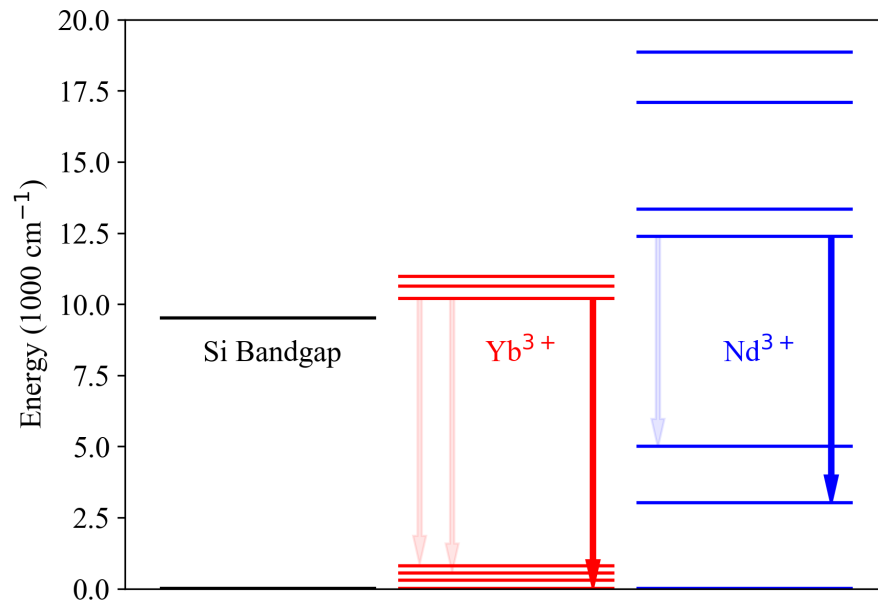


Figure 1: Representative energy levels diagram of NIR emitters for spectral conversion. Light color and dark color arrows indicate emission lines below and above the Si bandgap, respectively.

photons; however, the PV electrical output is not a function of this single variable, and neither correlates straightforwardly to it. In some materials exhibiting high conversion efficiencies, a high dopant concentration of Yb^{3+} or Nd^{3+} is used, which could reduce the electricity output of Si-cells.

It is essential to highlight that several reports on high conversion efficiencies have been demonstrated in the last few years. However, none have included experimental measurements to quantify a prototype’s electrical output under sunlight irradiation. As recently shown in a Pr^{3+} -doped tellurite glass [67], it is possible to detect rare-earth emission bands under natural light, and we believe the SCs should be evaluated under this situation. In section 3.3.3, we propose an analysis considering this goal.

As one can imagine, the list of ions that could be explored to provide UV-Blue absorption and NIR emission is extensive. Other rare-earths such as Tb^{3+} [160], Er^{3+} [161], Dy^{3+} [162], Ho^{3+} [163], Tm^{3+} [154] have also been investigated. However, as we have discussed, a “too rich” energy diagram will often result in a loss of sunlight power somewhere in the spectrum by one of two mechanisms: 1) undesirable absorption of photons or 2) undesirable emission of photons without overall gains for the electricity output.

3.3.2. Non-rare-earth ions for spectral conversion

Several transition metals (TMs) have also been investigated as active ions for spectral conversion [164, 165, 166, 167]. Some of the most exciting results reported concern the possibility of replacing cerium by a TM to block UV transmission, as Cerium may react with traces of iron in the SLS glass under UV radiation. The result, in this case, is an increase of the Fe^{2+} concentration in the CG [158], a NIR absorber that will have a deleterious effect on the PV electricity output. It has been demonstrated by using TMs [164] that significant UV blocking capabilities can be achieved, with the bonus that some TMs exhibit VIS/NIR emission, and down-conversion can potentially be achieved as well.

Silicon nanocrystals are another alternative to develop spectral converters [168]. A few different techniques to produce silicon nanocrystals are available [169, 170, 171], and some works have even demonstrated solar panel prototypes with enhanced performance [169, 171]. Authors have explained these promising results due to the conversion of UV photons into visible ones and reduced surface reflectance. Some undesirable aspects reported include a reduced transmittance of the host material with increasing nanocrystal concentration. Silicon is an abundant mineral, and some authors [171] have

demonstrated its deployment using a silica gel as a host, which could be a path to improve the efficiency of solar panels on-field.

3.3.3. A benchmark framework for spectral converters

To the best of our knowledge, there is no standardized test to measure the performance of SCs. Indeed, as we have discussed, most works proposing an SC have some information about the conversion efficiency of the absorbed light. However, they lack specific measurements of the effect of the material on the electrical output of a PV. On the other hand, we recognize how difficult it is to produce solar cell prototypes covered by the SC. It can be a resource and time-consuming task that requires a different set of skills and equipment and could introduce uncertainties in comparing different SCs. With this aim, we propose a framework for quantifying some parameters that could be used as a benchmark to compare SCs.

Our approach is based on the following considerations:

1. The Global 37° tilt ASTM-G173-03 sunlight spectrum (1.5G spectrum) is used as the reference for standard sunlight illumination.
2. The Thorlabs S120VC Si sensor responsivity spectrum is used to represent a Si solar cell spectral sensitivity.
3. The product of these two spectra represents the solar cell current output per nm under sunlight illumination.

These three curves enumerated above are shown in figure 2, for the range 280-1100 nm, with a resolution of 5 nm. The area under these curves was calculated for different sections of the data, and all of them were performed using the trapezoidal rule. The integral of the 1.5G spectrum in this range and resolution corresponds to 805.65 W/m², and as one can see, the sunlight intensity peaks at ~500 nm. On the other hand, the Si sensitivity peaks at ~1000 nm. At the bottom of the figure, we show the resulting “current output spectrum” obtained by multiplying the sunlight irradiance times the sensitivity curve.

The total area under the last curve corresponds to 24159 mA/m², and it is essential to highlight the “flat” region, between 450-900 nm, which is responsible for about 75% of the total current output (~17917 mA/m²). One fundamental insight of this approach is that, in the flat region of the current curve, its value is ~40 mA m⁻²nm⁻¹. This means a production of about 200 mA/m² for each 5 nm interval. As one can see, even a narrow absorption band may significantly affect electricity production depending on

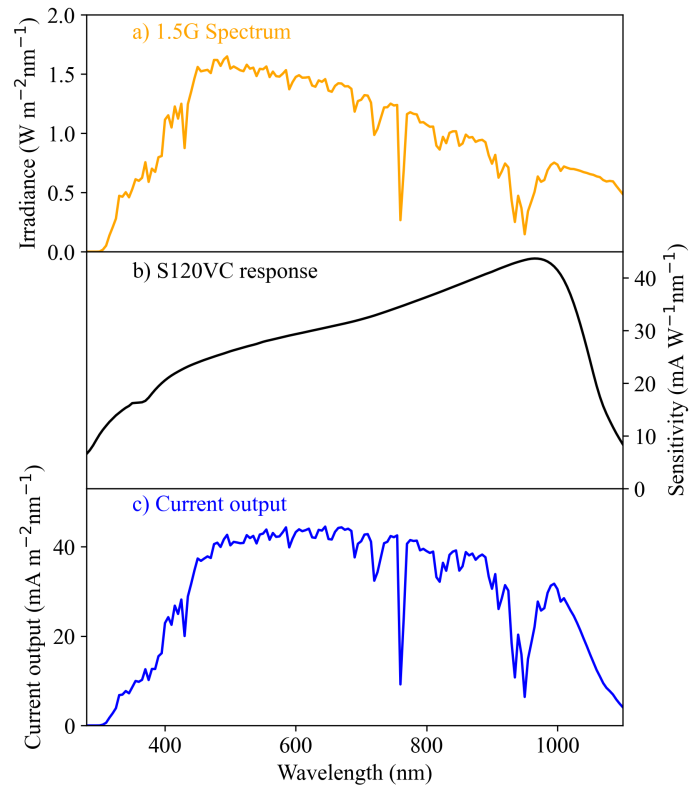


Figure 2: a) 1.5G irradiance spectrum and b) spectral sensitivity of commercial S120VC silicon sensor. The combination of these two results in a curve of c) current output of the sensor per nm of the 1.5G spectrum.

the SC thickness. This way, if we have a 5 nm narrow band in the 450-900 nm range that absorbs 50% of the incoming light, this will reduce the current output per square meter in $\sim 100 \text{ mA/m}^2$, which corresponds to about 0.41% of the current output under direct sunlight.

Using the material absorption spectrum and this current output reference curve, one can estimate the negative impact of an SC on the electricity output. To illustrate that, we evaluated the absorption data in the range 280-900 nm from a 0.1 mm thick Cerium-doped xerogel [172], and the results are shown in Figure 3.

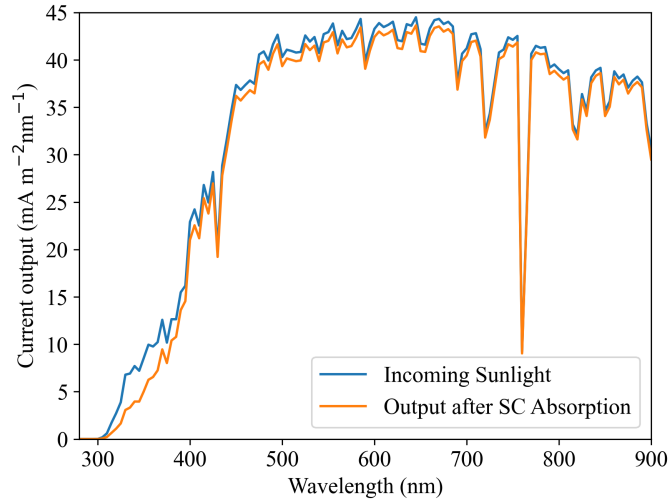


Figure 3: Calculated current output under 1.5G sunlight spectrum and the effect of a 0.1 mm thick Ce-doped xerogel based film [172].

Considering the sunlight spectrum in that range, this material applied to a PV would reduce the current output from 20114 to 19471 mA/m² due to its absorbance. From this 643 mA/m² loss, 265 mA/m² are related to wavelengths below 420 nm, demonstrating the reduction, in this case, is more significant in the UV range. This illustrates how to quantify the losses introduced by the material, though, for an SC, it is also necessary to evaluate the potential gains which can be introduced. A viable SC must add enough spectral conversion to overcome its absorption losses. In the next section, we introduce a model for an “ideal SC”, which could be used as a reference scale for different materials proposed as SCs.

3.3.4. *The ideal SC*

We can think on different types of SCs, made from different compositions and having specific spectroscopic characteristics. However, to develop our reference for an ideal SC, it is enough to consider that it exhibits the following attributes:

- Full absorption of light below a certain wavelength;
- Full transparency above this same wavelength;
- Convert all the absorbed radiation into wavelengths near the Si sensitivity peak;
- Do not introduce any other loss due to the sunlight reflection or scattering;

The immediate implication is that this ideal SC will have more photons emitted than absorbed because we are converting high-energy photons into NIR ones without generating any phonons. Though a quantum efficiency as high as this is unlikely, the above considerations are enough to provide a simple and helpful reference. On the other hand, the wavelength that delimits the absorption and transparency of the SC is arbitrary. Though, as we discussed before, 75% of the current output in our framework originates from sunlight in the range 450-900 nm, and in this way, it seems reasonable not to consider absorption near that range. In this context, we chose the wavelength limit between absorption/transparency for our ideal SC to be 420 nm.

The Si sensitivity response we are considering, as shown in Figure 2, peaks around 965 nm. An ideal SC should profit from that by emitting radiation near it. Here again, there is room for discussion on the shape and width of the SC luminescence band. A “laser-like” luminescence is quite unlikely, but on the other hand, a too-broad band would mean some photons falling below the Si bandgap. In this way, we choose a simple flat emission band between 940-990 nm, which is 50 nm wide and centered at 965 nm.

Using the reference spectra shown in Figure 2, we could evaluate some estimates of this ideal SC effect on PV performance. The main results are presented in Figure 4 and discussed next.

By integrating the irradiance spectrum below 420 nm we obtain a value of 71.85 Wm^{-2} for the total radiation absorbed by the ideal SC. This radiation

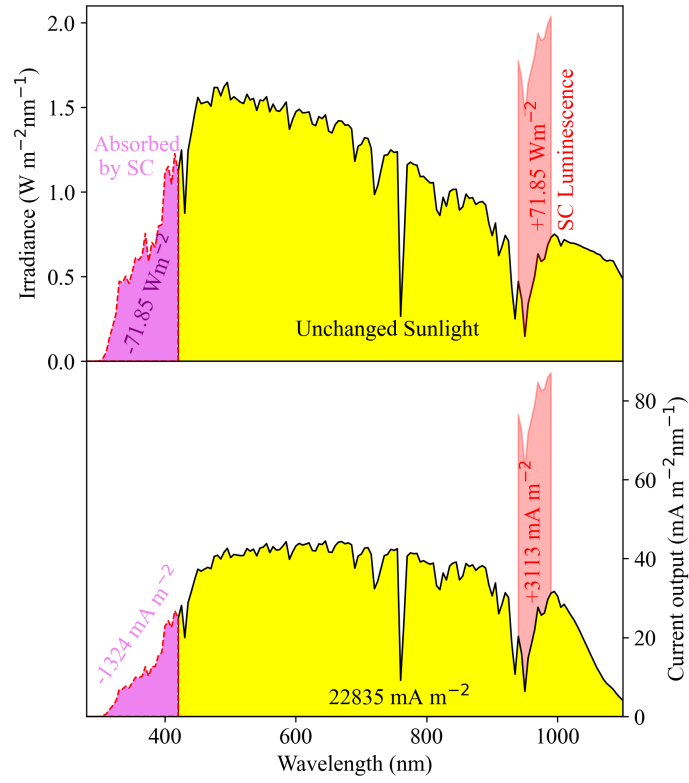


Figure 4: Ideal spectral converter (SC) effect on sunlight spectrum (top) and in the current output (bottom), demonstrating the balance between losses (at left, in purple) and the gains (at right, in red) that should remain positive for a viable SC.

would produce 1324 mA m^{-2} if it could reach the PV, and we will call it “SC current drop” (C_D). Accordingly, it represents a primary adverse effect of the SC on the PV performance. As the total current output without the SC accounts for 24159 mA m^{-2} , even for our ideal SC, the current drop is significant, corresponding to 5.5 % of the total.

However, our ideal SC is supposed to have total efficiency in converting incident radiation. Assuming this same 71.85 Wm^{-2} is emitted around 965 nm, it would produce an additional current output of about 3113 mA m^{-2} , which we will call “SC current gain” (C_G). In other words, the net effect of a SC would be,

$$C_G - C_D = C_N, \quad (2)$$

where C_N is the net current for the SC. For reference, the proposed ideal SC described above would result in $C_N = 1789 \text{ mA m}^{-2}$. This net current increment corresponds to a 7.4 % increase in the total current output (from 24159 to 25948 mA m^{-2}).

Unfortunately, collecting data from most of the materials proposed as SCs in the literature is challenging, and this review does not include a comparison between them in terms of the net current described above. We believe, though, this balance of negative and positive impacts of the SCs is critical, and its evaluation under our proposed framework can accelerate the development of SCs and be helpful to all researchers in this field.

In summary, our framework to characterize and compare materials proposed as SCs can be split into the following steps:

1. Measure the material absorption spectrum;
2. Define a thickness, depending on how this material is intended to be deployed in PV (nanometer/micrometer film, thick sample, etc);
3. Calculate the absorbance spectrum for this specific material and thickness.
4. Calculate C_D , due to this absorbance spectrum;
5. Estimate the C_G , due to SC luminescence;
6. Obtain the C_N associated to the SC.

We intentionally used the term “estimate” for the fifth step, recognizing the complexity of measuring or calculating luminescence. Even though luminescence can be quantified for one sample in a specific range, measuring it from the visible to the infrared often requires different sensors, gratings, etc. It may be challenging to have calibrated equipment to perform luminescence

measurements in such a broad range. Comparing the luminescence intensity between several samples can be even more difficult, as reflection and scattering of the pump source and luminescent light self-absorption may vary among them (mainly for SCs containing resonant emitters, such as Yb^{3+}).

4. Emerging trends

4.1. Lowering carbon emission with Hydrogen

Scientists are pursuing to reduce CO_2 emissions related to glass production by replacing natural gas used in the float process. One of the most promising approaches is replacing natural gas with hydrogen, though this also looks challenging. The energy content of these two gases is significantly different, and the combustion of each one results in different amounts of heat transfer through radiation. The modified atmosphere composition inside the furnace also seems to increase the water and NO_x content. Consequently, recent studies have addressed the effect of this hydrogen-modified float process on the optical quality of the final glass sheet [173, 174, 175].

By one hand it seems interesting to look for alternatives to the SLS glass, or modify it. However, by another, it seems likely that the float process itself will need adjustments to become greener. In both cases, there are plenty of work for the glass science community in understanding and proposing methods to optimize the quality of the float glass in light of this new challenge to fit the industry inside environmental boundaries.

4.2. Alternative materials and methods

A modern float SLS industry produces several thousand square meters of glass per hour [67], and some thin films may be produced inline with the process by chemical vapor deposition (CVD). Though this enables fast and cheap production of coatings, many other cannot be produced by the CVD method. In such a context, here we highlight some recent studies concerning materials, often produced by alternative methods, which are proposed for PV applications.

Besides several glassy films [45, 176, 177] and glass-polymer matrices [172, 178, 179], one may find several innovative methods to introduce dopants [82] and coatings [180, 181] which include even the use of organic molecules such as Chlorophyll [181]. As one can see, even though there are robust materials and techniques available at the industry level, the need to decarbonize the industry [173, 182, 175], expand PV lifespan and efficiency as well as increase

the reuse [183] and recyclability [184, 185, 186] of glass indicates a wide range of possibilities to be explored by glass scientists.

5. Discussion

Glass is undoubtedly an essential part of PV devices, and there is room for glass-related breakthroughs that could result in expanded net energy production of silicon based solar electricity. There is the possibility to develop CGs with reduced energy intensity and the need to reduce emissions from the flat glass production process.

On the other hand, particular features, such as self-cleaning and anti-reflective coatings, are already available at the industry level. Others, such as SCs still in the early research and development stage. Regarding this latter one, there are countless works published in the last few decades, though the different techniques and methods used to characterize SC materials make it quite hard to compare them.

Based on this fact, we proposed a benchmark framework for SCs, that could also be applied to UV filters for PV. As we have demonstrated, even narrow absorption bands can significantly affect the current output, mainly if those bands are between 450-900 nm. Our framework considers the ASTM-G173-03 sunlight spectrum and a commercial Si sensor response, resulting in a “current output spectrum” more suitable for comparing spectrally selective materials. Such a model seems straightforward and effective. If we aim to use a material to cover PVs, one should consider the spectral response of silicon and the overall net effect of this material in the electrical output.

As we have discussed in a previous work [67], a class AAA solar simulator should reproduce the solar irradiance within a margin of $\pm 25\%$ in six bands of the spectrum (five 100 nm wide and the last one between 900 and 1100 nm), using the AM1.5G as reference. Though such an approach is fundamental at the industry level to evaluate PVs, this low-resolution analysis is inadequate to compare and develop spectrally selective materials, namely SCs and UV filters. As demonstrated here, even a narrow absorption band just 5 nm wide of a cover material can significantly reduce the PV current output. The proposed model is an essential step towards a standard for theoretically and experimentally comparing different SCs.

Considering some of the emerging trends presented in this review, it seems clear that the glass industry is again looking for a revolution. If, on the one hand, there are not yet a candidate glass to replace the SLS in PVs, the

need to decarbonize the glass industry by developing a fossil fuel-free float glass process is itself a breakthrough. This could also be an opportunity to develop a modified-SLS glass more suitable to this new environmentally friendly process or even to develop new glass systems.

In conclusion, continued research and development in the field of spectrally selective materials could lead to significant advancements in the efficiency and sustainability of PV technology, ultimately contributing to a cleaner and greener future.

6. Conclusion

In this work, the literature on cover glasses and spectral converters has been reviewed. Several new glasses, glass ceramics, and multi-functional thin films have been investigated for PV applications in the last few years, and promising results have been reported. However, the quantitative comparison between these materials has not been performed correctly. There is a lack of standardized parameters to enable scientists to do so, which we propose here, as an instructive model for standardization.

Considering the AM1.5G solar spectrum and the Si's spectral response, our model enables a path to quantify the effect of these new materials on PV's electrical output, no matter where the absorption and emission bands are located. By calculating both the current drop and gain due to the SC, we can theoretically evaluate the effect of the spectral properties of the material on the electrical output. There are no restrictions to the material's geometry, so the model can also compare bulk and thin film materials.

The solar photovoltaic industry remains focused on Silicon technology. There are predictions of a critical increment in the share of bifacial solar panels in the following decades, evidencing we can expect an increment in flat glass demand for this sector. In this context, innovation is needed as it is mandatory to decarbonize the glass industry as soon as possible. Such a challenging task may be accomplished by replacing natural gas in the float process and developing modified SLS glasses. Besides that, expanding the efficiency or the lifespan of PVs will also contribute to reducing the environmental impact and, consequently, the cost of solar power worldwide.

This contribution summarizes the role of the cover glass in PVs, highlighting some of the most recent and exciting research results of glassy materials for solar silicon photovoltaic applications. The glass community has plenty

of opportunities to develop new materials and processes that may reduce our carbon emissions and environmental footprint.

7. Acknowledgement

The authors would like to thank the *Conselho Nacional de Desenvolvimento Científico e Tecnológico* (CNPq), Brazil, grant 409475/2021-1, and the Central de Análises laboratory in UTFPR-PB.

References

- [1] C. D. Westbrook, J. Bitting, M. Craglia, J. M. C. Azevedo, J. M. Cullen, Global material flow analysis of glass: From raw materials to end of life, *Journal of Industrial Ecology* 25 (2) (2021) 333–343. doi:10.1111/jiec.13112.
URL <https://onlinelibrary.wiley.com/doi/10.1111/jiec.13112>
- [2] N. M. Haegel, R. Margolis, T. Buonassisi, D. Feldman, A. Froitzheim, R. Garabedian, M. Green, S. Glunz, H.-m. Henning, B. Holder, I. Kaizuka, B. Kroposki, K. Matsubara, S. Niki, K. Sakurai, R. A. Schindler, W. Tumas, E. R. Weber, G. Wilson, M. Woodhouse, S. Kurtz, Terawatt-scale photovoltaics: Trajectories and challenges, *Science* 356 (6334) (2017) 141–143. doi:10.1126/science.aal1288.
URL <http://www.sciencemag.org/lookup/doi/10.1126/science.aal1288>
- [3] P. J. Verlinden, Future challenges for photovoltaic manufacturing at the terawatt level, *Journal of Renewable and Sustainable Energy* 12 (5) (2020). doi:10.1063/5.0020380.
- [4] International Technology Roadmap for Photovoltaic (ITRPV) 2022, Tech. rep. (2022).
- [5] A. Sinha, D. B. Sulas-Kern, M. Owen-Bellini, L. Spinella, S. Uličná, S. Ayala Pelaez, S. Johnston, L. T. Schelhas, Glass/glass photovoltaic module reliability and degradation: a review, *Journal of Physics D: Applied Physics* 54 (41) (2021) 413002. doi:10.1088/1361-6463/ac1462.
URL <https://iopscience.iop.org/article/10.1088/1361-6463/ac1462>

- [6] N. M. Haegel, H. Atwater, T. Barnes, C. Breyer, A. Burrell, Y.-M. Chiang, S. De Wolf, B. Dimmler, D. Feldman, S. Glunz, J. C. Goldschmidt, D. Hochschild, R. Inzunza, I. Kaizuka, B. Kroposki, S. Kurtz, S. Leu, R. Margolis, K. Matsubara, A. Metz, W. K. Metzger, M. Morjaria, S. Niki, S. Nowak, I. M. Peters, S. Philipps, T. Reindl, A. Richter, D. Rose, K. Sakurai, R. Schlatmann, M. Shikano, W. Sinke, R. Sinton, B. Stanbery, M. Topic, W. Tumas, Y. Ueda, J. van de Lagemaat, P. Verlinden, M. Vetter, E. Warren, M. Werner, M. Yamaguchi, A. W. Bett, Terawatt-scale photovoltaics: Transform global energy, *Science* 364 (6443) (2019) 836–838. doi:10.1126/science.aaw1845.
- [7] S. Davidsson, M. Höök, Material requirements and availability for multi-terawatt deployment of photovoltaics, *Energy Policy* 108 (June) (2016) 574–582. doi:10.1016/j.enpol.2017.06.028.
URL <http://dx.doi.org/10.1016/j.enpol.2017.06.028>
- [8] C. S. Tao, J. Jiang, M. Tao, Natural resource limitations to terawatt-scale solar cells, *Solar Energy Materials and Solar Cells* 95 (12) (2011) 3176–3180. doi:10.1016/j.solmat.2011.06.013.
URL <http://dx.doi.org/10.1016/j.solmat.2011.06.013>
- [9] S. Davidsson, M. Höök, Material requirements and availability for multi-terawatt deployment of photovoltaics, *Energy Policy* 108 (December 2016) (2017) 574–582. doi:10.1016/j.enpol.2017.06.028.
URL <https://linkinghub.elsevier.com/retrieve/pii/S0301421517303798>
- [10] M. D. Bazilian, The mineral foundation of the energy transition, *Extractive Industries and Society* 5 (1) (2018) 93–97. doi:10.1016/j.exis.2017.12.002.
URL <http://dx.doi.org/10.1016/j.exis.2017.12.002>
- [11] K. Burrows, V. Fthenakis, Glass needs for a growing photovoltaics industry, *Solar Energy Materials and Solar Cells* 132 (2015) 455–459. doi:10.1016/j.solmat.2014.09.028.
URL <http://dx.doi.org/10.1016/j.solmat.2014.09.028>
- [12] D. D. Furszyfer Del Rio, B. K. Sovacool, A. M. Foley, S. Griffiths, M. Bazilian, J. Kim, D. Rooney, Decarbonizing the glass industry:

A critical and systematic review of developments, sociotechnical systems and policy options, *Renewable and Sustainable Energy Reviews* 155 (November 2021) (2022) 111885. doi:10.1016/j.rser.2021.111885.

URL <https://doi.org/10.1016/j.rser.2021.111885>

- [13] B. L. Allsopp, R. Orman, S. R. Johnson, I. Baistow, G. Sanderson, P. Sundberg, C. Stålhandske, L. Grund, A. Andersson, J. Booth, P. A. Bingham, S. Karlsson, Towards improved cover glasses for photovoltaic devices, *Progress in Photovoltaics: Research and Applications* 28 (11) (2020) 1187–1206. doi:10.1002/pip.3334.
- [14] W. Shockley, H. J. Queisser, Detailed balance limit of efficiency of p-n junction solar cells, *Journal of Applied Physics* 32 (3) (1961) 510–519. doi:10.1063/1.1736034.
- [15] J.-F. Guillemoles, T. Kirchartz, D. Cahen, U. Rau, Guide for the perplexed to the Shockley–Queisser model for solar cells, *Nature Photonics* 13 (8) (2019) 501–505. doi:10.1038/s41566-019-0479-2.
URL <http://www.nature.com/articles/s41566-019-0479-2>
- [16] C. A. S. Hall, J. G. Lambert, S. B. Balogh, EROI of different fuels and the implications for society, *Energy Policy* 64 (2014) 141–152. doi:10.1016/j.enpol.2013.05.049.
URL <http://dx.doi.org/10.1016/j.enpol.2013.05.049>
- [17] K. P. Bhandari, J. M. Collier, R. J. Ellingson, D. S. Apul, Energy payback time (EPBT) and energy return on energy invested (EROI) of solar photovoltaic systems: A systematic review and meta-analysis, *Renewable and Sustainable Energy Reviews* 47 (2015) 133–141. doi:10.1016/j.rser.2015.02.057.
URL <http://dx.doi.org/10.1016/j.rser.2015.02.057>
- [18] K. P. Bhandari, J. M. Collier, R. J. Ellingson, D. S. Apul, Energy payback time (EPBT) and energy return on energy invested (EROI) of solar photovoltaic systems: A systematic review and meta-analysis (2015). doi:10.1016/j.rser.2015.02.057.
- [19] M. Diesendorf, T. Wiedmann, Implications of Trends in Energy Return on Energy Invested (EROI) for Transitioning to Renewable Electric-

- ity, *Ecological Economics* 176 (oct 2020). doi:10.1016/j.ecolecon.2020.106726.
- [20] Z. Zhou, M. Carbajales-Dale, Assessing the photovoltaic technology landscape: Efficiency and energy return on investment (EROI), *Energy and Environmental Science* 11 (3) (2018) 603–608. doi:10.1039/c7ee01806a.
 - [21] L. A. B. Pilkington, Review Lecture: The float glass process, *Proceedings of the Royal Society of London. A. Mathematical and Physical Sciences* 314 (1516) (1969) 1–25. doi:10.1098/rspa.1969.0212.
URL <https://royalsocietypublishing.org/doi/10.1098/rspa.1969.0212>
 - [22] M. L. F. Nascimento, Brief history of the flat glass patent – Sixty years of the float process, *World Patent Information* 38 (2014) 50–56. doi:10.1016/j.wpi.2014.04.006.
URL <https://linkinghub.elsevier.com/retrieve/pii/S0172219014000507>
 - [23] R. E. Youngman, Borosilicate Glasses, in: *Encyclopedia of Glass Science, Technology, History, and Culture*, Vol. 35, Wiley, 2021, pp. 867–878. doi:10.1002/9781118801017.ch7.6.
URL <https://onlinelibrary.wiley.com/doi/10.1002/9781118801017.ch7.6>
 - [24] D. Manara, A. Grandjean, D. R. Neuville, Structure of borosilicate glasses and melts: A revision of the Yun, Bray and Dell model, *Journal of Non-Crystalline Solids* 355 (50-51) (2009) 2528–2531. doi:10.1016/j.jnoncrysol.2009.08.033.
 - [25] F. Angeli, O. Villain, S. Schuller, T. Charpentier, D. De Ligny, L. Bressel, L. Wondraczek, Effect of temperature and thermal history on borosilicate glass structure, *Physical Review B - Condensed Matter and Materials Physics* 85 (5) (feb 2012). doi:10.1103/PhysRevB.85.054110.
 - [26] N. J. Tostanoski, D. Möncke, R. Youngman, S. K. Sundaram, Structure-terahertz property relationship in sodium borosilicate

- glasses, *International Journal of Applied Glass Science* (2022). doi: 10.1111/ijag.16608.
- [27] D. E. Perea, D. K. Schreiber, J. V. Ryan, M. G. Wirth, L. Deng, X. Lu, J. Du, J. D. Vienna, Tomographic mapping of the nanoscale water-filled pore structure in corroded borosilicate glass, *npj Materials Degradation* 4 (1) (dec 2020). doi:10.1038/s41529-020-0110-5.
- [28] H. Zhu, F. Wang, Q. Liao, D. Liu, Y. Zhu, Structure features, crystallization kinetics and water resistance of borosilicate glasses doped with CeO₂, *Journal of Non-Crystalline Solids* 518 (2019) 57–65. doi: 10.1016/j.jnoncrysol.2019.04.044.
- [29] Y. Guyot, A. Steimacher, M. P. M. Belançon, A. A. N. Medina, M. M. L. Baesso, S. S. M. Lima, L. L. H. C. Andrade, A. Brenier, A.-M. A.-M. Jurdyc, G. Boulon, Spectroscopic properties, concentration quenching, and laser investigations of Yb³⁺-doped calcium aluminosilicate glasses, *Journal of the Optical Society of America B* 28 (10) (2011) 2510. doi:10.1364/JOSAB.28.002510.
URL <https://www.osapublishing.org/abstract.cfm?URI=josab-28-10-2510><https://opg.optica.org/abstract.cfm?URI=josab-28-10-2510>
- [30] M. P. Belançon, J. D. Marconi, M. F. Ando, L. C. Barbosa, Near-IR emission in Pr³⁺ single doped and tunable near-IR emission in Pr³⁺/Yb³⁺ codoped tellurite tungstate glasses for broadband optical amplifiers, *Optical Materials* 36 (6) (2014) 1020–1026.
- [31] P. Dragic, T. Hawkins, P. Foy, S. Morris, J. Ballato, Sapphire-derived all-glass optical fibres, *Nature Photonics* 6 (9) (2012) 629–635. doi: 10.1038/nphoton.2012.182.
URL <http://dx.doi.org/10.1038/nphoton.2012.182>
- [32] M. P. Belançon, M. F. Ando, J. D. Marconi, H. N. Yoshimura, E. F. Chillice, L. C. Barbosa, H. L. Fragnito, Tellurite microstructured optical fibers doped with rare-earths for optical amplification, in: *Workshop on Specialty Optical Fibers and their Applications*, OSA, Washington, D.C., 2013, p. F2.25. doi:10.1364/WSOF.2013.F2.25.
URL <https://opg.optica.org/abstract.cfm?URI=WSOF-2013-F2.25>

- [33] J. Zhong, D. Chen, Y. Peng, Y. Lu, X. Chen, X. Li, Z. Ji, A review on nanostructured glass ceramics for promising application in optical thermometry, *Journal of Alloys and Compounds* 763 (2018) 34–48. doi:10.1016/j.jallcom.2018.05.348. URL <https://doi.org/10.1016/j.jallcom.2018.05.348>
- [34] B. Du, Z. Tong, X. Mu, J. Xu, S. Liu, Z. Liu, W. Cao, Z. M. Qi, A potassium ion-exchanged glass optical waveguide sensor locally coated with a crystal violet-sio2 gel film for real-time detection of organophosphorus pesticides simulant, *Sensors (Switzerland)* 19 (19) (2019) 1–12. doi:10.3390/s19194219.
- [35] S. Y. Z. Chen, W. H. Song, J. K. Cao, F. F. Hu, H. Guo, Highly sensitive optical thermometer based on FIR technique of transparent NaY2F7:Tm³⁺/Yb³⁺ glass ceramic, *Journal of Alloys and Compounds* 825 (2020) 154011. doi:10.1016/j.jallcom.2020.154011. URL <https://doi.org/10.1016/j.jallcom.2020.154011>
- [36] M. Sandrini, R. F. Muniz, V. S. Zanuto, F. Pedrochi, Y. Guyot, A. C. Bento, M. L. Baesso, A. Steimacher, A. M. Neto, Enhanced and tunable white light emission from Ag nanoclusters and Eu³⁺-co-doped CaBaAl glasses, *RSC Advances* 8 (61) (2018) 35263–35270. doi:10.1039/c8ra07114d.
- [37] L.-Y. Chen, W.-C. Cheng, C.-C. Tsai, Y.-C. Huang, Y.-S. Lin, W.-H. Cheng, High-performance glass phosphor for white-light-emitting diodes via reduction of Si-Ce³⁺:YAG inter-diffusion, *Optical Materials Express* 4 (1) (2014) 121. doi:10.1364/OME.4.000121. URL <https://www.osapublishing.org/ome/abstract.cfm?uri=ome-4-1-121>
- [38] H. Wang, Y. Mou, Y. Peng, Y. Zhang, A. Wang, L. Xu, H. Long, M. Chen, J. Dai, C. Chen, Fabrication of phosphor glass film on aluminum plate by using lead-free tellurite glass for laser-driven white lighting, *Journal of Alloys and Compounds* 814 (2020) 152321. doi:10.1016/j.jallcom.2019.152321. URL <https://doi.org/10.1016/j.jallcom.2019.152321>
- [39] J. G. Kang, M. K. Kim, K. B. Kim, Preparation and luminescence characterization of GGAG:Ce³⁺,B³⁺ for a white light-emitting

- diode, *Materials Research Bulletin* 43 (8-9) (2008) 1982–1988. doi:10.1016/j.materresbull.2007.10.001.
URL <http://linkinghub.elsevier.com/retrieve/pii/S0025540807004400>
- [40] L. G. Silveira, L. F. Cótica, I. A. Santos, M. P. Belançon, J. H. Rohling, M. L. Baesso, Processing and luminescence properties of Ce:Y3Al5O12 and Eu:Y3Al5O12 ceramics for white-light applications, *Materials Letters* 89 (2012) 86–89. doi:10.1016/j.matlet.2012.08.106.
URL <http://linkinghub.elsevier.com/retrieve/pii/S0167577X12012268>
<https://linkinghub.elsevier.com/retrieve/pii/S0167577X12012268>
- [41] S. Yi, W. J. Chung, J. Heo, Phosphor-in-glasses composites containing light diffusers for high color uniformity of white-light-emitting diodes, *Journal of Solid State Lighting* 2 (1) (2015) 4–9. doi:10.1186/s40539-015-0027-8.
URL <http://dx.doi.org/10.1186/s40539-015-0027-8>
- [42] Q. Q. Zhu, X. Xu, L. Wang, Z. F. Tian, Y. Z. Xu, N. Hirosaki, R. J. Xie, A robust red-emitting phosphor-in-glass (PiG) for use in white lighting sources pumped by blue laser diodes, *Journal of Alloys and Compounds* 702 (2017) 193–198. doi:10.1016/j.jallcom.2017.01.256.
URL <http://dx.doi.org/10.1016/j.jallcom.2017.01.256>
- [43] P. Zheng, S. Li, L. Wang, T. L. Zhou, S. You, T. Takeda, N. Hirosaki, R. J. Xie, Unique Color Converter Architecture Enabling Phosphor-in-Glass (PiG) Films Suitable for High-Power and High-Luminance Laser-Driven White Lighting, *ACS Applied Materials and Interfaces* 10 (17) (2018) 14930–14940. doi:10.1021/acsami.8b03168.
- [44] M. Sandrini, R. F. Muniz, V. S. Zanuto, J. R. Marques Viana, R. D. Bini, J. H. Rohling, M. L. Baesso, A. Medina Neto, Glass frits as an enabler in the production process of OH⁻-free calcium aluminosilicate glasses, *Journal of Alloys and Compounds* 816 (2020) 152651. doi:10.1016/j.jallcom.2019.152651.
URL <https://linkinghub.elsevier.com/retrieve/pii/S0925838819338976>

- [45] E. L. Savi, R. F. Muniz, A. A. J. Silva, G. J. Schiavon, J. W. Berrar, F. R. Estrada, P. Schio, J. C. Cezar, J. H. Rohling, V. S. Zanuto, A. C. Bento, A. N. Medina, L. A. O. Nunes, M. L. Baesso, Thin-film of Nd $3+$ -Yb $3+$ co-doped low silica calcium aluminosilicate glass grown by a laser deposition technique, *Journal of Applied Physics* 131 (5) (2022) 055304. doi:10.1063/5.0067794.
URL <https://aip.scitation.org/doi/10.1063/5.0067794>
- [46] Y. Tai, X. Li, B. Pan, Efficient near-infrared down conversion in Nd $3+$ -Yb $3+$ co-doped transparent nanostructured glass ceramics for photovoltaic application, *Journal of Luminescence* 195 (September 2017) (2018) 102–108. doi:10.1016/j.jlumin.2017.10.051.
URL <https://doi.org/10.1016/j.jlumin.2017.10.051>
- [47] H. Fu, S. Cui, Q. Luo, X. Qiao, X. Fan, X. Zhang, Broad-band downshifting luminescence of Cr $3+$ /Yb $3+$ -codoped fluorosilicate glass, *Journal of Non-Crystalline Solids* 358 (9) (2012) 1217–1220. arXiv:\protect\vrulewidth0pt\protect\href{http://arxiv.org/abs/1209.4226}{arXiv:1209.4226}v1, doi:10.1016/j.jnoncrysol.2012.02.024.
URL <http://dx.doi.org/10.1016/j.jnoncrysol.2012.02.024>
- [48] F. Bengtsson, I. B. Pehlivan, L. Österlund, S. Karlsson, Alkali ion diffusion and structure of chemically strengthened TiO 2 doped soda-lime silicate glass, *Journal of Non-Crystalline Solids* 586 (January) (2022). doi:10.1016/j.jnoncrysol.2022.121564.
- [49] A. N. Babkina, K. S. Zyryanova, D. A. Agafonova, R. K. Nuryev, A. I. Ignatiev, D. Valiev, The effect of chromium concentration on luminescent properties of alkali-alumina-borate glass-ceramics, *Journal of Non-Crystalline Solids* 521 (June) (2019) 119487. doi:10.1016/j.jnoncrysol.2019.119487.
URL <https://doi.org/10.1016/j.jnoncrysol.2019.119487>
- [50] R. F. Muniz, V. O. Soares, G. H. Montagnini, A. N. Medina, M. L. Baesso, Thermal, optical and structural properties of relatively depolymerized sodium calcium silicate glass and glass-ceramic containing CaF 2 , *Ceramics International* 47 (17) (2021) 24966–24972. doi:10.1016/j.ceramint.2021.05.224.
URL <https://doi.org/10.1016/j.ceramint.2021.05.224>

- [51] R. F. Muniz, A. Steimacher, F. Pedrochi, V. S. Zanuto, L. M. Azevedo, J. H. Rohling, M. L. Baesso, A. N. Medina, Eu²⁺-Nd³⁺ co-doped glasses for solar spectrum modification via NUV/visible to NIR down-conversion, *Journal of Alloys and Compounds* 888 (2021) 161484. doi:10.1016/j.jallcom.2021.161484.
URL <https://doi.org/10.1016/j.jallcom.2021.161484>
- [52] S. Gómez, I. Urra, R. Valiente, F. Rodríguez, Spectroscopic study of Cu²⁺/Cu⁺ doubly doped and highly transmitting glasses for solar spectral transformation, *Solar Energy Materials and Solar Cells* 95 (8) (2011) 2018–2022. doi:10.1016/j.solmat.2010.07.022.
URL <https://linkinghub.elsevier.com/retrieve/pii/S0927024810004472>
- [53] S. Gómez-Salces, J. A. Barreda-Argüeso, R. Valiente, F. Rodríguez, A study of Ce³⁺ to Mn²⁺ energy transfer in high transmission glasses using time-resolved spectroscopy, *Journal of Materials Chemistry C* 4 (38) (2016) 9021–9026. doi:10.1039/c6tc01408a.
- [54] L. Yuliantini, N. Nursam, L. Pranoto, Shobih, J. Hidayat, R. Sova, Isnaeni, E. Rahayu, M. Djamal, P. Yasaka, K. Boonin, J. Kaewkhao, Photon up-conversion in er³⁺ ion-doped zno-al₂o₃-bao-b₂o₃ glass for enhancing the performance of dye-sensitized solar cells, *Journal of Alloys and Compounds* 954 (2023) 170163. doi:<https://doi.org/10.1016/j.jallcom.2023.170163>.
URL <https://www.sciencedirect.com/science/article/pii/S0925838823014664>
- [55] R. Reisfeld, L. Boehm, Energy transfer between samarium and europium in phosphate glasses, *Journal of Solid State Chemistry* 4 (3) (1972) 417–424. doi:10.1016/0022-4596(72)90157-0.
URL <https://linkinghub.elsevier.com/retrieve/pii/0022459672901570>
- [56] R. REISFELD, S. NEUMAN, Planar solar energy converter and concentrator based on uranyl-doped glass, *Nature* 274 (5667) (1978) 144–145. doi:10.1038/274144a0.
URL <http://www.nature.com/articles/274144a0>

- [57] R. Reisfeld, Y. Kalisky, Improved planar solar converter based on uranyl neodymium and holmium glasses, *Nature* 283 (5744) (1980) 281–282. doi:10.1038/283281a0.
URL <http://www.nature.com/articles/283281a0>
- [58] A. Pan, A. Ghosh, New family of lead-bismuthate glass with a large transmitting window, *Journal of Non-Crystalline Solids* 271 (1) (2000) 157–161. doi:10.1016/S0022-3093(00)00111-3.
- [59] A. K. Rufino Souza, A. P. Langaro, J. R. Silva, F. B. Costa, K. Yukimitu, J. C. Silos Moraes, L. Antonio de Oliveira Nunes, L. Humberto da Cunha Andrade, S. M. Lima, On the efficient Te^{4+} - Yb^{3+} cooperative energy transfer mechanism in tellurite glasses: A potential material for luminescent solar concentrators, *Journal of Alloys and Compounds* 781 (2019) 1119–1126. doi:10.1016/j.jallcom.2018.12.038.
URL <https://linkinghub.elsevier.com/retrieve/pii/S0925838818345961>
- [60] R. L. Leonard, S. K. Gray, S. D. Albritton, L. N. Brothers, R. M. Cross, A. N. Eastes, H. Y. Hah, H. S. James, J. E. King, S. R. Mishra, J. A. Johnson, Rare earth doped downshifting glass ceramics for photovoltaic applications, *Journal of Non-Crystalline Solids* 366 (1) (2013) 1–5. doi:10.1016/j.jnoncrysol.2013.01.029.
URL <http://dx.doi.org/10.1016/j.jnoncrysol.2013.01.029>
- [61] B. Ahrens, S. Brand, T. Büchner, P. Darr, S. Schoenfelder, C. Paßlick, S. Schweizer, Mechanical properties of fluorozirconate-based glass ceramics for medical and photovoltaic applications, *Journal of Non-Crystalline Solids* 357 (11-13) (2011) 2264–2267. doi:10.1016/j.jnoncrysol.2010.11.084.
URL <http://dx.doi.org/10.1016/j.jnoncrysol.2010.11.084>
- [62] M. M. Taniguchi, V. S. Zanuto, P. N. Portes, L. C. Malacarne, N. G. C. Astrath, J. D. Marconi, M. P. Belançon, Glass engineering to enhance Si solar cells: A case study of Pr^{3+} - Yb^{3+} codoped tellurite-tungstate as spectral converter, *Journal of Non-Crystalline Solids* 526 (September) (2019) 119717. doi:10.1016/j.jnoncrysol.2019.119717.
URL [10.1016/j.jnoncrysol.2019.119717https://linkinghub.elsevier.com/retrieve/pii/S0022309319305885](https://linkinghub.elsevier.com/retrieve/pii/S0022309319305885)

- [63] B. Han, Y. Yang, J. Wu, J. Wei, Z. Li, Y. Mai, Al₂O₃:Cr³⁺/tellurite glass composites: An efficient light converter for silicon solar cell, *Ceramics International* 41 (9) (2015) 12267–12272. doi:10.1016/j.ceramint.2015.06.050.
URL <https://linkinghub.elsevier.com/retrieve/pii/S0272884215011669>
- [64] X. Zhou, J. Shen, Y. Wang, Z. Feng, R. Wang, L. Li, S. Jiang, X. Luo, An Efficient Dual-Mode Solar Spectral Modification for c-Si Solar Cells in Tm³⁺/Yb³⁺ Codoped Tellurite Glasses, *Journal of the American Ceramic Society* 99 (7) (2016) 2300–2305. doi:10.1111/jace.14133.
URL <http://doi.wiley.com/10.1111/jace.14133>
- [65] J. A. Garcia, L. Bontempo, L. A. Gomez-Malagon, L. R. Kassab, Efficiency boost in Si-based solar cells using tellurite glass cover layer doped with Eu³⁺ and silver nanoparticles, *Optical Materials* 88 (November 2018) (2019) 155–160. doi:10.1016/j.optmat.2018.11.028.
URL <https://doi.org/10.1016/j.optmat.2018.11.028>
- [66] M. M. Taniguchi, E. da Silva, M. A. T. da Silva, L. S. Herculano, R. F. Muniz, M. Sandrini, M. P. Belançon, The role of Ce³⁺/Ce⁴⁺ in the spectroscopic properties of cerium oxide doped zinc-tellurite glasses prepared under air, *Journal of Non-Crystalline Solids* 547 (July) (2020) 120307. doi:10.1016/j.jnoncrysol.2020.120307.
URL <https://doi.org/10.1016/j.jnoncrysol.2020.120307><https://linkinghub.elsevier.com/retrieve/pii/S0022309320304191>
- [67] M. Belançon, M. Sandrini, H. Muniz, L. Herculano, G. Lukasiewicz, E. Savi, O. Capeloto, L. Malacarne, N. Astrath, M. Baesso, G. Schiavon, A. Silva Junior, J. Marconi, Float, borosilicate and tellurites as cover glasses in Si photovoltaics: Optical properties and performances under sunlight, *Journal of Physics and Chemistry of Solids* 161 (March 2021) (2022) 110396. doi:10.1016/j.jpcs.2021.110396.
URL <https://doi.org/10.1016/j.jpcs.2021.110396><https://linkinghub.elsevier.com/retrieve/pii/S0022369721004625>
- [68] A. Bosio, S. Pasini, N. Romeo, The History of Photovoltaics with Emphasis on CdTe Solar Cells and Modules, *Coatings* 10 (4) (2020) 344.

doi:10.3390/coatings10040344.

URL <https://www.mdpi.com/2079-6412/10/4/344>

- [69] T. Graedel, On the Future Availability of the Energy Metals, *Annual Review of Materials Research* 41 (1) (2011) 323–335. doi:10.1146/annurev-matsci-062910-095759.
URL <http://www.annualreviews.org/doi/10.1146/annurev-matsci-062910-095759>
- [70] T. E. Graedel, E. M. Harper, N. T. Nassar, P. Nuss, B. K. Reck, B. L. Turner, Criticality of metals and metalloids, *Proceedings of the National Academy of Sciences of the United States of America* 112 (14) (2015) 4257–4262. doi:10.1073/pnas.1500415112.
- [71] K. Zhang, A. N. Kleit, A. Nieto, An economics strategy for criticality – Application to rare earth element Yttrium in new lighting technology and its sustainable availability, *Renewable and Sustainable Energy Reviews* 77 (March 2016) (2017) 899–915. doi:10.1016/j.rser.2016.12.127.
URL <http://dx.doi.org/10.1016/j.rser.2016.12.127>
- [72] G. A. Rosales-Sosa, A. Masuno, Y. Higo, H. Inoue, Crack-resistant Al₂O₃–SiO₂ glasses, *Scientific Reports* 6 (1) (2016) 23620. doi:10.1038/srep23620.
URL <https://www.nature.com/articles/srep23620>
- [73] D. F. De Sousa, L. A. Nunes, J. H. Rohling, M. L. Baesso, Laser emission at 1077 nm in Nd³⁺-doped calcium aluminosilicate glass, *Applied Physics B: Lasers and Optics* 77 (1) (2003) 59–63. doi:10.1007/s00340-003-1247-y.
- [74] K. U. Hess, D. B. Dingwell, E. Rössler, Parametrization of viscosity-temperature relations of aluminosilicate melts, *Chemical Geology* 128 (1-4) (1996) 155–163. doi:10.1016/0009-2541(95)00170-0.
- [75] K. Hara, H. Ichinose, T. N. Murakami, A. Masuda, Crystalline Si photovoltaic modules based on TiO₂-coated cover glass against potential-induced degradation, *RSC Advances* 4 (83) (2014) 44291–44295. doi:10.1039/c4ra06791f.

- [76] D. M. Giolando, Transparent self-cleaning coating applicable to solar energy consisting of nano-crystals of titanium dioxide in fluorine doped tin dioxide, *Solar Energy* 124 (2016) 76–81. doi:10.1016/j.solener.2015.11.024.
URL <http://dx.doi.org/10.1016/j.solener.2015.11.024>
- [77] N. Pratiwi, Zulhadjri, S. Arief, D. V. Wellia, A Facile Preparation of Transparent Ultrahydrophobic Glass via TiO₂/Octadecyltrichlorosilane (ODTS) Coatings for Self-Cleaning Material, *ChemistrySelect* 5 (4) (2020) 1450–1454. doi:10.1002/slct.201904153.
- [78] S. B. Khan, Z. Zhang, S. L. Lee, Single component: Bilayer TiO₂ as a durable antireflective coating, *Journal of Alloys and Compounds* 834 (2020). doi:10.1016/j.jallcom.2020.155137.
- [79] K. Saito, A. J. Ikushima, Effects of fluorine on structure, structural relaxation, and absorption edge in silica glass, *Journal of Applied Physics* 91 (8) (2002) 4886–4890. doi:10.1063/1.1459102.
- [80] D. P. Mukherjee, S. K. Das, SiO₂-Al₂O₃-CaO glass-ceramics: Effects of CaF₂ on crystallization, microstructure and properties, *Ceramics International* 39 (1) (2013) 571–578. doi:10.1016/j.ceramint.2012.06.066.
- [81] F. Pei, G. Zhu, P. Li, H. Guo, P. Yang, Effects of CaF₂ on the sintering and crystallisation of CaO–MgO–Al₂O₃–SiO₂ glass-ceramics, *Ceramics International* 46 (11) (2020) 17825–17835. doi:10.1016/j.ceramint.2020.04.089.
- [82] R. Muniz, V. Soares, V. Zanuto, M. Melo, M. Sandrini, M. Belançon, A. Medina, M. Baesso, Color tunability and synergistic effect of PiG materials based on YAG:Ce³⁺ phosphor in SCS:Eu³⁺ glass, *Journal of Non-Crystalline Solids* 574 (September) (2021) 121169. doi:10.1016/j.jnoncrysol.2021.121169.
URL <https://doi.org/10.1016/j.jnoncrysol.2021.121169>
<https://linkinghub.elsevier.com/retrieve/pii/S0022309321005329>

- [83] R. Kikuchi, T. Sato, N. Fujii, M. Shimbashi, C. A. Arcilla, Natural glass alteration under a hyperalkaline condition for about 4000 years, *Scientific Reports* (2022) 1–10doi:10.1038/s41598-022-20482-3.
URL <https://doi.org/10.1038/s41598-022-20482-3>
- [84] Q. Guo, T. Feng, M. J. Lance, K. A. Unocic, S. T. Pantelides, E. Lara-Curzio, Evolution of the structure and chemical composition of the interface between multi-component silicate glasses and yttria-stabilized zirconia after 40,000 h exposure in air at 800 °C, *Journal of the European Ceramic Society* 42 (4) (2022) 1576–1584. doi:10.1016/j.jeurceramsoc.2021.11.013.
URL <https://doi.org/10.1016/j.jeurceramsoc.2021.11.013><https://linkinghub.elsevier.com/retrieve/pii/S0955221921008116>
- [85] S. Gin, J. M. Delaye, F. Angeli, S. Schuller, Aqueous alteration of silicate glass: state of knowledge and perspectives, *npj Materials Degradation* 5 (1) (2021). doi:10.1038/s41529-021-00190-5.
URL <http://dx.doi.org/10.1038/s41529-021-00190-5>
- [86] T. Geisler, L. Dohmen, C. Lenting, M. B. K. Fritzsche, Real-time in situ observations of reaction and transport phenomena during silicate glass corrosion by fluid-cell Raman spectroscopy, *Nature Materials* 18 (4) (2019) 342–348. doi:10.1038/s41563-019-0293-8.
URL <http://dx.doi.org/10.1038/s41563-019-0293-8><https://www.nature.com/articles/s41563-019-0293-8>
- [87] T. Du, H. Li, Atomistic origin of the passivation effect in hydrated silicate glasses, *npj Materials Degradation* (November 2018) (2019). doi:10.1038/s41529-019-0070-9.
URL <http://dx.doi.org/10.1038/s41529-019-0070-9>
- [88] Y. Wang, C. F. Jove-colon, C. Lenting, J. Icenhower, K. L. Kuhlman, Morphological instability of aqueous dissolution of silicate glasses and minerals, *npj Materials Degradation* (August) (2018). doi:10.1038/s41529-018-0047-0.
URL <http://dx.doi.org/10.1038/s41529-018-0047-0>
- [89] V. Guiheneuf, F. Delaleux, O. Riou, P. O. Logerais, J. F. Durastanti, Investigation of damp heat effects on glass properties for photovoltaic

- applications, *Corrosion Engineering Science and Technology* 52 (3) (2017) 170–177. doi:10.1080/1478422X.2016.1234803.
URL <http://dx.doi.org/10.1080/1478422X.2016.1234803>
- [90] M. Seshadri, I. T. Santos, M. J. V. Bell, J. Lapointe, Y. Messaddeq, V. Anjos, Near-infrared quantum cutting luminescence in $\text{Pr}^{3+}/\text{Yb}^{3+}$ doped lead bismuth borate glass, *Scientific Reports* 12 (1) (2022) 1–8. doi:10.1038/s41598-022-23808-3.
URL <https://doi.org/10.1038/s41598-022-23808-3>
- [91] W. Romero-Romo, S. Carmona-Téllez, R. Lozada-Morales, O. Soriano-Romero, U. Caldiño, M. E. Álvarez-Ramos, M. E. Zayas, A. N. Meza-Rocha, Down-shifting and down-conversion emission properties of novel $\text{CdO-P}_2\text{O}_5$ invert glasses activated with Pr^{3+} and $\text{Pr}^{3+}/\text{Yb}^{3+}$ for photonic applications, *Optical Materials* 116 (February) (2021). doi:10.1016/j.optmat.2021.111009.
- [92] F. Aouaini, A. Maaoui, N. B. H. Mohamed, M. M. Alanazi, L. A. El Maati, Visible to infrared down conversion of Er^{3+} doped tellurite glass for luminescent solar converters, *Journal of Alloys and Compounds* 894 (2022) 162506. doi:10.1016/j.jallcom.2021.162506.
URL <https://doi.org/10.1016/j.jallcom.2021.162506>
- [93] S. Kaniyarakkal, K. Culala, R. Dagupati, Down conversion and efficient NIR to visible up-conversion emission analysis in $\text{Ho}^{3+} / \text{Yb}^{3+}$ co-doped tellurite glasses, *Boletín de la Sociedad Española de Cerámica y Vidrio* (2023) 1–8doi:10.1016/j.bsecv.2023.01.002.
URL <https://doi.org/10.1016/j.bsecv.2023.01.002>
- [94] M. Bouzidi, A. Maaoui, N. Chaaben, A. S. Alshammari, Z. R. Khan, M. Mohamed, Downconversion mechanism in $\text{Er}^{3+}/\text{Yb}^{3+}$ codoped fluorotellurite glasses to enhance the efficiency of c-Si PV cells, *Journal of Non-Crystalline Solids* 595 (July) (2022) 121837. doi:10.1016/j.jnoncrysol.2022.121837.
URL <https://doi.org/10.1016/j.jnoncrysol.2022.121837>
- [95] H. Singh, T. Singh, D. Singh, V. Bhatia, D. Kumar, S. P. Singh, Up-conversion and downconversion studies of Nd^{3+} doped borophosphate glasses, *Optical Materials* 137 (February) (2023) 113586. doi:

10.1016/j.optmat.2023.113586.

URL <https://doi.org/10.1016/j.optmat.2023.113586>

- [96] Y. Chen, G. Chen, X. Liu, J. Xu, T. Yang, C. Yuan, C. Zhou, Down-conversion luminescence and optical thermometric performance of Tb³⁺/Eu³⁺ doped phosphate glass, *Journal of Non-Crystalline Solids* 484 (January) (2018) 111–117. doi:10.1016/j.jnoncrysol.2018.01.027.
URL <https://doi.org/10.1016/j.jnoncrysol.2018.01.027>
- [97] H. Benrejeb, K. Soler-Carracedo, S. Hraiech, I. R. Martin, Analysis of down conversion and back-transfer processes in Pr³⁺-Yb³⁺ co-doped phosphate glasses, *Optical Materials* 131 (June) (2022) 112604. doi:10.1016/j.optmat.2022.112604.
URL <https://doi.org/10.1016/j.optmat.2022.112604>
- [98] T. Zhang, D. Zhang, P. A. Wang, C. Cui, Preparation of Dy³⁺/Tm³⁺-Co-doped Phosphate Glasses by Melt Method and its Luminescence Properties, *Journal of Physics: Conference Series* 2226 (1) (2022). doi:10.1088/1742-6596/2226/1/012004.
- [99] D. Y. Shi, S. bao Lin, X. xia Zhao, A. ling Feng, Q. Xu, Near-infrared quantum cutting in Tm³⁺/Yb³⁺-doped phosphate glasses, *Results in Physics* 19 (2020) 103411. doi:10.1016/j.rinp.2020.103411.
URL <https://doi.org/10.1016/j.rinp.2020.103411>
- [100] T. Markvart, Solar cell as a heat engine: Energy-entropy analysis of photovoltaic conversion, *Physica Status Solidi (A) Applications and Materials Science* 205 (12) (2008) 2752–2756. doi:10.1002/pssa.200880460.
- [101] T. Markvart, From steam engine to solar cells: can thermodynamics guide the development of future generations of photovoltaics?, *Wiley Interdisciplinary Reviews: Energy and Environment* 5 (5) (2016) 543–569. doi:10.1002/wene.204.
- [102] S. Chu, A. Majumdar, Opportunities and challenges for a sustainable energy future, *Nature* 488 (7411) (2012) 294–303. doi:10.1038/nature11475.
URL <http://www.nature.com/doifinder/10.1038/nature11475>

- [103] Y. Xu, T. Gong, J. N. Munday, The generalized Shockley-Queisser limit for nanostructured solar cells, Nature Publishing Group (2015) 1–9doi:10.1038/srep13536.
URL <http://dx.doi.org/10.1038/srep13536>
- [104] M. S. Kim, J. H. Lee, M. K. Kwak, Review: Surface Texturing Methods for Solar Cell Efficiency Enhancement, International Journal of Precision Engineering and Manufacturing 21 (7) (2020) 1389–1398. doi:10.1007/s12541-020-00337-5.
URL <https://doi.org/10.1007/s12541-020-00337-5>
- [105] Z. Zhou, Y. Jiang, N. Ekins-Daukes, M. Keevers, M. A. Green, Optical and Thermal Emission Benefits of Differently Textured Glass for Photovoltaic Modules, IEEE Journal of Photovoltaics 11 (1) (2021) 131–137. doi:10.1109/JPHOTOV.2020.3033390.
- [106] P. Buskens, M. Burghoorn, M. C. D. Mourad, Z. Vroon, Antireflective Coatings for Glass and Transparent Polymers, Langmuir 32 (27) (2016) 6781–6793. doi:10.1021/acs.langmuir.6b00428.
- [107] P. Löbmann, Sol-Gel Processing of MgF₂ Antireflective Coatings, Nanomaterials 8 (5) (2018) 295. doi:10.3390/nano8050295.
- [108] F. Wiesinger, G. S. Vicente, A. Fernández-García, F. Sutter, Á. Morales, R. Pitz-Paal, Sandstorm erosion testing of anti-reflective glass coatings for solar energy applications, Solar Energy Materials and Solar Cells 179 (September 2017) (2018) 10–16. doi:10.1016/j.solmat.2018.02.018.
URL <https://linkinghub.elsevier.com/retrieve/pii/S0927024818300692>
- [109] G. Womack, K. Isbilir, F. Lisco, G. Durand, A. Taylor, J. M. Walls, The performance and durability of single-layer sol-gel anti-reflection coatings applied to solar module cover glass, Surface and Coatings Technology 358 (November 2018) (2019) 76–83. doi:10.1016/j.surfcoat.2018.11.030.
URL <https://doi.org/10.1016/j.surfcoat.2018.11.030>
- [110] M. R. Maghami, H. Hizam, C. Gomes, M. A. Radzi, M. I. Rezadad, S. Hajighorbani, Power loss due to soiling on solar panel: A review,

- Renewable and Sustainable Energy Reviews 59 (2016) 1307–1316. doi:10.1016/j.rser.2016.01.044.
URL <http://dx.doi.org/10.1016/j.rser.2016.01.044>
- [111] A. Syafiq, A. K. Pandey, N. N. Adzman, N. A. Rahim, Advances in approaches and methods for self-cleaning of solar photovoltaic panels, *Solar Energy* 162 (May 2017) (2018) 597–619. doi:10.1016/j.solener.2017.12.023.
- [112] H. Lu, R. Cai, L. Z. Zhang, L. Lu, L. Zhang, Experimental investigation on deposition reduction of different types of dust on solar PV cells by self-cleaning coatings, *Solar Energy* 206 (May) (2020) 365–373. doi:10.1016/j.solener.2020.06.012.
URL <https://doi.org/10.1016/j.solener.2020.06.012>
- [113] H. Cheng, F. Wang, J. Ou, W. Li, R. Xue, Solar reflective coatings with luminescence and self-cleaning function, *Surfaces and Interfaces* 26 (oct 2021). doi:10.1016/j.surfin.2021.101325.
- [114] D. Biswas, N. Chundi, S. R. Atchuta, K. K. Phani Kumar, M. Shiva Prasad, S. Sakthivel, Fabrication of omnidirectional broadband dual-functional coating with high optical and self-cleaning properties for photovoltaic application, *Solar Energy* 246 (2022) 36–44. doi:10.1016/j.solener.2022.09.038.
- [115] A. C. Bento, N. Cella, S. M. Lima, L. A. O. Nunes, L. H. C. Andrade, J. R. Silva, V. S. Zanuto, N. G. C. Astrath, T. Catunda, A. N. Medina, J. H. Rohling, R. F. Muniz, J. W. Berrar, L. C. Malacarne, W. R. Weinand, F. Sato, M. P. Belancon, G. J. Schiavon, J. Shen, L. C. M. Miranda, H. Vargas, M. L. Baesso, Photoacoustic and photothermal and the photovoltaic efficiency of solar cells: A tutorial, *Journal of Applied Physics* 131 (14) (2022) 141101. doi:10.1063/5.0088211.
URL <https://aip.scitation.org/doi/10.1063/5.0088211>
- [116] X. Huang, S. Han, W. Huang, X. Liu, Enhancing solar cell efficiency: the search for luminescent materials as spectral converters, *Chemical Society Reviews* 42 (1) (2013) 173–201. doi:10.1039/c2cs35288e.
URL <http://xlink.rsc.org/?DOI=C2CS35288E>

- [117] P. K. Tawalare, Optimizing photovoltaic conversion of solar energy, *AIP Advances* 11 (10) (2021) 100701. doi:10.1063/5.0064202.
URL <https://aip.scitation.org/doi/10.1063/5.0064202>
- [118] A. Ghazy, M. Safdar, M. Lastusaari, H. Savin, M. Karppinen, Advances in upconversion enhanced solar cell performance, *Solar Energy Materials and Solar Cells* 230 (April) (2021) 111234. doi:10.1016/j.solmat.2021.111234.
URL <https://doi.org/10.1016/j.solmat.2021.111234>
- [119] A. Khare, A critical review on the efficiency improvement of upconversion assisted solar cells, *Journal of Alloys and Compounds* 821 (2020) 153214. doi:10.1016/j.jallcom.2019.153214.
URL <https://doi.org/10.1016/j.jallcom.2019.153214>
- [120] C. C. Lin, P. J. Krommenhoek, S. S. Watson, X. Gu, Depth profiling of degradation of multilayer photovoltaic backsheets after accelerated laboratory weathering: Cross-sectional Raman imaging, *Solar Energy Materials and Solar Cells* 144 (2016) 289–299. doi:10.1016/j.solmat.2015.09.021.
URL <http://dx.doi.org/10.1016/j.solmat.2015.09.021>
- [121] J. Schlothauer, S. Jungwirth, M. Köhl, B. Röder, Degradation of the encapsulant polymer in outdoor weathered photovoltaic modules: Spatially resolved inspection of EVA ageing by fluorescence and correlation to electroluminescence, *Solar Energy Materials and Solar Cells* 102 (2012) 75–85. doi:10.1016/j.solmat.2012.03.022.
- [122] N. Katayama, S. Osawa, S. Matsumoto, T. Nakano, M. Sugiyama, Degradation and fault diagnosis of photovoltaic cells using impedance spectroscopy, *Solar Energy Materials and Solar Cells* 194 (September 2018) (2019) 130–136. doi:10.1016/j.solmat.2019.01.040.
URL <https://doi.org/10.1016/j.solmat.2019.01.040>
- [123] K. Zhang, L. Hao, M. Du, J. Mi, J.-N. Wang, J.-p. Meng, A review on thermal stability and high temperature induced ageing mechanisms of solar absorber coatings, *Renewable and Sustainable Energy Reviews* 67 (2017) 1282–1299. doi:10.1016/j.rser.2016.09.083.
URL <http://dx.doi.org/10.1016/j.rser.2016.09.083><https://linkinghub.elsevier.com/retrieve/pii/S1364032116305731>

- [124] M. P. Belançon, M. Sandrini, F. Tonholi, L. S. Herculano, G. S. Dias, Towards long term sustainability of c-Si solar panels: The environmental benefits of glass sheet recovery, *Renewable Energy Focus* 42 (2022) 206–210. doi:10.1016/j.ref.2022.06.009.
URL <https://linkinghub.elsevier.com/retrieve/pii/S1755008422000515>
- [125] H. Gopalakrishna, P. Arularasu, K. Dolia, A. Sinha, G. Tamizhmani, Characterization of Encapsulant Degradation in Accelerated UV Stressed Mini-Modules with UV-cut and UV-pass EVA, *Conference Record of the IEEE Photovoltaic Specialists Conference* (2019) 1961–1964doi:10.1109/PVSC40753.2019.8980897.
- [126] D. Yu, T. Yu, H. Lin, S. Zhuang, D. Zhang, Recent Advances in Luminescent Downconversion: New Materials, Techniques, and Applications in Solar Cells, *Advanced Optical Materials* 10 (12) (2022) 2200014. doi:10.1002/adom.202200014.
URL <https://onlinelibrary.wiley.com/doi/10.1002/adom.202200014>
- [127] N. S. Satpute, C. M. Mehare, A. Tiwari, H. C. Swart, S. J. Dhoble, Synthesis and Luminescence Characterization of Downconversion and Downshifting Phosphor for Efficiency Enhancement of Solar Cells: Perspectives and Challenges, *ACS Applied Electronic Materials* 4 (7) (2022) 3354–3391. doi:10.1021/acsaelm.2c00595.
URL <https://pubs.acs.org/doi/10.1021/acsaelm.2c00595>
- [128] A. Lupei, V. Lupei, C. Gheorghe, S. Hau, A. Ikesue, Multicenters in Ce³⁺ visible emission of YAG ceramics, *Optical Materials* 37 (C) (2014) 727–733. doi:10.1016/j.optmat.2014.09.001.
- [129] L. Teng, Y. Jiang, W. Zhang, R. Wei, H. Guo, Highly transparent cerium doped glasses with full-band UV-shielding capacity, *Journal of the American Ceramic Society* 103 (5) (2020) 3249–3256. doi:10.1111/jace.17020.
- [130] K. Annapurna, R. N. Dwivedi, P. Kundu, S. Buddhudu, Blue emission spectrum of Ce³⁺:ZnO-B₂O₃-SiO₂ optical glass, *Materials Letters* 58 (5) (2004) 787–789. doi:10.1016/j.matlet.2003.07.012.

- [131] G. Pullaiah, K. Venkata Rao, B. C. Jamalaiah, N. Madhu, V. Nutalapati, Spectroscopic and luminescent properties of Ce³⁺ -doped TeO₂-WO₃-GeO₂ glasses, *Materials Science and Engineering B: Solid-State Materials for Advanced Technology* 284 (oct 2022). doi:10.1016/j.mseb.2022.115879.
- [132] L. H. C. Andrade, S. M. Lima, a. Novatski, a. Steimacher, J. H. Rohling, a. N. Medina, a. C. Bento, M. L. Baesso, Y. Guyot, G. Boulon, A step forward toward smart white lighting: Combination of glass phosphor and light emitting diodes, *Applied Physics Letters* 95 (8) (2009) 2007–2010. doi:10.1063/1.3186784.
- [133] Y. Tai, G. Zheng, H. Wang, J. Bai, Near-infrared quantum cutting of Ce³⁺-Nd³⁺ co-doped Y₃Al₅O₁₂ crystal for crystalline silicon solar cells, *Journal of Photochemistry and Photobiology A: Chemistry* 303–304 (2015) 80–85. doi:10.1016/j.jphotochem.2015.02.009.
- [134] Q. Wang, J. B. Qiu, Z. G. Song, Z. W. Yang, Z. Y. Yin, D. C. Zhou, Optical properties of Ce³⁺-Nd³⁺ co-doped YAG nanoparticles for visual and near-infrared biological imaging, *Spectrochimica Acta - Part A: Molecular and Biomolecular Spectroscopy* 149 (2015) 898–903. doi:10.1016/j.saa.2015.04.082.
- [135] Z. Zhou, W. Lei, P. Zhang, H. Liang, Z. Luo, A. Lu, Influence of CaF₂ addition on structure and luminescence properties of the Na₂O–CaO–SiO₂–Al₂O₃–ZnO–P₂O₅ glass co-doped with Ce³⁺/Yb³⁺, *Optical Materials* 134 (dec 2022). doi:10.1016/j.optmat.2022.113171.
- [136] R. Reddappa, K. Suresh, C. K. Jayasankar, Down conversion studies in Ce³⁺ and Yb³⁺ doped Ca₂SiO₄ phosphors from agricultural waste: Si based solar cell applications, *Optical Materials* 122 (PB) (2021) 111700. doi:10.1016/j.optmat.2021.111700.
URL <https://doi.org/10.1016/j.optmat.2021.111700>
- [137] A. A. Pathak, R. A. Talewar, C. P. Joshi, S. V. Moharil, Sensitization of Yb³⁺ emission in CaYAl₃O₇ host, *Optical Materials* 64 (2017) 217–223. doi:10.1016/j.optmat.2016.12.018.

- [138] A. D. Sontakke, J. Ueda, S. Tanabe, Effect of synthesis conditions on Ce³⁺ + luminescence in borate glasses, *Journal of Non-Crystalline Solids* 431 (2016) 150–153. doi:10.1016/j.jnoncrysol.2015.04.005.
- [139] K. S. Ranasinghe, R. Singh, D. Leshchev, A. Vasquez, E. Stavitski, I. Foster, Synthesis of Nanocerium with Varied Ratios of Ce³⁺/Ce⁴⁺ Utilizing Soluble Borate Glass, *Nanomaterials* 12 (14) (jul 2022). doi:10.3390/nano12142363.
- [140] E. Kaewnuam, N. Wantana, Y. Ruangtaweep, M. Cadatal-Raduban, K. Yamanoi, H. J. Kim, P. Kidkhunthod, J. Kaewkhao, The influence of CeF₃ on radiation hardness and luminescence properties of Gd₂O₃–B₂O₃ glass scintillator, *Scientific Reports* 12 (1) (dec 2022). doi:10.1038/s41598-022-14833-3.
- [141] P. Song, C. Jiang, Modeling of downconverter based on Pr³⁺–Yb³⁺ codoped fluoride glasses to improve sc-Si solar cells efficiency, *AIP Advances* 2 (4) (dec 2012). doi:10.1063/1.4766187.
- [142] J. Zhao, X. Zhao, Z. Leng, M. Han, Efficient blue to near-infrared luminescence properties in Pr³⁺ - Yb³⁺ co-doped Li₈Bi₂(MoO₄)₇ phosphor, *Optical Materials* 108 (oct 2020). doi:10.1016/j.optmat.2020.110232.
- [143] G. Zhang, Q. Cui, G. Liu, Efficient near-infrared quantum cutting and downshift in Ce³⁺–Pr³⁺ codoped SrLaGa₃S₆O suitable for solar spectral converter, *Optical Materials* 53 (2016) 214–217. doi:10.1016/j.optmat.2016.01.042.
- [144] P. Meejitpaisan, R. Doddaji, S. Kothan, C. K. Jayasankar, J. Kaewkhao, Visible to infrared emission from (Eu³⁺/Nd³⁺):B₂O₃ + AlF₃ + NaF + CaF₂ glasses for luminescent solar converters, *Optics and Laser Technology* 141 (December 2020) (2021). doi:10.1016/j.optlastec.2021.107170.
- [145] J. Luo, S. ichi Amma, L. Chen, D. Ngo, J. C. Mauro, C. G. Pantano, S. H. Kim, Relative abundance of subsurface hydroxyl and molecular water species in silicate and aluminosilicate glasses, *Journal of Non-Crystalline Solids* 510 (January) (2019) 179–185. doi:

10.1016/j.jnoncrysol.2019.01.012.

URL <https://doi.org/10.1016/j.jnoncrysol.2019.01.012>

- [146] P. Dorenbos, Energy of the first $4f^7 \rightarrow 4f^6 5d$ transition of Eu^{2+} in inorganic compounds, *Journal of Luminescence* 104 (4) (2003) 239–260. doi:10.1016/S0022-2313(03)00078-4.
URL <https://linkinghub.elsevier.com/retrieve/pii/S0022231303000784>
- [147] P. Dorenbos, Relation between Eu^{2+} and Ce^{3+} f d-transition energies in inorganic compounds, *Journal of Physics: Condensed Matter* 15 (27) (2003) 4797–4807. doi:10.1088/0953-8984/15/27/311.
URL <https://iopscience.iop.org/article/10.1088/0953-8984/15/27/311>
- [148] Y. Chen, J. Wang, M. Zhang, Q. Zeng, Light conversion material: $\text{LiBaPO}_4\text{:Eu}^{2+}$, Pr^{3+} , suitable for solar cell, *RSC Advances* 7 (34) (2017) 21221–21225. doi:10.1039/c7ra01834g.
- [149] C. Wang, T. Xuan, J. Liu, H. Li, Z. Sun, Long Afterglow $\text{SrAl}_2\text{O}_4\text{:Eu}^{2+}, \text{Dy}^{3+}$ Phosphors as Luminescent Down-Shifting Layer for Crystalline Silicon Solar Cells, *International Journal of Applied Ceramic Technology* 12 (4) (2015) 722–727. doi:10.1111/ijac.12281.
- [150] R. A. Talewar, C. P. Joshi, S. V. Moharil, Near infrared emission and energy transfer in Eu^{2+} - Nd^{3+} co-doped $\text{Ca}_2\text{BO}_3\text{Cl}$, *Optical Materials* 55 (2016) 44–48. doi:10.1016/j.optmat.2016.03.007.
- [151] X. Luo, J. Y. Ahn, S. H. Kim, Aerosol synthesis and luminescent properties of $\text{CaAl}_2\text{O}_4\text{:Eu}^{2+}, \text{Nd}^{3+}$ down-conversion phosphor particles for enhanced light harvesting of dye-sensitized solar cells, *Solar Energy* 178 (2019) 173–180. doi:10.1016/j.solener.2018.12.029.
URL <https://linkinghub.elsevier.com/retrieve/pii/S0038092X18312040>
- [152] J. Zhou, Y. Teng, X. Liu, Z. Ma, J. Qiu, Broadband spectral conversion of visible light to near-infrared emission via energy transfer from Ce^{3+} to $\text{Nd}^{3+}/\text{Yb}^{3+}$ in YAG, *Journal of Materials Research* 26 (5) (2011) 689–692. doi:10.1557/jmr.2010.84.

- [153] W. Romero-Romo, S. Carmona-Téllez, R. Lozada-Morales, O. Soriano-Romero, U. Caldiño, M. E. Álvarez-Ramos, M. E. Zayas, A. N. Meza-Rocha, Down-shifting and down-conversion emission properties of novel CdO–P2O5 invert glasses activated with Pr³⁺ and Pr³⁺/Yb³⁺ for photonic applications, *Optical Materials* 116 (March) (2021). doi:10.1016/j.optmat.2021.111009.
- [154] X. Zhou, J. Shen, Y. Wang, Z. Feng, R. Wang, L. Li, S. Jiang, X. Luo, An Efficient Dual-Mode Solar Spectral Modification for c-Si Solar Cells in Tm³⁺/Yb³⁺ Codoped Tellurite Glasses, *Journal of the American Ceramic Society* 99 (7) (2016) 2300–2305. doi:10.1111/jace.14133.
- [155] R. Elleuch, R. Salhi, J.-L. Deschanvres, R. Maalej, Antireflective down-conversion ZnO:Er³⁺, Yb³⁺ thin film for Si solar cell applications, *Journal of Applied Physics* 117 (5) (2015) 055301. doi:10.1063/1.4906976.
URL <http://aip.scitation.org/doi/10.1063/1.4906976>
- [156] M. Bouzidi, A. Maaoui, N. Chaaben, A. S. Alshammari, Z. R. Khan, M. Mohamed, Downconversion mechanism in Er³⁺/Yb³⁺ codoped fluorotellurite glasses to enhance the efficiency of c-Si PV cells, *Journal of Non-Crystalline Solids* 595 (July) (2022) 121837. doi:10.1016/j.jnoncrysol.2022.121837.
URL <https://doi.org/10.1016/j.jnoncrysol.2022.121837>
- [157] N. Saad, M. Ibrahim, K. H. Sadok, M. Haouari, Fluoroborophosphate glasses doped with Cr³⁺, Nd³⁺ and Yb³⁺ as efficient light converters for silicon based solar cells, *Journal of Non-Crystalline Solids* 591 (May) (2022) 121707. doi:10.1016/j.jnoncrysol.2022.121707.
URL <https://doi.org/10.1016/j.jnoncrysol.2022.121707>
- [158] M. D. Kempe, T. Moricone, M. Kilkenny, Effects of Cerium Removal from Glass on Photovoltaic Module Performance and Stability Preprint (September) (2009).
- [159] H. K. Dan, N. D. Trung, D. Zhou, J. Qiu, Influences of Mn²⁺ ions, and Mn²⁺–Yb³⁺ dimer on the optical band gaps and bandwidth flatness of near-infrared emissions of Ho³⁺/Tm³⁺, Ho³⁺/Tm³⁺/Yb³⁺ co-doped calcium aluminosilicate glasses, *Journal of Non-Crystalline Solids* 603 (October 2022) (2023) 122086. doi:

10.1016/j.jnoncrysol.2022.122086.

URL <https://doi.org/10.1016/j.jnoncrysol.2022.122086>

- [160] G. R. Mattos, C. D. Bordon, O. C. Vilela, L. A. Gómez-Malagón, L. R. Kassab, Enhancement of multijunction solar cell efficiency using a cover layer of Eu^{3+} , Tb^{3+} and $\text{Eu}^{3+}/\text{Tb}^{3+}$ doped $\text{GeO}_2\text{-PbO-Al}_2\text{O}_3$ glasses as spectral converter of solar radiation, *Optical Materials* 132 (August) (2022) 1–7. doi:10.1016/j.optmat.2022.112833.
- [161] F. Yang, C. Liu, D. Wei, Y. Chen, J. Lu, S. E. Yang, $\text{Er}^{3+}\text{-Yb}^{3+}$ co-doped $\text{TeO}_2\text{-PbF}_2$ oxyhalide tellurite glasses for amorphous silicon solar cells, *Optical Materials* 36 (6) (2014) 1040–1043. doi:10.1016/j.optmat.2014.01.020.
- [162] A. R. Kadam, S. J. Dhoble, Energy transfer mechanism of $\text{KAlF}_4\text{:Dy}^{3+}$, Eu^{3+} co-activated down-conversion phosphor as spectral converters: An approach towards improving photovoltaic efficiency by downshifting layer, *Journal of Alloys and Compounds* 884 (2021) 161138. doi:10.1016/j.jallcom.2021.161138.
URL <https://doi.org/10.1016/j.jallcom.2021.161138>
- [163] H. Jia, Z. Liu, L. Liao, Y. Gu, C. Ding, J. Zhao, W. Zhang, X. Hu, X. Feng, Z. Chen, X. Liu, J. Qiu, Upconversion Luminescence from $\text{Ln}^{3+}(\text{Ho}^{3+}, \text{Pr}^{3+})$ Ion-Doped BaCl_2 Particles via NIR Light of Sun Excitation, *Journal of Physical Chemistry C* 122 (17) (2018) 9606–9610. doi:10.1021/acs.jpcc.8b02434.
- [164] B. L. Allsopp, G. Christopoulou, A. Brookfield, S. D. Forder, P. A. Bingham, Optical and structural properties of d0 ion-doped silicate glasses for photovoltaic applications, *Physics and Chemistry of Glasses: European Journal of Glass Science and Technology Part B* 59 (4) (2018) 193–202. doi:10.13036/17533562.59.4.003.
URL <https://www.ingentaconnect.com/content/sgt/ejgst/2018/00000059/00000004/art00005>
- [165] K. Fujita, R. Watanabe, Y. Iso, T. Isobe, Preparation and characterization of $\text{Y}_2\text{O}_3\text{:Bi}^{3+}, \text{Yb}^{3+}$ nanosheets with wavelength conversion from near-ultraviolet to near-infrared, *Journal of Luminescence* 198 (January) (2018) 243–250. doi:10.1016/j.jlumin.2018.02.023.
URL <https://doi.org/10.1016/j.jlumin.2018.02.023>

- [166] M. Peng, L. Wondraczek, Bismuth-doped oxide glasses as potential solar spectral converters and concentrators, *Journal of Materials Chemistry* 19 (5) (2009) 627–630. doi:10.1039/b812316k.
- [167] D. Ghosh, S. Balaji, K. Biswas, K. Annapurna, Broad NIR emission near c - Si band gap from Bi-doped Ba–Al metaphosphate glasses as promising solar spectral converter, *Journal of Materials Science* 50 (16) (2015) 5450–5457. doi:10.1007/s10853-015-9090-1.
- [168] V. Švrček, A. Slaoui, J. C. Muller, Silicon nanocrystals as light converter for solar cells, *Thin Solid Films* 451-452 (2004) 384–388. doi:10.1016/j.tsf.2003.10.133.
- [169] S. L. Luxembourg, A. R. Burgers, R. Limpens, T. Gregorkiewicz, A. Weeber, Application of a silicon nanocrystal down-shifter to a c-Si solar cell, *Energy Procedia* 55 (2014) 190–196. doi:10.1016/j.egypro.2014.08.115.
URL <http://dx.doi.org/10.1016/j.egypro.2014.08.115>
- [170] Z. Yuan, T. Nakamura, Spectral tuning of colloidal Si nanocrystal luminescence by post-laser irradiation in liquid, *RSC Advances* 10 (54) (2020) 32992–32998. doi:10.1039/d0ra05205a.
- [171] B. Das, S. M. Hossain, A. Nandi, D. Samanta, A. K. Pramanick, S. O. Martínez Chapa, M. Ray, Spectral conversion by silicon nanocrystal dispersed gel glass: Efficiency enhancement of silicon solar cell, *Journal of Physics D: Applied Physics* 55 (2) (2021). doi:10.1088/1361-6463/ac29e3.
- [172] M. Sandrini, J. C. Gemelli, M. S. Gibin, V. S. Zanuto, R. F. Muniz, F. S. de Vicente, M. P. Belançon, Synthesis and properties of Cerium-doped organic/silica xerogels: A potential UV filter for photovoltaic panels, *Journal of Non-Crystalline Solids* 600 (July 2022) (2023) 122033. doi:10.1016/j.jnoncrysol.2022.122033.
URL <https://doi.org/10.1016/j.jnoncrysol.2022.122033><https://linkinghub.elsevier.com/retrieve/pii/S0022309322006275>
- [173] M. Zier, P. Stenzel, L. Kotzur, D. Stolten, A review of decarbonization options for the glass industry (jun 2021). doi:10.1016/j.ecmx.2021.100083.

- [174] P. W. Griffin, G. P. Hammond, R. C. McKenna, Industrial energy use and decarbonisation in the glass sector: A UK perspective, *Advances in Applied Energy* 3 (aug 2021). doi:10.1016/j.adapen.2021.100037.
- [175] D. D. Furszyfer Del Rio, B. K. Sovacool, A. M. Foley, S. Griffiths, M. Bazilian, J. Kim, D. Rooney, Decarbonizing the glass industry: A critical and systematic review of developments, sociotechnical systems and policy options (mar 2022). doi:10.1016/j.rser.2021.111885.
- [176] L. F. Flores, K. Y. Tucto, J. A. Guerra, J. A. Töfflinger, E. S. Serquen, A. Osvet, M. Batentschuk, A. Winnacker, R. Grieseler, R. Weingärtner, Luminescence properties of Yb³⁺-Tb³⁺ co-doped amorphous silicon oxycarbide thin films, *Optical Materials* 92 (March) (2019) 16–21. doi:10.1016/j.optmat.2019.04.003.
URL <https://doi.org/10.1016/j.optmat.2019.04.003>
- [177] I. Bubli, S. Ali, M. Ali, K. Hayat, Y. Iqbal, S. Zulfiqar, A. ul Haq, E. Cattaruzza, Enhancement of solar cell efficiency via luminescent downshifting by an optimized coverglass, *Ceramics International* 46 (2) (2020) 2110–2115. doi:10.1016/j.ceramint.2019.09.193.
URL <https://doi.org/10.1016/j.ceramint.2019.09.193><https://linkinghub.elsevier.com/retrieve/pii/S0272884219327300>
- [178] A. Bouajaj, S. Belmokhtar, M. Britel, C. Armellini, B. Boulard, F. Belluomo, A. Di Stefano, S. Polizzi, A. Lukowiak, M. Ferrari, F. Enrichi, Tb³⁺/Yb³⁺ codoped silica–hafnia glass and glass–ceramic waveguides to improve the efficiency of photovoltaic solar cells, *Optical Materials* 52 (2016) 62–68. doi:10.1016/j.optmat.2015.12.013.
URL <http://dx.doi.org/10.1016/j.optmat.2015.12.013><https://linkinghub.elsevier.com/retrieve/pii/S0925346715301543>
- [179] F. Enrichi, E. Cattaruzza, P. Riello, G. C. Righini, A. Vomiero, Ag-sensitized Tb³⁺/Yb³⁺ codoped silica-zirconia glasses and glass-ceramics: Systematic and detailed investigation of the broadband energy-transfer and downconversion processes, *Ceramics International* 47 (13) (2021) 17939–17949. doi:10.1016/j.ceramint.2021.03.107.
URL <https://doi.org/10.1016/j.ceramint.2021.03.107>
- [180] M. Langenhorst, D. Ritzer, F. Kotz, P. Risch, S. Dottermusch, A. Roslizar, R. Schmager, B. S. Richards, B. E. Rapp, U. W. Paetzold,

- Liquid Glass for Photovoltaics: Multifunctional Front Cover Glass for Solar Modules, *ACS Applied Materials and Interfaces* 11 (38) (2019) 35015–35022. doi:10.1021/acsami.9b12896.
- [181] P. Wang, X. Yan, H. Wang, C. Luo, C. Wang, Study on improving the efficiency of crystalline silicon photovoltaic module with down-conversion chlorophyll film, *Optical Materials* 132 (May) (2022) 112821. doi:10.1016/j.optmat.2022.112821.
URL <https://doi.org/10.1016/j.optmat.2022.112821>
- [182] C. Bataille, M. Åhman, K. Neuhoﬀ, L. J. Nilsson, M. Fishedick, S. Lechtenböhmer, B. Solano-Rodriguez, A. Denis-Ryan, S. Stiebert, H. Waisman, O. Sartor, S. Rahbar, A review of technology and policy deep decarbonization pathway options for making energy-intensive industry production consistent with the Paris Agreement, *Journal of Cleaner Production* 187 (2018) 960–973. doi:10.1016/j.jclepro.2018.03.107.
URL <https://linkinghub.elsevier.com/retrieve/pii/S0959652618307686>
- [183] M. P. Belançon, Brazil electricity needs in 2030: Trends and challenges, *Renewable Energy Focus* 36 (00) (2021) 89–95. doi:10.1016/j.ref.2021.01.001.
URL <https://linkinghub.elsevier.com/retrieve/pii/S1755008421000016>
- [184] M. M. Lunardi, J. P. Alvarez-Gaitan, J. I. Bilbao, R. Corkish, A Review of Recycling Processes for Photovoltaic Modules, Solar Panels and Photovoltaic Materials (2018). doi:10.5772/intechopen.74390.
URL <http://www.intechopen.com/books/solar-panels-and-photovoltaic-materials/a-review-of-recycling-processes-for-photovoltaic-modules>
- [185] K. Ren, X. Tang, M. Höök, Evaluating metal constraints for photovoltaics: Perspectives from China’s PV development, *Applied Energy* 282 (October 2020) (2021). doi:10.1016/j.apenergy.2020.116148.
- [186] P. R. Dias, M. G. Benevit, H. M. Veit, Photovoltaic solar panels of crystalline silicon: Characterization and separation, *Waste*

Management and Research 34 (3) (2016) 235–245. doi:10.1177/0734242X15622812.

- [187] V. Svrcek, T. Yamanari, D. Mariotti, S. Mitra, T. Velusamy, K. Matsubara, A silicon nanocrystal/polymer nanocomposite as a down-conversion layer in organic and hybrid solar cells, Nanoscale 7 (27) (2015) 11566–11574. doi:10.1039/c5nr02703a.