Effect of X-Ray Irradiation on Magnetocaloric Material, (MnNiSi)1-x(Fe2Ge)x

John Peter J. Nunez^{*1}, Vaibhav Sharma¹, Jessika V. Rojas¹, Radhika Barua¹, Ravi L. Hadimani^{*1,2,3}

¹Department of Mechanical and Nuclear Engineering, Virginia Commonwealth University, Richmond, VA 23284, USA

²Department of Biomedical Engineering, Virginia Commonwealth University, Richmond, VA 23284, USA

³Department of Psychiatry, Harvard Medical School, Harvard University, Boston, MA 02115, USA

Abstract

 $(MnNiSi)_{1-x}(Fe_2Ge)_x$ composition (x=0.34) alloy was prepared by arc melting, crushed, and sieved to approximately <32 microns. They were utilized in examining the possible magnetic and structural changes when exposed to a dosage of a continuous sweeping rate of $\sim > 120$ Gy/min and an absorbed dose of 35 kGy of X-ray radiation. This study reports observable trends in X-ray diffraction and magnetic measurements. Magnetization in the magnetization vs. temperature (both heating and cooling) measurements showed an increase from 2.72 emu/g to 4.01 emu/g in the irradiated sample. The Magnetization vs. magnetic field loops exhibited irradiation-induced magnetic hysteresis. The irradiated sample also exhibited an observable change in its coercivity of $\Delta H_c = 14.7\%$ at 200 K. A maximum entropy change ΔS_{mag} of ~ 11.139 J/kg*K and a T_{ave} peak of 317.5 K was achieved for the pristine sample in comparison to ΔS_{mag} of ~ 11.349 J/kg*K and a Tave peak of 312.5 K for the irradiated sample. These presented results provided deeper insights into tuning the effect of irradiation to the magnetic properties of $(MnNiSi)_{1-x}(Fe_2Ge)_x$ for composition (x=0.34) that can be utilized in a wide range of magnetocaloric applications in highenergy radiation environments. The irradiation applied to the sample did not induce any structural or magnetic phase changes in the selected composition but modified the magnetic properties marginally.

Keywords: Magnetocaloric Effect, Multicaloric materials, Radiation effect, MTX alloys

Corresponding Authors: John Peter J. Nunez – nunezjj2@vcu.edu Ravi L. Hadimani – rhadimani@vcu.edu

Introduction

Magnetic refrigeration based on magnetocaloric effect (MCE) at room temperature is considered a promising substitution for classical vapor compression systems due to its high efficiency and environmental friendliness. Various materials systems and their magnetocaloric properties have been studied and reported in the literature [1–7]. Although rare-earth-based magnetocaloric materials such as Gd₅(Si_xGe_{1-x})₄ exhibit remarkably high isothermal entropy change near room temperature, they are expensive and need complex and prolonged thermal treatment procedures [8–11]. Some of these materias have been studied for biomedical applications due to their extreme magnetic property changes at transition temperatures [12-15]. (MnNiSi)_{1-x}(Fe₂Ge)_x belongs to the MTX system where M and T are transition metals such as Mn, Fe, Ni, and Co and X is a p-block element such as Si, Ge, Ga or Sn are attractive multicaloric materials that change their magnetic properties with the application of magnetic field, pressure, and temperature [6,16,17]. In addition to their potential refrigeration and cooling effect, they exhibit large magnetostriction/volumetric strain upon application of a magnetic field and pressure near room temperature. These properties make this material system attractive for sensor and actuator applications. The transition temperature of the MTX system on which the material system this study utilized most, specifically the X = 0.34 composition can be tuned by varying the composition of constituent materials. MnTX (T = Co, Fe, Ni; X = Si, Ge), the composition utilized in this study, x = 0.34 exhibits a first-order magnetic phase transition from a paramagnetic (PM) to a ferromagnetically ordered state and a structural transition from a high-temperature Ni₂In-type hexagonal phase (P63/mmc) to a low-temperature TiNiSi-type orthorhombic structure (Pnma) with the hexagonal phase having the smallest unit cell volume [6]. By controlling the composition by doping, or isostructural substitution, it is possible to bring the two transitions close together so that the magnetic and structural transitions become coupled hence, designing magnetocaloric materials to a specific temperature range. Furthermore, at this magneto-structural transition, there is a large decrease in the volume of the unit cell (3%-4%), and the transition temperature becomes highly sensitive to the application of hydrostatic pressure.

Materials that undergo a first-order phase transition and or high accompanied strain will experience training effects due to the generation of micro-cracks or a substantial number of dislocations. These defects progressively increase and deteriorate magnetocaloric and strain effects over the life span of the material operation. In addition to defects formed due to large strain from the first-order phase transition, materials also experience the generation of defects from ionizing radiation. Several researchers have reported significant effects of various types of radiation magnetocaloric materials [18–20]. The effect of proton irradiation in magnetocaloric material, La(Fe_{0.89}Si_{0.11})₁₃ resulted in an increase in atomic displacement as the increase of lattice constant and Curie temperature. Moreover, the maximum hysteresis loss almost disappeared, and the relative cooling power increased slightly under proton irradiation [19]. Nanocrystalline materials should present a better irradiation resistance compared with large-grain materials because the large volume fraction

of grain boundaries acts as an important aspect for irradiation-induced defects [21]. Assar et al. have focused more on gamma-ray irradiation techniques where the magnetic materials studied were Mg-Cu-Zn and Ni-Cu-Zn ferrites. The authors have shown that gamma-ray irradiation on the Mg-Cu-Zn increased the saturation and remnant magnetization [22]. Mane et al. reported that laser irradiation on polycrystalline cobalt ferrite resulted in an increase in saturation magnetization as laser dose increased in hysteresis loops [23]. In this paper, we investigated primarily on x-ray radiation effect on $(MnNiSi)_{1-x}(Fe_2Ge)_x$ for composition x= 0.34 as this composition has a T_c at approximately room temperature. We have shown that x-ray irradiation did change the magnetization, saturation magnetization permeability, and coercivity but did not affect the isothermal entropy change at a field change of 3T.

Experimental Procedure

Material Synthesis: Polycrystalline (MnNiSi)_{1-x}(Fe₂Ge)_x (x=0.34) samples were prepared by arcmelting the constituent elements of purity better than 99.9% in an ultrahigh purity argon atmosphere. The mass of all the elements was selected based on the nominal stoichiometric composition. Arc-melting was conducted several times to ensure sample homogeneity. The stoichiometric composition of X = 0.34 was used for this study and additional details on the preparation of this magnetocaloric material are found in Clifford et al. [6] and Deepak et al. [7]. *X-ray Irradiation*: The experimental procedure for this study utilized X-ray radiation from X-RAD 225XL Precision X-Ray with a tungsten target set at 225 kV, 13.3 mA. As shown in Fig. 1, The sample was irradiated with a continuous sweeping rate of ~>120 Gy/min. X-rays were emitted from the x-ray source in a cone beam with a beam angle of 40 degrees. The uniformity of the beam changes significantly from the outer perimeter thus it collimated the beam angle to 31.4 degrees to achieve a homogenous x-ray beam across the field of radiation. The study proposes that there is an observable effect in the (MnNiSi)_{1-x}Fe₂Ge_x system particularly, for the composition x = 0.34 composition when exposed to an intense amount of X-ray radiation absorbed dose up to ~35kGy.

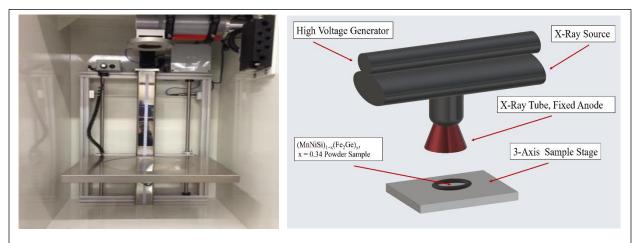


Fig 1. Experimental setup of the X-rad 225 XL for irradiation treatment of $(MnNiSi)_{1-x}(Fe_2Ge)_x$, where x = 0.34

XRD: Multipurpose X-Ray Diffractometer using a Copper Ka X-Ray radiation source ($\lambda = 1.54060 \text{ Å}$) in determining the crystalline structure of the (MnNiSi)_{1-x}(Fe₂Ge)_x, where x = 0.34 and any changes associated to irradiation. For this purpose, powders of non-irradiated and irradiated materials were placed onto a silicon wafer in the spinner stage of the X-ray Diffractometer.


Magnetic Characterization: A Quantum Design physical property measurement system (PPMS) was used to measure the magnetization (M) of the $(MnNiSi)_{1-x}(Fe_2Ge)_x$ samples within the temperature interval of 200–345 K and, depending on the analysis, within the applied magnetic fields from -3T to 3T.


Isothermal Entropy Calculations: The Curie temperature, T_c was determined as the inflection point of the magnetothermal data collected upon heating at a sweep rate of 5 K/min where the derivative with the lowest value between magnetization and temperature was calculated. The magnetocaloric response, entropy change ΔS_{mag} of the pristine and irradiated samples was calculated by Maxwell relationship applied to the specified isotherms measured at an interval of 2.5 K near the transition temperature and 5 K intervals away from the transition temperature under an applied field of $0T \le H_{app} \le 3T$.

Results and Discussions: XRD and magnetic measurement results including M vs. T, M vs. H, hysteresis, and ΔS vs. T are presented in this section.


XRD Analysis:

The XRD patterns for the pre-and post-irradiated samples are shown in Fig. 2. Their crystalline structure was found to be a hexagonal Ni₂In-type structure (P6₃/mmc space group) and orthorhombic (Pnma) TiNiSi-type crystal structure. The patterns of the irradiated samples show slight changes to their peak intensity ratio but do not show peak shifting compared to non-irradiated, which indicates little changes in the interplanar distances. Furthermore, the peaks did not reveal significant changes in the full-width half maximum (FWHM) after sample irradiation.

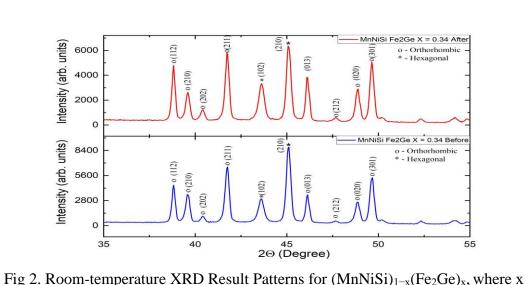





Magnetic Property Changes:

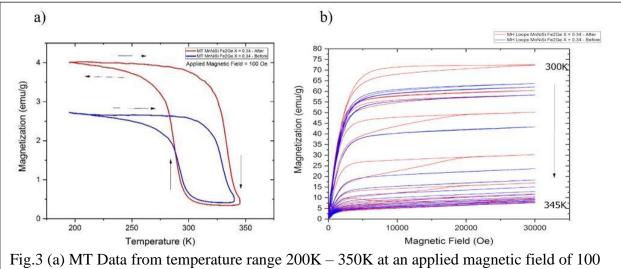

Oe. (b) MH Loops (heating) 300K – 345K exhibiting induced hysteresis.

Fig. 3 (a) shows the MT (magnetization vs temperature) data from 200K to 350K at an applied magnetic field of 100 Oe. The red-labeled plots are the reported magnetic properties results of the irradiated sample and the blue-labeled plots are for the pristine sample respectively. The samples exhibited first-order magneto-structural phase transition temperatures indicated by a large thermal hysteresis at the transition temperature in both the pristine and irradiated samples. The dM/dT curves (not presented in the paper) showed a first-order phase transition temperature at $T_c = \sim 292K$ for the pristine sample before irradiation treatment and at $T_c = \sim 286K$ for the irradiated sample. The phase transition is almost complete at 350K but would have continued completed at a slightly higher temperature if the measurement were conducted beyond 350K. There was also a notable change in the saturation magnetization at 100 Oe from 2.72 emu/g to 4.01 emu/g with an estimated increase of ~ 47.4% between the pristine and irradiated samples. Fig. 3 (b) presents the MH

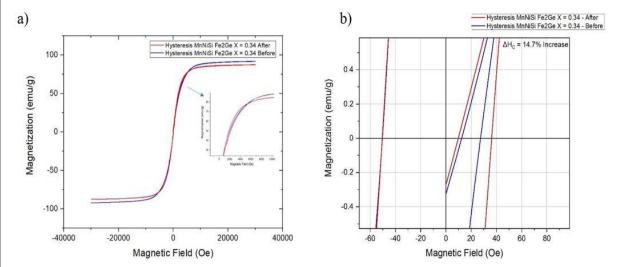



(magnetization vs. magnetic field) loops from 300K to 345K with an applied magnetic field range of 0 to 30,000 Oe (μ_0 H= 3Tesla). It is evident from the measurement that (MnNiSi)_{1-x}(Fe₂Ge)_x, x = 0.34 exhibited irradiation-induced magnetic hysteresis in comparison to the pristine sample, more specifically in the range of 300K to 320K, which is near T_c as observed from Fig 4(a). It can also be seen from the isotherms that the magnetization of the irradiated sample at 300K is higher than the magnetization of the pristine sample at the same temperature. This is consistent with MT measurements, where pristine samples show lower magnetization as compared to the irradiated sample. Irradiation showed to change the magnetic properties marginally. However, the selected dose didn't induce a structural or magnetic phase change in the material for this composition in both M vs. T or M vs. H measurements near the transition temperature.

Fig. 4 (a) presents the hysteresis graphs at T = 200K of the before and after 5-hour treatment. As observed in the presented results, the (MnNiSi)_{1-x}(Fe₂Ge)_x sample that underwent irradiation treatment shows a small decrease in saturation magnetization. However, it can then be seen on the enlarged image that the results correspond to previously reported results that magnetization is higher for the irradiated sample before saturation than the pristine sample. T = 200 K was the temperature selected as the range is away from T_c and the saturation reported in the figure is the true saturation of (MnNiSi)_{1-x}(Fe₂Ge)_x. The increase in the coercivity could be attributed to reversible or irreversible defect formation due to irradiation. We have noticed the sample left for several days showed recovery in magnetic property changes (not presented in the paper). This

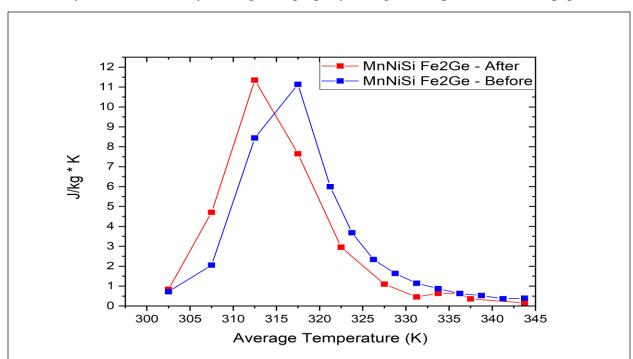


Fig. 5 Magnetic entropy change for a magnetic field change of 3 T before irradiation (blue) treatment of $(MnNiSi)_{1-x}(Fe_2Ge)_x$, where x = 0.34 and magnetic entropy change curve after irradiation (red) treatment of $(MnNiSi)_{1-x}(Fe_2Ge)_x$, where x = 0.34

could be due to the annihilation of reversible defects (dislocation) from the room-temperature thermal energy. Further systematic studies are needed to investigate the time-dependent recovery in magnetic property changes. Fig. 4 (b) exhibits an observable change of $\Delta H_c = 14.7\%$ which revealed a 10 Oe increase in the magnetic coercivity of (MnNiSi)_{1-x}(Fe₂Ge)_x, x = 0.34 at 200K after irradiation treatment.

Temperature-dependent magnetic entropy curves with instantaneous and applied magnetic field of $\mu_0 H = 0T$ and 3T were calculated from the MH isotherms in the range of 300-350 K using Maxwell's relations for before and after irradiation-treated samples. Fig. 5 presents a maximum entropy change for the irradiated sample at ΔS_{mag} at ~ 11.349 J/kgK and a T_{ave} peak of 312.5 K. Moreover, the pristine sample in Fig. 5 shows maximum entropy change at ΔS_{mag} at ~ 11.139 J/kgK and a T_{ave} peak of 317.5 K. There was a slight difference in its entropy change value and a difference of 5K in the average temperature where it had its major ΔS_{mag} peak. The peak ΔS_{mag} values at the transition temperature are lower than the bulk samples reported in the literature [6] which is because of the powdered nature of our samples used for irradiation.

Conclusions

The powdered samples of the $(MnNiSi)_{1-x}(Fe_2Ge)_x$ with composition x=0.34 were irradiated with X-ray radiation absorbed dose up to ~35kGy. The samples' magnetic properties were characterized and showed that the irradiated samples show higher magnetization at saturation when measured between 200 to 350K with $T_c = 292K$ for the pristine sample before irradiation treatment and 286K for the irradiated sample. Irradiate samples exhibited irradiation-induced magnetic hysteresis in comparison to the pristine sample in the range of 300K to 320K. The samples' magnetocaloric effect was not affected by irradiation. Isothermal entropy change, ΔS_{mag} in the temperature range of 200-350 K with an applied magnetic field change, ΔH of 3T was 11.349 J/kgK for the irradiated sample and 11.139 J/kgK for the pristine sample. Thus, this study demonstrated that prolonged exposure to multicaloric materials that undergo structural phase transition can change magnetic properties, including the phase transition temperature. Although our study did not observe changes in isothermal entropy due to irradiation, however, changes in transition temperature can affect the operating parameters such as the temperature range of the multicaloric materials. The increase in coercivity due to irradiation can induce additional heat generated from the magnetic hysteresis during the high-frequency operation. Further studies are needed to investigate if higher doses of irradiation induce magnetic or structural phase transition.

Acknowledgments

The authors would like to acknowledge the Dean's Undergraduate Research Initiative Fellowship – VCU College of Engineering awarded to John Peter J. Nunez and Ravi L. Hadimani.

References:

- V. K. Pecharsky and Jr. Gschneidner K. A., Tunable Magnetic Regenerator Alloys with a Giant Magnetocaloric Effect for Magnetic Refrigeration from [Bold ~]20 to [Bold ~]290 K, Applied Physics Letters 70, 3299 (1997).
- [2] J. Liu, T. Gottschall, K. P. Skokov, J. D. Moore, and O. Gutfleisch, Giant Magnetocaloric Effect Driven by Structural Transitions., Nature Materials **11**, 620 (2012).
- [3] V. Franco, J. S. Blázquez, J. J. Ipus, J. Y. Law, L. M. Moreno-Ramírez, and A. Conde, Magnetocaloric Effect: From Materials Research to Refrigeration Devices, Progress in Materials Science 93, 112 (2018).
- [4] E. Brück, O. Tegus, D. T. Cam Thanh, N. T. Trung, and K. H. J. Buschow, A Review on Mn Based Materials for Magnetic Refrigeration: Structure and Properties, International Journal of Refrigeration 31, 763 (2008).
- [5] J. Lyubina et al., Magnetocaloric Materials for Energy Efficient Cooling, Journal of Physics D: Applied Physics **50**, 053002 (2017).
- [6] D. Clifford, V. Sharma, K. Deepak, R. V. Ramanujan, and R. Barua, Multicaloric Effects in (MnNiSi)1-x (Fe2Ge)x Alloys, IEEE Transactions on Magnetics 1 (2020).
- K. Deepak and R. V. Ramanujan, "Near room temperature giant magnetocaloric effect in (MnNiSi)1-x(Fe2Ge)_x alloys," *Journal of Alloys and Compounds*, vol. 743, pp. 494–505, 2018.
- [8] V. K. Pecharsky and K. A. Gschneidner Jr., Gd5(SixGe1-x)4: An Extremum Material, Advanced Materials **13**, 683 (2001).
- [9] R. L. Hadimani, Y. Melikhov, J. E. Snyder, and D. C. Jiles, Field Induced Structural Phase Transition at Temperatures above the Curie Point in Gd[Sub 5](Si[Sub x]Ge[Sub 1-x])[Sub 4], Journal of Applied Physics 105, 07A927 (2009).
- [10] R. L. Hadimani, P. a. Bartlett, Y. Melikhov, J. E. Snyder, and D. C. Jiles, Field and Temperature Induced Colossal Strain in Gd5(SixGe1-x)4, Journal of Magnetism and Magnetic Materials 323, 532 (2011).
- [11] J. H. Belo et al., Giant Negative Thermal Expansion at the Nanoscale in the Multifunctional Material Gd5(Si, Ge)4, Phys. Rev. B 100, 134303 (2019).
- [12] A. ur Rashid and S. Manzoor, Optimizing Magnetic Anisotropy of La1-xSrxMnO3 Nanoparticles for Hyperthermia Applications, Journal of Magnetism and Magnetic Materials 420, 232 (2016).
- [13] A. A. El-Gendy, S. M. Harstad, V. Vijayaragavan, S. Gupta, V. K. Pecharsky, J. Zweit, and R. L. Hadimani, Ferromagnetic Gd5Si4 Nanoparticles as T2 Contrast Agents for Magnetic Resonance Imaging, IEEE Magnetics Letters 8, 1507504 (2017).

[14] S. G. Hunagund, S. M. Harstad, A. A. El-Gendy, S. Gupta, V. K. Pecharsky, and R. L. Hadimani, Investigating Phase Transition Temperatures of Size Separated Gadolinium Silicide Magnetic Nanoparticles, AIP Advances **8**, 056428 (2018).

- [15] G. Naresh, J. P. Borah, C. Borgohain, and N. Paul, Synthesis, Characterization and Effect of Dopant on Magnetic Hyperthermic Efficacy of Gd2O3 Nanoparticles, Mater. Res. Express 8, 115014 (2021).
- [16] T. Q. Hartnett, V. Sharma, S. Garg, R. Barua, and P. V. Balachandran, Accelerated Design of MTX Alloys with Targeted Magnetostructural Properties through Interpretable Machine Learning, Acta Materialia 231, 117891 (2022).
- [17] C. L. Zhang, H. F. Shi, E. J. Ye, Y. G. Nie, Z. D. Han, B. Qian, and D. H. Wang, Magnetostructural Transition and Magnetocaloric Effect in MnNiSi-Fe2Ge System, Appl. Phys. Lett. **107**, 212403 (2015).
- [18] S. Sun, H. Qin, H. Wang, R. Ning, Y. Zhao, J. Zhu, Z. Gao, D. Cong, Y. Wang, and W. Cai, Colossal Magnetocaloric Effect in Ni–Co–Mn–In Alloys Induced by Electron Irradiation, Materials Today Energy 18, 100533 (2020).
- [19] S. J. Kim, K. J. Lee, M. H. Jung, H. J. Oh, and Y. S. Kwon, Magnetocaloric Effect in La(Fe0.89Si0.11)13 Irradiated by Protons, Journal of Magnetism and Magnetic Materials 323, 1094 (2011).
- [20] S. Cervera et al., Modulating the Phase Transition Temperature of Giant Magnetocaloric Thin Films by Ion Irradiation, Phys. Rev. Materials **1**, 065402 (2017).
- [21] Y.-Q. Chang, Q. Guo, J Zhang, L.Chen, Y.Long, and F.-R. Wan, "Irradiation effects on nanocrystalline materials," Frontiers of Materials Science, vol. 7, no. , pp. 143-155, (2013).
- [22] S.T. Assar, H. F. Abosheiasha, and A. R. El Sayed, "Effect of γ-rays irradiation on the structural, magnetic, and electrical properties of Mg–Cu–Zn and Ni–Cu–Zn ferrites," *Journal* of Magnetism and Magnetic Materials, vol. 421, pp.355-367, (2017).
- [23] M. L. Mane, V. N. Dhage, S. E. Shirsath, R. Sundar, K. Ranganathan, S. M. Oak, and K. M. Jadhav, "Nd:YAG laser irradiation effects on the structural and magnetic properties of Polycrystalline Cobalt Ferrite," *Journal of Molecular Structure*, vol. 1035, pp. 27–30, 2013.