

Near-Atomic Scale Perspective on the Oxidation of $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes: Insights from Atom Probe Tomography

Mathias Krämer¹, Bar Favelukis², Ayman A. El-Zoka^{1,3}, Maxim Sokol², Brian A. Rosen², Noam Eliaz², Se-Ho Kim^{1,4,*}, and Baptiste Gault^{1,3,*}

¹Max-Planck-Institut für Eisenforschung, Max-Planck-Straße 1, 40237 Düsseldorf, Germany

²Department of Materials Science and Engineering, Tel Aviv University, P.O.B 39040, Ramat Aviv 6997801, Israel

³Department of Materials, Royal School of Mines, Imperial College London, London, SW7 2AZ, United Kingdom

⁴Department of Materials Science and Engineering, Korea University, Seoul 02841, Republic of Korea

*Corresponding authors: sehonetkr@korea.ac.kr, b.gault@mpie.de

Abstract

MXenes are a family of 2D transition metal carbides and nitrides with remarkable properties and great potential for energy storage and catalysis applications. However, their oxidation behavior is not yet fully understood, and there are still open questions regarding the spatial distribution and precise quantification of surface terminations, intercalated ions, and possible uncontrolled impurities incorporated during synthesis and processing. Here, atom probe tomography analysis of as-synthesized $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes reveals the presence of alkali (Li, Na) and halogen (Cl, F) elements as well as unetched Al. Following oxidation of the colloidal solution of MXenes, it is observed that the alkalis enriched in TiO_2 nanowires. Although these elements are tolerated through the incorporation by wet chemical synthesis, they are often overlooked when the activity of these materials is considered, particularly during catalytic testing. This work demonstrates how the capability of atom probe tomography to image these elements in 3D at the near-atomic scale can help to better understand the activity and degradation of MXenes, in order to guide their synthesis for superior functional properties.

Keywords

atom probe tomography, 2D materials, MXene, nanowires, oxidation

The discovery of MXenes by the Barsoum and Gogotsi groups in 2011 has reignited scientific interest in 2D and layered materials [1]. To date, numerous MXenes have been synthesized [2], and are being intensively studied and tested in applications including supercapacitors and batteries [3, 4], optoelectronics [5], catalysis [6], and biosensors or antibacterial membranes [7, 8]. Their properties and performance in various applications are significantly affected by unavoidable surface terminations, denoted by T_x in the chemical formula, which saturate the bare MXene surface during synthesis [9]. Changes in the electronic properties of the MXenes, for example, have been explained by careful consideration of these functional groups and possible intercalants originating from wet chemical synthesis [10]. Using them to fine-tune properties would require establishing relationships between activity and their spatial distribution and concentration, which remain extremely difficult to characterize.

Atom Probe Tomography (APT) is one of the few techniques that can measure composition in 3D at the near-atomic scale [11]. In recent years, the application of APT to nanoparticles [12–14], nanowires [15, 16] and nanosheets [17] has triggered a reckoning that the detailed composition and the presence of trace impurities are of paramount importance when it comes to understanding the activity of nanomaterials [18]. Impurity elements in the raw materials used during the synthesis may not react at the same rate and hence be preferentially incorporated into the final product [17], or may be incorporated into the structure during processing or synthesis by wet chemistry [19, 20]. For MXenes and their surface terminations, most studies to date have relied on X-ray spectroscopy and electron microscopy techniques for compositional measurements [21–25], leaving many questions unanswered that could be potentially be addressed by using APT. However, APT has never been applied to MXenes before.

As the structural and chemical stability of MXenes can also be extremely fragile, APT could also be a tool for better understanding the mechanisms behind the degradation. MXenes degrade particularly fast in an oxidizing environment (H_2O , O_2 , etc.), leading to their transformation into transition metal oxides [26, 27]. Oxidation, in its early stage, can affect the surface terminations [28] and thus the properties. For example, an increased concentration of O functional groups results in an increased catalytic activity [29]. Several studies have demonstrated how further oxidation severely destroys the integrity of the MXene structure, thereby limiting its lifetime in service and precluding many useful applications due to a decrease in the properties of interest [30–33]. Although efforts have been made to understand the details of their evolving chemistry during oxidation [34, 35], some questions are still unanswered, such as the role of non-O surface terminations, intercalants or impurities from synthesis. Designing MXenes with improved oxidation resistance is therefore extremely challenging, and for this reason the improvement of chemical and temperature stability of MXenes is considered in the community to be one of the research challenges of this decade [36].

In order to further the understanding of the chemical evolution of colloidal $Ti_3C_2T_x$ MXene solution, we introduce here the first APT analyses of as-synthesized MXenes, alongside with the transition metal oxides formed during oxidation. APT revealed the

incorporation of alkali (Li, Na) and halogen (Cl, F) elements into the MXene nanosheets, probably inherited from the synthesis. Following oxidation, these elements remained within the newly formed TiO_2 nanowires, indicating that they lowered their free energy and helped to stabilize them. Although most of these elements are considered to be an essential part of the MXenes themselves, these results emphasize that discussions of the activity of MXene-based materials, including throughout oxidation, should take account of them, which are likely to play an important role in the activity [37] and their resistance to degradation.

$\text{Ti}_3\text{C}_2\text{T}_x$ MXenes were synthesized by wet chemical etching of the Al layer from a Ti_3AlC_2 MAX phase via the HCl-LiF route (synthesis of both materials is described in detail in the Supporting Information). In Figure 1 (a), the as-synthesized MXenes shows very clean edges and a defect-free surface, suggesting no major internal defects. Small black dots on the edges may indicate the formation of oxidation products immediately after synthesis. To observe the oxidation of the nanosheets with electron microscopy, the colloidal $\text{Ti}_3\text{C}_2\text{T}_x$ MXene solution was kept at a temperature below 5°C throughout the oxidation experiment, as described in Ref. [38].

Oxidation of the nanosheets in the colloidal solution may have started from the edges due to local structural variations [39], where nanoparticles were observed in Figure 1 (b). Previous research has reported the formation of carbon-supported anatase during the oxidation of $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes [40], indicating that the nanoparticles formed are TiO_2 . Because atomic vacancies and microstructural defects such as wrinkles are unavoidable in the course of the wet chemical synthesis processes, these preexisting defects on the $\text{Ti}_3\text{C}_2\text{T}_x$ MXene may have created a local electric field that drives the development of the TiO_2 particles by promoting the migration of both Ti cations and electrons [41]. These pinhole defects then gradually evolved into larger voids, resulting in the degradation and accelerated oxidation of the MXene structure. Zhang et al. [42] reported that oxidation starts at the defective edges of the MXene sheets and propagates inwards, causing cracks to nucleate and grow. This so-called 'scissor effect' shreds the MXene sheets into small pieces and leads to a complete loss of the original structure of the MXene into TiO_2 debris, such as those imaged in Figure 1 (c).

Dense and sharp needle-shaped APT specimens containing either the as-synthesized or the oxidized $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes were prepared from a nanosheet-metal composite (detailed APT specimen preparation is provided in the Supporting Information). The electrodeposition within a metallic matrix, used as an encapsulating material, increases the success rate and data quality [43, 44]. Here, a Co matrix was used, which, compared to the more commonly used Ni, presents the advantage of having only a single isotope, making it less likely to create peaks that can obscure the signal from the material of interest in the APT mass spectrum. For example, the use of Ni would cause an unavoidable peak overlap with TiO molecular ions in the APT mass spectrum [16].

The reconstructed 3D atom map in Figure 2 (a) shows the $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes nanosheets with a complex 2D morphology, likely arising from agglomerated or folded nanosheets. These are embedded in Co, shown in yellow. Differences in the evaporation field between the matrix and the nanosheets lead to an irregular curvature of the end surface of the specimen, which results in trajectory aberrations, varying magnification and intermixing

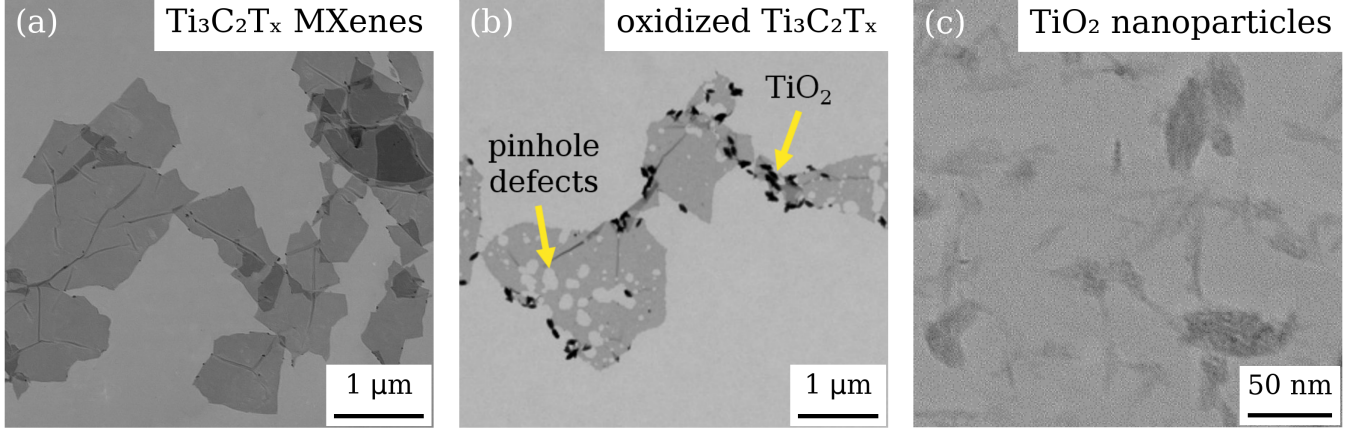


Figure 1: Oxidation processes of the $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes. (a) As-synthesized $\text{Ti}_3\text{C}_2\text{T}_x$ MXene nanosheets. (b) Oxidized $\text{Ti}_3\text{C}_2\text{T}_x$ MXene after storage in a colloidal solution in a refrigerator. (c) TiO_2 nanoparticles as products of $\text{Ti}_3\text{C}_2\text{T}_x$ MXene oxidation.

zones in the reconstruction [45]. An indicative thickness at full width at half maximum of 3.2 nm was obtained by evaluating the Co 1D composition profile in Figure 2 (b). The nominal thickness of a $\text{Ti}_3\text{C}_2\text{T}_x$ monolayer has been reported to be within the order of 1 nm to 1.5 nm [46, 47], whereas the interlayer distance between two separate nanosheets can vary depending on the intercalated species [48]. A single nanosheet or stack of up to three $\text{Ti}_3\text{C}_2\text{T}_x$ nanosheets was hence analyzed.

A region of interest, delineated by the dark green-cyan iso-composition surface, encompassing regions in the 3D atom map containing over 6 at.% Ti, in Figure 2 (a), was extracted to exclude the Co matrix and any CoO layer from electrodeposition for compositional analysis. Compared to the nominal value of 1.5, the atomic ratio of Ti to C was measured to be 2.2. Losses of C have been reported in the APT analysis of carbides [49–51], depending on the analysis conditions, and partly due to detector saturation associated with two $^{12}\text{C}^+$ ions [52]. Importantly, it has been questioned whether most MAX phases and their derived MXenes are actually pure carbides or rather oxycarbides [53]. Pure carbides may be more resistant to oxidation than oxycarbides, as recent results suggest [53, 54].

The specimen was analyzed immediately after synthesis; however, a significant amount of O was measured in the material, approximately 46.7 at.%. The presence of O can be attributed to synthesis in an aqueous solution, as the highly reactive surface is immediately bonded to, for example, O or OH. Previous reports have shown that under certain controlled high vacuum conditions in the transmission electron microscope the O surface terminations can reach a supersaturation level of 41 at.% while retaining the $\text{Ti}_3\text{C}_2\text{T}_x$ MXene nanosheet structure [28], and the MXenes directly used from the solution were unlikely to be already oxidized MXenes. However, the measured amount of O was not entirely attributable to O or OH surface terminations, but was also associated with weakly bonded water molecules to these surface terminations. Besides ion

intercalation, intercalation of water molecules is a crucial factor for the aqueous MXene delamination [55]. Intrinsically hygroscopic cations, such as Li^+ and Na^+ , which were also detected as discussed below, also increase the amount of intercalated water molecules [56]. Characteristic peaks in the mass spectrum at 17, 18, and 19 Da confirmed the evaporation of H_{1-3}O^+ molecular ions, while peaks at 81, 82, 83, 84, and 85 Da, partially overlapping with peaks from TiO_2^+ , were attributed to the evaporation of $\text{TiO}(\text{OH}_3)^+$. Quantification of the H content was deliberately omitted, as it is known to be extremely challenging from APT to distinguish between H from the analysis chamber and the sample in form of OH surface terminations or intercalated water molecules itself [57]. In the future, isotopic labeling using heavy water (D_2O) during MXene synthesis may clarify the controversial question of the intrinsic existence of OH terminations on the MXene surface [21, 58, 59].

Not entirely unexpected, several functional surface terminations, intercalated elements, and impurities including Cl, F, Li, Na, and Al were also incorporated and could be quantified within the extracted region of interest of the $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes. The incorporation of Cl and F results from the wet chemical etching process of Al from the precursor MAX phase and the synthesis of delaminated MXenes. High concentrations of HCl and LiF are used in the wet chemical synthesis [60, 61]. Here, the Cl content was measured to be 2.49 at.%. Accurate quantification of the amount of F was complicated by the overlapping peaks of F^+ and H_3O^+ in the mass spectrum region at 19 Da. However, TiF^{2+} molecular ions were measured (see the mass spectrum in the Supporting Information), so that the F content could be quantified to at least 1.16 at.%. Tuning the termination groups on the surface of the MXene may influence its oxidation stability, for instance, Cl-terminated MXenes have been shown to have higher stability than F-terminated MXenes [62].

Despite vigorous washing protocols, residuals of Li and Na elements were still present in the analyzed material at 0.02 at.% and 0.11 at.%, respectively. The amount of Na was obtained by means of a peak decomposition with the overlapping peak of $^{46}\text{Ti}^{2+}$ at 23 Da. Na likely originated as an impurity in the synthesis chemicals, as was similarly observed for MoS_2 synthesized by wet chemistry [17]. For example, Na is a known impurity even in high-purity Li salts for battery applications [63, 64], and here LiF (99 %) was used during synthesis. It should be noted that the spatial resolution of APT [65] does not allow to conclude whether these alkali impurities are on the surface or integrated into the structure of a single layer MXene. Due to electrostatic effects, these elements could be absorbed on the surface to stabilize it [66], or they could spontaneously intercalate between two MXene layers [67], as is even desired in the case of Li in the synthesis route used here. The presence of Li or Na atoms on the surface may also directly impact the properties by intercalation doping [68], which should grant further targeted investigations.

The complete removal of residual Al atoms is possible by harsh HF etching, often confirmed by X-ray (photoelectron) spectroscopy [69]. Although the wet etching environment removes the Al layers within the MAX phase by mixing HCl and LiF to form in situ HF, and the desired MXenes were rinsed seven times with deionized water, a trace amount of Al residual atoms at 0.17 at.% was still measured within the $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes.

Figure 3 (a) shows the reconstructed 3D atom map of the MXene oxidized in the colloidal solution. The structures highlighted by red iso-compositional surfaces of 0.5 at.% TiO_2

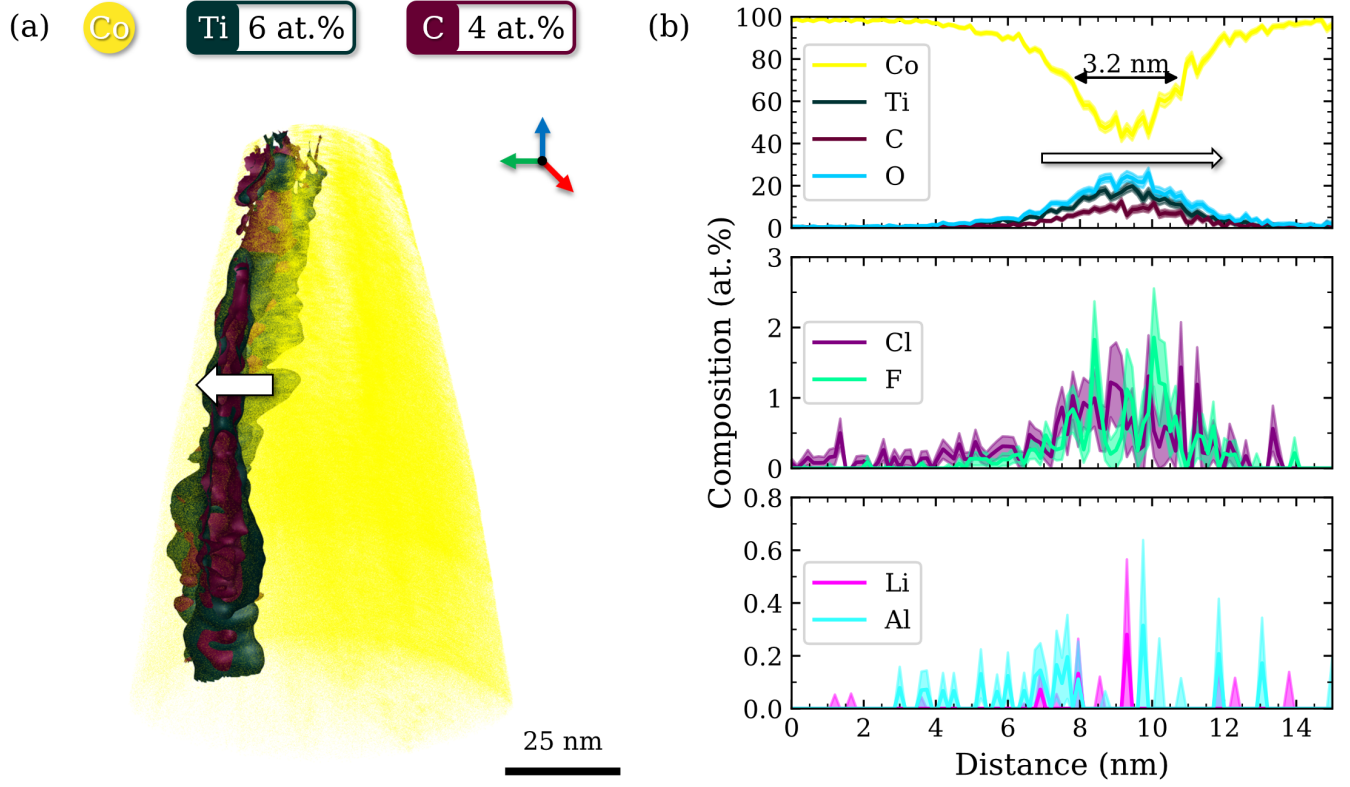


Figure 2: APT analysis of as-synthesized $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes. (a) Reconstructed 3D atom map. Agglomerated $\text{Ti}_3\text{C}_2\text{T}_x$ MXene nanosheets are highlighted by a dark green-cyan iso-compositional surface at 6 at.% Ti and a reddish-purple iso-compositional surface at 4 at.% C. (b) 1D compositional profile ($\varnothing 15 \text{ nm} \times 15 \text{ nm}$) across the agglomerated MXenes as indicated in (a).

are similar to those imaged by scanning transmission electron microscopy in Figure 1 (c), which have a nanowire-like morphology. The atomic ratio of Ti to O within the extracted oxide particle, indicated by the black box, was measured to be 0.54, which is close to the stoichiometric ratio of TiO_2 . Changes in the acquisition parameters in APT [70] or a slight O deficiency could be responsible for the off-stoichiometry of TiO_2 . Figure 3 (b) is a close-up of one of these nanowire-like structures with distribution maps of the individually detected elements. The measured impurity contents of C, Cl, F, Li, and Na were 2.09, 2.58, 1.62, 0.79, and 0.71 at.%, respectively. 54 ± 30 atomic parts per million of Al was collected in the oxidized MXene.

Overall, the oxidation reaction of the MXene led to an enrichment of alkali elements and a depletion of unetched Al, as visualized in Figure 4. Oxidation of Al to Al_2O_3 [71] may be responsible for the depletion of Al, as the Al_2O_3 and TiO_2 phases have a positive mixing enthalpy [72], making the incorporation of Al in the TiO_2 phase unfavorable [73]. However, fundamental atomistic calculations comparing the stability of the incorporated alkali elements in the MXene and the oxide are missing. While the incorporation of Li into anatase TiO_2 is energetically feasible in general [74], Na is a known impurity of TiO_2

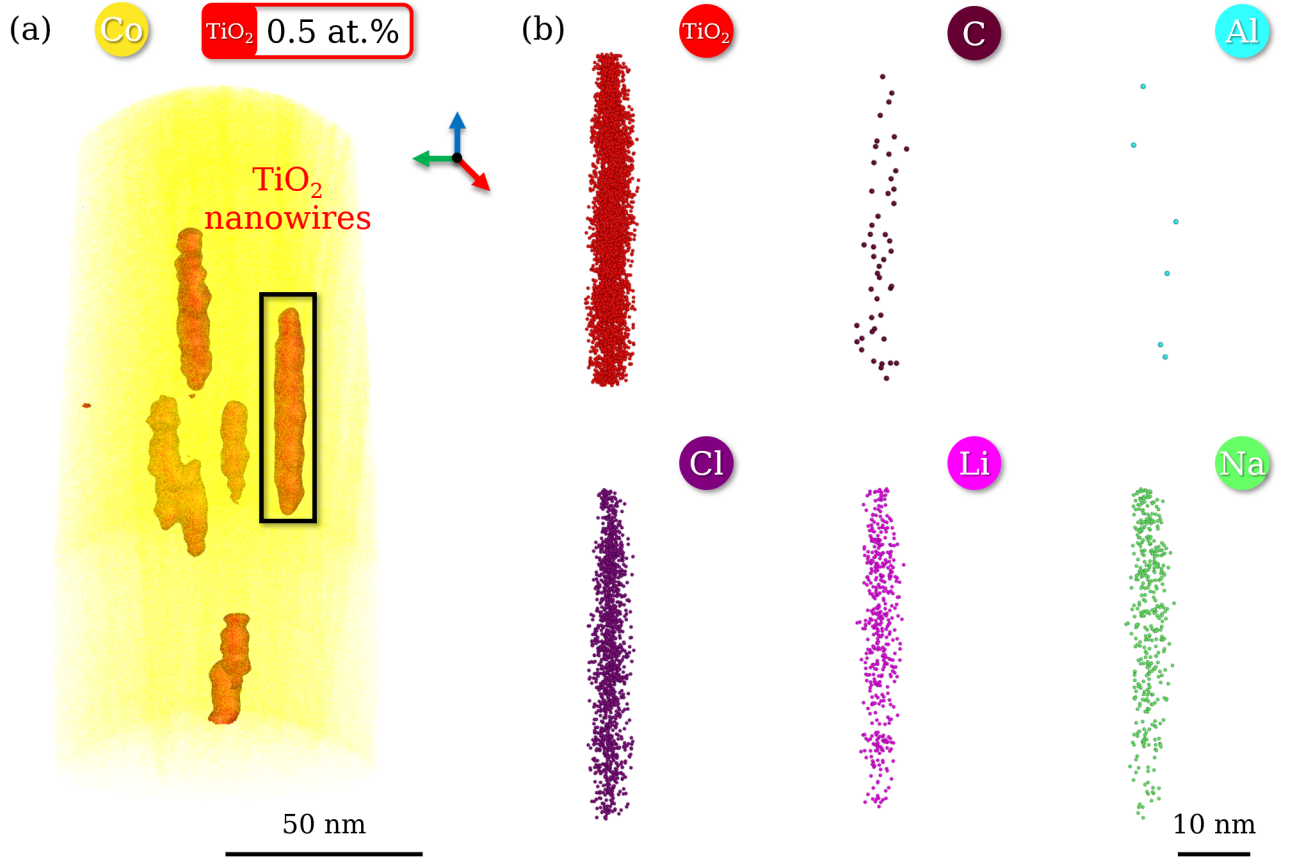


Figure 3: APT analysis of oxidized $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes. (a) Reconstructed 3D atom map. TiO_2 nanowires are highlighted by red iso-compositional surfaces at 0.5 at.%. (b) Molecular distribution map of TiO_2 and elemental distribution maps of impurity elements in the extracted region of interest indicated in (a).

synthesized on a soda-lime glass substrate [75]. Since several Li [76] and Na titanate derivatives [77–80] were synthesized by oxidative treatment of $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes with these alkali elements, it is reasonable to assume that they promote the formation of the oxide and stabilize it by lowering the free energy.

Because metal-semiconductor heterostructures can provide rapid separation of photo-generated charge carriers [81], $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes were intentionally oxidized to form $\text{Ti}_3\text{C}_2\text{T}_x/\text{TiO}_2$ derivatives for photocatalysis [82–85]. Other promising applications for these derivatives include electrodes for supercapacitors [86] and lithium-ion batteries [87]. However, in our previous report on TiO_2 hollow nanowires, it was pointed out that the lack of precise characterization of impurities has an impact on the laboratory-synthesized TiO_2 properties, which vary and are inconsistent with reported results [16]. For example, incorporated Na influences the growth and crystallization of TiO_2 , and thus the resulting properties [75]. From this point of view together with the observations made in this study, the alkali elements may have a significant influence on the oxidation mechanism and its kinetics, and consequently also on the properties of the $\text{Ti}_3\text{C}_2\text{T}_x/\text{TiO}_2$ derivatives.

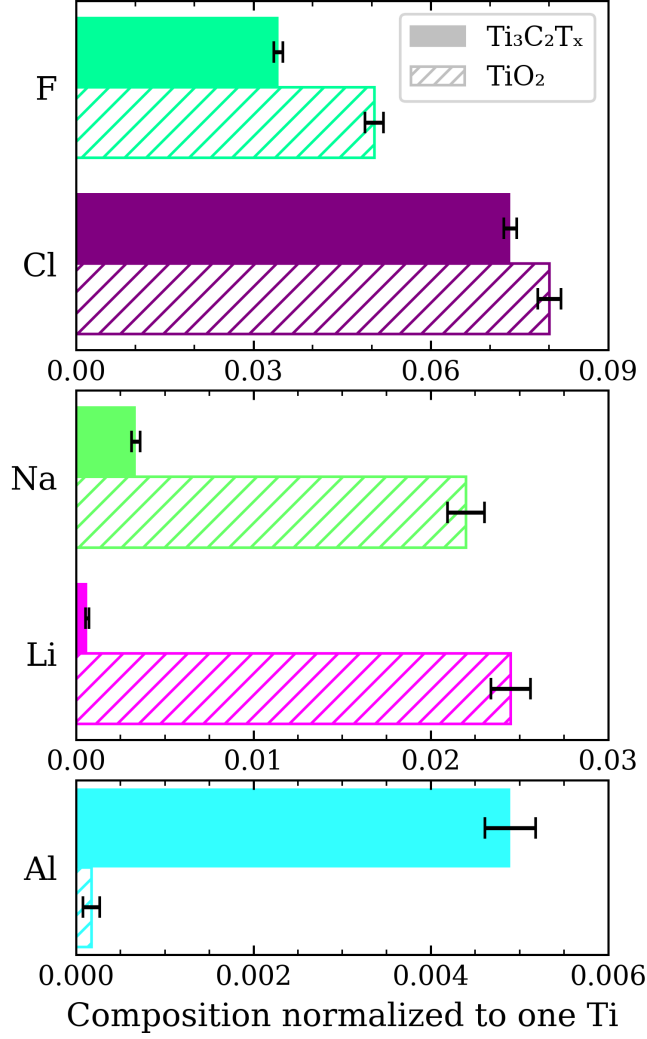


Figure 4: Comparison of the composition of the halogens, alkalis, and Al in the as-synthesized $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes and the oxidized TiO_2 . For easier comparability of the data, the compositions were normalized to one Ti (data given in at.% are provided in the Supporting Information).

In addition, the detected elements may also work as a dopant for both the as-synthesized $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes and oxidized TiO_2 . Doping is a proven and effective engineering strategy to enhance the performance of TiO_2 , particularly with alkalis and halogens. For instance, Li-doped TiO_2 has shown significantly improved properties by increasing electronic conductivity, and thus faster electron transport [88]. Density functional theory calculations predicted an influence of Cl- and F-doping on the band gap of TiO_2 [89] and incorporated Cl shifts the absorption edge to a higher wavelength [90], both effects enabling excellent photocatalytic activity. Doping TiO_2 with C can effectively facilitate photo-generated charge transfer and prevent electron-hole recombination [91]. Surface terminations such as halogens are likely to influence the band structure, as

functionalization of $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes with halogens could lead to the formation of Dirac cones near the Fermi level, resulting in semi-metallic behavior [92]. Experimentally, it was observed that preintercalated Na leads to a reduced diffusion barrier for Na ions and an increased number of active sites due to the increased interlayer spacing of the MXenes [93]. In summary, both alkali and halogen elements can affect the functional properties of $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes and the oxidized TiO_2 . It is therefore essential to study these incorporated elements on the near-atomic scale, for example using APT.

It has been recognized that the methods used to synthesize high-quality MXenes with chemical and structural stability can be critical. We have demonstrated the capability of APT to study the incorporation of alkalis and halogens as surface terminations, intercalated ions, or impurities introduced by the wet chemical synthesis of the MXenes. The alkali elements tended to further concentrate during the oxidation of the $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes to TiO_2 nanowires. Their presence may affect the physical properties of the MXenes themselves, but, importantly, this suggests that the presence and concentration of these elements may contribute to the oxidation mechanism and kinetics, by stabilizing the oxide to the detriment of the MXene itself. In the future, a broader understanding of the influence of these elements may enable targeted utilization to tailor the functional properties of the MXenes and their derived transition metal oxides.

Supporting Information Available

Synthesis of Ti_3AlC_2 MAX phase; Synthesis of $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes; Electron Microscopy; APT specimen preparation; APT analysis; Mass spectrum analysis

Acknowledgment

The authors acknowledge financial support from the German Research Foundation (DFG) through DIP Project No. 450800666. The support to the FIB and APT facilities at MPIE by Uwe Tezins, Andreas Sturm and Christian Broß is gratefully acknowledged.

Conflict of Interest


The authors declare no conflict of interest.

Data Availability Statement

The data that support the findings of this study are available from the corresponding author upon reasonable request.

Table of Contents

Following oxidation of $\text{Ti}_3\text{C}_2\text{T}_x$ MXenes, atom probe tomography reveals that alkalis concentrate in TiO_2 nanowires, indicating that their presence influences the oxidation mechanisms and kinetics. These results highlight how atom probe tomography can be utilized to better understand the functional surface terminations, intercalated ions or impurities that are inevitable in the wet chemical synthesis of MXenes.

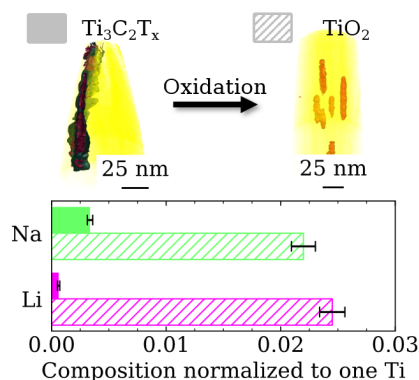

References

- [1] M. Naguib, M. Kurtoglu, V. Presser, J. Lu, J. Niu, M. Heon, L. Hultman, Y. Gogotsi, and M. W. Barsoum. “Two-Dimensional Nanocrystals Produced by Exfoliation of Ti_3AlC_2 .” In: *Advanced Materials* 23.37 (2011), pp. 4248–4253. DOI: 10.1002/adma.201102306.
- [2] M. Naguib, M. W. Barsoum, and Y. Gogotsi. “Ten Years of Progress in the Synthesis and Development of MXenes.” In: *Advanced Materials* 33.39 (2021), p. 2103393. DOI: 10.1002/adma.202103393.
- [3] B. Anasori, M. R. Lukatskaya, and Y. Gogotsi. “2D metal carbides and nitrides (MXenes) for energy storage.” In: *Nature Reviews Materials* 2.2 (2017), p. 16098. DOI: 10.1038/natrevmats.2016.98.
- [4] X. Li, Z. Huang, C. E. Shuck, G. Liang, Y. Gogotsi, and C. Zhi. “MXene chemistry, electrochemistry and energy storage applications.” In: *Nature Reviews Chemistry* 6.6 (2022), pp. 389–404. DOI: 10.1038/s41570-022-00384-8.
- [5] K. Maleski, C. E. Shuck, A. T. Fafarman, and Y. Gogotsi. “The Broad Chromatic Range of Two-Dimensional Transition Metal Carbides.” In: *Advanced Optical Materials* 9.4 (2021), p. 2001563. DOI: 10.1002/adom.202001563.
- [6] Z. Li and Y. Wu. “2D Early Transition Metal Carbides (MXenes) for Catalysis.” In: *Small* 15.29 (2019), p. 1804736. DOI: 10.1002/smll.201804736.

- [7] K. Huang, Z. Li, J. Lin, G. Han, and P. Huang. “Two-dimensional transition metal carbides and nitrides (MXenes) for biomedical applications.” In: *Chemical Society Reviews* 47 (14 2018), pp. 5109–5124. DOI: 10.1039/C7CS00838D.
- [8] M. Soleymaniha, M.-A. Shahbazi, A. R. Rafieerad, A. Maleki, and A. Amiri. “Promoting Role of MXene Nanosheets in Biomedical Sciences: Therapeutic and Biosensing Innovations.” In: *Advanced Healthcare Materials* 8.1 (2019), p. 1801137. DOI: 10.1002/adhm.201801137.
- [9] K. R. G. Lim, M. Shekhirev, B. C. Wyatt, B. Anasori, Y. Gogotsi, and Z. W. Seh. “Fundamentals of MXene synthesis.” In: *Nature Synthesis* 1.8 (2022), pp. 601–614. DOI: 10.1038/s44160-022-00104-6.
- [10] J. L. Hart, K. Hantanasirisakul, A. C. Lang, B. Anasori, D. Pinto, Y. Pivak, J. T. van Omme, S. J. May, Y. Gogotsi, and M. L. Taheri. “Control of MXenes’ electronic properties through termination and intercalation.” In: *Nature Communications* 10.1 (2019), p. 522. ISSN: 2041-1723. DOI: 10.1038/s41467-018-08169-8.
- [11] B. Gault, A. Chiaramonti, O. Cojocaru-Mirédin, P. Stender, R. Dubosq, C. Freysoldt, S. K. Makineni, T. Li, M. Moody, and J. M. Cairney. “Atom probe tomography.” In: *Nature Reviews Methods Primers* 1.1 (2021), p. 51. DOI: 10.1038/s43586-021-00047-w.
- [12] K. Tedsree, T. Li, S. Jones, C. W. A. Chan, K. M. K. Yu, P. A. J. Bagot, E. A. Marquis, G. D. W. Smith, and S. C. E. Tsang. “Hydrogen production from formic acid decomposition at room temperature using a Ag–Pd core–shell nanocatalyst.” In: *Nature Nanotechnology* 6.5 (2011), pp. 302–307. DOI: 10.1038/nnano.2011.42.
- [13] T. Li, P. A. J. Bagot, E. Christian, B. R. C. Theobald, J. D. B. Sharman, D. Ozkaya, M. P. Moody, S. C. E. Tsang, and G. D. W. Smith. “Atomic Imaging of Carbon-Supported Pt, Pt/Co, and Ir@Pt Nanocatalysts by Atom-Probe Tomography.” In: *ACS Catalysis* 4.2 (2014), pp. 695–702. DOI: 10.1021/cs401117e.
- [14] P. Felfer, P. Benndorf, A. Masters, T. Maschmeyer, and J. M. Cairney. “Revealing the Distribution of the Atoms within Individual Bimetallic Catalyst Nanoparticles.” In: *Angewandte Chemie International Edition* 53.42 (2014), pp. 11190–11193. DOI: 10.1002/anie.201405043.
- [15] D. E. Perea, J. E. Allen, S. J. May, B. W. Wessels, D. N. Seidman, and L. J. Lauhon. “Three-Dimensional Nanoscale Composition Mapping of Semiconductor Nanowires.” In: *Nano Letters* 6.2 (2006), pp. 181–185. DOI: 10.1021/nl051602p.
- [16] J. Lim, S.-H. Kim, R. Aymerich Armengol, O. Kasian, P.-P. Choi, L. T. Stephenson, B. Gault, and C. Scheu. “Atomic-Scale Mapping of Impurities in Partially Reduced Hollow TiO₂ Nanowires.” In: *Angewandte Chemie International Edition* 59.14 (2020), pp. 5651–5655. DOI: 10.1002/anie.201915709.
- [17] S.-H. Kim, J. Lim, R. Sahu, O. Kasian, L. T. Stephenson, C. Scheu, and B. Gault. “Direct Imaging of Dopant and Impurity Distributions in 2D MoS₂.” In: *Advanced Materials* 32.8 (2020), p. 1907235. DOI: 10.1002/adma.201907235.

- [18] T. Li, A. Devaraj, and N. Kruse. “Atomic-scale characterization of (electro-)catalysts and battery materials by atom probe tomography.” In: *Cell Reports Physical Science* 3.12 (2022), p. 101188. ISSN: 2666-3864. DOI: 10.1016/j.xcrp.2022.101188.
- [19] S.-H. Kim, S.-H. Yoo, P. Chakraborty, J. Jeong, J. Lim, A. A. El-Zoka, X. Zhou, L. T. Stephenson, T. Hickel, J. Neugebauer, C. Scheu, M. Todorova, and B. Gault. “Understanding Alkali Contamination in Colloidal Nanomaterials to Unlock Grain Boundary Impurity Engineering.” In: *Journal of the American Chemical Society* 144.2 (2022), pp. 987–994. DOI: 10.1021/jacs.1c11680.
- [20] S.-H. Kim, S.-H. Yoo, S. Shin, A. A. El-Zoka, O. Kasian, J. Lim, J. Jeong, C. Scheu, J. Neugebauer, H. Lee, M. Todorova, and B. Gault. “Controlled Doping of Electrocatalysts through Engineering Impurities.” In: *Advanced Materials* 34.28 (2022), p. 2203030. DOI: 10.1002/adma.202203030.
- [21] V. Natu, M. Benchakar, C. Canaff, A. Habrioux, S. Célérier, and M. W. Barsoum. “A critical analysis of the X-ray photoelectron spectra of Ti₃C₂T_z MXenes.” In: *Matter* 4.4 (2021), pp. 1224–1251. DOI: 10.1016/j.matt.2021.01.015.
- [22] H. Alnoor, A. Elskova, J. Palisaitis, I. Persson, E. Tseng, J. Lu, L. Hultman, and P. Persson. “Exploring MXenes and their MAX phase precursors by electron microscopy.” In: *Materials Today Advances* 9 (2021), p. 100123. DOI: 10.1016/j.mtadv.2020.100123.
- [23] V. Natu, J. L. Hart, M. Sokol, H. Chiang, M. L. Taheri, and M. W. Barsoum. “Edge Capping of 2D-MXene Sheets with Polyanionic Salts To Mitigate Oxidation in Aqueous Colloidal Suspensions.” In: *Angewandte Chemie International Edition* 58.36 (2019), pp. 12655–12660. DOI: 10.1002/anie.201906138.
- [24] Y. Lee, S. J. Kim, Y.-J. Kim, Y. Lim, Y. Chae, B.-J. Lee, Y.-T. Kim, H. Han, Y. Gogotsi, and C. W. Ahn. “Oxidation-resistant titanium carbide MXene films.” In: *Journal of Materials Chemistry A* 8 (2020), pp. 573–581. DOI: 10.1039/C9TA07036B.
- [25] P. H. Nguyen, D. H. Nguyen, D. Kim, M. K. Kim, J. Jang, W. H. Sim, H. M. Jeong, G. Namkoong, and M. S. Jeong. “Regenerating MXene by a Facile Chemical Treatment Method.” In: *ACS Applied Materials & Interfaces* 14.45 (2022), pp. 51487–51495. DOI: 10.1021/acsami.2c13993.
- [26] A. Iqbal, J. Hong, T. Y. Ko, and C. M. Koo. “Improving oxidation stability of 2D MXenes: synthesis, storage media, and conditions.” In: *Nano Convergence* 8.1 (2021), p. 9. DOI: 10.1186/s40580-021-00259-6.
- [27] J. Jiang, S. Bai, J. Zou, S. Liu, J.-P. Hsu, N. Li, G. Zhu, Z. Zhuang, Q. Kang, and Y. Zhang. “Improving stability of MXenes.” In: *Nano Research* 15.7 (2022), pp. 6551–6567. DOI: 10.1007/s12274-022-4312-8.
- [28] I. Persson, J. Halim, T. W. Hansen, J. B. Wagner, V. Darakchieva, J. Palisaitis, J. Rosen, and P. O. Å. Persson. “How Much Oxygen Can a MXene Surface Take Before It Breaks?” In: *Advanced Functional Materials* 30.47 (2020), p. 1909005. DOI: 10.1002/adfm.201909005.

- [29] G. Gao, A. P. O'Mullane, and A. Du. "2D MXenes: A New Family of Promising Catalysts for the Hydrogen Evolution Reaction." In: *ACS Catalysis* 7.1 (2017), pp. 494–500. DOI: 10.1021/acscatal.6b02754.
- [30] F. Cao, Y. Zhang, H. Wang, K. Khan, A. K. Tareen, W. Qian, H. Zhang, and H. Ågren. "Recent Advances in Oxidation Stable Chemistry of 2D MXenes." In: *Advanced Materials* 34.13 (2022), p. 2107554. DOI: 10.1002/adma.202107554.
- [31] X. Li, Z. Huang, and C. Zhi. "Environmental Stability of MXenes as Energy Storage Materials." In: *Frontiers in Materials* 6 (2019). DOI: 10.3389/fmats.2019.00312.
- [32] H. Liang and J. Liu. "Insights on the Corrosion and Degradation of MXenes as Electrocatalysts for Hydrogen Evolution Reaction." In: *ChemCatChem* 14.6 (2022), e202101375. DOI: 10.1002/cctc.202101375.
- [33] A. Bhat, S. Anwer, K. S. Bhat, M. I. H. Mohideen, K. Liao, and A. Qurashi. "Prospects challenges and stability of 2D MXenes for clean energy conversion and storage applications." In: *npj 2D Materials and Applications* 5.1 (2021), p. 61. DOI: 10.1038/s41699-021-00239-8.
- [34] H. Ghassemi, W. Harlow, O. Mashtalir, M. Beidaghi, M. R. Lukatskaya, Y. Gogotsi, and M. L. Taheri. "In situ environmental transmission electron microscopy study of oxidation of two-dimensional Ti₃C₂ and formation of carbon-supported TiO₂." In: *Journal of Materials Chemistry A* 2 (35 2014), pp. 14339–14343. DOI: 10.1039/C4TA02583K.
- [35] K. Badawy, K. Liao, and N. Singh. "Atomistic Insights of Ti-Based MXenes Thermal Decomposition and Transformation to Carbon-Supported Ti–O Phases for Energy Applications." In: *ACS Applied Nano Materials* 5.11 (2022), pp. 16731–16740. DOI: 10.1021/acsanm.2c03723.
- [36] Y. Gogotsi and Q. Huang. "MXenes: Two-Dimensional Building Blocks for Future Materials and Devices." In: *ACS Nano* 15.4 (2021), pp. 5775–5780. DOI: 10.1021/acsnano.1c03161.
- [37] O. Westhead, R. Jervis, and I. E. L. Stephens. "Is lithium the key for nitrogen electroreduction?" In: *Science* 372.6547 (2021), pp. 1149–1150. DOI: 10.1126/science.abi8329.
- [38] Y. Chae, S. J. Kim, S.-Y. Cho, J. Choi, K. Maleski, B.-J. Lee, H.-T. Jung, Y. Gogotsi, Y. Lee, and C. W. Ahn. "An investigation into the factors governing the oxidation of two-dimensional Ti₃C₂ MXene." In: *Nanoscale* 11 (17 2019), pp. 8387–8393. DOI: 10.1039/C9NR00084D.
- [39] L. H. Karlsson, J. Birch, J. Halim, M. W. Barsoum, and P. O. Å. Persson. "Atomically Resolved Structural and Chemical Investigation of Single MXene Sheets." In: *Nano Letters* 15.8 (2015), pp. 4955–4960. DOI: 10.1021/acs.nanolett.5b00737.

- [40] M. Naguib, O. Mashtalir, M. R. Lukatskaya, B. Dyatkin, C. Zhang, V. Presser, Y. Gogotsi, and M. W. Barsoum. “One-step synthesis of nanocrystalline transition metal oxides on thin sheets of disordered graphitic carbon by oxidation of MXenes.” In: *Chemical Communications* 50 (56 2014), pp. 7420–7423. DOI: 10.1039/C4CC01646G.
- [41] F. Xia, J. Lao, R. Yu, X. Sang, J. Luo, Y. Li, and J. Wu. “Ambient oxidation of Ti₃C₂ MXene initialized by atomic defects.” In: *Nanoscale* 11 (48 2019), pp. 23330–23337. DOI: 10.1039/C9NR07236E.
- [42] C. J. Zhang, S. Pinilla, N. McEvoy, C. P. Cullen, B. Anasori, E. Long, S.-H. Park, A. Seral-Ascaso, A. Shmeliov, D. Krishnan, C. Morant, X. Liu, G. S. Duesberg, Y. Gogotsi, and V. Nicolosi. “Oxidation Stability of Colloidal Two-Dimensional Titanium Carbides (MXenes).” In: *Chemistry of Materials* 29.11 (2017), pp. 4848–4856. DOI: 10.1021/acs.chemmater.7b00745.
- [43] S.-H. Kim, P. W. Kang, O. O. Park, J.-B. Seol, J.-P. Ahn, J. Y. Lee, and P.-P. Choi. “A new method for mapping the three-dimensional atomic distribution within nanoparticles by atom probe tomography (APT).” In: *Ultramicroscopy* 190 (2018), pp. 30–38. DOI: 10.1016/j.ultramicro.2018.04.005.
- [44] H. Jun, K. Jang, C. Jung, and P.-P. Choi. “Atom Probe Tomography Investigations of Ag Nanoparticles Embedded in Pulse-Electrodeposited Ni Films.” In: *Microscopy and Microanalysis* 27.5 (2021), pp. 1007–1016. DOI: 10.1017/S1431927621012137.
- [45] M. K. Miller. “The effects of local magnification and trajectory aberrations on atom probe analysis.” In: *Le Journal De Physique Colloques* 48 (1987), pp. 565–570.
- [46] X. Wang, X. Shen, Y. Gao, Z. Wang, R. Yu, and L. Chen. “Atomic-Scale Recognition of Surface Structure and Intercalation Mechanism of Ti₃C₂X.” In: *Journal of the American Chemical Society* 137.7 (2015), pp. 2715–2721. DOI: 10.1021/ja512820k.
- [47] A. Lipatov, M. Alhabeab, M. R. Lukatskaya, A. Boson, Y. Gogotsi, and A. Sinitskii. “Effect of Synthesis on Quality, Electronic Properties and Environmental Stability of Individual Monolayer Ti₃C₂ MXene Flakes.” In: *Advanced Electronic Materials* 2.12 (2016), p. 1600255. DOI: 10.1002/aelm.201600255.
- [48] A. Lipatov, H. Lu, M. Alhabeab, B. Anasori, A. Gruverman, Y. Gogotsi, and A. Sinitskii. “Elastic properties of 2D Ti₃C₂T_x MXene monolayers and bilayers.” In: *Science Advances* 4.6 (2018), eaat0491. DOI: 10.1126/sciadv.aat0491.
- [49] M. Thuvander, J. Weidow, J. Angseryd, L. Falk, F. Liu, M. Sonestedt, K. Stiller, and H.-O. Andrén. “Quantitative atom probe analysis of carbides.” In: *Ultramicroscopy* 111.6 (2011), pp. 604–608. DOI: 10.1016/j.ultramicro.2010.12.024.
- [50] Z. Peng, F. Vurpillot, P.-P. Choi, Y. Li, D. Raabe, and B. Gault. “On the detection of multiple events in atom probe tomography.” In: *Ultramicroscopy* 189 (2018), pp. 54–60. DOI: 10.1016/j.ultramicro.2018.03.018.

- [51] S. Ndiaye, C. Bacchi, B. Klaes, M. Canino, F. Vurpillot, and L. Rigutti. “Surface Dynamics of Field Evaporation in Silicon Carbide.” In: *The Journal of Physical Chemistry C* 127.11 (2023), pp. 5467–5478. DOI: 10.1021/acs.jpcc.2c08908.
- [52] Z. Peng, D. Zanuttini, B. Gervais, E. Jacquet, I. Blum, P.-P. Choi, D. Raabe, F. Vurpillot, and B. Gault. “Unraveling the Metastability of Cn^{2+} ($n = 2-4$) Clusters.” In: *The Journal of Physical Chemistry Letters* 10.3 (2019), pp. 581–588. DOI: 10.1021/acs.jpclett.8b03449.
- [53] P. P. Michałowski, M. Anayee, T. S. Mathis, S. Kozdra, A. Wójcik, K. Hantanasirisakul, I. Jóźwik, A. Piątkowska, M. Moździońek, A. Malinowska, R. Diduszko, E. Wierzbicka, and Y. Gogotsi. “Oxycarbide MXenes and MAX phases identification using monoatomic layer-by-layer analysis with ultralow-energy secondary-ion mass spectrometry.” In: *Nature Nanotechnology* 17.11 (2022), pp. 1192–1197. DOI: 10.1038/s41565-022-01214-0.
- [54] T. S. Mathis, K. Maleski, A. Goad, A. Sarycheva, M. Anayee, A. C. Foucher, K. Hantanasirisakul, C. E. Shuck, E. A. Stach, and Y. Gogotsi. “Modified MAX Phase Synthesis for Environmentally Stable and Highly Conductive Ti_3C_2 MXene.” In: *ACS Nano* 15.4 (2021), pp. 6420–6429. DOI: 10.1021/acsnano.0c08357.
- [55] M. Alhabeab, K. Maleski, B. Anasori, P. Lelyukh, L. Clark, S. Sin, and Y. Gogotsi. “Guidelines for Synthesis and Processing of Two-Dimensional Titanium Carbide (Ti_3C_2Tx MXene).” In: *Chemistry of Materials* 29.18 (2017), pp. 7633–7644. DOI: 10.1021/acs.chemmater.7b02847.
- [56] N. Shpigel, M. D. Levi, S. Sigalov, T. S. Mathis, Y. Gogotsi, and D. Aurbach. “Direct Assessment of Nanoconfined Water in 2D Ti_3C_2 Electrode Interspaces by a Surface Acoustic Technique.” In: *Journal of the American Chemical Society* 140.28 (2018), pp. 8910–8917. DOI: 10.1021/jacs.8b04862.
- [57] Y.-S. Chen, P.-Y. Liu, R. Niu, A. Devaraj, H.-W. Yen, R. K. W. Marceau, and J. M. Cairney. “Atom Probe Tomography for the Observation of Hydrogen in Materials: A Review.” In: *Microscopy and Microanalysis* 29.1 (Dec. 2022), pp. 1–15. DOI: 10.1093/micmic/ozac005.
- [58] P. Persson and J. Rosen. “Current state of the art on tailoring the MXene composition, structure, and surface chemistry.” In: *Current Opinion in Solid State and Materials Science* 23.6 (2019), p. 100774. DOI: 10.1016/j.cossms.2019.100774.
- [59] L.-Å. Näslund and I. Persson. “XPS spectra curve fittings of Ti_3C_2Tx based on first principles thinking.” In: *Applied Surface Science* 593 (2022), p. 153442. ISSN: 0169-4332. DOI: 10.1016/j.apsusc.2022.153442.
- [60] M. Ghidui, M. R. Lukatskaya, M.-Q. Zhao, Y. Gogotsi, and M. W. Barsoum. “Conductive two-dimensional titanium carbide ‘clay’ with high volumetric capacitance.” In: *Nature* 516.7529 (2014), pp. 78–81. DOI: 10.1038/nature13970.

- [61] Y.-J. Kim, S. J. Kim, D. Seo, Y. Chae, M. Anayee, Y. Lee, Y. Gogotsi, C. W. Ahn, and H.-T. Jung. “Etching Mechanism of Monoatomic Aluminum Layers during MXene Synthesis.” In: *Chemistry of Materials* 33.16 (2021), pp. 6346–6355. DOI: 10.1021/acs.chemmater.1c01263.
- [62] J. Lu, I. Persson, H. Lind, J. Palisaitis, M. Li, Y. Li, K. Chen, J. Zhou, S. Du, Z. Chai, Z. Huang, L. Hultman, P. Eklund, J. Rosen, Q. Huang, and P. O. Persson. “Tin+1Cn MXenes with fully saturated and thermally stable Cl terminations.” In: *Nanoscale Advances* 1 (9 2019), pp. 3680–3685. DOI: 10.1039/C9NA00324J.
- [63] L. Fu, H. Xie, J. Huang, X. Chen, and L. Chen. “Determination of metal impurity elements in lithium hexafluorophosphate using inductively coupled plasma tandem mass spectrometry based on reaction gas mixtures.” In: *Spectrochimica Acta Part B: Atomic Spectroscopy* 181 (2021), p. 106217. ISSN: 0584-8547. DOI: 10.1016/j.sab.2021.106217.
- [64] R. Merrifield. *Determination of Impurities in Lithium Materials with the NexION 5000 ICP-MS*. Application Note. PerkinElmer Inc., 2021.
- [65] B. Gault, B. Klaes, F. F. Morgado, C. Freysoldt, Y. Li, F. De Geuser, L. T. Stephenson, and F. Vurpillot. “Reflections on the Spatial Performance of Atom Probe Tomography in the Analysis of Atomic Neighborhoods.” In: *Microscopy and Microanalysis* 28.4 (2022), pp. 1116–1126. DOI: 10.1017/S1431927621012952.
- [66] S. Doo, A. Chae, D. Kim, T. Oh, T. Y. Ko, S. J. Kim, D.-Y. Koh, and C. M. Koo. “Mechanism and Kinetics of Oxidation Reaction of Aqueous Ti₃C₂T_x Suspensions at Different pHs and Temperatures.” In: *ACS Applied Materials & Interfaces* 13.19 (2021), pp. 22855–22865. DOI: 10.1021/acsami.1c04663.
- [67] M. R. Lukatskaya, O. Mashtalir, C. E. Ren, Y. Dall’Agnese, P. Rozier, P. L. Taberna, M. Naguib, P. Simon, M. W. Barsoum, and Y. Gogotsi. “Cation Intercalation and High Volumetric Capacitance of Two-Dimensional Titanium Carbide.” In: *Science* 341.6153 (2013), pp. 1502–1505. DOI: 10.1126/science.1241488.
- [68] J. Wan, S. D. Lacey, J. Dai, W. Bao, M. S. Fuhrer, and L. Hu. “Tuning two-dimensional nanomaterials by intercalation: materials, properties and applications.” In: *Chemical Society Reviews* 45 (24 2016), pp. 6742–6765. DOI: 10.1039/C5CS00758E.
- [69] E. Saita, M. Iwata, Y. Shibata, Y. Matsunaga, R. Suizu, K. Awaga, J. Hirotsu, and H. Omachi. “Exfoliation of Al-Residual Multilayer MXene Using Tetramethylammonium Bases for Conductive Film Applications.” In: *Frontiers in Chemistry* 10 (2022). DOI: 10.3389/fchem.2022.841313.
- [70] R. Verberne, D. W. Saxey, S. M. Reddy, W. D. A. Rickard, D. Fougereuse, and C. Clark. “Analysis of Natural Rutile (TiO₂) by Laser-assisted Atom Probe Tomography.” In: *Microscopy and Microanalysis* 25.2 (2019), pp. 539–546. DOI: 10.1017/S1431927618015477.

- [71] Y. Xie, Y. Dall’Agnese, M. Naguib, Y. Gogotsi, M. W. Barsoum, H. L. Zhuang, and P. R. C. Kent. “Prediction and Characterization of MXene Nanosheet Anodes for Non-Lithium-Ion Batteries.” In: *ACS Nano* 8.9 (2014), pp. 9606–9615. DOI: 10.1021/nn503921j.
- [72] J. Zheng, X. Hu, Z. Ren, X. Xue, and K. Chou. “Solid-state Reaction Studies in Al₂O₃–TiO₂ System by Diffusion Couple Method.” In: *ISIJ International* 57.10 (2017), pp. 1762–1766. DOI: 10.2355/isijinternational.ISIJINT-2017-042.
- [73] M.-K. Sun, I.-H. Jung, and H.-G. Lee. “Morphology and chemistry of oxide inclusions after Al and Ti complex deoxidation.” In: *Metals and Materials International* 14.6 (2008), pp. 791–798. DOI: 10.3365/met.mat.2008.12.791.
- [74] F. Tielens, M. Calatayud, A. Beltrán, C. Minot, and J. Andrés. “Lithium insertion and mobility in the TiO₂-anatase/titanate structure: A periodic DFT study.” In: *Journal of Electroanalytical Chemistry* 581.2 (2005), pp. 216–223. DOI: 10.1016/j.jelechem.2005.04.009.
- [75] H. Xie, N. Li, B. Liu, J. Yang, and X. Zhao. “Role of Sodium Ion on TiO₂ Photocatalyst: Influencing Crystallographic Properties or Serving as the Recombination Center of Charge Carriers?” In: *The Journal of Physical Chemistry C* 120.19 (2016), pp. 10390–10399. DOI: 10.1021/acs.jpcc.6b01730.
- [76] J. Wang, S. Dong, H. Li, Z. Chen, S. Jiang, L. Wu, and X. Zhang. “Facile synthesis of layered Li₄Ti₅O₁₂-Ti₃C₂T_x (MXene) composite for high-performance lithium ion battery.” In: *Journal of Electroanalytical Chemistry* 810 (2018), pp. 27–33. DOI: 10.1016/j.jelechem.2017.12.079.
- [77] Y. Dong, Z.-S. Wu, S. Zheng, X. Wang, J. Qin, S. Wang, X. Shi, and X. Bao. “Ti₃C₂ MXene-Derived Sodium/Potassium Titanate Nanoribbons for High-Performance Sodium/Potassium Ion Batteries with Enhanced Capacities.” In: *ACS Nano* 11.5 (2017), pp. 4792–4800. DOI: 10.1021/acsnano.7b01165.
- [78] J. Huang, R. Meng, L. Zu, Z. Wang, N. Feng, Z. Yang, Y. Yu, and J. Yang. “Sandwich-like Na_{0.23}TiO₂ nanobelt/Ti₃C₂ MXene composites from a scalable in situ transformation reaction for long-life high-rate lithium/sodium-ion batteries.” In: *Nano Energy* 46 (2018), pp. 20–28. DOI: 10.1016/j.nanoen.2018.01.030.
- [79] C. Zeng, F. Xie, X. Yang, M. Jaroniec, L. Zhang, and S.-Z. Qiao. “Ultrathin Titanate Nanosheets/Graphene Films Derived from Confined Transformation for Excellent Na/K Ion Storage.” In: *Angewandte Chemie International Edition* 57.28 (2018), pp. 8540–8544. DOI: 10.1002/anie.201803511.
- [80] W. Zhong, M. Tao, W. Tang, W. Gao, T. Yang, Y. Zhang, R. Zhan, S.-J. Bao, and M. Xu. “MXene-derivative pompon-like Na₂Ti₃O₇@C anode material for advanced sodium ion batteries.” In: *Chemical Engineering Journal* 378 (2019), p. 122209. DOI: 10.1016/j.cej.2019.122209.

- [81] L. Yuan, Z. Geng, J. Xu, F. Guo, and C. Han. “Metal-Semiconductor Heterostructures for Photoredox Catalysis: Where Are We Now and Where Do We Go?” In: *Advanced Functional Materials* 31.27 (2021), p. 2101103. DOI: 10.1002/adfm.202101103.
- [82] J. Low, L. Zhang, T. Tong, B. Shen, and J. Yu. “TiO₂/MXene Ti₃C₂ composite with excellent photocatalytic CO₂ reduction activity.” In: *Journal of Catalysis* 361 (2018), pp. 255–266. DOI: 10.1016/j.jcat.2018.03.009.
- [83] J. Chen, H. Zheng, Y. Zhao, M. Que, W. Wang, and X. Lei. “Morphology and photocatalytic activity of TiO₂/MXene composites by in-situ solvothermal method.” In: *Ceramics International* 46.12 (2020), pp. 20088–20096. DOI: 10.1016/j.ceramint.2020.05.083.
- [84] S. Debow, T. Zhang, X. Liu, F. Song, Y. Qian, J. Han, K. Maleski, Z. B. Zander, W. R. Creasy, D. L. Kuhn, Y. Gogotsi, B. G. DeLacy, and Y. Rao. “Charge Dynamics in TiO₂/MXene Composites.” In: *The Journal of Physical Chemistry C* 125.19 (2021), pp. 10473–10482. DOI: 10.1021/acs.jpcc.1c01543.
- [85] J. Vida, P. Gemeiner, M. Pavličková, M. Mazalová, P. Souček, D. Plašienka, and T. Homola. “Nanocrystalline TiO₂/Ti₃C₂T_x MXene composites with a tunable work function prepared using atmospheric pressure oxygen plasma.” In: *Nanoscale* 15 (3 2023), pp. 1289–1298. DOI: 10.1039/D2NR04465J.
- [86] M. Cao, F. Wang, L. Wang, W. Wu, W. Lv, and J. Zhu. “Room Temperature Oxidation of Ti₃C₂ MXene for Supercapacitor Electrodes.” In: *Journal of The Electrochemical Society* 164.14 (2017), A3933. DOI: 10.1149/2.1541714jes.
- [87] Y. Jia, J. Liu, and L. Shang. “Layered structure 2D MXene/TiO₂ composites as high-performance anodes for lithium-ion batteries.” In: *Ionics* 29.2 (2023), pp. 531–537. DOI: 10.1007/s11581-022-04862-3.
- [88] R. Teimouri, Z. Heydari, M. P. Ghaziani, M. Madani, H. Abdy, M. Kolahdouz, and E. Asl-Soleimani. “Synthesizing Li doped TiO₂ electron transport layers for highly efficient planar perovskite solar cell.” In: *Superlattices and Microstructures* 145 (2020), p. 106627. DOI: 10.1016/j.spmi.2020.106627.
- [89] P.-P. Filippatos, N. Kelaidis, M. Vasilopoulou, D. Davazoglou, N. N. Lathiotakis, and A. Chroneos. “Defect processes in F and Cl doped anatase TiO₂.” In: *Scientific Reports* 9.1 (2019), p. 19970. DOI: 10.1038/s41598-019-55518-8.
- [90] X.-K. Wang, C. Wang, W.-Q. Jiang, W.-L. Guo, and J.-G. Wang. “Sonochemical synthesis and characterization of Cl-doped TiO₂ and its application in the photodegradation of phthalate ester under visible light irradiation.” In: *Chemical Engineering Journal* 189-190 (2012), pp. 288–294. DOI: 10.1016/j.cej.2012.02.078.
- [91] X. Han, L. An, Y. Hu, Y. Li, C. Hou, H. Wang, and Q. Zhang. “Ti₃C₂ MXene-derived carbon-doped TiO₂ coupled with g-C₃N₄ as the visible-light photocatalysts for photocatalytic H₂ generation.” In: *Applied Catalysis B: Environmental* 265 (2020), p. 118539. DOI: 10.1016/j.apcatb.2019.118539.

- [92] M. Faraji, A. Bafekry, M. M. Fadlallah, F. Molaei, N. N. Hieu, P. Qian, M. Ghergherehchi, and D. Gogova. “Surface modification of titanium carbide MXene monolayers (Ti₂C and Ti₃C₂) via chalcogenide and halogenide atoms.” In: *Physical Chemistry Chemical Physics*. 23 (28 2021), pp. 15319–15328. DOI: 10.1039/D1CP01788H.
- [93] J. Luo, C. Fang, C. Jin, H. Yuan, O. Sheng, R. Fang, W. Zhang, H. Huang, Y. Gan, Y. Xia, C. Liang, J. Zhang, W. Li, and X. Tao. “Tunable pseudocapacitance storage of MXene by cation pillaring for high performance sodium-ion capacitors.” In: *Journal of Materials Chemistry A* 6 (17 2018), pp. 7794–7806. DOI: 10.1039/C8TA02068J.