

Determining the Wiedemann-Franz ratio from the thermal Hall conductivity: Application to Cu and YBa₂Cu₃O_{6.95}.

Y. Zhang¹, N.P. Ong¹, Z.A. Xu¹, K. Krishana^{1y}, R. Gagnon², and L. Taillefer³

¹Joseph Henry Laboratories of Physics, Princeton University, Princeton, New Jersey 08544.

²Department of Physics, McGill University, Montreal, Quebec, Canada H3A 2T8.

³Department of Physics, University of Toronto, Toronto, Ontario, Canada M5S 1A7.

(April 14, 2024)

The Wiedemann-Franz (WF) ratio compares the thermal and electrical conductivities in a metal. We describe a new way to determine its value, based on the thermal Hall conductivity. The technique is applied to copper and to untwinned YBaCuO. In the latter, we uncover a T-linear dependence and suppression of the Hall-channel WF ratio. We discuss the implications of this suppression. The general suppression of the WF ratio in systems with predominant electron-electron scattering is discussed.

74.72.-h, 72.15.Eb, 72.15.Gd, 72.15.Lh

The electron fluid in a metal is an excellent conductor of both electric charge and entropy. In familiar metals such as Au, Pb and Cu, the thermal conductivity of the electrons is so large that the phonons account for less than one percent of the heat current at any temperature. Wiedemann and Franz (WF) observed that the ratio of the thermal and electrical conductivities is very nearly the same in many metals [1]. This ratio is expressed as the Lorenz number, which is conveniently written in dimensionless form as

$$L = \frac{\kappa_e}{T} \frac{e^2}{k_B}; \quad (1)$$

where κ_e is the electronic thermal conductivity, κ the electrical conductivity, e the elementary charge, and k_B is Boltzmann's constant. In standard transport theory, L equals the Sommerfeld value $L_0 = \frac{\pi^2}{3} \frac{e^2}{k_B T}$ if the mean-free-paths (mfp) are assumed identical for charge and heat transport. Indeed, in all conventional metals, the observed L is rather close to this number above 273 K [2]. However, below 273 K, the observed L falls significantly below this value, implying that the heat current is more strongly scattered relative to the charge current. Because L compares directly the charge and entropy currents, it has contributed strongly to our current understanding of how charge and entropy currents are affected by distinct scattering processes in conventional metals [3].

In solids, the observed thermal conductivity is the sum of the electronic and phonon conductivity κ_{ph} , viz. $\kappa = \kappa_e + \kappa_{ph}$. In conventional metals where $\kappa_{ph} \gg \kappa_e$, one may use κ_{ph} instead of κ to evaluate L with negligible error. However, in conductors with relatively small carrier densities, κ_{ph} is often much larger than κ_e . These conductors (with resistivities exceeding 100 $\mu\Omega\text{cm}$) include many interesting conductors such as the cuprates, doped fullerenes, quasicrystals, and newer materials such as CaB₆ [4]. Recent theoretical discussions of charge versus entropy currents are most applicable to these conductors. Ironically, their WF ratio seems experimentally in-

accessible using conventional techniques. Hence, a fresh experimental approach is desirable.

The thermal Hall effect provides a rather efficient way to screen out the phonon heat current (even when it is dominant). In zero field, the observed thermal current J_Q is parallel to the temperature gradient ∇T (applied $\parallel \hat{x}$). A field $H \parallel \hat{z}$ generates a Lorentz force that acts only on the electronic component of J_Q . This produces a transverse Hall current parallel to \hat{y} (depending on the sign of the charge carriers). Thus, the transverse Hall conductivity κ_{xy} involves only the electrons (the phonon current is strictly unaffected by H). By forming the ratio in Eq. 1 with κ_{xy} and the electrical Hall conductivity κ_{xy} , we may measure directly the Hall Lorenz number $L_{xy} = \frac{\kappa_{xy}}{T} \frac{e^2}{k_B}$. At sufficiently high T , L_{xy} approaches the Sommerfeld value [8].

We have applied the technique to a detwinned crystal of optimally-doped cuprate YBa₂Cu₃O_{6.95} (YBCO) with a critical temperature $T_c = 93.3$ K, and to elemental Cu. A longitudinal gradient $\partial_x T$ (≈ 2 K) is applied \parallel a of the YBCO crystal, and the transverse gradient $\partial_y T$ is measured using a pair of thermocouples (chromel-constantan) versus field $H \parallel c$. The Hall signal $\partial_y T$ is the field-odd component of $\partial_x T$ [9]. κ_{xy} is computed as $[\partial_y T = \partial_x T] (\kappa_{xy} = \kappa_a)$. We measured $\kappa_a = \kappa_{xx}$, and used the anisotropy $\kappa_b = \kappa_a$ previously measured in another crystal from the same batch (see Ref. [10]). The copper sample was cut from oxygen-free high-conductivity (OFHC) stock, but was not vacuum annealed to further reduce lattice disorder.

First, we discuss the T-dependence of κ_{xy} in Cu, and compare L_{xy} with the standard Lorenz number (see Ref. [7] for early data on κ_{xy}). Figure 1 displays traces of κ_{xy} versus H between 60 and 350 K measured in Sample 1. In order to calculate L and L_{xy} , we have also measured its electrical conductivity and Hall conductivity κ_{xy} . (Below 50 K, where κ_{xy} and κ_{xx} display increasing curvature vs. H , L_{xy} is obtained from their values in the limit of weak-fields.)

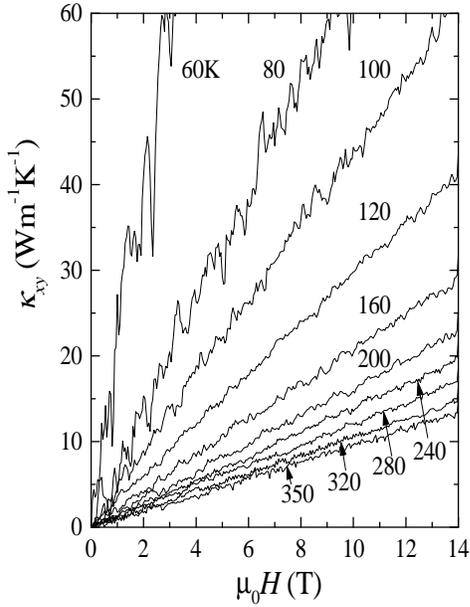


FIG. 1. The field dependence of κ_{xy} (electron-like) in unannealed OFHC copper at selected T in Sample 1 (dimensions 4 mm \times 0.3 mm \times 50 μ m). A gradient $\partial_x T = 0.4$ K is applied along the sample length (\hat{x}). In the lowest curve (350 K), the value of κ_{xy} at 14 T corresponds to a Hall temperature difference $\partial_y T$ across the sample width of ~ 1.6 mK.

The values of κ_{xy} vs. T in Sample 1 are in close agreement with a compilation by Powell et al. [5]. However, in samples that have been carefully annealed, the peak value (at 20 K) may be twice as large [see Bernan and MacDonald (BM) [6]].

Figure 2 shows that L and L_{xy} in our sample start at values slightly higher than the Sommerfeld value at 350 K, and decrease with falling T , with L_{xy} decreasing slightly faster. In Cu, the Debye temperature Θ_D is 343 K. Both Lorenz numbers reach a minimum near 60 K, and increase again at lower T . For comparison, we show (broken line) L reported by BM [6]. The minimum is deeper and occurs at a lower T (20 K). As discussed later, this is consistent with its higher purity.

In conventional metals, electronic currents are limited by scattering of electrons by phonons (at finite T). Large-angle scattering involving phonons with large wavevectors q ($q > k_F$, the Fermi wavevector) are equally disruptive of the charge and heat currents. By contrast, small-angle scattering ($q \ll k_F$) relaxes only the heat current, leaving the charge current relatively unaffected [3]. In terms of λ_s and λ_e (the mean-free-paths for entropy and charge transport, respectively) we may express L as $(\pi^2/3)h^2\lambda_s^2/\lambda_e^2$, where h denotes averaging over the Fermi Surface FS. At high temperature ($T \gg \Theta_D$), we have $\lambda_s \approx \lambda_e$ because large-angle scattering is dominant. As T decreases below Θ_D , the phonon population is increasingly skewed towards the small- q limit, so that λ_e increases relatively faster than λ_s .

This accounts for the decrease in L in Fig. 2. At very low T , when elastic scattering from impurities dominates,

λ_e and λ_s are again equal, and L returns to the Sommerfeld value. In our sample, this turnaround occurs near 60 K, whereas in the cleaner sample of BM, it occurs at 20 K.

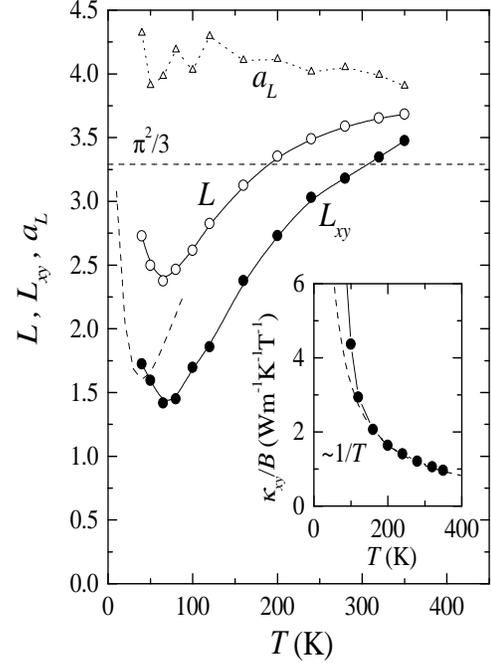


FIG. 2. (Main Panel) The T dependence of the conventional Lorenz number L (open) and Hall-Lorenz number L_{xy} (solid circles) measured in OFHC copper (Sample 1). Both L and L_{xy} decrease from their high- T asymptotic values ($\sim 10\%$ higher than the Sommerfeld value), with the latter falling faster. To compare the two rates, we plot (open triangles) the quantity $a_L = L^2/L_{xy}$. The near constancy of a_L implies that $L_{xy} \propto L^2$ (see text). The inset shows the T dependence of κ_{xy}/B measured in the limit $B \rightarrow 0$. The dash line varies as $1/T$.

In comparing L with L_{xy} , we find that both display a minimum at nearly the same T . However, on the high- T side, L_{xy} falls faster with decreasing T . The two rates are compared via $a_L = L^2/L_{xy}$. The near constancy of a_L is consistent with the expectation [8] that $L \propto h_s^2 i = h_e^2 i$, whereas $L_{xy} \propto h_s^2 i^2 = h_e^2 i^2$. Hence, L_{xy} falls faster because it involves the squares of the mfp's. In Cu, the Hall-Lorenz number approaches the same WF ratio at high T , so that it provides information comparable to L . Moreover, additional information on scattering processes may be derived from its low T behavior.

Thermal conductivity measurements have produced a wealth of information on the superconducting state of the cuprates. In YBCO, they provided early evidence favoring an unconventional pairing symmetry [11,12], and long lifetimes for the quasiparticles at low temperatures [13]. The contributions of the chains to κ [10], and the effect of hole doping [14] also have been investigated. Above T_c , however, the problem of estimating κ_{ph} has been a serious obstacle to the extraction of κ_e . In fact, neither the mag-

nitude nor the T dependence of κ_e in the normal state may be regarded as experimentally established. Hence, the present technique is especially appropriate. While the behavior of κ_{xy} in YBCO was investigated previously [13,15,16] in the superconducting state, the rapid attenuation of the thermal Hall signal precluded measurements above 100 K. The improved resolution now allows κ_{xy} to be determined reliably up to 320 K.

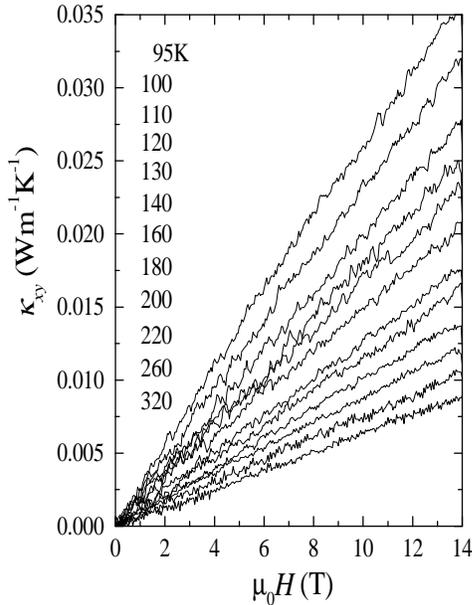


FIG. 3. The field dependence of κ_{xy} (hole-like) measured in untwinned $\text{YBa}_2\text{Cu}_3\text{O}_{6.95}$ at selected T (with H in kG). Each trace is in sequence with values of T indicated. At 320 K and 14 T, the value of κ_{xy} corresponds to a Hall signal of 1.5 mK (in an applied gradient $\times T = 2$ K).

Figure 3 displays the H -dependence of κ_{xy} at selected temperatures from 95 to 320 K. It is worth a second remark that, as κ_{xy} derives no contribution from the phonons, the raw experimental curves directly mirror the electronic heat current. We proceed to compare it with the charge current. In the normal state of YBCO, κ_{xy} is known to vary as $1=T^3$. This produces the anomalous T dependence of the Hall coefficient R_H that is so characteristic of the cuprates [17]. It is interesting to ask if the same dependence is observed in $\kappa_{xy}=T$ (dividing by T to remove the heat capacity contribution). As shown in Fig. 4 (open symbols), the T dependence of the $\kappa_{xy}=B$ is well-fitted to $T^{1.2}$. Hence, we find that $\kappa_{xy}=T$ actually has a weaker dependence than κ_{xy} .

When we calculate L_{xy} , we find that it varies linearly with T (solid circles in Fig. 4). In addition to this unusual T dependence, its value from 95 to 320 K is significantly smaller than the Sommerfeld value.

In some previous reports, values of L (often close to the Sommerfeld value) were obtained using a variety of arguments to subtract κ_{ph} from κ . However, these arguments are suspect for the following reasons. In the cuprates, κ_{ph} is strongly decreased by lattice disorder associated

with dopants (κ_{ph} is 2 to 4 times larger in the pristine parent compound La_2CuO_4 compared with doped compounds [14]). Moreover, within the plane, κ_{ph} is strongly anisotropic. In both $\text{YBa}_2\text{Cu}_3\text{O}_7$ and its two-chain variant $\text{YBa}_2\text{Cu}_4\text{O}_8$, κ_{ph} is significantly larger along b (the chain axis) compared with a , because of the anisotropy in elastic constants [18]. These factors make comparisons between doped and undoped crystals, or between κ measured along the axes a and b in the same sample, quite unreliable. A different approach is to extrapolate the value of κ_e of quasiparticles in the superconducting state to temperatures just above T_c . A recent experiment [15] reports extrapolated values of κ_e in the range 0.8-1.0 W/mK at T_c . With $\mu_0 H_a = 100$ mT, this gives $L = 1.1-1.4$, which is closer to our L_{xy} than to the Sommerfeld value.

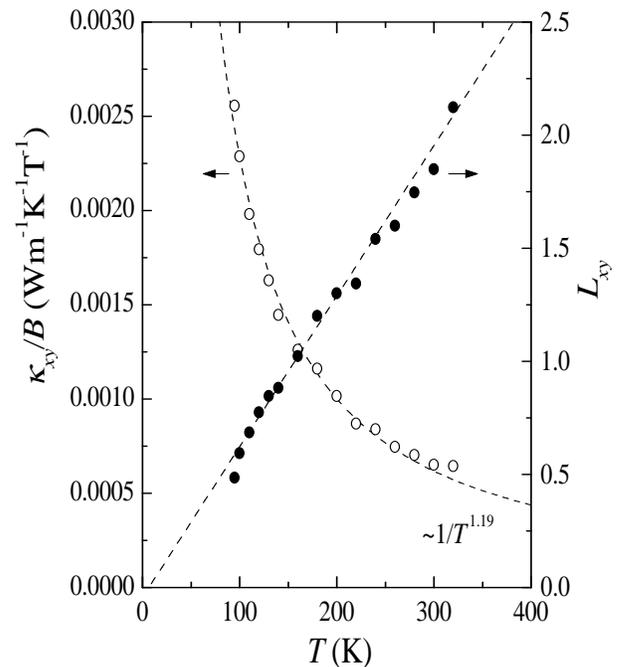


FIG. 4. The T dependence of the Hall-Lorenz number L_{xy} (solid circles) in untwinned $\text{YBa}_2\text{Cu}_3\text{O}_{6.95}$ determined from $\kappa_{xy}=T \kappa_{xy}$ (L is unavailable for comparison). Linear extrapolation of L_{xy} (broken line) shows that it attains the Sommerfeld value $L^2=3$ near 500 K. The open circles represent the weak-field values of $\kappa_{xy}=B$ derived from Fig. 3 (fit to curve $1=T^{1.19}$ is shown).

A side from the overall suppressed scale, the nominally T -linear dependence of L_{xy} is also unusual. An extrapolation (broken line in Fig. 4) shows that it intersects the Sommerfeld value near 500 K. We note that, the acoustic phonons in YBCO have a maximum energy of 20 meV. Above 200 K, the dominant acoustic phonons should have sufficient momenta to span the full FS ($\mu_D = 420$ K is higher because of the large unit cell). Certainly, by 320 K, we should have $\hbar^2 \epsilon_i = \hbar^2 \epsilon_i$ if electron-phonon scattering is the dominant mechanism for relaxing the two currents. Hence, the small values of L_{xy} and the high

temperature scale at which it attains the Sommerfeld value (500 K) seem incompatible with dominant electron-phonon scattering.

In contrast, a suppressed W F ratio may be expected in system with dominant electron-electron (ee) scattering. A discussion of this point illustrates how normal (N) and Umklapp (U) scattering processes influence the W F ratio. As in the case of lattice thermal conduction [19,20], N processes leave the total momentum of the electron gas unchanged, so that the charge current cannot relax without U processes. However, (unlike lattice conduction) N-process ee scattering does relax the heat current because it causes a redistribution of energy between hot and cold electrons [21]. This distinction implies that systems in which ee scattering is dominant have a strongly reduced Lorenz number. Moreover, because the relative weights of N versus U processes are not determined by ρ_D in ee scattering, this reduction could prevail to very high T. These issues are intimately related to behavior of the W F ratio. Hence, the T dependences of κ_{xy} and L_{xy} displayed in Fig. 4 should place strong constraints on transport models for YBCO.

In summary, we have described measurements of the Hall-Lorenz number, obtained as the ratio of $\kappa_{xy}=T$ to ρ_{xy} . In Cu, this method gives results comparable to direct measurements of L. However, in systems in which lattice conduction is not small, the Hall-Lorenz experiment provides a direct comparison of the heat and charge currents of the charge carriers. A quantitative understanding of the information derived from L_{xy} awaits comparison with microscopic calculations. In view of the increased interest in system with dominant ee scattering, we expect high-temperature W F ratio to play an increasingly prominent role.

We acknowledge useful discussions with P.W. Anderson, B. Keimer, K. Damle, and S. Uchida. N.P.O. and K.K. acknowledge support by the U.S. Office of Naval Research. N.P.O. acknowledges an award from the International Joint-Research grants from the New Energy and Industrial Tech. Develop. Org. (NEDO). Y.Z. and Z.X. were supported by funds from a DMR-MRSEC award (NSF DMR 9809483) from the U.S. National Science Foundation.

Permanent address of Z.A.X.: Department of Physics, Zhejiang University, Hangzhou, China

^yPresent address of K.K.: Division of Engineering and Applied Sciences, Harvard University, Cambridge MA 02138

- [3] Electrons and Phonons, J.M. Ziman, (Oxford, 1960), Ch. IX.
- [4] D.P. Young et al., Nature 397, 412 (1999).
- [5] R.L. Powell, H.M. Roder, and W.M. Rogers, Jnl. Appl. Phys. 28, 1282 (1957).
- [6] R. Bemman and D.K.C. MacDonald, Proc. Roy. Soc. London A 211, 122 (1952).
- [7] G. Borelius, Grundlagen des metallischen Zustandes. Physikalische Eigenschaften. Handbuch der Metallphysik, 1 (Leipzig) (1935).
- [8] In the Boltzmann equation approach, κ_{xy} (in a 2D metal with arbitrary in-plane anisotropy) may be expressed as $\kappa_{xy} = (2eB = \hbar^2 T) d^2 \frac{\partial f}{\partial \epsilon} A_S$, where $A_S = d^2 \frac{\partial f}{\partial \epsilon} = (2)^2$ is evaluated at the FS. The electrical Hall conductivity is $\kappa_{xy} = (2e^2 = \hbar) (eB = \hbar) A_e$; where A_e is defined as A_S but in terms of ∇_{ϵ} [N.P. Ong, Phys. Rev. B 43, 193 (1991)]. With these expressions, $L_{xy} = (\frac{2}{3}) A_S = A_e \frac{\hbar^2}{2} i = \hbar^2 e i$.
- [9] To attain the resolution used here ($\partial_y T = 0.3$ mK at 100 K), the long-term drift was kept below 3 mK during the 3 hours of the field sweep. At some T, we verified that sweeps from +14 ! 14T agreed with sweeps in the opposite sequence (14 ! +14T). The linearity of $\partial_y T$ vs. heat current was also verified.
- [10] R. Gagnon, S. Pu, B. Elm an, and L. Taillefer, Phys. Rev. Lett. 78, 1976 (1997).
- [11] R.C. Yu et al., Phys. Rev. Lett. 69, 1431 (1992).
- [12] F. Yu et al., Phys. Rev. Lett. 74, 5136 (1995).
- [13] K. Kishana, J.M. Harris, and N.P. Ong, Phys. Rev. Lett. 75, 3529 (1995).
- [14] Y. Nakamura et al., Physica C 185, 1409 (1991).
- [15] K. Kishana et al., Phys. Rev. Lett. 82, 5108 (1999).
- [16] B. Zein et al., Phys. Rev. Lett. 82, 2175 (1999).
- [17] T.R. Chien et al. Phys. Rev. Lett. 67, 2088 (1991).
- [18] Y. Zhang, N.P. Ong, H. Takagi, to be published.
- [19] The Quantum Theory of Solids, R.E. Peierls (Oxford, 1955), p. 40.
- [20] Joseph Callaway, Phys. Rev. 113, 1046 (1958).
- [21] We elaborate on N vs. U scattering. With only N processes present, ee scattering leads to a large, rigid displacement of the FS (limited by impurity scattering). This implies a very large charge current. The associated Peltier heat current is negligibly small because the particle heat current is opposed by a hole counterflow (hence it vanishes with strict particle-hole symmetry). In an experiment that measures κ , the boundary condition ($J_e = 0$) produces an undisplaced FS with a skewed Fermi distribution. This leads to a heat current that is far larger than the Peltier current, but sensitive to relaxation by N processes. By contrast, in lattice conduction, the absence of U processes leads to a rigid displacement of the Bose-Einstein distribution, but there is no cancelling backflow corresponding to the hole current. Phonon heat conduction is convective, while the electronic current is particle-number conserving. See Ref. [3].

[1] G. Wiedemann and R. Franz, Ann. Phys. (2), 89, 497 (1853).

[2] See table in Solid State Physics, ed. Neil W. Ashcroft and N. David Mermin (Saunders College, 1976), p. 21.