

Paper number: E090

Title:

Conformal lattice of magnetic bubble domains in garnet film

Authors:

M. Gutowski, K. Piotrowski, M. Gutowska and A. Szewczyk

Address (valid for all authors):

Institute of Physics, Polish Academy of Sciences
Al. Lotników 32/46, PL 02-668 Warsaw, Poland

Abstract:

We report experimental observations of magnetic bubble domain arrays with no apparent translational symmetry. Additionally the results of comparative numerical studies are discussed. Our goal is to present experimental evidence for *natural* occurrence of conformal structures.

Keywords:

conformal matter, domain pattern, garnets – thin films, magnetic bubbles, triangular lattice

Corresponding author:

Marek W. Gutowski
Institute of Physics, Polish Academy of Sciences
PL-02-668 Warsaw (Warszawa)
POLAND
e-mail: gutow@ifpan.edu.pl
tel.: +48-22-8437001 ext. 3122
fax: +48-22-8430926

Our work was motivated by few earlier articles [1, 2, 3, 4, 5] concerning the equilibrium configurations of identical interacting objects subjected additionally to strong external fields. While majority of papers concentrate on small- to medium-sized clusters and their thermodynamic [6, 7] and elastic [3, 4] properties, the aim of this paper is to demonstrate the very existence of conformal structures in the Nature, beyond the traditional examples of living things, like sunflower and alike.

The trivial examples of conformal transformations include: Euclidean "rigid movements", i.e. translations and rotations, point reflections, as well as uniform scaling, simultaneously in all dimensions. Generally, the conformal image of any domain contains parts which are stretched, compressed and rotated. Here, we are interested in such nontrivial conformal mappings, which do not preserve the distances between images of originally equidistant points.

The object of our study was the thin layer of magnetic material (garnet, with composition given by its chemical formula $(\text{TmBi})_3(\text{FeGa})_5\text{O}_{12}$) deposited epitaxially on non-magnetic substrate (GGG, $\langle 111 \rangle$ oriented). The sample was held at room temperature in the uniform bias field, produced by a pair of Helmholtz coils, directed perpendicularly to the sample plane. The magnitude of bias field was chosen in such a way to fall within range, in which the so called bubble domains exist and are stable [8]. Due to their size, with diameter around $10\text{ }\mu\text{m}$, those domains can be easily viewed using ordinary optical microscope equipped with two polarizers. The Faraday effect, i.e. the difference of refraction indices for circularly polarized light propagating in direction parallel or anti-parallel to the magnetization vector, is responsible for the contrast in the observed images. We have used the white light in our investigations. Many authors [9] reported observations of regular triangular or hexagonal arrays of bubble domains created in such conditions. In addition to the coils producing the bias field, we have used another small coil, with diameter of few mm , driven with AC current ($\sim 15\text{ kHz}$, rectangular waveform), resting on the sample, to generate and equilibrate new domain structures. In several cases we have also used a DC current flowing through the additional small coil, thus mimicking the confinement of

domains by axially symmetric parabolic potential, as in [10].

The resulting picture, after sudden switching off the current in an AC coil, was subsequently captured to the computer memory by means of a CCD camera, with MultiScan software by CSS Ltd. The obtained bitmap file was subsequently converted to a list of positions of the centers of all visible bubbles and stored in text format.

A single example of many generated structures is shown in Fig. 1. The interacting bubble domains organize themselves in a structure, which is neither periodic nor chaotic. One can easily see that almost all bubble domains have six nearest neighbors forming a slightly distorted hexagon. The hexagons themselves differ in their sizes and orientations, so there is no long range ordering in the usual sense, i.e. the observed pattern has no translational symmetry. On the other hand, we may distinguish fairly regular, crystal-like regions, which may be regarded as a set of crossing points of three families of arcs corresponding to the lattice lines.

The angles, at which those arcs cross, are of main interest in this work. We are going to show that they all are approximately equal to $\pi/3$ (60°), like in ordinary triangular (hexagonal) lattice. This result remains true even for extremely deformed structures, in which the ratio of distances between nearest neighbors located in various regions of the sample reaches the value of ~ 3 .

The first step in experimental data processing is the triangulation, which is performed using our own Fortran procedure, which perhaps should be replaced by, tailored to our needs, standard Delaunay triangulation. As a result of this step we obtain the list of nearest neighbors for each bubble domain. This way we are able to identify the short segments approximating the lattice lines, each segment consisting of two straight pieces sharing common endpoint.

Two segments, with common endpoint, located at any given bubble domain, are considered as approximating the same lattice line when the angle between them does not exceed some predefined threshold value, Θ_t . The results are not very sensitive to the exact value of Θ_t , unless it is unreasonably high or small. Taking Θ_t too close to zero results in ignoring many connections between lattice

nodes, which are obvious for human eye. Contrary, if Θ_t is too high, then we face many misinterpretations, especially in the vicinity of sample defects. We have checked, by careful inspection of the results obtained with Θ_t in range $[0^\circ, 35^\circ]$ with step of 0.5° , that almost identical results are produced with $\Theta_t \in [7^\circ, 20^\circ]$, so we adopted in subsequent calculations $\Theta_t = \pi/12$, i.e. 15° as a safe value.

In regular cases, i.e. away from the boundaries of investigated data set, we usually find three sections of "lattice lines" crossing at any given node. The task is to measure the angles between the true lattice lines, which are different from those between straight segments. To achieve this, we make use of the notion of curvature and curvature radius. A circle passing through each triade of consecutive points (lattice nodes connected with segments) is constructed, together with vector parallel to curvature radius pointing to the middle node of the triade. The scalar product of two such vectors, after their normalization, gives us the cosine of the searched angle Θ . The rest is obvious: the procedure is repeated for every node and the results are stored in computer's memory.

One of many distributions of crossing angles, obtained this way, is presented in Fig. 2. By broad range of experimental conditions we mean various values of the bias field as well as the additional field produced by small coil.

We have also performed some numerical Monte Carlo simulations combined with simulated annealing. In the course of simulations we have adopted the following assumptions: *i*) the domains are identical, non-penetrable hard disks with fixed diameter and carrying identical magnetic moments, *ii*) each single domain is represented by a magnetic dipole with only two translational degrees of freedom, and *iii*) the external field is directed perpedicularly to the sample plane and its strength changes quadratically with position relative to the center of available circular region, bounded with hard wall potential.

Starting with random initial configuration the Brownian jump in randomly chosen direction was attempted for each domain. The average amplitude of jumps was dynamically adjusted in such a way, that $\sim 50\%$ of them were accepted at current temperature, according to the well known Metropolis algorithm. The temperature was slowly, but systematically, reduced until the

amplitude of jumps decreased to one thousands of disk diameter. The one-time decrease of temperature never exceeded one half of the average single domain energy change (fluctuation) in last simulation cycle. It was possible to trace the evolution of the entire system, not only its final configuration. In particular, we were able to observe the collective movements of domains, in form of outer shell rotations, previously described in [6]. The radial diffusion [7], although certainly present, was not so evident.

We conjecture that another example of conformal matter could be the vortex lattice in type II superconductors, which is, unfortunately, only rarely directly observed due to the small size of each single vortex. We have tested our method on the scanned image of vortex lattice taken from [12] and have found results very similar to those presented in Fig. 2. This, however, may be accidental, since the lattice presented there contains only a small number of defects, and in such case our method should produce the histogram consisting of precisely one non-empty bin, located exactly at $\pi/3$ (60°). Additionally, the above lattice shows almost negligible variance of distances between nearest neighbors.

We think, that small clusters (and, perhaps, quasicrystals and nucleation centers) might be the formidable objects for further studies concerning conformal structures. The conformal structures should be created also when the interactions are purely repulsive, but the set of objects is confined in space either by strong external field or by hard-wall potential (we have investigated both such cases in our computer simulations). In the latter case even the external field is no longer necessary to create conformal structure, which may be hard to detect, but on the other hand – this very structure may be responsible for increased stability of small clusters compared to their bulk counterparts, as was very recently demonstrated for tin clusters [13] containing 15–30 atoms. The cited observation may be one of the first clear indications, that conformal matter, if this is the case, is the qualitatively different form of condensed matter.

Our computer simulations show, that conformal matter may exist in a nice form only as an assembly of relatively small number of individual constituents, typically 80–200 objects. Larger sets of objects tend to form the structures

resembling those of polycrystals, no matter how slowly the temperature is decreased during simulated crystallization. The role of *magic numbers* [6, 10] of the objects is not clear in those cases. On the other hand, it is obvious that the conformal matter cannot exist in arbitrarily large chunks – they would have to be unstable. Our calculations of structure factors for the conformal crystals, consisting of few hundreds of objects, show that the resulting X-ray image reflects the symmetry elements of the sample as a whole rather than the local (six-fold) symmetry, if any. In this respect the conformal matter appears as an amorphous material. In conclusion, it would be rather difficult to detect non-trivial conformal forms by traditional X-ray (or neutron) analysis.

Summarizing, we think that conformal (poly)crystals should be regarded as another form of the condensed matter, different from well known periodic, quasiperiodic [11], modulated or incommensurate crystals.

This work was supported in part within European Community program ICA1-CT-2000-70018 (Centre of Excellence CELDIS).

References

- [1] Piotr Pierański, Philos. Mag. **A37**, 107, 1978
- [2] Paweł Pierański, Phys. Rev. Lett. **45**(7), 569, 1980
- [3] François Rothen and Piotr Pierański, Phys. Rev. E **53**(3), 2828–2842, 1996
- [4] Krzysztof W. Wojciechowski and Jarosław Kłos, J. Phys. A: Math. Gen. **29**, 3963–3976, 1996
- [5] Krzysztof W. Wojciechowski, in proceedings of V Domestic Conference on Computer Aided Scientific Research, Wrocław – Polanica Zdrój (Poland), October 15–17, 1998, page 139 (in polish).
- [6] A.I. Belousov and Yu.E. Lozovik, Eur. Phys. J. D **8**, 251–264, 2000
- [7] I.V. Schweigert, V.A. Schweigert and F.M. Peeters, Phys. Rev. Lett. **84**(19), 4381, 2000
- [8] A.A. Thiele, Bell Syst. J., **50**(3), 725–773, 1971
- [9] W.F. Druyvesteyn, J.W.F. Dorleijn, Philips Res. Rep. **26**, 11–28, 1971
- [10] M. Golosovsky, Y. Saado and D. Davidov, `cond-mat/0008117`
- [11] Ron Lifshitz, `cond-mat/0008152`, submitted to *Ferroelectrics*
- [12] A.C. Rose-Innes, E.H. Rhoderick, *Introduction to superconductivity*, Pergamon Press, 1969
- [13] Alexandre A. Shvartsburg and Martin F. Jarrold, Phys. Rev. Lett. **85**(12), 2530, 2000

List of Figures

1	Microscopic image of the bubble array structure.	9
2	Distribution of crossing angles for the structure shown in Fig. 1. The center of the peak is located at 59.889° and its dispersion is 5.655° . For comparison the Gaussian distribution with the same parameters is superimposed on the original plot. The values given here are representative for the broad range of experimental conditions.	9

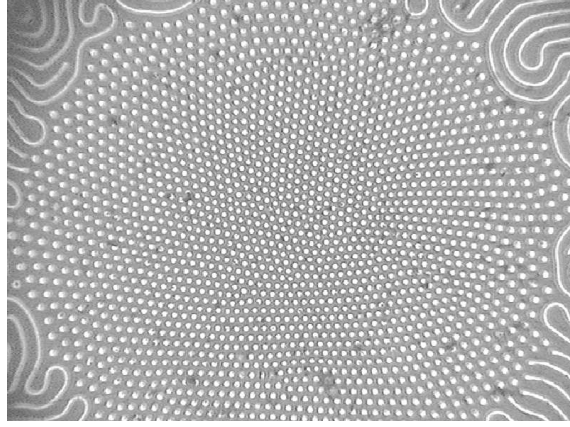


Figure 1: Microscopic image of the bubble array structure.

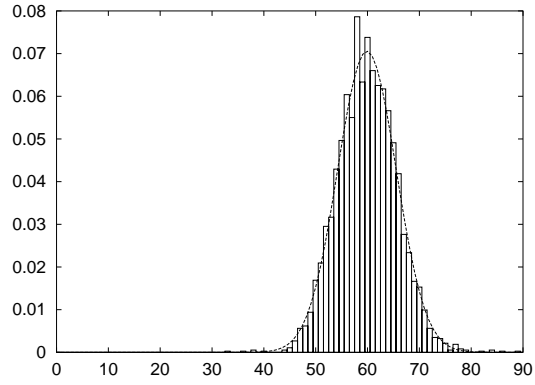


Figure 2: Distribution of crossing angles for the structure shown in Fig. 1. The center of the peak is located at 59.889° and its dispersion is 5.655° . For comparison the Gaussian distribution with the same parameters is superimposed on the original plot. The values given here are representative for the broad range of experimental conditions.