

Coupling of the lattice and superlattice deformations and hysteresis in thermal expansion for the quasi one-dimensional conductor TaS_3

A. V. Golovnya, V. Ya. Pokrovskii, and P. M. Shadrin

Institute of Radioengineering and Electronics, Russian Academy of Sciences, 103907 Moscow, Russia
(March 22, 2024)

An original interferometer-based setup for measurements of length of needle-like samples is developed, and thermal expansion of o-TaS_3 crystals is studied. Below the Peierls transition the temperature hysteresis of length L is observed, the width of the hysteresis loop $\Delta L = L - L_{\text{eq}}$ being up to $5 \cdot 10^5$. The behavior of the loop is anomalous: the length changes so that it is in front of its equilibrium value. The hysteresis loop couples with that of conductivity. The sign and the value of the length hysteresis are consistent with the strain dependence of the charge-density waves (CDW) wave vector. With lowering temperature down to 100 K the CDW elastic modulus grows achieving a value comparable with the lattice Young modulus. Our results could be helpful in consideration of different systems with intrinsic superstructures.

PACS Numbers: 71.45.Lr, 65.40.De

Internal degrees of freedom is a feature of a random system; in principle, they can give rise to metastable size states resulting, say, to hysteresis in thermal expansion.¹ A special class form the compounds with intrinsic superstructures. Comprising two periodicities, generally incommensurate, the compounds occupy intermediate place between genuine aperiodic and truly periodic systems.² In these systems, such as charge- and spin-density waves (CDW and SDW),³ Wigner crystals, superconductors in magnetic fields,⁴ structurally incommensurate crystal phases,⁵ the superstructure periodicities could be varied by external fields or temperature changes. The resulting metastable configurations can be reflected back onto the elastic properties and size of the underlying lattice,^{3,5} though this question is still poorly understood.

Quasi one-dimensional conductors with CDW belong to a widely studied class of materials, in which intrinsic superstructure develops through the Peierls transition⁶. When electrons condense into CDW they form a deformable medium, i.e. an electronic crystal. Deformation of the CDW affects their main static and dynamic properties and gives rise to metastability and hysteresis.

The straightforward treatment of the CDW as a spring, whose strain is just applied to the crystal at the ends or via the impurities is not valid. Moreover, in the simple one-dimensional model the strains of the CDW and the crystal do not couple at all: if initially the CDW are relaxed, any change of the crystal length would not draw the CDW away from the equilibrium, i.e. give rise to a CDW deformation,⁷ as it was noticed in Refs. 8{11. Similarly, once the CDW is deformed, any change of the lattice constant, c , would neither decrease nor increase the deviation of the CDW wavelength from the equilibrium value, λ_{eq} . So, within this model a CDW deformation would not give rise to a length change.

At the same time, the interaction of the CDW and the lattice is clearly seen from the elastic anomalies, including a drop of the Young modulus of the lattice,^{8{11} Y_1 , up to 4%,¹⁰ when the CDW become depinned.

Mozurkewich⁸ has concluded that the lattice deformation does give rise to a deformation of the CDW: when the CDW are at rest, they cannot relax, and so they contribute to the total elastic energy; the sliding CDW relax rapidly and their contribution drops out.⁸ For his model Mozurkewich⁸ introduced an empirical parameter g reflecting the deviation of λ_{eq} from the simple one-dimensional model:

$$\lambda_{\text{eq}}(c) = \lambda_{\text{eq}}(c_{\text{eq}}) = (g + 1) c = c_{\text{eq}}; \quad (1)$$

$g \notin 0$. However, no way was proposed to estimate g .

Another remarkable observation was reported in Ref. 12: the length L of TaS_3 samples as a function of electric field demonstrated hysteresis partly scaling with that of resistance. The values of L obtained at different directions of the voltage sweep differed by 10^6 . This result was also treated in terms of coupling of the CDW strains with the deformation of the pristine lattice. Note that the field-induced length change (as well as the change of resistance) results only from an inhomogeneity of the sample properties: obviously, the length could depend on the voltage polarity only if the inversion symmetry of the sample is broken¹². Thus, study of the electric-field induced hysteresis of length can not provide complete understanding of the CDW-lattice coupling.

To study the effect of the CDW deformation on the crystal length it could be more fruitful to observe thermal hysteresis of L . With changing temperature the q -vector ($q = 2\pi/\lambda$) falls behind its equilibrium value, which is temperature dependent;¹³ the deviation of q from the equilibrium is limited by the critical deformation at which the phase slippage (PS) begins.¹⁴ So, thermal cycling creates a CDW deformation, which is relatively uniform along the sample and is of the maximum possible value.

For our study we chose o-TaS_3 as a representative CDW conductor. Among the quasi one-dimensional conductors TaS_3 is one of the most widely studied, including the elastic properties. TaS_3 demonstrates the Peierls

transition at $T_P = 220$ K, below which the resistance follows an activation law revealing the half-gap $E_g = 700$ K. The dependence $R(T)$ demonstrates a pronounced hysteresis, the width of the loop $R = R$ being up to 50 % at T around 100 K.

In the present Letter we report temperature hysteresis of length for o-TaS₃; the hysteresis couples with that of resistance having an anomalous sign. A quantitative treatment of the effect is proposed.

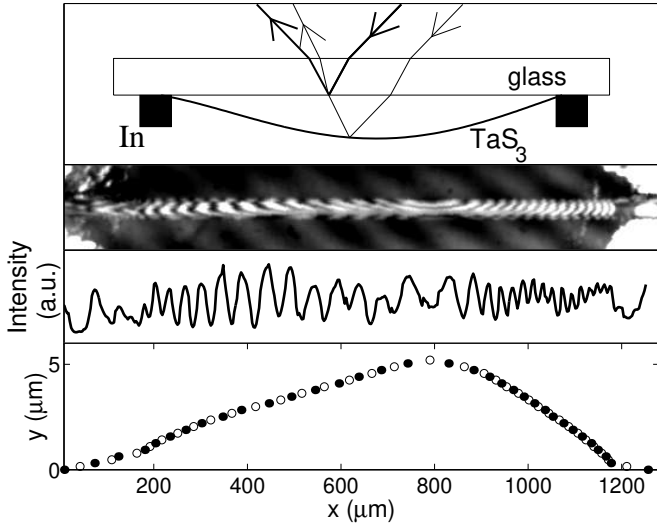


FIG. 1. a) Arrangement of a TaS₃ sample on the substrate and the scheme of the reflections and interference of the laser beams (the incidence is close to normal). b) An example of an image obtained, c) the section of the image, d) the resulting profile of the sample. The open circles correspond to the minima in the section (Fig.1c), and the closed circles to the maxima.

We studied samples of TaS₃ with typical length 1 mm, width 15(35) μm, and thickness 5-10 times less. The samples were arranged on a transparent glass substrate (Fig. 1a). The contacts were fixed on the substrate with indium, while the central part of the sample formed an arc. The inner surface of the substrate played the role of a semi-transparent mirror. The laser beam with wavelength $\lambda = 635$ nm fell down through the substrate, and partially reflected from the inner surface of the substrate and from the sample surface forming an interference pattern (similar with the wedge interference). The pattern was fixed with a video camera combined with a microscope. An example of such a pattern is shown in Fig. 1b. The neighboring dark or bright fringes correspond with change of the sample distance y from the substrate surface by $\lambda/2$. Making sections of such images (an example is shown in Fig. 1c) we obtained the profiles $y(x)$ of the samples, like the curve presented in Fig. 1d. Finally, the length of such curves was calculated. We detect a length change about 5 Å which corresponds to the relative length change $\Delta L/L = 5 \cdot 10^{-6}$, though in principle

the sensitivity could be improved.¹⁵ Our estimates have shown that the contributions to ΔL due to the changes of stress and Y_1 are negligible.¹⁶ Thus, the observed changes of L with temperature were associated with the change of the equilibrium sample length with respect to the substrate. To have absolute results we have measured thermal expansion of the glass substrate in addition.

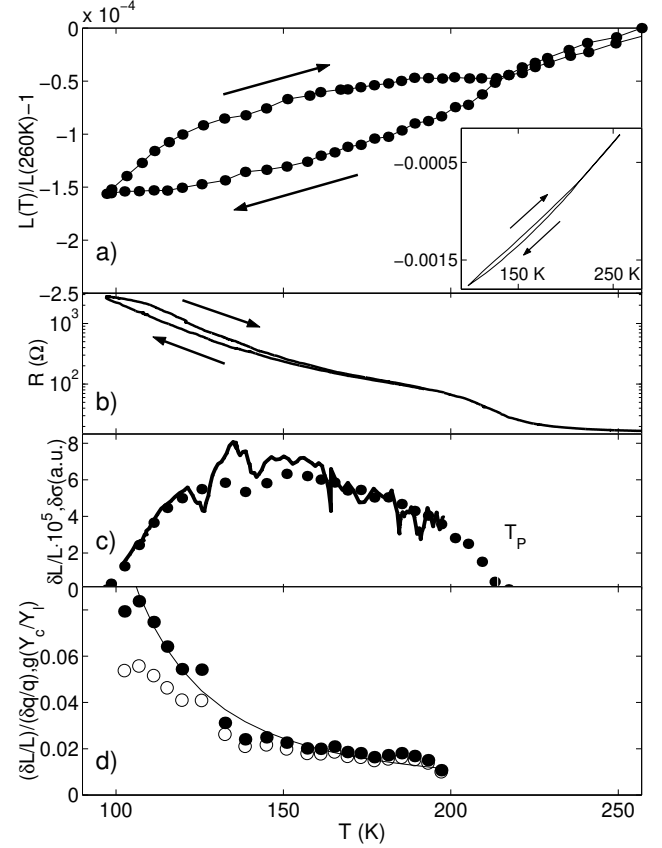


FIG. 2. a) Temperature dependence of $\Delta L = L$ with respect to glass. The absolute thermal expansion is shown in the inset. b) $R(T)$ measured simultaneously. c) The width of the length (the circles) and conductivity (the solid line) hysteresis loops as a function of T . d) The ratio $(\Delta L/L) = (\Delta g/g) \cdot (Y_c/Y_1)$ (open circles) and gY_c/Y_1 (black circles) resulting from Fig. 2c. We use Eq. 3 and the $R(T)$ dependence.²¹ The solid line indicates $Y_c / \exp(470/T)$.

Figs. 2a) and b) show the temperature dependences of length (with respect to glass) and of the resistance for the representative sample of TaS₃. In the inset to Fig. 2a) the absolute dependence of length is shown.¹⁷ The dependences of length and resistance both clearly show hysteresis below the Peierls transition temperature $T_P = 214$ K. The length hysteresis loop opens immediately below T_P . The development of hysteresis is the dominating effect near T_P , on whose background it is difficult to distinguish a feature coupled to the transition in itself.¹⁸ The length hysteresis grows below T_P achieving

$L=L = 5 \cdot 10^6$ (Fig. 2a), which by 1.5 orders of magnitude exceeds the maximum value reported in Ref. 12. At the same temperature the states approached from lower temperature have higher length than those approached from above. Correspondingly, application of electric field exceeding the threshold reduces the length after heating the sample, and increases after cooling. Thus, the main effect of electric field is the relaxation of the thermally induced states. The length change induced by the field in itself was 10^6 , like in Ref. 12. Note, that the sign of the hysteresis is non typical: the length is in front of its equilibrium value (inset to Fig. 2a), but not behind.

The length hysteresis apparently couples with the resistance hysteresis, higher length corresponding to higher resistance at a given temperature.¹⁹ The coupling between R and L is well seen from Fig. 2c, where the temperature dependence of $L=L$ is presented together with the loop of conductivity, $L=R_{cool}$, $L=R_{heat}$. Note that in the unipolar approximation $300(\text{K}) = (300)$, where the index "300" marks the room temperature values. So, the hysteresis reflects that of the CDW wavelength to the accuracy of the temperature dependence of the mobility, which in turn can be found from Ref. 21. Fig. 2d shows the ratio $(L=L) = (\text{K})$ vs. T . At the low temperatures $L=L$ is 6% of the CDW deformation.

As we have noticed in the beginning, the interactions of the CDW and the sample cannot be presented as that of two springs connected in parallel (the lower inset to Fig. 3). Though we do not see a way to obtain quantitatively the strain dependence of the q -vector for TaS_3 , one can recall experimental results, from which it is possible to estimate the value of g (Eq. 1). It has been found²² that at a certain value of uniaxial strain S the properties of the CDW change abruptly: e.g., the non-linear conduction nearly disappears. This has been attributed to the transition of the CDW to the 4-fold commensurability. Comparing the normalized dependences of the q -vector¹³ and of the strain S ²² on temperature (Fig. 3) one can see that they become similar²² if one multiplies the value of S by 6. Thus, one can assume that a deformation of the lattice induces the change of the equilibrium CDW wavelength $\lambda_{eq}(c)$ in accordance with Eq. (1) with $g = 6$. Such a large value of g indicates that the simple 1-dimensional model⁷ cannot even roughly describe the strain-induced change of λ_{eq} . Evidently, the change of λ_{eq} is dominated by transverse effects: the longitudinal strain decreases the thickness of the sample resulting in an increase of the intrachain coupling. This modifies the form of the Fermi surfaces, and consequently, the q -vector.²² To comprehend the sign and the value of the q change one should study the evolution of the Fermi surface in detail. In principle, we cannot exclude that g is temperature dependent. However, as we shall see below, the assumption that $g = \text{const}$, namely $g = 6$, is consistent with our experiment.

For the next step, we present the elastic energy density W as a sum of the lattice and the CDW energies:

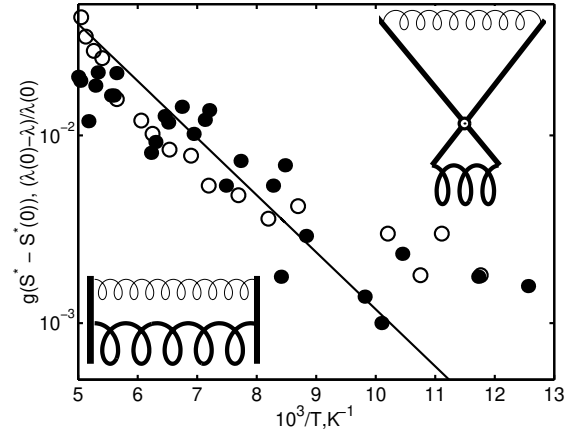


FIG. 3. The temperature dependences of $S - S(0)$ (open circles)²² and of the wave vector¹³ $(q - q(0))/q(0)$ (closed circles).²³ S is multiplied by $g = 6$. Insets: the equivalent schemes illustrating the interaction of the CDW (the thin-line spring) and the pristine lattice (the thick-line spring). The lower-left sketch is the naive scheme, which is invalid. The upper-right sketch illustrates Eq. 3 ($g > 1$).

$$W = \frac{1}{2} (Y_1 (\frac{c}{c_{eq}} - \frac{c_{eq}}{c})^2 + Y_c (\frac{c}{c_{eq}} - \frac{c_{eq}}{c})^2); \quad (2)$$

where Y_1 and Y_c are the elastic moduli of the lattice and the CDW respectively. Taking into account the condition (1)²⁴ and assuming that no PS occurs ($c = \text{const}$), we can minimize W and obtain the resulting length change:

$$\frac{L}{L_0} = \frac{c}{c_{eq}} = g \frac{Y_c}{Y_1 + g^2 Y_c} = \frac{Y_c}{Y_1}; \quad (3)$$

where L_0 is the initial CDW deformation (at fixed c). The approximation implies that $g^2 Y_c \ll Y_1$. Eq. 3 is quite transparent: the crystal deformation as a spring connected in parallel to the CDW, but with a factor g . $g > 0$ means that, say, compressed CDW ($c < c_{eq}$) would result in a decrease of the sample length, which agrees with our observation. E.g., cooling corresponds to growth of c_{eq} ¹³, so the CDW is in compressed state ($c_{eq} < c$), which results in decreased L (Fig 2a). The CDW { crystal interaction could be illustrated with a scheme consisting of two springs connected via a lever (Fig. 3, upper inset).

From Eq. 3 it follows that the ratio $(L=L) = (\text{K})$ (Fig. 2d) equals $g Y_c = Y_1$. Note, however, that with $g = 6$, $g^2 Y_c$ at low temperatures is comparable with Y_1 , and one should use the exact version of Eq. 3. The resulting value of $g Y_c = Y_1$ is also shown in Fig. 2d. One can see the growth of the CDW elastic modulus with lowering temperature, though slower than $Y_c / \exp(-T)$ ^{14,25} (see the solid line in Fig. 2d).²⁶ Note that the curve $(L=L) = (\text{K})$ vs. T resembles the temperature dependences of the lattice softening in electric field¹⁰. This could be expected, since from Eqs. 1 and 2 it follows that the value $g^2 Y_c$ is added to Y_1 when the CDW are at rest, while in the sliding state the CDW contribution drops out⁸.

From the condition of neutrality²⁵ accompanying the CDW deformation we can obtain for the CDW Young modulus: $Y_c = \frac{d}{dq} \frac{q^2}{s}$ ¹⁴, where $\frac{d}{dq}$ is the derivative of the chemical potential level by the CDW q -vector, and s is the area per chain. Substituting this in Eq. 3, we obtain:

$$\frac{L}{L} = \frac{2}{g \frac{d}{dY_1}}: \quad (4)$$

For the unipolar (p -type for TaS_3) conduction^{14;21} $= T \ln(R_{\text{heat}}/R_{\text{cool}})$. Substituting into Eq. 4 $g = 6$, $= 50 \text{ K}$ (for $T = 120 \text{ K}$, Fig. 2b), $= 10 \text{ A}$, $s = 80 \text{ \AA}^2$ (Ref. 27), $Y_1 = 380 \text{ GPa}$ ²⁸, we obtain $L = L = 3 \cdot 10^8$, in agreement with the experiment (Fig. 2b). This agreement supports the approach we used to estimate g , and proves that under a certain uniaxial strain (S) the CDW in fact transit to the 4-fold commensurability.²²

In conclusion, we have observed thermal hysteresis of length for the quasi one-dimensional conductor TaS_3 . In the framework of the model proposed the observed anomalous sign and value of the hysteresis loop are consistent with the dependence of the q -vector on the lattice strain. The results could be helpful in understanding the behavior of other systems with intrinsic superstructures, whose parameters could be rearranged due to the temperature effects or external fields.

We are thankful to G.P. Vorob'ev, S.G. Zybtshev, and S.V. Zaitsev-Zotov for help in the experiment and discussions, to S.N. Artemenko, A.A. Sinchenko, V.B. Preobrazhenskii, G.V. Stepanov, J.W. Brill, and M.E. Itkis for helpful discussions. We acknowledge RFBR (02-02-17301, 00-02-22000 CNRS), the State programs "Physics of Solid-State nanostructures" and "Low-Dimensional quantum structures", NW O and INTAS-01-0474.

- ¹ For a recent example see: P. Nagel, V. P. Laster, C. Meingast, A. Rykov, and S. Tajima, Phys. Rev. Lett. 85, 2376 (2000).
- ² J. Voit, L. Perfetti, F. Zwirk, H. Berger, G. Margaritondo, G. G. Guner, H. Hochst, M. G. Rioni, Science 290, 501 (2000).
- ³ J.W. Brill in: Handbook of Elastic Properties of Solids, Liquids, and Gases, Volume II, Ed. by M. Levy, H.E. Bass, and R.R. Stein, (Academic Press 2001), pp. 143-162.
- ⁴ V.V. Eremenko, V.A. Sirenko, H. Szymczak, and A. N. Abilek, Low Temp. Phys. 25, 225 (1999).
- ⁵ H.Z. Cummins, Physics Reports 185, 211 (1990).
- ⁶ Charge Density Waves in Solids, edited by L.Gorkov, G.G. Guner (Elsevier Science, Amsterdam, 1989); G.G. Guner in: Density Waves in Solids (Addison-Wesley Reading, Massachusetts, 1994);
- ⁷ This follows from the fact that on longitudinal deformation of a sample the number of electrons per the lattice period does not change, and $\epsilon_{eq}(c)$ changes proportionally to c , i.e. $\epsilon_{eq}(c) = \epsilon_{eq}(C_{eq}) = C_{eq} \epsilon_{eq}$.
- ⁸ G.M. Ozurkewich, Phys. Rev. B 42, 11183 (1990).
- ⁹ J.W. Brill and W. Roark, Phys. Rev. Lett. 53, 846 (1988); Phys. Rev. B 36, 2969 (1987).

- ¹⁰ R.L. Jacobsen and G.M. Ozurkewich, Phys. Rev. B 42, 2778 (1990).
- ¹¹ Z.G. Xu and J.W. Brill, Phys. Rev. B 45, 3953 (1992).
- ¹² S. Hoen, B. Burk, A. Zettl, and M. Inui, Phys. Rev. B 46, 1874 (1991).
- ¹³ Z.Z. Wang, H. Salva, P. Monceau, M. Renard, C. Roucau, R. Ayroles, F. Levy, L. Guemas, and A. Meerschaut, J. Phys. Lett. France 44, L315 (1983).
- ¹⁴ V.Ya. Pokrovskii and S.V. Zaitsev-Zotov, Synthetic Metals 32 321 (1989).
- ¹⁵ The interferometric methods for thermal expansion resolve 10^{-2} to 10^{-4} of a fringe [T.H.K. Barron, J.G. Collins and G.K. White, Adv. Phys. 29, 609 (1980)]; in our conformation this corresponds to $L = L \cdot 10^8$ to 10^{10} .
- ¹⁶ A.V. Golovnya, V.Ya. Pokrovskii, to be published.
- ¹⁷ D. Maclean and M.H. Jericho, Phys. Rev. B 47, 16169 (1993): the presented thermal expansion (at considerable sample strain and at high electric fields) is in rough agreement with our data.
- ¹⁸ If one takes $L(T) = (L_{\text{cool}}(T) + L_{\text{heat}}(T))/2$, he will obtain a decrease of length $\sim 10^{-5}$ associated with the Peierls transition, in qualitative agreement with Ref. 17.
- ¹⁹ In Ref. 12 the state with smaller L corresponded to higher R . Evidently, both the R and L changes reported¹² result from non-complete compensation of the contact CDW deformations of opposite signs. In this case one can obtain an arbitrary relation between the R and L hysteresis dominated by the non-linear effects. Concerning our experiment, the small difference in the forms of the loops of L and R (Fig. 2c), as well as the small loop of L above T_p (Fig. 2a), is evidently within our experimental error.
- ²⁰ D.V. Borodin, S.V. Zaitsev-Zotov and F.Ya. Nad', Zh. Eksp. Teor. Fiz. 93, 1394 (1987); [Sov. Phys. JETP 66, 793 (1987)]; this relation could be easily obtained from the neutrality condition if one notes that a variation of the q -vector changes the number of the states under the Peierls gap, and, thus, the number of quasiparticles.
- ²¹ Yu.I. Latyshev, Ya.S. Savitskaya, and V.V. Frolov, JETP Lett. 38, 541 (1983).
- ²² V.B. Preobrazhensky, A.N. Taldenkov, I.Yu. Kalnova, Pis'ma v Zh.ETF, 40, 182 (1984) [JETP Lett. 40, 944 (1984)]; V.B. Preobrazhensky, A.N. Taldenkov, S.Yu. Shabanov, Solid State Commun. 54, 1399 (1985).
- ²³ We took $S(0) = 3.9 \cdot 10^3$, and $q(0) = 0.2503c$ suggesting that both dependences follow the Arrhenius law (the slope of the line corresponds to 700 K, which is close to T_p).
- ²⁴ Eq. 2 implies that the principal part of the CDW elastic energy is associated with their longitudinal deformations, while Eq. (1) takes into account the dependence of ϵ_{eq} on all components of the crystal deformation.
- ²⁵ S.N. Artemenko and A.F. Volkov, Zh. Eksp. Teor. Fiz. 81, 1872 (1981); [Sov. Phys. JETP, 54, 992 (1981)]
- ²⁶ Actually the CDW deformation is spatially non-uniform, so one can expect non-linear effects, e.g. the reduction of Y_c at low T .
- ²⁷ P. Monceau in: Electronic Properties of Inorganic Quasi-one-dimensional Conductors, Part 2. Ed. by P. Monceau. Dordrecht: D. Reidel Publ. Comp., 1985.
- ²⁸ J.W. Brill, Solid State Commun. 41, 925 (1982).