

# Structural transformation induced by magnetic field and colossal magnetoresistance response above 313 K in $\text{MnAs}$

J. M. Iriarte,<sup>1</sup> F. Rivadulla,<sup>2</sup> J. Rivas,<sup>1</sup> A. Fondado,<sup>1</sup> R. Caciuc,<sup>3</sup> F. Carsughi,<sup>3</sup> T. Guidi,<sup>3</sup> and J. B. Goodenough<sup>2</sup>

<sup>1</sup>Departamento de Física Aplicada, Universidad de Santiago de Compostela, E-15782 Santiago de Compostela, Spain

<sup>2</sup>Texas Materials Institute, ETC 9.102, The University of Texas at Austin, Austin, Texas 78712, USA

<sup>3</sup>Istituto Nazionale per la Fisica della Materia, Dipartimento di Fisica ed Ingegneria dei Materiali e del Territorio, Università di Ancona, I-60131 Ancona, Italy

$\text{MnAs}$  exhibits a first-order phase transition from a ferromagnetic, high-spin metallic  $\text{NiAs}$ -type hexagonal phase to a paramagnetic, lower-spin insulator  $\text{MnP}$ -type orthorhombic phase at  $T_C = 313$  K. Here, we report the results of neutron diffraction experiments showing that an external magnetic field,  $B$ , stabilizes the hexagonal metallic phase above  $T_C$ . The phase transformation is reversible and constitutes the first demonstration of a bond-breaking transition induced by a magnetic field. At 322 K the hexagonal structure is restored for  $B > 4$  tesla. The field-induced phase transition is accompanied by an enhanced magnetoresistance of about 17 % at 310 K. We discuss the origin of this phenomenon, which appears to be similar to that of the colossal magnetoresistance response observed in some members of the manganese perovskite family.

$\text{MnAs}$  is a commercially available material, intensively studied, both theoretically and experimentally, since the beginning of the last century. Interest in this compound could come up again as a consequence of new ideas and conjectures formulated during the last decade in connection with the study of the colossal magnetoresistance (CMR) response in  $\text{Mn}$  perovskites [1]. Among these ideas is the invocation of a phase separation scenario for CMR manganese oxides and related materials [2], that might be of particular relevance in systems, like  $\text{MnAs}$ , where first-order phase transitions occur.

To our knowledge,  $\text{MnAs}$  was first studied by Heusler [3], and later by Hilpert and Dieckmann [4, 5, 6], who discovered that the compound is ferromagnetic with a Curie temperature of  $T_C \approx 313$  K. Serres [7] and Guillaud [8] found that a metal-insulator transition occurs at  $T_C$ . The abrupt loss of magnetization at  $T_C$  led Meyer and Taglang [9] to assume a ferromagnetic-antiferromagnetic transition at  $T_C$ . However, a neutron-diffraction study by Bacon and Street [10] showed that this was not the case. At the same time, Willis and Rooksby [11] measured a large (1.86 %) discontinuous density change at  $T_C$  that had been previously detected by Smith, Gerding, and Verma [12]. Bean and Rodbell [13] used the volume change to describe the first-order loss of magnetization, which takes place with a latent heat of 1.79 cal/K [14], in terms of a volume-dependent exchange interaction. DeBlois and Rodbell [15] explored the change in  $T_C$  with pressure to  $P = 1$  kbar in fields  $0 < B < 11$  T. A second-order phase transition, with no volume change, was detected by calorimetric measurements at  $T_t = 399$  K [9, 16]. Between  $T_C$  and  $T_t$ , the magnetic susceptibility increases with temperature [7, 17], transforming to a

Curie-Weiss law above  $T_t$ . X-ray diffraction studies [18] revealed a change in the crystallographic arrangement at the first-order transition point, from the  $\text{NiAs}$ -type ( $B_8$ ) hexagonal structure to the  $\text{MnP}$ -type ( $B_{31}$ ) orthorhombic one. The orthorhombic distortion decreases with increasing temperature and the hexagonal  $B_{31}$  structure reappears above  $T_t$ . It was soon recognized that a crossover from high to low spin states on the manganese site could occur on going from the  $B_8$  to the  $B_{31}$  structure [19] (Fig. 1). This conjecture led to a study of the  $\text{MnAs}_{1-x}\text{Px}$  and  $\text{MnAs}_{1-x}\text{Sbx}$  systems that demonstrated the spin transition [20]. Studies of the influence of higher hydrostatic pressure on  $\text{MnAs}$  led to a modification of the Bean-Rodbell theory [16, 21]. The spin-state instability appears to be responsible for a giant magnetoelastic response reported recently by Chemenko et al. [22].

Our neutron diffraction study of the stability of the orthorhombic  $B_{31}$  phase of  $\text{MnAs}$  in an applied magnetic field  $B$  was performed on the high-resolution powder diffractometer D2B of the Institute Laue-Langevin in Grenoble, France. Two kinds of polycrystalline samples were measured for this work, namely a commercial one provided by Western Inorganics and another synthesized in our laboratory by solid-vapor reaction.  $\text{Mn}$  and  $\text{As}$  powder ( $\sim 325$  mesh) were sealed in evacuated ( $P \approx 10^{-5}$  torr.) quartz tubes and heated at 823 K for 24 hours. This process was repeated several times with intermediate grindings to obtain the pure compound. In the commercial sample we detected the presence of  $\text{MnO}$  impurities, but this has no influence on the structural results here discussed. For neutron diffraction experiments, two grams of  $\text{MnAs}$  were packed in a cylindrical vanadium holder and inserted into a 5-tesla superconducting cryomagnet. The instrument is equipped with 64 collimated  $^3\text{He}$  detectors spaced at 2.5 intervals and covering a 2 angular range from  $5^\circ$  to  $165^\circ$ . A complete diffraction pattern was obtained by moving the detector bank 100

On leave from Departamento de Química-Física, Universidad de Santiago de Compostela, E-15782 Santiago de Compostela, Spain

times in angular steps of 0.025°. Data have been collected with incident neutrons of wavelength  $\lambda = 1.5943$  (Å) selected by Ge (3 3 5) monochromators.

At room temperature, below  $T_C = 313$  K, the diffraction pattern was that of the hexagonal  $B_{81}$  phase with lattice parameters in agreement with those reported by Willis and Rooksby [11]. Reflections belonging to the orthorhombic  $B_{31}$  structure described by Wilson and Kasper [18] appeared above  $T_C$ . As shown in Fig. 2, the differences between the diffraction patterns measured in zero field at 300 K and 322 K are readily apparent. However, with the sample held at 322 K, the application of a magnetic field modifies substantially the diffraction profile. For a  $B = 5$  T, the diffraction pattern at 322 K is essentially the same as that at 300 K in zero applied field. The hexagonal  $B_{81}$  structure is clearly restored fully by the application of a  $B = 5$  T. As is clear from Fig. 3, the extent of the orthorhombic distortion decreases continuously as  $B$  increases, nearly vanishing by  $B = 4$  T. These data do not show a sharp transition, but rather the coexistence of two phases with the growth of the ferromagnetic phase at the expense of the paramagnetic  $B_{31}$  phase as  $B$  increases. Growth of the ferromagnetic phase is possible because the  $B_{31}$  phase is derived from the  $B_{81}$  phase by a co-operative displacement of pairs of  $[1, -1, 0]$  rows toward one another to form stronger Mn-Mn bonds, across shared octahedral-site edges in zig-zag chains within the basal planes. These displacements also create shorter Mn-A s bonds, which raises the antibonding states that  $\sigma$ -bond to the A s atoms and triggers the transition to a low-spin state [21].

Extrapolation of the Brillouin temperature dependence of the magnetization of the  $B_{81}$  phase to above the first-order transition at  $T_C$  gives a fictitious Curie temperature  $T_C = 388$  K. Since an applied magnetic field  $B$  stabilizes the high-spin, ferromagnetic phase relative to the  $B_{31}$  paramagnetic phase, a global insulator-metal  $B_{31}$ - $B_{81}$  transition might be induced by  $B$  in the interval  $T_C < T < T_t$ . Alternatively, if  $B_{81}$  regions exist within a  $B_{31}$  matrix in the interval  $T_C < T < T_t$ , we can expect that below  $T_C$  the ferromagnetic  $B_{81}$  regions will grow in a magnetic field at the expense of the paramagnetic  $B_{31}$  matrix to beyond the percolation threshold. In either case, a CMR would occur between  $T_C$  and  $T_t$ . If the  $B$  field induces a global  $B_{31}$ - $B_{81}$  transition, it would give a CMR analogous to that found, for example, at the metal-magnetic transition of the charge and orbital-ordered CE phase of the perovskite  $\text{Nd}_{0.5}\text{Sr}_{0.5}\text{MnO}_3$  [23]. If, on the other hand, the magnetic field nucleates and/or grows the  $B_{81}$  phase, it would give a CMR phenomenon analogous, for example, to that of the perovskite system  $(\text{La}_{0.7-x}\text{Pr}_x\text{Ca}_{0.3})\text{MnO}_3$  [24]. However, whereas the CMR occurs in the manganese oxides at too low a temperature to be technically practical, it would occur in MNAs a little above room temperature and could easily be adjusted to operate at room temperature by small

compositional changes.

Fig. 4 shows the enhanced magnetoresistance response of MNAs measured in the predicted temperature range,  $T_C < T < T_t$ . Almost the same results were obtained for both samples used in this study. Although the absolute value of the magnetoresistance is not as large as in other compounds like  $\text{La}_{2/3}\text{Ca}_{1/3}\text{MnO}_3$  [25], we call it a CMR to highlight the common origin with that in the manganites. Analogies between the behavior of MNAs in a magnetic field above  $T_C$  and that of the manganese-oxide perovskites are noteworthy. In the manganese perovskites, the  $\sigma$ -bonding d electron of a high-spin octahedral site Mn(III) ion occupies a twofold-degenerate pair of e-orbitals. This e-orbital degeneracy is removed by a local distortion of the  $\text{MnO}_6$  octahedron; and at lower temperatures and high Mn(III) concentrations, the local distortions are ordered cooperatively so as to minimize the associated elastic energy. A recent study of  $\text{LaMn}_{1-x}\text{Ga}_x\text{O}_3$  [26] has shown that in this single-valent system, dilution of the Mn(III) atoms suppresses the orbital ordering in local ferromagnetic regions; a vibronic superexchange is ferromagnetic whereas the orbitally ordered matrix is antiferromagnetic. In this system, application of  $B$  disorders the orbital order of the matrix to transform a spin glass to a ferromagnet [26]. In the mixed-valent perovskite system  $\text{La}_{1-x}\text{Sr}_x\text{MnO}_3$ , an orthorhombic-rhombohedral structural phase transition is induced by an external magnetic field for  $x = 0.17$  [27]; this transition involves a change from  $[1, -1, 0]$  to  $[1, 1, 1]$  of the axis of cooperative rotation of the  $\text{MnO}_6$  octahedra. A crossover from localized to itinerant behavior of the  $\sigma$ -bonding e-electrons occurs in the compositional interval  $0.1 < x < 0.17$  [28]. In this interval, hole-rich ferromagnetic regions are segregated from a hole-poor paramagnetic matrix in the paramagnetic temperature range  $T_C < T < 300$  K by cooperative oxygen displacements. The hole-rich regions are mobile, and they grow in  $B$  to beyond a percolation threshold by  $B = 5$  T to give the CMR phenomenon. In the interval  $0.1 < x < 0.15$ , the transition at  $T_C$  is first-order; and in a narrow temperature range  $T_{00} < T < T_C$ , the orbitals undergo a rearrangement to another type of order below  $T_{00}$ . Near  $x = 0.1$ , the interval  $T_{00} < T < T_C$  narrows, and the matrix remains orbitally ordered in zero magnetic field to give spin-glass behavior typical of ferromagnetic clusters having a  $T_C$  greater than the Neel temperature of the matrix. However, the orbitals of the matrix become disordered in a modest  $B$  to give ferromagnetic order below a  $T_C$ . Recently, Mira et al. [29] have observed a second-order transition at a temperature  $T > T_C$  in the compositional interval where they had noted a first-order transition at  $T_C$  [30]. In the range  $T_C < T < T_t$ , a non-Curie-Weiss paramagnetism has been found by de Teresa et al. [31], similar to the behavior of MNAs in the range  $T_C < T < T_t$  [7, 8]. Moreo et al. [32] have made a computational study to argue that in the mixed-valent

manganese-oxide perovskites, hole-rich clusters that are metallic and ferromagnetic coexist with a paramagnetic, hole-poor insulating matrix; the ferromagnetic clusters grow in a magnetic field B. G. Goodenough [33] has invoked the virial theorem to make the same deduction for the manganese-oxide perovskites at the crossover from localized to itinerant behavior of the  $d$ -bonding electrons. However,  $MnAs$  is single-valent, so the analogy with  $LaMn_{1-x}Ga_xO_3$  is more appropriate even though this perovskite remains insulating in the ferromagnetic phase. In  $MnAs$ , the basal-plane orbitals on the  $Mn$  atoms are half-filled, and the electrons approach the crossover from localized to itinerant electronic behavior. In the paramagnetic  $B31$  phase, the  $Mn$  atoms become displaced below  $T_c$  so as to form stronger  $Mn-Mn$  bonds in the zig-zag chains and weaker  $Mn-Mn$  bonds between the chains. These displacements not only order the  $Mn-As$  bonding so as to induce the low-spin state, but they also represent an ordering of the in-plane  $Mn-Mn$  bonds that changes the translational symmetry so as to split the basal-plane band at the Fermi energy. Ferromagnetic interactions by the other  $d$  electrons are dominant, but these interactions are weakened by the transition to the low-spin state, which reduces the  $Mn-Mn$  separation and strengthens the in-plane  $Mn-Mn$  bonding. Since no bonding occurs between half-filled orbitals with parallel spins, stabilization of the high-spin ferromagnetic  $B8_1$  phase suppresses in-plane  $Mn-Mn$  bonding and increases the in-plane  $Mn-Mn$  separation. Stabilization of the ferromagnetic phase in a  $B$  with removal of the in-plane  $Mn-Mn$  bonding is to be compared with suppression by a  $B$  of the orbital ordering at the  $Mn(III)$  ions in  $LaMn_{1-x}Ga_xO_3$ . This is the first crystallographic transition induced by a magnetic field that involves breaking of metallic bonds rather than orbital disorder.

We are pleased to thank the valuable aid provided by A. Hewat and the LL technical staff during the neutron diffraction experiment and the operation of the cryomagnet in unusual conditions and J. S. Zhou, from the Texas Materials Institute for his help with the magnetoresistance measurements. F. R. thanks the Fulbright foundation and MEC from Spain for a postdoctoral fellowship. We also acknowledge the DGI of the Ministry of Science and Technology of Spain for financial support under project MAT2001-3749 JBG thanks the NSF for financial support.

---

[1] J. M. D. Coey, M. Viret, and S. von Molnar, *Adv. Phys.* 48, 167 (1999).

[2] A. Moreo, S. Yunoki, and E. Dagotto, *Science* 283, 2034 (1999).

- [3] F. Heuser, *Z. Angew. Chem.* 17, 260 (1904).
- [4] S. Hilpert and T. Dieckmann, *Ber. D. Chem. Ges.* 44, 2378 (1911).
- [5] S. Hilpert and T. Dieckmann, *Ber. D. Chem. Ges.* 44, 2831 (1911).
- [6] S. Hilpert, T. Dieckmann, and E. Colver-Glauert, *Trans. Faraday Soc.* 8, 207 (1912).
- [7] A. Serres, *J. Phys. Radium* 8, 146 (1947).
- [8] C. Guillaud, *J. Phys. Radium* 12, 223 (1951).
- [9] A. J. P. Meyer and P. Taglang, *J. Phys. Radium* 12, 63S (1951).
- [10] G. E. Bacon and R. Street, *Nature* 175, 518 (1955).
- [11] B. T. M. Willis and H. P. Rooksby, *Proc. Phys. Soc. (London)* B 67, 290 (1954).
- [12] A. Smits, H. Gerding, and F. Vermaast, *Z. Physik. Chem. Bodenstein Festband (Leipzig)*, 357 (1931).
- [13] C. P. Bean and D. S. Rodbell, *Phys. Rev.* 126, 104 (1962).
- [14] L. F. Bates, *Proc. Roy. Soc. (London)* A 117, 680 (1928).
- [15] R. W. de Blois and D. S. Rodbell, *Phys. Rev.* 130, 1347 (1963).
- [16] M. Menyuk, J. A. Kafalas, K. Dwight, and J. B. Goodenough, *Phys. Rev.* 177, 942 (1969).
- [17] F. Bates, *Phil. Mag.* 8, 714 (1929).
- [18] R. H. Wilson and J. S. Kasper, *Acta Cryst.* 17, 95 (1964).
- [19] J. B. Goodenough, In *Unconventional metallic bonding on structures derived from  $NiAs$  structure*, MIT technical report, No. 345 (1964), unpublished.
- [20] J. B. Goodenough, D. H. Ridley, and W. A. Newman, *Proceedings of the International Conference in Magnetism*, Nottingham, 1964 (The Institute of Physics and the Physical Society, London, 1965).
- [21] J. B. Goodenough and J. A. Kafalas, *Phys. Rev.* 157, 389 (1967).
- [22] V. A. Chernenko, L. Wee, P. G. McCormick, and R. Street, *J. Appl. Phys.* 85, 7833 (1999).
- [23] S. Shimomura, K. Tajima, N. Wakabayashi, H. Kuwahara, and Y. Tokura, *J. Phys. Soc. Japan* 68, 1943 (1999).
- [24] H. Y. Hwang, S.-W. Cheong, P. G. Radaelli, M. Morez, and B. Batlogg, *Phys. Rev. Lett.* 75, 914 (1995).
- [25] S. Jin, T. H. Tiefel, M. McCormack, R. A. Fastnacht, R. Ramesh, and L. H. Chen, *Science* 264, 413 (1994).
- [26] J. S. Zhou, H. Q. Yin, and J. B. Goodenough, *Phys. Rev. B* 63, 184423 (2001).
- [27] A. Asamitsu, Y. Morimoto, Y. Tomioka, T. Arita, and Y. Tokura, *Nature* 373, 407 (1995).
- [28] G. L. Liu, J. S. Zhou, and J. B. Goodenough, *Phys. Rev. B* 64, 144414 (2001).
- [29] J. M. Iba, J. Rivas, L. E. Hueso, F. Rivadulla, M. A. Lopez Quintela, M. A. Sanja Rodriguez, and C. A. Ramos, *Phys. Rev. B* 65, 024418 (2001).
- [30] J. M. Iba, J. Rivas, F. Rivadulla, C. Vazquez Vazquez, and M. A. Lopez Quintela, *Phys. Rev. B* 60, 2998 (1999).
- [31] J. M. de Teresa, M. R. Ibarra, P. A. Algarabel, C. Ritter, C. Marquina, J. Blasco, J. Garcia, A. del Moral, and Z. Arnold, *Nature* 386, 256 (1997).
- [32] A. Moreo, M. Mayr, A. Feiguin, S. Yunoki, and E. Dagotto, *Phys. Rev. Lett.* 84, 5568 (2000).
- [33] J. B. Goodenough, *Aust. J. Phys.* 52, 155 (1999).

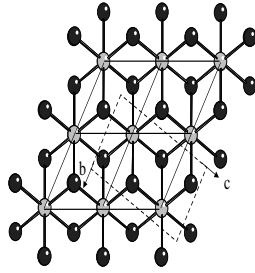


FIG .1: The orthorhombic unit cell of the B31 form of MnAs in relation to the hexagonal  $B_{81}$  type cell. Mn (white circles) and As (black circles) atoms are in the 4c special positions of the  $Pnma$  space group,  $(x, 1/4, z)$ , with  $x = -0.005$  and  $z = 0.223$  for Mn,  $x = 0.275$  and  $z = -0.082$  for As.

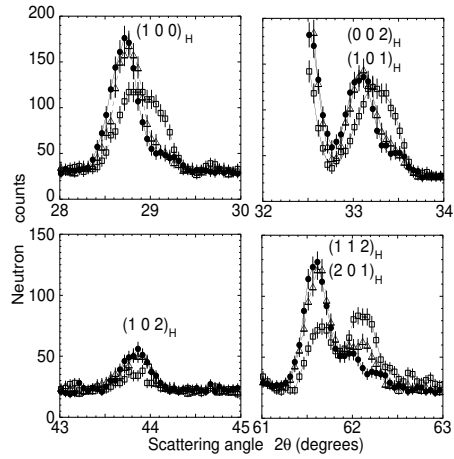


FIG .2: Selected regions of the diffraction patterns recorded at 27 °C with no field (circles), at 49 °C with no field (squares) and at 49 °C with an applied field of 5 tesla (triangles).

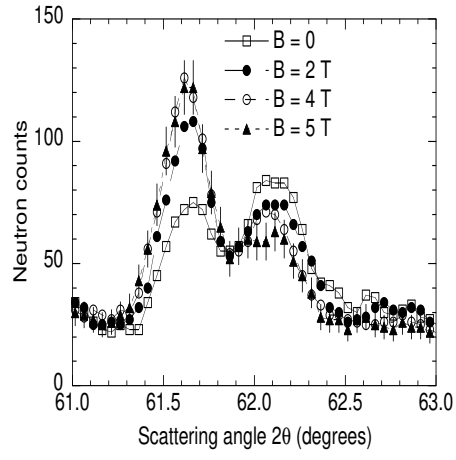


FIG. 3: Magnetic field dependence of a selected region of the diffraction pattern recorded at 322 K, showing the evolution from the orthogonal to the hexagonal form of MnAs.

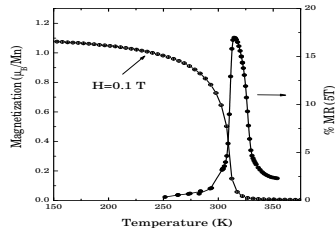


FIG. 4: Magnetoresistance ( $MR = [(R(0) - R(5T)) / R(0)] \times 100$ ) versus temperature of MnAs and magnetisation measured at 0.1 T in zero-field-cooling conditions.