

Novel dynamical effects and persistent memory in phase separated manganites

P. Levy, F. Parisi, L. Granja, E. Indelicato and G. Polla.

Departamento de Física, Comisión Nacional de Energía Atómica, General Paz 1499 (1650) San Martín, Buenos Aires, Argentina
(29 October 2001)

The time dependent response of the magnetic and transport properties of Fe-doped phase separated (PS) manganite $\text{La}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ is reported. The nontrivial coexistence of ferromagnetic (FM) and non FM regions induces a slow dynamics which leads to time relaxation and cooling rate dependence within the PS regime. This dynamics influences drastically on physical properties. On one hand, metallic like behavior, assumed to be a fingerprint of percolation, can be also observed before the FM phase percolates as a result of dynamical contributions. On the other one, two novel effects for the manganites are reported, namely the rejuvenation of the resistivity after ageing, and a persistent memory of low magnetic fields (< 1 T), imprinted in the amount of the FM phase. As a distinctive fact, this memory can be recovered through transport measurements.

Phase separation (PS), namely the simultaneous presence of submicrometer ferromagnetic (FM) and charge ordered (CO) regions, is emerging as the most important issue in the physics of the manganese-oxide-based compounds. [1] The PS scenario appears as particularly favorable for the existence of out-of-equilibrium features. The competition between the coexisting phases opens the possibility for the appearance of locally metastable states, giving rise to interesting time dependent effects, as cooling rate dependence, [2] relaxation, [3][5] giant $1/f$ noise, [6] two level fluctuations, [7] non equilibrium fluctuations, [8] noise [9] and relaxor ferroelectric like behavior. [10] The similarity between PS manganites and glassy systems, coming from the frustration of the FM and the CO states at the phases boundary was also suggested. [11]

Most of the relaxation experiments were performed after the induction of metastable states by, for instance, application of magnetic field H after zero field cooling, [9][11] removal of H after field cooling, [5] x-ray illumination, [12] electron beam irradiation, [8] etc. Such external perturbation can also be an abrupt change of the temperature, as observed in the prototypical PS compounds $\text{La}_{5/8}\text{Pr}_{1/8}\text{Ca}_{3/8}\text{MnO}_3$ ($y = 0.35$) and $\text{La}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$. [2] The extremely slow relaxation observed in all the mentioned works opens an interesting question not previously addressed about the path followed towards equilibrium in the PS state of manganites.

In this work we present a detailed study of time dependent effects in the PS compound $\text{La}_{0.5}\text{Ca}_{0.5}\text{Mn}_{0.95}\text{Fe}_{0.05}\text{O}_3$ (LCMFO). The parent compound $\text{La}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ exhibits PS with the temperature of charge ordering T_{CO} lower than that of the ferromagnetic order T_{C} . [13] From a microscopic point of view, the inclusion of Fe in the Mn site of $\text{La}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ yields the same overwhelming effect on the CO state as Cr doping does on other half doped manganites as $\text{Nd}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$

[10] and $\text{Pr}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$, [14] a feature ascribed to the presence of a random field quenched by the impurities. [15] But, unlike what happens with Cr doping, Fe doping also disrupts the double exchange interaction due to its filled e_g orbitals. Moreover, Fe-O-Mn superexchange interactions are likely to be antiferromagnetic [16]. All these facts are reflected by the decrease of T_{C} as a function of Fe doping. [17]

We use transport and magnetization measurements to study the dynamic of the coexisting phases, which is observed close below $T_{\text{C}} \approx 90$ K. We found cooling rate dependence and slow relaxation effects in the temperature range between T_{C} and 50 K, indicating the enlargement of the FM phase as the PS state evolves with time. Within this scenario, our main results are two novel effects. One, the rejuvenation in the resistivity curve when cooling is resumed after ageing, which resembles the behavior of glassy systems [18,19] and disorder ferromagnets. [20] The other is the effect produced by the application of a low $H < 1$ T while ageing which, instead of inducing metastable states, can drive the system towards its zero field equilibrium point. As this process is irreversible, the effects of H on the resistivity remain even after it is removed, and the system keeps memory of the magnetic history, acting as a magnetic field recorder.

Polycrystalline samples of LCMFO were synthesized by the sol-gel technique, their average grain size was around 0.5 microns. DC resistivity was measured using the four probe technique, magnetization was measured using a commercial SQUID magnetometer. Figure 1 displays magnetization M and resistivity as a function of temperature on cooling. $M(T)$ increases continuously between 100 and 50 K, reaching a low temperature plateau which reveals a mostly FM state. M vs H loops at 5 K show a saturation magnetization of $3 \mu_B/\text{Mn}$ at 5 T. An insulator to metal transition is suggested at $T_{\text{P}} \approx 80$ K. Both T_{P} and the resistivity below $T_{\text{D}} \approx 85$ K were found to be very sensitive to the cooling rate v_c (inset Fig. 1). The dependence of the peak resistivity with v_c reassures that this cooling rate effect is not an exper-

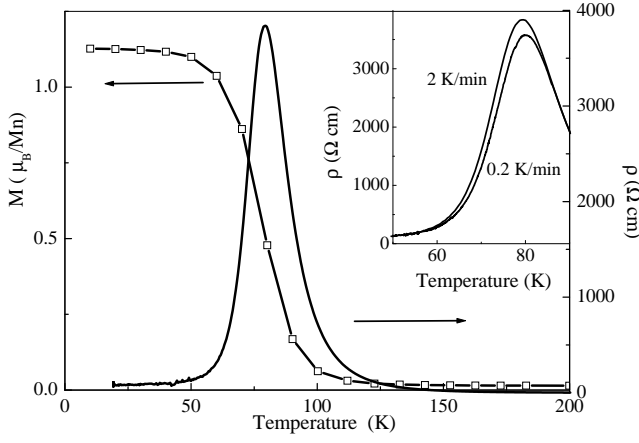


FIG. 1. Temperature dependence of M ($H = 0.1$ T) and ($H = 0$) on cooling for LCMFO. Inset: ρ (T) when cooling at $v_c = 2$ and 0.2 K/m in.

mental artifact.

We studied the time relaxation of ρ at several $T < T_D$ using $v_c = 0.2$ K/m in as the cooling rate to approach and depart from the values at which T was stabilized for one hour (Fig. 2). The relaxations are characterized by the decrease of ρ following a logarithmic time dependence, and are as high as an 18% in one hour at 73.8 K. A related behavior (inset of Fig. 2) was observed in the relaxation of M . Both relaxations are consistent with the isotherm al growth of FM regions embedded in a non FM host. A noticeable fact is that, when the cooling process is resumed with $v_c = 0.2$ K/m in after relaxation, ρ merges smoothly with the curve obtained at that v_c without T stabilization steps. This effect is similar to that found in the dissipation of some disordered ferromagnets and spin glasses, [18,20] and has been named rejuvenation. Another striking feature is that the slope of the ρ (T) curve in this range is highly dependent on the previous history of the sample. For instance, while $\partial \rho / \partial T > 0$ is found when cooling continuously, suggesting metallic behavior, a typical insulator response is obtained if, after one hour ageing, cooling is resumed (Fig. 2).

This last result is opposite to that expected from a static vision of transport properties in PS systems, in which the change from metallic-like to insulator-like behavior is driven by a decrease in the amount of the metallic fraction. This fact points to the existence of dynamical contributions to the resistivity in the continuously cooling procedure. To get a better description of this behavior we have studied the time dependence of the resistivity slope $\partial \rho / \partial T$ by performing small thermocycles ($\Delta T = 0.6$ K) around a fixed T value while the system is relaxing (Fig. 3). After a sudden initial change from positive to negative, the slope $\partial \rho / \partial T$ increases smoothly and slowly (see Fig. 3 inset) as the system evolves. The obtained ageing behavior of $\partial \rho / \partial T$ is now consistent with the static image for transport, the negative slope indi-

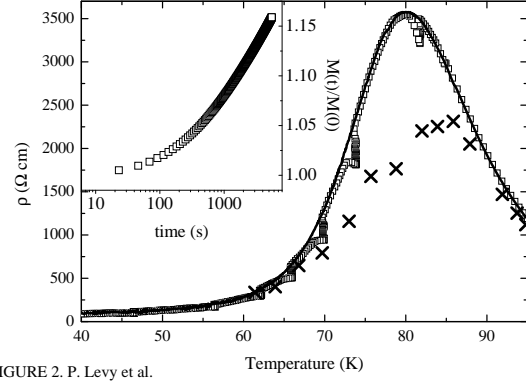


FIGURE 2. P. Levy et al.

FIG. 2. Temperature dependence of ρ on cooling at 0.2 K/m in continuously (solid line) and with intermediate stops of one hour (open symbols). The crosses indicate the values corresponding to the equilibrium state. Inset: time dependence of M after zero field cooling to 80 K and application of $H = 0.1$ T.

cating that percolation of the FM phase has not been achieved close below T_p . As in this T range the state of the system is characterized by the slow enlargement of the FM regions against the non FM host, the approach to equilibrium drives the system towards the percolation threshold, increasing the resistivity slope. The metallic-like behavior of the continuously cooling curve is then to be ascribed to the existence of non-static contributions to $\partial \rho / \partial T$ arising from the out-of-equilibrium dynamics of the coexisting phases. As the approach to equilibrium becomes slower as time goes by, it is not possible to reach it within laboratory times, so at this point we can not give conclusive statements about the nature of the equilibrium state (homogeneous FM or PS). However, as the system evolves by increasing the FM phase, an external H may assist in the path towards equilibrium. Following this idea, we have studied the effect of low H applied for a short time while the system is relaxing after zero field cooling the sample to a T close below T_p .

Fig. 4-a displays ρ as a function of elapsed time upon the application of several H values at $T = 72$ K, showing jumps when the field was applied and removed. The sudden decrease of ρ when the field is turned on can be ascribed to two independent mechanisms, one originated in the alignment of spins and domains, and the other due to the enlargement of the FM phase driven by H . [21] It is worth noting the hysteretic behavior of ρ after application and removal of H , indicating that the system keeps memory of the magnetic history in printed in its zero field resistivity.

The slow relaxation of the persistent resistivity value observed after H was removed indicates that, depending on the strength of the field, the FM phase may still be growing against the non-FM one (Fig. 4-a inset).

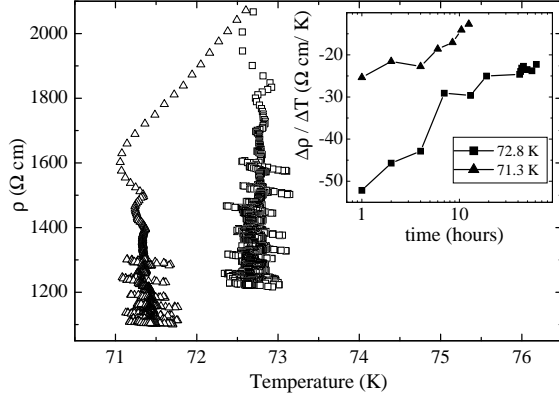


FIG. 3. Resistivity relaxation data obtained at 71.3 and 72.8 K; while the system was ageing, small thermal cycles ($\Delta T = 0.6$ K) were performed at 0.2 K/min, to evaluate $\partial \rho / \partial T$. After these sweeps, cooling was resumed at 0.2 K/min in confirming that the data rejoins the dynamic curve. Inset: time dependence of $\partial \rho / \partial T$ at 71.3 and 72.8 K.

Upon increasing H , we found a T -dependent threshold H_{th} value above which the ulterior relaxation of ρ after the field is turned off reverses its sign: after $H > H_{th}$ is applied and removed slowly increases (instead of decreasing) indicating that the system is evolving by diminishing the amount of the FM phase (Fig. 4-a inset). This fact signs unambiguously that the equilibrium state is of PS nature, characterized by the FM fraction $f_0(T)$. The application of H_{th} while ageing drives the system towards its zero field equilibrium point, having an effect which is equivalent to a long relaxation process. The equilibrium points depicted in Fig. 2 provide a demonstration of the magnitude of the dynamical effects. By applying a $H > H_{th}$ the amount of the FM phase overcomes the equilibrium volume, leading to a subsequent decrease of the FM fraction.

In what follows we discuss the overall results. At T_c an inhomogeneous FM state appears, consisting in the coexistence of isolated FM clusters of definite size within a non-FM host. At $T_D = 85$ K the FM regions start to grow against the host material with the equilibrium size of the clusters increasing as T is lowered. The process followed by the clusters to reach their equilibrium size can be thought as a stepwise movement of the phase boundaries through energy barriers. Before the FM clusters reach the percolation threshold, the temperature and rate dependent resistivity $\rho(T; v_c)$ can be modeled as a series circuit, i.e.

$$\rho(T; v_c) = n(T; v_c) \rho_F(T) + [1 - n(T; v_c)] \rho_{nF}(T) \quad (1)$$

where $\rho_F(T)$ and $\rho_{nF}(T)$ are the resistivities of the FM and non-FM constitutive media respectively and $n(T; v_c)$ is a measure of the relative fraction $f(T; v_c)$ of the FM phase. As the system is rather close to the percola-

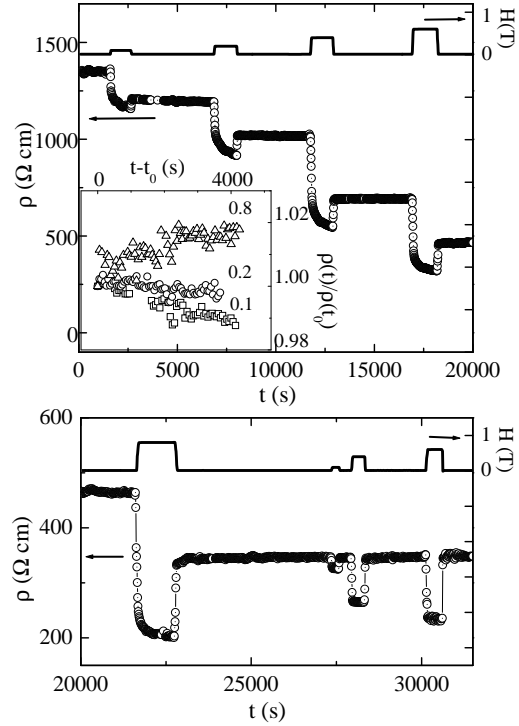


FIG. 4. a) Resistivity (open circles) at $T = 72$ K as a function of time upon application of $H = 0.1, 0.2, 0.4$ and 0.6 T (solid line). Inset: time dependence of ρ (72 K) in $H = 0$ normalized to the value after the field H was turned off; the labels are the H fields. b) Resistivity at $T = 72$ K as a function of time upon application of $H = 0.1, 0.4$ and 0.6 T after $H = 0.8$ T was applied and removed.

tion limit, $n(T; v_c)$ can be a cumbersome functional of $f(T; v_c) - f_c$, (where f_c is the percolation threshold), but is always a monotonous increasing function of $f(T; v_c)$, and can be obtained from conduction models through binary alloys. [22] Within this frame, the slope of the resistivity curve has two components. On one hand, a static contribution given by $n(T; v_c) \frac{\partial \rho_F}{\partial T} + [1 - n(T; v_c)] \frac{\partial \rho_{nF}}{\partial T}$ which is typically less than zero in the non-percolative regime. On the other hand, a "dynamical" term defined as $\frac{\partial n(T; v_c)}{\partial T} (\rho_F - \rho_{nF})$ related to the change of the size of the FM clusters as T is varied. This term gives a positive contribution to $\partial \rho / \partial T$ in the whole range in which $f(T; v_c)$ increases as T is lowered. As the system is cooling down at a rate v_c , the appearance of energy barriers at the clusters surface below T_D prevent their free growth, and the FM fraction $f(T; v_c)$ no longer follows its equilibrium value $f_0(T)$, larger differences corresponding to higher v_c values. This fact accounts (Eq. 1) for the overall increase of ρ as v_c is increased (Fig. 1, inset). Close below T_D , $f(T; v_c)$ increases slower than $f_0(T)$, yielding a low dynamical contribution, i.e., larger (negative) slopes are achieved with higher v_c . As the difference between $f_0(T)$ and $f(T; v_c)$ becomes larger, the rate at which the FM clusters grow increases, and

the dynamical contribution approaches the static one. Both terms are of the same magnitude at T_p , and below, the dynamical contribution is even larger than the static one. A positive slope resembling "metallic-like" behavior is then obtained below T_p , although the FM clusters do not percolate.

The history-dependent $\rho = \rho(T)$ obtained after a relaxation process (Figs. 2 and 3) is consistent with this scenario. By ageing at a given temperature $f(T; v_c)$ slowly approaches its equilibrium value $f_0(T)$ and the growth dynamics becomes partially frozen. When cooling is resumed a small dynamical contribution is obtained, compared with that of the non-stop process, because of the "clamping" of the interface. The main contribution to $\rho = \rho(T)$ after ageing comes then from the static part, giving rise to the "insulator like" response. On further cooling, the frozen-in state is released, the system falls again in the dynamical regime mainly determined by v_c , and the resistivity curves (with and without ageing) merge into a single one.

This dynamical process produces ageing and rejuvenation effects which bear similarities with those found in glassy systems. [18-20] Slow relaxations following stretched exponential or logarithmic dependences were accounted for with models based on a hierarchical constrained dynamics, [23] in which the system evolves through a hierarchy of energy barriers, constrained to accomplish determined requisites after a process at time t can proceed. In our case the existence of a hierarchy of energy barriers is revealed by the response of the system to H while ageing at a fixed T showed in Fig. 4-a. When H is applied all the barriers of height $< H$ are overcome, yielding the sudden growth of the FM phase. As H is increased, higher barriers are crossed, giving rise to further enlargement effect. In this context, once all the energy barriers of height up to some applied H_{MAX} were overcome, the subsequent application of a $H < H_{MAX}$ should have no immediate effect on the relative fractions of the coexisting phases. This picture is confirmed by the results shown in Fig 4-b. As can be seen, once $H_{MAX} = 0.6$ T has determined the relative phase fractions, ulterior application of $H < 0.6$ T produces only domain alignment, without inducing additional changes on the amount of the coexisting phases. Then, after the system was driven to a "close to equilibrium state" by some H_{MAX} , the process can not be reversed and the system keeps memory of the largest H applied in its magnetic history.

The above described scenario seems to be characteristic of the low T_c PS systems. We have obtained very similar data in other samples of LCMFO with slight different Fe doping and in $\text{La}_{5/8}\text{Pr}_{3/8}\text{Ca}_{3/8}\text{MnO}_3$ ($y = 0.30$), a PS compound with rather different hole doping but similar PS characteristics.

Summarizing, we have presented robust evidence of the importance of the coexisting phase dynamics in the behavior of the PS manganites. When dynamical effects

are present the amount and spatial distribution of the FM phase (percolative or not) can not be directly inferred from metallic or insulator behavior. The rejuvenation found in the resistivity curve after ageing and the persistent memory after the application of a low H are novel features in the physics of manganites. The possibility to record an external magnetic field as a sizeable and persistent change of the resistivity is a distinctive fact of the memory effect, and opens a route for applications. Memory effects in manganites have been previously reported, [4,10-12] related to the field induction of metastable states. In our case, instead, the low field carries the system closer to its zero field equilibrium state. Since both, the "virgin" state and the "H-enlarged" state are, in general, out of equilibrium, the memory could be erased after a very long time, but the effect is protected by the very slow dynamics displayed by the system.

Project partially financed by CONICET, Fundacion Antorchas and Balseiro.

-
- [1] E. Dagotto, T. Hotta and A. Moreo, Phys. Rep. 344 (1-3), 1 (2001).
 - [2] M. Uehara and S-W. Cheong, Europhys. Lett. 52 (6), 674 (2000).
 - [3] I. F. Voloshin et al., JETP Letters 71, 106 (2000).
 - [4] N. A. Babushkina et al., Phys. Rev. B 59, 6994 (1999).
 - [5] V. N. Smolyaninova et al., available at cond-mat/9907087 (unpublished).
 - [6] V. Podzorov et al., Phys. Rev. B 61, R3784 (2000).
 - [7] R. D. M. Erithew et al., Phys. Rev. Lett. 84, 3442 (2000).
 - [8] V. Podzorov et al. to appear in Europhys. Lett. (2001).
 - [9] A. Anane et al., Phys. Rev. B 59, 77 (1999).
 - [10] T. Kimura et al., Phys. Rev. Lett. 83, 3940 (1999).
 - [11] M. Roy, J. F. Mitchell and P. Schiffer, J. Appl. Phys. 87, 5831 (2000).
 - [12] D. Casa et al., Europhys. Lett. 47, 90 (1999); D. Casa et al., Phys. Rev. B 64, 100404 (2001).
 - [13] P. Levy et al., Phys. Rev. B 62, 6437 (2000); Q. Huang et al., ibid 61, 8895 (2000); R. S. Freitas et al., ibid 65, 104403 (2002).
 - [14] R. Mahendiran et al., Solid State Commun. 114, 429 (2000).
 - [15] T. Katsufuji, et al., J. Phys. Soc. Jpn. 68, 1090 (1999).
 - [16] L. K. Leung, A. H. Morrish and B. J. Evans, Phys. Rev. B 13, 4069 (1976).
 - [17] P. Levy et al. J. Magn. Magn. Mat. 226, 794 (2001).
 - [18] K. Jonason et al., Phys. Rev. Lett. 81, 3243, (1998).
 - [19] J. P. Bouchaud, in Soft and Fragile Matter, M. E. Cates and M. R. Evans, Eds., IOP Publishing (Bristol and Philadelphia) pp 285-304 (2000).
 - [20] E. Vincent et al. Europhys. Lett. 50 (5), 674 (2000).
 - [21] F. Parisi et al., Phys. Rev. B 63, 144419 (2001).
 - [22] D. S. Mc Lachlan, J. Phys. C 20, 865 (1987).
 - [23] R. G. Palmer et al., Phys. Rev. Lett. 53, 958 (1984).