

MAGNETIC FIELD EFFECTS ON T_c AND THE PSEUDOGAP ONSET TEMPERATURE IN CUPRATE SUPERCONDUCTORS

QIJIN CHEN

National High Magnetic Field Laboratory, 1800 East Paul Dirac Drive,
Tallahassee, Florida 32310

YING-JER KAO, ANDREW P. IYENGAR, AND K. LEVIN

James Franck Institute, University of Chicago, Chicago, Illinois 60637

We study the sensitivity of T_c and the pseudogap onset temperature, T^* , to low fields, H , for cuprate superconductors, using a BCS-based approach extended to arbitrary coupling. We find that T^* and T_c , which are of the same superconducting origin, have very different H dependences. The small coherence length makes T^* rather insensitive to the field. However, the presence of the pseudogap at T_c makes T_c more sensitive to H . Our results for the coherence length fit well with existing experiments. We predict that very near the insulator T_c will rapidly increase.

The pseudogap phenomena have been a great challenge to condensed matter physicists since last century. Yet there has been no consensus on the origin of the pseudogap and its relation to the superconducting order parameter. Theories about the pseudogap physics fall into two categories: (1) precursor versus (2) non-precursor superconductivity. For the former, pseudogap forms as a consequence of precursor superconducting pairing, and therefore, shares the same origin as the order parameter. In contrast, for the latter category, pseudogap has a different origin, e.g., a hidden DDW (d-density wave) order.¹

On the other hand, experiment has revealed different behaviors of T_c and the pseudogap onset temperature T^* in magnetic fields.² However, there is still no proper theoretical explanation. This difference has been used as evidence against precursor superconductivity scenarios. Here we show that it can be well explained within the present precursor superconductivity theory.^{3;4;5}

Our calculation is based on an extension of BCS theory which incorporates incoherent pair excitations. These pair excitations become increasingly important at large coupling g , and lead to a pseudogap in the single-particle excitation spectrum, as seen in the cuprates. As the temperature increases from $T = 0$, these pairs can survive a higher temperature ($> T_c$) than the condensate, until they are completely destroyed by the thermal effect at T^* . In agreement with experiment, we find that T^* and T_c have very different field (H) dependences. The small coherence length (ξ) makes T^* rather insensitive to the field. However, the presence of the pseudogap at T_c (at optimal and

under-doping) makes T_c relatively more sensitive to H . Our results for the coherence length ξ well with existing experiments. Furthermore, we predict that very near the insulator ξ will rapidly increase.

We first consider the zero magnetic field case. We include, in addition to time-reversal state pairing, finite center-of-mass momentum pair excitations in the problem and then treat the interrelated single- and two-particle propagators self-consistently. We truncate the infinite series of equation of motion at the three-particle level, and then factorize the three-particle Green's function G_3 into single-particle (G) and two-particle (G_2) Green's functions.⁶

Here we consider an electron system near half filling on a quasi-two dimensional (2D) square lattice, with tight-binding dispersion ϵ_k . The electrons interact via a separable potential $V_{k,k'} = g'_{\mathbf{k}} \delta_{\mathbf{k},\mathbf{k}'}$; where $\delta_{\mathbf{k}} = \cos k_x - \cos k_y$ (for d-wave). We use a T-matrix approximation for the self-energy, and have

$$G(\mathbf{K}) = G_0^{-1}(\mathbf{K}) - G^{-1}(\mathbf{K}) = \sum_{\mathbf{Q}} t(\mathbf{Q}) G_0(\mathbf{Q} - \mathbf{K})'_{\mathbf{k}}^2_{q=2}; \quad (1)$$

$$t(\mathbf{Q}) = \frac{j_{sc} j_{\mathbf{Q}}^2}{T} (\epsilon_{\mathbf{Q}} - T) + \frac{g}{1 + g(\mathbf{Q})}; \quad (2)$$

where j_{sc} is the order parameter, and $g(\mathbf{Q}) = \sum_{\mathbf{K}} G(\mathbf{K}) G_0(\mathbf{Q} - \mathbf{K})'_{\mathbf{k}}^2_{q=2}$. For small $Q \neq 0$, $t(Q)$ can be written in a standard propagator form. The pseudogap is given by $\sum_{\mathbf{Q}} t(\mathbf{Q})$, the total gap⁴ by $\sum_{\mathbf{Q}} \frac{2}{2_{sc} + 2_{pg}}$, and the quasiparticle dispersion by $E_k = \sum_{\mathbf{Q}} \frac{2}{2_k + 2_{pg}}$.

T_c is determined by the superconducting instability condition $1 + g(0) = 0$, in conjunction with the number constraint $n = 2 \sum_{\mathbf{K}} G(\mathbf{K})$. We obtain a set of three equations.⁴ Taking into account that the cuprates is close to the Mott insulator and thus in-plane hopping $t_k(x) = t_0(1 - n) = t_0 x$, where x is the doping concentration, we solve for T_c , μ , chemical potential, and j_{pg} . The results for T_c , $j_{pg}(T_c)$, and $\xi(T=0)$ as a function of x are summarized in Fig. 1(a). Our predictions fit experiment well with $g = 4t_0 = 0.045$ and $t_0 = 0.6$ eV. For more details, see Refs. 3{5.

In a finite field, the Ginzburg-Landau free energy functional near T_c can be expanded to quadratic order in the order parameter j_{sc} :

$$F_0(T) + \frac{1}{2} \left(\frac{r}{i} - \frac{2eA}{c} \right)^2 j_{sc}^2; \quad (3)$$

where $r(T) = r_0 \left(1 - \frac{T}{T_c} \right)$, and $\frac{1}{T_c} \frac{dT_c}{dH} \Big|_{H=0} = \frac{2}{r_0} \frac{r_0}{2} = \frac{2}{r_0} \frac{1}{2}$. As an estimate, one has $H_{c2}(0) = (2/r_0)$. ($r_0 = \hbar c / 2e$ is the flux quantum).

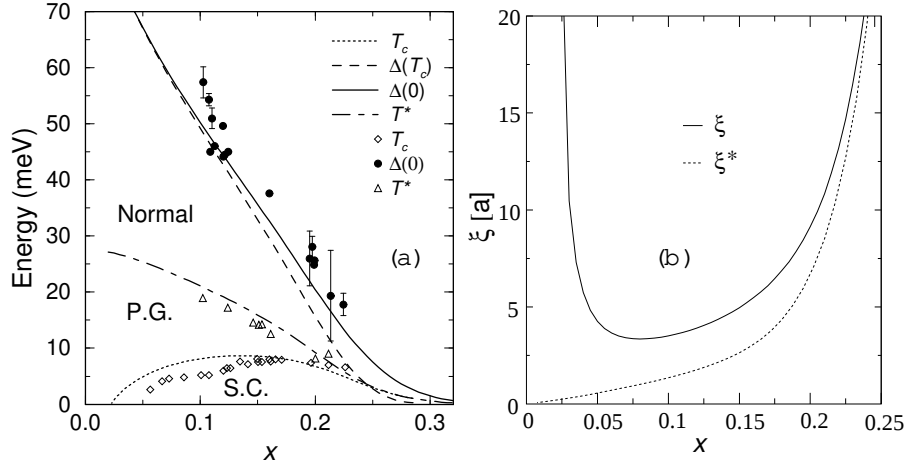


Figure 1. (a) Calculated cuprate phase diagram. T_c was estimated using the BCS mean-field solution. Experimental data are taken from: () Ref. 7; () Ref. 8; () Ref. 9. For more details see Ref. 4. Note here $\Delta(0)$ has been multiplied by 2 to compare with experiment, since $\gamma_k = 2$ at $k = (\pi; 0)$. (b) Magnetic length scales associated with T_c and T^* as a function of doping concentration in the cuprates.

For 3D weak coupling (BCS), $\chi_0 = N(0)$ and the phase stiffness $\chi^2 = N(0)7(3) = 48^2 (v_F = T_c)^2$. Therefore $N(0)$ is canceled in $\chi_{BCS}^2 = 7(3) = 48^2 (v_F = T_c)^2$. In general, χ_0 and χ^2 can be determined from the expansion of $t^1(Q)$:

$$\chi_0 = \frac{1}{g} + t^1(0;0); \quad \chi^2 = \frac{1}{2} \frac{t^2(Q)}{\det \epsilon_{q_i} \epsilon_{q_j}(Q)} \Big|_{Q=0}; \quad (4)$$

In weak field, $T \ll \epsilon_H = m c$, we use semiclassical phase approximation to treat the single-particle and pair propagators. Both the single-particle and pair momenta can be modified by the interaction with the field. But formally, the Dyson's equation remains the same, and the superconducting transition is still determined by the pairing instability (Thouless) condition: $g^{-1} + \chi^2(0) = 0$ or $\chi_0 + \chi^2 \frac{2eH}{c} = 0$, where $\chi^2(Q)$ is the pair susceptibility in the field. To linear order in H , we can evaluate χ_0 and χ^2 at $H = 0$.

At T_P , the pseudogap is zero, only the bare Green's function is involved, $\chi_0(Q) = \sum_K G_0(K) G_0(Q-K) \gamma_k^2 \gamma_{q=2}$. We have

$$\frac{1}{T} \frac{dT}{dH} \Big|_{H=0} = \frac{\chi^2}{\chi_0} \frac{2}{\chi_0}; \quad \chi^2 = \frac{\chi^2}{\chi_0}; \quad (5)$$

where $\rho_0 = \sum_k \rho_k^2 f^0(k) + \frac{dT}{dT} \frac{1}{k} \frac{2f(k)}{2k} + f^0(k)$ $T = T_c$

At weak coupling (for s-wave, $\rho_{k_F} = 1$), we recover the BCS limit: $E_F, \rho_0 = \sum_k f^0(k) \rho_k^2 N(0) \rho_{k_F}^2 N(0)$. And ρ^2 is determined by expanding $\rho(q;0) = \sum_k \frac{1}{k + k_q} \frac{f(k) f(k_q)}{k_q^2}$ to the q^2 order.

At large g (for the underdoped cuprates), $\rho_{pg}(T_c)$ is large. Noticing that T is very weakly H dependent in the strong pseudogap regime [see Fig. 1(b)], and that T / ρ_{pg} in zero field, we assume ρ_{pg} is only weakly H dependent. In other words, only the superconducting order parameter is strongly coupled to the field. Then we obtain $\rho_0 = \sum_k \rho_k^2 f^0(E_k)$, which decreases rapidly as ρ_{pg} increases. ρ^2 is obtained by expanding to the q^2 order

$$\rho(q;0) = \sum_k \frac{1}{E_k + k_q} \frac{f(E_k) f(k_q)}{u_k^2} \frac{f(E_k) f(k_q)}{E_k - k_q} v_k^2 \rho_{k_q=2}^2 : (6)$$

At weak coupling, ρ and ρ_{BCS} coincide. But they split apart as g increases and the pseudogap opens (see Ref. 10 for details). In Fig. 1(b), we plot the doping dependence of the calculated ρ and ρ_{BCS} . At large x (overdoping, weak coupling), the two are nearly equal. But for underdoping, while ρ_{BCS} continues to decrease with decreasing x , ρ remains nearly flat for a broad range of x until its final rapid increase toward the insulator limit. Since $dT = dH / \rho^2$, T is rather insensitive and T_c is relatively more sensitive to H . These results are in agreement with experimental observations.^{2,11}

This work was supported by NSF-MRSEC, grant No. DMR-9808595, and by the State of Florida (QCL).

References

1. S. Chakravarty et al, Phys. Rev. B 63, 094503 (2001).
2. V.M. Krasnov et al, Phys. Rev. Lett. 84, 5860 (2000); 86, 2657 (2001); Ch. Renner et al, Phys. Rev. Lett. 80, 3606 (1998); K. Gorny et al, Phys. Rev. Lett. 82, 177 (1999); G. Zheng et al, Phys. Rev. Lett. 85, 405 (2000).
3. I. Kosztin, Q. J. Chen, B. Janko, and K. Levin, Phys. Rev. B 58, R5936 (1998).
4. Q. J. Chen, I. Kosztin, B. Janko, and K. Levin, Phys. Rev. Lett. 81, 4708 (1998).
5. Q. J. Chen, I. Kosztin, and K. Levin, Phys. Rev. Lett. 85, 2801 (2000).
6. L.P. Kadano and P.C. Martin, Phys. Rev. 124, 670 (1961).
7. N.M. Iyankawa, Phys. Rev. Lett. 80, 157 (1998); 83, 1018 (1999).
8. J. Rossat-Mignod et al, Physica B 169, 58 (1991).
9. M. Oda et al, Physica C 281, 135 (1997).
10. Y.-J. Kao, A.P. Iyengar, Q. J. Chen and K. Levin, Phys. Rev. B 64, 140505 (2001).
11. H.H. Wen et al, Phys. Rev. Lett. 85, 2805 (2000); T. Shibauchi et al, Phys. Rev. Lett. 86, 5763 (2001).