

X-ray spectra of 3d metals of Heusler alloys and $\text{La}_{1-x}\text{Sm}_x\text{Mn}_2\text{Si}_2$ compounds

M. V. Yablonskikh, Yu. M. Yarmoshenko, E. G. Gerasimov, and V. S. Gaviko and E. Z. Kumeev
Institute of Metal Physics, Russian Academy of Sciences-Ural Division, 620219 Yekaterinburg GSP-170, Russia

S. Bartkowski and M. Neumann
Department of Physics, Osnabrück University, D-49069 Osnabrück, Germany

The Mn x-ray emission spectra and x-ray photoemission spectra of Mn-based Heusler alloys Co_2MnAl , Co_2MnSb and $\text{La}_{1-x}\text{Sm}_x\text{Mn}_2\text{Si}_2$ compounds ($x=0, 0.8$) have been measured and discussed in connection with a value of local magnetic moment at Mn site. The spectra peculiarities reflect also the localization degree of 3d valence electrons of 3d metals in considered compounds.

PACS numbers: 75.20.Hr, 78.70.En, 79.60.-i

I. INTRODUCTION

Magnetic properties of localized and delocalized magnetics are usually bound with the peculiarities of their electronic structure and found to be explained within the framework of these terms. Here x-ray emission (XE) and x-ray photoemission (XPE) spectroscopy is used to bring light on the differences in 3d metal spectra of close to half-metallic [1] Mn-based Heusler alloys and rare-earth Mn containing compounds both within general problem of strong magnetism of the 3d metal alloys and compounds. Using the samples well studied experimentally before by different techniques we will discuss the difference at x-ray spectra of 3d metals in connection with the value of the local magnetic moment and different spin polarization of the valence electrons using the x-ray spectroscopy. The selection of the samples will be explained below. First let us pay attention to the techniques being used.

The x-ray spectroscopy is a well-known to be an element-selective probe of electronic structure. That opens the principal ability to provide information about the relation between a magnetic properties and x-ray spectra, because it deals with a short-lived states, so it is complementary with data obtained from static magnetic measurements. The emission process occurs in a first coordination sphere, therefore it is good to use that to investigate the formation of local magnetic moment of 3d metal. General techniques being used are the x-ray emission, x-ray photoemission and x-ray absorption spectroscopy using the circularly polarized energy-variable excitation source, that allows to study a fine structure of electronic states and their spin configuration. That could be combined with a traditional techniques using non-polarized excitation with a fixed excitation energy. Provided information gives a chance to distinguish localized and itinerant magnetics containing 3d transition metals by processing of x-ray spectra of 3d metals in different types of magnetic alloys and compounds. Here we considered 3d transition metal spectra of Heusler Alloys (HA) (Co_2MnAl , Co_2MnSb) and $\text{La}_{1-x}\text{Sm}_x\text{Mn}_2\text{Si}_2$ compounds ($x=0, 0.8$).

First attention to Heusler alloys has been paid in 1903 when Heusler [2] discovered ferromagnetic behavior in compounds of nonmagnetic elements. Such ternary alloys are determined by the generic formulas X_2YZ or XYZ [3, 4, 5]. For the Y-element Heusler alloys usually contain Mn, the X element, for example, can be X: Fe, Co, Ni, Cu, Pd, or Rh. For the Z element it is considered Al, Ga, Si, Sn, Sb, or In. Crystallizing in the space groups $\text{L}2_1$, Mn-based HAs have been found at most in a ferromagnetic ground state. They offer the unique possibility to study manganese compounds where the Mn atom has only other transition X metals as nearest neighbors and non-transition Z elements of group III-V in the second coordination sphere. Webster et al. and later on Robinson et al. [6, 7] have investigated the crystal structure of these alloys in detail. Furthermore, it has been shown that some disorder is often appearing in Mn-based HAs and that in total up to 10% of the Mn atoms change places with elements from a different sublattice. The neighborhood of Mn atoms is mainly built by X and Z elements. Mn-based Heusler alloys have an effective magnetic moment of about $\mu_{\text{Mn}} = 3.0 - 4.0 \mu_B$ localized at the Mn site. Traditionally they are considered as ideal system with local magnetic moments. First principle band structure calculations [8] for these alloys have shown that in the electron system with spins directed along the magnetization axis (\uparrow) the Mn-3d states are occupied and hybridized with the 3d states of the X atoms. In the electron system with spins directed against the magnetization (\downarrow) local, not hybridized empty Mn-d states have been observed, located at $1.0 - 1.5$ eV above the Fermi level [8, 9, 10, 11]. Z atoms supply sp electrons, which take part in an indirect Mn-Mn exchange and therefore determine the degree of occupation of hybridized pd orbitals. Further investigations on Mn-based HAs Refs. [1, 12, 13] predict the existence of a half-metallic ferromagnetic (HMF) state, for example, in NiMnSb , PtMnSb , PdMnSb , and PtMnSb . This means that an energy gap at the Fermi level exists for one spin orientation and a metallic behavior has been obtained for the other spin direction. Other band structure calculations reveal that a HMF ground state may also exist for Co_2MnZ alloys [14]. Both neutron scattering measurements [15, 16, 17] and theoretical predictions [18] show well defined local moments μ_{Mn} (see Table I). The local magnetic moment at Co atoms is much smaller than at Mn (less than $0.5 \mu_B$,

[6, 19]. The remarkable feature of Mn 3d valence band for alloys being considered is a theoretically predicted pseudo gap for minority spin electrons, that makes alloys to be close to class of half-metallic ferromagnets.

The RMn_2Si_2 compounds (R is rare-earth metal) crystallize in the tetragonal $ThCr_2Si_2$ structure, where separate layers are stacking along c-axis in the $Mn-X-R-X-Mn$ sequence. The compounds are assumed to exhibit an unusual strong dependence of Mn-Mn exchange interaction from the distance between Mn atoms in a single layer [20, 21]. The relation of such unusual Mn behaviour in RMn_2X_2 and peculiarities of their electronic structure is suggested to be dependent of the d_{Mn-Mn} in the nearest neighborhood. In case of $d_{Mn-Mn} < d_c$ where $d_c = 2.85 - 2.87$ Å is the critical distance for the space localization of Mn 3d electrons, magnetic moments are aligned primarily along the c-axis that leads to antiferromagnetic order. In case of d_{Mn-Mn} ferromagnetic order is appeared. The distance between R (001) and Mn (100) planes is about $c/2 = 5.2$ Å, that exceeds the one between R atoms ($d_R = a/4 = 4.2$ Å) and Mn atoms ($d_{Mn-Mn} = \frac{a}{2} = 2.8$ Å). Last value is close to the critical $d_c \approx 2.84$ for space localization-delocalization of Mn 3d electrons in the crystal space according to predicted [22]. The doping of the second rare-earth metal in RMn_2Si_2 compounds allows to gradually change Mn-Mn distance from $d_{Mn-Mn} > d_c$ for $LaMn_2Si_2$ to $d_{Mn-Mn} < d_c$ for $SmMn_2Si_2$ [23].

The system has an effective magnetic moment about $\mu_{eff} = 3.5 - 3.8 \mu_B$, that is similar to Heusler alloys, although the value of μ_{Mn} is smaller and found to be in range $2.3 - 2.5 \mu_B$. The value of local magnetic moment μ_{Mn} changes from 0 to $1.45 \mu_B$ with x changing from 1 to 0. The relation of such unusual Mn behavior in RMn_2X_2 and peculiarities of their electronic structure is suggested to be depended of the d_{Mn-Mn} in the nearest neighborhood. In case of $d_{Mn-Mn} < d_c$, where $d_c = 2.85 - 2.87$ Å is the critical distance for space localization of Mn 3d electrons, magnetic moments align primarily along the c-axis that leads to antiferromagnetic order, and in case of $d_{Mn-Mn} > d_c$ the ferromagnetic ordering appears. Note that in set RM_2X_2 doping by different 3d transition metals $M = Fe, Co, Ni, Mn$, only manganese contains the non-zero local magnetic moment. Calculations [24] show the non-strongly spin-polarized Mn DOS, unlike in Heusler alloys. It was suggested that Mn 3d states of RMn_2X_2 have been hybridized with X-p states, in our case with Si-p states due to close positions in a single layer. The direct Mn-Mn exchange interaction prevails in a single layer of Mn atoms. The one between the nearest single layers is realized by the La-f and Sm-f electrons hybridized with Mn 3d and also Si-p electrons.

Finally we concentrate on the question of the influence of localization degree of 3d electrons, the values of the local magnetic moments of 3d metals at x-ray spectra. The Mn-Mn distance in Heusler alloys exceeds the value for RMn_2Si_2 in factor two. In other hand, the magnetic ordering is formed by indirect intralayer exchange, that is opposite to direct exchange mechanism in RMn_2Si_2 . Calculations also predict the localization difference in k-space [24]. These factors defined the choice of selected materials. The principal opportunity of using the spectroscopy to detect the influence of an atom magnetic moment to X-ray spectra had been shown by van Acker et al. [25]. The corresponding experimental data have been obtained for a series of alloys and compounds containing Fe. The energy splitting of the Fe-3s band is essentially different for each material, but without strong correlation effects. From more recent experiments, in which polarized radiation has been used it is evident that the dispersion as well as the energetic position of the Fe-3s band varies as a function of the electron spin [26].

II. EXPERIMENTAL DETAILS

The specimens were prepared from a melt in an atmosphere of purified argon, annealed at 720 °C during 24 h for Heusler alloys and at the temperature $T = 900$ °C for $La_{1-x}Sm_xMn_2Si_2$ in argon and quenched in water. According to X-ray diffraction patterns (Cu K α) samples were in single phase.

X-ray photoelectron spectra (XPS) were measured using a PHI 5600ci spectrometer with an energy resolution of 0.35 eV with monochromatized AlK α radiation. The compounds were crushed in situ in vacuum $1 \cdot 10^{-7}$ Torr. The surface cleanliness was tested by monitoring the C-1s and O-1s peaks. During the measurements in vacuum $1 \cdot 10^{-9}$ Torr no significant increase in the contamination was observed.

X-ray emission spectra were obtained using an x-ray spectrometer of the type RSM-500. The measurements have been carried out at a voltage of $U = 4.5$ kV, an anode current of about 0.3-0.4 mA and $1 \cdot 10^{-7}$ Torr vacuum. The energy resolution in the XE spectra resulted in 0.7 eV. Last but not least the rest contamination with oxygen has been estimated during the heating procedure. This has been done by controlling the intensity ratio of the lines O K and Mn L $_1$ in the corresponding XE spectra.

III. DISCUSSION

The Mn 3s photoemission spectra of compounds and pure manganese are shown at Fig.1. The multiplet splitting is observed in form of two peaks at the binding energies $E_B = 83$ and $E_B = 87.5$ eV for pure Mn and RMn_2Si_2 . No clear

dependence of the spectra shape and the local magnetic moment at Mn site is observed for whole series of compounds, but roughly it is possible to distinguish only small splitting of Mn 3s core level due to interaction between 3d valence electrons and 3s core hole created and the binding energy shift of Mn 3s XPS about 0.6 eV toward high energy side.

Briefly, such effect is explained by the difference in the energy for Mn $3\uparrow 3d^5 S$ final state, that comes to be result of the strong exchange interaction between Mn $3s\downarrow$ hole and strongly spin-polarized Mn 3d electrons in case of Co_2MnSb . At Fig. 2 the Mn 2p XPS have been shown.

The spin-orbit splitting at the Mn $2p_{1=2}$ peak with the binding energy $E_B = 649.7$ eV and at the Mn $2p_{3=2}$ peak with $E_B = 638.5$ eV are observed clearly. Opposite to Mn 3s photoemission spectrum at Fig.1, Mn 2p spectrum differs from pure Mn for both series of compounds. The Mn $2p_{3=2}$ peak splits at two, each position of is marked as A and B. The energy position of peak A is the same for all Mn 2p spectra. The energy position of the peak B is moving toward high binding energies and the intensity is rising in line $La_{0.2}Sm_{0.8}Mn_2Si_2$, $LaMn_2Si_2$, Co_2MnAl , Co_2MnSb . For RMn_2Si_2 compounds the value of splitting is 0.7-0.8 eV and for Heusler alloys it is approximately 1 eV. No energy shifts of Mn 2p XPS have been observed comparing to pure metal spectrum. Peak of very weak intensity at the $E_B = 641$ eV appears at the edge of Mn $2p_{3=2}$ spectra due small amount of oxygen at the surface.

The Mn $2p_{3=2}$ energy splitting is connected to the strong 2p-3d exchange interaction [27] that correlates with M_n . Such qualitative dependence is observed between RMn_2Si_2 with $M_n = 2:3$ [28] and Heusler alloys with M_n see Table I. The absence of satellite peaks and energy shifts at whole Mn 2p XPS allows to expect that effects being observed for Mn 3s XPS are due to local magnetic moment at Mn site, like in cases [25, 26]. That also is in agreement with Co 2p and La 3d photoelectron spectra at Fig.3 and Fig.4 displaying no significant changes.

The Mn L_2, L_3 X-ray emission spectra corresponds to emission transition of Mn 3d valence electron to $2p_{1=2}$ and $2p_{3=2}$ core hole respectively. Comparing spectra between each other (Fig.5) one finds two remarkable features. The height of $I(L_2)=I(L_3)$ intensity ratio correlates with M_n . The L_3 peak consist of two peaks A^0 and B^0 , that is observed in case of Heusler alloys and again is due to high localization of strongly spin-polarized Mn 3d electrons [28].

In x-ray emission spectra of 3d metals such a peak B^0 located toward high photon energies is explained by the influence of inner Coster-Kronig transition [29, 30, 31], but that is opposite to the high intensity ratio observed. Both the presence of the peak B^0 with energy exceeding the Mn $2p_{3=2}$ core level binding energy and the $I(L_2)=I(L_3)$ high intensity ratio are indicating the existence of pseudo gap for one of Mn 3d spin-projection at valence band. That is characteristic for the case of the strong localization of 3d electrons [28, 32, 33].

The Co XPS spectra of Heusler alloys and La, Sm spectra of core levels are shown at Fig.3, Fig.4. There is no difference between the pure metal spectra and one in compounds. Co L_2, L_3 emission spectra resemble with one of pure Co, that correlates with a small value (less than $0.5 \mu_B$), thought [33] of atom magnetic moment in compounds. It is also confirmed by Co L_2, L_3 spectra exhibiting no changes in comparison to the pure Co L_2, L_3 spectra (see Fig.6).

IV. CONCLUSION

The presented analysis gives an opportunity to discuss the degree of valence electron localization for different compound with a metallic type of conductivity. For example, analyzing the same of spectra of metal oxides, x-ray spectra contains not only Coulomb exchange interaction appears in x-ray spectra, but also charge-transfer effects. Latter factor makes complicated the interpretation of x-ray spectra. Both the degree of localization of 3d valence electrons and type of chemical bonding is to be reflected in x-ray spectra, that is observed at the example of Mn spectra in compounds even using non-polarized and non-resonant energy excitation source.

-
- [1] R. D. Groot, F. M. Ueller, P. V. Engen, K. H. J. Buschow, Phys. Rev. Lett. 50 (25) (1983) 2024{2027}.
 - [2] F. Heusler, Verh. Dtsch. Phys. Ges. 5 (1903) 219.
 - [3] P. J. Webster, R. S. Tebble, Phil. Mag 16 (1967) 347{362}.
 - [4] M. Parsons, J. G. Randle, B. Dennis, K. Neumann, K. Ziebeck, J. MAGN. MAGN. MAT. 140-144 (1995) 185.
 - [5] Ferromagnetic materials, E. P. Wohlfarth and K. H. J. Buschow Edition, Vol. 4, Elsevier, Amsterdam, 1998, pp. 287{290}.
 - [6] P. Webster, Contemp. Phys. 10 (6) (1969) 559{577}.
 - [7] J. S. Robinson, S. J. Kennedy, R. Street, J. Phys. Cond. Mat. 9 (8) (1997) 1877{1886}.
 - [8] S. Ishida, Y. Kubo, J. Ishida, S. A. Sano, J. Phys. Soc. Jpn. 48 (1980) 814{821}.
 - [9] S. Ishida, J. Ishida, S. A. Sano, J. Yamashita, J. Phys. Soc. Jpn. 48 (1978) 1239{1243}.
 - [10] S. Ishida, S. A. Kasawa, Y. Kubo, J. Ishida, J. Phys. F: Met Phys 13 (1983) 161{174}.
 - [11] A. R. Williams, V. L. Moruzzi, C. D. Gellat, J. Kubler, J. Magn. Mater 31-34 (1983) 88.
 - [12] R. D. Groot, K. H. J. Buschow, J. Magn. Mater. 54-57 (1986) 1377{1381}.
 - [13] R. D. Groot, F. M. Ueller, P. V. Engen, K. H. J. Buschow, J. Appl. Phys. 55 (1984) 2151{2154}.

- [14] S. Ishida, S. Fujii, S. Kawhiwagi, S. A sano, J. Phys. Soc. Jpn. 64 (6) (1995) 2152{2157.
- [15] Y. Noda, Y. Ishikawa, J. Phys. Soc. Jap 40 (1976) 690{698.
- [16] Y. Ishikawa, Y. Noda, Solid. State. Com m . 15 (1974) pp.833{836.
- [17] Y. I. K . Tajim a, P. W ebster, M . Stringfellow, D . Tocchetti, K . Ziebeck, J. Phys. Soc. Jpn. 43 (1977) 483{489.
- [18] T. M oria, Spin uctuations in m agnetics, 1998.
- [19] P. J. W ebster, J. Phys. Chem . Solids 32 (1971) 1221{1231.
- [20] A. Szytula, Handbook of m agnetic m aterials, Vol. 6, Elsevier, North Holland, Am sterdam , 1991, Ch. M agnetic properties of Ternary Intermetallic Rare-earth Com pounds, pp. 85{180.
- [21] J. Brabers, A. Holten, F. K ayzel, S. Lenczowski, K. H. J. Buschow, F. de Boer, Phys. Rev. B. 50 (22) (1994) 16410{16417.
- [22] D. G oodenought, M agnetism and chem ical bonding, 1968.
- [23] E. G erasim ov, V. G aviko, V. Neverov, A. K orolyov, submitted to J. of Alloys and Com p. (2002).
- [24] S. Ishida, S. A sano, J. Ishida, J. of Phys. Soc. Jpn 55 (3) (1986) 936{945.
- [25] J. van A cker, Z. Stadnik, J. Fuggle, H. Hoekstra, K. H. J. Buschow, G. Stronik, Phys. Rev. B 37 (12) (1988) 6827{6834.
- [26] W. Ladem an, L. K lebano, Phys. Rev B 54 (16) (1996) 11725{11730.
- [27] Y. Yam oshenko, M . K atselson, E. Shreder, E. K um aev, A. Slebarski, S. P logm ann, T. Schlatholter, J. Braun, M . Neumann, Europ. Phys Journal B 2 (1) (1998) 1{3.
- [28] M . V. Yablonskikh, V. I. G rebennikov, Y. M . Yam oshenko, E. Z. K um aev, S. M . Butorin, L.-C. Duda, , J. Nordgren, S. P logm ann, M . Neumann, PRB 63 (2001) 02351xx.
- [29] C. Hague, J. Marriot, G. Guo, K. H ricovini, G. K rill, PRB 51 (2) (1995) 1370{1373.
- [30] L.-C. Duda, J. S. D . M anchini, A Nilson, N W ashdahl, J. Nordgren, M . Sam ant, PRB 50 (22) (1994) 16758{16761.
- [31] M . M agnusson, N. W asdahl, J. Nordgren, PRB 56 (19) (1997) 12238{12242.
- [32] A. Titov, A. K uranov, V. P leshev, Y. Yam oshenko, M . Yablonskikh, A. Postnikov, S. P logm ann, M . N . A . Ezhov, E. K um aev, PRB 63 (2001) 035106.
- [33] S. P logm ann, T. Schlatholter, J. Braun, M . Neumann, Y. Yam oshenko, M . Yablonskikh, E. Shreder, E. K um aev, A. W rona, A. Slebarski, Phys. Rev. B 60 (9) (1999) 6428{6437.

TABLE I: Structural and magnetic properties of Mn-based compounds

material	structure	d_{Mn-Mn}, nm	Mn/B	eff/B	T_C, K	T_N, K
Mn	Mn		1.9; 1.7; 0.6; 0.2			95
$La_{0.2}Sm_{0.8}Mn_2Si_2$	$ThCr_2Si_2$	0.283	2.3	3.8		430
$LaMn_2Si_2$	$ThCr_2Si_2$	0.291	2.5	3.5	305	470
Co_2MnAl	$B2=L2_1$	0.407	3.01	4.01	693	
Co_2MnSb	$L2_1$	0.419	3.75	4.9	600	

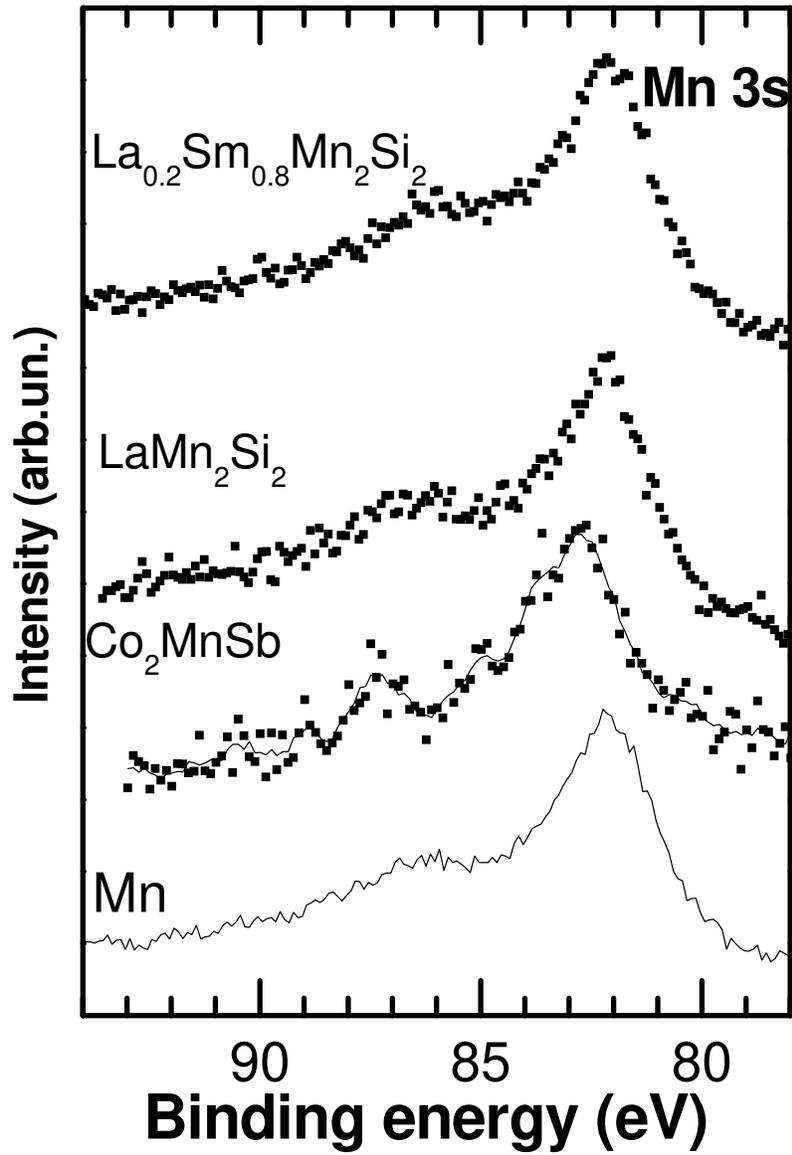


FIG. 1: Mn 3s X-ray photoemission spectra.

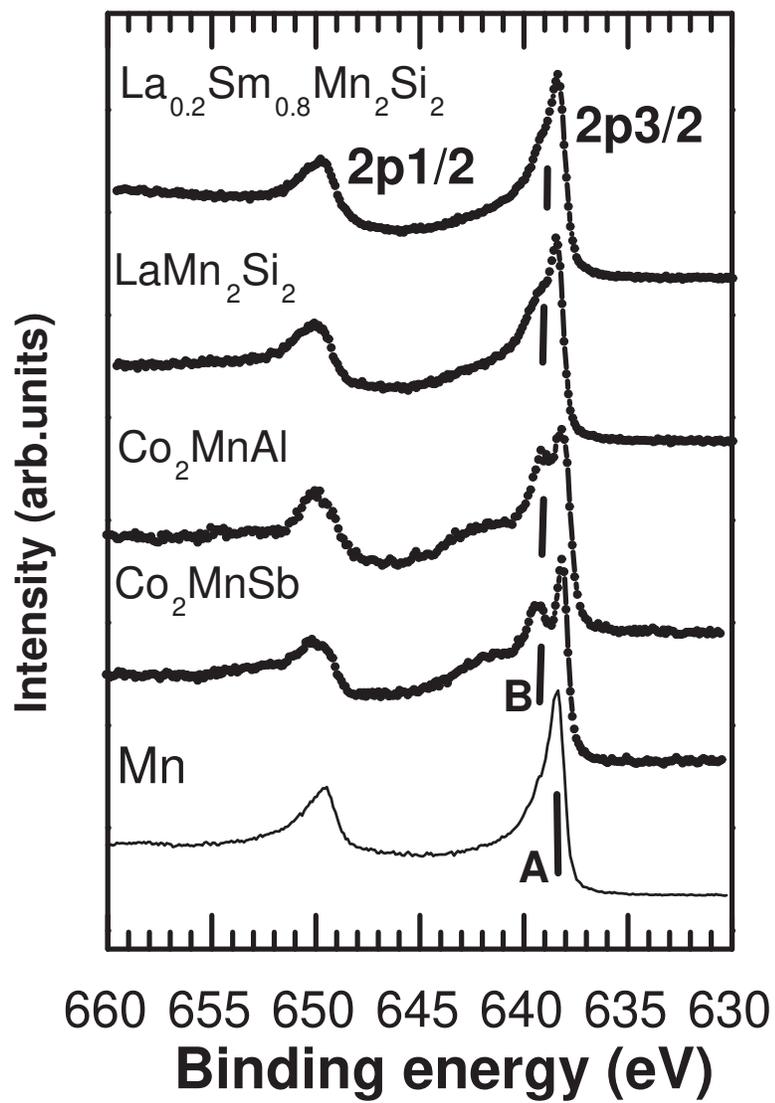


FIG. 2: Mn 2p X-ray photoemission spectra.

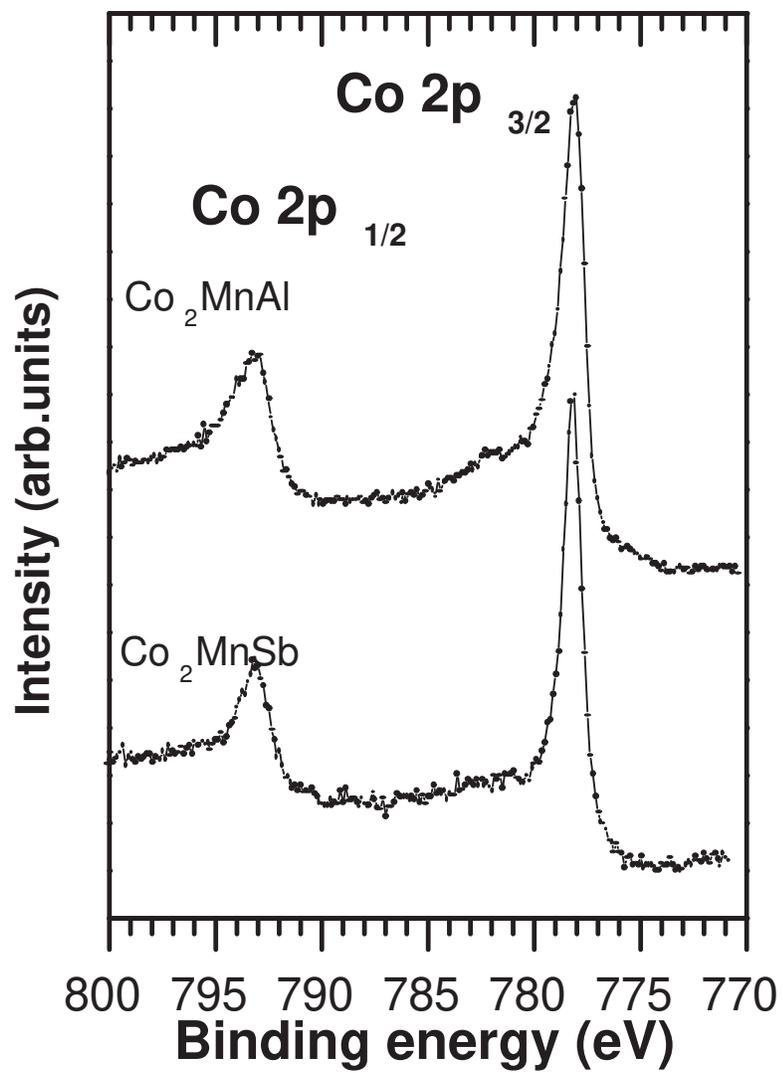


FIG. 3: Co 2p X-ray photoemission spectra of Heusler alloys.

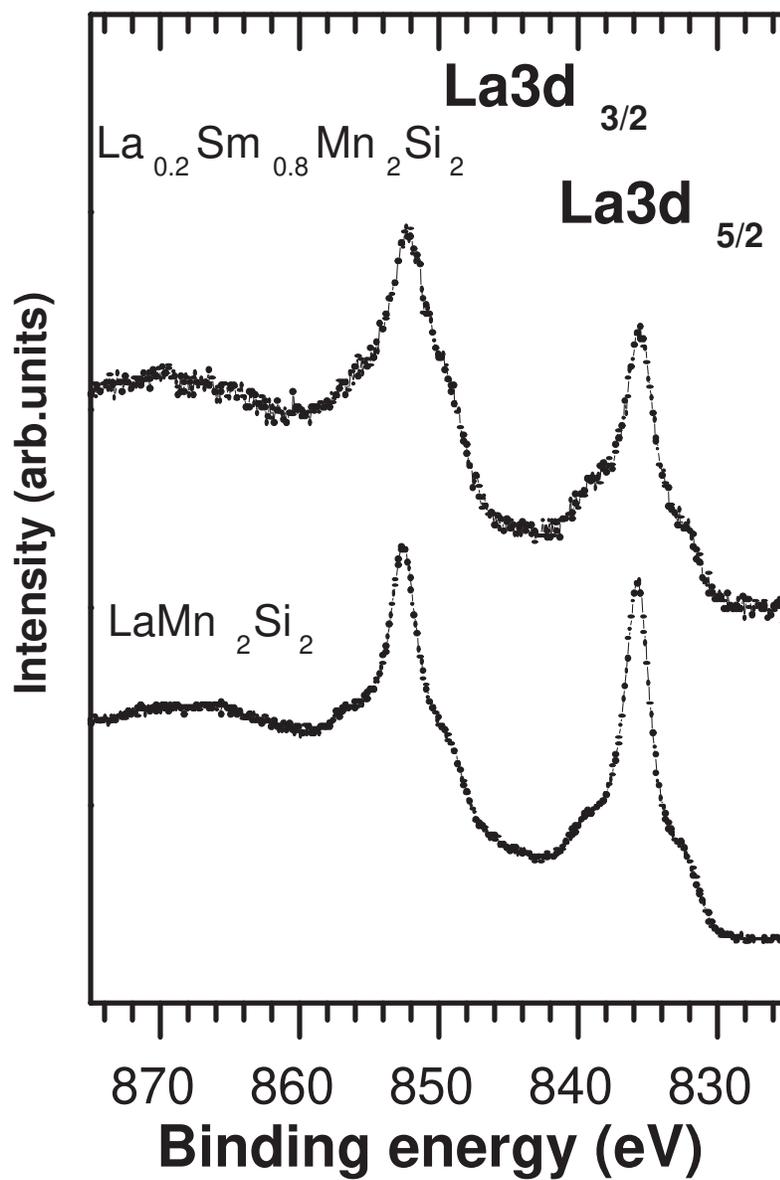


FIG . 4: La 3d X-ray photoemission spectra of rare-earth compounds.

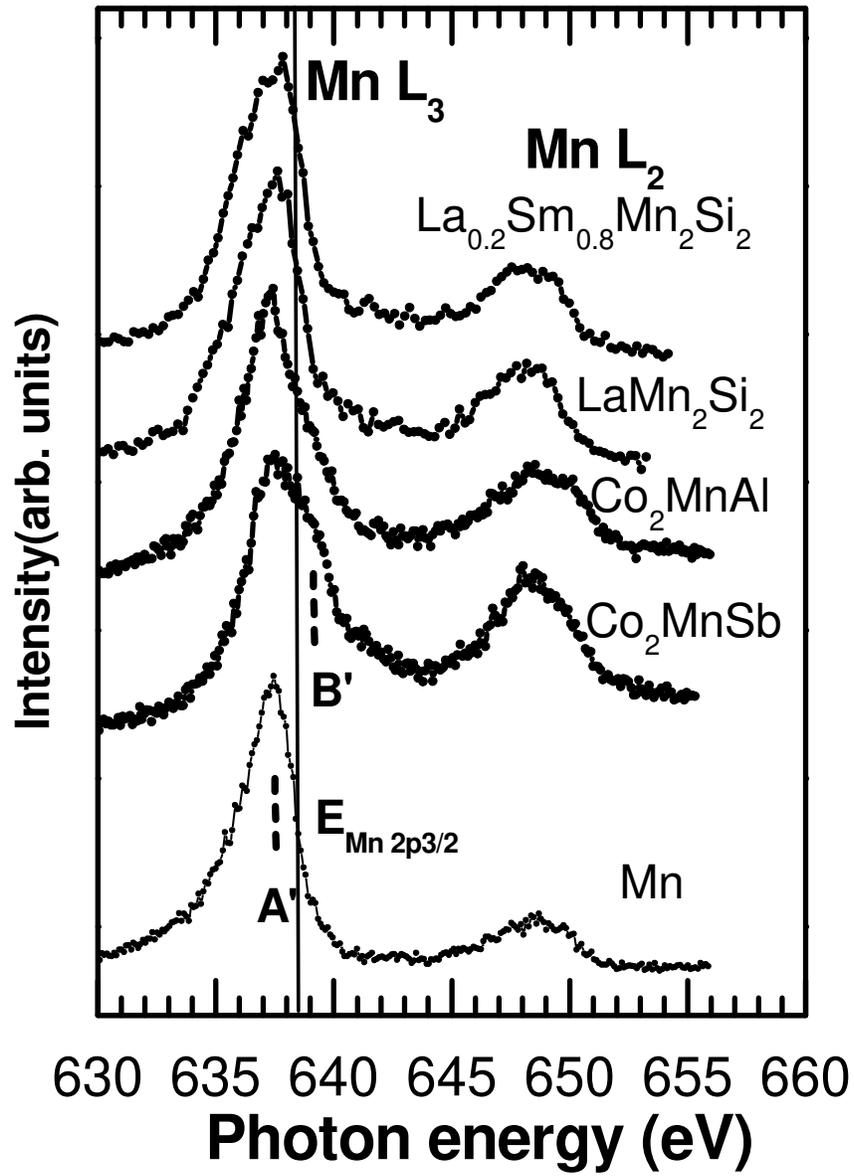


FIG. 5: Mn $L_{2,3}$ X-ray emission spectra of Heusler alloys.

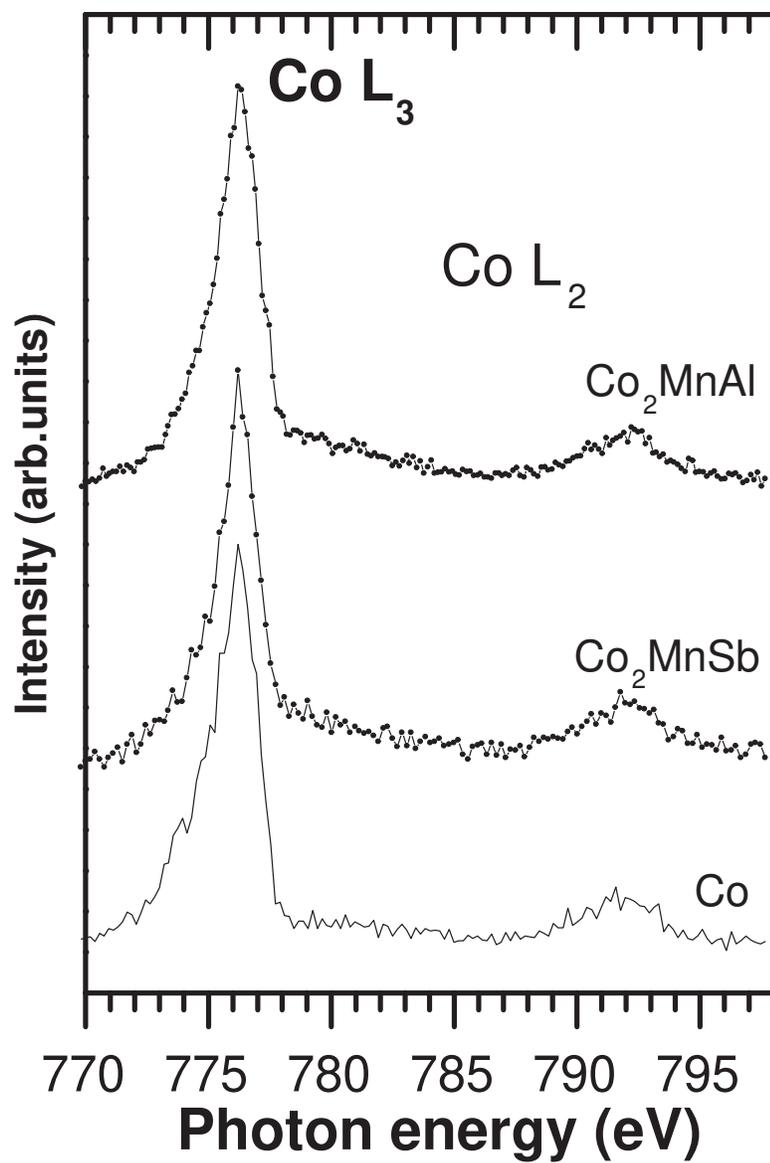


FIG . 6: $\text{Co } L_{2,3}$ X-ray emission spectra of Heusler alloys.