

Peak effect in single crystal MgB_2 superconductor for $H \parallel c$ -axis

M. Pissas

Institute of Materials Science, NCSR, Demokritos, 15310 Aghia Paraskevi, Athens, Greece

S. Lee, A. Yamamoto, and S. Tajima

Superconductivity Research Laboratory, ISTEC, Tokyo 135-0062, Japan

We have studied the phase diagram of MgB_2 superconductor using a single crystal for $H \parallel c$ -axis. For the first time we report the existence of peak effect in the screening current in MgB_2 single crystal for $H \parallel c$ -axis. In the magnetic field regime $10 < H < 13.5$ kOe the local fundamental diamagnetic moment displays a very narrow diamagnetic step, with a temperature width of the same size as the zero dc-magnetic field transition. For higher field this step is transformed to a peak which is related with the peak effect in the screening current. Finally, for $H < 10$ kOe the diamagnetic step is transformed to a gradual transition. Our findings for the vortex matter phase diagram for the MgB_2 are closely related with theoretical predictions concerning the vortex matter phase diagram of a type II superconductor in the presence of weak point disorder.

PACS numbers: 74.60.Ge, 74.60.Jg, 74.60.-w, 74.62.Bf

The recent discovery [1] that MgB_2 compound is a superconductor with remarkably high transition temperature $T_c = 39$ K has generated extensive scientific research (for a review see Ref. 2). MgB_2 is an anisotropic [3, 4, 5, 6, 7, 8] type II superconductor with a sample dependent anisotropic constant $\gamma = H_{c2}^{ab}/H_{c2}^c$, taking values [9, 10, 11, 12, 13, 14, 15] into interval 2–6. The absence of weak link problem [16] in polycrystalline MgB_2 samples gives expectations for its using in practical applications. Furthermore, the intermediate T_c of MgB_2 , in comparison with high- T_c and low- T_c conventional superconductors, makes significant the experimental exploration of its vortex matter phase diagram, considering MgB_2 as a model physical system where both thermal fluctuations and disorder must be treated on an equal footing. In addition, the MgB_2 gives us the opportunity for experimental verification of theoretically proposed issues, like the melting transition of the vortex matter, the Bragg and amorphous vortex phases [17].

In this paper, we report a detailed study of the vortex matter phase diagram for $H \parallel c$ -axis. In the magnetic field regime $10 < H < 13.5$ kOe the local fundamental diamagnetic moment displays a very narrow diamagnetic step, with a temperature width of the same size as the zero dc-magnetic field superconducting transition. For higher fields this step is transformed to peak which is related with the peak effect. Finally, for $H < 10$ kOe the diamagnetic step is transformed to a gradual transition. Our findings for the vortex matter phase diagram for the MgB_2 are closely related with the theoretical ideas proposed recently [18, 19, 20, 21, 22, 23, 24, 25].

MgB_2 single crystals have been grown under high pressure in the quasibinary $\text{Mg-MgB}_2\text{-BN}$ system at a pressure of 4–6 GPa and temperature 1400–1700°C for 5–60 mins, in a BN container, using a cubic-anvil press (TRY Engineering). The present experiments were performed on a small ($250 \times 250 \times 40 \text{ } \mu\text{m}^3$) MgB_2 single crystal

using as magnetic induction sensor a GaAsIn Hall sensor with an active area of $50 \times 50 \text{ } \mu\text{m}^2$, superimposing ac ($H_{ac} = H_0 \sin(2\pi ft)$; $f = 0.8 \text{ Hz}$) and dc magnetic fields parallel to the crystal's c -axis ($H_{dc} \parallel H_{ac} \parallel c$). The real and imaginary part ($V = V^0 + iV^\omega$) of the modulated Hall voltage, which is proportional to the local magnetic induction (V/B_z), in the surface of the crystal, was measured by means of two lock-in amplifiers. Measurements were performed as a function of temperature (isothermal measurements) and also as a function of the applied field (isothermal measurements). As cryogenic environment and for the dc-field production a 10 T OXFORD cryostat has been used. Besides the superior sample quality, one of the most important aspects of our measurements is the sample's microscopic size, restricting to a minimum any residual inhomogeneities.

Measurements of local magnetic induction in zero dc-magnetic field for $H_0 = 1.4$ Oe, display a $T_c = 38.3$ K with a transition width (defined at the levels 10% and 90% of the real part of B^0) $T = 0.16$ K, indicating a high quality single crystal. Fig. 1 (a) shows the real and imaginary parts of the local fundamental susceptibility ($V^0 = V^0/H_0$, $V^\omega = V^\omega/H_0$) as function of temperature, measured under a dc-magnetic field of $H_{dc} = 15$ kOe for ac-field $H_0 = 3.4$ Oe. The measurements have been taken during cooling and heating. As temperature decreases both V^0 and V^ω traces remain zero. Right below a temperature, which is denoted by T_{irr} , both real and imaginary parts form a peak, with a peak-width roughly 0.5 K. Moreover, the characteristic points of the peak, the onset temperature T_0 , the location of the peak, T_p , and T_{irr} do not depend on the amplitude of the ac-field. The same holds and for the other dc-fields where the peak effect is present (vide infra). As temperature further decreases both V^0 and V^ω exhibit the characteristic functional form of a superconducting sample, which supports a screening current, increasing monotonically

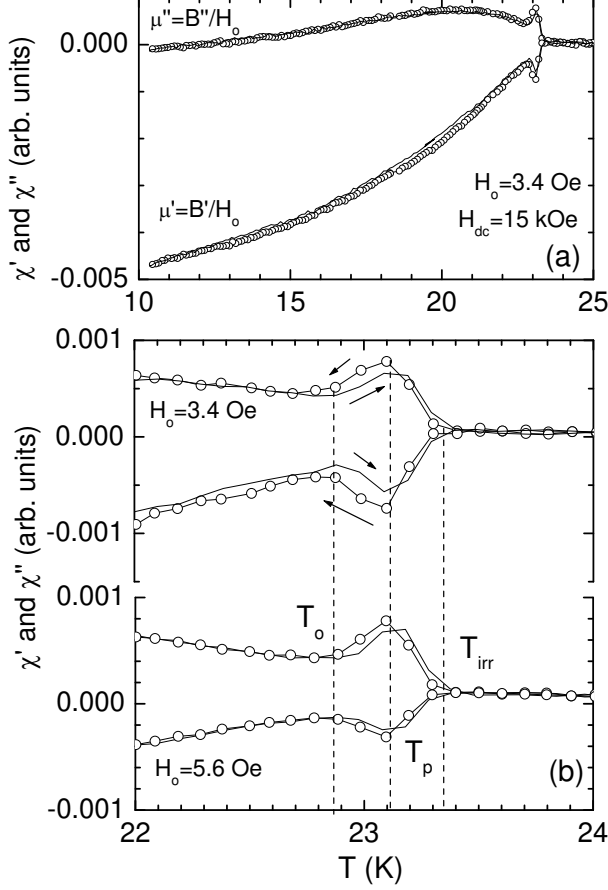


FIG. 1: (a) Temperature variation of the real χ' and imaginary χ'' local fundamental susceptibility for $H_0 = 3.4$ Oe ($H_{dc} = 15$ kOe). (b) Zoom of the measurements near the diamagnetic onset (for $H_0 = 3.4; 5.6$ Oe and $H_{dc} = 15$ kOe) where the hysteretic behavior is observed.

down to $T = 0$. The broad second maximum in $\chi''(T)$ -curve, implies a small critical current density (low pinning). More importantly, Fig. 1(b) shows that in the region $T_0 < T < T_p$, the curves measured during cooling are above those measured during heating. Our observation can be attributed to the so-called peak effect which appears both in low and high T_c superconductors. To the best of our knowledge it is the first time that such an experimental result concerning the MgB₂ is reported. At the T_{irr} the vortex lattice, due to the pinning of flux lines, can support a finite critical current which leads to the screening of ac magnetic field. Both the temperature and field dependance of screening current display a peak. Different scenarios have been suggested for the peak effect. The explanation for the peak effect in terms of flux lattice properties was first suggested by Pippard [26]. Pippard's idea was that the energy to shear a flux lattice elastically goes to zero near H_{c2} more rapidly than the pinning energy. This allows the lattice to become

more distorted near H_{c2} . It adjusts to increase pinning energy and thus has a higher critical current. Subsequently, Larkin and Ovchinnikov [27] interpreted the peak effect based on the hypothesis that the elastic moduli of the vortex lattice suddenly soft while going from local to nonlocal elasticity. Recently the onset of the peak effect has been associated with the proliferation of dislocations in the flux-line lattice [18, 19, 20, 21, 22, 23].

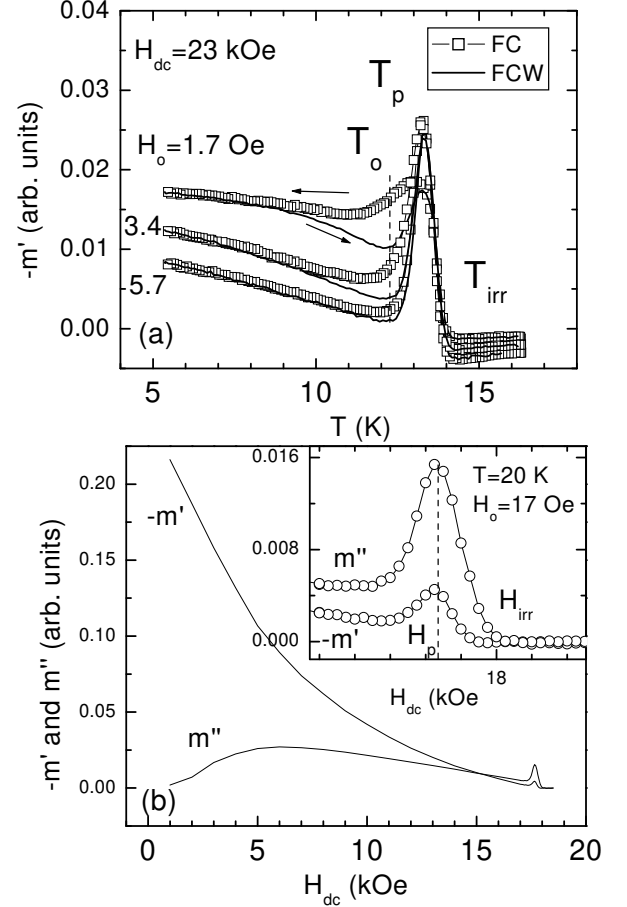


FIG. 2: (a) Real $m' = H_0 V_0$ local fundamental ac magnetic moment as a function of temperature, for $H_0 = 1.7; 3.4$ and 5.7 Oe ($H_{dc} = 23$ kOe). The data with open squares (solid line) have been measured during cooling (warming after field cooling), respectively. (b) (a) Real $m' = V_0 H_0$ and imaginary $m'' = V'' H_0$ local fundamental ac magnetic moment as a function of dc magnetic field at $T = 20$ K for $H_0 = 17$ Oe. The inset shows the detail of the measurement in the region of the peak effect.

Fig. 2 shows the real part of the local magnetic moment near the peak regime for $H_{dc} = 23$ kOe, for various ac fields, during cooling and heating. In the particular magnetic field for $H_0 = 1.7$ Oe the measurement shows a strong hysteretic behavior for $T < T_p$. This hysteretic behavior reduces as the amplitude of ac-field increases [28]. Indeed, in the measurement for $H_0 = 5.7$

Of the hysteretic behavior is negligible. In addition, the width of the peak now is ~ 1 K in comparison with the width observed for $H_{dc} = 15$ kOe. More importantly, the peak is more obvious as the amplitude of ac-field increases. The peak effect has also been observed in isothermal measurements, as Fig. 2(b) illustrates. The observed thermomagnetic history dependence of the ac-response is not compatible with the conventional critical-state model. This model treats the critical current, J_c as a single valued function of the magnetic induction B and temperature T , while our measurements indicate that J_c depends on the measuring path in the regime $T < T_p$. The observed behavior can be understood as follows: as we expose the system to an applied dc-field followed by cooling, through the H_{c2} -line, the topological defects remain as temperature decreases (the field cooling disordered phase is simply supercooled from the phase existing above T_p). In other words, the field cooling state yields a disordered vortex glass phase. During heating this disordered state becomes more order with consequent lower critical current in comparison with the field cooling one. The observation of the peak effect, with negligible thermomagnetic history effects, for large amplitude of the ac-field, may be related with the unblocking of the vortices from their pinned meta-stable configuration. The ac-field triggers a transition into the stable low pinning state which does not change on subsequent larger ac-field measurements.

More interestingly, detailed measurements in the regime $8 < H < 15$ kOe revealed that the peak effect has been transformed to a very narrow diamagnetic step with a temperature width of similar size (or less) as the zero dc-field transition. Moreover, for fields $H_{dc} \sim 10$ kOe (see Fig. 3) the diamagnetic step at the onset of the transition becomes a gradual transition (see Fig.3). Our findings concerning the diamagnetic step in m'' are in accordance with the magnetoresistance results of Elisei et al. [12] where an extremely sharp drop in the magnetoresistance has been observed, in the same magnetic field regime. Our observations resemble the vortex flux lines lattice melting transition observed in $YBa_2Cu_3O_{7-x}$ [29] near critical points. Based on this analogy is plausible that in this regime the transition concerns a first order transition of the vortex lattice. Below and above the low (H_{lcp}) and upper (H_{ucp}) boundaries of this regime the transition is transformed to a second order.

Based on the local measurements a phase diagram for MgB_2 has been constructed. In Fig. 4 plotted are the onset points of the appearance of diamagnetic local moment that coincide with the end point of peak effect. If the pinning of the vortex lattice starts exactly below the upper critical field H_{c2} of MgB_2 . In transport measurements the H_{c2} line is determined by the onset of the magnetoresistance drop [12]. The locus of these points is distinctly different from our H_{irr} , but most probably the onset of non-ohmic

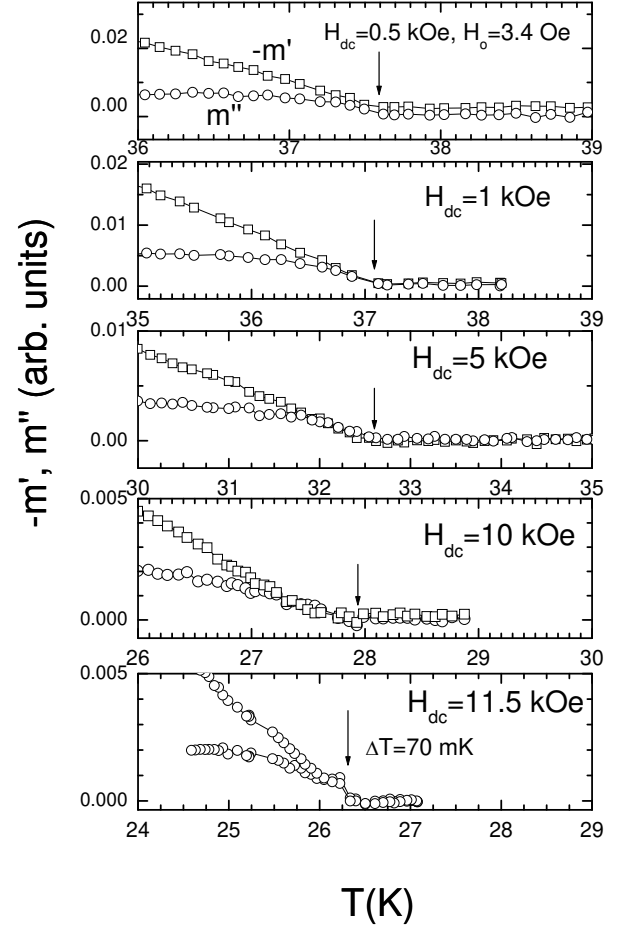


FIG. 3: Real $m' = H_0 \cdot V'$, and imaginary, $m'' = V''$ local fundamental ac magnetic moment as a function of temperature, for $H_0 = 3.4$ Oe ($H_{dc} = 0.5; 1; 5; 10$ and 11.5 kOe).

behavior[30] has to do with surface superconductivity.

As illustrated in Fig. 4, for $T > T_c=2$, the H_{irr} line displays a positive curvature, while for $T < T_c=2$ it displays a negative curvature and approaches zero temperature with nearly zero slope at $H_{irr}(0) \sim 29$ kOe. The experimental points can be reproduced very well using the empirical formula $H_{irr}(T) = 29[1 - (T/T_c)^2]^{1/45}$. Included also are the points where the peak is located, as well as the onset. The region at which the peak effect occurs, occupies a small fraction of the region of the mixed state, located slightly below the $H_{irr}(T)$ line. In the regime between 10 and 15 kOe the peak effect is transformed to a very narrow diamagnetic step and finally, for lower fields the transition becomes gradual.

It is widely accepted that the vortex phase diagram in the presence of weak point disorder consists of three generic phases, the vortex liquid, the high field amorphous vortex glass and the low field, low temperature Bragg glass [17]. These phases are governed by the three basic energies: the energy of the thermal fluctuations, pin-

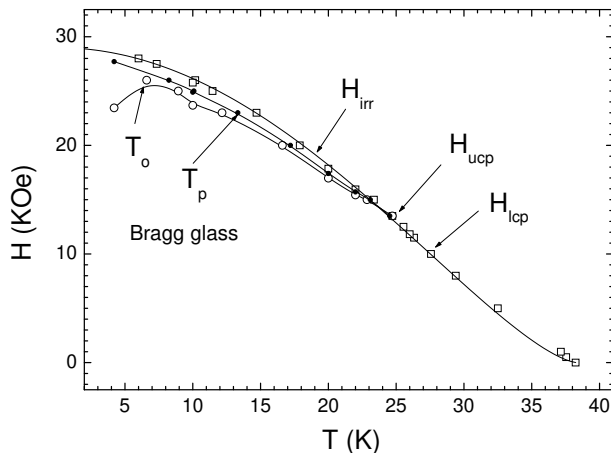


FIG. 4: The phase diagram of vortex matter of MgB_2 compound for $H \parallel c$ -axis. Presented are the onset point, T_o , (open circles), the peak temperature, T_p , (solid circles), and the irreversibility points, T_{irr} , (open squares). The solid line through $(T; H_{irr})$ -points is a plot of the empirical formula $H_{irr}(T) = 29[1 - (T/T_c)^2]^{1.45}$. The H_{ucp} and H_{lcp} are the points where the peak effect and the diamagnetic step disappear respectively.

ning and elastic energies. The transition lines are determined by matching any of the two basic energies and the match of all three energies marks the tricritical point [18, 19, 20, 21, 22, 23]. Based on this unified picture we associate the line defined by the onset of peak effect to the transition of a Bragg glass phase to an amorphous vortex glass. The point where the peak effect is terminated can be attributed to an upper tricritical point. At this point the Bragg glass transition line intersects the H_{irr} -line [24]. Based on the sharpness of the onset of the diamagnetic local moment in the regime $10 < H < 13.5$ kOe, the transition in this regime resembles the first order melting transition. Finally, at the regime $0 < H < 10$ kOe the transition becomes second order. Since the thermal energies (kT) and the fluctuation effects ($\omega^2 = \omega_B^2$) for MgB_2 are of the same order of magnitude as the high- T_c superconductors this scenario is very realistic.

In the case of Nb there is structural evidence [31] for a first-order vortex solid-liquid transition at the peak temperature of the peak effect. In analogy, MgB_2 may exhibit a melting of the vortex lattice at the peak temperature, T_p . Above T_p we have a vortex liquid up to T_{c2} where the sample transits from the mixed state to the normal.

In summary, we experimentally estimated the vortex matter phase diagram for MgB_2 single crystal superconductor for $H \parallel c$ -axis. We found that in a narrow temperature (or field) regime a peak in the screening current exists. The three distinct behaviors of the onset of the diamagnetic local moment resemble the picture of the

melting transition with two critical points.

This work was partially supported by the New Energy and Industrial Technology Development Organization (NEDO) as collaborative research and development of fundamental technologies for superconductivity applications

-
- [1] J. Nagamatsu et al, Nature (London) 410, 63 (2001).
 - [2] C. Buzea and T. Yamashita, Supercond. Sci. Technol. 14, R115 (2001).
 - [3] O. F. de Lima et al, Phys. Rev. Lett. 86, 5974 (2001);
 - [4] S. Lee et al, J. Phys. Soc. Jpn 70, 2255 (2001);
 - [5] M. Xu et al, Appl. Phys. Lett. 79, 2779 (2001).
 - [6] F. Simon et al, Phys. Rev. Lett. 87, 047002 (2001).
 - [7] S. L. Bud'ko, et al, Phys. Rev. B 64, 180506 (2001); S. L. Bud'ko, et al, cond-mat/0201085.
 - [8] G. Papavassiliou et al, Phys. Rev. B 65, 012510 (2002).
 - [9] A. V. Sologubenko et al, Phys. Rev. B 65, 180505R (2002).
 - [10] A. V. Sologubenko et al, cond-mat/0201517.
 - [11] A. V. Sologubenko et al, cond-mat/0112191.
 - [12] Yu. E. Irtsev et al, Phys. Rev. B 65, 140501(R) (2002).
 - [13] A. K. Pradhan et al, Phys. Rev. B 64, 212509 (2001).
 - [14] F. Manzano et al, Phys. Rev. Lett. 88, 047002 (2002).
 - [15] M. Angst et al, Phys. Rev. Lett. 88, 167004 (2002).
 - [16] S. L. Bud'ko et al, Phys. Rev. B 63, 220503R (2001); Y. Bugoslavsky et al, London, 411, 561, (2001); M. Pissas, et al, J. of Superconductivity 14, 615 (2001).
 - [17] G. B. Lattar et al, Rev. Mod. Phys. 66, 1125 (1994); E. H. Brandt, Rep. Prog. Phys. 58, 1465 (1995); T. Nattermann and S. Scheidl, Adv. Phys. 49, 607 (2000); T. Giamarchi and S. Bhattacharya cond-mat/0111052 (2001).
 - [18] T. Giamarchi, and P. Le Doussal, Phys. Rev. B 55, 6577 (1997);
 - [19] D. Ertaş, and D. R. Nelson, Physica C 272, 79 (1996).
 - [20] M. J. P. Gingras, and D. A. Huse, Phys. Rev. B 53, 15193 (1996).
 - [21] A. E. Koshelev, and V. M. Vinokur, Phys. Rev. B 57, 8026 (1998).
 - [22] V. Vinokur et al, Physica C 295, 209 (1998).
 - [23] J. Kierfeld, Physica C 300, 171-183 (1998).
 - [24] G. P. Mikitik, and E. H. Brandt, Phys. Rev. B 64, 184514 (2001).
 - [25] Y. Radzyner, A. Shaulov, Y. Yeshurun, cond-mat/0201024.
 - [26] A. B. Pippard, Philos. Mag. 19, 217 (1967).
 - [27] A. I. Larkin and Yu. N. Ovchinnikov, J. Low Temp. Phys. 34, 409 (1979).
 - [28] D. Stamopoulos and M. Pissas, Phys. Rev. B 65, 134524 (2002).
 - [29] G. W. Crabtree et al, Physics and Materials Science of Vortex States, Flux pinning and Dynamics, 357-385 1999, Kluwer Academic Publishers.
 - [30] During the submission of this paper we became aware of a related work on MgB_2 by U. Welp et al. [cond-mat/0203337 (2002)]. The results of this work agree very well with ours.
 - [31] X. S. Ling et al, Phys. Rev. Lett. 86, 712 (2001).