

Magnetooptical reactivity of superconducting MgB_2 single crystals

A. Perucchi, L. Degiorgi, J. Jun, M. Angst and J. Karpinski
 Laboratorium für Festkörperphysik, ETH Zurich, CH-8093 Zurich, Switzerland
 (Dated: April 14, 2024)

We present magnetooptical reactivity results in the basal plane of the hexagonal MgB_2 . The data were collected on a mosaic of MgB_2 single crystals with $T_c = 38$ K from the ultraviolet down to the far infrared as a function of temperature and magnetic field oriented along the c -axis. In the far infrared there is a clear signature of the superconducting gap with a gap-ratio $2\Delta/k_B T_c \approx 1.2$, well below the weak-coupling value. The gap is suppressed in an external magnetic field, which is a function of temperature. We extract the upper critical field H_{c2} along the c -axis. The temperature dependence of H_{c2} is compatible with the Helfand-Werthamer behaviour.

PACS numbers: 78.20.-e, 74.70.-b,

Since the discovery of superconductivity in MgB_2 with $T_c \approx 40$ K [1], substantial experimental activity has been devoted to elucidate the nature of its superconducting state. The issue is to assess whether MgB_2 is one of the best-optimized Bardeen-Cooper-Schrieffer (BCS) materials or whether its superconducting properties stem from a novel pairing mechanism. The amplitude of the superconducting gap and its spectroscopic signature, as a function of temperature and magnetic field, are expected to depend on the driving mechanism [2].

Infrared spectroscopy is a very promising and powerful method for the observation of the gap. Optical experiments, besides being contact-less techniques, offer the important advantage that the electromagnetic radiation penetrates deeply inside the bulk. Analysis of previous optical data [3, 4, 5, 6] revealed gap values in the range $2\Delta \approx 3\text{--}6$ meV, which are rather small compared to the BCS estimate $2\Delta = 12$ meV [2]. The range of superconducting gaps proposed for MgB_2 is even wider when considering other techniques, such as Raman or tunneling spectroscopy, photoemission or specific heat [7, 8, 9, 10, 11], which yield values of 2Δ between 3 and 10 meV. This wide spread of gap values is also accompanied in some cases by deviations from the BCS temperature dependence, pointing to complex behaviour in this novel superconductor. Possible origins of the large gap distribution might include effects associated with the sample quality (i.e., imperfections and distribution of the surface composition) and with the specimen type (i.e., polycrystalline or films). More intrinsic origins of the wide range of gaps comprise the existence of an anisotropic (s -wave) superconducting gap as well as a multi-gap mechanism [12]. It has been also conjectured that the different values of the gap might be partly explained by the preferential sensitivity of particular experiments to different portions of the gap distribution [12].

Here, we present infrared reactivity data $R(\omega)$ on high quality single crystals of MgB_2 with well-characterized optical surface parallel to the basal plane. We focus our attention to the dependence of $R(\omega)$ to the magnetic

field oriented along the c -axis at selected temperatures close to and below T_c . The corresponding real part of the optical conductivity exhibits a depletion of oscillator strength due to the opening of the superconducting gap. The gap size is less than half the value expected from an isotropic BCS model. By applying magnetic fields along the c -axis we induce a suppression of superconductivity, as suggested by the disappearance of the gap. We extract the upper critical field H_{c2} along the c -axis and find it to be compatible with the Helfand-Werthamer [13] calculation. This seems to indicate that no unconventional mechanism needs to be invoked to explain the bulk upper critical field. Moreover, our magnetooptical results suggest a dirty-limit metallic normal state.

Single crystals of MgB_2 with $T_c = 38$ K were grown using a high-pressure cubic anvil cell and were synthesized from a precursor mixture of 99.9% pure Mg powder and 97% pure amorphous boron. The crystals were grown in a BN container of 6 mm diameter under a pressure of 30 kbar. The temperature was increased up to 1800 °C and kept constant for 0.5 h. The temperature was then decreased and pressure released. Flat crystals of MgB_2 of a size up to $1.2 \times 0.8 \times 0.05$ mm³ have been obtained [14]. We built a mosaic consisting of three crystallites from the same batch and with optical surface oriented perpendicular to the c -axis.

We measured the optical reactivity $R(\omega)$ in the basal plane of the hexagonal MgB_2 . The mosaic had an optical measurable surface of 2×2 mm². The largest crystallite has been placed in the center of the mosaic. A series of measurements identifying different spots on the specimen were performed and equivalent results were collected, excluding important effects due to the surface scattering. In the far infrared (FIR) spectral range, data were collected as a function of temperature (1.5–300 K) and with varying magnetic field H (0–7 T) oriented along the c -axis with possible misalignment of less than 5°. The FIR spectral range (i.e., 20–600 cm⁻¹) was covered with a Bruker Fourier spectrometer equipped with He-cooled Ge bolometer detector and with an Oxford magnet cryostat with appropriate optical windows. We present our

FIR results down to approximately 25 cm^{-1} , the lower frequency limit where the collected data are reproducible over several runs and in different combinations of temperature and magnetic field. Because of the mosaic configuration of our specimen as well as the residual surface scattering and diffraction limit effects, we cannot fully trust the data below 25 cm^{-1} .

Figure 1 provides an overview, showing the magnetic field dependence of $R(\omega)$ in FIR at 1.6 and 20 K [15]. The normal state $R(\omega)$ at 40 K and 0 T is shown in Fig. 1, as well. At zero field $R(\omega)$ at $T < T_c$ is remarkably enhanced below 50 cm^{-1} : $R(\omega)$ at 1.6 K reaches the total reflection at about 30 cm^{-1} , while $R(\omega)$ at 20 K is still enhanced but only approaches the total reflection. By applying a magnetic field along the c-axis, the obvious trend at all temperatures is to reduce the enhancement of $R(\omega)$ (e.g., already at 1.6 K and 4 T $R(\omega)$ clearly deviates from the total reflection behaviour seen at 0 T). At any temperature, there is a specific magnetic field for which $R(\omega)$ recovers the normal state shape. We have also verified the field independence of $R(\omega)$ above 38 K. It is worth mentioning that our FIR results in zero field merge nicely with the submillimeter range data of Pimenov et al. obtained with a MgB₂ film [3]. As it will be stressed below, the change of slope in $R(\omega)$ for $T < T_c$ with respect to the normal state behaviour (i.e., at 40 K) is associated to the optical manifestation of the superconducting gap (arrow in Fig. 1a). While the overall $R(\omega)$ shape below T_c is compatible with the BCS-like behaviour [2], we note the rather pronounced drop of $R(\omega)$ in FIR. This leads to a shallow minimum in $R(\omega)$ at about 100 cm^{-1} [15], which bears a striking similarity with the result on thin film [3]. In passing, the consequence of such a minimum is an excitation spectrum, which may be interpreted within a multiband (i.e., two-D dimensional component) scenario [15, 16, 17]. Above 50 cm^{-1} the spectra were found to be temperature and magnetic field independent. The inset of Fig. 1 displays an overall view of $R(\omega)$ at 300 K, measured up to 10^5 cm^{-1} , which is in fair agreement with $R(\omega)$ on films and dense polycrystalline samples [3, 16, 18]. Therefore, the 300 K reflectivity was used in the Kramers-Kronig transformation in order to calculate the optical conductivity. To this end, the standard extrapolation was employed above 10^5 cm^{-1} [19]. Below 25 cm^{-1} $R(\omega)$ at $T > T_c$ was extrapolated using the Hagen-Rubens law [19]. Below T_c , $R(\omega)$ was approximated to 100% when $R(\omega)$ reached total reflection at finite frequency in the measured spectral range, otherwise $R(\omega)$ was assumed to gradually increase to 100% for $\omega \rightarrow 0$. Alternative extrapolation methods were checked for $\omega \rightarrow 0$ but this issue does not affect the main argument of our discussion.

Figure 2 shows the magnetic field dependence of the ratio of the real part $\sigma_1(\omega)$ of the optical conductivity to its normal state value (at 40 K) at selected temperatures. Focusing first on the 0 T data, we observe the

strong depletion of $\sigma_1(\omega)$ for $T < T_c$. The conductivity is very small or even zero (i.e., as a consequence of the total reflection for $T < T_c$ (Fig. 1)) below 30 cm^{-1} and then increases monotonically at higher photon energies. We identify the frequency, where the onset of absorption (i.e., increase of $\sigma_1(\omega)$), Fig. 2) occurs, as the superconducting gap value. The superconducting gap $2\Delta = 31 \text{ cm}^{-1}$ (3.8 meV) at $T = T_c$ for our MgB₂ single crystal agrees fairly well with those previously achieved with optical methods on films ($3 - 5 \text{ meV}$ [3, 4, 5]), as well as on polycrystalline samples ($3 - 4 \text{ meV}$ [6]). The resulting gap-ratio $2\Delta/k_B T_c = 1.2$ seems to confirm the trend of an optical superconducting gap in MgB₂ substantially below the estimate of the weak-coupling BCS theory [2].

There is an increasing consensus for a double gap scenario [20, 21]; the larger gap with $2\Delta = k_B T_c = 4$ associated with the two-dimensional band and the smaller one with $2\Delta = k_B T_c = 1.3$ associated with the three-dimensional band [22]. All optical data consistently show a single gap feature [3, 4, 5, 6] and seem to rather yield the lower limit of the gap distribution. While theoretical calculations of the optical conductivity within a multi-gap scenario would be imperative, we note another intriguing aspect of our data: the optical conductivity rises in a s-wave like manner but much more steeply than a Mattis-Bardeen (MB) calculation for photon energies larger than the gap [2, 23]. A similar situation was encountered already in the superconducting fullerenes [24]. It was shown that the Eliashberg formalism can explain this behaviour. It goes beyond the MB calculation by taking into account a realistic phonon spectrum (i.e., also phonon assisted absorptions, like in the Holstein process) and arbitrary impurity scattering [15, 24].

Another key aspect of this study is the possibility to exploit bulk sensitive and contact-less optical data in order to extract the upper critical field H_{c2} along the c-axis. The fields for which the normal state is recovered (i.e., the conductivity in Fig. 2 yield a ratio close to one) represent the optical counterpart of H_{c2} along the c-axis. These characteristic fields are shown in Fig. 3 [25]. While the temperature-grid considered here does not allow any conclusion about possible anomalous curvature of $H_{c2}(T)$ (particularly close to T_c), it is safe to say that our values of H_{c2} are compatible with the temperature dependence derived by Helfand and Werthamer (HW) (Fig. 3) [13]. This also agrees with the trend seen in other experiments [26, 27, 28]. The roughly linear temperature dependence of H_{c2} above 20 K, besides being in broad agreement with the BCS theory [2], allows the determination of $H_{c2}(0)$ within the HW approach: $H_{c2}(0) = 0.7(dH_{c2}/dT)T_c = 5.2 \text{ T}$ [13]. This value is in accord with the $T \rightarrow 0$ limit of the optical estimation of H_{c2} . Our values of H_{c2} along the c-axis are somehow larger than those estimated from the thermal conductivity [26], torque magnetometry [27], magnetization and specific heat [28] on single crystals. As far as the compar-

ison with magneto-transport data is concerned, our H_{c2} values agree perfectly with the most recent data of Welsh et al. [28] but are substantially lower than those of Sologubenko et al. [26]. In order to explain the discrepancy between H_{c2} from the thermal conductivity and from the resistivity, Sologubenko et al. argued that surface effects are important in relation to superconductivity.

From $H_{c2}(0) = 5.2$ T along the c -axis, we can calculate the coherence length in the basal plane [13]: $\xi(0) = (0.7 \phi_0 = 2 H_{c2}(0))^{1/2} = 7$ nm, a value in broad agreement with estimations from other experiments [12, 26, 28]. For comparison, the BCS coherence length, calculated with the expression $\xi_0 = \hbar v_F = \xi(0) = 52$ nm using the optical gap $\Delta(0) = 15$ cm⁻¹, is three times larger than the value $\xi_0 = \hbar v_F = 1.76 k_B T_c = 17$ nm for $T_c = 38$ K and the Fermi velocity $v_F = 4.8 \times 10^7$ cm/sec [2, 22]. Obviously, these values of ξ_0 suffer from the fact that the gap ratio is sizeably smaller than the weak-coupling limit prediction (i.e., $2\Delta = 3.52 k_B T_c$). In accordance with previous optical investigation [4, 5, 16], our normal state properties suggests a relaxation time $\tau = 1.8 \times 10^{-14}$ sec [15], which leads to the mean free path $l = v_F \tau = 8.5$ nm. Our value of l is smaller than or at most comparable to the coherence length. This, together with the fact that the optical scattering rate $1/\tau = 2$, puts MgB₂ among the so-called dirty limit superconductors [2]. All optical experiments so far [3, 4, 5, 6, 16, 18] unanimously support the dirty limit scenario. However, this is a controversial and puzzling issue, since magnetic and thermodynamic probes are more in favor of the clean limit [26, 28].

In summary, we have performed magneto-optical measurements on MgB₂ single crystals. Besides identifying the signature of the superconducting gap with $2\Delta = k_B T_c = 1.2$, we have also extracted H_{c2} along the c -axis. It remains to be seen how one can reconcile an overall BCS-like H_{c2} with less conventional manifestations of the superconducting state, like the small gap value. Moreover, the controversy about the clean versus dirty limit scenario awaits resolution.

We wish to thank A. Sologubenko, R. Monnier, I. Landau, S. Broderick and H. Rott for fruitful discussions. This work has been financially supported by the Swiss National Foundation for the Scientific Research.

- [8] P. Sensor et al., Phys. Rev. B 65, 012505 (2001) and G. Karapetrov et al., Phys. Rev. Lett. 86, 4374 (2001).
- [9] T. Takahashi et al., Phys. Rev. Lett. 86, 4915 (2001).
- [10] Ch. Walti et al., Phys. Rev. B 64, 172515 (2001).
- [11] F. Bouquet et al., Phys. Rev. Lett. 87, 047001 (2001).
- [12] For a review see C. Buzea et al., cond-mat/0108265 and Refs. therein.
- [13] E. Helfand and N. R. Werthamer, Phys. Rev. 147, 288 (1966) and N. R. Werthamer et al., Phys. Rev. 147, 295 (1966).
- [14] J. Karpinski et al., in preparation.
- [15] A comprehensive review of the full data set will be presented elsewhere (in preparation).
- [16] A. B. Kuzmenko et al., Solid State Commun. 121, 479 (2002).
- [17] O. V. Dolgov et al., preprint (2001).
- [18] J. J. Tu et al., Phys. Rev. Lett. 87, 277001 (2001).
- [19] F. Wooten, Optical Properties of Solids, (Academic Press, New York, 1972).
- [20] F. Giubileo et al., Phys. Rev. Lett. 87, 177008 (2001) and cond-mat/0105146.
- [21] P. Szabo et al., Phys. Rev. Lett. 87, 137005 (2001).
- [22] J. Kortus et al., Phys. Rev. Lett. 86, 4656 (2001).
- [23] D. C. Mattis and J. Bardeen, Phys. Rev. 111, 412 (1958).
- [24] L. Degiorgi et al., Phys. Rev. B 49, 7012 (1994).
- [25] We note that the point at 15 K corresponds to the upper value of H_{c2} evaluated from the optical spectra. For a few measurements the normal state at 15 K was already reached at 4 T. This is shown by the error bar in Fig. 3. For the other temperatures the estimation of the H_{c2} fields was unique.
- [26] A. Sologubenko et al., cond-mat/0112191.
- [27] M. Angst et al., Phys. Rev. Lett. 88, 167004 (2002).
- [28] U. Welsh et al., cond-mat/0203337.

[1] J. Nagamatsu et al., Nature 410, 63 (2001).

[2] M. Tinkham, Introduction to superconductivity, 2nd ed. (McGraw-Hill, New York, 1996).

[3] A. Pimenov et al., cond-mat/0109449 (Phys. Rev. B, in press).

[4] J. H. Jung et al., Phys. Rev. B 65, 052413 (2002).

[5] R. A. Kandle et al., Phys. Rev. Lett. 88, 027003 (2002).

[6] B. Gorshunov et al., Eur. Phys. J. B 21, 159 (2001).

[7] J. W. Quilty et al., Phys. Rev. Lett. 88, 087001 (2002).

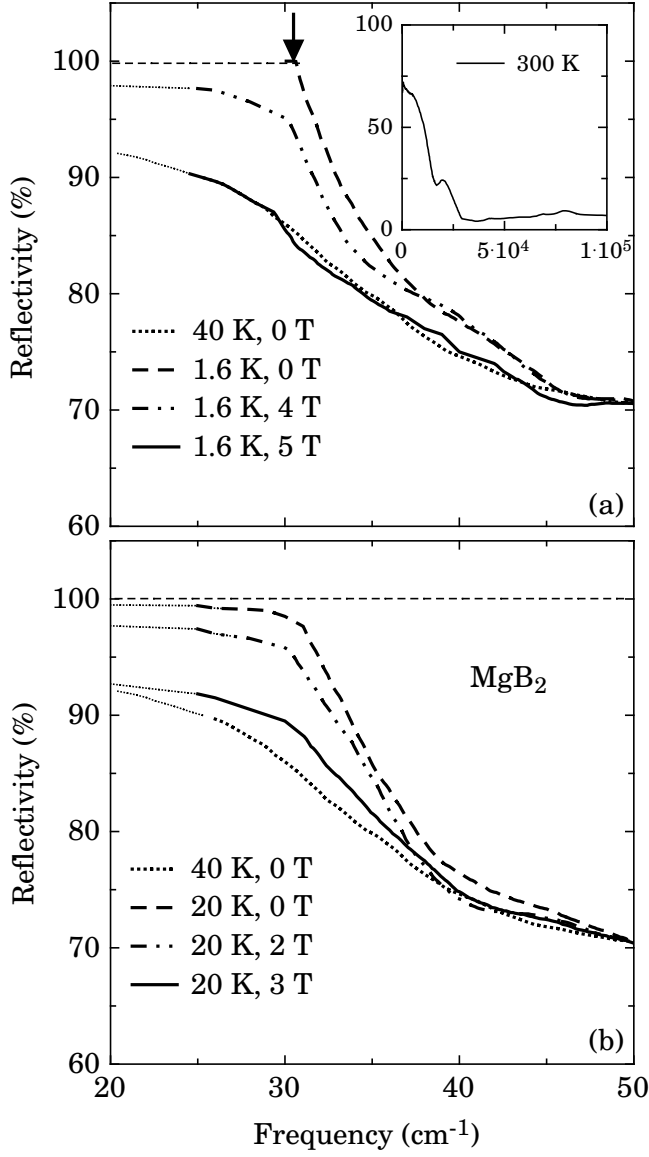


FIG. 1: Magnetic field dependence ($H \parallel c$) of the far infrared optical reflectivity $R(\%)$, measured in the basal plane, of a mosaic of MgB_2 single crystals at (a) 1.6 K and (b) 20 K. The reflectivity at 40 K in zero field is shown in both figures, as reference for the normal state behaviour. The arrow marks the energy where total reflection is reached at 1.6 K, as signature for the superconducting gap. The thin dotted line highlights the extrapolation towards zero energy for the Kramers-Kronig transformation. The inset in part (a) gives the overall behaviour of $R(\%)$ at 300 K up to 10^5 cm^{-1} .

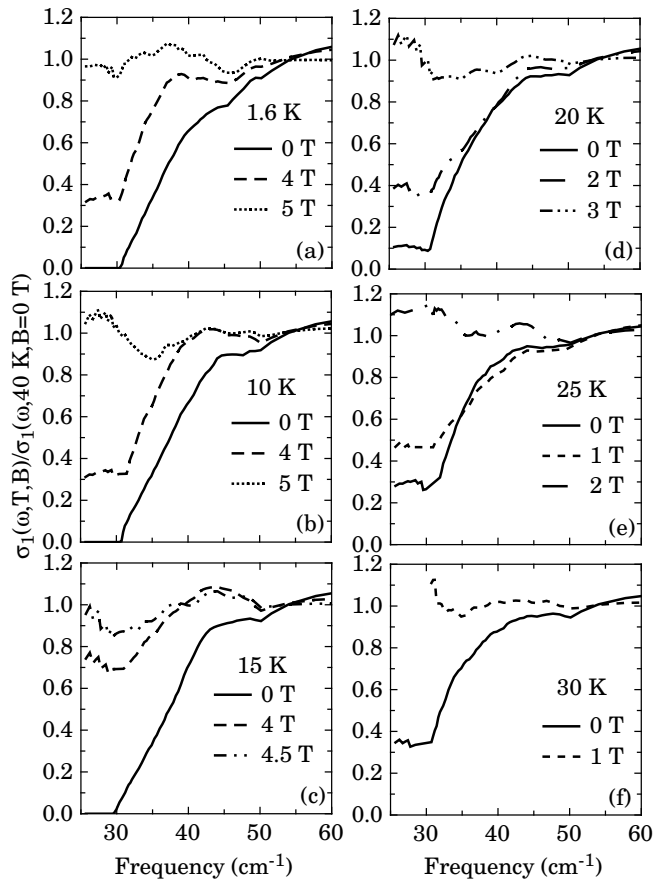


FIG. 2: Magnetic field dependence (H k c) of the conductivity ratio $\sigma_1 = \sigma_{1n}$ at selected temperatures in the FIR spectral range. The normal state σ_{1n} corresponds to the measurement at 40 K in zero field.

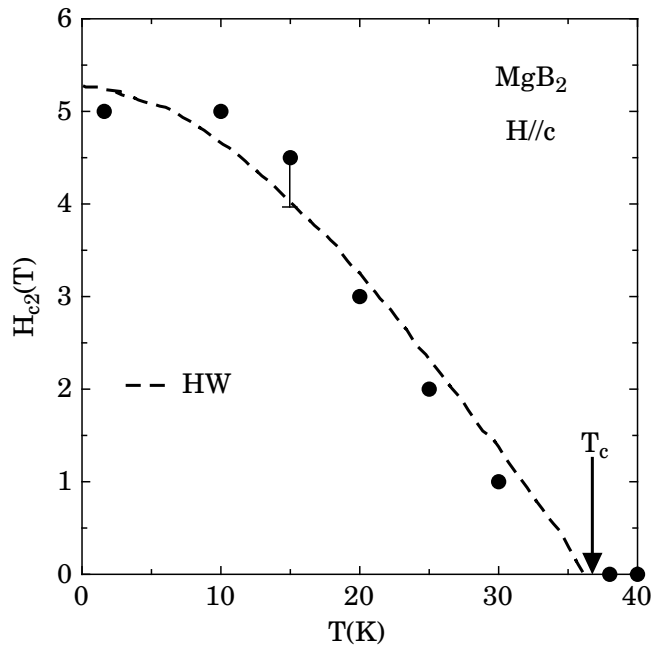


FIG . 3: Temperature dependence of H_{c2} along the c -axis, evaluated from the optical experiment. The thick dashed line is compatible with calculations due to Helfand and Werthamer (HW) [13].