

# Crystal structure of mixed fluorites $\text{Ca}_{1-x}\text{Sr}_x\text{F}_2$ and $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2$ and luminescence of $\text{Eu}^{2+}$ in these crystals.

A. E. Nikiforov,

A. Yu. Zaharov, V. A. Chernyshev (Vladimir.Chernyshev@usu.ru),

M. Yu. Ougrumov, S. V. Kotomarov

Ural State University, Ekaterinburg, Russia

**Abstract.** Within the framework of the virtual crystal method implemented in the shell model and pair potential approximation the crystal structure of mixed fluorites  $\text{Ca}_{1-x}\text{Sr}_x\text{F}_2$  and  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2$  has been calculated. The structure of impurity center  $\text{Eu}^{2+}$  and the distance  $\text{Eu}^{2+}-\text{F}$  in these crystals have been also calculated. The low level position of excited  $4f^65d$  configuration of the  $\text{Eu}^{2+}$  ion has been expressed using phenomenological dependence on distance  $\text{Eu}^{2+}-\text{F}$ . The dependences of Stokes shift and Huang-Rhys factor on  $x$  have been received for yellow luminescence in  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2:\text{Eu}^{2+}$ . The value  $x$ , for which the  $e_g$ -level of  $\text{Eu}^{2+}$  ion will be in conduction band in  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2:\text{Eu}^{2+}$  has been calculated.

## 1 Introduction

Fluorites  $\text{CaF}_2$ ,  $\text{SrF}_2$ ,  $\text{BaF}_2$  and mixed crystals on their base attract attention of researchers more than four decades [1, 2, 3, 4, 5]. The crystals, doped by rare earth ions, are good lumino-phors and are a basis for solid state lasers. The properties of luminescence and absorption depend on electronic structure of matrix crystal. The blue luminescence with zero phonon line (ZPL) is observed in  $\text{Ca}_{1-x}\text{Sr}_x\text{F}_2:\text{Eu}^{2+}$ . The yellow luminescence without ZPL is observed in  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2:\text{Eu}^{2+}$  at  $x > 0.2$ .

## 2 Calculation of the crystal structure

$\text{Ca}_{1-x}\text{Sr}_x\text{F}_2$  and  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2$ .

The method of virtual crystal have been implemented within the framework of the pair potential approximation and shell model. The method used has been described in previous work [6]. We have calculated the crystal structure of mixed fluorites  $\text{Ca}_{1-x}\text{Sr}_x\text{F}_2$  and  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2$  and of impurity center  $\text{Eu}^{2+}$  in this crystals. Dependence of a lattice constant of  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2$  from  $x$  is given on fig.1.

The calculated dependence is in agreement with W egard rule, though at medial concentrations is appreciable some difference from results of calculation. Similar dependence has been calculated for  $\text{Ca}_{1-x}\text{Sr}_x\text{F}_2$ .

## 3 Impurity ion $\text{Eu}^{2+}$ in crystals $\text{Ca}_{1-x}\text{Sr}_x\text{F}_2$ and $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2$

The luminescence and adsorption spectra of  $\text{Eu}^{2+}$  in  $\text{Ca}_{1-x}\text{Sr}_x\text{F}_2$ ,  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2$  deals with interconfigurational transitions between low excited levels of  $4f^65d$  configuration and by  $^8S(4f^7)$  ground state [5]. The ion  $\text{Eu}^{2+}$  is in center of cube formed by eight fluorines F. The splitting of  $^8S(4f^7)$  ground state is small in cubic crystal field and does not exceed  $0.2\text{cm}^{-1}$  [7]. Level  $5d$  is enough feebly bound by with  $4f^6$  orbitals in excited configuration  $4f^65d$ . The level splits to  $e_g$  and  $t_{2g}$  levels  $12-16 \cdot 10^3\text{cm}^{-1}$  [5]. The split considerably exceeds LS interaction in  $t_{2g}$  state and multiplet split of  $4f^6$  levels [8]. Spectrum of the impurity ion is substantially defined by distance impurity ion{ligand}. We have calculated the distance  $\text{Eu}^{2+}-\text{F}$  in the crystals and then have calculated a phenomenological dependence of standing  $e_g$  and  $t_{2g}$  levels from the distance. Standing of  $e_g$  level in  $\text{Ca}_{1-x}\text{Sr}_x\text{F}_2 : \text{Eu}^{2+}$ , is expressed by dependence:

$$(r) = C + \frac{A}{r^n} - \frac{B}{r^k} \quad (1)$$

where  $n = 12$ ,  $k = 5$ . The first term determines standing of  $5d$  level in free ion  $\text{Eu}^{2+}$ , the second term determines shift of the level at placing  $\text{Eu}^{2+}$  in a crystal and third term deals with influence of crystal field on  $t_{2g}-e_g$  splitting. Parameters  $A, B, C$  have been received by fitting the dependence to standing

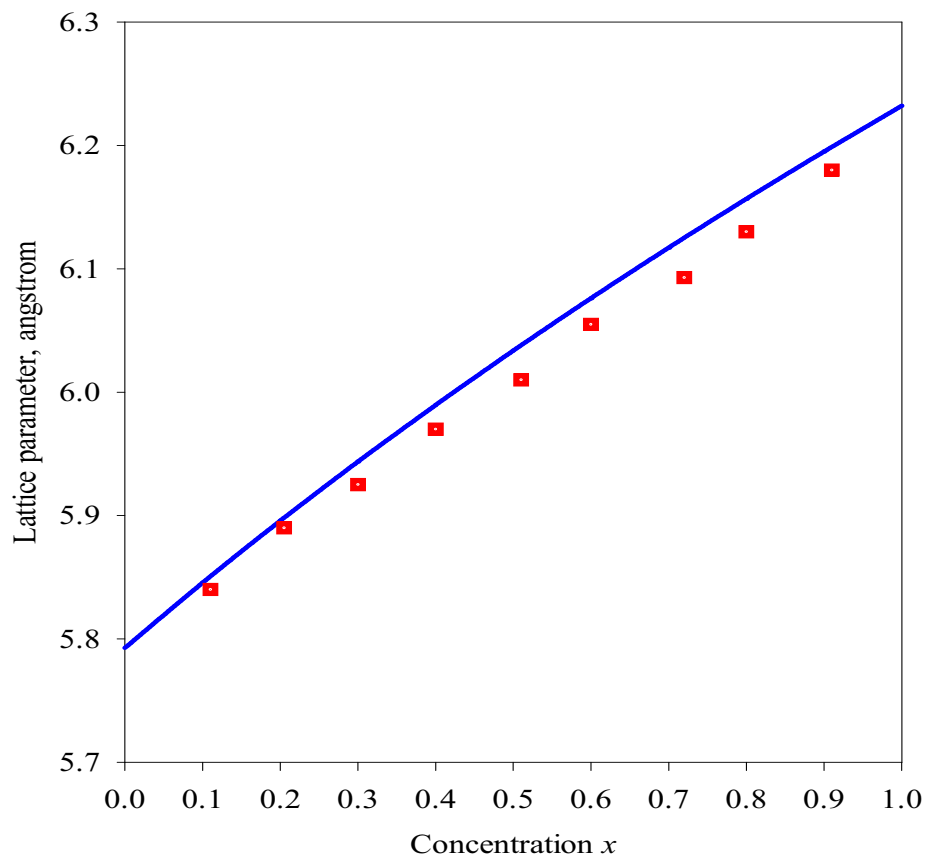


Figure 1: The lattice constant of  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2$  from  $x$ . Square symbol refer to experiment [1].

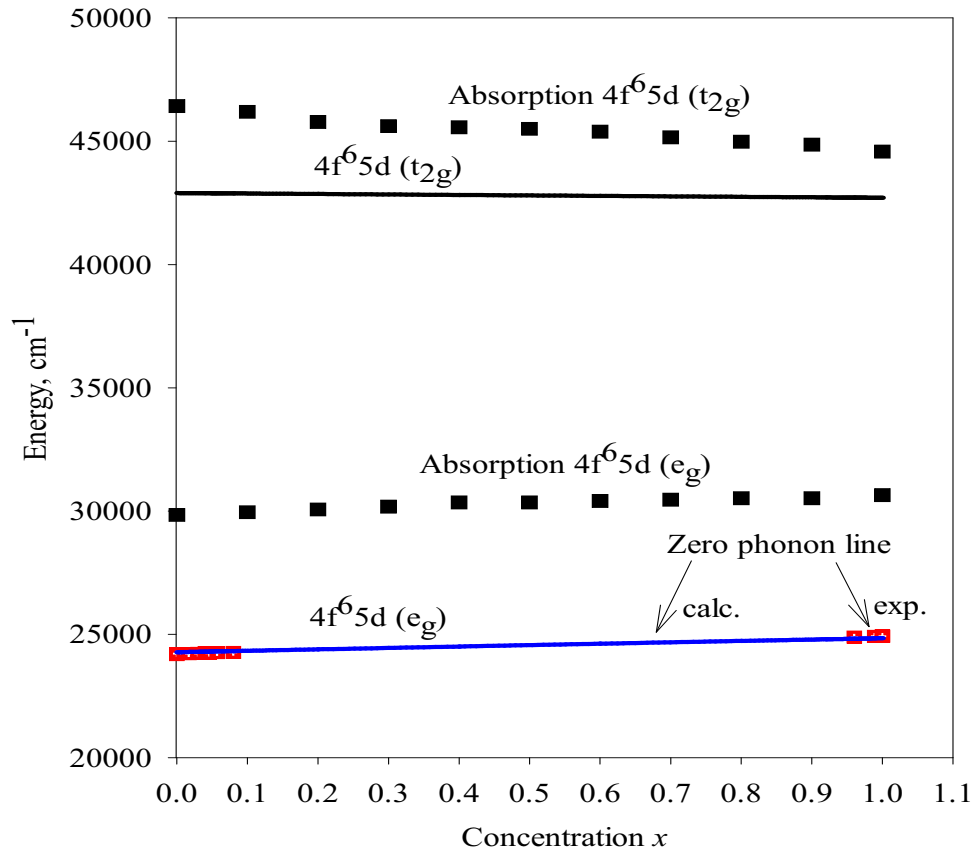


Figure 2:  $t_{2g}$  and  $e_g$  levels of  $\text{Eu}^{2+}$ . Square symbol refer to experiment [2].

ZPL in  $\text{CaF}_2$  and  $\text{SrF}_2$  crystals [2] and  $t_{2g} - e_g$  splitting in  $\text{MeF}_2$  ( $\text{Me} = \text{Ca; Sr; Ba}$ ) [3, 4]. The parameters are:  $A = 439;7 \cdot 10^6 \text{ cm}^{-1} \text{ \AA}^{12}$ ,  $B = 280 \cdot 10^5 \text{ cm}^{-1} \text{ \AA}^5$ ,  $C = 36940 \text{ cm}^{-1}$ . The dependence of ZPL position from  $x$  we can receive using calculated distance  $\text{Eu}^{2+} - \text{F}$  in  $\text{Ca}_{1-x}\text{Sr}_x\text{F}_2 : \text{Eu}^{2+}$  at various  $x$ . It is possible to calculate the  $t_{2g}$ -level position by means of [7] taking into account that third term in [7] is equal to  $6Dq (g_2)$ . The difference of the calculated  $t_{2g}$ -level position with short-wave adsorption peak can be explained by Stokes shift in adsorption.

The blue and yellow luminescence is observed in  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2 : \text{Eu}^{2+}$  for  $x \in [0.2; 0.5]$  in intervals 430–450 and 500–580 nm. accordingly. The yellow luminescence at  $x > 0.5$  is only observed [3]. Yellow luminescence due to interconformational transitions between levels of impurity exciton (which is formed by transition of electron to twelve nearby cations) and the ground state  $^8\text{S} (4f^7)$  [3, 10] ( $g_3$ ). Position of  $e_g$ -level can be calculated in  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2 : \text{Eu}^{2+}$  using the expression (1). The top of valence band is formed by 2p-states of fluorine in  $\text{SrF}_2$  and  $\text{BaF}_2$ . The bottom of conduction band is formed by s-states of cation. Forbidden zone varies practically linearly in row  $\text{CaF}_2, \text{SrF}_2, \text{BaF}_2$  [9]. The distance from  $e_g$  level to bottom of conduction band in  $\text{SrF}_2 : \text{Eu}^{2+}$  was taken from McCure work [10]. Assuming the position of 2p-states of fluorine does not change at replacing cations  $\text{Sr}^{2+}$  by  $\text{Ba}^{2+}$ , it is possible to calculate the changing of conduction zone bottom as a function from  $x$ . According to our calculation,  $e_g$ -level will be in a conduction band for  $x = 0.2$  in  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2 : \text{Eu}^{2+}$ . The yellow luminescence will begin at this  $x$  in  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2 : \text{Eu}^{2+}$  [3]. We have calculated conformation curves connected with  $A_{1g}$ -coordinate knowing how the energy of the crystal  $E$  depends on compression or expansion of a fluorine cube which surrounds  $\text{Eu}^{2+}$ . The deduced dependences  $E(Q)$  (where  $Q$  is the symmetrical coordinate) for  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2 : \text{Eu}^{2+}$  are close to parabolic form  $kQ^2 = 2$ . Similar calculations was carried out for exciton state. The coefficient  $k$  dependences of the conformational curves on  $x$  are received:  $k_{ES} = 33.95 - 5.26x$ ,  $k_{GS} = 21.18 - 4.61x$ , where  $x \in [0; 1]$ , (in  $\text{eV \AA}^{-2}$ ). The coefficients  $k_{ES}$  and  $k_{GS}$  are decreasing at increasing the barium concentration. It compounded with the fact that the elastic modules  $\text{BaF}_2$  are less than  $\text{SrF}_2$ . The fluorine cube is exposed to compression at formation of the exciton, the compression depends linearly on the concentration  $x$  in  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2 : \text{Eu}^{2+}$ :  $4R = 0.143 + 0.036x$  (in  $\text{\AA}$ ). We can receive the Stokes shift for yellow luminescence as we know  $k_{GS}$  and change of distance  $\text{Eu}^{2+} - \text{F}$  at transition from exciton to the ground state:

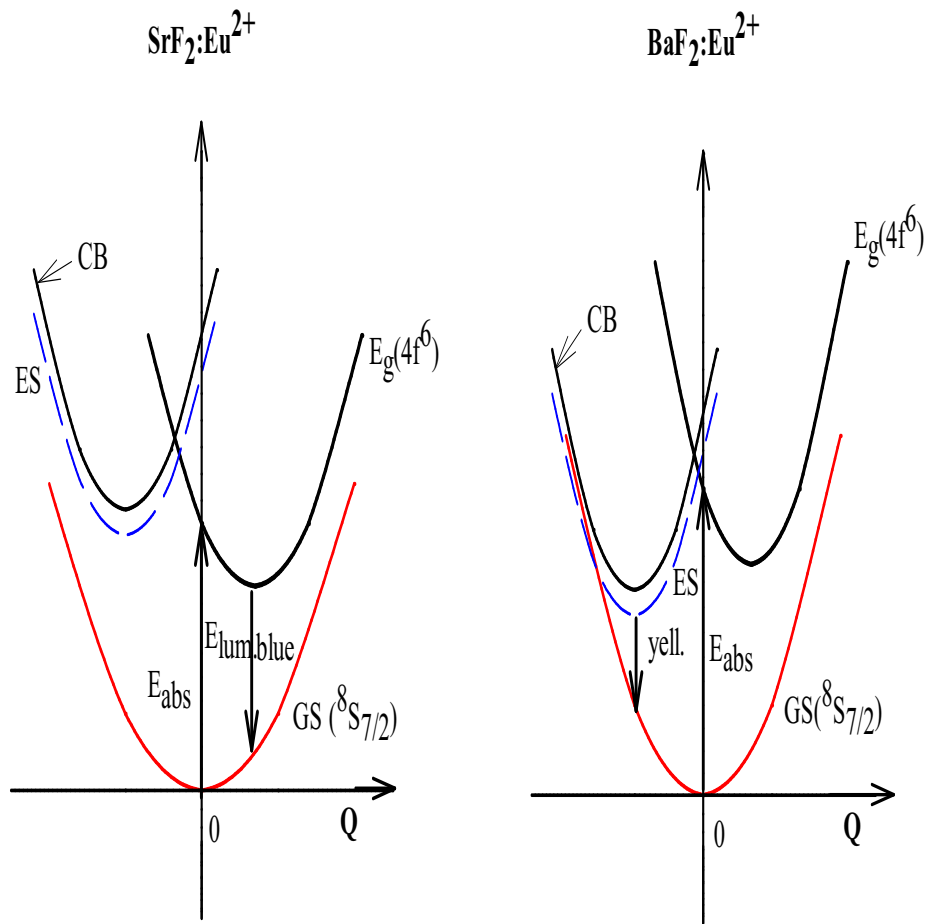


Figure 3: Configuration coordinate diagrams for describing of the blue and yellow luminescence in  $\text{CaF}_2:\text{Eu}^{2+}$  and  $\text{SrF}_2:\text{Eu}^{2+}$  [10]

$E_s = 1090x + 5011$  (in  $\text{cm}^{-1}$ ). The yellow luminescence have been observed in  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2:\text{Eu}^{2+}$  at  $2 \leq x \leq 1$ , and with increasing  $x$  its peak is shifting to the long-wave part of the spectrum [3]. According to our calculation the Stokes shift is increased on  $800\text{cm}^{-1}$ . We can estimate  $A_{1g}$  frequency of a cube from eight ions F :

$$A_{1g} = \frac{s}{\frac{k_{GS}}{m_F}} \quad (2)$$

where  $m_F$  is a mass of the fluorine. According to our calculations  $s = 547.63x$ , ( $n$  in  $\text{cm}^{-1}$ ). We can calculate Huang-Rhys factor for yellow luminescence as we know  $E_s$  and  $n$ . The factor is increasing from 9 to 12 at increasing  $x$  from 0 to 1 in  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2:\text{Eu}^{2+}$ .

## 4 Conclusion

The method of virtual crystal implemented in shell model and framework of pair potential approximation allows us to calculate the crystal structure and lattice constant for mixed fluorites  $\text{Ca}_{1-x}\text{Sr}_x\text{F}_2$  and  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2$ . This method allows us to calculate the distance  $\text{Eu}^{2+} \cdots \text{F}$  in doped crystals  $\text{Ca}_{1-x}\text{Sr}_x\text{F}_2:\text{Eu}^{2+}$  and  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2:\text{Eu}^{2+}$ . The low level position of excited  $4f^65d$  configuration of an ion  $\text{Eu}^{2+}$  is expressed by phenomenological dependence on  $\text{Eu}^{2+} \cdots \text{F}$  distance. The dependences of Stokes shift and Huang-Rhys factor on  $x$  have been calculated for yellow luminescence in  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2:\text{Eu}^{2+}$ . According to our calculation the Stokes shift is increasing by  $1000\text{cm}^{-1}$ , the Huang-Rhys factor is increasing from 9 to 12 while  $x$  changes from 0 to 1. According to calculation the  $e_g$  level of  $\text{Eu}^{2+}$  ion will be within the conduction band for  $x \geq 0.2$  in  $\text{Sr}_{1-x}\text{Ba}_x\text{F}_2:\text{Eu}^{2+}$ .

This study was supported by grant no. REC 005 (CRDF).

## References

- [1] E.G. Chemevskaya and G.V. Anan'eva, Sov. Phys. Solid State 8, 169 (1966).
- [2] R. Nakata, H. Satoh, J. Tomimaga, K. Kawano, M. Sumita. J. Phys. C, 3, 5903 (1991).

- [3] K Kawano, K Kato, R Nakata. J. Phys. Soc. Jpn., 66, 6, 1803 (1997).
- [4] P P. Feofilov in: Spectroscopy of crystals (in Russian). 'Nauka', Moscow. (1966). P. 87.
- [5] A A. Kaplyanskii, P P. Feofilov. Opt. Spectroscopia, 13, 2, 235 (1962).
- [6] A E. Nikiforov, A Yu. Zaharov, V A. Chernyshev, M Yu. Ougumov, S. V. Kotomarov. Fiz. Tverd. Tela, 44, 8, 1446 (2002).
- [7] C. Ryter. Helv. Phys. Acta, 30, 353 (1957).
- [8] Z. M. Efessel, D. M. Attis. Magnetic semiconductors. Mir, Moscow (1972), P. 157.
- [9] G W. Rubb. Phys. Rev. B5, 2, 663 (1972).
- [10] D S. McClure. In Tenth Feofilov Symposium on Spectroscopy of Crystals Activated by Rare-Earth Transitional Metal Ions, A I. Ryskin, V F. M asterov, Editors, Proc. SPIE 2706. (1996). C. 315.