

Temperature and field dependence of MgB₂ energy gaps from tunneling spectra

Mohamed H. Badr^{1,2} and K.-W. Ng¹

¹*Department of Physics and Astronomy, University of Kentucky, Lexington, KY 40506-0055, U.S.A.*

²*Department of Physics, Faculty of Science, Menoufiya University, Menoufiya, Egypt.*

(Dated: March 22, 2022)

We have synthesized MgB₂/Pb planar junctions to study the temperature and field dependence of the superconducting energy gap of MgB₂. The major peak occurs at Δ of about 2 meV, and this corresponds to a $2\Delta/k_B T_c$ value of 1.18. While this is significantly smaller than the BCS weak coupling value, there are features in the tunneling spectra indicating the possibility of another larger gap. By fitting the dI/dV curves with a simple model, the larger gap is estimated to be about 4.5 times the smaller gap. The study of the effect of magnetic field on the junctions shows a stability only up to a field of 3.2T then junctions "collapsed" into Josephson tunneling for higher fields. Estimation of the major energy gap from Josephson tunneling is consistent with that from quasiparticle tunneling.

PACS numbers: 74.70.Ad, 74.50.+r, 74.80.Fp

I. INTRODUCTION

One interesting feature in the superconductivity of MgB₂ ($T_c = 40$ K)¹ is the possibility of coexistence of two energy gaps. This immediately leads to many intriguing questions, like whether the two gaps follow $\Delta_{BCS}(T)$ and share the same critical temperature. There have been numerous tunneling spectroscopic studies to investigate this phenomenon at low temperatures. Most of these studies are performed with scanning tunneling microscope² or point contact³. To provide the needed stability for temperature and field dependence studies, we have synthesized planar tunnel junctions⁴ on bulk MgB₂ with Pb as the counter electrode.

II. RESULTS AND DISCUSSIONS

As indicated in figure 1,⁴ the major peak (Δ_1) in most of our junctions occurs consistently around 2 meV. This is significantly smaller than the BCS value. The second gap (Δ_2) appears as a small feature at around 9 meV. For conductance curves when Pb is normal, we can fit the data with a simple model by mixing two BCS density of states (with energy gaps Δ_1 and Δ_2) at a ratio of C. A depairing term Γ is introduced to account for different depairing effects, and barrier strength Z is also included to account for the zero bias offset by Andreev reflection⁵. Thermal broadening is included at the particular temperature of the fitting. C, Γ , and Z are determined by the curve at temperature = 7.78 K above Pb $T_c \approx 7.2$ K. They have the best fitted values of 0.064, 0.95 meV, and 1.33 meV respectively. These values are then fixed for all subsequent fittings at higher temperatures. Δ_1 and Δ_2 are the only adjustable parameters for higher temperature curves.

The temperature dependence of the two energy gaps is shown in the right insert of figure 1. It is clear that both energy gaps follow a BCS-like behavior and both gaps survive up to the bulk T_c of MgB₂. From this we can

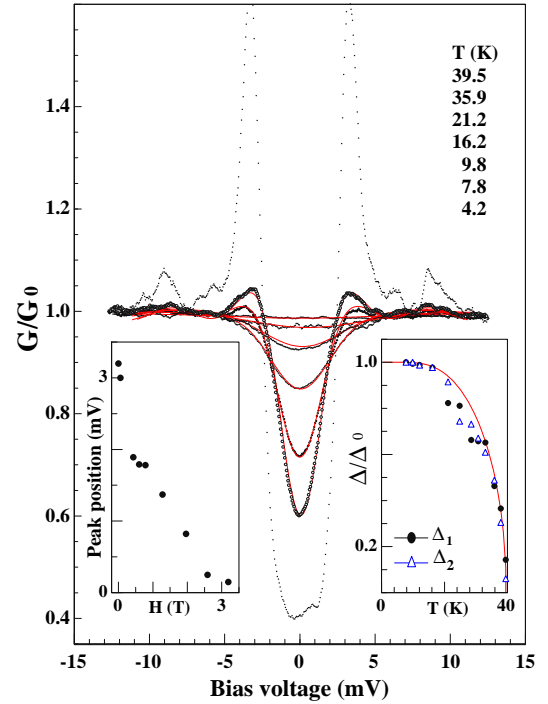


FIG. 1: Temperature dependence of the normalized conductance. The lowest curve at 4.2 K is SIS tunneling, while the others are SIN tunneling. Solid lines are the best fitted curves from which Δ_1 and Δ_2 are determined. Right insert: Temperature dependence of Δ_1 and Δ_2 . Δ_0 is the gap value at 7.78 K. Left insert: Field dependence of the major peak position.

conclude that the commonly observed small energy gap is not a result of surface degradation, but a true bulk property of MgB₂. $\Delta_1(0)$ and $\Delta_2(0)$ are 1.8 meV and 8.2 meV respectively, and the ratio Δ_2/Δ_1 is about 4.5 through out the temperature range. This ratio is close to both the theoretically predicted⁶ and experimentally

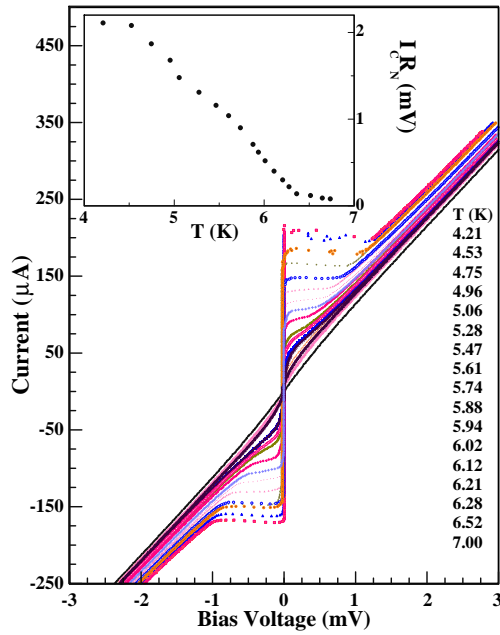


FIG. 2: Josephson tunneling at different temperatures. The listed temperatures are in the same order as the curves presented. Insert: $I_c R_N$ vs. T .

suggested⁷ values.

The left insert in figure 1 shows the field dependence of the major peak position at 4.2 K. At low fields, this corresponds to the sum of Pb gap (Δ_{Pb}) and Δ_1 . It can be seen that there is a discontinuity in the peak position at the critical field of Pb ($H_c(0) \approx 0.08T$), when Pb ceases to be superconducting. The peak position corresponds to Δ_1 at all higher fields. At a field of about 3.2 T most of our junctions "collapse" into Josephson tunneling and the change is not reversible.

The behavior of one of these Josephson junctions is shown in figure 2. The Josephson tunneling is between MgB_2 and Pb. The normal resistance (R_N) varies only very slightly with temperature. $I_c R_N$ is estimated to be about 2.1 mV (insert, Fig. 2) for the curve at 4.2 K. If we assume $I_c R_N \approx \frac{\pi}{e} \frac{\Delta_1 \Delta_{Pb}}{\Delta_1 + \Delta_{Pb}}$ and $\Delta_{Pb}(at 4.2K) \approx 1.08$ meV, we can estimate Δ_1 to be 1.75 meV. This is consistent with our result from the quasiparticle tunneling discussed above.

This work was supported by NSF Grant No. DMR9972071. The corresponding author would like to thank the Egyptian Ministry of Higher Education and Scientific Research for supporting this work as well.

Corresponding author Email: mhbadr0@uky.edu

-
- ¹ J. Nagamatsu, N Nakagawa, T. Muranaka, Y. Zenitani, J. Akimitsu, *Nature (London)* **410** (2001) 63.
² G. Rubio-Bollinger, H. Suderow, S. Vieira, *Phys. Rev. Lett.* **86** (2001) 5582.
³ P. Szabo, P. Samuely, J. Kacmarcik, T. Klein, J. Marcus, D. Fruchart, S. Miraglia, C. Marcenat, A. G. M. Jansen, *Phys. Rev. Lett.* **87** (2001) 137005.
⁴ M. H. Badr, M. Freamat, Y. Sushko, K.-W. Ng, *Phys. Rev.*

- B* **65** (2002) 184516.
⁵ G. E. Blonder, M. Tinkham, T. M. Klapwijk, *Phys. Rev. B* **25** (1982) 4515.
⁶ A. Y. Liu, I. I. Mazin, J. Kortus, *Phys. Rev. Lett.* **87** (2001) 087005.
⁷ F. Bouquet, R. A. Fisher, N. E. Phillips, D. G. Hinks, J. D. Jorgensen, *Phys. Rev. Lett.* **87** (2001) 047001.