

In 1992 Moruzzi and Marcus performed *ab initio* calculations using spin polarized density functional theory (DFT) in the framework of the local density approximation (LDA) and the augmented spherical wave (ASW) formalism.<sup>18,20,21</sup> They calculated the total energy of FeRh as a function of volume for different magnetic structures. They found that the AF-II spin structure is the ground state, whereas the FM structure is another stable

	$V_0$		$E$		$m_{\text{Fe}}$		$B$		$N(E_F)$			
	a.u./atom		m Ry		$B$		GPa		states/Ry			
	AF	FM	AF	FM	AF	FM	AF	FM	AF	FM	AF	FM
Ref. 18	90.2	91.8	1.9	2.98	3.15	214	202	37	32			
Ref. 25	91.9	92.9	2.2	3.13	3.20	227	244	13	32			
This work	91.4	93.0	2.5	3.18	3.23	197	193	13	29			

TABLE I: Comparison of ab initio results. Here,  $V_0$  is the equilibrium volume of AF and FM phases,  $E = E_{\text{FM}} - E_{\text{AF}}$  is the energy difference per atom,  $m_{\text{Fe}}$  is the Fe magnetic moment,  $B$  is the bulk modulus, and  $N(E_F)$  the density of states per formula unit at the Fermi level. The moment on the Rh sites is  $1.0 \mu_B$  in the FM phase and zero in the AF phase in all calculations.

solution with higher energy and a larger volume. For the moments they obtained  $\mu_{\text{Fe}} = 2.98 \mu_B$ ,  $\mu_{\text{Rh}} = 1.02 \mu_B$  (AF phase) and  $\mu_{\text{Fe}} = 3.15 \mu_B$  (FM phase), in agreement with experimental results.

In this work, we present further ab initio total energy calculations of stoichiometric  $\text{FeRh}$  using the ASW formalism and the generalized gradient approximation (GGA).<sup>22</sup> The corresponding code also allows to evaluate noncollinear alignment of spins (see Ref. 23 and references therein). For many cases LDA gives a reasonable description of the ground state properties of solids. However, in some cases it predicts the wrong ground state as e.g. for iron<sup>24</sup>. For Fe, the hcp structure is found to be 10 m Ry lower in energy than the bcc phase. Because  $\text{FeRh}$  has also a bcc ground state lattice structure (unlike pure Rh), it is necessary to go beyond LDA by using GGA. We have considered different possible magnetic ground state structures presented in section II. Based then on the specific energetic order of resulting energy versus volume curves, we discuss a new mechanism for the temperature driven metamagnetic transition in  $\text{FeRh}$ . In contrast to prior explanations, our model does not rely on ground state properties or low temperature data alone. Instead, we propose that thermal excitations at finite temperatures are the driving force for the transition. This is demonstrated in section III on the basis of Monte Carlo simulations of an Ising-type spin model, showing that a competition between AF Fe-Fe exchange-interactions and a nonmagnetic Rh state on the one hand and FM Fe-Rh interactions on the other is sufficient to explain the metamagnetic transition of  $\text{FeRh}$ . Inclusion of spatial degrees of freedom (section IV) by adding pair-potentials and assuming a linear variation of the exchange parameter with the lattice parameter proves that this model explanation is in accordance with the ab initio data and leads furthermore to a nearly quantitative description of experimental details.

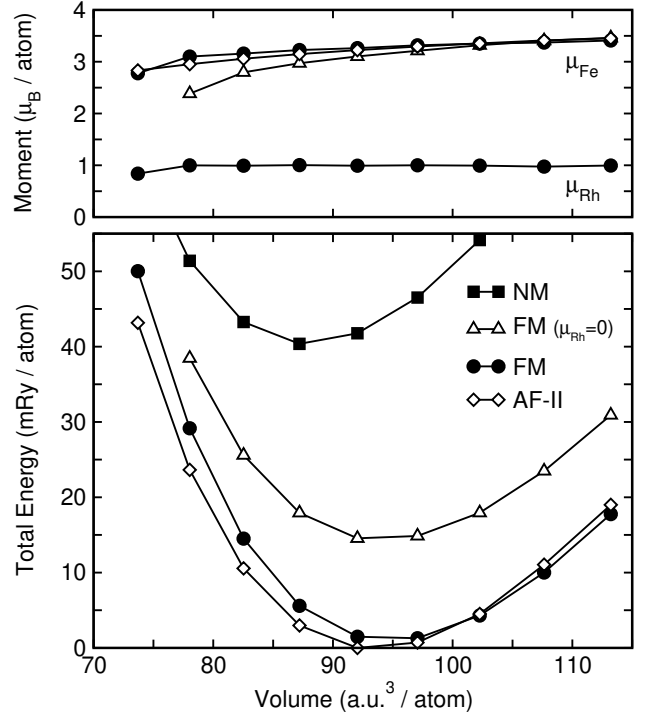


FIG. 2: Total energy and magnetic moment versus atomic volume as obtained by ab initio calculations (present work).

## II. AB INITIO TOTAL ENERGY CALCULATIONS

We have performed ab initio calculations by using the ASW method<sup>26</sup> and GGA. Relativistic effects are included in the scalar relativistic approximation. The basis wave functions of Fe and Rh atoms include  $s$  and  $f$  states which are sufficient to obtain the correct magnetic behavior of  $\text{FeRh}$ . We assume that the AF-like spin structure can best be described by a spin-spiral (Ref. 23) with wave vector  $(0.5; 0.5; 0.5)$  in units of  $2\pi/a$ . As first step, we optimized the volume of the AF-II state with equal ASA-radii for both types of atoms. For the resulting equilibrium volume, the total energy is then minimized with respect to the ratio of the ASA-spheres leading to  $r_{\text{Rh}} = r_{\text{Fe}} = 1.15$ . In order to investigate the influence of the Rh moment in the FM phase we have also used the fixed spin moment method<sup>23</sup> to restrict  $\mu_{\text{Rh}}$  to zero. Table I contains the calculated equilibrium properties for AF-II and FM phases which are in fair agreement with previous calculations. Compared to previous non-relativistic ASW LDA calculations (Moruzzi et al.<sup>18</sup>), we obtain equilibrium volumes which are about 1-2% larger, being typical for GGA. In contrast to the cases of pure iron<sup>27</sup> and FeNi Invar alloys<sup>28</sup>, the magnetic energy differences are only slightly influenced by the gradient corrections. Also, no evidence was found that a noncollinear structure could be lower in energy than the previously found collinear AF and FM spin arrangements. With re-

spect to the density of states at the Fermi level our results compare better with results of Szałek et al.<sup>25</sup> than with results of Ref. 18. Since the latter results were obtained by using LDA+SW (with a spd basis), we conclude that the density of states at the Fermi level is very sensitive to computational details. The values obtained for the bulk moduli,  $B_{AF}$  and  $B_{FM}$ , are lower compared to those of Ref. 18 (where  $B_{AF} > B_{FM}$  was obtained in contrast to  $B_{FM} > B_{AF}$  in Ref. 25).

The calculated total energy curves are shown in Fig. 2. The large energetic difference between the usual FM phase and the hypothetical FM phase with zero rhodium moment implies that a finite Rh moment plays an important role for the stability of the FM phase. It seems unlikely that a magnetic field at the Rh sites induced by the surrounding iron atoms is responsible for the appearance of a Rh moment in the FM phase, as was proposed in previous discussions. However, a strong ferromagnetic exchange interaction between the Rh and the iron atoms that overrides an antiferromagnetic exchange between next nearest neighbor iron sites, would explain how the existence of a Rh moment can help to stabilize the FM phase. We have evidence as shown in the following sections, that a competition between a low lying nonmagnetic Rh state and another one with higher energy and finite moment (which can benefit from exchange with ferromagnetic iron neighbors) is the main reason for the metamagnetic transition.

### III. A SPIN-ANALOGOUS MODEL

In order to confirm our hypothesis we have constructed a model being suitable for an examination of the metamagnetic transition at finite temperatures. The simplest way to do this is by means of Monte Carlo simulations with a localized spin model. To keep the model tractable, we neglect spin wave excitations and restrict ourselves to Ising spins. This is justified because the transition takes place between two ordered structures and both phases have collinear spin structures. For a description of the nonmagnetic Rh state in addition to the magnetic Fe and Rh states, we chose a spin-1 Ising model, where the spin variables can take the values  $S_i = -1; 0; +1$ . The spins are located on a bcc lattice with nearest and next nearest neighbor interactions. Depending on their positions, we distinguish between Fe or Rh sites, where each type occupies a simple cubic sublattice, corresponding to an ordered equiatomic alloy. The interaction parameters depend then on the type of sites involved. This situation can be described by the following Hamiltonian,

$$H = \sum_i D_i S_i^2 + \sum_{\langle nn, nnn \rangle} J_{ik} S_i S_k : \quad (1)$$

Without the assumption of different types of atoms, Hamiltonian (1) is also known as the Blume-Capel model.<sup>29,30</sup> The first term separates the nonmagnetic

$D_{Fe}$	$D_{Rh}$	$J_{FeRh}^{nn}$	$J_{FeFe}^{nnn}$	$J_{RhRh}^{nnn}$
$k_B T$	11.1	2.13	1.00	0

TABLE II: Parameters for the spin-analogous model (in mRy).

$S_i = 0$  and the magnetic  $S_i = \pm 1$  states. For Fe we choose a large positive value in order to suppress the  $S_i = 0$  state. For Rh we choose a negative value leading to a nonmagnetic ground state. The second term contains the exchange parameters  $J_{ik}$  which depend only on the type of atoms located at the sites  $i$  and  $k$ . In the case of ordered equiatomic FeRh, we have only three different parameters:  $J_{FeFe}^{nnn}$ ,  $J_{FeRh}^{nn}$  and  $J_{RhRh}^{nnn}$ . The first one is chosen to be negative in order to accomplish an AF ground state. The second is taken to be large and positive as outlined in the previous section. The third one, for the sake of simplicity, is set equal to zero. The choice for  $J_{FeFe}^{nnn}$  is fixed by the Neel temperature  $T_N$  of the AF phase assuming that no transition to a FM phase takes place.  $T_N$  can be determined from the P-T phase diagram by extrapolating the transition line between AF and PM phases (occurring at pressures larger than 6 GPa) to zero pressure.  $J_{FeRh}^{nn}$  and  $D_{Rh}$  have been chosen to yield realistic values for  $T_C$  and  $T_m$ , respectively. The values of parameters used in the simulations are given in Table II.

#### A. Details of computation

The evaluation of thermodynamic properties of (1) is done on the basis of Monte Carlo simulations according to the Metropolis scheme<sup>31</sup> using a sequential update. Interesting quantities like magnetization or magnetic moment are computed and summed up every 10 to 20 lattice sweeps, which ensures that the evaluated lattice configurations are sufficiently uncorrelated. Furthermore, we discard the first 20 000 lattice sweeps in order to allow the system to reach thermal equilibrium before computing averages. In order to speed this up, we have also used the final configuration of the last run to initialize the simulation for the next temperature. Simulations which involve a phase transition are performed twice, with increasing and decreasing temperatures, in order to assure that thermal equilibrium has been reached.

The computed AF and FM phases are metastable, i.e. they are separated by a large energy barrier, which arises from the fact that in the transition states a considerable amount of FM domains have to be created in the AF phase and vice versa. So the standard algorithm is unlikely to overcome this barrier and as a result the metamagnetic transition might not be seen at all. Instead the phases have to be overheated or undercooled before transforming, which results in a large hysteresis or irreversible behavior which makes it difficult to obtain reliable information about the transition point. Therefore,

it is necessary to modify the algorithm in order to allow for a direct jump to the other phase by circumventing the energy barrier with a global update step, where all spins will be updated at once. This algorithm ideally connects equilibrium configurations of the AF phase directly with equilibrium configurations of the FM phase while ensuring that the entropy difference between the states is correctly reproduced. This can be done by choosing a unique mapping between lattice configurations of the AF and FM phases, respectively. Or, more general, the selection probability of a specific target configuration must be the same as the selection probability of the previous start configuration in the backward direction.

Since it is a priori not clear how equilibrium configurations will look like at finite temperatures, we simply use an update scheme which connects the ground state configurations of both phases and thus works at least at low temperatures. In the vicinity of the transition temperature, this algorithm might not reproduce equilibrium states for the trial configuration, because nature and amount of excitations are presumably different in both phases. Since non-equilibrium means that most of the trial states are too high in energy, the probability that the trial state is by chance close enough to an equilibrium state to be accepted, decreases for larger system sizes.

In order to obtain a trial configuration, we divide the system into Rh and Fe sublattices. The Fe sublattice is again divided into two sublattices according to spin up and spin down positions (see Fig. 1). For each of these sublattices, it is decided randomly (with probability  $1/2$ ), whether the corresponding sublattice is flipped as a whole. For the Rh sublattice another random number decides whether the spin values  $S_i \in \{1/2, 0, +1\}$  are rotated clockwise or counter-clockwise (i.e.  $1$  becomes  $0$ ,  $0$  becomes  $+1$ ,  $+1$  becomes  $-1$ , or vice versa). So, each trial configuration is chosen with the same probability. Afterwards the energy difference  $\Delta H$  between the present and the previous configuration is computed and the new configuration is accepted with probability  $\min(\exp(-\Delta H/k_B T); 1)$  assuring detailed balance. This global update step is performed after each complete lattice sweep.

We performed for each temperature between 100 000 and 1 000 000 (around  $T_m$ ) lattice sweeps for different linear system sizes  $L = 6$  to  $16$ . However, our global update scheme does only show a metamagnetic transition within reasonable simulation times up to a system size of  $L = 10$ . Looking for a different way to determine the transition point which would also work for larger system sizes, we estimate the free energy by integrating the specific heat,

$$F(T) = E(T) - T S(0) + \int_0^T \frac{C}{T} dT : \quad (2)$$

In the computation we set the simulated results for the specific heat divided by temperature,  $C/T$ , and the internal energy  $E$  with 10th order polynomials, which can

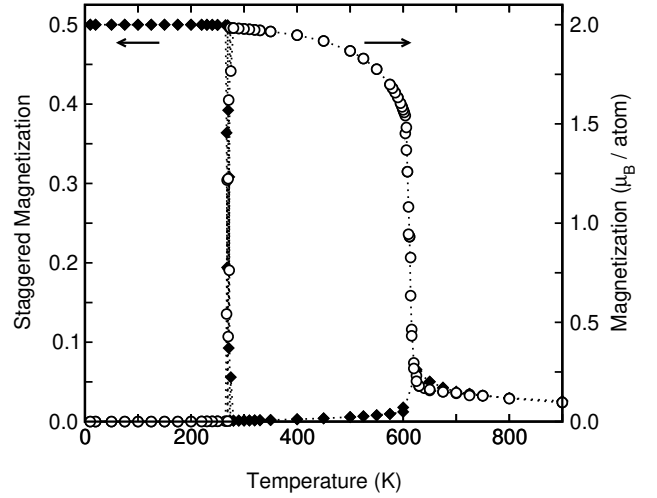


FIG. 3: AF order parameter (diamonds) and magnetization (circles) as a function of temperature. The magnetization is obtained by multiplying the spin values with a value of  $3\mu_B$  for Fe and  $1\mu_B$  for Rh before averaging. The simulated system size is  $L = 10$ .

be integrated analytically. For the system characterized by the Hamiltonian (1), we neglect the entropy contribution at zero temperature  $S(0)$ , since the ground state spin structure in both phases is nondegenerate except for systems with spin inversion symmetry. Furthermore, concerning the estimation of the free energy finite size effects are not expected to affect the results, since phase transitions are not encountered during these simulations. For the rest of the calculations a comparison of the results for smaller and larger system sizes (as can be seen in the upcoming figures) reveals that the main issues of this paper are also not affected by the restricted system sizes.

## B. Computational results

The order parameter of the AF phase is the staggered magnetization for the AF-II spin structure, i.e. the sum (of the absolute values) of the staggered magnetizations of the two simple cubic sublattices that constitute the bcc lattice structure. The staggered magnetization of a simple cubic (NaCl) lattice is defined as sum of spins multiplied with a sign which alternates depending on whether the corresponding spin occupies a Na or a Cl position. The order parameter of the FM phase is given by the magnetization of the lattice. The variation of both order parameters with temperature is shown in Fig. 3 for a system of size  $L = 10$ . At low temperatures the staggered magnetization approaches a maximum value of 0.5 due to the fact that the Rh sublattice has no moment (Fig. 4) and therefore does not contribute to the sum. At  $T_m = 268$  K the staggered magnetization abruptly drops to zero, whereas magnetic moment and magneti-

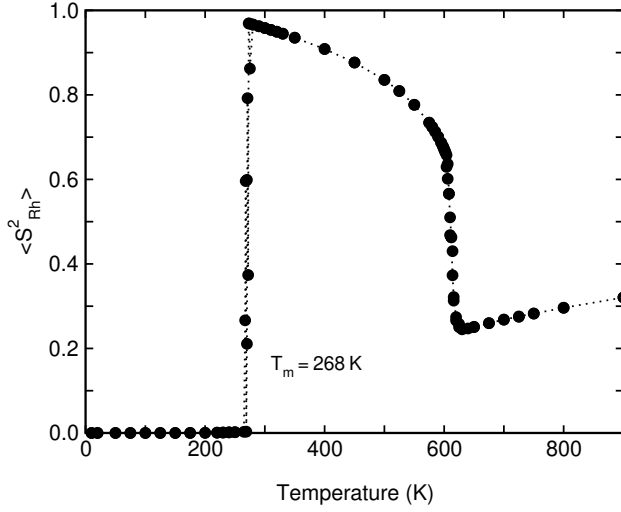


FIG. 4: Mean magnetic moment of the Rh atoms.

ization increase close to their saturation values. Above  $T_c = 610$  K ferromagnetism breaks down and the system becomes paramagnetic. At the same time, the average moment of the Rh atoms falls down to a value of 0.2  $\mu_B$ . This is also the reason, why the decrease in the magnetization appears unusually sharp. From the data, a phase transition of second as well as of first order seems to be possible. Accordingly, it is known that for negative values of  $D$  the Blume-Emery-Gruber model can show both kinds of phase transitions separated by a tricritical point in the  $T$ - $D$  plane.<sup>32,33,34</sup> Hence in order to safely determine the nature of this phase transition further calculations are necessary.

A close look at the specific heat (Fig. 5) helps to explain the occurrence of a metamagnetic transition. At first sight it seems as if the specific heats of FM and AF phases do not differ very much below 350 K. Above this temperature the specific heat of the AF phase increases more rapidly with temperature until around 570 K the overheated AF phase is not stable anymore in the simulations and transforms to the FM phase. However, the inset shows that starting around 100 K the specific heat of the FM phase is enhanced compared to the AF heat. We explain this enhancement by a Schottky-type anomaly which adds up to the excitations from spin flips. Schottky anomalies are observed in systems with two levels separated by a small energy barrier. In fact a crossover from magnetic to nonmagnetic Rh atoms is conform with this picture. In the FM phase the Rh atoms have a moment being ferromagnetically aligned to the Fe moments, because the loss of the moment would correspond to an energy loss of eight times the exchange constant. This amount is diminished by the energy gain due to the  $D_{Rh}$  term, which is smaller than  $8 J_{FeRh}^{nn}$  but larger than  $4 J_{FeRh}^{nn}$ , since the ground state is otherwise not antiferromagnetic. Increasing fluctuations of the magnetization of the Fe sublattice cause this energy difference to de-

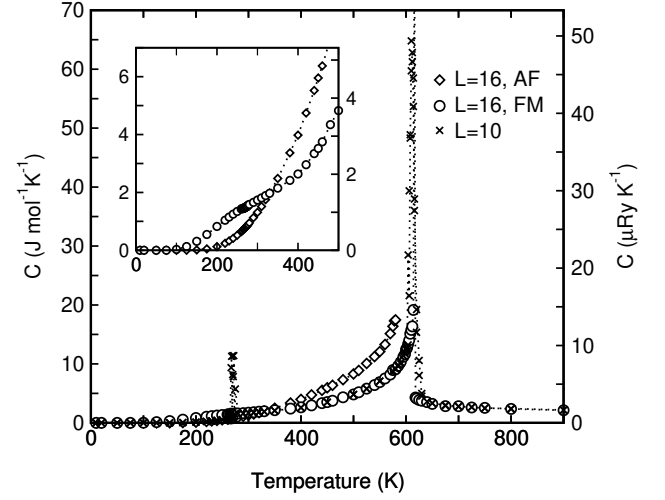


FIG. 5: Specific heat as a function of temperature for the FM and the AF phases ( $L = 16$ ) and for simulations on smaller lattices using the global MC step ( $L = 10$ ). Inset: The specific heat of the AF and FM phase between 0 and 500 K. Clearly visible is a Schottky-type enhancement below 300 K in the FM phase, which is responsible for the metamagnetic transition. The sharp peak around 270 K corresponds to the metamagnetic transition, which is observed in the small system due to the global MC step.

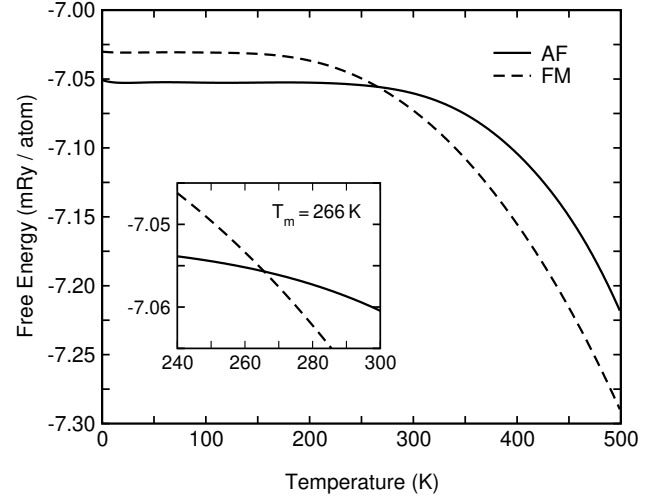


FIG. 6: Free energy of the FM and AF phases obtained by integrating  $C = T$ , with the transition point at  $T_m = 266$  K.

crease and finally lead to a breakdown of the average Rh moment at  $T_c$ . In the AF phase magnetic Rh atoms can be excited at the expense of the energy  $D_{Rh}$ . There is, however, no gain in energy due to the exchange interaction, since the contributions from the AF Fe atoms cancel at the Rh site. This corresponds to a much larger energy difference between magnetic and nonmagnetic Rh states compared to the FM phase and does not lead to an appreciable contribution to the specific heat.

This view is further supported by a comparison of the free energy of both phases shown in Fig. 6: The curves intersect at  $T = 266\text{ K}$ , which is in excellent agreement with the simulated  $T_m = 268\text{ K}$ . This accuracy could be achieved, because the data for the specific heat obtained from the simulations have only little spread and the fitted curves interpolate the data points perfectly. From the difference between the internal energies of both phases at the transition point, the entropy jump at  $T_m$  is determined to  $\Delta S(T_m) = 5.2\text{ J K}^{-1}\text{ g}^{-1}\text{ K}^{-1}$ , which is only 30 to 45% of the experimental values (but of the right order of magnitude). But, one has to bear in mind that with the choice of an Ising model we neglected the possibility of non-collinear moments. For the Rh moments this can only occur in the FM phase, and would therefore contribute to  $\Delta S(T_m)$ . A second point is that the weight of the  $S_i = 0$  state is the same as for each magnetic state  $S_i = \pm 1$ . This is a natural choice for the spin-1 Ising model; but for the real system this is somehow arbitrary, because we have no information about the electronic origin of both Rh states.

#### IV. AN EXTENDED MODEL

Since the simple spin Hamiltonian (1) can reproduce a metamagnetic transition as observed in  $\text{FeRh}$ , it remains an interesting question whether other outstanding properties of this alloy, as the large volume increase at  $T_m$ , can also be explained. Furthermore, it has still to be proven whether our spin analogy is a good approximation to the *ab initio* results in the sense that it has comparable low temperature properties. In order to check this we have to extend (1) for a description of elastic and magneto-volume properties:

$$H = \sum_i D_i S_i^2 + \sum_{\langle ij \rangle} J_{ij}(r_{ij}) S_i S_j + \sum_{\langle nn \rangle} V_{nn}(r_{nn}) + \sum_{\langle nnn \rangle} V_{nnn}(r_{nnn}) : \quad (3)$$

For  $V(r_{ij})$  we use simple pair potentials of the Lennard-Jones type:

$$V(r_{ij}) = 4 \left[ \frac{12}{r_{ij}^{12}} - \frac{6}{r_{ij}^6} \right] : \quad (4)$$

Since in general the lattice structure of a Lennard-Jones system is closely packed, two different pair potentials for nearest and next-nearest neighbors have to be used in order to stabilize the bcc structure. The potentials, however, do neither distinguish between different atom types nor between the different spin states, as has been done in previous simulations of related materials like  $\text{Fe-Ni Invar}$  or  $\text{Y (Mn}_x\text{Al}_{1-x})_2$ .<sup>35,36</sup> The use of Lennard-Jones potentials is far from being optimum for metals, but has numerical advantages that enable us to speed up the calculations substantially. It is then sufficient to choose the

$D_{\text{Fe}}$	$D_{\text{Rh}}$	$J_{\text{FeRh}}^{\text{nn}} (2.6 \text{ \AA})$	$J_{\text{FeFe}}^{\text{nnnn}} (3.0 \text{ \AA})$	$J_{\text{RhRh}}^{\text{nnnn}} (3.0 \text{ \AA})$
$k_B T$	11.1	2.10	1.04	0
		$\partial J_{\text{FeRh}}^{\text{nn}} / \partial r$	$\partial J_{\text{FeFe}}^{\text{nnnn}} / \partial r$	$\partial J_{\text{RhRh}}^{\text{nnnn}} / \partial r$
		1.97	1.58	0
		nn	nn	nnn
		25.23	2.32	25.23
				nnn
				2.67

TABLE III: Magnetic and elastic parameters for the extended spin model (energies in  $m\text{ Ry}$ , distances in  $\text{\AA}$ ).

parameters so that basic elastic properties like low temperature lattice constant, bulk modulus or thermal expansion are reproduced.

Another change compared to (1) is that the exchange parameter is now taken to be a function of interatomic distance. For simplicity, we assume a linear distance dependence:

$$J_{ik}(r_{ik}) = J_{ik} + \frac{\partial J_{ik}}{\partial r} r_{ik} : \quad (5)$$

The values for  $J_{ik}$  which we take in the extended calculations are roughly the same as in Table II. The relation between the derivatives of  $J_{\text{FeRh}}^{\text{nn}}$  and  $J_{\text{FeFe}}^{\text{nnnn}}$  with respect to the interatomic distance was determined by the relation of the pressure derivatives of the Curie and Neel temperatures, respectively, which have been obtained from the experimental phase diagram by assuming a linear dependence between  $\partial J_{ik} / \partial r$  and  $\partial T_{C/N} / \partial p$ . The absolute values have been adapted to reproduce the volume jump at  $T_m$ . An exchange interaction of this form has also been used to describe magneto-volume effects in  $\text{Fe-Ni Invar}$ .<sup>37,38,39</sup> In this case, the derivative of the exchange constant  $\partial J_{ik} / \partial r$  was a factor of 2 to 20 larger than in the present work. The values of parameters are summarized in Table III.

#### A. Details of computation

For the evaluation of Hamiltonian (3) we use a textbook isothermal-isobaric Monte Carlo method (e.g. Ref. 40) consisting of alternating spin and position updates for each atom and a global volume update step after finishing each lattice sweep. This algorithm has been used by the authors in previous calculations and is explained in detail in the corresponding references.<sup>35,36,41</sup> In order to simulate the metamagnetic transition, an additional global spin update step has to be introduced. We use the same algorithm as described in the last section for the spin system in connection with a simultaneous volume adaption. Since the latter reduces the acceptance probability considerably, the global update scheme has to be repeated several thousands of times. It is not practicable to use a new spin configuration for each trial step, because the evaluation of the energy is comparatively

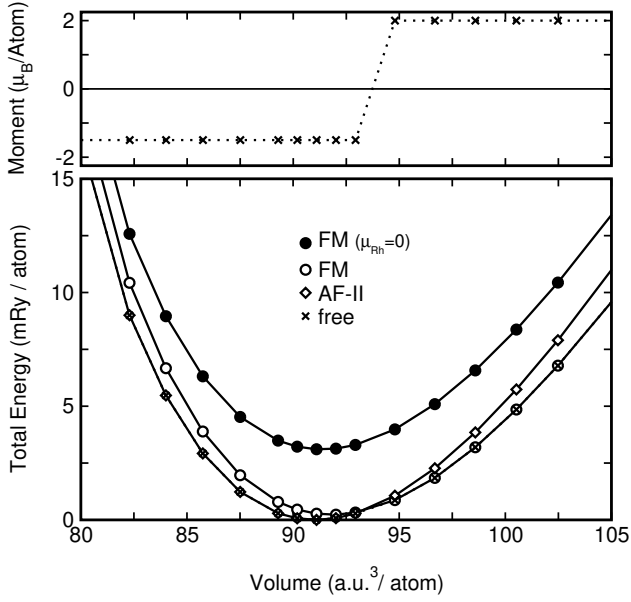


FIG. 7: Internal energy and moment as a function of the atomic volume obtained for Hamiltonian (3) at  $T = 4$  K. The simulations have been performed for fixed spin structures as well as for a freely relaxed spin system.

time consuming. On the other hand, the new energy after solely rescaling the volume can be calculated very quickly, since due to the use of Lennard-Jones potentials the energy can be written as a function of integral powers of the lattice parameter. Therefore, we choose a trial spin configuration as described before and compute the new energy. Then we attempt a previously fixed number  $N$  of Metropolis steps, each with a newly chosen volume. If one step is accepted, we continue with the original spin configuration as trial system (and so on) until  $N$  steps have been made. Since the number of trial steps  $N$  has been previously fixed, detailed balance is still valid.

We have performed simulations with system sizes of  $L = 6$  to  $12$ . A direct metamagnetic transition could only be seen for system sizes up to  $L = 8$ . The simulation time ranged from 120 000 up to 1 000 000 lattice sweeps around  $T_m$  with values from 1000 to 10 000 for  $N$ . As before we estimated Gibbs' free energy for zero pressure by integrating the specific heat according to Eq. (2).

### B. Computational results

For a comparison of our model properties with the results of *ab initio* calculations, we calculated in isochoric simulations the energy as a function of the volume at low temperatures for different fixed spin structures (Fig. 7). Here, we cooled a system of size  $L = 16$  exponentially down from 100 K down to 4 K. We find good agreement with the results of Fig. 2 in the sense that the order of magnetic phases is similar. Although the *ab initio* to-

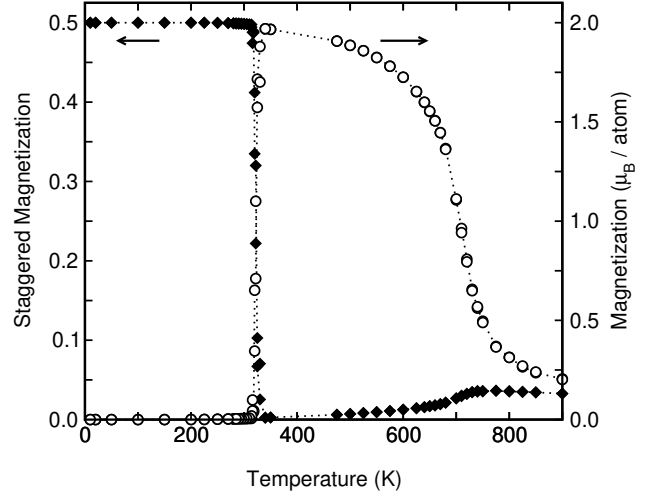


FIG. 8: AF order parameter (diamonds) and magnetization (circles) as a function of temperature as obtained for the extended model Hamiltonian (3). The system size is  $L = 8$ .

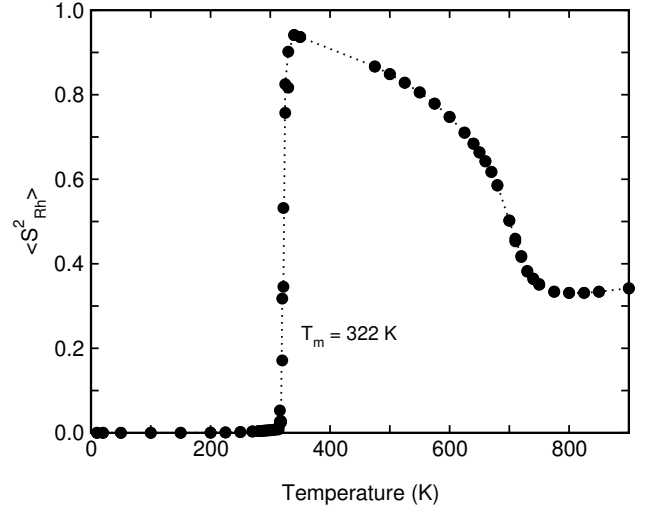


FIG. 9: Mean magnetic moment of the Rh atoms for the extended model ( $L = 8$ ).

tal energy differences are somewhat larger, this indicates that our model Hamiltonian (3) is a qualitatively correct description of the mechanisms leading to a metamagnetic transition in FeRh.

As in the simple model without volume-dependent terms, we find an abrupt increase of the magnetization in combination with a discontinuous decrease for the staggered magnetization with increasing temperature (Fig. 8). Consequently the mean moment at the Rh sites (Fig. 9) also raises sharply around the metamagnetic transition temperature of  $T_m = 322$  K. Around the Curie temperature  $T = 720$  K the magnetization decreases more smoothly than for the simple model. This may be due to the enhancement of the effective exchange

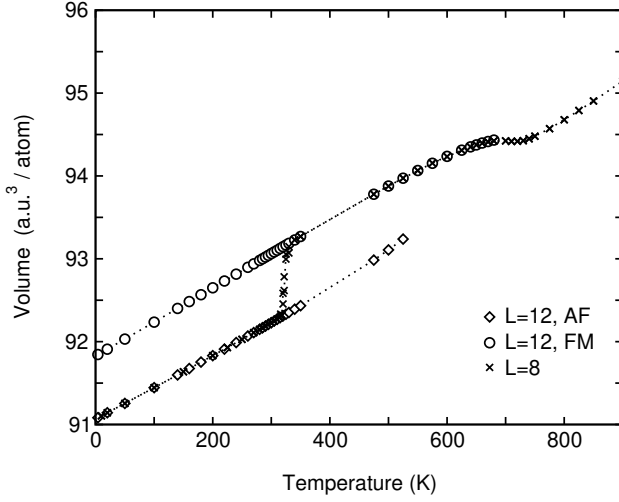


FIG. 10: Volume per atom plotted over temperature as obtained for the AF and FM phases ( $L = 12$ ) and by our simulations with the global update scheme ( $L = 8$ ).

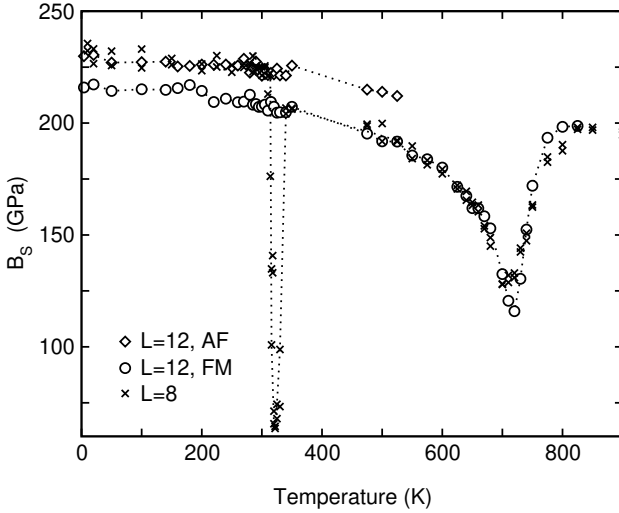


FIG. 11: Adiabatic bulk modulus as a function of temperature for the AF and FM phases ( $L = 12$ ) and with the global update scheme ( $L = 8$ ). The latter data, which show the metamagnetic transition, reveal a very large softening of the lattice around  $T_m$ .

parameter given by Eq. (5) which is caused by the lattice expansion.

As expected from the low temperature calculations, the volume of the AF phase is smaller than the volume of the FM phase throughout the stability range (Fig. 10). For the freely fluctuating system a volume jump of 0.8% occurs at  $T_m$ . Below  $T_C$  the volume expansion is reduced in the FM phase, which is in qualitative agreement with experiment<sup>4,42</sup>.

The bulk modulus  $B_s$  of the AF phase is about 6% larger than the FM bulk modulus throughout the stabil-

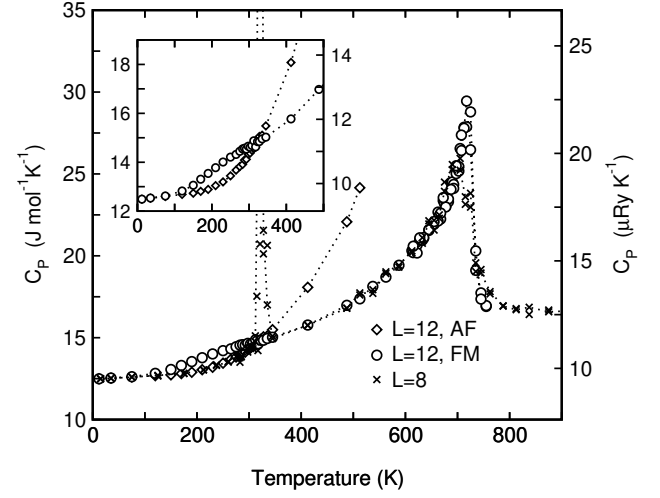


FIG. 12: Specific heat for the extended model as a function of temperature for FM and the AF phases ( $L = 12$ ) and for simulations on smaller lattices using the global MC step ( $L = 8$ ). The relationship between the specific heats of AF and FM phases below 400 K is shown in the inset.

ity range (Fig. 11). Around  $T_m$  and  $T_C$  we find a considerable weakening of the material which is caused by the magneto-volume anomalies. The values for  $B_s$  at low temperatures can be estimated more accurately by using a polynomial fit to the  $E-V$  curves in Fig. 7. We find  $B_s = 231$  GPa for the AF phase and  $B_s = 217$  GPa for the FM phase. These values are in good agreement with results of isobaric calculations shown in Fig. 11. Compared with the results of *ab initio* calculations (Table I) the absolute values are too large, whereas these calculations do not give a unanimous prediction for the sign and the magnitude of the difference  $B_s$  (with respect to the magnetic structures). Experimental measurements<sup>4</sup> of Young modulus suggest that the bulk modulus of the AF phase should in fact be lower than in the FM phase. The modulus of the AF phase, however, has only been estimated in the vicinity of  $T_m$ , where a weakening of the material (as a precursor of the transition) is present (as in our simulations).

The specific heats obtained for the extended model (Fig. 12) resemble the findings for the spin-only Hamiltonian (1), except that now additional contributions due to atomic displacements are included. This shows that the proposed explanation of the metamagnetic transition is still valid. Since the Hamiltonian (3) does not contain any kinetic terms, the low temperature value of the specific heat is only half of the Dulong-Petit limit of  $3R$ , where  $R$  is the kinetic gas constant.

### C. Estimation of Gibbs free energy

The calculation of Gibbs free energy  $G$  for the model with classical motion (3) is more complicated than in the



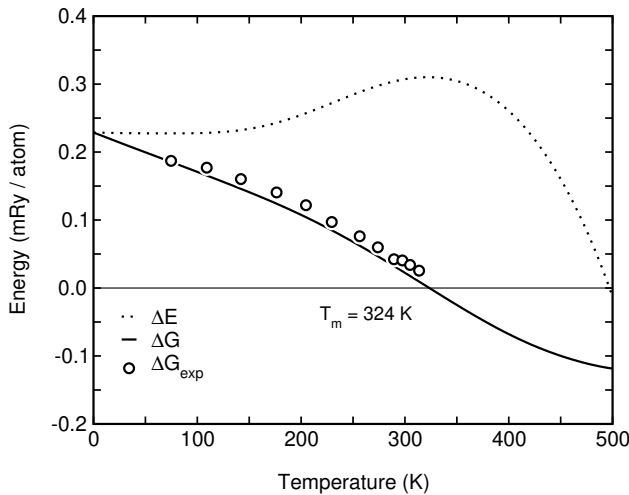


FIG. 13: Differences of internal energies and Gibbs free energies for FM and AF phases obtained by integrating  $C_p = T$ . The transition point is  $T_m = 324$  K. The experimental data have been obtained by integrating over the hysteresis loop for different temperatures.<sup>17</sup>

spin-only case (1). First of all absolute values of  $G$  cannot be given, since the specific heat at zero temperature is finite and the resulting entropy would diverge. But since the limit for  $T \rightarrow 0$  of  $C_p$  is  $1.5R$  and hence the same for all magnetic structures, differences of free energies can be computed. In contrast to the previous section, the entropy contribution at zero temperature  $S(0)$  must be considered. As before a contribution from the magnetic system can be neglected, while we have to account for the differences in the elastic properties of FM and the AF phases. Since we only need the entropy at zero temperature, we choose an ensemble of harmonic oscillators as an approximation for our spatial degrees of freedom, neglecting the anharmonicity of the potentials and the coupling of the oscillators. Differentiating the free energy obtained from the logarithm of the partition function leads then to a simple expression for the entropy difference,

$$S = \frac{3}{2} N k_B \ln(k_{AF} = k_{FM}); \quad (6)$$

where  $k_{AF}$  and  $k_{FM}$  are the force constants of the harmonic potentials which are estimated from the curvature of the ground state energy (versus lattice parameter) curve. For the entropy difference we obtain then:

$S(0) = 9.17 \text{ J kg}^{-1} \text{ K}^{-1}$ . Taking this into account, we achieve again a rather good value for  $T_m$ . From the differences of internal energies at  $T_m$  we obtain for the entropy jump at the transition  $S(T_m) = 15.9 \text{ J kg}^{-1} \text{ K}^{-1}$ , which is within the range of experimental results. Comparison of the calculated free energy with experimental values for  $G$  shows excellent agreement. The experimental values have been obtained by a graphical integration of the magnetic field expressed as a function of

the measured magnetization.<sup>17</sup> Extrapolation of experimental values to zero temperature shows that the energy difference  $E(0)$  between the AF and FM phases is much better described by our model parameters than by *ab initio* results, since the latter show that  $E$  is one order of magnitude too large. This discrepancy has already been noticed by Monuzzi and Marcus<sup>20</sup> who relate this to the omission of zero point energy corrections in their total energy calculations.

## V. CONCLUSIONS

We propose on the basis of new *ab initio* results a mechanism for the metamagnetic transition in FeRh at finite temperatures. In contrast to previous explanations, our model does not rely on a large difference between the low temperature specific heat constants of both phases. These are expected to be sensitive to external influences as both experimental measurements and band structure calculations suggest, so that it seems implausible that a constant contribution of the given magnitude might survive up to room temperature. Instead, we propose that the existence of two magnetic states of Rh atoms connected with competing FM Fe-Rh and AF Fe-Fe exchange interactions are at the origin of the metamagnetic transition. The magneto-volume effects can simply be explained on the basis of distance dependent exchange parameters. The applicability of this mechanism to the Fe-Rh problem has been verified by Monte Carlo model calculations, showing that a metamagnetic transition of the desired kind does in fact occur and, by extending the model, magneto-volume effects and other experimental properties can be sufficiently well described.

As we have pointed out, our explanation is in agreement with existing experimental data. However, a further check of our model would be a comparison with (non-existing) specific heat data from above  $T_C$  down to very low temperatures for both, the AF and FM phases. From this one could then estimate the magnetic contribution by subtracting the lattice part within the Debye approximation, the electronic part and the contribution by the anharmonicity of the potentials.<sup>43,44</sup> So far, the specific heat has only been determined in the range from 100 K to 500 K and only for the nearly stoichiometric Rh-rich alloy.<sup>45,46</sup> Systematic measurements on the Fe-rich side with a FM ground state and measurements under pressure, suppressing the metamagnetic transition would yield information whether a Schottky-type excitation plays an important role, which should show up around 200 K in the magnetic contribution to the specific heat of ferromagnetic samples.

Monte Carlo simulations with applied pressure are left for future work, since with increasing pressure and hence increasing  $T_m$  a reliable estimation of the transition temperature is rather difficult and requires an improvement of the global MC step. First tests, however, showed that the location of the phase boundaries under pressure is in

sufficient agreement with experimental data for pressures below 20 kbar and above 40 kbar, where the metamagnetic transition is completely suppressed. The tricritical point, if one exists, should be located somewhere between 20 kbar and 40 kbar for the parameters used here.

#### Acknowledgments

This work has been supported by the DFG (Deutsche Forschungsgemeinschaft) through the SFB (Sonder-

forschungsbereich) 445 and the Graduate College Structure and Dynamics of Heterogeneous Systems.

- 
- Electronic address: me@thp.uni-duisburg.de
- <sup>1</sup> M. Fallot, *Ann. Phys. (Paris)* **10**, 291 (1938).
  - <sup>2</sup> M. Fallot and R. Horcart, *Rev. Scient.* **77**, 498 (1939).
  - <sup>3</sup> J. S. Kouvel, *J. Appl. Phys.* **37**, 1257 (1966).
  - <sup>4</sup> A. I. Zakharov, A. M. Kadomtseva, R. Z. Levitin, and E. G. Ponyatovskii, *Zh. Eksp. Teor. Fiz.* **46**, 2003 (1964), [*Sov. Phys. JETP* **19**, 1348 (1964)].
  - <sup>5</sup> J. S. Kouvel and C. C. Hartelius, *J. Appl. Phys. Suppl.* **33**, 1343 (1962).
  - <sup>6</sup> F. de Bergevin and L. Muldrew, *C. R. Acad. Sci.* **252**, 1347 (1961).
  - <sup>7</sup> G. Shirane, C. W. Chen, P. A. Flinn, and R. Nathans, *J. Appl. Phys.* **34**, 1044 (1963).
  - <sup>8</sup> G. Shirane, C. W. Chen, and R. Nathans, *Phys. Rev.* **134**, A1547 (1964).
  - <sup>9</sup> N. Kunitomi, M. Kohgi, and Y. Nakai, *Phys. Lett. A* **37A**, 333 (1971).
  - <sup>10</sup> C. Kittel, *Phys. Rev.* **120**, 335 (1960).
  - <sup>11</sup> M. P. Annaorazov, S. A. Nikitin, A. L. Tyurin, K. A. Asatryan, and A. K. Dvoretov, *J. Appl. Phys.* **79**, 1689 (1996).
  - <sup>12</sup> J. M. Lommel, *J. Appl. Phys.* **40**, 3880 (1969).
  - <sup>13</sup> J. B. McInnon, D. Melville, and E. W. Lee, *J. Phys. C* **3**, S46 (1970).
  - <sup>14</sup> P. Tu, A. J. Heeger, J. S. Kouvel, and J. B. Comly, *J. Appl. Phys.* **40**, 1368 (1969).
  - <sup>15</sup> J. Ivarsson, G. R. Pickett, and J. Toth, *Phys. Lett. A* **35A**, 167 (1971).
  - <sup>16</sup> L. I. Vinokurova, A. V. Vlasov, V. Y. Ivanov, M. Pardavi-Horvath, and E. Schwab, in *The Magnetic and Electron Structures of Transition Metals and Alloys*, edited by V. G. Veselago and L. I. Vinokurova, *Proceedings of the Institute of General Physics of the Academy of Sciences of the USSR (Nova Science, Commack, 1988)*, vol. 3, pp. 1-43.
  - <sup>17</sup> B. K. Ponomarev, *Zh. Eksp. Teor. Fiz.* **63**, 199 (1972), [*Sov. Phys. JETP* **36**, 105 (1973)].
  - <sup>18</sup> V. L. Moruzzi and P. M. Marcus, *Phys. Rev. B* **46**, 2864 (1992).
  - <sup>19</sup> B. Fogarassy, T. Kemeny, L. Pal, and J. Toth, *Phys. Rev. Lett.* **29**, 288 (1972).
  - <sup>20</sup> V. L. Moruzzi and P. M. Marcus, *Solid State Commun.* **83**, 735 (1992).
  - <sup>21</sup> V. L. Moruzzi and P. M. Marcus, *Phys. Rev. B* **48**, 16106 (1993).
  - <sup>22</sup> J. P. Perdew, J. A. Chevary, S. H. Vosko, K. A. Jackson, M. R. Pederson, D. J. Singh, and C. Fiolhais, *Phys. Rev. B* **46**, 6671 (1992).
  - <sup>23</sup> M. Uhl, L. M. Sandratskii, and J. Kubler, *Phys. Rev. B* **50**, 291 (1994).
  - <sup>24</sup> L. Stixrude, R. E. Cohen, and D. J. Singh, *Phys. Rev. B* **50**, 6442 (1994).
  - <sup>25</sup> A. Szałek and J. A. Morkowski, *Physica B* **193**, 81 (1994).
  - <sup>26</sup> A. R. Williams, J. Kubler, and C. D. Gelatt, *Phys. Rev. B* **19**, 6094 (1979).
  - <sup>27</sup> H. C. Herper, E. Homann, and P. Entel, *Phys. Rev. B* **60**, 3839 (1999).
  - <sup>28</sup> B. Barbiellini, E. G. Moroni, and T. Jarlborg, *Helv. Phys. Acta* **64**, 164 (1991).
  - <sup>29</sup> M. Blume, *Phys. Rev.* **141**, 517 (1966).
  - <sup>30</sup> H. W. Capel, *Physica* **32**, 966 (1966).
  - <sup>31</sup> N. Metropolis, A. W. Rosenbluth, M. N. Rosenbluth, and E. Teller, *J. Chem. Phys.* **21**, 1087 (1953).
  - <sup>32</sup> M. Blume, V. J. Emery, and R. B. Grieths, *Phys. Rev. A* **4**, 1071 (1971).
  - <sup>33</sup> D. M. Saul, M. W. Ortiz, and D. Staufer, *Phys. Rev. B* **9**, 4964 (1974).
  - <sup>34</sup> A. K. Jain and D. P. Landau, *Phys. Rev. B* **22**, 445 (1980).
  - <sup>35</sup> M. E. G. Runer, R. Meyer, and P. Entel, *Eur. Phys. J. B* **2**, 107 (1998).
  - <sup>36</sup> M. E. G. Runer and P. Entel, *Phase Trans.* **75**, 221 (2002).
  - <sup>37</sup> B. Grossmann and D. G. Rancourt, *Phys. Rev. B* **54**, 12294 (1996).
  - <sup>38</sup> D. G. Rancourt and M. Z. Dang, *Phys. Rev. B* **54**, 12225 (1996).
  - <sup>39</sup> K. Lagarec and D. G. Rancourt, *Phys. Rev. B* **62**, 978 (2000).
  - <sup>40</sup> M. P. Allen and D. J. Tildesley, *Computer Simulation of Liquids* (Clarendon, Oxford, 1987).
  - <sup>41</sup> M. E. G. Runer and P. Entel, *Comp. Mat. Sci.* **10**, 230 (1998).
  - <sup>42</sup> P. A. Aigarabel, M. R. Ibarra, C. Marquina, S. Yuasa, H. Miyajima, and Y. Otani, *J. Appl. Phys.* **79**, 4659 (1996).
  - <sup>43</sup> W. Bendick, H. H. Ertwig, and W. Pepperhoff, *J. Phys. F: Met. Phys.* **8**, 2525 (1978).
  - <sup>44</sup> B. Rellinghaus, J. Kastner, T. Schneider, E. F. Wasermann, and P. Mohn, *Phys. Rev. B* **51**, 2983 (1995).
  - <sup>45</sup> M. J. Richardson, D. Melville, and J. A. R. Iodeau, *Phys. Lett.* **46A**, 153 (1973).
  - <sup>46</sup> M. P. Annaorazov, K. A. Asatryan, G. M. Yalikgulyev, S. A. Nikitin, A. M. Tishin, and A. L. Tyurin, *Cryogenics* **32**, 867 (1992).